

# UC Irvine

## UC Irvine Previously Published Works

### Title

High-temperature weak ferromagnetism in a low-density free-electron gas

### Permalink

<https://escholarship.org/uc/item/02g0m3m6>

### Journal

Nature, 397(6718)

### ISSN

0028-0836

### Authors

Young, DP  
Hall, D  
Torelli, ME  
[et al.](#)

### Publication Date

1999-02-01

### DOI

10.1038/17081

### Copyright Information

This work is made available under the terms of a Creative Commons Attribution License, available at <https://creativecommons.org/licenses/by/4.0/>

Peer reviewed

**Table 1 Doping dependence of the strong coupling ratio**

Doping level	Arpes*	Tunnelling	Andreev reflection	$\lambda(T)$	Raman scattering
Optimally doped					
BSCCO	9 (ref. 3)	5 (refs 4, 15)		6 (ref. 20)	6 (ref. 22)
YBCO		8 (ref. 11)	5 (ref. 12)	5 (ref. 20)	
LSCO		7.5 (refs 17, 18)	5 (ref. 17)		5 (ref. 25)
HgBa <sub>2</sub> CaCu <sub>2</sub> O <sub>6+δ</sub>					5 (ref. 26)
Overdoped					
BSCCO (60 K)		6–9 (refs 4, 15)			6 (ref. 22)
Underdoped					
BSCCO (80 K)	11–13 (ref. 27)	12 (refs 4, 15)	6.2 (ref. 16)		
BSCCO (70 K)		14 (ref. 15)			5 (ref. 22)
YBCO (60–65 K)		20 (ref. 3)	4.6 (ref. 14)	5 (ref. 21) 4 (ref. 20)	
LSCO (15 K)			4.5 (ref. 17)		

The values of the strong coupling ratio ( $2\Delta/kT_c$ ) shown here were obtained using the indicated methods of gap measurement (see text for details). The strong coupling ratio ranges from 6 to 20 for  $\Delta_p$  (ARPES, tunnelling), and from 4 to 6 for  $\Delta_c$  (Andreev reflection,  $\lambda(T)$ , Raman scattering).

\* Angle-resolved photoemission spectroscopy.

values have been obtained by surface-sensitive measurements, while  $\Delta_c$  values have been obtained from both surface (Andreev) and bulk measurements ( $\lambda(T)$  and Raman), and may therefore be more reliable. Yet the persistence of  $\Delta_p$  above  $T_c$  in the underdoped regime is in good agreement with a decrease of the spin susceptibility below a temperature  $T^* > T_c$ , which is a bulk measurement<sup>1</sup>.

A related question is that of the mechanism leading to pair formation. A non-mean-field behaviour may just indicate the presence of strong phase fluctuations, and not necessarily the presence of preformed pairs in the Mott sense<sup>23</sup>. Both local pairs and the stripe model may explain the continuous increase of  $\Delta_p$  in the underdoped regime. But if the existence of two energy scales was simply due to fluctuation effects, one would expect  $\Delta_p$  to saturate in the underdoped regime<sup>24</sup>. It is also possible that  $\Delta_p$  might be unrelated to a pairing amplitude.

In any case, I consider that the existence of two energy scales is well established in the underdoped regime, with the scales converging in the overdoped regime. I have assigned the lower scale, obtained from Andreev reflection experiments, to coherence properties of the condensate; the higher scale reflects the properties of single-particle excitations. □

**Note added in proof:** I have learned of theoretical work on the superfluid density and the excitation gap in a BCS–Bose–Einstein crossover scenario<sup>28</sup>.

Received 21 July; accepted 23 November 1998.

- Alloul, H., Ohno, T. & Mendels, P. Y. NMR evidence for a Fermi liquid behavior in YBa<sub>2</sub>Cu<sub>3</sub>O<sub>6+x</sub>. *Phys. Rev. Lett.* **63**, 1700–1703 (1989).
- Ding, H. *et al.* Spectroscopic evidence for a pseudogap in the normal state of underdoped high- $T_c$  superconductors. *Nature* **382**, 51–54 (1996).
- Racah, D. & Deutscher, G. Properties of normal metal/dielectric/high  $T_c$  junctions obtained by in-situ oxidation. *Physica C* **263**, 218–224 (1996).
- Renner, C. *et al.* Pseudo-gap precursor of the superconducting gap in under- and overdoped Bi<sub>2</sub>Sr<sub>2</sub>CaCu<sub>2</sub>O<sub>8-δ</sub>. *Phys. Rev. Lett.* **80**, 149–152 (1998).
- Griffin, A., Snoko, D. W. & Stringari, S. (eds) *Bose-Einstein Condensation* (Cambridge Univ. Press, 1995).
- Emery, V. J., Kivelson, S. A. & Zachar, O. Spin-gap proximity effect mechanism of high temperature superconductivity. *Phys. Rev. B* **56**, 6120–6147 (1997).
- Deutscher, G. Superconducting glass and related properties. *Physica C* **153–155**, 15–20 (1988).
- Pines, D. The spin fluctuation model for high temperature superconductivity: progress and prospects. In *The Gap Symmetry and Fluctuations in High Temperature Superconductors* (eds Bok, J., Deutscher, G., Pavuna, D. & Wolf, S.) (NATO ASI ser., Plenum, 1998).
- Uemura, Y. J. Bose Einstein to BCS cross-over picture for high  $T_c$  cuprates. *Physica C* **282–287**, 194–197 (1997).
- Zhao, G.-m., Hunt, M. B., Keller, H. & Müller, K. A. Evidence for polaronic supercarriers in the copper oxide superconductors La<sub>2-x</sub>Sr<sub>x</sub>CuO<sub>4</sub>. *Nature* **385**, 236–239 (1996).
- Maggio-Aprile, I. *et al.* Direct vortex imaging and tunneling spectroscopy of flux lines in YBa<sub>2</sub>Cu<sub>3</sub>O<sub>7-δ</sub>. *Phys. Rev. Lett.* **75**, 2754–2757 (1997).
- Hass, N. *et al.* Sharp gap edge and determination of the Fermi velocity in YBa<sub>2</sub>Cu<sub>3</sub>O<sub>7-δ</sub> by point contact spectroscopy. *J. Supercond.* **5**, 191–194 (1992).
- Tanaka, Y. in *Coherence in High Temperature Superconductors* (eds Deutscher, G. & Revcolveschi, A.) 393–413 (World Scientific, Singapore, 1996).

- Yagil, Y. *et al.* Experimental evidence for strong electron-phonon coupling to selected phonon modes in point contact spectroscopy. *Physica C* **250**, 59–66 (1995).
- Miyakawa, N. *et al.* Strong dependence of the superconducting gap on oxygen doping from tunneling measurements on Bi<sub>2</sub>Sr<sub>2</sub>CaCu<sub>2</sub>O<sub>8-δ</sub>. *Phys. Rev. Lett.* **80**, 157–160 (1998).
- Sinha, S. & Ng, K. W. Zero bias conductance peak enhancement in Bi<sub>2</sub>Sr<sub>2</sub>CaCu<sub>2</sub>O<sub>8</sub>/Pb tunneling junctions. *Phys. Rev. Lett.* **80**, 1296–1299 (1998).
- Achraf, N. *et al.* in *Coherence in High Temperature Superconductors* (eds Deutscher, G. & Revcolveschi, A.) 428–442 (World Scientific, Singapore, 1996).
- Ekino, T. *et al.* Superconducting energy gap of La<sub>1.85</sub>Sr<sub>0.15</sub>CuO<sub>4</sub> single crystals from breakjunction tunneling. *Physica C* **263**, 249–256 (1996).
- Kohen, A. *Transition from s-wave to d-wave Gap Symmetry in La<sub>2-x</sub>Sr<sub>x</sub>CuO<sub>4</sub>*. Thesis, Tel Aviv Univ. (1997).
- Panapogoulos, C., Cooper, J. R. & Xiang, T. Systematic behavior of the in-plane penetration depth in d-wave superconductors. *Phys. Rev. B* **57**, 13422–13425 (1998).
- Bonn, D. A. *et al.* Comparison of the influence of Ni and Zn impurities on the electromagnetic properties of YBa<sub>2</sub>Cu<sub>3</sub>O<sub>6.95</sub>. *Phys. Rev. B* **50**, 4051–4063 (1995).
- Nemetschek, R. *et al.* Pseudogap and superconducting gap in the electronic Raman spectra of underdoped cuprates. *Phys. Rev. Lett.* **78**, 4837–4840 (1997).
- Mott, N. V. High temperature superconductors above  $T_c$ . *Physica A* **168**, 221–228 (1990).
- Lee, P. A. & Wen, X. G. Unusual superconducting state of underdoped cuprates. *Phys. Rev. Lett.* **21**, 4111–4114 (1997).
- Chen, X. K. *et al.* Investigation of the superconducting gap in La<sub>2-x</sub>Sr<sub>x</sub>CuO<sub>4</sub> by Raman scattering. *Phys. Rev. Lett.* **73**, 3290–3293 (1994).
- Sacuto, A. *et al.* Nodes of the superconducting gap probed by electronic Raman scattering in HgBa<sub>2</sub>CaCu<sub>2</sub>O<sub>6+δ</sub>. *Europhys. Lett.* **39**, 207–210 (1997).
- Harris, J. M. *et al.* Anomalous superconducting gap size versus  $T_c$  behavior in underdoped Bi<sub>2</sub>Sr<sub>2</sub>Ca<sub>1-x</sub>Dy<sub>x</sub>Cu<sub>2</sub>O<sub>8+δ</sub>. *Phys. Rev. B* **54**, 15665–15668 (1996).
- Chen, Q. *et al.* *Phys. Rev. Lett.* **81**, 4708 (1998).

**Acknowledgements.** I thank J. Friedel, P. Nozieres, R. Maynard and B. K. Chakraverty for discussions on the two-energy scale issue, and V. Emery for detailed comments on the manuscript. This work was supported in part by the Israel Science Foundation, by the Heinrich Hertz Minerer Center for Superconductivity, by the US Navy, and by the Oren Family Chair for Experimental Solid State Physics.

Correspondence and requests for materials should be addressed to the author.

## High-temperature weak ferromagnetism in a low-density free-electron gas

D. P. Young\*, D. Hall\*, M. E. Torelli\*, Z. Fisk\*†, J. L. Sarrao†, J. D. Thompson†, H.-R. Ott‡, S. B. Oseroff§, R. G. Goodrich|| & R. Zysler¶

\* NHMFL, Florida State University, Tallahassee, Florida 32306, USA

† Material Science and Technology Division, Los Alamos National Laboratory, Los Alamos, New Mexico 87454, USA

‡ Laboratorium für Festkörperphysik, ETH-Hönggerberg, CH-8093 Zürich, Switzerland

§ Department of Physics, San Diego State University, San Diego, California 92182, USA


|| Department of Physics, Louisiana State University, Baton Rouge, Louisiana 70803, USA

¶ Centro Atomico Bariloche, Bariloche RN 8400, Argentina


**The magnetic properties of the ground state of a low-density free-electron gas in three dimensions have been the subject of theoretical speculation and controversy for seven decades<sup>1</sup>. Not only is this a difficult theoretical problem to solve, it is also a problem which has not hitherto been directly addressed experimentally. Here we report measurements on electron-doped calcium hexaboride (CaB<sub>6</sub>) which, we argue, show that—at a density of  $7 \times 10^{19}$  electrons cm<sup>-3</sup>—the ground state is ferromagnetically polarized with a saturation moment of 0.07  $\mu_B$  per electron. Surprisingly, the magnetic ordering temperature of this itinerant ferromagnet is 600 K, of the order of the Fermi temperature of the electron gas.**

The cubic hexaborides of the rare-earth elements have long attracted interest because of their wide variety of physical properties in spite of their simple crystallographic structures. These physical properties include very low work functions leading to the use of LaB<sub>6</sub> as a thermionic emitter<sup>2,3</sup>, dense Kondo behaviour and electric quadrupole ordering in CeB<sub>6</sub> (ref. 4), Kondo insulating properties in SmB<sub>6</sub> (ref. 5), and low-carrier-density ferromagnetism in the local moment system EuB<sub>6</sub> (refs 6, 7).

The host material for the present experiments is the divalent alkaline-earth hexaboride CaB<sub>6</sub>. The crystal structure of this material

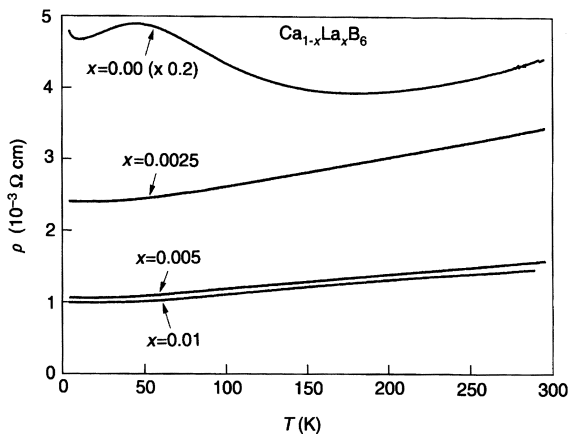

**Figure 1** Temperature dependences of the electrical resistivities of La-doped  $\text{CaB}_6$ . The resistivity for pure  $\text{CaB}_6$  has been multiplied by 0.2.

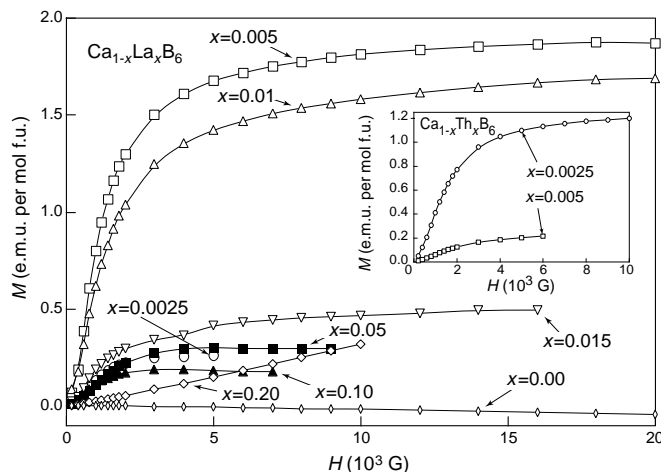

**Figure 2** Magnetization per mol of compound versus applied field for La-doped  $\text{CaB}_6$ , measured at 5 K (f.u., formula unit). The data for  $x = 0$  were taken at 10 K. Inset, magnetization versus applied field at 5 K for  $\text{Ca}_{0.9975}\text{Th}_{0.0025}\text{B}_6$  and  $\text{Ca}_{0.995}\text{Th}_{0.005}\text{B}_6$ . Magnetizations have been measured after cooling in zero field, using a Quantum Design SQUID magnetometer.


can be thought of as a simple cubic CsCl-type arrangement of  $\text{B}_6$ -octahedra and metal ions. The early electronic structure cluster calculations of Longuet-Higgins and Roberts<sup>8</sup> found that the linked  $\text{B}_6$ -network required 20 electrons for a ‘closed shell’ electronic configuration, indicating that the alkaline-earth hexaborides would be semiconductors. A study of the low-temperature properties of single crystals of  $\text{SrB}_6$ , however, found a non-zero conductivity due to approximately 0.001 electrons per  $\text{SrB}_6$ , and indications of the importance of electron-hole Coulomb effects<sup>9</sup>. More recent band structure calculations<sup>10</sup> show that hexaborides with divalent cations should be semimetals, with a small direct overlap of a primarily boron-derived valence band with a primarily alkaline-earth-derived conduction band at the X-point in the Brillouin zone.

Our experiments, including measurements of the electrical resistivity, the magnetic susceptibility and the magnetization, were performed on single crystals of  $\text{CaB}_6$  doped with trivalent La; these crystals were grown from stoichiometric amounts of the hexaboride components in molten Al. On similarly prepared single crystals of  $\text{Sr}_{1-x}\text{Ce}_x\text{B}_6$ , we have verified that Ce is incorporated stoichiometrically into the crystals by measuring the magnetic susceptibility and fitting the data to a Curie-Weiss law with an effective moment  $\mu_{\text{eff}} = 2.54 \mu_B$  per trivalent Ce ion. It is reasonable to assume that the neighbour of Ce in the rare-earth sequence, La, is also incorporated stoichiometrically in  $\text{SrB}_6$  and  $\text{CaB}_6$ . X-ray diffraction has confirmed the cubic hexaboride structure in all cases.

Figure 1 shows the electrical resistivity data obtained between 5 K and 300 K from single crystals of  $\text{Ca}_{1-x}\text{La}_x\text{B}_6$ . Already for  $x = 0.005$ , we find a change to a metallic-like temperature dependence and a drop in resistivity by a factor of  $\sim 50$  at low temperature, relative to the pure host ( $x = 0$ ). A single band interpretation of the Hall constant obtained using the van der Pauw geometry for the  $x = 0.005$  sample indicates electron-like carriers, with a density of 0.005 electrons per formula unit, as one naively expects for the trivalent La substitution. Our preliminary de Haas-van Alphen experiment on  $x = 0.005$  La-doped  $\text{CaB}_6$  along (100) reveals two orbits. Interpreting these as orthogonal extremal orbits of an ellipsoid gives an occupied volume (taking account of the ellipsoids at the equivalent X-points in the Brillouin zone) enclosing  $\sim 0.01$  electrons for unpolarized electrons. This value is within experimental error of 0.005 electrons, given the small number of oscillations observed; the observation of two rather than four extremal orbits is consistent with the small hole pocket being filled, leaving only a small filling of the conduction band.

The unusual aspect of these La-doped borides is seen in Fig. 2, where we plot magnetization versus field at 5 K for a range of values of  $x$ , measured on single crystals of  $\text{Ca}_{1-x}\text{La}_x\text{B}_6$ . A weak ferromagnetic moment is evident, its magnitude peaking near  $x = 0.005$  at  $0.07 \mu_B$  per La, with no moment found in crystals with composition  $\text{Ca}_{0.80}\text{La}_{0.20}\text{B}_6$  (Fig. 3); hysteresis loops for the  $x = 0.005$  material are shown in Fig. 3 inset. We find nearly identical magnetic effects with La-doping of  $\text{CaB}_6$ ,  $\text{SrB}_6$  and  $\text{BaB}_6$ . In all cases, the maximum moment is found at  $x = 0.005$ . That this moment is a function of the carrier concentration is supported by data for  $\text{Ca}_{0.9975}\text{Th}_{0.0025}\text{B}_6$  and  $\text{Ca}_{0.995}\text{Th}_{0.005}\text{B}_6$  (Fig. 2 inset): here the moment is maximum at  $x = 0.0025$ . Because Th is incorporated in a tetravalent configuration, it will contribute one more electron than trivalent La, and hence if the moment is a function of carrier count, compounds with  $\text{Th}_{0.0025}$  and  $\text{La}_{0.005}$  should have the same moment. In Fig. 4, we show the temperature dependence of the magnetic moment of  $\text{Ca}_{0.995}\text{La}_{0.005}\text{B}_6$  in a fixed field of 0.1 T as a function of temperature: the data show loss of magnetization near the Curie temperature,  $T_C$ , of approximately 600 K.

The essential point is to determine that the observed weak ferromagnetism is an intrinsic effect and not of some extrinsic origin. The magnitude of the ordered moment is  $\sim 1$  e.m.u. per mol hexaboride for  $x = 0.005$  in  $\text{CaB}_6$ , and is  $\sim 2$  e.m.u. per mol for  $\text{Sr}_{0.995}\text{La}_{0.005}\text{B}_6$ . We find consistently that the moment per mole is at a maximum near  $x = 0.005$  in both  $\text{SrB}_6$  and  $\text{CaB}_6$ . The same systematic study has not yet been made for  $\text{BaB}_6$ . We find similarly that Ce- and Sm-doped  $\text{SrB}_6$  samples have an ordered moment which peaks at  $x = 0.005$ . In addition, however, we recognize the expected paramagnetic background due to the local magnetic moment due to the f-electrons of these atoms, which is absent for La-doped material. These data indicate that the doping does not produce the moment through trace rare-earth impurities carried by the high-purity La used for the doping. For the pure alkaline-earth hexaborides, we find that a moment is present sometimes, and that this varies from crystal to crystal. This moment is generally distinctly smaller than that found at  $x = 0.005$ , usually by at least an order of magnitude. We also find a variation in the temperature dependence of the electrical resistivity of pure  $\text{SrB}_6$  and  $\text{CaB}_6$  from crystal to crystal; crystals showing weak ferromagnetism have a more metallic temperature dependence of the electrical resistivity. Doping divalent hexaborides with other alkaline earths also produces weak ferromagnetism, for instance in  $\text{Ca}_{0.995}\text{Ba}_{0.005}\text{B}_6$ . We can understand this variable behaviour of the crystals with no

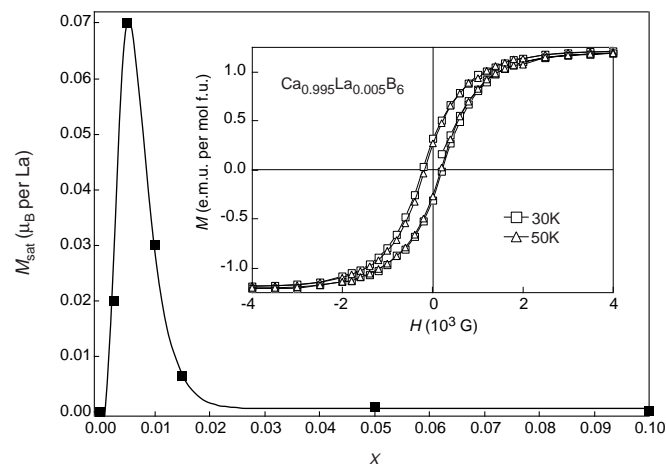


**Figure 3** Saturation moment at  $T = 5$  K per mol La as a function of La concentration in  $\text{CaB}_6$ . The line is a guide to the eye. Inset, hysteresis loops at 30 K and 50 K for  $\text{Ca}_{0.995}\text{La}_{0.005}\text{B}_6$ .

carrier doping on the basis of the band structure of the alkaline-earth hexaborides. Calculations<sup>10</sup> show that the details of the overlap of valence and conduction bands at the X-point of the Brillouin zone depend sensitively on the crystallographic parameter fixing the location of the borons in the unit cell; this parameter determines the relative length of the inter- and intra-octahedral boron–boron bonds. Even small changes in this parameter in the calculations alter the behaviour from insulating to metallic. So we might expect vacancies and foreign-atom additions to alter significantly the properties of the divalent hexaborides for very small dopings, such as seen in materials with similar band structure features (for example, grey tin and bismuth).

Two suggestions for the origin of the weak ferromagnetism which we have observed are (1) ordered defect moments and (2) ferromagnetic polarization of the low-density electron gas. Because no obvious source for a strong coupling giving rise to a Curie temperature as high as  $T_C = 600$  K presents itself, the coupling of magnetic moments localized on the La or other unspecified impurities on this scale seems rather implausible. A more likely candidate for the origin of the magnetic polarization emerges from studies of electronic correlations in the low-density electron gas, such as those of Ceperley and Alder<sup>11</sup>. This is a topic of theoretical speculation with a long history, going back to Bloch and Wigner<sup>1</sup>. The study of Ceperley and Alder is a  $T = 0$  K computation, comparing unpolarized and completely polarized states of the electron gas, with ferromagnetism showing up for values of  $r_s$  of the order  $80 a_B$ . (Here  $r_s$  is the radius of the sphere containing one conduction electron;  $a_B$  the Bohr radius.) Later calculations have lowered this value to  $\sim 20 a_B$  (ref. 12). For  $x = 0.005$ , we compute  $r_s = 15.0 \text{ \AA} = 28.4 a_B$ , using the Bohr radius for the free electron. A recent calculation by Ortiz, Harris and Ballone<sup>13</sup> treating partially spin-polarized states of the low-density electron gas has, in fact, found evidence that near  $r_s = 30 a_B$  the stable state is one with ferromagnetic polarization of the order of 10%; this is essentially our experimental finding of an ordered moment of  $\sim 0.07 \mu_B$  per carrier at  $x = 0.005$ . The natural energy scale here is the Fermi energy,  $E_F$ ; for free electrons we have  $E_F = 0.062 \text{ eV} = 720 \text{ K}$  for  $x = 0.005$  in  $\text{CaB}_6$ , of the order of the observed Curie temperature.

The ferromagnetic ground state of a dilute, three-dimensional electron gas has not previously been reported experimentally. But such a ground state seems to provide a possible description of the weak ferromagnetism reported here, although the temperature scale of the phenomenon is unexpected. Detailed calculations appropriate to the lattice case at finite temperature are clearly needed, as

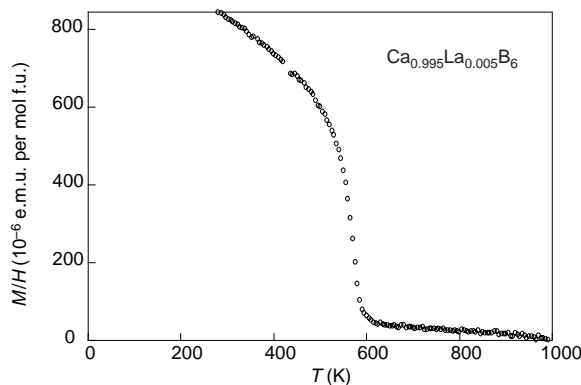

**Figure 4** Magnetization of  $\text{Ca}_{0.995}\text{La}_{0.005}\text{B}_6$  in a fixed applied field of 0.1 T as a function of temperature. These data were measured using a Faraday balance magnetometer.

is much further experimental elaboration of the details of this ferromagnetism. □

Received 14 July; accepted 4 November 1998.

- Herring, C. *Magnetism* Vol. IV (eds Rado, G. T. & Suhl, H.) Ch. 2 (Academic, New York, 1966).
- Schmidt, P. H. *et al.* Anisotropy of thermionic electron emission values for  $\text{LaB}_6$  single-crystal emitter cathodes. *Appl. Phys. Lett.* **29**, 400–410 (1976).
- Lafferty, J. M. *J. Appl. Phys.* **22**, 299–301 (1951).
- Erkelens, W. A. C. *et al.* Neutron scattering study of the antiferroquadrupolar ordering in  $\text{CeB}_6$  and  $\text{Ce}_{0.75}\text{La}_{0.25}\text{B}_6$ . *J. Magn. Magnet Mater.* **63/64**, 61–63 (1987).
- Nyhus, P., Cooper, S. L., Fisk, Z. & Sarrao, J. L. Low-energy excitations of the correlation-gap insulator  $\text{SmB}_6$ . *Phys. Rev. B* **55**, 12488–12496 (1997).
- Süllow, S. *et al.* Structure and magnetic order of  $\text{EuB}_6$ . *Phys. Rev. B* **57**, 5860–5869 (1998).
- Degiori, L., Felder, E., Ott, H. R., Sarrao, J. L. & Fisk, Z. Low-temperature anomalies and ferromagnetism in  $\text{EuB}_6$ . *Phys. Rev. Lett.* **79**, 5134–5137 (1997).
- Longuet-Higgins, H. C. & Roberts, M. de V. The electronic structure of the borides  $\text{MB}_6$ . *Proc. R. Soc. Lond. A* **224**, 336–347 (1954).
- Ott, H. R. *et al.* Structure and electronic properties of  $\text{SrB}_6$ . *Z. Phys. B* **102**, 337–345 (1997).
- Massida, S., Continenza, A., de Pascale, T. M. & Monnier, R. Z. Electronic structure of divalent hexaborides. *Z. Phys. B* **102**, 83–89 (1997).
- Ceperley, D. M. & Alder, B. J. Ground state of the electron gas by a stochastic method. *Phys. Rev. Lett.* **45**, 566–569 (1980).
- Alder, B. J., Ceperley, D. M. & Pollock, E. L. *Int. J. Quantum Chem. Symp.* **16**, 49–61 (1982).
- Ortiz, G., Harris, M. & Ballone, P. cond-mat/9810126.

**Acknowledgements.** Z.F. thanks E. Abrahams, G. Aeppli, L. Gor'kov, P. Kumar, E. Manousakis, G. Ortiz and D. Pines for discussions. Work at NIMFL was supported by the NSF; work at Los Alamos was done under the auspices of the US Department of Energy; and the work at ETH Zürich was supported by the Schweizerische Nationalfonds zur Förderung der wissenschaftlichen Forschung.

Correspondence and requests for materials should be addressed to Z.F. (e-mail: fisk@magnet.fsu.edu).

## Improved quantum efficiency for electroluminescence in semiconducting polymers

Yong Cao, Ian D. Parker, Gang Yu, Chi Zhang & Alan J. Heeger

UNIAx Corporation, 6780 Cortona Drive, Santa Barbara, California 93117-3022, USA

Some conjugated polymers have luminescence properties that are potentially useful for applications such as light-emitting diodes, whose performance is ultimately limited by the maximum quantum efficiency theoretically attainable for electroluminescence<sup>1,2</sup>. If the lowest-energy excited states are strongly bound excitons (electron–hole pairs in singlet or triplet spin states), this theoretical upper limit is only 25% of the corresponding quantum