

Lawrence Berkeley National Laboratory

Lawrence Berkeley National Laboratory

Title

POTASSIUM CATALYZED METHANE PRODUCTION FROM GRAPHITE AT LOW TEMPERATURES
(473-673 K)

Permalink

<https://escholarship.org/uc/item/1ft0k4sf>

Author

Cabrera, A.L.

Publication Date

1981-04-01



Lawrence Berkeley Laboratory

UNIVERSITY OF CALIFORNIA

Materials & Molecular Research Division

Submitted to Chemical Physics Letters


POTASSIUM CATALYZED METHANE PRODUCTION FROM
GRAPHITE AT LOW TEMPERATURES (473-673 K)

A.L. Cabrera, H. Heinemann, and G.A. Somorjai

April 1981

TWO-WEEK LOAN COPY

*This is a Library Circulating Copy
which may be borrowed for two weeks.
For a personal retention copy, call
Tech. Info. Division, Ext. 6782*

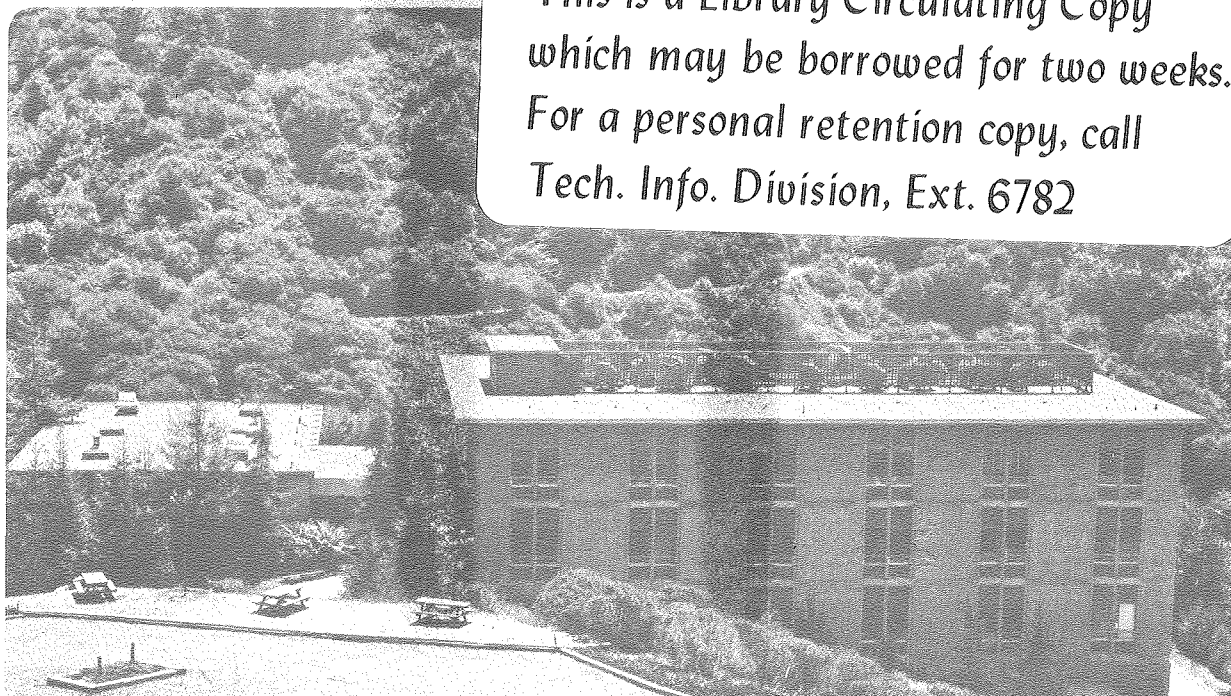

LBL-12665
c. 2

DISCLAIMER

This document was prepared as an account of work sponsored by the United States Government. While this document is believed to contain correct information, neither the United States Government nor any agency thereof, nor the Regents of the University of California, nor any of their employees, makes any warranty, express or implied, or assumes any legal responsibility for the accuracy, completeness, or usefulness of any information, apparatus, product, or process disclosed, or represents that its use would not infringe privately owned rights. Reference herein to any specific commercial product, process, or service by its trade name, trademark, manufacturer, or otherwise, does not necessarily constitute or imply its endorsement, recommendation, or favoring by the United States Government or any agency thereof, or the Regents of the University of California. The views and opinions of authors expressed herein do not necessarily state or reflect those of the United States Government or any agency thereof or the Regents of the University of California.

POTASSIUM CATALYZED METHANE PRODUCTION FROM
GRAPHITE AT LOW TEMPERATURES (473-673 K)

A. L. Cabrera, H. Heinemann, and G.A. Somorjai

Materials and Molecular Research Division, Lawrence Berkeley Laboratory
and
Department of Chemistry, University of California, Berkeley, CA 94720

Abstract

The steady state production of methane from high-density pure graphite and water vapor in the temperature range of 473-673 K is reported. The reaction is catalyzed by potassium compounds that are formed on the surface of the graphite. Surface composition is characterized by Auger electron spectroscopy.

This work was jointly supported by the Director, Office of Energy Research, Office of Basic Energy Sciences, Chemical Science Division, and the Assistant Secretary for Fossil Energy, Office of Coal Research, Liquifaction Division of the U. S. Department of Energy under Contract W-7405-ENG-48 through the Pittsburgh Energy Technology Center, Pittsburgh, PA.

Introduction

Potassium carbonate and potassium hydroxide at present are among the best catalysts used for the gasification of coal with steam to carbon monoxide and hydrogen at high temperatures, in the range of 900-1000 K [1]. In this temperature regime, hydrocarbons are unstable and their formation is not expected [2,3]. There have been no reports of studies of the reaction of water vapor with carbon at lower temperatures where the conditions for the formation of hydrocarbons are more favorable. We have been exploring the possibility of catalyzed conversion of graphite directly to hydrocarbons using various gases as reactants, including H₂O, H₂, CO, and CO₂ near 1 atm and at low temperatures (300-700 K), and using potassium as a catalyst. We found no evidence for chemical reactions of the high purity graphite samples with H₂, CO, or CO₂ in this temperature range. However, in the presence of water vapor, the potassium covered graphite produced methane at a surprisingly low temperature (500 K) and this catalyzed methanation reaction continues for many hours without poisoning.

Experimental Details

A pyrolytic graphite sample with a surface area of $\sim 1 \text{ cm}^2$ was mounted on the manipulator of an ultrahigh vacuum system ($<10^{-9}$ Torr). When the sample holder was positioned properly inside the system, the sample surface was accessible to surface composition analysis by Auger electron spectroscopy (AES), using the cylindrical mirror analyzer (CMA), ion sputter cleaning, and mass spectrometry. The system is also equipped with a high pressure cell which isolates the sample and allows us to perform chemical reaction studies at high pressures (atmospheres). The

product distribution obtained at high pressures were monitored by an HP 5880 A gas chromatograph with a thermal conductivity detector. This system is an improved version of a high pressure-low pressure instrument reported earlier.[4] A schematic diagram of the system with the high pressure cell closed or open is shown in Figure 1. The graphite samples were heated resistively by a high current AC power supply and the sample temperature was monitored by a chromel-alumel thermocouple that was in direct contact with it. Half a monolayer of potassium was then deposited on the graphite using a potassium-zeolite gun at the background pressure of 1×10^{-9} Torr. Then the sample was exposed to a mixture of 30 Torr of vapor obtained from distilled water and 1 atm of helium and heated to the desired temperatures in this gas mixture. It should be noted here that the only sources of hydrogen and oxygen in the system was the water vapor, since the high density graphite sample was free of hydrogen and of oxygen. The cleanliness of the graphite surface and the potassium surface concentration was monitored by AES before and after the high pressure experiments.


Results and Discussion

No chemical reaction between graphite and water vapor is detectable in the absence of the potassium catalyst. In the presence of potassium the production of CH_4 can be readily observed. The concentrations of CH_4 , CO_2 , and CO produced during the reaction of water vapor and the graphite samples were monitored as a function of time (in the temperature range of 475-600 K). We were also able to detect H_2 among the reaction products, but due to the similarity of its thermal conductivity to that

of the carrier gas (He), it was difficult to quantitatively follow its concentration change. The buildup of CH_4 concentration for two temperatures, 475 and 523 K, is displayed in Figure 2. From this figure and similar data obtained at other temperatures, an activation energy for the production of CH_4 of 10 ± 3 Kcal/mole can be estimated. The turnover frequency for the methane formation reaction is about 10^{-3} sec^{-1} at 523 K, assuming that all the graphite surface atoms are active.

The concentrations of CO_2 and CO that accumulated in the reaction chamber were about 10-30 times higher, respectively, than the CH_4 concentration. In order to determine whether there were other sources for the formation of the detected reaction products in the high pressure chamber in addition to graphite, several blank experiments were performed. A gold foil with and without potassium was substituted for the high density graphite sample in the chamber and the experiments were repeated using identical conditions of water vapor pressures and temperature. No methane could be detected in this circumstance. However, the production of CO_2 and CO could be observed at rates that are not too different from those detected in the presence of graphite. It appears that the walls of the stainless steel reaction chamber provide a source of carbon for CO_2 formation in the presence of water vapor. In order to obtain carbon mass balance for the graphite-water reaction that produces methane, the CO_2 and CO produced by the blank studies must be subtracted from the total amount of CO_2 and CO detected under reaction conditions. The buildup of CO and CO_2 concentrations as a function of time obtained with the gold foil and with the graphite samples for the two temperatures (475 and 513 K) are displayed in Figures 3 and 4, respectively. In the case of CO production, the concentration appears to be independent of temperature

and after subtracting the amount that was produced in the blank experiment, there is no CO left within the experimental sensitivity. However, the CO₂ concentration does depend on temperature and, after subtraction of the amount produced in the blank experiments, some CO₂ still remained, as seen in Figure 4. This amount of CO₂ is comparable to the CH₄ concentration produced at the same temperature. Therefore the reaction that produces CH₄ and CO₂ may be expressed as:



The graphite-water reaction was studied in the temperature range of 473-673 K and it was found that the highest fraction of conversion to CH₄ occurs at 523 K. At temperatures higher than 523 K the potassium surface concentration diminishes and the surface is covered with an increasing concentration of CO as detected by AES; at the same time, the production of CH₄ stops. (CO is present as strongly chemisorbed specie on the sample surface as revealed by thermal desorption experiments.) However, when the CO is removed by argon ion bombardment or by thermal desorption, the production of CH₄ starts up again.

The production of both H₂ and CO₂ was enhanced when CO was added to water vapor. It appears that much of the H₂ and the excess CO₂ are produced by the potassium-catalyzed water-gas shift reaction:



When using mixtures of CO and H₂O, only H₂ and CO₂ formation could be detected indicating that the water-gas shift reaction was taking place efficiently and at the expense of the methanation reaction. In the

presence of CO₂ and H₂O gas mixtures, no products of any kind were detected.

The production of CH₄ is readily reproducible using a variety of graphite samples and different amounts of potassium. In one of the experiments a sample of graphite was dipped in a KOH solution to rule out the possibility that metallic potassium present on the surface would play a role in the formation of CH₄. We obtained in this case the production of CH₄ in steady state for a period longer than 24 hours.

Potassium appears to catalyze both the reduction of carbon to CH₄ and its oxidation to CO₂. This striking and complex catalytic process will be scrutinized with several surface science techniques in the near future. We shall also explore the possible formation of other hydrocarbons in addition to CH₄ by the combined use of potassium and transition metal catalysts.

References

1. Wen-Yang Wen, Catal. Rev.-Sci. Eng. 22, 1 (1980).
2. R.B. Anderson, in Catalysis, Vol. IV, ed. P.H. Emmett, (Reinhold Publishing Corp., New York, 1956) p.29.
3. D.W. McKee and D. Chatterji, Carbon, 1978, Vol.16, pp. 53-57.
4. D.W. Blakely, E.I. Kozak, B.A. Sexton, and G.A. Somorjai, J. Vac. Sci. & Technol. 13, No. 5, 1091 (1976).

Acknowledgement: This work was jointly supported by the Director, Office of Energy Research, Office of Basic Energy Sciences, Chemical Science Division, and the Assistant Secretary for Fossil Energy, Office of Coal Research, Liquifaction Division of the U.S. Department of Energy under Contract W-7405-ENG-48 through the Pittsburgh Energy Technology Center, Pittsburgh, Pa.

Figure Captions

Figure 1. (a) Schematic diagram of the apparatus with high pressure cell closed, (b) detail with high pressure cell open.

Figure 2. Number of CH_4 molecules produced during the potassium catalyzed water-graphite reaction as a function of time for two different temperatures.

Figure 3. Number of CO molecules in the gas phase produced as a function of time for two different temperatures. Open circles and triangles correspond to blank experiments performed with potassium covered gold foils. Full circles and triangles correspond to experiments with potassium covered graphite in the reaction chamber.

Figure 4. Number of CO_2 molecules produced as a function of reaction time for two different temperatures. Dashed curves correspond to blank experiments performed with potassium covered gold foil. Solid lines correspond to experiments with potassium covered graphite in the reaction chamber.

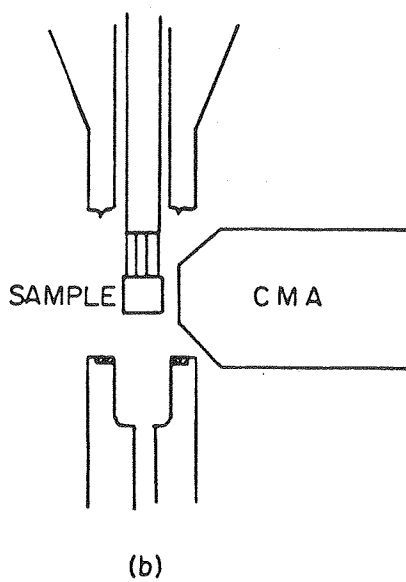
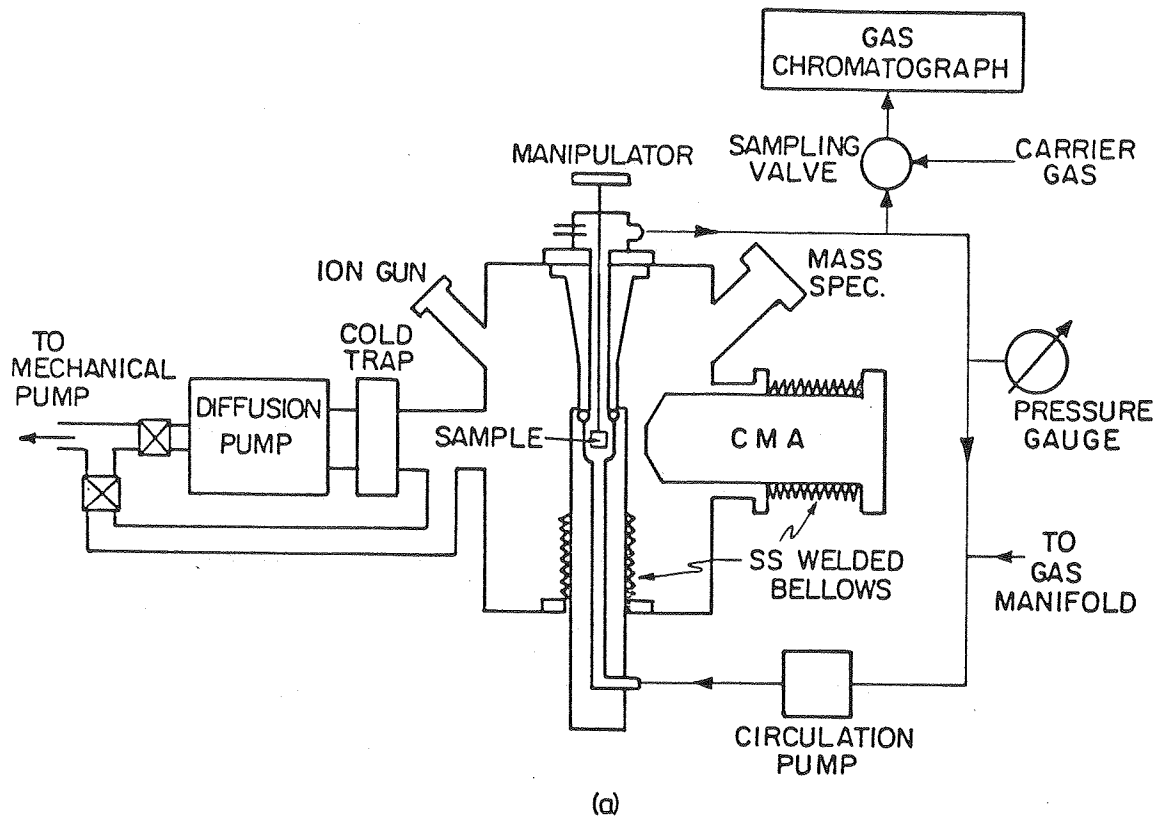


Fig. 1

XBL 814-5584

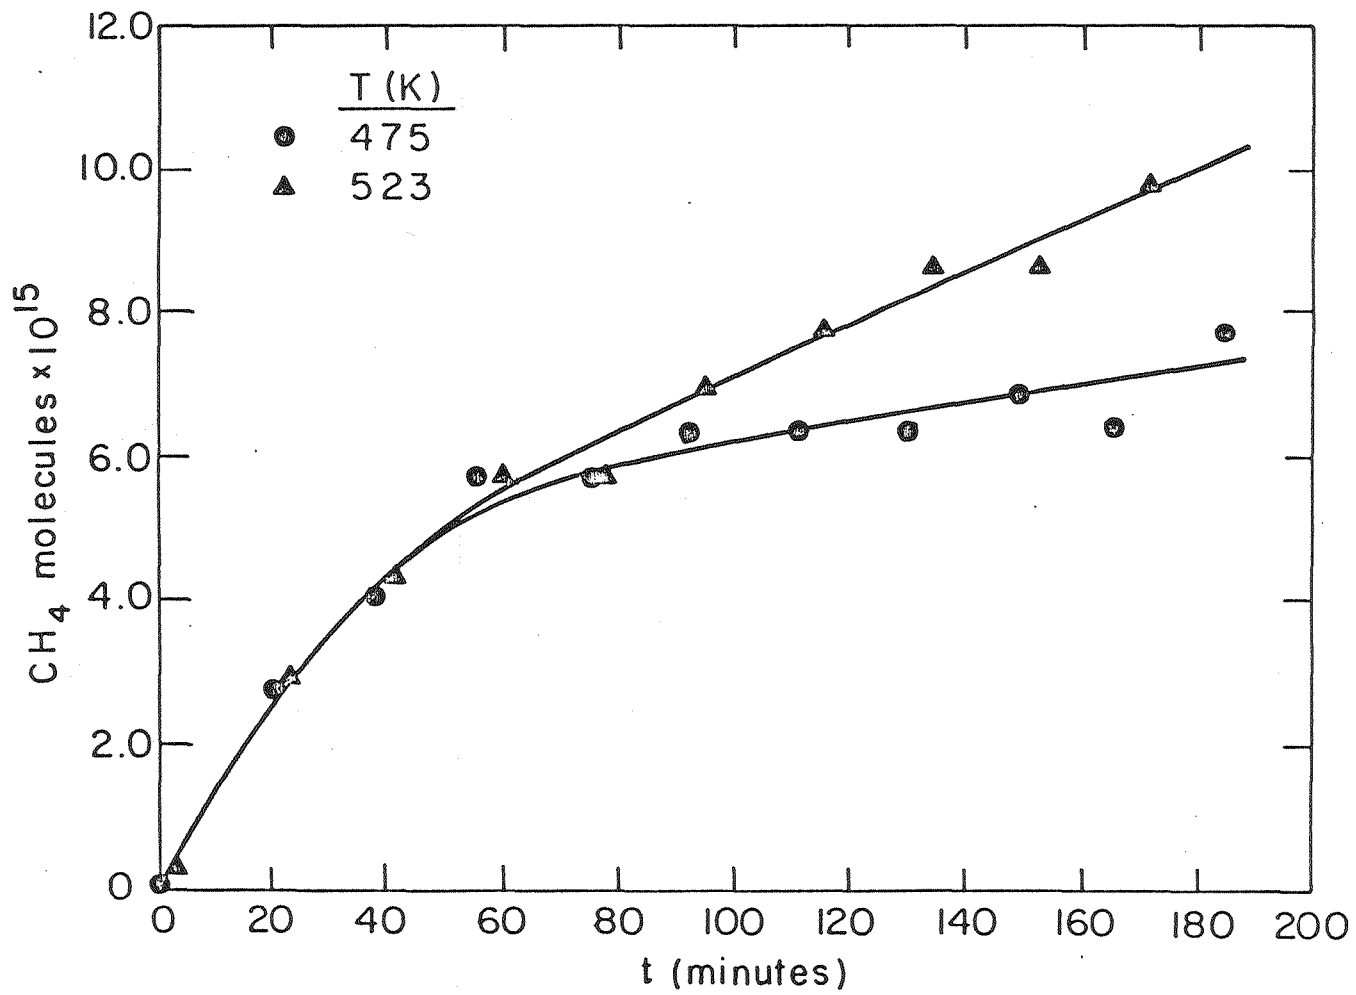


Fig. 2

XBL 814-5650


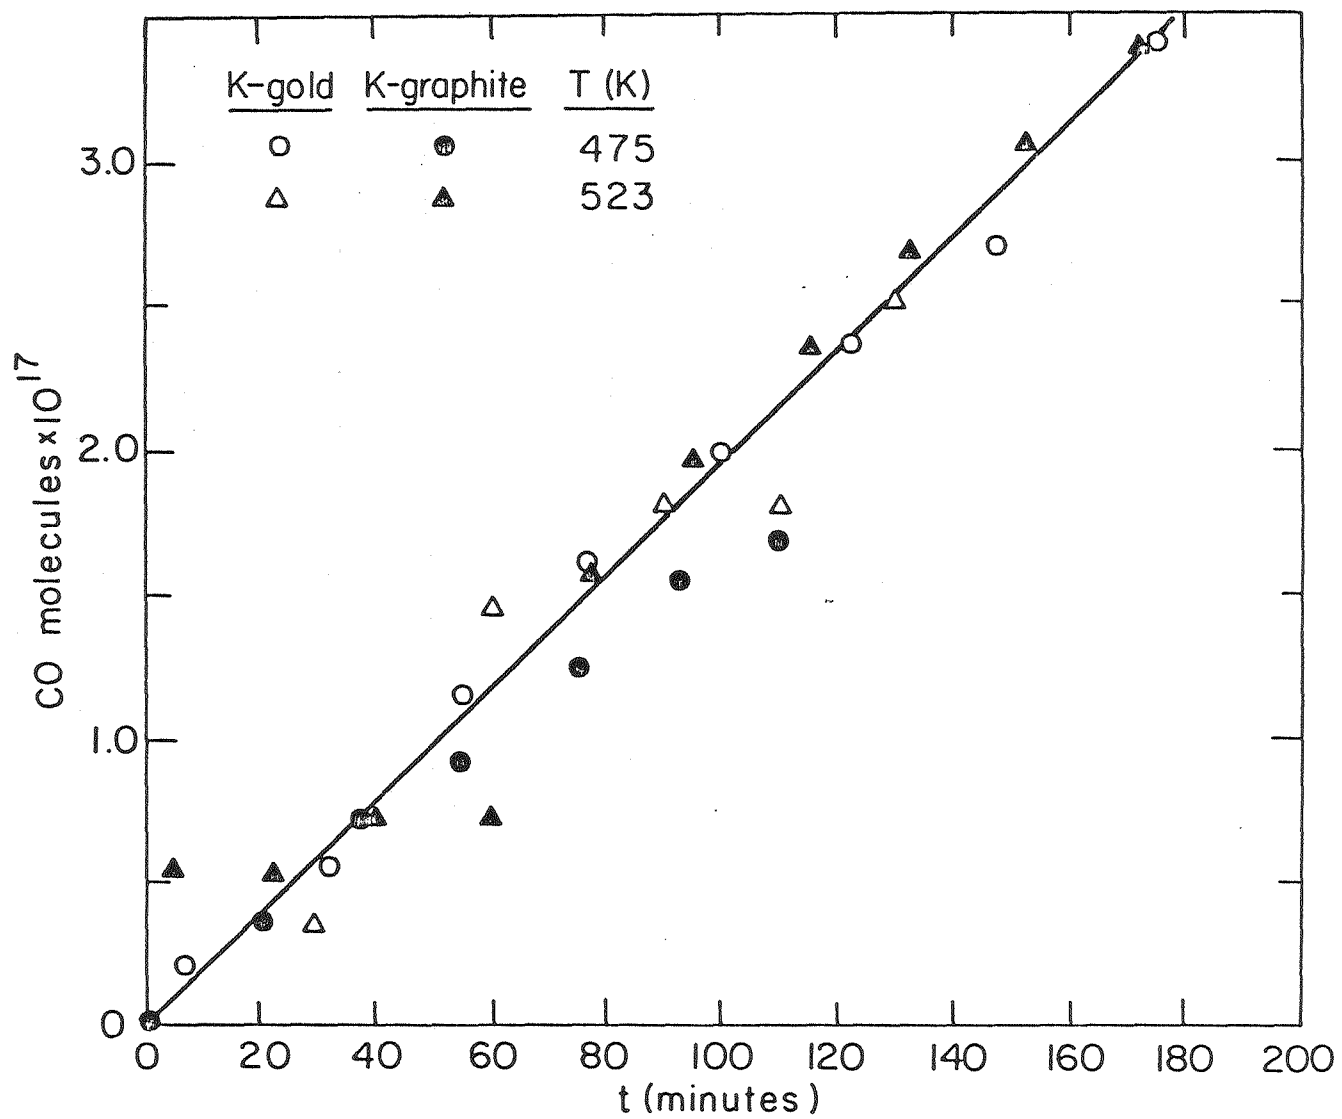


Fig. 3

XBL 814-5652

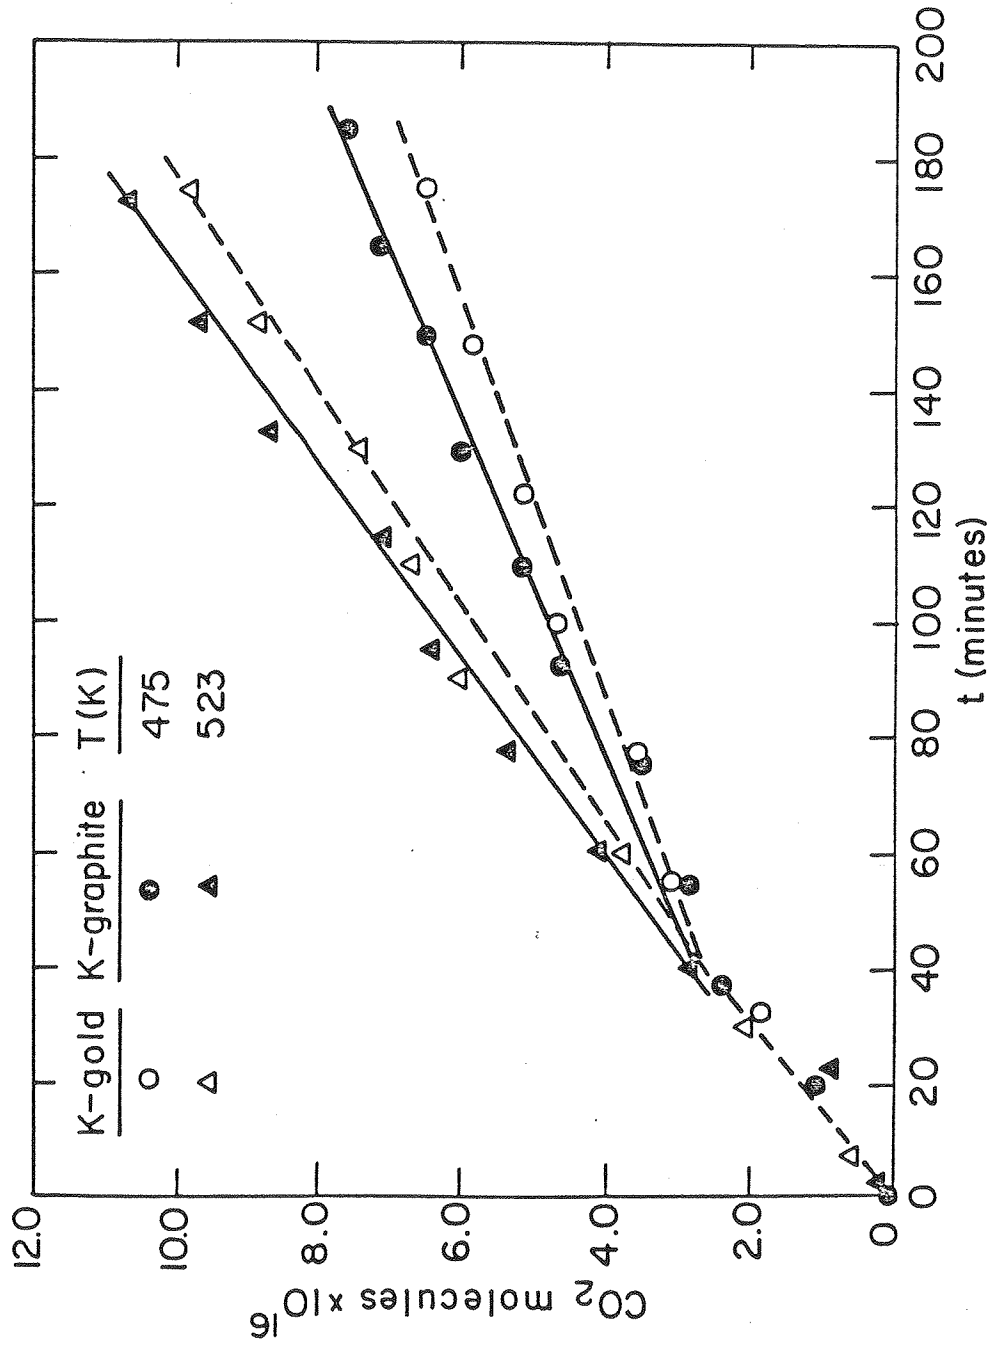

XBL814-5651

Fig. 4

