

Lawrence Berkeley National Laboratory

Recent Work

Title

ADVANCED HEAT-MIRROR FILMS FOR ENERGY-EFFICIENT WINDOWS

Permalink

<https://escholarship.org/uc/item/1mp6n406>

Author

Lampert, CM.

Publication Date

1982-03-01



Lawrence Berkeley Laboratory

UNIVERSITY OF CALIFORNIA

RECEIVED
LAWRENCE
BERKELEY LABORATORY

MAY 18 1982

LIBRARY AND
DOCUMENTS SECTION

ENERGY & ENVIRONMENT DIVISION

To be presented at The Renewable Challenge, the 1982
Annual Meeting of the American Section of the Inter-
national Solar Energy Society (ASISES), Houston, TX,
June 1-5, 1982


ADVANCED HEAT-MIRROR FILMS FOR ENERGY-EFFICIENT
WINDOWS

Carl M. Lampert

March 1982

TWO-WEEK LOAN COPY

*This is a Library Circulating Copy
which may be borrowed for two weeks.
For a personal retention copy, call
Tech. Info. Division, Ext. 6782.*

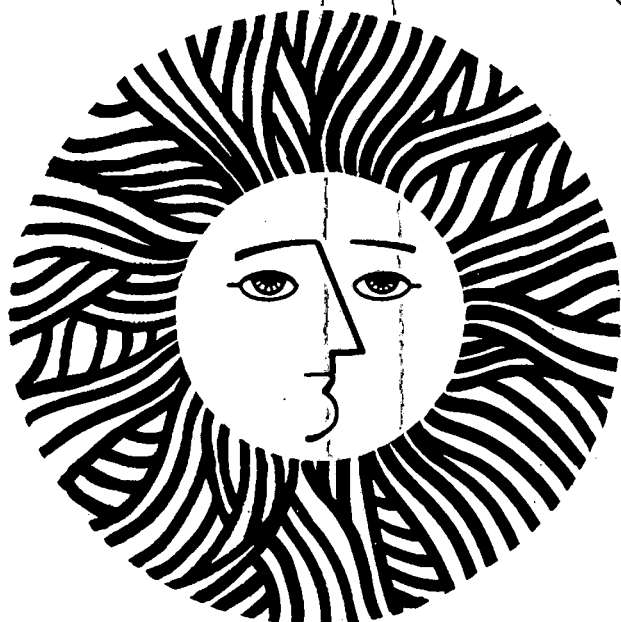

LBL-14250
e.2

DISCLAIMER

This document was prepared as an account of work sponsored by the United States Government. While this document is believed to contain correct information, neither the United States Government nor any agency thereof, nor the Regents of the University of California, nor any of their employees, makes any warranty, express or implied, or assumes any legal responsibility for the accuracy, completeness, or usefulness of any information, apparatus, product, or process disclosed, or represents that its use would not infringe privately owned rights. Reference herein to any specific commercial product, process, or service by its trade name, trademark, manufacturer, or otherwise, does not necessarily constitute or imply its endorsement, recommendation, or favoring by the United States Government or any agency thereof, or the Regents of the University of California. The views and opinions of authors expressed herein do not necessarily state or reflect those of the United States Government or any agency thereof or the Regents of the University of California.

LBL-14250
EEB-W 82-03
W-119

To be presented at The Renewable Challenge, the 1982 Annual Meeting of the American Section of the International Solar Energy Society (ASISES), Houston TX, June 1-5, 1982.

ADVANCED HEAT-MIRROR FILMS
FOR ENERGY-EFFICIENT WINDOWS

Carl M. Lampert

Materials and Molecular Research Division
and
Energy and Environment Division
Lawrence Berkeley Laboratory
University of California
Berkeley, CA 94720

March 1982

This work was supported by the Assistant Secretary for Conservation and Renewable Energy, Office of Buildings and Community Systems, Buildings Division of the U.S. Department of Energy under Contract No. DE-AC03-76SF00098.

ADVANCED HEAT-MIRROR FILMS FOR ENERGY-EFFICIENT WINDOWS

Carl M. Lampert
Materials and Molecular Research Division
and Energy and Environment Division
Lawrence Berkeley Laboratory
One Cyclotron Road, Bldg. 62
University of California
Berkeley, CA 94720 USA

ABSTRACT

Heat-mirror coatings can play a significant role as transparent insulation for architectural windows. These coatings effectively reduce the thermal emittance of glass or plastic glazings, thereby decreasing the overall radiative loss of the glazing or window assembly. Coating techniques are detailed for both doped semiconductor and dielectric/metal multilayer films. For highly doped semiconductors, Drude theory is discussed. New and innovative materials systems are also suggested.

1. INTRODUCTION

Coatings classified as heat mirrors or transparent conductors can be used to reduce radiative loss through architectural windows (1-3). Numerous thin-film systems exist which exhibit the potential for design of energy-efficient glazings (4). Some of these coatings have been used as transparent electrical conductors and to a lesser extent as infrared radiation reflectors. This work will attempt to put these heat-mirror films in the proper context for window usage.

For this study a "heat mirror" is defined as a coating which is predominately transparent over the visible wavelengths (0.3 - 0.77 microns) and reflective in the infrared (2.0 - 100 microns). For the near-infrared (0.77 - 2.0), the material may exhibit combined properties depending upon design and end use. Idealized properties of a heat mirror are shown schematically in Fig. 1. Also shown are the solar (airmass 2) and blackbody spectra. With heat mirrors for windows, the coating's infrared reflec-

tance property provides a low emittance (E) surface related by: $R = 1 - E$ and $A = E$ at the same wavelength and temperature, where R is spectral reflectance and A is absorptance, and assuming $T = 0$ in the infrared. The lower the emittance, the less the magnitude of radiative transfer by the window. Hence by using these nearly transparent coatings on a window surface the thermal characteristics can be dramatically altered and energy can be more efficiently managed. For example, Fig. 2. shows a triple and double glazed window incorporating heat mirrors. In the separation between the glazing sheets a low-conductivity gas may be used to provide further reductions in convective heat transfer. Figure 3 shows the effect of multiple glazing and coating placement on overall thermal conductance, or U-value. Results were derived by computer modeling (5). A nonglass insulated wall has $U = 0.6 \text{ W/m}^2\text{K}$ (R-11) to $0.3 \text{ W/m}^2\text{K}$ (R-19).

2. THEORY OF HEAT-REFLECTING COATINGS

Heat mirrors can be classified under two broad categories: single-layer materials such as highly doped $\text{SnO}_2:\text{F}$ and $\text{In}_2\text{O}_3:\text{Sn}$, and multilayer metal-based thin films such as SiO_2/Ag , $\text{ZnS}/\text{Cu}/\text{ZnS}$, and $\text{TiO}_2/\text{Ag}/\text{TiO}_2$. Both categories are linked by the conductive metal-like properties described by classical Drude theory (6). In this theory, a well defined plasma edge characterizes the material. It occurs due to excitation of free carriers by incident electromagnetic radiation. Since the charge carriers are actually moving in a potential field of the crystal, an effective mass (m^*) must be used. The $m^* = m_r m_e$, where m_e is the rest mass and m_r is the relative mass of the

charge carriers in the field. The complex dielectric constant is related to the optical constants by: $\epsilon = \epsilon_1 - \epsilon_2 = (n - ik)^2$; where $\epsilon_1 = n^2 - k^2$ and $\epsilon_2 = 2nk$.

For a Drude-like reflector, the dielectric constant can be expressed in terms of (W/w_p) and (Y/w_p) as follows:

$$\epsilon_1 = \epsilon_b \left[1 - \left(1 + \left(\frac{Y}{w_p} \right)^2 \right) / \left(\left(\frac{W}{w_p} \right)^2 + \left(\frac{Y}{w_p} \right)^2 \right) \right],$$

$$\epsilon_2 = \epsilon_b \left[\frac{Y}{w_p} \left(1 + \left(\frac{Y}{w_p} \right)^2 \right) / \frac{W}{w_p} \left(\left(\frac{W}{w_p} \right)^2 + \left(\frac{Y}{w_p} \right)^2 \right) \right],$$

where ϵ_b is the dielectric constant associated with bound carriers (at very high frequency) and Y is the relaxation frequency, $Y = e/um_e$, u is the carrier mobility, and e is the electron charge. The damped plasma frequency is derived as:

$$w_p = (Ne^2/\epsilon_b \epsilon_0 m^*)^{1/2} - Y^2,$$

where N is the carrier density and ϵ_0 is the dielectric constant of air. From this theory, n and k can be extracted in terms of frequency (W). Reflectance in air (normal-specular) can be derived by:

$$R = ((n-1)^2 + k^2) / ((n+1)^2 + k^2).$$

The theoretical reflectance for a doped transparent semiconductor is shown in Fig. 1. The Drude-modeled reflectance agrees well with that obtained by experimental films. One should note that in the Drude equation as $W \gg w_p > Y$, n becomes constant and $k \rightarrow 0$, implying that the material is transparent at short wavelengths and for $W \ll Y < w_p$, $n = k$ are about equal and large in magnitude, implying a high reflectance.

3. DISCUSSION

Transparent conductors, or heat mirrors, can be physically deposited by a variety of methods including physical vapor deposition (sputtering, evaporation) and chemical vapor deposition (pyrolysis, hydrolysis). Other methods include plasma-enhanced, reactive and polycondensation of organometallics. The thermal and chemical stability of the substrate (glass or poly-

mer) are significant in determining which deposition process can be used. The optical properties of the substrate influence how effective a coating will be in producing the desired heat-mirror properties. During deposition, secondary and competing reactions have to be suppressed by the control of reaction kinetics and the understanding of thermodynamic constraints.

An important consideration in optimizing solar transmittance (T_g) versus infrared reflectance (R_{IR}) (or infrared emittance) is to understand the fundamental properties of the heat-mirror film. The optical properties are a direct result of the electronic, morphological, and chemical structure of the film. Also the role of atomic defects, degree of order, impurity, and dopant atoms are significant to the electronic properties. The ratio of T_g/R_{IR} also relates solar gain and daylighting potential to infrared insulation value. One of the most difficult situations to satisfy is where appreciable winter heating and summer cooling loads exist. A film having reversible or variable properties such as an optical shutter material would be appropriate (7).

3.1 Doped Semiconductor Films

Doped semiconductors are single-layer materials that generally have a high carrier concentration on the order of 10^{20} to 10^{23} cm^{-3} and high mobility (>10 $\text{cm}^2/\text{V-sec}$). Thin, partially transparent metal films are not included in this category since they generally require overcoating films for chemical stability, mechanical durability, and increased transmission. Thicker, less transparent metallic films are used for solar control functions. The best known transparent semiconductors are $\text{SnO}_2:\text{F}$, $\text{SnO}_2:\text{Sb}$, $\text{In}_2\text{O}_3:\text{Sn}$ and Cd_2SnO_4 . Characteristic spectral transmission and reflectance values are delineated in Fig. 4 for research films on glass substrates. By etching microgrids into the coatings, their transmission can be increased (19). Obtaining a reproducible, high quality commercial coating is totally a different matter. Present techniques need to be improved to deposit these coatings on polymeric substrates. Examples of films are shown in Fig. 5. In Table 1 the physical properties of selected single-layer films are enumerated. Further detailed

information is cited elsewhere (4). Other promising single-layer materials for heat mirrors are in the rare earth oxides, borides, transition metal nitrides, and possibly carbide systems. Little is known optically about many of these materials except that they all have Drude-like electrical conduction. Also graded-index and textured single-layer heat mirrors have yet to be developed, and such coatings could have enhanced solar and visible properties.

3.2 Multilayer Heat-Mirror Filters

Thin metal films below about 100 angstroms thick exhibit partial transparency. Generally, metal films have to be overcoated for improved chemical stability. Dielectric overlayers also serve to antireflect the metal film in the solar wavelength, increasing transmission. This can be done by proper design of an interference filter. The dielectric film must have high infrared transparency to preserve the metallic infrared reflectance. Example systems (4) are polymer/M, SiO_2/M , $\text{Bi}_2\text{O}_3/\text{M}$, $\text{Al}_2\text{O}_3/\text{M}$, $\text{Bi}_2\text{O}_3/\text{M}/\text{Bi}_2\text{O}_3$, $\text{ZnO}/\text{M}/\text{ZnO}$, $\text{TiO}_2/\text{M}/\text{TiO}_2$, and $\text{ZnS}/\text{M}/\text{ZnS}$ where M is a metal of Ag, Al, Au, Cu, Cr, Ti, Ni. Additional designs can include X/M and X/M/X, where X is an appropriate semiconductor or polymer. Multilayer films can approximate the responses of doped semiconductors with the added advantage of wavelength tunability. Durability of multilayer films still remains an important research area. Spectral properties of selected multilayer films on glass and polymeric substrates are shown in Figs. 6 and 7. Detailed property data is provided in Table 2. Three domestic manufacturers of multilayer heat-mirror coated windows (Southwall of Palo Alto CA, Airco Temescal of Concord CA, and Guardian Ind. of Carleton MI, have had their products reviewed recently (8). There is also considerable international activity in both categories of film coating.

4. CONCLUSIONS

In covering much data on heat-mirror films, several observations have been noted. When spectral data is provided it should state whether or not the substrate is

included in the measurement. For solar applications it is extremely important to qualify T_{vis} , T_s , R_{ir} , or E_{ir} . They should be integrated with respect to the photopic, solar spectrum (air mass 2), or appropriate blackbody distribution. Many times only average values are given.

Several types of transparent conductors useful as heat mirrors and their production techniques have been discussed. One of the major obstacles that impedes further progress is the need to develop less costly deposition techniques. Coating of flexible plastic substrates is one solution. Lower temperature, atmospheric pressure, and chemical-filming processes need to be devised. Film stability over long periods of time (> 10 yrs) has yet to be demonstrated. Analysis of coatings and understanding of materials chemistry as it relates to optical properties and environmental stability is also highly important.

5. ACKNOWLEDGEMENTS

The author wishes to thank his research group colleagues for supporting this effort: Mr. Steve Selkowitz, Dr. Mike Rubin, Dr. Sam Berman, and Dr. Jack Washburn. This work was performed at the Lawrence Berkeley Laboratory, Materials and Molecular Research Division, under a joint program with the Energy and Environment Division, Energy Efficient Buildings Program. The work was supported by the Assistant Secretary for Conservation and Renewable Energy, Office of Buildings and Community Systems, Buildings Division of the U.S. Department of Energy under Contract No. DE-AC03-76SF00098.

6. REFERENCES

- (1) S. Selkowitz, Proc. of 3rd Passive Solar Conf. San Jose, CA, Jan 1979.
- (2) S. Selkowitz, ASHRAE Trans. 85-2, 669 (1979).
- (3) R. Johnson, S. Selkowitz, F. Winklemann, and M. Zenter, Proc. of Third Int. Symp. on Energy Conservation in the Built Environ., Dublin, Ireland,

March 1982.

- (4) C.M. Lampert, *Solar Energy Materials* 6,1 (1981).
- (5) M. Rubin, R. Creswick, and S. Selkowitz, *Proc. of 5th National Passive Solar Conf.* Amherst, MA, Oct. 1980.
- (6) P. Drude, *Phys Z.* 1, 161 (1900).
- (7) C. M. Lampert, "Thin Films Electrochromic Materials for Energy Efficient Windows," Lawrence Berkeley Laboratory Report LBL-10862 Rev., to be published in 1982.
- (8) V.E. Smay, *Pop. Sci.* 220, 59 (1982).
- (9) H. Kostlin, R. Jost, and W. Lems, *Phys. Status Sol.* A29, 87 (1975).
- (10) G. Haacke, *Appl. Phys Lett.* 30, 380 (1977).
- (11) M. Van der Leij, Ph.D. Thesis, Delft Univ. Press, Delft The Netherlands 1979.
- (12) R.P. Howson and M.I. Ridge, *Proc. of SPIE* 324 (1982).
- (13) K. Itoyama, *J. Electrochem. Soc.* 126, 691 (1979).
- (14) W.J. King, "High Performance Solar Control Windows" Lawrence Berkeley Laboratory Report LBL-12119, 1981.
- (15) B.P. Levin and P.E. Schumacher, "A Discussion of Heat Mirror Film: Performance, Production Process and Cost Estimates," Lawrence Berkeley Laboratory Report LBL-7812, Oct. 1977.
- (16) K. Chiba, S. Sobajima, U. Yonemura, and N. Suzuki, *Proc. of SPIE* 324 (1982).
- (17) J.C. Fan, F. Bachner, G. Foley, and P. Zavracky, *Appl. Phys. Lett.* 25, 693 (1974).
- (18) H. Kostlin, *Philips Techn. Rev.* 34, 242 (1974).
- (19) J.C. Fan, *Proc. of SPIE* 85, 39 (1977).
- (20) M.M. Koltun and S.A. Faiziev, *Geliotekhnika* 10, 58 (1974).

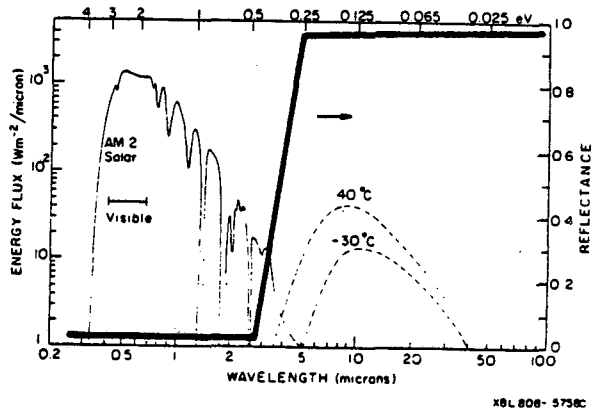


Fig. 1. Solar irradiance (airmass 2) with two blackbody distributions (40°C, -30°C). Superimposed is the idealized reflectance of a heat-mirror coating.

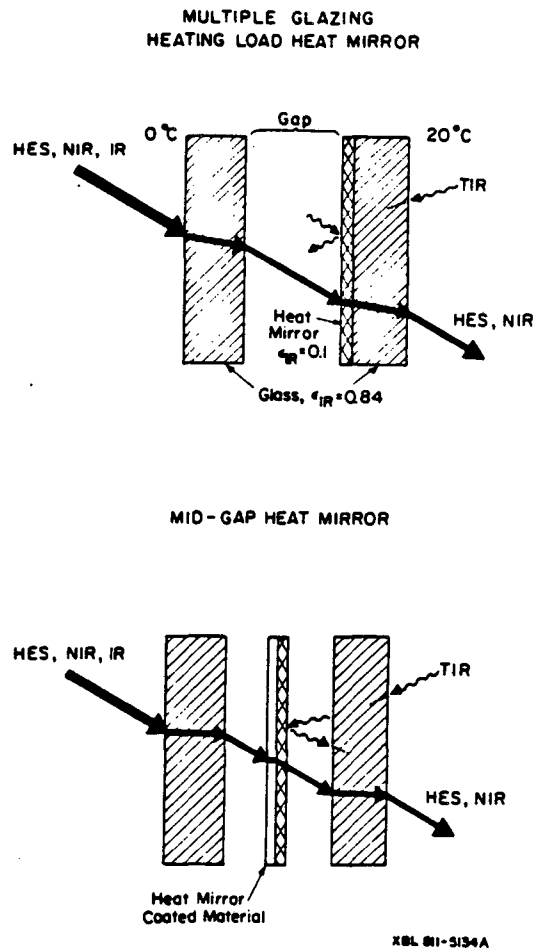


Fig. 2. Multiple glazed windows employing heat-mirror coatings.

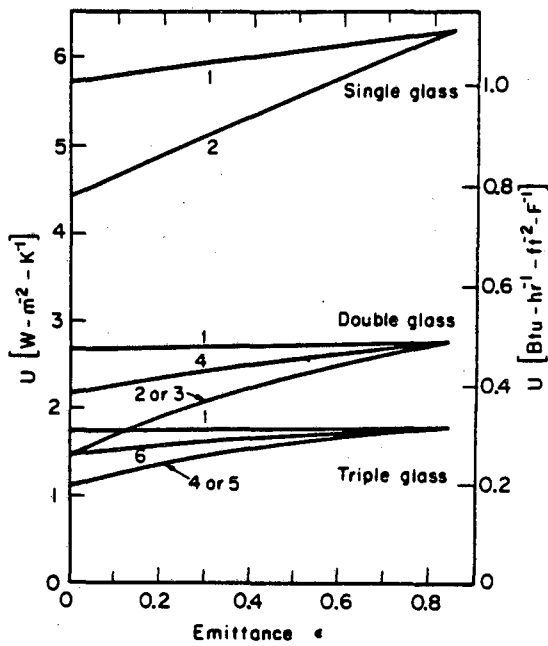


Fig. 3. Modeled thermal conductance (U) for various window designs (5) using ASHRAE Standard winter conditions ($T_{out} = 18^{\circ}C$, $T_{in} = 18^{\circ}C$, wind speed = 24 km/hr). The effect of lowering the emittance of a single surface by the addition of a heat mirror. The surfaces on which the heat mirror appears are given as consecutive numbers, starting from the outside surface labeled 1. Air gap is 1.27cm.

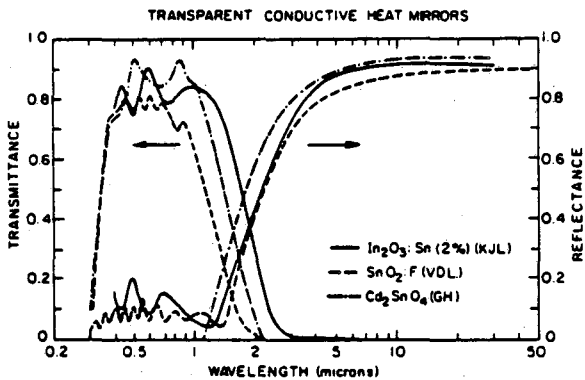


Fig. 4. Spectral normal transmittance and reflectance of heat-mirror coatings based on $In_2O_3:Sn$, Cd_2SnO_4 , $SnO_2:F$ (9-11).

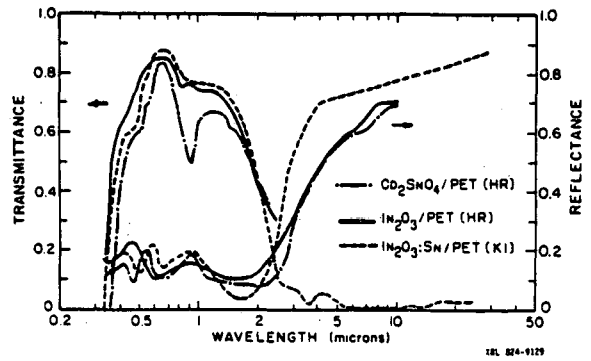


Fig. 5. Spectral normal transmittance and reflectance of single-layer heat-mirror coatings deposited on polyethylene terephthalate (PET) film (12, 13).

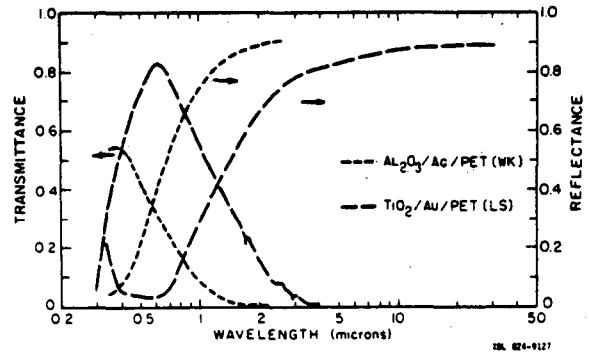


Fig. 6. Dielectric/metal coatings on PET (14, 15).

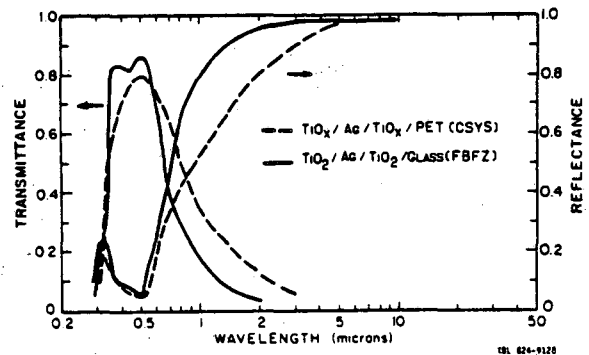


Fig. 7. Titania/silver/titania coatings on PET (16) and glass (17).

TABLE 1
Selected Heat-Mirror Films (4)

Material	SnO ₂ :F	Cd ₂ SnO ₄	In ₂ O ₃ :Sn	In ₂ O ₃ :Sn
Deposition tech.	Spray Hydro. 500-570°C	RF Sputt. Anneal 420°C	Spray Hydro.	RF Sputt. etched microgrid
Sheet Resist. (ohm/sq)	4	26-43	15-20	3
Thickness (microns)	1.0	< 0.3	-	0.35
Mobility (cm ² /V-sec)	37	-	-	-
Carrier Density (cm ⁻³ x 10 ²⁰)	4.4	-	15	-
T _{vis} (ave) or (T _s)	(0.75)	(0.86)	-0.9	(0.90, AM2)
R _{ir} or (E _{ir})	(0.15)	(0.12, 77°C)	0.85	0.83, 10um
Reference	11	10	18	19

TABLE 1 (continued)

Material	Cd ₂ SnO ₄ /PET	In ₂ O ₃ /PET	In ₂ O ₃ :Sn/PET
Deposition tech.	REACT DC Sputt. & RF BIAS	REACT DC Sputt. & RF BIAS	REACT RF Sputt.
Sheet Resist. (ohm/sq)	24	30	<30
Thickness (microns)	0.28	0.34	0.5
Mobility (cm ² /V-sec)	30	29	-
Carrier Density (cm ⁻³ x 10 ²⁰)	3.4	2.1	-
T _{vis} (ave) or (T _s)	-0.65	-0.78	0.8
R _{ir} or (E _{ir})	0.7, 10um	0.7, 10um	0.8, 10um
Reference	12	12	13

TABLE 2
Multilayer Heat-Mirror Films (4)

Material	Al ₂ O ₃ /Ag	TiO ₂ /Au/PET	TiO ₂ /Ag/TiO ₂	TiO _x /Ag/TiO _x	ZnS/Ag/ZnS
Deposition tech.	Ion Beam Sputt.	e-Beam Evap. & Chemical Dep.	RF Sputter	Chemical Dep. & Vac Evap.	Vac. Evap.
Sheet Resist. (ohm/sq)	-	10	-	-	10
Thickness (angstroms)	-	-	180/180/180	270/150/270	520/100/770
T _{vis} (ave) or T _s	0.47, 5um	0.80	0.84	-0.75	0.68
R _{ir} or (E _{ir})	0.93, 2.5um	0.87	0.99, 10um	0.98, 5um	(0.06)
Reference	14	15	17	16	20

This report was done with support from the Department of Energy. Any conclusions or opinions expressed in this report represent solely those of the author(s) and not necessarily those of The Regents of the University of California, the Lawrence Berkeley Laboratory or the Department of Energy.

Reference to a company or product name does not imply approval or recommendation of the product by the University of California or the U.S. Department of Energy to the exclusion of others that may be suitable.

TECHNICAL INFORMATION DEPARTMENT
LAWRENCE BERKELEY LABORATORY
UNIVERSITY OF CALIFORNIA
BERKELEY, CALIFORNIA 94720