

Lawrence Berkeley National Laboratory

Lawrence Berkeley National Laboratory

Title

RRP Nb₃Sn Strand Studies for LARP

Permalink

<https://escholarship.org/uc/item/2z6362r4>

Author

Barzi, Emanuela

Publication Date

2009-04-16

RRP Nb₃Sn Strand Studies for LARP

Emanuela Barzi, Rodger Bossert, Shlomo Caspi, Daniel R. Dietderich, Paolo Ferracin, Arup Ghosh, and Daniele Turrioni

Abstract—The Nb₃Sn strand chosen for the next step in the magnet R&D of the U.S. LHC Accelerator Research Program is the 54/61 sub-element Restacked Rod Process by Oxford Instruments, Superconducting Technology. To ensure that the 0.7 mm RRP strands to be used in the upcoming LARP magnets are suitable, extensive studies were performed. Measurements included the critical current, I_c , using the voltage-current ($V - I$) method, the stability current, I_S , as the minimal quench current obtained with the voltage-field ($V - H$) method, and RRR . Magnetization was measured at low and high fields to determine the effective filament size and to detect flux jumps. Effects of heat treatment temperature and durations on I_c and I_S were also studied. Using strand billet qualification and tests of strands extracted from cables, the short sample limits of magnet performance were obtained. The details and the results of this investigation are herein described.

Index Terms—Critical current density, magnetic instability, Nb₃Sn, restack rod process.

I. INTRODUCTION

LARP Technology Quadrupoles (TQ) [1], [2] and all other LHC Accelerator Research Program (LARP) magnet designs [3], [4] are presently based on 0.7 mm Nb₃Sn strands. The workhorse material chosen for the next step in the magnet R&D is the 54/61 subelement (i.e. 54 subelements in a 61-stack billet) Restacked Rod Process (RRP) by Oxford Instruments, Superconducting Technology (OIST). Meanwhile, the Conductor Development Program (CDP) and Fermilab [5] are working with designs with larger number of restacks to reduce the effective filament diameter, d_{eff} , which is known to play a substantial role in magnetic instabilities.

Strand studies start by checking that the billets being produced meet specifications. Extensive heat treatment (HT) optimization studies are then performed to meet the two conflicting requests of large critical current, I_c , at high field, and good stability at low fields. After cable fabrication, both high field I_c degradation and low field stability are studied and measured for all cables. Using witness (i.e. sample reacted with the coils) strand and cable samples, short sample limit predictions are calculated for each coil that is wound and heat treated from measurements of extracted strands.

Manuscript received August 28, 2006. This work was supported by the U.S. Department of Energy, under Contract No. DE-AC02-05CH11231.

E. Barzi, R. Bossert, and D. Turrioni are with the Fermi National Accelerator Laboratory, Batavia, IL 60510 USA (e-mail: barzi@fnal.gov).

S. Caspi, D. R. Dietderich, and P. Ferracin are with the Lawrence Berkeley National Laboratory, Berkeley, CA 94720 USA.

A. Ghosh is with the Brookhaven National Laboratory, Upton, NY 11973 USA.

Digital Object Identifier 10.1109/TASC.2007.899579

TABLE I
STRAND SPECIFICATIONS

Technology	Ternary RRP Nb ₃ Sn
Diameter, mm	0.7
$J_c(12\text{ T}), \text{A/mm}^2$	≥ 2400
$d_{eff}, \mu\text{m}$	< 70
I_S, A	> 1000
Cu, %	53 ± 2
RRR	≥ 100
RH twist, mm	14 ± 2
Piece length, m	≥ 350
High temperature HT time, h	≥ 48

TABLE II
TQ CABLE SPECIFICATIONS

Parameter	Specification	Tolerance
No. strands	27	-
Strand diameter, mm	0.7	± 0.002
Width, mm	10.077 max	+0.000, -0.100
Thickness, mm	1.26	± 0.01
Keystone angle, °	1	± 0.10
Pitch length, mm	78	± 2
Length, m	65	-

II. STRAND AND CABLE SPECIFICATIONS

Based on feedback from previous R&D work [6], strand and cable specifications were formulated for the next LARP quadrupole models, as shown in Tables I and II. A description of the many cables fabricated within the LARP program is in [7].

III. REACTION AND STRAND TEST PROCEDURES

A. Reaction and Strand Test Procedures

The strand samples were mounted on grooved cylindrical barrels made of either Ti-6Al-4V (FNAL, LBNL) or stainless steel (BNL). After reaction in vacuum (BNL) or in Argon (FNAL, LBNL), the samples were either tested on the same barrel (FNAL, LBNL) or transferred to a Ti-alloy barrel (BNL) [6]. Unless otherwise specified, BNL used end splices soldered in parallel to a couple of sample end turns in the region of transition from the Cu to the Ti-alloy section of the barrel, and no bonding agent, and FNAL and LBNL used end splices and STYCAST to bond the sample. The I_c was determined from the $V - I$ curve using the $10^{-14} \Omega \cdot \text{m}$ resistivity criterion. In $V - H$ tests the transport current is ramped to a fixed value, and the field is swept up and down between 0 and 4 T with ramp rates of 5 to 17 mT/s. If no quench is observed the current

TABLE III
ROUND ROBIN TEST RESULTS

SRS01-C01 Reaction								
Strand ID	I_c , A at 15 T	12 T ^a	11 T	10 T	9 T	8 T	I_S , A	RRR
Extr. 935R, BNL		[577]	706	859	1038	-	575±25	183
Extr. 935R, BNL		[557]	682	827	1001	1203	>1200	225
Extr. 935R, FNAL	243	517	[639]	(793)	-	-	1287±12.5	-
SRS01-C02 Reaction								
Strand ID	I_c , A at 15 T	12 T ^a	11 T	10 T	9 T	8 T	I_S , A	RRR
Extr. 935R, BNL		[544]	667	812	983	-	950±50	176
Extr. 935R, BNL		[566]	694	838	1011	1216	1050±50	174
Extr. 935R, BNL		[564]	684	841	1010	1225	>1200	355
Extr. 935R, FNAL	245	525	(646)	(796)	-	(1157)	975±25	297

^a Values in square parentheses were parameterized using [8], values in round parentheses were extrapolated from the $V - I$ curve.

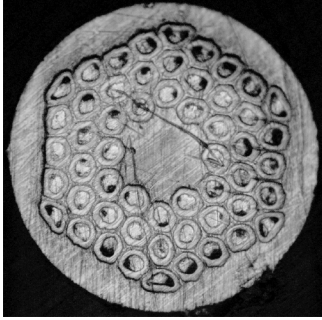


Fig. 1. Cross section of a reacted 0.7 mm RRP strand.

is increased and the test repeated. This test is done to determine the minimum quench current, or stability current, I_S , in the presence of a magnetic field variation. For strands, the I_S value was reported as the average between the minimal current at which a quench occurred and the maximum current that the sample could sustain without quenching.

Magnetization measurements at FNAL were conducted with a balanced coil magnetometer at low and high fields.

B. Comparison of Test Results (Round Robin)

The reaction of SRS01, which is made of two double-layer racetrack coils, SRS01-C01 and SRS01-C02, was used also as a round robin test run among the Labs. These two coils underwent separate reactions at BNL. In each case strand and cable samples were included together with the coils to serve as witnesses of the coil reaction. Table III shows the test results obtained for extracted strands tested on Ti-alloy barrels. The difference in I_c test results between BNL and FNAL was 6% to 9% at 11 T.

IV. BILLET PRODUCTION

OIST has presently produced for LARP eight billets for a total of about 280 kg of 0.7 mm RRP strand with 54/61 subelement design. Fig. 1 shows a strand cross section. The piece length distribution is shown in Fig. 2. Excluding the first billet (8220) that was produced with a larger twist pitch, the average right-hand pitch was $13.4 \text{ mm} \pm 1.4 \text{ mm}$, and the average $Cu\%$ was 46.5 ± 0.5 . For a HT with a final step of 50 h at 665°C , the average RRR was 187 ± 32 , and the average $J_c(4.2 \text{ K}, 12 \text{ T})$

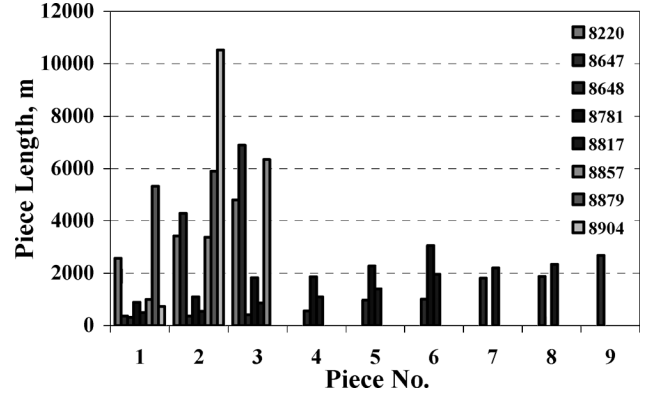


Fig. 2. Distribution of piece lengths for the OIST billets.

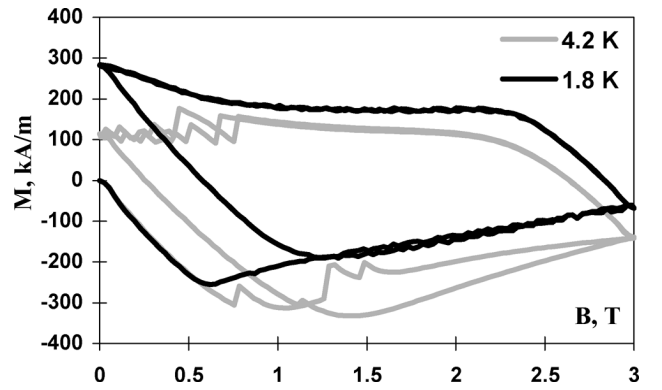


Fig. 3. Magnetization curves per total volume of an 8817 RRP strand at low field at 4.2 K and at 1.8 K.

as measured by OIST at the front and back end of each billet was 2891 A/mm^2 with a standard deviation of 152 A/mm^2 .

Magnetization as measured at 4.2 K and 1.8 K at FNAL for a sample of billet 8817 is given in Fig. 3. The final HT step was 60 h at 635°C . Magnetization $\mu_0 M(4.2 \text{ K}, 12 \text{ T})$ per total strand volume was $(55.4 \pm 1.8) \text{ mT}$. The $I_c(4.2 \text{ K}, 12 \text{ T})$ was 532 A. The resulting d_{eff} in the round filament approximation was $(78.7 \pm 2.6) \mu\text{m}$. At 1.8 K, $\mu_0 M(1.8 \text{ K}, 12 \text{ T})$ per total strand volume was $(75.1 \pm 3.9) \text{ mT}$, which indicates that the $I_c(1.8 \text{ K}, 12 \text{ T})$ is a factor of 1.35 larger than $I_c(4.2 \text{ K}, 12 \text{ T})$. However, at low field flux jumps at 1.8 K are so large that they reduce the magnetization amplitude by about 30% compared to data at 4.2 K. More magnetization test results on LARP strands can be found in [9].

V. OPTIMIZATION OF REACTION CYCLE

To establish a suitable heat treatment schedule for the first RRP TQ and SR magnets, heat treatment optimization cycles that provide good I_c and I_S were searched. Three billets, 8220, 8647 and 8648, were used for this study. The $I_c(11 \text{ T})$ and the I_S as measured at 4.2 K for round strands at BNL are plotted in Figs. 4 and 5 as a function of maximum reaction temperature. The duration was 48 to 50 h in all cases. The spread in data associated to a same temperature is a measure of the reproducibility that can be attained in I_c and I_S tests. One can see that whereas

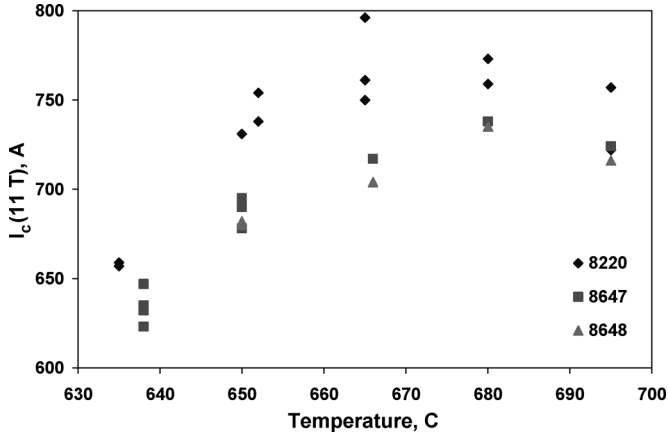


Fig. 4. $I_c(11 T)$ as measured at 4.2 K at BNL for round strands of three billets as a function of reaction temperature for 48 to 50 h durations.

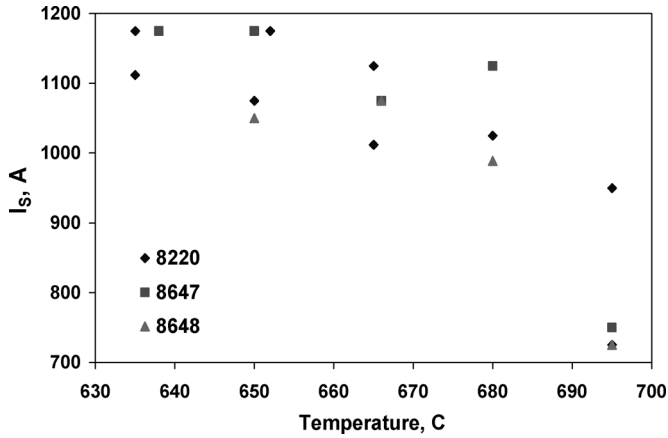


Fig. 5. I_S as measured at 4.2 K at BNL for round strands of three billets as a function of reaction temperature for 48 to 50 h durations.

the largest I_c are obtained at temperatures between 660°C and 680°C, the largest I_S are found below 660°C.

VI. CABLE QUALIFICATION

An example of cable qualification is given for three different cables that were all made out of the same billet 8220. Cables 933R and 939R meet TQ cable specs, cable 935 is a narrower rectangular cable made of 20 strands, to be used in the small and long racetracks [7].

A. High Field I_c Degradation

For these three cables, the $I_c(11 T)$ as measured at 4.2 K at BNL for extracted strands is given as a function of reaction temperature for 48 to 50 h durations in Fig. 6. Results are compared against round strand data. One can see that I_c degradation is usually contained, albeit not always reproducible. For instance in the case of cable 939R, which was deemed damaged after microscopic evaluation [7], the maximum I_c degradation ranged between 3% and 8%, which is very similar to that of cable 935R, which was of $\sim 5\%$. Cable 935R was not deemed damaged after microscopic analysis.

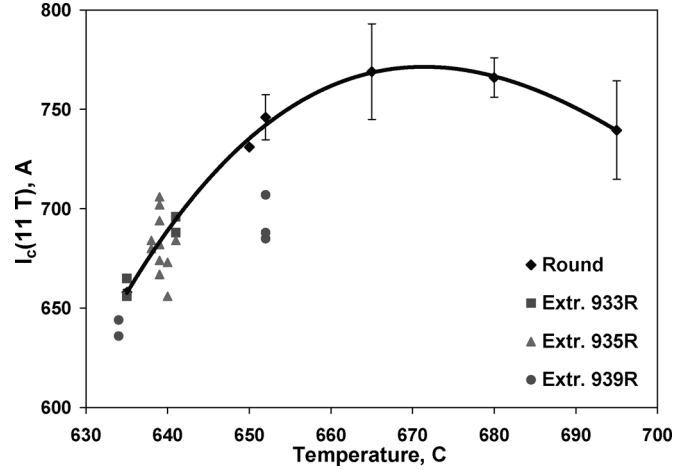


Fig. 6. $I_c(11 T)$ as measured at 4.2 K at BNL for strands extracted from three different cables as a function of reaction temperature for 48 to 50 h durations. Results are compared against round strand data.

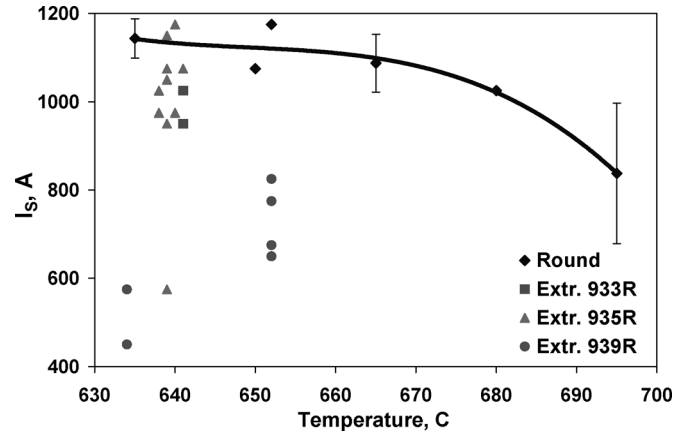


Fig. 7. I_S as measured at 4.2 K at BNL for strands extracted from three different cables as a function of reaction temperature for 48 to 50 h durations. Results are compared against round strand data.

B. Low Field Stability

The I_S as measured at 4.2 K at BNL for strands extracted from the three cables is given as a function of reaction temperature for 48 to 50 h durations in Fig. 7. Results are compared against round strand data. The RRR values obtained as the ratio of $R(295 K)$ and $R(18 K)$ for 20 cm long samples are shown in Fig. 8. The I_S and RRR values of extracted strands usually lie beneath the upper envelope defined by round strand data, and are not as reproducible as in round strands as the spread in results associated to a same temperature is usually larger for extracted strands, at least up to 680°C. It is also interesting to notice that the damage of cable 939R is best seen through the I_S degradation rather than through either I_c or RRR degradation. For this cable, I_S is reduced by a factor of 2 or larger in the extracted strands with respect to the round wires, whereas its RRR is not degraded more, if anything less, than in the other two non-damaged cables shown in figure.

To verify stability margins, the cables were measured at self-field with a SC transformer equipped with a Rogowski coil to measure the secondary current [9]. Cable test results are

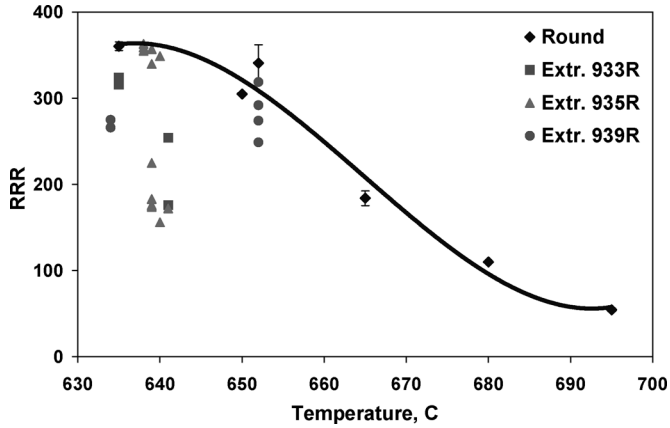


Fig. 8. RRR (averaged over the whole Cu area) as measured at BNL for strands extracted from three different cables as a function of reaction temperature for 48 to 50 h durations. Results are compared against round strand data.

TABLE IV
CABLE TEST RESULTS

Cable ID	Techn	Impreg	No.	Cable	Ave. I_q	Min. I_q	R_{splice}
	ology	nation	quenches	Ave. I_q , kA	strand, A	strand, A	$n\Omega$
926R (SQ)	MJR	Y	12	18.4	918	898	2.9
"	"	N	13	18.9	943	892	4.8
928R-B (TQ)	MJR	Y	12	19.8	734	697	3.1-3.9
"	"	N	16	19.7	729	688	2.3
928R-B (TQ)	"	N	14	20.4	755	732	2.8-3.2
932R-A (TQ)	"	N	14	23.5	869	851	2.5
935R (SR)	RRP	Y	18	18.1	906	807	2.7-2.5
"	"	N	16	18.7	935	878	2.9-3.1
942R (LR)	"	N	17	19.7	987	945	3.0-3.2
933R (TQ)	RRP	N	11	22.6	836	762	2.9-3.0
"	"	N	15	20.1	745	583	3.2-3.4
939R (TQ)	"	N	15	19.1	708	666	2.6-2.8
"	"	N	16	18.7	693	650	4.1-4.4
940R (TQ)	"	N	17	21.1	780	721	3.0
946R (TQ)	"	N	9	21.9	811	768	2.2-4
947R (TQ)	"	N	13	23.3	864	848	1.7

in Table IV. All of the cables in Table IV were reacted in the vicinity of 640°C. Cable tests are usually well reproducible, and there is a good consistency between the strand I_S and the cable quench currents.

VII. PREDICTION OF SHORT SAMPLE LIMITS

Witness samples are used to predict short sample limits (SSL) for coils, which are typically tested at 4.5 K. Round and extracted strand as well as cable samples were included as witnesses during reaction of quadrupoles TQS01 and TQC01, and of small racetrack SRS01. The former are made of four double-layer cos-theta coils, whose cable is made of 27 MJR strands. The latter is a small racetrack model to be used as technology transfer from LBNL to BNL. In this case the cable (ID 935R) is made of 20 RRP strands. For an accurate representation of the actual thermal cycles respectively seen by the coils and by the witness samples, type K calibrated thermocouples are placed in various locations.

Given a difference of up to ~9% at 11 T between average I_C values obtained at BNL and those obtained at FNAL for extracted strands belonging to the same billet, short sample limits

TABLE V
SHORT SAMPLE LIMIT PREDICTIONS

Magnet	I_q (FNAL), kA	I_q (BNL), kA	B_{peak} , T	G_s , T/m	I_q strands, A
SRS01	9.6	9.8	12.2-12.4	-	480-490
TQS01	12.1	12.3	11.1-11.3	217-220	448-455
TQC01	12.7	12.8	10.9-11.1	212-215	470-478

were calculated separately from FNAL and BNL data. Each I_C vs. B curve was parameterized using [8], and the critical surfaces for the cable were then obtained at 4.5 K. Billet blend was included in the prediction, the effect of self-field was not. Table V shows the SSL limit values.

VIII. SUMMARY

An RRP strand of 0.7 mm diameter is being used as work-horse material in the LARP Magnet R&D program. HT optimization studies showed that whereas the largest I_C 's are obtained at reaction temperatures between 660°C and 680°C, the largest I_S 's are found below 660°C. To provide a conservative margin to magnet operation, 640°C was chosen for LARP coil reaction. Effects of cabling were measured using strands extracted from all the produced cables. It was found that filament damage in a cable is best seen through I_S degradation rather than either I_C or RRR degradation. Cable tests at self field are usually in good consistency with strand I_S . Short sample limit predictions were obtained using witness samples for all fabricated magnets.

Through magnetization measurements, it was found that the I_C (1.8 K, 12 T) is a factor of 1.35 larger than I_C (4.2 K, 12 T). However, at low field flux jumps at 1.8 K are so large that they reduce the magnetization amplitude by about 30% compared to data at 4.2 K. This will be a concern for magnet operation in superfluid He, and prompts once again strand designs with smaller filament sizes.

ACKNOWLEDGMENT

The authors thank Lance Cooley for his contribution to the heat treatment studies.

REFERENCES

- [1] R. Bossert *et al.*, Development of LARP Technological Quadrupole (TQC) Magnets paper 1LK02, this Conference.
- [2] S. Caspi *et al.*, Fabrication and Test of TQS01—A 90 mm Nb₃Sn Quadrupole Magnet for LARP paper 4LX03, this Conference.
- [3] P. Wanderer *et al.*, Design of Nb₃Sn Coils for LARP Long Magnets paper 1LL01, this Conference.
- [4] F. Nobrega *et al.*, Fabrication and Test of 2-m Long Nb₃Sn Dipole Mirror Magnet paper 1LK08, this Conference.
- [5] E. Barzi *et al.*, Performance of Nb₃Sn RRP Strands and Cables Based on a 108/127 Stack Design Paper paper 4MW06, this Conference.
- [6] E. Barzi *et al.*, "Round and extracted Nb₃Sn strand tests for LARP magnet R&D," *IEEE Trans. Appl. Sup.*, vol. 16, no. 2, p. 319, June 2006.
- [7] D. R. Dietrich *et al.*, Cable R&D for LARP this Conference.
- [8] L. T. Summers *et al.*, "A model for the prediction of Nb₃Sn critical current as a function of field, temperature, strain and radiation damage," *IEEE Trans. Magn.*, vol. 27, no. 2, pp. 2041-2044, 1991.
- [9] D. Turrioni *et al.*, "Study of Nb₃Sn cable stability at self-field using a SC transformer," *IEEE Trans. Appl. Sup.*, vol. 15, no. 2, p. 1537, June 2005.