

Lawrence Berkeley National Laboratory

Materials Sciences

Title

Identification of nematic superconductivity from the upper critical field

Permalink

<https://escholarship.org/uc/item/48x8k0r6>

Journal

Physical Review B, 94(9)

ISSN

2469-9950

Authors

Venderbos, Jörn WF
Kozii, Vladyslav
Fu, Liang

Publication Date

2016-09-01

DOI

10.1103/physrevb.94.094522

Peer reviewed

Identification of nematic superconductivity from the upper critical field

Jörn W. F. Venderbos, Vladyslav Kozii, and Liang Fu

Department of Physics, Massachusetts Institute of Technology, Cambridge, MA 02139, USA

Recent nuclear magnetic resonance and specific heat measurements have provided concurring evidence of spontaneously broken rotational symmetry in the superconducting state of the doped topological insulator $\text{Cu}_x\text{Bi}_2\text{Se}_3$. This suggests that the pairing symmetry corresponds to a two-dimensional representation of the D_{3d} crystal point group, and that $\text{Cu}_x\text{Bi}_2\text{Se}_3$ is a nematic superconductor. In this work, we present a comprehensive study of the upper critical field H_{c2} of nematic superconductors within Ginzburg-Landau (GL) theory. Contrary to typical GL theories which have an emergent $U(1)$ rotational symmetry obscuring the discrete symmetry of the crystal, the theory of two-component superconductors in trigonal D_{3d} crystals reflects the true crystal rotation symmetry. This has direct implications for the upper critical field. First, H_{c2} of trigonal superconductors with D_{3d} symmetry exhibits a sixfold anisotropy in the basal plane. Second, when the degeneracy of the two components is lifted by, e.g., uniaxial strain, H_{c2} exhibits a twofold anisotropy with characteristic angle and temperature dependence. Our thorough study shows that measurement of the upper critical field is a direct method of detecting nematic superconductivity, which is directly applicable to recently-discovered trigonal superconductors $\text{Cu}_x\text{Bi}_2\text{Se}_3$, $\text{Sr}_x\text{Bi}_2\text{Se}_3$, $\text{Nb}_x\text{Bi}_2\text{Se}_3$, and $\text{Tl}_x\text{Bi}_2\text{Te}_3$.

I. INTRODUCTION

Unconventional superconductors can be defined by superconducting order parameters that transform nontrivially under crystal symmetries. For a given superconductor, possible unconventional order parameters are classified by non-identity representations of the crystal point group. Such representations are either one-dimensional or multi-dimensional, and this distinction defines two classes of unconventional superconductivity [1, 2]. The first class is exemplified by d -wave superconductors in cuprates [3, 4], while the second class is exemplified by the p -wave superconductivity in Sr_2RuO_4 [5], with two degenerate components (p_x, p_y) at the superconducting transition temperature. Superconducting states in the second class spontaneously break lattice or time-reversal symmetry [6], in addition to the $U(1)$ gauge symmetry, leading to novel thermodynamic and transport properties not seen in single-component superconductors. The search for new superconductors with multi-component order parameters is therefore of great interest.

The doped topological insulator $\text{Cu}_x\text{Bi}_2\text{Se}_3$, a superconductor with $T_c \sim 3.8\text{K}$ [7, 8], has recently attracted a lot of attention as a promising candidate for unconventional superconductivity [9–19]. Fu and Berg proposed that it may have an odd-parity pairing symmetry resulting from inter-orbital pairing in a strongly spin-orbit-coupled normal state [9]. While previous surface-sensitive experiments [20, 21] drew disparate conclusions regarding the nature of superconductivity in this material, direct tests of the pairing symmetry in the *bulk* of $\text{Cu}_x\text{Bi}_2\text{Se}_3$ are carried out only very recently. A nuclear magnetic resonance (NMR) measurement [22] found that despite the three-fold rotational symmetry of the crystal, the Knight shift displays a twofold anisotropy below T_c as the field is rotated in the basal plane. The twofold anisotropy is also found in the specific heat of the superconducting state under magnetic fields down to $H = 0.03\text{T}$ corresponding to $H/H_{c2} \sim 0.015$ [23]. Both

experiments found that the twofold anisotropy vanishes in the normal state, establishing that the superconducting state of $\text{Cu}_x\text{Bi}_2\text{Se}_3$ spontaneously breaks the three-fold rotational symmetry. This is only possible when the order parameter belongs to the two-dimensional E_u or E_g representation of the D_{3d} point group. The E_g pairing has been ruled out by comparing the theoretically expected gap structure [24] with specific heat data [8, 23]. These results taken together strongly suggest that the pairing symmetry of $\text{Cu}_x\text{Bi}_2\text{Se}_3$ is E_u , an odd-parity pairing with two-component order parameters [9].

Spontaneous rotational symmetry breaking due to superconductivity is a rare and remarkable phenomenon. Superconductors exhibiting rotational symmetry breaking from multi-component order parameters can be called nematic superconductors [24], in analogy with the nematic liquid crystals and nematic electronic states in non-superconducting metals [25, 26]. Nematic and chiral superconductivity, the latter breaking time-reversal symmetry, are the two distinct and competing states of multi-component superconductors, corresponding to real and complex order parameters respectively [1, 6]. Broken rotational symmetry has previously been reported in the heavy-fermion superconductor UPt_3 [29] under a magnetic field [28]. In addition, the A phase in a narrow temperature range at zero field is likely rotational symmetry breaking, which however may be due to antiferromagnetic order already present in the normal state [30, 31]. Thus the recent discovery of broken rotational symmetry in $\text{Cu}_x\text{Bi}_2\text{Se}_3$, without broken time-reversal symmetry, may potentially open a fruitful research direction.

Motivated by the recent experimental progress, in this work we study the upper critical field H_{c2} of trigonal nematic superconductors within the framework of Ginzburg-Landau (GL) theory. Such GL theory admits a new trigonal gradient term which is not allowed in hexagonal crystals [27]. We relate the gradient terms to Fermi surface and gap function anisotropies by a mi-

microscopic calculation of the GL coefficients. Building on and generalizing the previous work [27], we show that the upper critical field generically displays a sixfold anisotropy within the basal plane of trigonal crystals. We further show that a uniaxial strain acts as a symmetry-breaking field in nematic superconductors, which directly couples to the bilinear of the two-component superconducting order parameter. As a result, H_{c2} in the basal plane exhibits a twofold anisotropy with a distinctive angle and temperature dependence, similar to theoretically expected results for UPt₃ in the presence of antiferromagnetic order [46, 47]. Our findings suggest that measurement of the upper critical field is a direct method of detecting nematic superconductivity. In particular, this method may shed light on the pairing symmetries of other superconducting doped topological insulators Sr_xBi₂Se₃ [32, 33], Nb_xBi₂Se₃ [34] and Tl_xBi₂Te₃ [35], which have yet to be determined.

II. GINZBURG-LANDAU THEORY

We start by constructing the GL theory of odd-parity two-component superconductivity in crystals with D_{3d} point group and strong spin-orbit coupling. The pairing potential $\hat{\Delta}(\vec{k})$, which is a \vec{k} -dependent matrix in spin space, takes the following form

$$\hat{\Delta}(\vec{k}) = \eta_1 \hat{\Delta}_1(\vec{k}) + \eta_2 \hat{\Delta}_2(\vec{k}). \quad (1)$$

The pairing potential is a linear superposition of two degenerate components $\hat{\Delta}_{1,2}(\vec{k})$, the basis functions of the two-dimensional pairing channel E_u (specific gap functions are given in the Supplementary Material, Sec. III). For odd-parity superconductors the pairing components satisfy $\hat{\Delta}_{1,2}(-\vec{k}) = -\hat{\Delta}_{1,2}(\vec{k})$. As basis functions of E_u , the two partners $\hat{\Delta}_{1,2}(\vec{k})$ transform differently under the mirror symmetry $x \rightarrow -x$, i.e., $\hat{\Delta}_1(\vec{k})$ is even whereas $\hat{\Delta}_2(\vec{k})$ is odd. A key property of (doped) Bi₂Se₃ materials is strong spin-orbit coupling that locks the electron spin to the lattice. The two complex fields $\eta_{1,2}$ define the superconducting order parameters $\eta = (\eta_1, \eta_2)^T$. In contrast, in case of triplet superconductors in spin-rotation invariant materials the order parameter components are vectors in spin space.

The GL theory of two-component superconductivity is formulated in terms of the order parameters η and the GL free energy $F_{\text{tot}} = \int d^3\vec{x} f_{\text{tot}}$ is the sum of a homogeneous term and a gradient term given by $f_{\text{tot}} = f_{\text{hom}} + f_D$, where f_{hom} and f_D are the corresponding free energy densities. In addition, the free energy contains a Maxwell term $f_{\text{EM}} = (\vec{\partial} \times \vec{A})^2 / 8\pi$, which for our purposes can be taken as a constant. The free energy densities f_{hom} and f_D are polynomial expansions in the order parameter fields and their gradients, and consist of all terms invariant under the symmetry group of the crystal. For two-component trigonal superconductors the homogeneous

contribution is the same as the corresponding expression for hexagonal symmetry [1, 6],

$$f_{\text{hom}} = A\eta^\dagger\eta + B_1(\eta^\dagger\eta)^2 + B_2|\eta_1^*\eta_2 - \eta_2^*\eta_1|^2, \quad (2)$$

to fourth order in η , and we have defined $\eta^\dagger = (\eta_1^*, \eta_2^*)$. The coefficients $A \propto T - T_c$ and $B_{1,2}$ are phenomenological constants of the GL theory. The sign of GL coefficient B_2 determines the nature of the superconducting state, selecting either chiral or nematic order [24, 36].

Spatial variation of the superconducting order parameter is captured by the gauge-invariant gradient $D_i = -i\partial_i - qA_i$, with \vec{A} the electromagnetic vector potential and $q = -2e$. In case of multicomponent order parameters, there generally exist multiple independent gradient terms which are allowed by crystal symmetry. It is insightful to present all gradient terms in order of ‘‘emergent symmetry’’. For crystals with a principal rotation axis along the z direction, such as the three- and sixfold rotations of trigonal and hexagonal crystals, four gradient terms with full continuous in-plane rotational symmetry are present and given by [1, 38, 39]

$$\begin{aligned} f_D = & J_1(D_i\eta_a)^*D_i\eta_a + J_2\epsilon_{ij}\epsilon_{ab}(D_i\eta_a)^*D_j\eta_b \\ & + J_3(D_z\eta_a)^*D_z\eta_a + J_4[|D_x\eta_1|^2 + |D_y\eta_2|^2 \\ & - |D_x\eta_2|^2 - |D_y\eta_1|^2 + (D_x\eta_1)^*D_y\eta_2 + (D_y\eta_1)^*D_x\eta_2 \\ & + (D_x\eta_2)^*D_y\eta_1 + (D_y\eta_2)^*D_x\eta_1] \quad (3) \end{aligned}$$

(summation understood, $i = x, y$, $a = 1, 2$), and $J_{1,2,3,4}$ are the phenomenological GL coefficients. The first three terms are invariant under independent U(1) rotation of coordinates and order parameters, and thus have an emergent U(1) \times U(1) symmetry, whereas the gradient term with coefficient J_4 is invariant under arbitrary joint rotations of coordinates and order parameters, i.e., an emergent U(1) symmetry. Therefore, f_D does not reflect the discrete rotational symmetry of the crystal. However, a new gradient term $f_{D,\text{trig}}$, which we call trigonal gradient term, is uniquely present in crystals with trigonal symmetry, but not allowed in hexagonal crystals [27]. It is given by the expression

$$\begin{aligned} f_{D,\text{trig}} = & J_5[(D_z\eta_1)^*D_x\eta_2 + (D_z\eta_2)^*D_x\eta_1 \\ & + (D_z\eta_1)^*D_y\eta_1 - (D_z\eta_2)^*D_y\eta_2 + c.c.]. \quad (4) \end{aligned}$$

The appearance of this new gradient term, which has D_{3d} symmetry, can be understood from angular momentum, since in trigonal symmetry $L = 3$ is equivalent to $L = 0$. Indeed, in momentum space ($D_i \rightarrow q_i$) the trigonal gradient term can be expressed as $iq_z(q_-\eta_+^*\eta_- - q_+\eta_-^*\eta_+)$, where $q_\pm = q_x \pm iq_y$ and similarly for $\eta_{1,2}$. The relative phases between η_+ (q_+) and η_- (q_-) are determined by mirror symmetry: η_1 (η_2) is even (odd) under $x \rightarrow -x$. It follows from the structure of $f_{D,\text{trig}}$ that the spatial variation of the order parameter in the basal plane is coupled to spatial variation in the z -direction, which is in sharp contrast to hexagonal and tetragonal crystals.

In the rest of this work we map out the consequences of trigonal crystal anisotropy in the GL theory for the upper critical field.

III. UPPER CRITICAL FIELD IN THE BASAL PLANE

The angular dependence of H_{c2} was first proposed as a method to establish the multicomponent nature of unconventional superconductors in the context of heavy-fermion superconductors [41–43]. The key idea is as follows. For the class of single-component (e.g., s -wave) superconductors with trigonal, tetragonal, and hexagonal symmetry, H_{c2} is always isotropic within the GL theory, due to the emergence of $U(1)$ rotational symmetry to second order in the gradients. In case of multicomponent superconductors, effects of crystal anisotropy can appear in the GL theory, removing the emergent $U(1)$ symmetry, but this crucially depends on crystal symmetry. For instance, hexagonal systems with multicomponent order parameters do not show in-plane H_{c2} -anisotropy due to the emergent rotational symmetry of Eq. (3), whereas tetragonal symmetry can give rise to an angular dependence of H_{c2} with fourfold symmetry [42]. In trigonal crystals, H_{c2} can exhibit a sixfold anisotropy in the basal plane [27] as of Eq. (4). Here we map out the basal plane upper critical field of trigonal superconductors for general GL gradient coefficients.

Within GL theory, the upper critical field is calculated by solving the GL equations obtained from F_{tot} , keeping only terms linear in η since the order parameter is small at H_{c2} . Therefore, the calculation also applies to chiral superconductors. The resulting system of GL equations, which is given by

$$\begin{aligned} -A\eta_a &= J_1(D_x^2 + D_y^2)\eta_a + J_3D_z^2\eta_a + J_2\epsilon_{ab}[D_x, D_y]\eta_b \\ &+ J_4[(D_x^2 - D_y^2)\tau_{ab}^z + \{D_x, D_y\}\tau_{ab}^x]\eta_b \\ &+ J_5[\{D_z, D_x\}\tau_{ab}^x + \{D_z, D_y\}\tau_{ab}^z]\eta_b, \end{aligned} \quad (5)$$

can be solved as a two-component harmonic oscillator problem, leading to a Landau-level spectrum from which H_{c2} is determined as the lowest Landau-level solution. The coupling of the two harmonic oscillators is determined by the structure of the GL equations, and is in general complicated by the presence of multiple gradient terms. In hexagonal and tetragonal systems, straightforward or even exact analytical expressions for H_{c2} can be found [42]. In contrast, the trigonal gradient term

of Eq. (4) couples basal plane gradients to gradients in the orthogonal direction, giving rise to a different set of harmonic oscillator equations to which previous methods do not apply. A special limiting case was considered in Ref. 27. We generalize this result by solving the GL equations in the presence an in-plane magnetic field for general gradient coefficients. In deriving the general solution we adopt an operator based approach and exploit that harmonic oscillator mode operators corresponding different cyclotron frequencies can be related by squeezing operators. Here we present and discuss the main results, and give a detailed account of the lengthy calculations in the Supplemental Material (SM). For convenience, below we will refer to the appropriate section of the SM.

To demonstrate the key features of H_{c2} in trigonal crystals, we will focus the discussion on the most physical case, where trigonal anisotropy effects may be considered weak and J_5 can be treated as perturbation. We take the magnetic field \vec{H} in the basal plane to be given by $\vec{H} = H(\cos\theta, \sin\theta, 0)^T$, which corresponds to a vector potential $\vec{A} = Hz(\sin\theta, -\cos\theta, 0)^T$. It is convenient to rotate the basal plane GL gradients $D_{x,y} = -i\partial_{x,y} + 2eA_{x,y}$ according to the transformation

$$\begin{pmatrix} D_{\parallel} \\ D_{\perp} \end{pmatrix} = \begin{pmatrix} \cos\theta & \sin\theta \\ \sin\theta & -\cos\theta \end{pmatrix} \begin{pmatrix} D_x \\ D_y \end{pmatrix}, \quad (6)$$

such that D_{\parallel} is along the field and D_{\perp} is perpendicular to the field. These operators satisfy $[D_{\parallel}, D_{\perp}] = [D_{\parallel}, D_z] = 0$, and D_{\perp} and D_z define the magnetic algebra $[D_z, D_{\perp}] = -2ieH$. Writing Eq. (5) in terms of D_{\perp} and D_z , and setting $D_{\parallel}\eta_a = 0$ (i.e., no modulation along the field), one obtains

$$\begin{aligned} -A\eta_a &= (J_1D_{\perp}^2 + J_3D_z^2)\eta_a \\ &- J_4D_{\perp}^2(\cos 2\theta\tau_{ab}^z + \sin 2\theta\tau_{ab}^x)\eta_b \\ &+ J_5\{D_z, D_{\perp}\}(-\cos\theta\tau_{ab}^z + \sin\theta\tau_{ab}^x)\eta_b. \end{aligned} \quad (7)$$

Next, it is convenient to diagonalize the term proportional to J_4 . This is achieved by a the rotation of the order parameters given by

$$\begin{pmatrix} \eta_1 \\ \eta_2 \end{pmatrix} = \begin{pmatrix} \cos\theta & -\sin\theta \\ \sin\theta & \cos\theta \end{pmatrix} \begin{pmatrix} f_1 \\ f_2 \end{pmatrix}. \quad (8)$$

In terms of the rotated order parameters $(f_1, f_2)^T$ the GL equations read

$$-A \begin{pmatrix} f_1 \\ f_2 \end{pmatrix} = \begin{pmatrix} J_3D_z^2 + (J_1 - J_4)D_{\perp}^2 & 0 \\ 0 & J_3D_z^2 + (J_1 + J_4)D_{\perp}^2 \end{pmatrix} \begin{pmatrix} f_1 \\ f_2 \end{pmatrix} + J_5\{D_z, D_{\perp}\} \begin{pmatrix} -\cos 3\theta & \sin 3\theta \\ \sin 3\theta & \cos 3\theta \end{pmatrix} \begin{pmatrix} f_1 \\ f_2 \end{pmatrix}. \quad (9)$$

Note that only the term proportional to J_5 depends on

the angle θ . We now describe solutions to Eq. (56) ob-

tained by treating J_5 as a perturbation.

To start, let us consider taking both $J_4 = J_5 = 0$. Solving the GL equations then yields two degenerate series of Landau levels with cyclotron frequency $\omega = \sqrt{J_1 J_3}$, with the upper critical field given by $H_{c2} = -A/2e\omega = -A/2e\sqrt{J_1 J_3}$ (more details are provided in Sec. II B of the SM). Including the gradient contribution in Eq. (3) proportional to J_4 simply makes the cyclotron frequencies inequivalent, $\omega_{1,2} = \omega\sqrt{1 \mp |J_4|J_3/\omega^2} = \omega\sqrt{1 \mp |J_4|/J_1}$, and increases the upper critical field to $H_{c2} = -A/2e\omega_1$. This defines the exactly solvable unperturbed system. Then, introducing trigonal perturbation parametrized by J_5 couples the two series of Landau levels with different frequencies in a nontrivial way: the coupling of in-plane and out-of-plane gradients implies a coupling of canonically conjugate operators of the form $\{D_z, D_\perp\} \sim \{-i\partial_z, z\}$. To solve the system of GL equations we assume that crystal anisotropy effects are weak and use second order perturbation theory to obtain the correction to the cyclotron frequency $-\delta\omega_1$. (The calculations are lengthy and described in detail in Sec. II B 3 of the SM.) The upper critical field then becomes $H_{c2} = \tilde{H}_{c2}(1 + \delta\omega_1/\omega_1)$ with $\tilde{H}_{c2} \equiv -A/2e\omega_1$. We find H_{c2} to lowest order in J_5 as

$$\frac{H_{c2}(\theta)}{\tilde{H}_{c2}} = 1 + \frac{J_5^2}{2\omega_+^2} \left[\frac{\cos^2 3\theta}{(1 - \frac{\omega_-}{\omega_+})^2} + \frac{\sin^2 3\theta}{1 - \frac{\omega_-}{\omega_+}} F(\frac{\omega_-}{\omega_+}) \right], \quad (10)$$

where the frequencies ω_\pm are defined as $\omega_\pm = (\omega_2 \pm \omega_1)/2$. In the limit of small J_4/J_1 these frequencies become $\omega_+ \sim \omega$ and $\omega_- \sim \omega|J_4|/2J_1$. The function $F(x)$ arises due to the coupling of two series of Landau levels with different cyclotron frequencies and oscillator eigenfunctions. It takes the form

$$F(x) = \frac{(1-x^2)^{\frac{5}{2}}}{x^2} \sum_{m \geq 0}^{\infty} \frac{(2m)!}{(m!)^2 4^m} \frac{x^{2m} (2m - \frac{x^2}{1-x^2})^2}{2m + x(2m+1)} \\ = \frac{1-x}{x} \left[\sqrt{\frac{1+x}{1-x}} {}_2F_1\left(\frac{1}{2}, \frac{a}{2}; 1 + \frac{a}{2}; x^2\right) - 1 \right] \quad (11)$$

where $a = x/(1+x)$ and ${}_2F_1[\alpha, \beta; \delta; \gamma]$ is a hypergeometric function. The function $F(x)$ has the property $F(0) = 1$, which implies that for $J_4 = 0$ (corresponding to $\omega_-/\omega_+ = 0$) no angular dependence of H_{c2} exists. The latter is a consequence of an emergent rotational symmetry of $f_{D, \text{trig}}$ in Eq. (4): it is invariant under in-plane rotations of the order parameters and coordinates according to $q_+ \rightarrow q_+ e^{2i\varphi}$, $\eta_+ \rightarrow \eta_+ e^{-i\varphi}$. (Note that this is not a physical symmetry.)

In general, however, considering all regimes of gradient coefficients that satisfy the stability constraints of the free energy, H_{c2} exhibits a six-fold anisotropy in the basal plane of the crystal. For instance, the sixfold H_{c2} -anisotropy can be obtained starting from a solution of the GL equations derived from Eqs. (3) and (4) for $J_5 \neq 0$

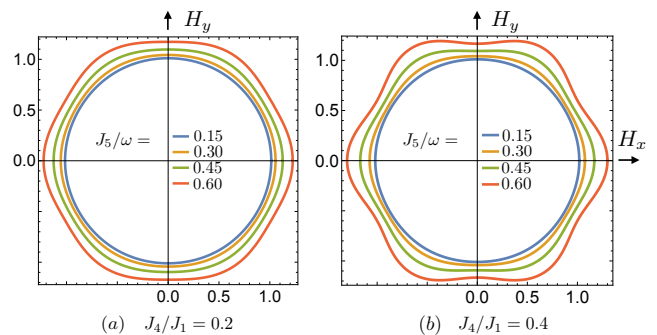


FIG. 1: Upper critical field (H_{c2}) anisotropy of two-component pairing in trigonal crystals with D_{3d} point group symmetry, originating from the trigonal GL anisotropy term (4). (a) Polar plot of the angular dependence of H_{c2} with six-fold symmetry given by Eq. (10) (normalized by \tilde{H}_{c2}) for $J_4/J_1 = 0.2$. Different curves correspond to $J_5/\omega = J_5/\sqrt{J_1 J_3} = (0.15, 0.30, 0.45, 0.60)$ (inward to outward). (b) Same as (a) but for $J_4/J_1 = 0.4$.

and $J_4 = 0$, and treating J_4 as a small perturbation. This case was considered in Ref. 27 and is described in Sec. II B 2 of the SM.

Figure 1 shows the angular dependence of the upper critical field for small to moderate $J_5/\omega = J_5/\sqrt{J_1 J_3}$ and J_4/J_1 as obtained from Eq. (10). Note that in general, for materials with weak to moderate (crystal) anisotropy effects, one expects $J_1 \sim J_3$. To make the interplay between J_4 and J_5 explicit, we expand Eq. (10) for small J_4/J_1 and find

$$\frac{H_{c2}(\theta)}{H_{c2}(\frac{\pi}{4})} = 1 + h \cos 6\theta, \quad (12)$$

where $h = 3|J_4|J_5^2/16J_1^2J_3$. This expression serves to highlight an important feature of the angular dependence of H_{c2} : $H_{c2}(\theta = \pi/2)/H_{c2}(\theta = 0) < 1$, which is independent of system specific parameters. Here $\theta = 0$ is defined by an axis orthogonal to a mirror plane.

Within weak coupling, the GL coefficients J_i can be obtained in terms of Fermi surface and gap function properties using a microscopic mean-field Hamiltonian with pairing potential $\hat{\Delta}(\vec{k})$ given by Eq. (1). The gradient coefficients J_1, J_3, J_4 , and J_5 are proportional to $N(\varepsilon_F)v_F^2/T_c^2 \sim N(\varepsilon_F)\xi_0^2$, where ε_F , v_F , and ξ_0 are the Fermi energy, Fermi velocity, and correlation length respectively, and $N(\varepsilon_F)$ is the density of states. (The calculations are presented in detail in Sec. III of the SM.) We find that their relative strength depends on the crystal anisotropy of the Fermi surface and of the gap functions $\hat{\Delta}_{1,2}(\vec{k})$. In particular, J_5 is nonzero only when trigonal Fermi surface anisotropy is present, or when the gap function is composed of trigonal crystal spherical harmonics of the E_u pairing channel (see Sec. III A of the SM), and is generally expected to be weak.

The general sixfold basal plane anisotropy of H_{c2} is a direct consequence of trigonal symmetry and a discrim-

inating characteristic of two-component pairing symmetry. Indeed, single-component superconductivity corresponding to one-dimensional pairing channels of point group D_{3d} cannot exhibit sixfold H_{c2} anisotropy: the in-plane gradient term is given by $\tilde{J}_1 |D_i \psi|^2$ and has emergent U(1) rotational symmetry. As a result, the sixfold anisotropy provides a clear experimental evidence for two-component pairing.

IV. NEMATIC SUPERCONDUCTIVITY AND UPPER CRITICAL FIELD

Within our GL theory, the rotational symmetry breaking superconducting state reported in Refs. [22, 23] corresponds to a *real* order parameter, i.e., $\eta = \eta_0(\cos \phi, \sin \phi)^T$. Up to fourth order [see Eq. (2)], the angle ϕ represents a continuous degeneracy. This degeneracy is lifted at sixth order by a crystal anisotropy term and leads to a discrete set of degenerate ground states [24, 36]. In materials, such as $\text{Cu}_x\text{Bi}_2\text{Se}_3$, the remaining degeneracy may be further lifted by a symmetry-breaking pinning field, selecting a unique ground state. The origin of such pinning can be strain-induced distortions of the crystal [37], but in principle, any order with the same symmetry, electronic or structural, can pin the order parameter. In case of two-component superconductors, the symmetry-breaking (SB) pinning field couples *linearly* to order parameter η in the following way

$$f_{\text{SB}} = g [(u_{xx} - u_{yy})(|\eta_1|^2 - |\eta_2|^2) + 2u_{xy}(\eta_1^* \eta_2 + \eta_2^* \eta_1)], \quad (13)$$

with coupling constant g . The order parameter bilinears ($|\eta_1|^2 - |\eta_2|^2, \eta_1^* \eta_2 + \eta_2^* \eta_1$) constitute a two-component subsidiary nematic order parameter [24] with the same symmetry as the symmetry-breaking field ($u_{xx} - u_{yy}, 2u_{xy}$). For comparison, uniaxial strain in single-component superconductors couples to the gradient of the order parameter ψ , taking the form $\tilde{J}_{1,x} |D_x \psi|^2 + \tilde{J}_{2,y} |D_y \psi|^2$ different from Eq. (13). It is worth noting that the coupling considered here differs from the candidate theories proposed for the hexagonal superconductor UPt_3 , in which case magnetic order couples quadratically, instead of linearly, to order parameter bilinears [29, 31, 38, 39, 44, 45].

From a microscopic perspective, the origin of the order parameter pinning in Eq. (13) can be understood as a (strain-induced) Fermi surface distortion, leading to different Fermi velocities $v_{F,x} \neq v_{F,y}$. A uniaxial distortion of this form couples to $|\eta_1|^2 - |\eta_2|^2$ and has the effect of selecting either $\eta = (1, 0)$ or $\eta = (0, 1)$ by raising T_c , resulting in a split transition. A quantitative calculation of the coupling constant g , relating the order parameter bilinear to such Fermi surface distortion can be obtained within weak-coupling (see [40]). This effect of a Fermi surface distortion should be compared to uniaxial gradient anisotropies such as $\sim |D_x \eta_a|^2 - |D_y \eta_a|^2$ and $\sim |D_x \eta_1|^2 - |D_y \eta_2|^2$, with the effect of the former being

enhanced by a factor of $\ln(\omega_D/T_c)(\xi/\xi_0)^2$ [40], where ξ is the coherence length, $\ln \omega_D/T_c \sim 1/VN(\varepsilon_F)$, ω_D is a cutoff frequency, and V is an effective interaction energy scale associated with the pairing. In addition, the effect of a uniaxial Fermi surface distortion $\sim v_{F,x}/v_{F,y}$ on the shift of T_c is enhanced by $\ln \omega_D/T_c$.

To address the effect of the SB field on H_{c2} in case of the trigonal nematic superconductors, we solve the linearized GL equations for small $J_{4,5}$ gradient coefficients in the presence of a uniaxial symmetry breaking term defined as $\delta(|\eta_1|^2 - |\eta_2|^2)$, taking δ as a measure of the uniaxial anisotropy. Here we focus the discussion on the most salient features, for which we take $J_5 = 0$, and relegate a more detailed account to the SM. A similar problem of upper critical field anisotropy was studied for split transitions in UPt_3 [46, 47].

Setting $J_5 = 0$ in Eq. (7) and adding the contribution from the symmetry breaking field, the GL equations take the form

$$\begin{aligned} -A\eta_a &= (J_1 D_\perp^2 + J_3 D_z^2)\eta_a + \delta\tau_{ab}^z \eta_b \\ &\quad - J_4 D_\perp^2 (\cos 2\theta \tau_{ab}^z + \sin 2\theta \tau_{ab}^x) \eta_b. \end{aligned} \quad (14)$$

The upper critical field is obtained by using the magnetic algebra of D_z and D_\perp , and projecting into the lowest Landau level. The upper critical field is then determined from the following implicit equation (see Sec. II D of the SM)

$$\frac{-A}{\omega} = \frac{1}{l_b^2} - \sqrt{\frac{J_4^2 J_3^2}{4\omega^4 l_b^4} + \frac{\delta^2}{\omega^2} - \frac{J_4 J_3 \delta}{\omega^3 l_b^2} \cos 2\theta}, \quad (15)$$

(recall $\omega = \sqrt{J_1 J_3}$) where the magnetic length l_b is defined as $2eH = 1/l_b^2$. For $\delta = 0$ we recover the result for $J_5 = 0$ in Eq. (10), to first order in J_4/J_1 (i.e., ω_1 expanded to first order in J_4/J_1). For $J_4 = 0$ we simply find $H_{c2} = H_{c2,0}$ [see Eq. (12)], but with critical temperature $T_c^* = T_c + \Delta T_c$ with $\Delta T_c \sim |\delta|$. This follows from comparing δ to $A \sim (T - T_c)$, i.e., δ shifts the transition temperature and can be taken as a measure of T . We define a dimensionless temperature t by $T = T_c^* - t\Delta T_c$.

For general J_4/J_1 and nonzero δ we solve Eq. (15) for H_{c2} and show the representative results for $J_4/J_1 = 0.1$ and $J_4/J_1 = 0.6$ in Figs. 2(a) and 2(b). Two key characteristics of H_{c2} in the presence of a pinning field are evident in Fig. 2(a)–(b). First, the angular dependence of H_{c2} exhibits a distinct two-fold anisotropy, with a typical “peanut”-shape close to T_c^* . This twofold anisotropy becomes more pronounced with increasing J_4/J_1 , as shown Fig. 2(b). Expanding the square root in Eq. (15) under the assumption of very small fields, i.e., $l_b^2 \gg J_4 J_3 / 2\omega\delta$, one finds $H_{c2} \propto (1 - J_4 \text{sgn}(\delta) \cos 2\theta / 2J_1)$ (see Sec. II D of the SM). This “peanut”-shape of the H_{c2} profile should be contrasted with the H_{c2} profile of single-component superconductor where uniaxial gradient anisotropy leads to a weak *elliptical* angular dependence of H_{c2} , an effect which is parametrically smaller than the twofold anisotropy in the two-component case. Consequently,

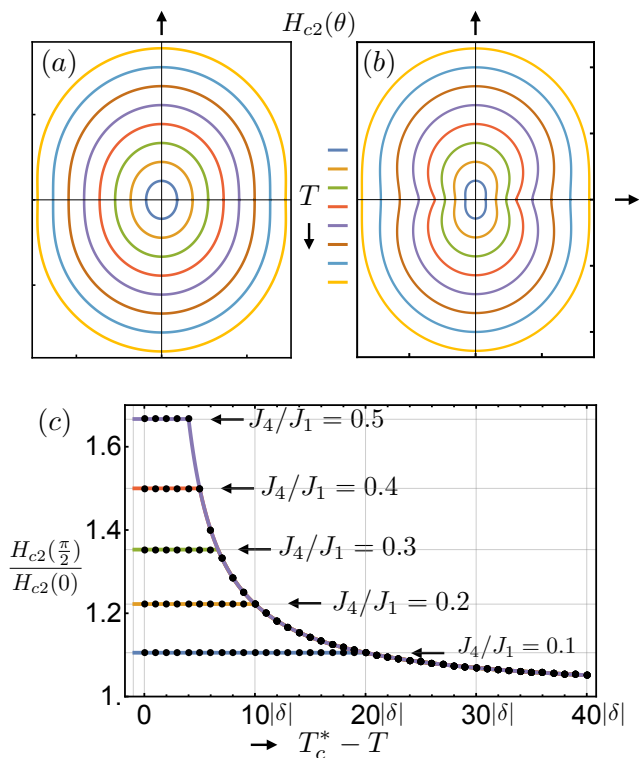


FIG. 2: (a) Polar plot of the angular dependence of H_{c2} in the presence of a symmetry-breaking field δ for $J_4/J_1 = 0.1$, calculated using Eq. (15) (in arbitrary units of H). Different curves represent different temperatures: $T = T_c^* - t\Delta T_c$ (recall that $\Delta T_c \sim |\delta|$), where $t = 1, \dots, 8$ and the outermost curve corresponds to $t = 8$. (b) Same as in (a) but for relatively large $J_4/J_1 = 0.6$. Figure (b) clearly shows the two-fold “peanut”-shape anisotropy expected for two-component superconductors in the presence of a symmetry breaking field. (c) Plot of the H_{c2} -anisotropy coefficient $H_{c2}(\pi/2)/H_{c2}(0)$ as function of effective temperature t for various values of J_4/J_1 . The horizontal grid lines correspond to the values $(1 + J_4/2J_1)/(1 - J_4/2J_1)$.

the twofold anisotropy of H_{c2} shown in Fig. 2, in particular the “peanut”-shape, is a discriminating property of two-component pairing.

Second, the angular dependence of H_{c2} is a function of temperature and has different shape in the vicinity of T_c^* (i.e., small fields) as compared to far below T_c (and high fields). This is in sharp contrast to the usual case, for instance Eq. (10), where only the overall magnitude of H_{c2} is temperature dependent. The unusual temperature dependence of H_{c2} can be more precisely captured by considering the upper critical field anisotropy ratio $H_{c2}(\pi/2)/H_{c2}(0)$ as function of temperature. In the vicinity of T_c^* , the anisotropy ratio should exhibit temperature independent behavior given by $\sim (1 + J_4 \text{sgn}(\delta)/2J_1)/(1 - J_4 \text{sgn}(\delta)/2J_1)$ (see Sec. II D of the SM). This is shown in Fig. 2(c), where the H_{c2} -

anisotropy ratio is plotted for various values of J_4/J_1 . In contrast, using Eq. (15) we find that the H_{c2} -anisotropy ratio approaches unity for large temperature t according to $\sim 2/(t - 1)$, which is independent of GL parameters. Within the model of Eq. (15), the temperature at which the transition between two behaviors occurs is given by $t = 2J_1/|J_4|$. This “kink” feature was also found and discussed in the context of a hexagonal applicable to UPt_3 [46–48]. The distinctive temperature dependence of H_{c2} -anisotropy is uniquely associated with two-component pairing since single-component pairing with uniaxial gradient anisotropy leads to temperature independent H_{c2} -anisotropy.

V. DISCUSSION AND CONCLUSION

To summarize, in this work we have addressed the magnetic properties of two-component superconductors in trigonal crystals with point group D_{3d} symmetry. Starting from a general GL theory of trigonal two-component superconductors, we find that the upper critical field exhibits a *sixfold* anisotropy in the basal plane, which is a discriminating property of two-component pairing. The sixfold anisotropy is a rare manifestation of discrete crystal symmetry, since effects of crystal anisotropy are typically obscured in GL theory by an emergent $U(1)$ rotational symmetry. In addition, in this work we show that when a symmetry breaking field originating from, e.g., structural distortions selects a *real* order parameter, H_{c2} exhibits a twofold anisotropy with characteristic angular and temperature dependence.

The recent NMR and specific heat measurements on $\text{Cu}_x\text{Bi}_2\text{Se}_3$, which reported spontaneously broken rotational symmetry, indicate that this material belongs to the class of superconductors with two-component pairing symmetry. Prominent other examples of materials with trigonal symmetry, which have attracted increasing attention recently, are the doped Bi_2Se_3 superconductors $\text{Sr}_x\text{Bi}_2\text{Se}_3$, $\text{Nb}_x\text{Bi}_2\text{Se}_3$, and $\text{Tl}_x\text{Bi}_2\text{Te}_3$. Our theory of in-plane anisotropy of upper critical field stands to contribute to uncovering the pairing symmetry of these superconductors, which remains to be determined.

VI. ACKNOWLEDGMENTS

We thank Anne de Visser, Shingo Yonezawa, Yoshi Maeno for discussions. This work is supported by the David and Lucile Packard Foundation (L.F.), the DOE Office of Basic Energy Sciences, Division of Materials Sciences and Engineering under Award No. DE-SC0010526 (V.K.), and the Netherlands Organization for Scientific Research (NWO) through a Rubicon grant (J.V.).

-
- [1] M. Sigrist and K. Ueda, *Rev. Mod. Phys.* **63**, 239 (1991).
- [2] V. Mineev and K. Samokhin, *Introduction to Unconventional Superconductivity*, (Gordon and Breach, New York, 1999).
- [3] D. J. Van Harlingen, *Rev. Mod. Phys.* **67**, 515 (1995).
- [4] C. C. Tsuei and J. R. Kirtley, *Rev. Mod. Phys.* **72**, 969 (2000).
- [5] A. Mackenzie and Y. Maeno, *Rev. Mod. Phys.* **75**, 657 (2003).
- [6] G. E. Volovik and L. Gork'ov, *Sov. Phys. JETP* **61**, 843 (1985).
- [7] Y. S. Hor, A. J. Williams, J. G. Checkelsky, P. Roushan, J. Seo, Q. Xu, H. W. Zandbergen, A. Yazdani, N. P. Ong, R. J. Cava, *Phys. Rev. Lett.* **104**, 057001 (2010).
- [8] M. Kriener, Kouji Segawa, Zhi Ren, Satoshi Sasaki, and Yoichi Ando, *Phys. Rev. Lett.* **106**, 127004 (2011).
- [9] L. Fu and E. Berg, *Phys. Rev. Lett.* **105**, 097001 (2010).
- [10] L. Hao and T. K. Lee, *Phys. Rev. B* **83**, 134516 (2011).
- [11] T. V. Bay, T. Naka, Y. K. Huang, H. Luigjes, M. S. Golden, and A. de Visser, *Phys. Rev. Lett.* **108**, 057001 (2012).
- [12] Y. Nagai, H. Nakamura, and M. Machida, *Phys. Rev. B* **86**, 094507 (2012).
- [13] B. J. Lawson, Y. S. Hor, and L. Li, *Phys. Rev. Lett.* **109**, 226406 (2012).
- [14] T. Hashimoto, K. Yada, A. Yamakage, M. Sato, and Y. Tanaka, *J. Phys. Soc. Jpn.* **82**, 044704 (2013).
- [15] S.-K. Yip, *Phys. Rev. B* **87**, 104505 (2013).
- [16] X. Wan and S. Y. Savrasov, *Nat. Comm.* **5**, 4144 (2014).
- [17] P. M. R. Brydon, S. Das Sarma, H.-Y. Hui, J. D. Sau, *Phys. Rev. B* **90**, 184512 (2014).
- [18] J. A. Schneeloch, R. D. Zhong, Z. J. Xu, G. D. Gu, and J. M. Tranquada, *Phys. Rev. B* **91**, 144506 (2015).
- [19] Y. Ando and L. Fu, *Ann. Rev. Condens. Mater. Phys.* **6**, 361 (2015).
- [20] S. Sasaki, M. Kriener, K. Segawa, K. Yada, Y. Tanaka, M. Sato, and Y. Ando, *Phys. Rev. Lett.* **107**, 217001 (2011).
- [21] N. Levy, T. Zhang, J. Ha, F. Sharifi, A. A. Talin, Y. Kuk, and J. A. Stroscio, *Phys. Rev. Lett.* **110**, 117001 (2013).
- [22] K. Matano, M. Kriener, K. Segawa, Y. Ando, and Guoqing Zheng, arXiv:1512.07086 (2015).
- [23] S. Yonezawa, K. Tajiri, S. Nakata, Y. Nagai, Z. Wang, K. Segawa, Y. Ando, and Y. Maeno, arXiv:1602.08941 (2016).
- [24] Liang Fu, *Phys. Rev. B* **90**, 100509(R) (2015).
- [25] S. A. Kivelson, E. Fradkin, and V. J. Emery, *Nature* **393**, 550-553 (1998).
- [26] E. Fradkin, S. A. Kivelson, M. J. Lawler, J. P. Eisenstein, A. P. Mackenzie, *Annu. Rev. Condens. Matter Phys.* **1**, 153 (2010).
- [27] P. L. Krotkov, and V. P. Mineev, *Phys. Rev. B* **65**, 224506 (2002).
- [28] Y. Machida, A. Itoh, Y. So, K. Izawa, Y. Haga, E. Yamamoto, N. Kimura, Y. Onuki, Y. Tsutsumi, and K. Machida, *Phys. Rev. Lett.* **108**, 157002 (2012).
- [29] R. Joynt and L. Taillefer, *Rev. Mod. Phys.* **74**, 235 (2002).
- [30] R. A. Fisher, S. Kim, B. F. Woodfield, N. E. Phillips, L. Taillefer, K. Hasselbach, J. Flouquet, A. L. Giorgi, and J. L. Smith, *Phys. Rev. Lett.* **62**, 1411 (1989).
- [31] G. Aeppli, E. Bucher, C. Broholm, J. K. Kjems, J. Baumann, and J. Hufnagl, *Phys. Rev. Lett.* **60**, 615 (1988).
- [32] Zhongheng Liu, Xiong Yao, Jifeng Shao, Ming Zuo, Li Pi, Shun Tan, Changjin Zhang, Yuheng Zhang, *J. Am. Chem. Soc.* **137**, 10512 (2015).
- [33] Shruti, V. K. Maurya, P. Neha, P. Srivastava, and S. Patnaik, *Phys. Rev. B* **92**, 020506(R) (2015).
- [34] Y. Qiu, K. Nocona Sanders, J. Dai, J. E. Medvedeva, W. Wu, P. Ghaemi, T. Vojta, Y. S. Hor, arXiv:1512.03519 (2015).
- [35] Z. Wang, A. A. Taskin, T. Frölich, M Braden, and Y. Ando, *Chem. Mater.* **28**, 779 (2016).
- [36] J. W. F. Venderbos, V. Kozii, L. Fu, arXiv:1512.04554 (2015).
- [37] C. W. Hicks, D. O. Brodsky, E. A. Yelland, A. S. Gibbs, J. A. N. Bruin, M. E. Barber, S. D. Edkins, K. Nishimura, S. Yonezawa, Y. Maeno, A. P. Mackenzie, *Science* **344**, 283 (2014).
- [38] J. A. Sauls, *Adv. Phys.* **43**, 113 (1994).
- [39] I. A. Luk'yanchuk, M. E. Zhitomirsky, *Superconductivity Review* **1**, 207 (1995).
- [40] See Supplemental Material at ...
- [41] L. P. Gor'kov, *Zh. Eksp. Teor. Fiz.* **40**, 351 (1984) [*JETP Lett.* **40**, 1155 (1984)].
- [42] L. I. Burlachkov, *Zh. Eksp. Teor. Fiz.* **89**, 1382 (1985) [*Sov. Phys. JETP* **62**, 800 (1985)].
- [43] K. Machida, T. Ohmi, and M. Ozaki, *J. Phys. Soc. Jpn.* **54**, 1552 (1985).
- [44] D. Hess, T. Tokuyasu, and J. A. Sauls, *J. Phys. Condens. Matter* **1**, 8135 (1989).
- [45] K. Machida and M. Ozaki, *J. Phys. Soc. Jpn.* **58**, 2244 (1989).
- [46] D. F. Agterberg and M. B. Walker, *Phys. Rev. B* **51**, 8481 (1994).
- [47] D. F. Agterberg and M. B. Walker, *Phys. Rev. Lett.* **74**, 3904 (1995).
- [48] J. A. Sauls, *Phys. Rev. B* **53**, 8543 (1996).

Supplemental material for “Identification of nematic superconductivity from the upper critical field”

Jörn W. F. Venderbos, Vladyslav Kozii, and Liang Fu
Department of Physics, Massachusetts Institute of Technology, Cambridge, MA 02139, USA

VII. LANDAU THEORY OF TRIGONAL TWO-COMPONENT SUPERCONDUCTORS

A Ginzburg-Landau (GL) theory of two-component superconductivity in a trigonal crystal with D_{3d} point group symmetry is formulated in terms of the superconducting order parameters, which in turn are obtained from pairing potential. In the presence of spin-orbit coupling, when spin-rotation symmetry is broken, and the symmetry group is the symmetry group D_{3d} of the crystal lattice, the superconducting pairing potential $\hat{\Delta}(\vec{k})$ is decomposed into irreducible representations of D_{3d} . In most cases, one is interested in a single pairing channel, i.e., a single representation of the symmetry group, which may be one- or multi-dimensional. The pairing matrix $\hat{\Delta}(\vec{k})$ corresponding to pairing channel Γ takes the form [1–3]

$$\hat{\Delta}(\vec{k}) = \sum_m \eta_{\Gamma,m} \hat{\Delta}_{\Gamma,m}(\vec{k}), \quad (16)$$

where Γ labels the representation (i.e., pairing channel) and m labels the components of the representation. The expansion coefficients $\eta_{\Gamma,m}$ are the superconducting order parameters and are complex scalars. In case of two-component superconductors the order parameter is the two-component complex number $\eta \equiv (\eta_1, \eta_2)^T$.

The GL free energy functional describing the two-component superconductor is then obtained as an expansion in the order parameters $\eta_{1,2}$ to given order,

$$F_{\Gamma}[\eta] = \int d^3\vec{x} f_0 + \int d^3\vec{x} \left(A(T) \sum_m |\eta_{\Gamma,m}|^2 + f^{(2n>2)} \right), \quad (17)$$

which consists of terms fully invariant under the symmetries of the crystal. Therefore, the GL free energy depends on the crystal symmetry group as well as the pairing channel. A trigonal crystal with D_{3d} point group symmetry admits two two-component representations, E_g (even parity) and E_u (odd parity), and in both cases the free energy density up to fourth order is given by

$$f = F/V = A(|\eta_1|^2 + |\eta_2|^2) + B_1(|\eta_1|^2 + |\eta_2|^2)^2 + B_2|\eta_1^*\eta_2 - \eta_1\eta_2^*|^2, \quad (18)$$

in terms of the expansion coefficients $A \propto (T - T_c)$ and $B_{1,2}$. When the GL coefficient B_2 is positive ($B_2 > 0$) the order parameter η is real and breaks rotational symmetry. In that case, a continuous degeneracy remains at fourth order, which is lifted by crystal anisotropy effects at sixth order. The sixth order contribution to the free energy density reads as

$$f^{(6)} = C_1[(\eta_+^*\eta_-)^3 + (\eta_-^*\eta_+)^3] + C_2(|\eta_1|^2 + |\eta_2|^2)^3 + C_3(|\eta_1|^2 + |\eta_2|^2)|\eta_1^*\eta_2 - \eta_1\eta_2^*|^2, \quad (19)$$

(where $\eta_{\pm} = \eta_1 \pm i\eta_2$) and it is the first term, proportional to C_1 , which is responsible for lifting the continuous degeneracy and selecting three degenerate ground states related by threefold rotation.

We extend the GL theory to include terms representing spatial inhomogeneity: the gradient terms. The superconductor is a charged superfluid with charge $q = -2e$, and gradient terms are introduced by defining the covariant derivative as $D_i = -i\partial_i - qA_i$, where A_i is the electromagnetic vector potential.

The gradient terms of the free energy expansion are obtained using the same representation theory recipe as before. The derivative components (D_x, D_y) transform as E_u , and D_z transforms as A_{2u} of the D_{3d} point group. These representations are used to form products with (η_1, η_2) , from which bilinears with the general structure

$$D_i X_{ia} \eta_a, \quad (20)$$

are obtained. Here X_{ia} is a tensor transforming irreducibly under crystal symmetry (see Table I). A gradient term is then simply given by $|D_i X_{ia} \eta_a|^2$, with an independent phenomenological stiffness constant for each distinct representation.

We now discuss all gradient terms of an odd-parity two-component superconductor in a trigonal crystal with D_{3d} symmetry. We start from the gradient terms which have a continuous U(1) rotational symmetry with respect to the

Symmetry	Irreducible tensor X_{ia}	$D_i X_{ia} \eta_a$	$\times A_{1g}$	$\times A_{2g}$	$\times E_g$
A_{1g}	$\tau_{ia}^0 = \delta_{ia}$	$D_x \eta_1 + D_y \eta_2$	A_{1g}	A_{2g}	E_g
A_{2g}	τ_{ia}^y	$-i(D_x \eta_2 - D_y \eta_1)$	A_{2g}	A_{1g}	E_g
E_g	$(\tau_{ia}^x, \tau_{ia}^z)$	$(D_x \eta_2 + D_y \eta_1, D_x \eta_1 - D_y \eta_2)$	E_g	E_g	$A_{1g} + A_{2g} + E_g$
E_g	$\delta_{iz}(\delta_{1a}, \delta_{2a})$	$(D_z \eta_1, D_z \eta_2)$	E_g	E_g	$A_{1g} + A_{2g} + E_g$

TABLE I: Table listing the gradients terms present in a trigonal crystal with D_{3d} point group symmetry. On the left the irreducible tensors X_{ia} and corresponding bilinears are shown. On the right, a multiplication table of D_{3d} representations is presented. This table assumes (η_1, η_2) have E_u symmetry, but the results for E_g are obtained by exchanging the symmetry labels $g \leftrightarrow u$.

coordinates and order parameters individually, thus giving rise to an emergent $U(1) \times U(1)$ symmetry. They are given by

$$f_{D,U(1) \times U(1)} = J_1(D_i \eta_a)^* D_i \eta_a + J_2 \epsilon_{ij} \epsilon_{ab} (D_i \eta_a)^* D_j \eta_b + J_3 (D_z \eta_a)^* D_z \eta_a, \quad (21)$$

with gradient coefficients J_i (and a sum over repeated i, j and a, b is understood, and $i, j = x, y$). As a result of the emergent $U(1) \times U(1)$ symmetry, these gradient terms obscure the true discrete crystal rotation symmetry.

Whether or not the true crystal symmetry is reflected in the GL gradient expansion of multicomponent order parameters depends on the crystal system. For instance, in case of hexagonal symmetry (i.e., point group D_{6h}) the gradient terms are obtained by considering all irreducible tensors X_{ia} of the hexagonal group. For the two-component representations $E_{1u,1g}$ the gradient terms are given by [2]

$$f_D = K_1 |D_x \eta_1 + D_y \eta_2|^2 + K_2 |D_x \eta_2 - D_y \eta_1|^2 + K_3 (|D_x \eta_1 - D_y \eta_2|^2 + |D_x \eta_2 + D_y \eta_1|^2) + K_4 (|D_z \eta_1|^2 + |D_z \eta_2|^2). \quad (22)$$

A very similar result is obtained for the $E_{2u,2g}$ representations. This can be rewritten to obtain (see also, e.g., [4, 5])

$$f_{D,U(1) \times U(1)} [J_1, J_2, J_3] + f_{D,4} [J_4] = J_1 (D_i \eta_a)^* D_i \eta_a + J_2 \epsilon_{ij} \epsilon_{ab} (D_i \eta_a)^* D_j \eta_b + J_3 (D_z \eta_a)^* D_z \eta_a + J_4 (\tau_{ij}^z \tau_{ab}^z + \tau_{ij}^x \tau_{ab}^x) (D_i \eta_a)^* D_j \eta_b, \quad (23)$$

where summation over repeated indices is understood. The gradient constants K_α and J_α are related by

$$J_1 = \frac{K_1 + K_2}{2} + K_3, \quad J_2 = \frac{K_1 + K_2}{2} - K_3, \quad J_3 = K_4, \quad J_4 = \frac{K_1 - K_2}{2}. \quad (24)$$

The term proportional to J_4 has an emergent $U(1)$ rotational symmetry: it is invariant under *joint* rotations of coordinates and order parameters. (Note that the J_4 gradient term for $E_{2u,2g}$ symmetry is given by $(\tau_{ij}^z \tau_{ab}^z - \tau_{ij}^x \tau_{ab}^x) (D_i \eta_a)^* D_j \eta_b$, which also possesses an emergent $U(1)$ symmetry.) Consequently, effects of crystal symmetry do not appear in the GL theory of hexagonal two-component superconductors.

When crystal symmetry is lowered to trigonal D_{3d} symmetry, an additional gradient term arises which reflects the true D_{3d} symmetry of the crystal. Table I lists all irreducible tensors X_{ia} and their symmetries. With the help of this table it is straightforward to obtain all gradient terms. One observes that there are two distinct tensors with E_g symmetry. As a result, a cross term of these two is an allowed gradient term. Specifically, the additional gradient term, defined as $f_{D,\text{trig}} [J_5]$ and referred to as trigonal anisotropy (gradient) term, takes the form [8]

$$\begin{aligned} f_{D,\text{trig}} [J_5] &= J_5 [(D_x \eta_2)^* D_z \eta_1 + (D_x \eta_1)^* D_z \eta_2 + (D_y \eta_1)^* D_z \eta_1 - (D_y \eta_2)^* D_z \eta_2 + c.c.], \\ &= J_5 [\tau_{ab}^x (D_x \eta_a)^* D_z \eta_b + \tau_{ab}^z (D_y \eta_a)^* D_z \eta_b + c.c.]. \end{aligned} \quad (25)$$

The new gradient term is a consequence of trigonal anisotropy and is absent in hexagonal crystals, as is clear from Eq. (23). This is rooted in the fact that in trigonal crystals (i.e., only threefold rotations) angular momenta $L = 0$ and $L = 3$ are equivalent, whereas in hexagonal crystals with sixfold rotations these belong to distinct representations.

In momentum space ($D_i \rightarrow q_i$) the trigonal gradient term can be expressed as $i q_z (q_- \eta_+^* \eta_- - q_+ \eta_-^* \eta_+)$, where $q_\pm = q_x \pm i q_y$ and similarly for $\eta_{1,2}$. The relative phases between η_+ (q_+) and η_- (q_-) are determined by mirror symmetry: η_1 (η_2) is even (odd) under $x \rightarrow -x$. Even though the trigonal gradient term has D_{3d} symmetry, and breaks the $U(1)$ symmetry of Eq. (23), it possesses an emergent rotational symmetry: it is invariant under in-plane

rotations of the order parameters and coordinates according to $q_+ \rightarrow q_+ e^{2i\varphi}$, $\eta_+ \rightarrow \eta_+ e^{-i\varphi}$. This, however, is not a physical symmetry.

For the gradient part of the free energy to be stable, the gradient coefficients $J_{1,\dots,5}$ have to satisfy the stability conditions [5–8]:

$$J_1 + J_2 > 2|J_4|, \quad J_3 > 0, \quad J_3(J_1 - J_2) > 2J_5^2. \quad (26)$$

The GL theory of odd-parity two-component superconductors can be further extended by considering the coupling to other orders. In general, multi-component orders can be characterized by subsidiary order parameters. In case of the two-component trigonal superconductors, the subsidiary order parameters have symmetry A_{2g} and E_g , and the corresponding bilinears of primary fields are given by

$$A_{2g} \rightarrow \kappa = \eta^\dagger \tau^y \eta = -i(\eta_1^* \eta_2 - \eta_1 \eta_2^*) = \frac{1}{2}(|\eta_+|^2 - |\eta_-|^2), \quad (27)$$

$$E_g \rightarrow (N_1, N_2) = (\eta^\dagger \tau^z \eta, \eta^\dagger \tau^x \eta) = (|\eta_1|^2 - |\eta_2|^2, -\eta_1^* \eta_2 - \eta_1 \eta_2^*) \quad (28)$$

Here κ and (N_1, N_2) define the chiral and nematic subsidiary order parameters, respectively.

The coupling of the superconducting order to other orders is easily understood in terms of the subsidiary orders. A general magnetic order parameter \vec{M} is a pseudo-vector and transforms as

$$M_z \rightarrow A_{2g}, \quad (M_x, M_y) \rightarrow E_g, \quad (29)$$

under trigonal symmetry D_{3d} . From Eq. (28) we find that the only term that can couple to the magnetic order is of the form $|\eta_+|^2 - |\eta_-|^2$, giving rise to a coupling $M_z(|\eta_+|^2 - |\eta_-|^2)$. The magnetic order parameter M_z can be thought of as a Zeeman field in the z direction coupling to the electron (pseudo)spin as $\sim M_z \sigma_z$.

A structural deformation of the crystal, which leads to the breaking of rotational symmetry, can be expressed in terms of the strain tensor u_{ij} . Specifically, the uniaxial and shear strain components $(u_{xx} - u_{yy}, 2u_{xy})$ transform as an E_g doublet. As a result, these two strain tensor components can couple to the nematic superconductor associated with E_g subsidiary order.

In terms of the coupling constants g_M and g_N we can write the contribution to the GL free energy coming from the magnetic and nematic coupling as

$$g_M M_z (|\eta_+|^2 - |\eta_-|^2) + g_N [(u_{xx} - u_{yy})N_1 + 2u_{xy}N_2] \quad (30)$$

As is clear from the form of this term, the effect of symmetry breaking induced by the magnetic and nematic fields is to lift the degeneracy of the two-component pairing.

It is important to note that when we use the term “strain” here we very generally mean any nonmagnetic spin-rotation invariant order transforming as E_g .

VIII. SOLVING GINZBURG-LANDAU EQUATIONS FOR UPPER CRITICAL FIELD H_{c2}

In this section we present the solutions of the GL equations in the presence of a magnetic field \vec{H} , from which we find the expressions for the upper critical field H_{c2} . We first derive the GL equations from collecting the free energy contributions of Eqs. (17), (23), and (25).

A. Ginzburg-Landau equations

We first derive the full set of GL equations governing the odd-parity two-component superconductor. To this end we write the total free energy as $F_{\text{tot}} = \int d^3\vec{x} f_{\text{tot}}$, where f_{tot} is the total free energy density. The free energy density has the following contributions

$$f_{\text{tot}} = f[A, B_1, B_2] + f_{D,U(1)\times U(1)}[J_1, J_2, J_3] + f_{D,4}[J_4] + f_{D,\text{trig}}[J_5], \quad (31)$$

where we make the functional dependence on GL coefficients explicit. The contribution from the electromagnetic field \vec{A} , given by $f_{EM} = (\vec{\partial} \times \vec{A})^2 / 8\pi$ is neglected since it does not play a role in our theory. The GL equations follow from functional variation with respect to the fields and are given by

$$0 = \frac{\delta F_{\text{tot}}}{\delta \eta_a^*} = \frac{\delta F}{\delta \eta_a^*} + \frac{\delta F_{D,U(1)\times U(1)}}{\delta \eta_a^*} + \frac{\delta F_{D,4}}{\delta \eta_a^*} + \frac{\delta F_{D,\text{trig}}}{\delta \eta_a^*}. \quad (32)$$

Starting with the homogeneous contribution to the free energy, this simply leads to

$$\frac{\delta F}{\delta \eta_a^*} = A\eta_a + 2B_1\eta^\dagger\eta\eta_a - 2B_2(\eta_1^*\eta_2 - \eta_2^*\eta_1)\epsilon_{ab}\eta_b. \quad (33)$$

For the gradient term F_D^c one finds the contribution to the GL equations as

$$\frac{\delta F_{D,U(1)\times U(1)}}{\delta \eta_a^*} = J_1(D_x^2 + D_y^2)\eta_a + \epsilon_{ab}J_2(\vec{D} \times \vec{D})_z\eta_b + J_3D_z^2\eta_a. \quad (34)$$

For the gradient term $f_{D,4}$ with U(1) symmetry one simply finds

$$\frac{\delta F_{D,4}}{\delta \eta_a^*} = J_4(\tau_{ij}^z\tau_{ab}^z + \tau_{ij}^x\tau_{ab}^x)D_iD_j\eta_b. \quad (35)$$

To conclude, the trigonal anisotropy term $f_{D,\text{trig}}$ gives a contribution to the GL equations which reads as

$$\frac{\delta F_{D,\text{trig}}}{\delta \eta_a^*} = J_5[\tau_{ab}^x\{D_z, D_x\} + \tau_{ab}^z\{D_z, D_y\}]\eta_b \quad (36)$$

B. The case $\vec{H} = H\hat{z}$

We consider the case of a magnetic field applied in the z -direction (i.e., perpendicular to the basal plane of the crystal) given by $\vec{H} = H\hat{z}$. The corresponding vector potential in the symmetric gauge is $\vec{A} = -H\vec{x} \times \hat{z}/2 = -H\epsilon_{ij}x_j/2$, whereas in the Landau gauge $\vec{A} = Hx\hat{y}$.

The GL equations (collecting the results J_1 - J_4) for the order parameter η read

$$-A\eta_a = J_1(D_x^2 + D_y^2)\eta_a + J_3D_z^2\eta_a + J_2\epsilon_{ab}[D_x, D_y]\eta_b + J_4[(D_x^2 - D_y^2)\tau_{ab}^z\eta_b + \{D_x, D_y\}\tau_{ab}^x\eta_b]. \quad (37)$$

It will be beneficial to perform a basis transformation to positive and negative angular momentum combinations $\eta_\pm = \eta_1 \pm i\eta_2$. The GL equations in this basis take the form

$$\begin{aligned} -A\eta_+ &= J_1(D_x^2 + D_y^2)\eta_+ + J_3D_z^2\eta_+ - iJ_2[D_x, D_y]\eta_+ + J_4(D_x^2 - D_y^2)\eta_- + iJ_4\{D_x, D_y\}\eta_- \\ -A\eta_- &= J_1(D_x^2 + D_y^2)\eta_- + J_3D_z^2\eta_- + iJ_2[D_x, D_y]\eta_- + J_4(D_x^2 - D_y^2)\eta_+ - iJ_4\{D_x, D_y\}\eta_+ \end{aligned} \quad (38)$$

In addition to an order parameter change of basis, we define the covariant derivatives $D_\pm = D_x \pm iD_y$. In terms of the angular momentum basis for the D_i operators, the operators appearing in the GL equations are given by

$$\begin{aligned} D_x^2 + D_y^2 &= \frac{1}{2}(D_+D_- + D_-D_+), & D_x^2 - D_y^2 &= \frac{1}{2}(D_+D_+ + D_-D_-), \\ [D_x, D_y] &= \frac{i}{2}(D_+D_- - D_-D_+), & \{D_x, D_y\} &= \frac{-i}{2}(D_+D_+ - D_-D_-) \end{aligned} \quad (39)$$

The problem of solving the GL equations is equivalent to the problem of two-component fermions in a magnetic field. To see this, we note that $[D_x, D_z] = [D_y, D_z] = 0$ and $[D_x, D_y] = iq\epsilon_{ij}\partial_i A_j = -2ieH = -i/l_b^2$. The latter commutation relation is the well-known commutation relation for momentum components in a magnetic field. We have defined a magnetic length $l_b = 1/\sqrt{2eH}$. Based on the commutation relation we define raising and lowering operators as $\Pi_\pm = l_b D_\pm/\sqrt{2}$ and substitute the expression in the GL equations to obtain

$$-A \begin{pmatrix} \eta_+ \\ \eta_- \end{pmatrix} = \frac{1}{l_b^2} \begin{pmatrix} J_1\{\Pi_-, \Pi_+\} + J_2[\Pi_+, \Pi_-] & 0 \\ 0 & J_1\{\Pi_-, \Pi_+\} - J_2[\Pi_+, \Pi_-] \end{pmatrix} \begin{pmatrix} \eta_+ \\ \eta_- \end{pmatrix} + J_3 \begin{pmatrix} D_z^2 & 0 \\ 0 & D_z^2 \end{pmatrix} \begin{pmatrix} \eta_+ \\ \eta_- \end{pmatrix}. \quad (40)$$

The J_4 term (and J_5 term) has been suppressed for the moment. The raising and lowering operators obey $[\Pi_-, \Pi_+] = 1$ by definition. Furthermore, we see that inhomogeneity in the z -direction can only increase the (energy) eigenvalues and therefore corresponds to lower H_{c2} . We take $D_z\eta = 0$. Then, including the J_4 term, the GL equations read

$$-A \begin{pmatrix} \eta_+ \\ \eta_- \end{pmatrix} = \frac{1}{l_b^2} \begin{pmatrix} J_1\{\Pi_-, \Pi_+\} - J_2 & 2J_4\Pi_+^2 \\ 2J_4\Pi_-^2 & J_1\{\Pi_-, \Pi_+\} + J_2 \end{pmatrix} \begin{pmatrix} \eta_+ \\ \eta_- \end{pmatrix}. \quad (41)$$

It may be simply checked that this system of equations is solved by either of the following solutions

$$\begin{pmatrix} \eta_+ \\ \eta_- \end{pmatrix} = \begin{pmatrix} |n=0\rangle \\ 0 \end{pmatrix}, \quad \begin{pmatrix} \eta_+ \\ \eta_- \end{pmatrix} = \begin{pmatrix} \alpha|n+2\rangle \\ \beta|n\rangle \end{pmatrix}, \quad (42)$$

where $|n\rangle$ are harmonic oscillator eigenfunctions with the property $\Pi_+\Pi_-|n\rangle = n|n\rangle$. The corresponding expressions for the upper critical field are given by

$$H_{c2} = -A[2e(J_1 - J_2)]^{-1}, \quad H_{c2} = -A \left[2e \left(J_1(2n+3) - \sqrt{(2J_1 - J_2)^2 + 4J_4^2(n+1)(n+2)} \right) \right]^{-1}, \quad (43)$$

and the actual physical upper critical field is given by the largest of the two values, with $n = 0$ in the latter [5].

As a next step, we consider the trigonal anisotropy term with gradient constant J_5 . Rewriting it in terms of the η_{\pm} basis and Π_{\pm} operators it takes the form

$$\frac{\sqrt{2}J_5}{l_b} \begin{pmatrix} 0 & i\{D_z, \Pi_+\} \\ -i\{D_z, \Pi_-\} & 0 \end{pmatrix}. \quad (44)$$

Trigonal anisotropy in the GL equations thus couples the raising and lowering operators to D_z , and does not affect any homogeneous solution defined by the condition $D_z\eta = 0$. It is possible that an inhomogeneous solution has lower energy and therefore higher H_{c2} . To investigate this we take $D_z\eta = q_z\eta$. Setting $J_4 = 0$ as a first step, this leads to the system of eigenvalue equations

$$-A \begin{pmatrix} \eta_+ \\ \eta_- \end{pmatrix} = \frac{1}{l_b^2} \begin{pmatrix} J_1\{\Pi_-, \Pi_+\} - J_2 + J_3\tilde{q}_z^2 & i\sqrt{2}J_5\tilde{q}_z\Pi_- \\ -i\sqrt{2}J_5\tilde{q}_z\Pi_+ & J_1\{\Pi_-, \Pi_+\} + J_2 + J_3\tilde{q}_z^2 \end{pmatrix} \begin{pmatrix} \eta_+ \\ \eta_- \end{pmatrix}. \quad (45)$$

where we have defined the dimensionless momentum $\tilde{q}_z = l_b q_z$. It is easy to see that wave functions of the form

$$\begin{pmatrix} \eta_+ \\ \eta_- \end{pmatrix} = \begin{pmatrix} \alpha|n\rangle \\ \beta|n+1\rangle \end{pmatrix}, \quad (46)$$

will solve this system. From the equations for α, β we find the eigenvalues and consequently H_{c2} is given by

$$H_{c2} = |A| \left[2e \left(2J_1(n+1) + J_3\tilde{q}_z^2 - \sqrt{(J_1 + J_2)^2 + 2J_5^2\tilde{q}_z^2(n+1)} \right) \right]^{-1}. \quad (47)$$

The largest H_{c2} corresponds to the $n = 0$ solution. Such solution for H_{c2} should be compared to the solution of the homogeneous case, i.e., choosing $\tilde{q}_z = 0$ to begin with. That solution is simply given by

$$H_{c2} = |A|[2e(J_1 - J_2)]^{-1}, \quad (48)$$

If this is larger, then a homogeneous solution gives the correct H_{c2} . For realistic values of the gradient coefficients, the homogeneous solution always leads to a larger H_{c2} .

C. The case $\vec{A} = Hz(\sin\theta\hat{x} - \cos\theta\hat{y})$

Next, we come to the case of magnetic field in the basal plane: $\vec{H} = H(\cos\theta, \sin\theta, 0)^T$. The corresponding vector potential configuration is given by $\vec{A} = Hz(\sin\theta, -\cos\theta, 0)^T$, and in this gauge we have

$$D_x = -i\partial_x + 2eHz\sin\theta, \quad D_y = -i\partial_y - 2eHz\cos\theta, \quad (49)$$

in addition to $D_z = -i\partial_z$. Since the field is directed along a unit vector $(\cos\theta, \sin\theta, 0)^T$ in the xy plane, it is convenient to rotate the covariant derivative operators so that they are aligned with and orthogonal to the field direction. We define

$$\begin{pmatrix} D_{\parallel} \\ D_{\perp} \end{pmatrix} = \begin{pmatrix} \cos\theta & \sin\theta \\ \sin\theta & -\cos\theta \end{pmatrix} \begin{pmatrix} D_x \\ D_y \end{pmatrix}, \quad (50)$$

where D_{\parallel} is along the field and D_{\perp} is orthogonal to the magnetic field. As a result, D_{\parallel} plays the same role as D_z when the field is applied along the z -axis (see Sec. VIII B), and we have that $[D_{\parallel}, D_{\perp}] = [D_{\parallel}, D_z] = 0$. The two

components D_\perp and D_z do not commute and define the magnetic algebra, i.e., $[D_z, D_\perp] = -2ieH$. In order to solve the GL Eq. (37) we reexpress them in terms of $D_{\parallel,\perp}$. The quadrature simply transforms as $D_x^2 + D_y^2 = D_\parallel^2 + D_\perp^2$, and we find for the two “ d -wave” components

$$\begin{aligned} D_x^2 - D_y^2 &= \cos 2\theta(D_\parallel^2 - D_\perp^2) + \sin 2\theta\{D_\parallel, D_\perp\}, \\ \{D_x, D_y\} &= \sin 2\theta(D_\parallel^2 - D_\perp^2) - \cos 2\theta\{D_\parallel, D_\perp\}. \end{aligned} \quad (51)$$

Note that $[D_x, D_y] = 0$. Following the standard approach, we assume homogeneity in the direction along the field, i.e., $D_\parallel\eta = 0$, implying that we can ignore all terms containing D_\parallel .

The trigonal contribution to the GL equations takes the form

$$J_5 [\{D_z, D_x\}\tau_{ab}^x\eta_b + \{D_z, D_y\}\tau_{ab}^z\eta_b], \quad (52)$$

which, after rewriting in terms of $D_{\parallel,\perp}$ and neglecting D_\parallel becomes

$$J_5 [-\cos\theta\tau_{ab}^z\eta_b + \sin\theta\tau_{ab}^x\eta_b] \{D_z, D_\perp\}. \quad (53)$$

We can now write the system of GL equations as a matrix equation for $\eta = (\eta_1, \eta_2)^T$ and find

$$-A\eta = [(J_1D_\perp^2 + J_3D_z^2)I - J_4D_\perp^2(\cos 2\theta\tau^z + \sin 2\theta\tau^x) + J_5\{D_z, D_\perp\}(-\cos\theta\tau^z + \sin\theta\tau^x)]\eta, \quad (54)$$

where I is the identity matrix. It is convenient to diagonalize the J_4 term by performing the following rotation

$$\begin{pmatrix} \eta_1 \\ \eta_2 \end{pmatrix} = \begin{pmatrix} \cos\theta & -\sin\theta \\ \sin\theta & \cos\theta \end{pmatrix} \begin{pmatrix} f_1 \\ f_2 \end{pmatrix}. \quad (55)$$

In terms of the rotated order parameters $(f_1, f_2)^T$ the GL equations read

$$-A \begin{pmatrix} f_1 \\ f_2 \end{pmatrix} = \begin{pmatrix} J_3D_z^2 + (J_1 - J_4)D_\perp^2 & 0 \\ 0 & J_3D_z^2 + (J_1 + J_4)D_\perp^2 \end{pmatrix} \begin{pmatrix} f_1 \\ f_2 \end{pmatrix} + J_5\{D_z, D_\perp\} \begin{pmatrix} -\cos 3\theta & \sin 3\theta \\ \sin 3\theta & \cos 3\theta \end{pmatrix} \begin{pmatrix} f_1 \\ f_2 \end{pmatrix}. \quad (56)$$

To solve this set of equations we employ the commutation relations of the operators D_z and D_\perp , which give rise to a magnetic algebra equivalent to the case of $D_{x,y}$ when the field is applied in the z -direction (see Sec. VIII B). Specifically, we have $[D_z, D_\perp] = -i/l_b^2$, which implies that D_z and D_\perp satisfy a canonical commutation relation. It will be convenient to define effective “momentum” and “position” operators $\hat{P} = l_b D_z$ and $\hat{X} = l_b D_\perp$, so that $[\hat{X}, \hat{P}] = i$.

The appearance of the anti-commutator $\{D_z, D_\perp\} \sim \{\hat{X}, \hat{P}\}$ in Eq. (56) complicates this set of equations significantly, as it is not diagonal in the basis of harmonic oscillator states defined by the raising and lowering operators obtained from \hat{X}, \hat{P} . Therefore, the presence of *two* gradient terms originating from (trigonal) crystal anisotropy, the J_4 and J_5 terms, does not allow for a straightforward exact solution for arbitrary gradient coefficients.

To proceed, we map out the consequences of trigonal anisotropy terms on H_{c2} , starting from a number of limiting cases. In doing so, we obtain the full functional dependence of the upper critical field on the gradient coefficients. We will start by considering the cases $J_5 = 0$ (as applicable to hexagonal crystals), and $J_4 = 0$, i.e., when only the trigonal gradient coefficient J_5 is present. Then, we introduce the neglected terms perturbatively.

1. The hexagonal symmetry case ($J_5 = 0$)

This is the simplest case, as it reduces to the case of hexagonal symmetry (rather than trigonal symmetry, we are effectively assuming additional artificial symmetry) and the result is well-known [10]. It is nevertheless helpful to express the result in the present language. The system to solve takes the form

$$-A \begin{pmatrix} f_1 \\ f_2 \end{pmatrix} = \frac{J_3}{l_b^2} \begin{pmatrix} \hat{P}^2 + \omega_1^2 \hat{X}^2 & 0 \\ 0 & \hat{P}^2 + \omega_2^2 \hat{X}^2 \end{pmatrix} \begin{pmatrix} f_1 \\ f_2 \end{pmatrix}, \quad (57)$$

in terms of the position and momentum operators. The system is diagonal, with two different cyclotron frequencies given by

$$\omega_1^2 = \frac{J_1 - J_4}{J_3}, \quad \omega_2^2 = \frac{J_1 + J_4}{J_3}. \quad (58)$$

Symbol	Definition	Physical meaning
l_b	$1/l_b^2 = 2eH$	Magnetic length
ω	$\sqrt{J_1/J_3}$	Cyclotron frequency of the system without crystal anisotropy effects
ω_1, ω_2	$\omega\sqrt{1 - J_4 /J_1}, \omega\sqrt{1 + J_4 /J_1}$	Cyclotron frequencies in presence of J_4
ω_{\pm}	$(\omega_2 \pm \omega_1)/2$	Sum and difference of frequencies in presence of gradient term J_4
\hat{X}, \hat{P}	$l_b D_{\perp}, l_b D_z$	Effective position and momentum operators with canonical commutation relation
Π_{\pm}	$(\hat{P} + i\omega\hat{X})/\sqrt{2\omega}$	Raising and lowering operators for Landau levels with cyclotron frequency ω
$\tilde{\Pi}_{\pm}$	$e^{\pm i\pi/4}\Pi_{\pm}$	Rotated raising and lowering operators
Ξ_{\pm}	$(\hat{P} + i\omega_1\hat{X})/\sqrt{2\omega_1}$	Raising and lowering operators for Landau levels with cyclotron frequency ω_1

TABLE II: This Table lists the definitions used in this section where we calculate the upper critical field in the basal plane. We note that in the Supplemental Material we define all cyclotron frequencies to be dimensionless by pulling out a factor J_3 . We use a different convention in the Main Text.

Hence, this system gives rise to two series of Landau levels. The upper critical field is simply determined by the lowest Landau level solution of the series with the smallest cyclotron frequency. Specifically, the upper critical field is given by

$$\tilde{H}_{c2} = \max_{i=1,2} \left\{ \frac{-A}{2eJ_3\omega_i} \right\}. \quad (59)$$

We note that here, in the Supplemental Material we define the cyclotron frequencies ω_1, ω_2 (and similarly for ω, ω_{\pm} below) in a dimensionless fashion. A different convention is used in the Main Text, where an overall factor J_3 is absorbed in the cyclotron frequencies.

2. The case when $J_4 = 0$ (only J_5)

As a next case, we make the assumption that $J_4 = 0$, yet J_5 is nonzero, which may be called pure trigonal case. For this case, it is helpful to go back to equation (54), which is expressed in terms of the η variables. The system to solve is then given by

$$-A\eta = [(J_1 D_{\perp}^2 + J_3 D_z^2)I + J_5 \{D_z, D_{\perp}\} (-\cos\theta\tau^z + \sin\theta\tau^x)] \eta, \quad (60)$$

and it is convenient to perform an order parameter rotation defined by

$$\begin{pmatrix} \eta_1 \\ \eta_2 \end{pmatrix} = \begin{pmatrix} \cos(\theta/2) & \sin(\theta/2) \\ -\sin(\theta/2) & \cos(\theta/2) \end{pmatrix} \begin{pmatrix} f_1 \\ f_2 \end{pmatrix}. \quad (61)$$

Performing this rotation we are left with a diagonal system which takes the form

$$-A \begin{pmatrix} f_1 \\ f_2 \end{pmatrix} = \begin{pmatrix} J_1 D_{\perp}^2 + J_3 D_z^2 - J_5 \{D_z, D_{\perp}\} & 0 \\ 0 & J_1 D_{\perp}^2 + J_3 D_z^2 + J_5 \{D_z, D_{\perp}\} \end{pmatrix} \begin{pmatrix} f_1 \\ f_2 \end{pmatrix}. \quad (62)$$

The diagonal system left to solve is rather different from the previous case (i.e., $J_4 \neq 0, J_5 = 0$). This becomes apparent when we rewrite it in terms of \hat{X} and \hat{P} ,

$$-A \begin{pmatrix} f_1 \\ f_2 \end{pmatrix} = \frac{J_3}{l_b^2} \begin{pmatrix} \omega^2 \hat{X}^2 + \hat{P}^2 - J_5 \{\hat{X}, \hat{P}\}/J_3 & 0 \\ 0 & \omega^2 \hat{X}^2 + \hat{P}^2 + J_5 \{\hat{X}, \hat{P}\}/J_3 \end{pmatrix} \begin{pmatrix} f_1 \\ f_2 \end{pmatrix}, \quad (63)$$

with $\omega^2 = J_1/J_3$. Since this system is diagonal, we can focus on the diagonal entries individually. To find the eigenvalues of such system, we introduce the raising and lowering operators $\Pi_{\pm} = (\hat{P} + i\omega\hat{X})/\sqrt{2\omega}$, with $\Pi_+ = \Pi_-^\dagger$. We then have for the right-hand side of Eq. (63)

$$\omega (\Pi_+\Pi_- + \Pi_-\Pi_+) \pm i \frac{J_5}{J_3} (\Pi_+^2 - \Pi_-^2). \quad (64)$$

To proceed, we redefine the raising and lowering operators by performing the following ‘‘rotation’’: $\tilde{\Pi}_{\pm} = e^{\pm i\pi/4}\Pi_{\pm}$. It can be checked that this corresponds to a rotation in the space of operator variables \hat{X} and \hat{P} . Note that such rotation preserves the operator algebra. We then find that (64) takes the form

$$\omega (\tilde{\Pi}_+\tilde{\Pi}_- + \tilde{\Pi}_-\tilde{\Pi}_+) \pm \frac{J_5}{J_3} (\tilde{\Pi}_+^2 + \tilde{\Pi}_-^2). \quad (65)$$

We now use squeezing operators (see Sec. VIII E) to bring the operator equation into a form that is diagonal in the occupation number basis corresponding to the raising and lowering operators. Specifically, we use the unitary transformation

$$\begin{pmatrix} f_1 \\ f_2 \end{pmatrix} = \begin{pmatrix} \hat{S}_+ & 0 \\ 0 & \hat{S}_- \end{pmatrix} \begin{pmatrix} g_1 \\ g_2 \end{pmatrix}, \quad (66)$$

where \hat{S}_{\pm} are squeezing operators with $\theta = 0$ for \hat{S}_+ and $\theta = \pi$ for \hat{S}_- . The squeezing parameter r is defined by the relation

$$\tanh 2r = \frac{J_5}{\sqrt{J_1 J_3}} \quad (67)$$

The new cyclotron frequency is given by

$$\omega' = \sqrt{\omega^2 - J_5^2/J_3^2} = \omega \sqrt{1 - J_5^2/J_3^2 \omega^2} = \omega \sqrt{1 - J_5^2/J_1 J_3} \quad (68)$$

This gives for the upper critical field

$$\tilde{H}'_{c2} = \frac{-A}{2eJ_3\omega'} = \frac{-A}{2e\sqrt{J_1 J_3 - J_5^2}}, \quad (69)$$

Note that this implies a stability condition on the value of J_5 in relation to $J_{1,3}$, since the system does not make sense if J_5 exceeds both $J_{1,3}$.

3. J_5 as a perturbation

Let us now reconsider Eqs. (56) and (57). We want to consider the J_5 term as a perturbation to Eq. (57). It is convenient to use squeezing operators to make the cyclotron frequencies match in Eq. (57). Let us assume that $\omega_2 > \omega_1$ (the calculation for the opposite case is equivalent), and take $\omega_2/e^{2r} = \omega_1$. We then have

$$\hat{S}^\dagger(r) \left(\hat{P}^2 + \omega_2^2 \hat{X}^2 \right) \hat{S}(r) = e^{2r} \left(\hat{P}^2 + \omega_1^2 \hat{X}^2 \right), \quad (70)$$

where we have used a squeezing operator with $\theta = \pi$ (see Sec. VIII E). With this transformation, we bring the matrix operator equation into the form

$$-A \begin{pmatrix} f_1 \\ \hat{S}^\dagger(r)f_2 \end{pmatrix} = \frac{J_3}{l_b^2} \begin{pmatrix} \hat{P}^2 + \omega_1^2 \hat{X}^2 & 0 \\ 0 & e^{2r}(\hat{P}^2 + \omega_1^2 \hat{X}^2) \end{pmatrix} \begin{pmatrix} f_1 \\ \hat{S}^\dagger(r)f_2 \end{pmatrix}, \quad (71)$$

which does not yet include the J_5 . The matrix operator in Eq. (53) proportional to J_5 , which we call H' and consider as a perturbation, takes the following form after applying the squeezing transformation

$$H' = \frac{J_5/J_3}{l_b^2} \begin{pmatrix} -\cos 3\theta\{\hat{X}, \hat{P}\} & \sin 3\theta\{\hat{X}, \hat{P}\}\hat{S}(r) \\ \sin 3\theta\hat{S}^\dagger(r)\{\hat{X}, \hat{P}\} & \cos 3\theta\{\hat{X}, \hat{P}\} \end{pmatrix} \quad (72)$$

Let us first consider the diagonal matrix elements. We recognize that they have the same structure as in the case considered above ($J_4 = 0, J_5 \neq 0$). They can therefore be diagonalized in the same manner. We make the substitutions $\hat{P}^2 + \omega_1^2 \hat{X}^2 \rightarrow \omega_1(\tilde{\Pi}_+ \tilde{\Pi}_- + \tilde{\Pi}_- \tilde{\Pi}_+)$, $\{\hat{X}, \hat{P}\} \rightarrow -(\tilde{\Pi}_+^2 + \tilde{\Pi}_-^2)$ and $\hat{S}(r, \theta = \pi) \rightarrow \hat{S}(r, \theta = \pi/2)$, where in the latter case the squeezing operator is defined in terms of $\tilde{\Pi}_\pm$.

We can immediately deduce an expression for H_{c2} in case $r \gg 1$, i.e., $\omega_1 \ll \omega_2$. In that case we can ignore the coupling between the two series of Landau levels. All we are then left with is diagonalizing the matrix entry corresponding to ω_1 . This was achieved in the previous section and we simply substitute $J_5 \rightarrow J_5 \cos 3\theta$. The cyclotron frequency ω_1 transforms in the same way as ω (see above) and we obtain

$$\omega'_1 = \sqrt{\omega_1^2 - J_5^2 \cos^2 3\theta / J_3^2} = \sqrt{(J_1 - |J_4|) / J_3 - J_5^2 \cos^2 3\theta / J_3^2}. \quad (73)$$

As a result, in the limit $\omega_1 \ll \omega_2$ the upper critical field is given by

$$H_{c2} = \frac{-A}{2eJ_3\omega'_1} = \frac{-A}{2e\sqrt{(J_1 - |J_4|)J_3 - J_5^2 \cos^2 3\theta}}. \quad (74)$$

It is important to note that this limit corresponds to $(J_1 - |J_4|) / (J_1 + |J_4|) \ll 1$ with the hard constraint $|J_5| < \sqrt{(J_1 - |J_4|)J_3}$, which also should be considered a rather unphysical limiting case.

Let us now explore the case $\omega_1 \sim e^{2r}\omega_1 (= \omega_2)$. In this case we cannot ignore the coupling between the two series of Landau levels. It is convenient to work with raising and lowering operators $\Xi_\pm = (\hat{P} + i\omega_1 \hat{X}) / \sqrt{2\omega_1}$ (instead of the operators Π_\pm , which are defined in terms of ω). The eigenstates of the unperturbed system are given by [note that this is *after* squeezing of the second component, i.e., in the basis $(g_1, g_2)^T \equiv (f_1, \hat{S}^\dagger f_2)^T$]

$$\begin{pmatrix} |n\rangle \\ 0 \end{pmatrix}, \quad \begin{pmatrix} 0 \\ |n\rangle \end{pmatrix}, \quad (75)$$

The ground state wave function of the unperturbed system is $(|0\rangle, 0)^T$. The operator part of the perturbation is given by $\{\hat{X}, \hat{P}\} = -i(\Xi_+^2 - \Xi_-^2)$.

In general, when applying perturbation theory one must make two assumptions. First, one must obviously require that $J_5/J_3 \ll \omega_1$ for the whole exercise to make sense. Second, one could naively think that whether to apply degenerate or non-degenerate perturbation theory depends on the smallness of J_5/J_3 as compared to the difference of the frequencies, i. e., whether the condition $J_5/J_3 \ll \omega_2 - \omega_1$ is satisfied or not. It turns out, however, that non-degenerate perturbation theory is sufficient even if the latter inequality is not satisfied. The reason for this is that the correction perturbative in J_5 remains small in the limit $\omega_1 \rightarrow \omega_2$. We confirm this conclusion explicitly applying degenerate perturbation theory.

In light of the latter discussion, we first consider non-degenerate perturbation theory. Given the operator part of the perturbation, we directly conclude that there is no first order correction to the cyclotron frequency. The second order correction to the cyclotron frequency is given by the sum of contributions from the two series of Landau level states, and it takes the form

$$\begin{aligned} \delta\omega &= \frac{J_5^2 \cos^2 3\theta}{J_3^2} \sum_{n \geq 1} \frac{|\langle n | (\Xi_+^2 - \Xi_-^2) | 0 \rangle|^2}{-2n\omega_1} + \frac{J_5^2 \sin^2 3\theta}{J_3^2} \sum_{n \geq 0} \frac{|\langle n | (\Xi_+^2 - \Xi_-^2) \hat{S} | 0 \rangle|^2}{\omega_1 - (2n+1)\omega_2}, \\ &= -\frac{J_5^2 \cos^2 3\theta}{2J_3^2 \omega_1} + \frac{J_5^2 \sin^2 3\theta}{J_3^2} \sum_{n \geq 0} \frac{|\langle n | (\Xi_+^2 - \Xi_-^2) \hat{S} | 0 \rangle|^2}{\omega_1 - (2n+1)\omega_2}. \end{aligned} \quad (76)$$

The presence of the squeezing operator complicates the summation in the last term. With the help of the properties of the squeezing operator, in particular the matrix elements with oscillator eigenstates (see Sec. VIII E), we find the matrix element of the numerator as

$$|\langle n | (\Pi_+^2 - \Pi_-^2) \hat{S} | 0 \rangle|^2 = \left(\frac{n}{\sinh^2 r} - 1 \right)^2 \tanh^2 r |\langle n | \hat{S} | 0 \rangle|^2 = \left(\frac{n}{\sinh^2 r} - 1 \right)^2 \frac{n!}{(\frac{n}{2}!)^2 2^{2n}} \frac{\tanh^{n+2} r}{\cosh r}, \quad (77)$$

Note that n has to be even for a non-vanishing matrix element. The hyperbolic functions can be easily expressed in terms of the cyclotron frequencies ω_1 and ω_2 . To simplify notation, and to express the results in terms of physically meaningful quantities, let us define $\omega_\pm = (\omega_2 \pm \omega_1)/2$. The hyperbolic functions then read

$$\sinh r = \frac{\omega_- / \omega_+}{\sqrt{1 - \omega_-^2 / \omega_+^2}}, \quad \cosh r = \frac{1}{\sqrt{1 - \omega_-^2 / \omega_+^2}}. \quad (78)$$

Using these expressions we rewrite the sum in Eq. (76) as

$$\sum_{n \geq 0} \frac{|\langle n | (\Xi_+^2 - \Xi_-^2) \hat{S} | 0 \rangle|^2}{\omega_1 - (2n+1)\omega_2} = -\frac{\omega_+^2}{\omega_-^2} \left(1 - \frac{\omega_-^2}{\omega_+^2}\right)^{5/2} \sum_{m \geq 0} \frac{(2m)!}{(m!)^2 4^m} \frac{(\omega_-/\omega_+)^{2m}}{4m\omega_2 + 2\omega_-} \left(2m - \frac{\omega_-^2/\omega_+^2}{1 - \omega_-^2/\omega_+^2}\right)^2, \quad (79)$$

where we have changed variables from n to m since n must be even. We notice that this sum is a function of the ratio of cyclotron frequencies ω_{\pm} only. Given this observation, we set $x \equiv \omega_-/\omega_+$ and we define a function $F_{\pm}(x, j)$, which depends on x and integer j , as

$$F_{\pm}(x, j) = \frac{(1-x^2)^{5/2}}{x^2} \sum_{m \geq j} \frac{(2m)!}{(m!)^2 4^m} \frac{x^{2m}}{2m \pm x(2m+1)} \left(2m - \frac{x^2}{1-x^2}\right)^2. \quad (80)$$

The correction to the cyclotron frequency $\delta\omega$ of Eq. (76), calculated using non-degenerate perturbation theory, can then be expressed as

$$\delta\omega = -\frac{J_5^2}{2J_3^2} \left[\frac{\cos^2 3\theta}{\omega_1} + \frac{\sin^2 3\theta}{\omega_+} F_+(\frac{\omega_-}{\omega_+}, 0) \right]. \quad (81)$$

We point out that the function $F_+(x, 0)$ is exactly the function $F(x)$ defined in the Main Text. It can be rewritten as

$$F_+(x, 0) = \frac{1-x}{x} \left[\sqrt{\frac{1+x}{1-x}} {}_2F_1\left(\frac{1}{2}, a; 1+a; x^2\right) - 1 \right], \quad (82)$$

where $a = x/2(1+x)$, and ${}_2F_1(\alpha, \beta; \delta; \gamma)$ is a hypergeometric function. In our special case, it admits convenient integral representation:

$${}_2F_1\left(\frac{1}{2}, a; 1+a; x^2\right) = a \int_0^{\infty} \frac{dt e^{-at}}{\sqrt{1-x^2 e^{-t}}}. \quad (83)$$

Including the correction (81), the cyclotron frequency becomes $\omega_1 + \delta\omega$. The upper critical field H_{c2} is always obtained from dividing $-A/2e$ by the cyclotron frequency, and therefore the upper critical field becomes, to lowest order in J_5/J_3 ,

$$H_{c2}(\theta) = \tilde{H}_{c2} \left\{ 1 + \frac{J_5^2}{2J_3^2 \omega_1} \left[\frac{\cos^2 3\theta}{\omega_1} + \frac{\sin^2 3\theta}{\omega_+} F_+(\omega_-/\omega_+, 0) \right] \right\}, \quad (84)$$

where we have defined \tilde{H}_{c2} as the upper critical field in the absence of trigonal correction J_5 , see Eq. (59).

Naively one would think that non-degenerate perturbation theory is no longer justified when J_5/J_3 is larger than $\omega_2 - \omega_1$, in which case we must resort to (quasi)-degenerate perturbation theory. We will now present calculation using (quasi)-degenerate perturbation theory, and show that the result exactly equals the result of Eq. (81). We comment on this below.

In order to do (quasi)-degenerate perturbation theory we define the (quasi)-degenerate subspace by the states

$$|1\rangle = \begin{pmatrix} |0\rangle \\ 0 \end{pmatrix}, \quad |2\rangle = \begin{pmatrix} 0 \\ |0\rangle \end{pmatrix}. \quad (85)$$

According to standard (quasi)-degenerate perturbation theory, the first and second order corrections to a Hamiltonian $H_{ij}^{(0)}$ are given by the general perturbative expression

$$H_{ij}^{(0)} + H_{ij}^{(1)} + H_{ij}^{(2)} = E_i \delta_{ij} + H'_{ij} + \frac{1}{2} \sum_k H'_{ik} H'_{kj} \left[\frac{1}{E_i - E_k} + \frac{1}{E_j - E_k} \right], \quad (86)$$

where E_i are the eigenvalues (i.e., cyclotron frequencies in the present problem) of the unperturbed problem, and H' is the perturbation. In our current problem, the indices i, j run over the basis states (85), and the perturbation H' is given by Eq (72). Its matrix elements in the (quasi)-degenerate lowest Landau level subspace are given by

$$H_{ij}^{(1)} = \frac{J_5 \sin 3\theta}{J_3} \begin{pmatrix} 0 & i\langle 0 | \Xi_-^2 \hat{S} | 0 \rangle \\ -i\langle 0 | \hat{S}^\dagger \Xi_+^2 | 0 \rangle & 0 \end{pmatrix}. \quad (87)$$

To obtain the full correction to the cyclotron frequency to second order in J_5/J_3 we require the correction to the Hamiltonian up to order J_5^2/J_3^2 , and therefore also need $H_{ij}^{(2)}$. Using the general expression of Eq. (86) we find the diagonal matrix elements of $H_{ij}^{(2)}$ as

$$\begin{aligned}
H_{11}^{(2)} &= \frac{J_5^2}{J_3^2} \cos^2 3\theta \sum_{n \geq 1} \frac{|\langle n | (\Xi_+^2 - \Xi_-^2) | 0 \rangle|^2}{-2n\omega_1} + \frac{J_5^2}{J_3^2} \sin^2 3\theta \sum_{n \geq 1} \frac{|\langle n | (\Xi_+^2 - \Xi_-^2) \hat{S} | 0 \rangle|^2}{\omega_1 - (2n+1)\omega_2}, \\
&= -\frac{J_5^2}{2J_3^2 \omega_1} \cos^2 3\theta + \frac{J_5^2}{J_3^2} \sin^2 3\theta \sum_{n \geq 1} \frac{|\langle n | (\Xi_+^2 - \Xi_-^2) \hat{S} | 0 \rangle|^2}{\omega_1 - (2n+1)\omega_2} \\
&= -\frac{J_5^2}{2J_3^2} \left[\frac{\cos^2 3\theta}{\omega_1} + \frac{\sin^2 3\theta}{\omega_+} F_+(\frac{\omega_-}{\omega_+}, 1) \right], \\
H_{22}^{(2)} &= \frac{J_5^2}{J_3^2} \cos^2 3\theta \sum_{n \geq 1} \frac{|\langle n | (\Xi_+^2 - \Xi_-^2) | 0 \rangle|^2}{-2n\omega_2} + \frac{J_5^2}{J_3^2} \sin^2 3\theta \sum_{n \geq 1} \frac{|\langle n | (\Xi_+^2 - \Xi_-^2) \hat{S} | 0 \rangle|^2}{\omega_2 - (2n+1)\omega_1}, \\
&= -\frac{J_5^2}{2J_3^2 \omega_2} \cos^2 3\theta + \frac{J_5^2}{J_3^2} \sin^2 3\theta \sum_{n \geq 1} \frac{|\langle n | (\Xi_+^2 - \Xi_-^2) \hat{S} | 0 \rangle|^2}{\omega_2 - (2n+1)\omega_1} \\
&= -\frac{J_5^2}{2J_3^2} \left[\frac{\cos^2 3\theta}{\omega_2} + \frac{\sin^2 3\theta}{\omega_+} F_-(\frac{\omega_-}{\omega_+}, 1) \right], \tag{88}
\end{aligned}$$

In principle we also need the off-diagonal matrix elements, however, these will only contribute to cyclotron frequency correction at order $\sim J_5^4/J_3^4$ and we therefore ignore them. The Hamiltonian matrix to order J_5^2/J_3^2 can be cast into the general form $aI_2 + b\tau^z + c\tau^x + d\tau^y$ where τ^i are Pauli matrices and a, b, c, d are real expansion coefficients. Then, the new cyclotron frequency ω' entering the expression for H_{c2} is given by $\omega' = a - \sqrt{b^2 + c^2 + d^2}$. We find that the coefficients a and b are given by

$$\begin{aligned}
a &= \omega_+ - \frac{J_5^2}{2J_3^2 \omega_+} \left[\frac{\cos^2 3\theta}{1 - (\omega_-/\omega_+)^2} + \sin^2 3\theta \frac{F_+ + F_-}{2} \right], \\
b &= -\omega_- - \frac{J_5^2}{2J_3^2 \omega_+} \left[\cos^2 3\theta \frac{\omega_-/\omega_+}{1 - (\omega_-/\omega_+)^2} + \sin^2 3\theta \frac{F_+ - F_-}{2} \right], \tag{89}
\end{aligned}$$

where F_{\pm} are abbreviations for $F_{\pm}(\omega_-/\omega_+, 1)$. The coefficients c and d are defined through the equation

$$c\tau^x + d\tau^y = \frac{J_5 \sin 3\theta}{J_3} \begin{pmatrix} 0 & i\langle 0 | \Xi_-^2 \hat{S} | 0 \rangle \\ -i\langle 0 | \hat{S}^\dagger \Xi_+^2 | 0 \rangle & 0 \end{pmatrix}. \tag{90}$$

These matrix elements are further simplified using $\langle 0 | \Xi_-^2 \hat{S} | 0 \rangle = -\tanh r \langle 0 | \hat{S} | 0 \rangle$. Putting everything together, we evaluate the square root $\sqrt{b^2 + c^2 + d^2}$ to second order in J_5/J_3 and find

$$\sqrt{b^2 + c^2 + d^2} = \omega_- + \omega_- \frac{J_5^2}{2J_3^2 \omega_+^2} \left[\cos^2 3\theta \frac{1}{1 - (\omega_-/\omega_+)^2} + \sin^2 3\theta \frac{\omega_+}{\omega_-} \frac{F_+ - F_-}{2} + \sqrt{1 - \frac{\omega_-^2}{\omega_+^2}} \sin^2 3\theta \right] + \mathcal{O}(J_5^4/J_3^4) \tag{91}$$

We then find the cyclotron frequency ω' to second order in J_5/J_3 as

$$\omega' = (\omega_+ - \omega_-) \left\{ 1 - \frac{J_5^2}{2J_3^2 \omega_+^2} \left[\frac{\cos^2 3\theta}{(1 - \omega_-/\omega_+)^2} + \frac{\sin^2 3\theta}{1 - \omega_-/\omega_+} \left(F_+(\frac{\omega_-}{\omega_+}, 1) + \frac{\omega_-}{\omega_+} \sqrt{1 - \frac{\omega_-^2}{\omega_+^2}} \right) \right] \right\}. \tag{92}$$

For convenience we have separated $\omega_+ - \omega_- = \omega_1$, which is the cyclotron frequency of the unperturbed case with $J_5 = 0$. Next, we notice that the term $\omega_- (1 - \omega_-^2/\omega_+^2)^{1/2}/\omega_+$ is precisely equal to the $m = 0$ term in the definition of $F_+(\omega_-/\omega_+, 0)$, and we can therefore add it to $F_+(\omega_-/\omega_+, 1)$ to obtain $F_+(\omega_-/\omega_+, 0)$. As a result, we arrive at the final expression for H_{c2} containing corrections to order J_5^2/J_3^2

$$H_{c2} = \tilde{H}_{c2} \left\{ 1 + \frac{J_5^2}{2J_3^2 \omega_+^2} \left[\frac{\cos^2 3\theta}{(1 - \omega_-/\omega_+)^2} + \frac{\sin^2 3\theta}{1 - \omega_-/\omega_+} F_+(\frac{\omega_-}{\omega_+}, 0) \right] \right\}. \tag{93}$$

Remarkably, this expression is precisely equal to the upper critical field of Eq. (84), which was obtained through non-degenerate perturbation theory.

4. J_4 as a perturbation

In this limiting case, we start by reconsidering Eq. (63). In order to treat the gradient term with coefficient J_4 , we first perform the same rotation of order parameter variables. This yields

$$\frac{J_4}{J_3} \hat{X}^2 \begin{pmatrix} \cos 3\theta & \sin 3\theta \\ \sin 3\theta & -\cos 3\theta \end{pmatrix} \begin{pmatrix} f_1 \\ f_2 \end{pmatrix} \quad (94)$$

In order to express this in the same operators that were used to solve Eq. (63), we first have to rotate the raising and lowering operators [i.e., $\Pi_{\pm} \rightarrow \tilde{\Pi}_{\pm}$, see Eq. (65)] and then apply the squeezing transformation. After rotation we have $\hat{X} \rightarrow (\hat{X} + \hat{P}/\omega)/\sqrt{2}$ and therefore $\hat{X}^2 \rightarrow (\hat{X}^2 + \hat{P}^2/\omega^2 + \{\hat{X}, \hat{P}\}/\omega)/2$. Applying the squeezing transformation leads to

$$\begin{pmatrix} \hat{S}_- & 0 \\ 0 & \hat{S}_+ \end{pmatrix} \frac{J_4}{2J_3} (\hat{X}^2 + \frac{1}{\omega^2} \hat{P}^2 + \frac{1}{\omega} \{\hat{X}, \hat{P}\}) \begin{pmatrix} \cos 3\theta & \sin 3\theta \\ \sin 3\theta & -\cos 3\theta \end{pmatrix} \begin{pmatrix} \hat{S}_+ & 0 \\ 0 & \hat{S}_- \end{pmatrix}. \quad (95)$$

We may then use the following properties (bearing in mind that $\hat{S}_- = \hat{S}_+^\dagger$): $\hat{S}_- \hat{P} \hat{S}_+ = e^{-r} \hat{P}$, $\hat{S}_- \hat{X} \hat{S}_+ = e^r \hat{X}$. We then obtain

$$\begin{aligned} & \frac{J_4 \cos 3\theta}{2J_3} \begin{pmatrix} (e^{2r} \hat{X}^2 + \frac{e^{-2r}}{\omega^2} \hat{P}^2 + \frac{1}{\omega} \{\hat{X}, \hat{P}\}) & 0 \\ 0 & -(e^{-2r} \hat{X}^2 + \frac{e^{2r}}{\omega^2} \hat{P}^2 + \frac{1}{\omega} \{\hat{X}, \hat{P}\}) \end{pmatrix} + \\ & \frac{J_4 \sin 3\theta}{2J_3} \begin{pmatrix} 0 & (e^{2r} \hat{X}^2 + \frac{e^{-2r}}{\omega^2} \hat{P}^2 + \frac{1}{\omega} \{\hat{X}, \hat{P}\}) \hat{S}_-^2 \\ \hat{S}_+^2 (e^{2r} \hat{X}^2 + \frac{e^{-2r}}{\omega^2} \hat{P}^2 + \frac{1}{\omega} \{\hat{X}, \hat{P}\}) & 0 \end{pmatrix}. \end{aligned}$$

In order to do degenerate perturbation theory we introduce the harmonic oscillator basis states

$$|1\rangle = \begin{pmatrix} |0\rangle \\ 0 \end{pmatrix}, \quad |2\rangle = \begin{pmatrix} 0 \\ |0\rangle \end{pmatrix}, \quad (96)$$

and calculate the first order correction to the Hamiltonian given by Eq. (86). We use the following standard results: $\langle 0|\hat{X}^2|0\rangle = 1/2\omega = \langle 0|\hat{P}^2|0\rangle/\omega^2$, and $\langle 0|\{\hat{X}, \hat{P}\}|0\rangle = 0$. We find for the diagonal part of $H^{(1)}$

$$\frac{J_4 \cos 3\theta \cosh 2r}{2\omega J_3} \begin{pmatrix} 1 & 0 \\ 0 & -1 \end{pmatrix}. \quad (97)$$

The next step is to evaluate the expectation value of the off-diagonal elements. This is more involved as a result of the appearance of the squeezing operators. We find that the off-diagonal elements take the form

$$\langle 0|(e^{2r} \hat{X}^2 + \frac{e^{-2r}}{\omega^2} \hat{P}^2 + \frac{1}{\omega} \{\hat{X}, \hat{P}\}) \hat{S}_-^2 |0\rangle = \frac{1}{\omega} \left(\frac{1 + i \sinh 2r}{\cosh 2r} \right) \langle 0|\hat{S}_-^2 |0\rangle. \quad (98)$$

Using this, we find the correction to the cyclotron frequency ω' , which was defined in Eq. (68), as

$$\delta\omega' = -\frac{J_4}{2J_3} \sqrt{\cos^2 3\theta \frac{\cosh^2 2r}{\omega^2} + \sin^2 3\theta \frac{|\langle 0|\hat{S}_-^2 |0\rangle|^2}{\omega^2}}. \quad (99)$$

This expression can be simplified by noting that $\hat{S}_-^2 = [\hat{S}(r, \theta = \pi)]^2 = \hat{S}(2r, \theta = \pi)$, and using the definition of r . One finds $\cosh 2r = \omega/\omega'$. In addition, the expectation value of the squeezing operator in the oscillator ground vacuum state is given by $|\langle 0|\hat{S}_-^2 |0\rangle|^2 = 1/\cosh 2r$. Putting this all together we find the correction $\delta\omega'$ as

$$\delta\omega' = -\frac{J_4}{2J_3\omega'} \sqrt{\frac{\omega'^3}{\omega^3} + \cos^2 3\theta \left(1 - \frac{\omega'^3}{\omega^3}\right)}. \quad (100)$$

Consequently, the upper critical field to the first order in J_4 is given by

$$\begin{aligned} H_{c2}(\theta) &= \tilde{H}'_{c2} \left[1 + \frac{J_4}{2J_3\omega'^2} \sqrt{\frac{\omega'^3}{\omega^3} + \cos^2 3\theta \left(1 - \frac{\omega'^3}{\omega^3}\right)} \right] \\ &= -\frac{A}{2e\sqrt{J_1 J_3 - J_5^2}} \left[1 + \frac{|J_4| J_3}{2(J_1 J_3 - J_5^2)} \sqrt{\cos^2 3\theta + \sin^2 3\theta \left(1 - \frac{J_5^2}{J_1 J_3}\right)^{3/2}} \right], \quad (101) \end{aligned}$$

where \tilde{H}'_{c2} is defined as the upper critical field in the absence of J_4 term, see Eq. (69).

5. Summary of the result for H_{c2} in the presence of trigonal anisotropy

For convenience and clarity of presentation, here we collect the main results of basal plane H_{c2} calculations. In particular, we list the expressions for H_{c2} in all limiting cases we considered, and state their ranges of applicability.

Taking $J_5 = 0$, the case which is applicable to a hexagonal crystal, the exact solution is

$$J_5 = 0, \quad H_{c2} = \frac{-A}{2e\sqrt{J_3(J_1 - |J_4|)}}. \quad (102)$$

H_{c2} does not exhibit any angular dependence due to the emergent $U(1)$ symmetry of the GL equations.

Taking $J_4 = 0$, where J_5 is the only gradient coefficients in addition to $J_{1,2,3}$ the exact solution of the GL equations is

$$J_4 = 0, \quad H_{c2} = \frac{-A}{2e\sqrt{J_1 J_3 - J_5^2}}. \quad (103)$$

Due to an emergent (but unphysical) rotational symmetry of the GL equations, H_{c2} is isotropic (see Main Text).

We obtain the following approximate solution in the case where $|J_4| \approx J_1$ and J_5 satisfies the stability constraint $J_5 < \sqrt{J_3(J_1 - |J_4|)}$

$$J_1 - |J_4| \ll J_1 + |J_4|, \quad H_{c2} = \frac{-A}{2e\sqrt{J_3(J_1 - |J_4|) - J_5^2 \cos^2 3\theta}}. \quad (104)$$

The most physical case arises when J_4 takes arbitrary values (but $|J_4| < J_1$ due to stability constraints) and J_5 is small. The expression for H_{c2} reads as

$$|J_5| \ll \sqrt{J_3(J_1 - |J_4|)}, \quad H_{c2}(\theta) = \frac{-A}{2e\sqrt{J_3(J_1 - |J_4|)}} \left\{ 1 + \frac{J_5^2}{2J_3^2 \omega_1} \left[\frac{\cos^2 3\theta}{\omega_1} + \frac{\sin^2 3\theta}{\omega_+} F(\omega_-/\omega_+) \right] \right\}, \quad (105)$$

where $F(x)$ is the function defined in Eq. (80), and definitions of ω , ω_{\pm} , $\omega_{1,2}$ are listed in Table II.

We also considered the opposite case, where J_5 is arbitrary and satisfies $J_5 < \sqrt{J_1 J_3}$, and J_4 is small. The result is

$$|J_4| J_3 \ll J_1 J_3 - J_5^2, \quad H_{c2}(\theta) = -\frac{A}{2e\sqrt{J_1 J_3 - J_5^2}} \left[1 + \frac{|J_4| J_3}{2(J_1 J_3 - J_5^2)} \sqrt{\cos^2 3\theta + \sin^2 3\theta \left(1 - \frac{J_5^2}{J_1 J_3} \right)^{3/2}} \right]. \quad (106)$$

This reproduces the result of Ref. 8. The advantage of this solution is that it can be obtained by first-order perturbation theory in J_4 .

We can expand Eq. (105) in small J_4 and Eq. (106) in small J_5 . In both cases the result is

$$|J_4| \ll J_1, \quad J_5^2 \ll J_1 J_3, \quad H_{c2} = -\frac{A}{2e\sqrt{J_1 J_3}} \left[1 + \frac{|J_4|}{2J_1} + \frac{J_5^2}{2J_1 J_3} + \frac{3|J_4| J_5^2}{8J_1^2 J_3} (1 + \cos^2 3\theta) \right]. \quad (107)$$

Finally, we mention that in the case of large $|J_4|$, $J_1 - |J_4| \ll J_1 + |J_4|$ (corresponding to $\omega_1 \ll \omega_2$), Eq. (105), which is correct for arbitrary $|J_4| < J_1$, reproduces to the first-order (in J_5^2) correction of Eq. (104):

$$\frac{J_1 - |J_4|}{J_1 + |J_4|} \ll 1, \quad J_5^2 \ll J_3(J_1 - |J_4|), \quad H_{c2} = \frac{-A}{2e\sqrt{J_3(J_1 - |J_4|)}} \left(1 + \frac{J_5^2 \cos^2 3\theta}{2J_3(J_1 - |J_4|)} \right). \quad (108)$$

D. Upper critical field in the presence of symmetry breaking field

We now come to the problem of calculating H_{c2} in the presence of a symmetry breaking field which pins the order parameter along a preferred axis. As in the main text, we take the symmetry breaking field to have $\epsilon_{xx} - \epsilon_{yy}$ symmetry, which implies a contribution to the free energy given by $\delta\tau_{ij}^z \eta_i^* \eta_j$. We then solve the GL equations in the presence of an in-plane magnetic field (see Sec. VIII C) for two cases: (i) when only J_4 is present ($J_5 = 0$), and (ii) when both J_4 and J_5 are present.

1. Symmetry breaking field δ and J_4

We first consider case of J_4 only, where trigonal anisotropy is set to zero [13, 14]. Starting from Eq. (54) and adding the symmetry breaking field, the GL equations take the form

$$-A\eta = [(J_1 D_{\perp}^2 + J_3 D_z^2)I - J_4 D_{\perp}^2 (\cos 2\theta \tau^z + \sin 2\theta \tau^x) + \delta \tau^z] \eta. \quad (109)$$

We follow the same approach as in prior parts of this section and rewrite the matrix equation in terms of position and momentum operators \hat{X} and \hat{P} to obtain

$$-\frac{A}{J_3} \eta = \left[\frac{1}{l_b^2} (\hat{P}^2 + \omega^2 \hat{X}^2) I - \frac{J_4}{J_3 l_b^2} \hat{X}^2 (\cos 2\theta \tau^z + \sin 2\theta \tau^x) + \frac{\delta}{J_3} \tau^z \right] \eta. \quad (110)$$

This system of equations is similar to what has been considered in the context of UPt₃ [13, 14]. In order to find the upper critical field, we simply project it into the lowest Landau level solutions $(|0\rangle, 0)^T$ and $(0, |0\rangle)^T$. This is justified as long as $J_4 \ll J_1$. Noting that $\langle 0 | \hat{X}^2 | 0 \rangle = 1/2\omega$, we find the following implicit equation for the upper critical field

$$-\frac{A}{J_3 \omega} = \frac{1}{l_b^2} - \sqrt{\frac{J_4^2}{4\omega^4 J_3^2 l_b^4} \sin^2 2\theta + \left(\frac{\delta}{J_3 \omega} - \frac{J_4}{2\omega^2 J_3 l_b^2} \cos 2\theta \right)^2}. \quad (111)$$

To extract physical information from this equation we define the following quantities

$$x = \frac{J_4}{\omega^2 J_3} = \frac{J_4}{J_1}, \quad y = \frac{\delta}{J_3 \omega} = \frac{\delta}{\sqrt{J_1 J_3}}. \quad (112)$$

Here x is a measure of the strength of the hexagonal anisotropy J_4 as compared to the (unperturbed) cyclotron frequency, and y is a measure the symmetry breaking field as compared to the cyclotron frequency. In terms of these parameters the equation reads

$$-\frac{A}{J_3 \omega} = \frac{1}{l_b^2} - \sqrt{\frac{x^2}{4l_b^4} \sin^2 2\theta + \left(y - \frac{x}{2l_b^2} \cos 2\theta \right)^2}. \quad (113)$$

It is important to note that the magnetic length, and therefore the magnetic field, enters this expression in a non-trivial way. The physical implication is that the upper critical field will exhibit different behavior close to T_c as compared to far below T_c . This may be understood from the fact that the symmetry breaking field splits the transitions of two order parameter components at zero field, as T_c depends linearly on δ within the framework of GL theory.

We further rewrite the implicit equation for H_{c2} to obtain

$$-\frac{A}{J_3 \omega} = \frac{1}{l_b^2} - \sqrt{\frac{x^2}{4l_b^4} + y^2 - \frac{xy}{l_b^2} \cos 2\theta}, \quad (114)$$

or, in terms of the original variables,

$$-\frac{A}{\sqrt{J_1 J_3}} = 2eH - \sqrt{\frac{e^2 H^2 J_4^2}{J_1^2} + \frac{\delta^2}{J_1 J_3} - \frac{2eH J_4 \delta}{\sqrt{J_1^3 J_3}} \cos 2\theta}. \quad (115)$$

In the limit of small fields, expressed as $x \ll y l_b^2$ (corresponding to $eH J_4 \sqrt{J_3} \ll \delta \sqrt{J_1}$), we can ignore the first term in the square root and expand it in $x/y l_b^2$. In this case, we obtain the equation

$$-\frac{A}{J_3 \omega} = \frac{1}{l_b^2} - |y| \left(1 - \frac{x}{2y l_b^2} \cos 2\theta \right), \quad (116)$$

from which we obtained the upper critical field in the limit of small fields as

$$H_{c2} = -\frac{A - |\delta|}{2e J_3 \omega} \left(1 - \frac{J_4 \operatorname{sgn}(\delta)}{2J_1} \cos 2\theta \right). \quad (117)$$

Since Eq. (114) is a quadratic equation for $1/l_b^2 \sim H$, we can solve it for H_{c2} . To this end, we first define $-A/|\delta| = t = t(T)$, which is a function of temperature. We then find for H_{c2}

Symbol	Definition	Physical meaning
l_b	$1/l_b^2 = 2eH$	Magnetic length
δ	$g(u_{xx} - u_{yy})$	Strength symmetry breaking pinning field
ω	$\sqrt{J_1/J_3}$	Cyclotron frequency of the system without crystal anisotropy effects
x	J_4/J_1	Dimensionless measure of J_4
y	$\delta/\sqrt{J_1 J_3}$	Effective measure of symmetry breaking field
z	$J_5/\sqrt{J_1 J_3}$	Dimensionless measure of J_5
ΔT_c	$ \delta /A'$	Shift of T_c due to symmetry breaking field
T_c^*	$T_c + \Delta T_c$	The new critical temperature in the presence of symmetry breaking field
t	$-1 - (T - T_c^*)/\Delta T_c$	Measure of temperature in units of ΔT_c

TABLE III: This Table lists and summarizes the definitions used in this section for calculating the upper critical field in the presence of a symmetry breaking field.

$$2eH_{c2} = \frac{xy \cos 2\theta - 2t|y| - \sqrt{(xy \cos 2\theta - 2t|y|)^2 - y^2(x^2 - 4)(1 - t^2)}}{(x^2/2 - 2)} \quad (118)$$

$$= \frac{-(2AJ_1 + \delta J_4 \cos 2\theta) + \sqrt{(2J_1A + \delta J_4 \cos 2\theta)^2 + (4J_1^2 - J_4^2)(A^2 - \delta^2)}}{(4J_1^2 - J_4^2)\sqrt{J_3/4J_1}}. \quad (119)$$

At this point, it is worth commenting on the variable t [the parameters x and y were defined in Eq. (112)]. To make its significance explicit, we write explicitly $A = A'(T - T_c)$. In weak-coupling A' is equal to (up to the constant of the order one) the density of states. Then, the transition temperature in the presence of the pinning field δ is shifted to $T_c^* = T_c + |\delta|/A'$, or $\Delta T_c = T_c^* - T_c = |\delta|/A'$. In this notation, $t = -1 - (T - T_c^*)/\Delta T_c$, and t takes the role of an effective temperature through $T = T_c^* - (t + 1)\Delta T_c$. Note that in the Main Text we have left the proportionality constant A' implicit in the definition of t . Also note that in the superconducting state t takes values $t \geq -1$. We thus observe that the upper critical field, in particular its angular dependence, is a function of temperature through $t = t(T)$.

Let us see how this is reflected in the H_{c2} anisotropy coefficient $H_{c2}(\frac{\pi}{2})/H_{c2}(0)$. We find that it takes the form

$$\frac{H_{c2}(\frac{\pi}{2})}{H_{c2}(0)} = \frac{-x \operatorname{sgn}(y) - 2t - |2 + x \operatorname{sgn}(y)t|}{x \operatorname{sgn}(y) - 2t - |2 - x \operatorname{sgn}(y)t|}. \quad (120)$$

Close to T_c^* , at $t < 2/x$ (corresponds to $T > T_c - 2J_1|\delta|/J_4A'$), it can be shown to reduce to

$$\frac{H_{c2}(\frac{\pi}{2})}{H_{c2}(0)} = \frac{1 + x \operatorname{sgn}(y)/2}{1 - x \operatorname{sgn}(y)/2} = \frac{1 + J_4 \operatorname{sgn}(\delta)/2J_1}{1 - J_4 \operatorname{sgn}(\delta)/2J_1}, \quad (121)$$

which is independent of temperature and in agreement with Eq. (116). In contrast, when $t > 2/x$, i.e., at temperatures far below T_c^* , we find that [in case $\operatorname{sgn}(y) > 0$]

$$\frac{H_{c2}(\frac{\pi}{2})}{H_{c2}(0)} = -\frac{1+t}{1-t} = 1 + \frac{2}{t-1} = 1 + \frac{2}{(T_c^* - T)/\Delta T_c - 2}. \quad (122)$$

Since this expression does not depend on x , we conclude that far below T_c^* (measured in units of ΔT_c), the upper critical field anisotropy ratio has a temperature dependence which is independent of J_4 (See Main Text).

Strictly speaking, Eq. (111) is valid when J_4 is small. We can also address a different limiting, in which no assumptions are made with regard to J_4 , but instead we assume relatively large magnetic field (temperature is far below T_c), expressed as $eH\sqrt{J_3(J_1 - |J_4|)} \gg |\delta|$. In this case, the equation from which H_{c2} can be determined reads

as

$$-\frac{A}{eH\sqrt{J_1J_3}} = \sqrt{1 - \frac{J_4}{J_1}} + \sqrt{1 + \frac{J_4}{J_1}} - \left[2 - 2\sqrt{1 - \frac{J_4^2}{J_1^2}} + \frac{2\delta}{eH\sqrt{J_1J_3}} \cos 2\theta \left(\sqrt{1 - \frac{|J_4|}{J_1}} - \sqrt{1 + \frac{|J_4|}{J_1}} \right) + \frac{\delta^2}{e^2H^2J_1J_3} \left(\cos^2 2\theta + \sin^2 2\theta \frac{2\sqrt{1 - \frac{J_4^2}{J_1^2}}}{\sqrt{1 - \frac{J_4}{J_1}} + \sqrt{1 + \frac{J_4}{J_1}}} \right) \right]^{1/2}. \quad (123)$$

This result is applicable as long as $|J_4| < J_1$. If, in addition, we demand that $|\delta| \ll eH\sqrt{J_3}(\sqrt{J_1 + |J_4|} - \sqrt{J_1 - |J_4|})$, the result takes the simple form

$$H_{c2} = \frac{-A - \delta \operatorname{sgn}(J_4) \cos 2\theta}{2e\sqrt{J_3}(J_1 - |J_4|)}. \quad (124)$$

2. Symmetry breaking field δ and $J_{4,5}$

As a next step we introduce the trigonal anisotropy term proportional to J_5 . Including this term, the GL equations take the following form

$$-A\eta = [(J_1D_\perp^2 + J_3D_z^2)I + J_4D_\perp^2(\cos 2\theta\tau^z + \sin 2\theta\tau^x) + J_5\{D_z, D_\perp\}(-\cos \theta\tau^z + \sin \theta\tau^x) + \delta\tau^z] \eta. \quad (125)$$

In terms of the position and momentum operators the equations read

$$-\frac{A}{J_3}\eta = \left[\frac{1}{l_b^2}(\hat{P}^2 + \omega^2\hat{X}^2)I - \frac{J_4}{J_3l_b^2}\hat{X}^2(\cos 2\theta\tau^z + \sin 2\theta\tau^x) + \frac{J_5}{J_3l_b^2}\{\hat{X}, \hat{P}\}(-\cos \theta\tau^z + \sin \theta\tau^x) + \frac{\delta}{J_3}\tau^z \right] \eta. \quad (126)$$

Under the assumption that both J_4 and J_5 are small, we can construct a degenerate perturbation theory up to second order. Such perturbation theory up to first order is what produced Eq. (111), and the effect of J_5 only enters at second order. Using the same basis states as in Eq. (85) and writing η as $\eta = \alpha|1\rangle + \beta|2\rangle$, we find the following matrix equation for the coefficients α, β

$$-\frac{A}{J_3}\eta = \left[\frac{\omega}{l_b^2}I - \frac{J_5^2}{2J_3^2l_b^2\omega}I - \frac{J_4^2}{8J_3^2l_b^2\omega^3}I - \frac{J_4}{2J_3l_b^2\omega}(\cos 2\theta\tau^z + \sin 2\theta\tau^x) + \frac{\delta}{J_3}\tau^z \right] \eta. \quad (127)$$

In the same way as above, the upper critical is found by considering the lowest eigenvalue of the matrix equation and setting it equal to $-A/J_3\omega$. This straightforwardly gives the following generalization of Eq. (111)

$$\begin{aligned} -\frac{A}{J_3\omega} &= \frac{1}{l_b^2} \left(1 - \frac{J_5^2}{2J_3^2\omega^2} - \frac{J_4^2}{8J_3^2\omega^4} \right) - \sqrt{\frac{J_4^2}{4\omega^4J_3^2l_b^4} \sin^2 2\theta + \left(\frac{\delta}{J_3\omega} - \frac{J_4}{2\omega^2J_3l_b^2} \cos 2\theta \right)^2} \\ &= \frac{1}{l_b^2} \left(1 - \frac{z^2}{2} - \frac{x^2}{8} \right) - \sqrt{\frac{x^2}{4l_b^4} \sin^2 2\theta + \left(\frac{z^2}{2l_b^2} - \frac{x^2}{8l_b^2} + y - \frac{x}{2l_b^2} \cos 2\theta \right)^2}, \end{aligned} \quad (128)$$

where we have used the same definitions of x, y as in Eq. (112), in addition to the definition $z = J_5/J_3\omega = J_5/\sqrt{J_1J_3}$. It is easy to see from this equation, that to second order in both J_4 and J_5 the corrections to Eq. (111) do not introduce qualitatively different behavior.

One can carry out perturbation theory up to third order in both J_4 and J_5 , which will introduce the sixfold anisotropy into the equation, entering as a term proportional to $\sim |J_4|J_5^2$.

To conclude, we consider a final limiting case, in which we take $J_4 = 0$ and assume that we are in a regime of large fields, i.e., far below T_c measured in units of δ . In this case we must again resort to quasi-degenerate perturbation theory and derive the Hamiltonian in the low-energy subspace to second order in J_5/J_3 . The calculation proceeds along the same line as the calculation based following Eq. (86). We find the Hamiltonian up to second order as

$$H_{ij}^{(0)} + H_{ij}^{(2)} = \frac{\omega}{l_b^2} \left[1 - \frac{J_5^2}{2\omega^2J_3^2} \left(\cos^2 \theta + \sin^2 \theta \frac{1}{1 - (\bar{\delta}/2)^2} \right) + \bar{\delta}\tau^z - \frac{J_5^2 \sin \theta}{2\omega^2J_3^2} \frac{\bar{\delta}/2}{1 - (\bar{\delta}/2)^2} (\sin \theta\tau^z + \cos \theta\tau^x) \right], \quad (129)$$

where we have defined $\bar{\delta} = l_b^2 \delta / \omega$. Since $l_b^2 \sim 1/H$ we see that this expression indeed only makes sense at high fields. Note that if we take symmetry breaking field to zero, $\delta \rightarrow 0$, we simply obtain

$$H_{ij}^{(0)} + H_{ij}^{(2)} = \frac{\omega}{l_b^2} \left[1 - \frac{J_5^2}{2\omega^2 J_3^2} \right], \quad (130)$$

which is the correct result up to second order in J_5/J_3 according to Eq. (69). Diagonalizing the matrix of Eq. (129) and setting it equal to $-A/J_3$ yields the following implicit equation for the upper critical field

$$-\frac{A}{J_3} = \frac{\omega}{l_b^2} \left[1 - \frac{J_5^2}{2\omega^2 J_3^2} \left(\cos^2 \theta + \sin^2 \theta \frac{1}{1 - (\bar{\delta}/2)^2} \right) - \sqrt{\frac{J_5^4 \sin^2 \theta}{4\omega^4 J_3^4} \frac{(\bar{\delta}/2)^2}{(1 - \bar{\delta}^2/4)^2} + \bar{\delta}^2 - \bar{\delta} \frac{J_5^2 \sin^2 \theta}{\omega^2 J_3^2} \frac{\bar{\delta}/2}{1 - (\bar{\delta}/2)^2}} \right]. \quad (131)$$

From this equation we can already infer that for large fields, i.e., $\bar{\delta} \rightarrow 0$ the twofold anisotropy of the angular dependence vanishes.

E. The operator algebra of squeezed states

In this section we provide additional information on the squeezing operators used to solve linearized GL equations in a magnetic field. The starting point is the simple harmonic oscillator Hamiltonian $\hat{P}^2 + \omega^2 \hat{X}^2$. The eigenvalues of this operator are found using the raising and lowering operators $\Pi_{\pm} = (\hat{P} + i\omega \hat{X})/\sqrt{2\omega}$, with $\Pi_+ = \Pi_-^\dagger$, which satisfy $[\Pi_-, \Pi_+] = 1$.

The squeezing operator is defined as

$$\hat{S}(z) = \exp \left\{ \frac{1}{2} (z^* \Pi_-^2 - z \Pi_+^2) \right\}, \quad z = r e^{i\theta} \quad (132)$$

where z is a complex number characterizing the squeezing. The name squeezing operator originates from the fact that momentum and position quadratures are ‘‘squeezed’’ under application of these unitary operators. Note that the squeezing operators are unitary and therefore preserve commutation relations.

Their action on the raising and lowering operators is given by

$$\begin{aligned} \hat{S}^\dagger(z) \Pi_- \hat{S}(z) &= \cosh r \Pi_- - e^{i\theta} \sinh r \Pi_+ \\ \hat{S}^\dagger(z) \Pi_+ \hat{S}(z) &= \cosh r \Pi_+ - e^{-i\theta} \sinh r \Pi_- \end{aligned} \quad (133)$$

Since the position and momentum operators are related to $\Pi_{\pm} \pm \Pi_{\mp}$, we have the for these quantities after application of the squeezing operators

$$\begin{aligned} \hat{S}^\dagger(z) \hat{P} \hat{S}(z) &= (\cosh r - \cos \theta \sinh r) \hat{P} + \omega \sin \theta \sinh r \hat{X} \\ \hat{S}^\dagger(z) \hat{X} \hat{S}(z) &= (\cosh r + \cos \theta \sinh r) \hat{X} + \frac{1}{\omega} \sin \theta \sinh r \hat{P} \end{aligned} \quad (134)$$

Note that in case z is purely real, $\theta = 0$, the momentum and position operators transform as

$$\begin{aligned} \hat{S}^\dagger(z) \hat{P} \hat{S}(z) &= e^{-r} \hat{P} \\ \hat{S}^\dagger(z) \hat{X} \hat{S}(z) &= e^r \hat{X} \end{aligned} \quad (135)$$

and it is precisely this rescaling which is a manifestation of squeezing. It is this property that will be used to express the solutions of two harmonic oscillator problems with different frequencies in terms of the same raising and lowering operators.

For the present purposes we need the matrix elements of the squeezing operators. In order to find them we first the structure of the squeezed vacuum. In particular, we relate the raising and lowering operation on the squeezed vacuum. We find

$$\hat{S} \Pi_- |0\rangle = 0 = \hat{S} \Pi_- \hat{S}^\dagger \hat{S} |0\rangle = (\cosh r \Pi_- + \sinh r \Pi_+) \hat{S} |0\rangle, \quad \rightarrow \quad \cosh r \Pi_- \hat{S} |0\rangle = -\sinh r \Pi_+ \hat{S} |0\rangle \quad (136)$$

With the help of this relation we find the following expressions for the matrix elements that need to be calculated,

$$\begin{aligned} \langle n | \Pi_+ \Pi_- \hat{S} |0\rangle &= n \langle n | \hat{S} |0\rangle, \\ \langle n | \Pi_- \Pi_+ \hat{S} |0\rangle &= (n+1) \langle n | \hat{S} |0\rangle, \\ \langle n | \Pi_+ \Pi_+ \hat{S} |0\rangle &= -n \frac{\cosh r}{\sinh r} \langle n | \hat{S} |0\rangle, \\ \langle n | \Pi_- \Pi_- \hat{S} |0\rangle &= -(n+1) \frac{\sinh r}{\cosh r} \langle n | \hat{S} |0\rangle, \end{aligned} \quad (137)$$

We find that the matrix elements $\langle n|\hat{S}|0\rangle$ are the only objects we need. Furthermore, for our purposes we only require the absolute value squared $|\langle n|\hat{S}|0\rangle|^2$, which is known in the literature [12], and given by

$$|\langle n|\hat{S}|0\rangle|^2 = \frac{n!}{(\frac{n}{2}!)^2 2^n} \frac{\tanh^n r}{\cosh r}, \quad n = 0, 2, 4, 6, \dots \quad (138)$$

IX. MICROSCOPIC CALCULATION OF GL COEFFICIENTS

The purpose of this section is to calculate the GL coefficients, which up to this point have been treated as phenomenological expansion constants, from a microscopic model for paired electrons within a weak-coupling BCS approach. This will allow us to express the GL coefficients in terms of quantities characterizing the electronic normal state, i.e., the Fermi surface properties.

The calculation proceeds as follows. We first consider a microscopic mean-field theory in which pairs of electrons are coupled to a bosonic order parameter field. The mean-field action is quadratic in the fermionic fields, which can be integrated out to obtain an effective free energy the superconducting order parameter fields. The effective action is an expansion of this free energy in the order parameter fields (i.e., the Ginzburg-Landau free energy) with the expansion coefficients given by fermion loop diagrams. Explicit evaluation of the loop diagrams yields expressions for GL coefficients in terms of quantities directly related to the Fermi surface electrons.

The starting point of our calculation is a mean-field action $S = S_0 + S_\Delta$, expressed in terms of the electron operators $\psi_\alpha(\vec{x}, \tau)$, where S_Δ represents a coupling to a pairing potential $\hat{\Delta}(\vec{x}, \vec{x}')$ (a matrix in spin space). Specifically, we start from the action

$$S = \int d\tau d^3\vec{x} \psi_\alpha^\dagger(\vec{x}, \tau) \left[\partial_\tau + \varepsilon(-i\partial/\partial\vec{x}) - \varepsilon_F \right] \psi_\alpha(\vec{x}, \tau) + \frac{1}{2} \int d\tau d^3\vec{x} d^3\vec{x}' \left[\hat{\Delta}_{\alpha\gamma}(\vec{x}, \vec{x}') (i\sigma^y)_{\gamma\beta} \psi_\alpha^\dagger(\vec{x}, \tau) \psi_\beta^\dagger(\vec{x}', \tau) + \text{h.c.} \right] \quad (139)$$

Here $\varepsilon(\vec{p})$ is the normal state kinetic energy as function of momentum operator $\vec{p} = -i\partial/\partial\vec{x}$, and ε_F is Fermi energy. At this stage we do not include the electromagnetic gauge potential explicitly, but instead impose gauge invariance at the end.

Taking the Fourier transform, the superconducting part of the action is expressed as

$$S_\Delta = \frac{1}{2} \int \frac{d\tau d^3\vec{k} d^3\vec{q}}{(2\pi)^6} \hat{\Delta}_{\alpha\gamma}(\vec{q}, \vec{k}) (i\sigma^y)_{\gamma\beta} \psi_\alpha^\dagger(\vec{k} + \frac{\vec{q}}{2}, \tau) \psi_\beta^\dagger(-\vec{k} + \frac{\vec{q}}{2}, \tau) + \text{h.c.}, \quad (140)$$

where \vec{k} is the momentum variable conjugate to the relative coordinate, and \vec{q} is conjugate to the center-of-mass coordinate as follows

$$\hat{\Delta}(\vec{q}, \vec{k}) = \int d\vec{x} d\vec{x}' \hat{\Delta}(\vec{x}, \vec{x}') \exp[-i\vec{q} \cdot \frac{\vec{x} + \vec{x}'}{2} - i\vec{k} \cdot (\vec{x} - \vec{x}')]. \quad (141)$$

The superconducting order parameter $\hat{\Delta}(\vec{q}, \vec{k})$ is decomposed as $\hat{\Delta}(\vec{q}, \vec{k}) = \sum_m \eta_m(\vec{q}) \hat{\Delta}_m(\vec{k})$. Here $\eta_m(\vec{q})$ are the complex order parameters and $\hat{\Delta}_m(\vec{k})$ are the superconducting structure factors corresponding to component m of the multi-dimensional representation [specified in Eq. (158) below].

To proceed, we define a Nambu spinor in particle-hole space as

$$\Phi(\vec{k}, \tau) = \begin{pmatrix} \psi_\alpha(\vec{k}, \tau) \\ \epsilon_{\alpha\beta} \psi_\beta^\dagger(-\vec{k}, \tau) \end{pmatrix}, \quad (142)$$

and with this definition the integrand of (140) can be expressed as

$$\Phi^\dagger(\vec{k} + \frac{\vec{q}}{2}, \tau) \hat{\Sigma}_\Delta(\vec{k}, \vec{q}) \Phi(\vec{k} - \frac{\vec{q}}{2}, \tau), \quad (143)$$

where the mean-field superconducting self energy $\hat{\Sigma}_\Delta$ is given by

$$\hat{\Sigma}_\Delta(\vec{k}, \vec{q}) = \begin{pmatrix} 0 & \hat{\Delta}(\vec{q}, \vec{k}) \\ \hat{\Delta}^\dagger(-\vec{q}, \vec{k}) & 0 \end{pmatrix} = \hat{\Delta}(\vec{q}, \vec{k}) \tau^+ + \hat{\Delta}^\dagger(-\vec{q}, \vec{k}) \tau^- \quad (144)$$

with $\tau^\pm = (1/2)(\tau^x \pm i\tau^y)$.

We are now in the position to write down the full action $S = S_0 + S_\Delta$, which is bilinear in the electron operators and can be integrated to obtain an effective $S_{\text{eff}}[\eta_i]$. First, we transform to Matsubara frequency space and write $k = (i\omega, \vec{k})$ and $q = (0, \vec{q})$. Note that we have set the bosonic frequencies to zero since we will only be interested in static spatial inhomogeneities. The full electronic action S then takes the form

$$S = -\frac{1}{2} \sum_{p,q} \Phi^\dagger(k) \hat{\mathcal{G}}_0^{-1}(k) \Phi(k) + \frac{1}{2} \sum_{p,q} \Phi^\dagger(k + \frac{q}{2}) \hat{\Sigma}_\Delta(\vec{k}, \vec{q}) \Phi(k - \frac{q}{2}), \quad (145)$$

where we omitted a constant part that does not contain Φ operators. Here $\hat{\mathcal{G}}_0^{-1}(k)$ is the inverse Fermi liquid Green's function, $\hat{\mathcal{G}}_0(\vec{k}, \tau) = -\langle \mathbf{T}_\tau \Phi_{\vec{k}}(\tau) \Phi_{\vec{k}}^\dagger(0) \rangle$, given by

$$\hat{\mathcal{G}}_0^{-1}(k) = i\omega - \xi(\vec{k})\tau^z. \quad (146)$$

We have abbreviated $\xi(\vec{k}) = \varepsilon(\vec{k}) - \varepsilon_F$. As a result, the Green's function $\hat{\mathcal{G}}_0$ is block diagonal, with the electron and hole Green's functions G_\pm on the diagonal. The hole Green's function is obtained from particle-hole conjugation of the electron Green's function, and one has

$$\hat{\mathcal{G}}_0 = \begin{pmatrix} \hat{G}_+ & \\ & \hat{G}_- \end{pmatrix} = \begin{pmatrix} \hat{G}_+(\vec{k}, i\omega) & \\ & -\hat{G}_+(\vec{k}, -i\omega) \end{pmatrix}. \quad (147)$$

The effective action $S_{\text{eff}}[\eta_i] = (1/T)F[\eta_i]$ is obtained by the standard procedure of integrating out the fermionic degrees of freedom,

$$e^{-S_{\text{eff}}[\eta_i]} = \int \mathcal{D}\psi^\dagger \mathcal{D}\psi e^{-S[\eta_i, \psi^\dagger, \psi]}. \quad (148)$$

The quasiparticle part of the mean-field free energy can be expressed as

$$F[\eta_i] = -T \text{Tr} \ln \hat{\mathcal{G}}^{-1} = F_0 - T \text{Tr} \ln(1 - \hat{\mathcal{G}}_0 \hat{\Sigma}_\Delta), \quad (149)$$

where F_0 is the normal state part of free energy. Here, the trace Tr is understood as a sum over frequency and momenta, and as a matrix trace over the matrix structure of $\hat{\mathcal{G}}_0$ and $\hat{\Sigma}_\Delta$: $\text{Tr} \equiv \sum_\omega \sum_{\vec{k}} \text{tr}$. We note that since we restrict to the quasiparticle part of the free energy, we have left the contribution to the free energy which is quadratic in the order parameter field and explicitly depends on the pairing interaction implicit.

We now focus on the derivation of the free energy to the second order in $\hat{\Delta}$. Explicitly, it is given by the expression

$$F[\eta_i] = F_0 + \frac{T}{2} \text{Tr} [\hat{\mathcal{G}}_0 \hat{\Sigma} \hat{\mathcal{G}}_0 \hat{\Sigma}] = F_0 + \frac{T}{2} \sum_\omega \sum_{\vec{k}, \vec{q}} \text{tr} [\hat{\mathcal{G}}_0(\vec{k} + \frac{\vec{q}}{2}, i\omega) \hat{\Sigma}_\Delta(\vec{q}, \vec{k}) \hat{\mathcal{G}}_0(\vec{k} - \frac{\vec{q}}{2}, i\omega) \hat{\Sigma}_\Delta(-\vec{q}, \vec{k})]. \quad (150)$$

The self-energy $\hat{\Sigma}_\Delta$ contains the order parameter fields and using Eq. (144) the expression for the superconducting part of free energy can be rewritten in the form

$$F_\Delta = \frac{T}{2} \text{Tr} [\hat{\mathcal{G}}_0 \hat{\Sigma} \hat{\mathcal{G}}_0 \hat{\Sigma}] = \sum_{\vec{q}} \sum_{m,n} \eta_m^*(\vec{q}) \mathcal{Q}_{mn}(\vec{q}) \eta_n(\vec{q}), \quad (151)$$

where $\eta_n(\vec{q})$ are the order parameter fields and the matrix $\mathcal{Q}_{mn}(\vec{q})$ is given by

$$\begin{aligned} \mathcal{Q}_{mn}(\vec{q}) &= T \sum_\omega \sum_{\vec{k}} G_+(\vec{k} + \frac{\vec{q}}{2}, i\omega) G_-(\vec{k} - \frac{\vec{q}}{2}, i\omega) \text{tr} [\hat{\Delta}_n(\vec{k}) \hat{\Delta}_m^\dagger(\vec{k})] \\ &\equiv T \sum_\omega \sum_{\vec{k}} G_+(\vec{k} + \frac{\vec{q}}{2}, i\omega) G_-(\vec{k} - \frac{\vec{q}}{2}, i\omega) Q_{mn}(\vec{k}). \end{aligned} \quad (152)$$

Here we have defined the form factor matrix $Q_{mn}(\vec{k}) = \text{tr} [\hat{\Delta}_n(\vec{k}) \hat{\Delta}_m^\dagger(\vec{k})]$.

Expanding now the electron Green functions in small momenta \vec{q} using

$$\xi(\vec{k} \pm \frac{\vec{q}}{2}) = \xi(\vec{k}) \pm \frac{1}{2} \vec{v}(\vec{k}) \cdot \vec{q} + \mathcal{O}(q^2), \quad (153)$$

(the second order term turns out to make parametrically smaller contribution) we obtain eventually

$$\mathcal{Q}_{mn}(\vec{q}) \approx -T \sum_{\omega, \vec{k}} \frac{1}{\omega^2 + \xi^2(\vec{k})} \left(1 + \frac{[\vec{v}(\vec{k}) \cdot \vec{q}]^2}{4} \frac{\xi^2(\vec{k}) - 3\omega^2}{[\omega^2 + \xi^2(\vec{k})]^2} \right) Q_{mn}(\vec{k}). \quad (154)$$

This expression is the starting point for the microscopic derivation of the coefficient in our GL theory.

Below we will consider small distortions of the Fermi surface, either due to trigonal crystal anisotropy, or uniaxial strain-induced anisotropy. In this case, one can write $\xi(\vec{k}) = \xi_0(\vec{k}) + \delta\xi(\vec{k})$, $\vec{v}(\vec{k}) = \vec{v}_0(\vec{k}) + \delta\vec{v}(\vec{k})$, with $\xi_0(\vec{k}) = k^2/2m - \varepsilon_F$, $\vec{v}_0(\vec{k}) = \vec{k}/m$ and $\delta\vec{v}(\vec{k}) = \partial\delta\xi(\vec{k})/\partial\vec{k}$. To the leading order, gradient term can be expanded as

$$\frac{(\vec{v} \cdot \vec{q})^2 (\xi^2 - 3\omega^2)}{(\xi^2 + \omega^2)^3} \approx \frac{(\vec{v}_0 \cdot \vec{q})^2 (\xi_0^2 - 3\omega^2)}{(\omega^2 + \xi_0^2)^3} + 2 \frac{(\vec{v}_0 \cdot \vec{q})(\delta\vec{v} \cdot \vec{q})(\xi_0^2 - 3\omega^2)}{(\omega^2 + \xi_0^2)^3} + 4\xi_0 \frac{(\vec{v}_0 \cdot \vec{q})^2 (5\omega^2 - \xi_0^2)}{(\omega^2 + \xi_0^2)^4} \delta\xi. \quad (155)$$

A. Calculation of gradient coefficients $J_{1,2,3,4,5}$ in presence of trigonal crystal anisotropy

We now proceed to the calculation of the gradient coefficients $J_{1,2,3,4,5}$. In particular, we demonstrate that the trigonal gradient term $f_{D,\text{trig}}$ (see Main Text) is generated only when the Fermi surface has trigonal crystal anisotropy, or when the gap functions are general linear combinations of crystal harmonics allowed by trigonal symmetry. Hence, we take into account the trigonal anisotropy of the Fermi surface (FS) and the specific form of the pairing potential $\hat{\Delta}_m(\vec{k})$ applicable to trigonal symmetry.

In the case of trigonal distortion, energy spectrum of electrons can be described as

$$\xi(\vec{k}) = \xi_0(\vec{k}) + \delta\xi(\vec{k}) = \xi_0(\vec{k}) + i \frac{\lambda_{\text{trig}}}{2mk_F^2} k_z (k_+^3 - k_-^3) = \xi_0(\vec{k}) + \frac{\lambda_{\text{trig}}}{mk_F^2} k_z k_y (k_y^2 - 3k_x^2), \quad (156)$$

where $\xi_0 = k^2/2m - \varepsilon_F$, $k_{\pm} = k_x \pm ik_y$ and $k_F = \sqrt{2m\varepsilon_F}$ is Fermi momentum. Here we have neglected all other fourth order contribution to the dispersion, since they affect the result only quantitatively and in a way unimportant for our purposes. In particular, they do not affect the gradient coefficient of $f_{D,\text{trig}}$, which is what we are mainly interested in. The corresponding change in the velocity equals

$$\delta\vec{v}(\vec{k}) = \frac{\lambda_{\text{trig}}}{2mk_F^2} \begin{pmatrix} -6k_x k_y k_z \\ 3k_z k_y^2 - 3k_z k_x^2 \\ k_y^3 - 3k_x^2 k_y \end{pmatrix}. \quad (157)$$

Then, the recipe is to plug $\delta\xi$ and $\delta\vec{v}$ back into Eq. (155) and perform the integration over ξ_0 , the summation over ω and the average over the directions of \vec{k} . Though straightforward, this procedure is somewhat tedious. We note that the third term in (155) is odd in ξ_0 and thus, to the leading order, is zero after integration. To obtain a non-zero contribution, one needs to carefully extract the ξ_0 dependence, i.e., take $k \approx k_F(1 + \xi_0/2\varepsilon_F)$ everywhere. In addition, the ξ_0 dependence of density of states must be taken into account. In three dimensions, and for a quadratic spectrum, it equals $N(\varepsilon_F + \xi_0) \approx N(\varepsilon_F)(1 + \xi_0/2\varepsilon_F)$.

In order to perform the averaging over angles, we calculate form factors $Q_{mn}(\vec{k}) = \text{tr} [\hat{\Delta}_n(\vec{k}) \hat{\Delta}_m^\dagger(\vec{k})]$. For the odd-parity two-component pairing in crystals with trigonal symmetry (D_{3d}) pairing potentials $\hat{\Delta}_{1,2}(\vec{k})$ are given by

$$\Delta_1(\vec{k}) = \lambda_a \hat{k}_x \sigma^z + \lambda_b \hat{k}_z \sigma^x + \lambda_c (\hat{k}_y \sigma^x + \hat{k}_x \sigma^y), \quad \Delta_2(\vec{k}) = \lambda_a \hat{k}_y \sigma^z + \lambda_b \hat{k}_z \sigma^y + \lambda_c (\hat{k}_x \sigma^x - \hat{k}_y \sigma^y) \quad (158)$$

with real coefficients $\lambda_{a,b,c}$. In hexagonal crystals, symmetry imposes the constraint $\lambda_c = 0$ (E_{1u} pairing) or $\lambda_a = \lambda_b = 0$ (E_{2u} pairing), whereas in trigonal crystals these p-wave spherical harmonics have E_u symmetry. With this pairing, we find for form-factors

$$\begin{aligned} Q_{11} &= 2\lambda_a^2 \hat{k}_x^2 + 2\lambda_b^2 \hat{k}_z^2 + 2\lambda_c^2 (\hat{k}_x^2 + \hat{k}_y^2) + 4\lambda_b \lambda_c \hat{k}_z \hat{k}_y, \\ Q_{22} &= 2\lambda_a^2 \hat{k}_y^2 + 2\lambda_b^2 \hat{k}_z^2 + 2\lambda_c^2 (\hat{k}_x^2 + \hat{k}_y^2) - 4\lambda_b \lambda_c \hat{k}_z \hat{k}_y, \\ Q_{12} = Q_{21} &= 2\lambda_a^2 \hat{k}_x \hat{k}_y + 4\lambda_b \lambda_c \hat{k}_z \hat{k}_x. \end{aligned} \quad (159)$$

After the straightforward calculations, the expression for the gradient part of free energy reads as (we omit indices m, n for brevity)

$$F_{\nabla} = \sum_{\vec{q}} \eta^\dagger(\vec{q}) \mathcal{Q}(\vec{q}) \eta(\vec{q}) \quad (160)$$

where

$$\mathcal{Q}(\vec{q}) = J_1(q_x^2 + q_y^2)I + J_3q_z^2I + J_4[(q_x^2 - q_y^2)\tau^z + 2q_xq_y\tau^x] + 2J_5[q_zq_y\tau^z + q_zq_x\tau^x]. \quad (161)$$

Coefficients J_i are given by

$$J_i = \tilde{J}_i \frac{7\zeta(3)N(\varepsilon_F)v_F^2}{120\pi^2T^2}. \quad (162)$$

$$\tilde{J}_1 = 2\lambda_a^2 + \lambda_b^2 + 4\lambda_c^2, \quad \tilde{J}_3 = \lambda_a^2 + 3\lambda_b^2 + 2\lambda_c^2, \quad \tilde{J}_4 = \lambda_a^2 - 2c\lambda_{\text{trig}}\lambda_b\lambda_c, \quad \tilde{J}_5 = 2\lambda_b\lambda_c - c\lambda_{\text{trig}}\lambda_a^2, \quad (163)$$

with $c = 22/21$.

We see that, indeed, trigonal anisotropy of Fermi surface and special form of the pairing function lead to the generation of the trigonal gradient term J_5 . We see also that, to the leading order, the term J_2 is absent. It becomes non-zero if one takes into account particle-hole unsymmetry (dependence of density of states on energy). This term is of the order $(T_c/\varepsilon_F)^2 \ll 1$.

B. Calculation of contributions of the symmetry breaking field

The effect of the symmetry breaking field can be described by the Hamiltonian

$$H_{\text{SB}} = \frac{\lambda_{\text{SB}}}{2m} \sum_{\vec{k}} \psi^\dagger(\vec{k})\psi(\vec{k})(k_x^2 - k_y^2). \quad (164)$$

For simplicity, we particularize to the case of hexagonal symmetry [i.e. take $\lambda_c = 0$ in (158)] and do not take into account any fourth-order terms in dispersion relation. The presence of the symmetry breaking field leads to the dispersion relation

$$\xi(\vec{k}) = \frac{k^2}{2m} - \varepsilon_F + \frac{\lambda_{\text{SB}}}{2m}(k_x^2 - k_y^2), \quad (165)$$

with $\delta\xi(\vec{k}) = \lambda_{\text{SB}}(k_x^2 - k_y^2)/2m$. Again, to extract the key physical features we treat λ_{SB} as a small perturbation (in principle, the problem can be solved exactly for any finite λ_{SB}).

To the leading order, the symmetry-breaking field couples to the superconducting order parameter, according to Eq. (30). To find this coupling explicitly, we consider the first term in Eq. (154), and write (we omit indices m, n)

$$\mathcal{Q}_0^{\text{SB}} = 2T \sum_{\omega, \vec{k}} \frac{\xi_0(\vec{k})\delta\xi(\vec{k})}{[\omega^2 + \xi_0^2(\vec{k})]^2} Q(\vec{k}). \quad (166)$$

Again, we carefully extract ξ_0 to obtain the leading non-vanishing contribution.

After the integration over ξ_0 , we end up with the formally diverging sum over ω , which requires a cut-off regularization by the (Debye) frequency $\omega_{\text{max}} \sim \omega_D$:

$$\sum_{\omega} \int d\xi_0 \frac{\xi_0^2}{(\omega^2 + \xi_0^2)^2} \approx \frac{1}{2T} \ln \frac{\omega_D}{T}. \quad (167)$$

After averaging over directions of \vec{k} , we find

$$\mathcal{Q}_0^{\text{SB}} \approx \frac{2}{5} \lambda_{\text{SB}} N(\varepsilon_F) \lambda_a^2 \ln \frac{\omega_D}{T} \tau^z, \quad (168)$$

or, equivalently, for free energy

$$F_0^{\text{SB}} = \sum_{\vec{q}} \eta^\dagger(\vec{q}) \mathcal{Q}_0^{\text{SB}} \eta(\vec{q}) = \left(\frac{2}{5} \lambda_{\text{SB}} N(\varepsilon_F) \lambda_a^2 \ln \frac{\omega_D}{T} \right) \sum_{\vec{q}} |\eta_1(\vec{q})|^2 - |\eta_2(\vec{q})|^2, \quad (169)$$

This term is responsible for the shift of T_c , $\Delta T_c/T_c \sim \lambda_{\text{SB}} \ln \omega_D/T$. This implies that the effect of a strain-induced Fermi surface distortion (λ_{SB}) on the shift of T_c is enhanced by $\ln \omega_D/T$. The coefficient on the right hand side of (169) is what we have called δ in the previous sections and Main Text.

Next, we calculate the gradient terms due to symmetry-breaking field, i.e., the second term in Eq. (154). Velocity is given now by

$$\delta \vec{v}(\vec{k}) = \frac{\lambda_{\text{SB}}}{m} \begin{pmatrix} k_x \\ -k_y \\ 0 \end{pmatrix}. \quad (170)$$

After straightforward integration, we find

$$F_{\nabla}^{\text{SB}} = \sum_{\vec{q}} \eta^\dagger(\vec{q}) \mathcal{Q}_{\nabla}^{\text{SB}}(\vec{q}) \eta(\vec{q}), \quad (171)$$

with the momentum-dependent matrix $\mathcal{Q}_{\nabla}^{\text{SB}}(\vec{q})$ given by

$$\mathcal{Q}_{\nabla}^{\text{SB}}(\vec{q}) = K_1(q_x^2 - q_y^2)I + K_2(q_x^2 + q_y^2)\tau^z + K_3q_z^2\tau^z. \quad (172)$$

These strain-induced contributions to the gradient terms have gradient coefficients given by

$$K_i = \tilde{K}_i \frac{\zeta(3)N(\varepsilon_F)v_F^2}{120\pi^2T^2} \lambda_{\text{SB}}, \quad (173)$$

where the \tilde{K}_i are given by

$$\tilde{K}_1 = 13\lambda_a^2 + 9\lambda_b^2, \quad \tilde{K}_2 = -\lambda_a^2, \quad \tilde{K}_3 = -5\lambda_a^2. \quad (174)$$

It is instructive to compare the coupling of symmetry-breaking field to the order-parameter and its derivatives. It is convenient to introduce the coherence length $\xi = \xi(T)$ and $\xi_0 = \xi(T=0) \sim v_F/T_c$ (Note that here ξ is used for coherence length). The ratio of the gradient term to the direct quadratic coupling to the order parameter equals

$$\frac{F_{\nabla}^{\text{SB}}}{F_0^{\text{SB}}} \sim \frac{v_F^2 q^2}{T^2 \ln \omega_D/T} \sim \frac{(\xi_0 q)^2}{\ln \omega_D/T}. \quad (175)$$

The relevant momenta are those where $q \sim 1/\xi$. Close to the transition temperature, $\xi_0 \ll \xi$, and we have

$$\frac{F_{\nabla}^{\text{SB}}}{F_0^{\text{SB}}} \sim \left(\frac{\xi_0}{\xi}\right)^2 \frac{1}{\ln \omega_D/T} \ll 1. \quad (176)$$

It follows from our calculation that the direct coupling of symmetry-breaking field to order parameter is much stronger than to its derivatives. It implies that the effect of uniaxial distortion field is much more pronounced in the case of two-component superconductors. Indeed, the effect of the symmetry breaking field in case of two-component order parameters is to shift the transition temperature. Single-component superconductors allow coupling to the derivatives of the order parameter only, thus significantly decreasing possible effects of the symmetry-breaking field.

-
- [1] G. E. Volovik and L. Gork'ov, Sov. Phys. JETP **61**, 843 (1985).
 - [2] M. Sigrist and K. Ueda, Rev. Mod. Phys. **63**, 239 (1991).
 - [3] V. Mineev and K. Samokhin, *Introduction to Unconventional Superconductivity*, (Gordon and Breach, New York, 1999).
 - [4] J. A. Sauls, Adv. Phys. **43**, 113 (1994).
 - [5] I. A. Luk'yanchuk, M. E. Zhitomirsky, Superconductivity Review 1, 207 (1995).
 - [6] M. E. Zhitomirsky, Zh. Eksp. Teor. Fiz. **97**, 1346 (1990) [Sov. Phys. JETP **70**, 760-768 (1990)].
 - [7] Yu. S. Barash and A. V. Galaktionov, Zh. Eksp. Teor. Fiz. **100**, 1699 (1991) [Sov. Phys. JETP **73**, 939 (1991)].
 - [8] P. L. Krotkov, and V. P. Mineev, Phys. Rev. B **65**, 224506 (2002).
 - [9] L. P. Gor'kov, Zh. Eksp. Teor. Fiz. **40**, 351 (1984) [JETP Lett. **40**, 1155 (1984)].
 - [10] L. I. Burlachkov, Zh. Eksp. Teor. Fiz. **89**, 1382 (1985) [Sov. Phys. JETP **62**, 800 (1985)].
 - [11] K. Machida, T. Ohmi, and M. Ozaki, J. Phys. Soc. Jpn. **54**, 1552 (1985).
 - [12] L. Albano, D. F. Mundarain, J. Stephany J. Opt. B Quant. Semiclass. Opt. **4**, 352 (2002).
 - [13] D. F. Agterberg and M. B. Walker, Phys. Rev. B **51**, 8481 (1994).
 - [14] D. F. Agterberg and M. B. Walker, Phys. Rev. Lett. **74**, 3904 (1995).