

Lawrence Berkeley National Laboratory

Recent Work

Title

A SMALL OXYGEN ISOTOPE SHIFT IN $\text{YBa}_2\text{Cu}_3\text{O}_7$

Permalink

<https://escholarship.org/uc/item/4wt1501p>

Author

Morris, D.E.

Publication Date

1987-12-01



Lawrence Berkeley Laboratory

UNIVERSITY OF CALIFORNIA

Physics Division

LAWRENCE
BERKELEY LABORATORY

FEB 1 1988

LIBRARY AND
DOCUMENTS SECTION

Submitted to Physical Review Letters


A Small Oxygen Isotope Shift in $\text{YBa}_2\text{Cu}_3\text{O}_7$

D.E. Morris, R.M. Kuroda, A.G. Markelz,
J.H. Nickel, and J.Y.T. Wei

December 1987

TWO-WEEK LOAN COPY

*This is a Library Circulating Copy
which may be borrowed for two weeks.*

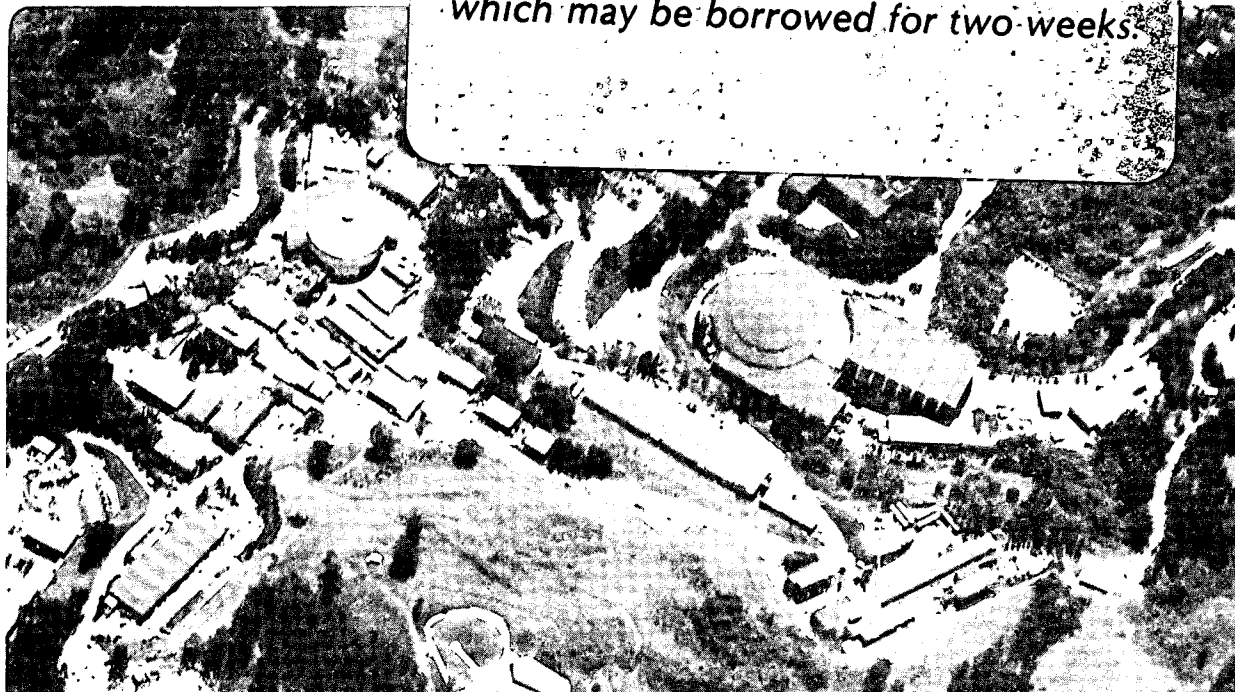

DISCLAIMER

This document was prepared as an account of work sponsored by the United States Government. While this document is believed to contain correct information, neither the United States Government nor any agency thereof, nor the Regents of the University of California, nor any of their employees, makes any warranty, express or implied, or assumes any legal responsibility for the accuracy, completeness, or usefulness of any information, apparatus, product, or process disclosed, or represents that its use would not infringe privately owned rights. Reference herein to any specific commercial product, process, or service by its trade name, trademark, manufacturer, or otherwise, does not necessarily constitute or imply its endorsement, recommendation, or favoring by the United States Government or any agency thereof, or the Regents of the University of California. The views and opinions of authors expressed herein do not necessarily state or reflect those of the United States Government or any agency thereof or the Regents of the University of California.

A Small Oxygen Isotope Shift in $\text{YBa}_2\text{Cu}_3\text{O}_7$

Donald E. Morris, Randy M. Kuroda, Andrea G. Markelz, Janice H. Nickel, and John Y. T. Wei

Physics Division, Lawrence Berkeley Laboratory, University of California,
Berkeley, California 94720

December, 1987

This work was prepared for the U S Department of Energy
under Contract Number DE-AC 03-76SF00098

A Small Oxygen Isotope Shift in $\text{YBa}_2\text{Cu}_3\text{O}_7$

Donald E. Morris, Randy M. Kuroda, Andrea G. Markelz, Janice H. Nickel, and John Y. T. Wei

Physics Division, Lawrence Berkeley Laboratory, University of California,
Berkeley, California 94720

Abstract

The oxygen isotope shift in $\text{YBa}_2\text{Cu}_3\text{O}_7$ has been measured to be 0.18 ± 0.04 K (with $\sim 85\%$ ^{18}O substitution) in disagreement with a recent published result. We find $\alpha = 0.019 \pm 0.005$ in the relation $T_c \propto M^{-\alpha}$. The methods used to measure such a small shift in T_c at ~ 92 K in a ceramic oxide superconductor are discussed, including preparation of material, reversible isotope substitution, measurement in a very small field, and control of thermometer drift.

The discovery of superconductivity in $\text{La}_{1.85}\text{Sr}_{0.15}\text{CuO}_4$ at temperatures above 30K by Bednorz and Müller¹, and in $\text{YBa}_2\text{Cu}_3\text{O}_7$ at temperatures above 90K by Wu *et al.*², and the hope that this may lead to materials with still higher transition temperatures, has triggered a flood of theoretical and experimental research. Several suggestions have been made³ to explain the underlying electron-electron interaction which is responsible for the extraordinarily high critical temperature of these compounds. In the earlier known elemental superconductors, the importance of phonon-mediated⁴ electron pairing was established by the isotope shift⁵, the change in critical temperature with ionic mass. In the original BCS⁶ theory $T_c \propto M^{-\alpha}$ with $\alpha = 1/2$. In the high temperature oxide superconductors, motion of the oxygen ions is dominant in the high frequency phonon modes which have been suggested⁷ as the cause of the high T_c . A non-zero value of α could indicate a significant role for phonon-mediated coupling in this material.

We have undertaken a careful measurement of the oxygen isotope shift in $\text{YBa}_2\text{Cu}_3\text{O}_7$, and find $\alpha = 0.019 \pm 0.005$. This is in conflict with the claim by Leary *et al.*⁸ of a shift of 0.3-0.5 K (with 75-90 % ^{18}O substitution) which implies $0.037 \leq \alpha \leq 0.051$. Our result is consistent with upper limits reported earlier by Bourne *et al.*⁹ and by Batlogg *et al.*¹⁰ of $\alpha < 0.027$ and $\alpha < 0.02$ respectively (see figure 1). Oxygen isotope substitution in $\text{YBa}_2\text{Cu}_3\text{O}_7$ can be accomplished by gas-phase diffusion¹¹. This permits reversible substitution in the same sample, thus avoiding the problem of sample-to-sample differences. Our method is similar to that described in Refs 8, 9 and 11, but special precautions were taken to reliably measure a small isotope shift in a high temperature ceramic oxide superconductor. It was necessary to produce samples with sharp transitions, and to minimize any differences in T_c except those caused by differences in isotope content. Measurements were made in a small field (3 Oe.) to reduce flux penetration below the transition. Temperature drift of sample vs. thermometer was minimized and corrections were made for residual drift.

Sharp diamagnetic transitions were obtained in samples prepared by solid-state reaction, using the heat treatment process described below. Stoichiometric quantities of Y_2O_3 , BaCO_3 and CuO powders (all Aesar 99.999% except BaCO_3 99.99%) were mixed thoroughly and calcined in flowing oxygen (4 h at 850°C, 12 h at 930°C, cooled at 115°C/h to 700°C, held 1 h, cooled at

60°C/h to 450°C, and furnace cooled at 220°C/h). The reacted mixture was finely ground in an agate mortar and pestle, pressed into 6 mm diameter tablets at 75 Kg/mm², and sintered in flowing oxygen (15 h at 930°C, cooled at 115°C/h to 700°C, held 1 h, cooled at 60°C/h to 450°C, and furnace cooled at 220°C/h). Calcining and sintering was carried out in alumina boats, lined with gold foil to minimize contamination. No reaction with the gold was observed. X-ray powder diffractometry indicated that the material was single-phase and that unreacted ingredients were absent. Our samples, which were porous to facilitate isotope exchange, had sintered density of 4.8 g/cm³, ~75% of the ideal density calculated from the lattice parameters. The grain size was ~2 μm by scanning electron microscopy (SEM). Careful storage of the samples proved necessary to maintain sample quality. Preliminary experiments showed that our porous samples deteriorate if stored in a desiccator containing ambient air and silica gel; the transition broadened by a factor of two in a period of one week. We then adopted the practice of storing the samples under vacuum (~0.2 Torr), with P₂O₅ in the container; this proved effective in preserving sharp superconducting transitions.

For the isotope shift measurements, two pieces, called A and B, were broken off from the same pellet, and underwent identical simultaneous thermal treatment during the diffusion process, which was carried out in a tube furnace. They were first weighed on a microbalance, wrapped loosely in gold foil, and placed in parallel 7 mm I. D. quartz tubes connected to 1064 cm³ reservoirs. A was heated in an ¹⁸O₂ enriched atmosphere (92% ¹⁸O + 8% ¹⁶O) and B in ¹⁶O₂ (~99.6% ¹⁶O + ~0.2% ¹⁸O)*. The reservoirs were outgassed and evacuated to < 10⁻² torr, then filled to 759 torr with their respective oxygen isotopes. The pressures were identical within one torr. At the diffusion temperature (930°C), the pressures in both sample tubes were 767 torr. Atmospheric pressure was also 767 torr. A and B were within 1 cm of each other at the center of the furnace during the heat treatment, which followed the same thermal program described above for sintering. The weight change of A relative to B was +1.77%; corresponding to 88% ¹⁸O content in A. (A gained 1.645%, while B lost 0.124% as a result of the annealing schedule.) After measuring the superconducting transitions of A and B (see below), a small chip was broken off from each for further tests. Since

* (+ A < 4000 ppm, N₂ < 500 ppm, (CH) < 25 ppm, CO₂ < 10 ppm, H₂O ~ 2 ppm)

the initial ^{18}O content of the gas was only 92%, we estimate that oxygen from the reservoir replaced ~96% of the oxygen originally present, indicating that oxygen in all sites was almost completely exchanged.

To separate the real isotope shift from any intrinsic difference in transition temperatures caused by sample nonuniformity, the remaining portions of A and B were again diffused, but with the opposite isotopes: B in an ^{18}O rich atmosphere (~90% ^{18}O + 10% ^{16}O), and A in the $^{16}\text{O}_2$ atmosphere. The procedure was the same as before, but the filling pressures were 753 ± 1 torr, and increased to 762 torr upon heating to 930°C . The same thermal program for diffusion was repeated. Weight changes indicated that B was now ^{18}O enriched, while A was depleted as expected, with an 83% higher ^{18}O fraction in B than in A. Taking into account ~4% residual ^{18}O expected in A, the replacement of oxygen in the sample by oxygen in the gas was again ~96% complete. The particle size and microstructure was again examined by S.E.M and appeared unchanged.

To observe a sharp diamagnetic transition, the measurements must be made in a very small magnetic field. At temperatures just below T_c , the lower critical field $H_{c1} < H_m$ the measuring field, since $H_{c1} \propto [1 - (T/T_c)^2]$, which goes to zero at T_c . Flux expulsion is incomplete and the transition is broadened. In Refs 8 and 9, measurements were made at 12 Oe; in Ref. 10 the field was 21 Oe. In a 12 Oe field $H_m > H_{c1}$ within ~1.5° K of T_c since $H_{c1} \approx 120$ Oe at 76 K in $\text{YBa}_2\text{Cu}_3\text{O}_7$ ¹². At $H_m = 3$ Oe the range is ~0.4° K. A sample was measured at two fields. At 10.3 Oe the transition width (to 1/2 the low temperature value of χ) was 1.8 K; at 3 Oe. the width was only 1 K. All measurements reported below were of Meissner diamagnetism cooling through T_c in a constant 2.7 or 3.0 Oe. The measurements were made on the same S.H.E. Model VTS-805 SQUID Magnetometer used in Refs 8 and 9.

Temperature drift of sample vs. thermometer must be minimized (The thermometer of the SHE magnetometer is in the He gas stream, and not in thermal contact with the sample.) When the transition of a single sample was measured repeatedly, T_c appeared to vary up to 0.3 K over ~6 h when the LHe level was as low as 40%. This may be the source of the relatively large temperature differences between samples reported in Ref. 8 and interpreted as an isotope shift. Further experiments showed that thermometer vs. sample temperature drift is minimized when the LHe level

is high. Thereafter, the susceptometer was filled before starting, and the LHe level remained between 100 % and 90 % throughout the measurements. The He gas flow was maintained at $450 \pm 25 \text{ cm}^3/\text{min}$ during all measurements.

The small residual drift was measured by alternating samples A and B and measuring the transition repeatedly, eight times within 16 hours. One run for each sample was made over a larger range to determine the shape of the curve down to low temperature. Figure 2a shows the results for several runs, selected for clarity. The transition temperature of sample A (^{18}O enriched) is clearly $\sim 0.2 \text{ K}$ lower than that of B (^{16}O). Table I gives the results for all eight runs. Measurements were made at intervals of $\sim 0.2 \text{ K}$, about the same as the difference in T_c of the two samples. For this reason, the susceptibility of B was nearly the same as that of A at the next measuring temperature. The demagnetization curves were interpolated to give the temperature at each of three susceptibility values $\chi = -1.2 \times 10^{-4}$, -3.2×10^{-4} and $-6.0 \times 10^{-4} \text{ emu/g}$, chosen because they lie near the measured data points. Since the curves of the two samples are not exactly parallel, the temperature shift between samples was determined separately for each column in Table I, by averaging the runs. The results are given in the row marked [$\langle B \rangle - \langle A \rangle$]. A small temperature drift is indicated by the monotonic change of temperature at the same χ for different runs of the same sample. Because measurements of A were made $\sim 1.56 \text{ h}$ later than B, a drift correction was necessary. A drift rate was computed separately for each χ by linear interpolation of the temperatures of runs 1 - 8, after shifting the temperatures of sample A by [$\langle B \rangle - \langle A \rangle$]. The correction was $< 0.01 \text{ K}$. The corrected values of temperature difference between A and B are given in Table I, with the values for $\chi = -3.2 \times 10^{-4}$ and $-6.0 \times 10^{-4} \text{ emu/g}$ underlined; the value for $\chi = -1.2 \times 10^{-4}$, though consistent, is considered less accurate because of low S/N at such a small χ .

After reverse diffusion of the samples, B is enriched in ^{18}O and A contains mainly ^{16}O . The transitions were again measured, with the same procedure and precautions. The results for several runs are shown in Fig. 2b. The transition temperatures of the two samples are now reversed; T_c of sample B is now lower than A, confirming that the difference is due to the isotope effect. The results for all eight runs are given in Table II. The chosen values of χ lie near the measured data points and are different from Table I. The temperature shift between samples was determined

separately for each column in the table. The temperature drift is somewhat greater than during the previous measurements, especially during the first three runs. The corrected values of temperature difference between A and B are given in Table II, with the values for $\chi = -4.5 \times 10^{-4}$ and $\chi = -8.0 \times 10^{-4}$ emu/g underlined; the value for $\chi = -14 \times 10^{-4}$ emu/g. is less reliable since the demagnetization curves are not parallel for large χ . An alternative analysis of the data in Table II was also made, excluding runs 1 and 2 because of the larger drift rate. This analysis gives smaller drift corrections of 0.004 K, 0.012 K and 0.001 K, and slightly raises the values of the corrected temperature shift to 0.16, 0.19 and 0.23 K, but the increases are small compared to the scatter in the values given in Tables I and II.

The Meissner demagnetization curves of A and B are not parallel at large χ ; the curve for A is steeper and reaches a limiting value of -38×10^{-4} emu/g at ~ 85 K, while the limiting value for B is -34×10^{-4} emu/g, reached at ~ 82 K. For these measurements, the two samples were sanded down to similar shapes, and orientation was kept constant in subsequent measurements. The screening-current susceptibility χ_{sc} was measured by increasing the field from 3 to 33 Oe while the sample was held at 25 K; A and B differed by only 4%, showing that the demagnetizing factors are similar. The Meissner diamagnetism at 25 K was 19.3% of χ_{sc} in A, while it was 17.9% in B. The difference in slope of A and B in Fig. 2b is unexplained. For determining the isotope shift the measured χ values were used without corrections.

An intrinsic difference in T_c between samples would result in a different temperature offset between samples after the second diffusion, compared to that observed after the first. By averaging the underlined values from each table, subtracting one average from the other, and dividing the difference by two, we estimate the difference in T_c to be <0.02 K (<0.01 K if runs 1 and 2 in Table II are deleted). The underlined values of corrected temperature difference were used to calculate values of α , which are given in the last line of each table.

Two possible causes of systematic error in this work have not been entirely excluded, although they are not expected to be significant. (1) A change in T_c might be caused by a difference in trace gas content of the ^{18}O and ^{16}O gases used for diffusion, and could mimic an isotope shift since it

would be correlated with isotope. (2) Isotope diffusion was done at 930°C, above the orthorhombic-tetragonal phase transition, but if any variation of T_c resulted it would be uncorrelated with isotope. In conclusion, a small oxygen isotope shift has been observed and measured in $\text{YBa}_2\text{Cu}_3\text{O}_7$. Considering the spread of measurements and possible systematic errors, we find $\alpha = 0.019 \pm 0.005$.

Acknowledgements: The authors thank R. A. Fisher and A. J. George for useful advice, and L. C. Bourne, J. Duisman, N. M. Edelstein, S. T. Hoen, C. T. Hultgren, A. J. Hunt, T. W. Lawhead, D. S. Lee, R. T. Lewis, K. D. Lofftus, E. F. Mah, A. Meuti, R. A. Muller, P. J. Oddone, N. E. Phillips, U. M. Scheven, G. V. Shalimoff, R. R. Stevenson, T. Walker, C. J. Williams, Perkin-Elmer, and Chevron Research Corp. for assistance. D. E. M. wishes to thank L. W. Alvarez.

References

- ¹J. G. Bednorz and K. A. Müller, *Z. Phys.* **B64**, 189 (1986).
- ²M. K. Wu, J. R. Ashburn, C. J. Torng, P. H. Hor, R. L. Meng, L. Gao, Z. J. Huang, Y. Q. Wang, and C. W. Chu, *Phys. Rev. Lett.* **58**, 908 (1987).
- ³See *Novel Superconductivity*, eds S. A. Wolf and V. Z. Kresin (Plenum Press, New York, 1987)
- ⁴H. Frölich, *Phys. Rev.* **97**, 845 (1950).
- ⁵E. Maxwell, *Phys. Rev.* **78**, 477 (1950); C. A. Reynolds, B. Serin, W. H. Wright, and L. B. Nesbitt, *Phys. Rev.* **78**, 487 (1950).
- ⁶J. Bardeen, L. N. Cooper, and J. R. Schrieffer, *Phys. Rev.* **106**, 162 (1957), and **108**, 1175 (1957).
- ⁷L. F. Mattheiss, *Phys. Rev. Lett.* **58**, 1028 (1987); W. Weber, *Phys. Rev. Lett.* **58**, 1371 (1987).
- ⁸K. J. Leary, H-C. zur Loye, S. W. Keller, T. A. Faltens, W. K. Ham, J. M. Michaels, and A. M. Stacy, *Phys. Rev. Lett.* **59**, 1236 (1987).
- ⁹L. C. Bourne, M. F. Crommie, A. Zettl, H-C. zur Loye, S. W. Keller, K. L. Leary, A. M. Stacy, K. J. Chang, M. L. Cohen and D. E. Morris, *Phys. Rev. Lett.* **58**, 2337 (1987).
- ¹⁰B. Batlogg, R. J. Cava, A. Jayaraman, R. B. van Dover, G. A. Kourouklis, S. Sunshine, D. W. Murphy, L. W. Rupp, H. S. Chen, A. White, K. T. Short, A. M. Muijsce, and E. A. Rietman, *Phys. Rev. Lett.* **58**, 2333 (1987).
- ¹¹D. E. Morris, U. M. Scheven, L. C. Bourne, M. L. Cohen, M. F. Crommie and A. Zettl, *Proc. of Symp. S of 1987 Spring Meet. of M. R. S., Vol. EA-11, 209-213 (Material Research Soc., Pittsburgh, PA)*
- ¹²J. F. Kwak, E. L. Venturini, D. S. Ginley, and W. Fu, in *Novel Superconductivity*, eds. S. A. Wolf and V. Z. Kresin (Plenum Press, New York, 1987), p. 983.

TABLE I. Superconducting transition temperature shift with oxygen isotope substitution. Samples B (^{16}O) and A (^{18}O) were measured alternately. Temperatures are given at which the Meissner diamagnetic susceptibility reached each of three values. The transition of A (^{18}O enriched) is at lower temperature than B(^{16}O).

Run	Sample	Time (hrs.)	Temp. (K) at which the χ vs. T curve crosses the indicated χ (emu/g).		
			$\chi = -1.2 \times 10^{-4}$	-3.2×10^{-4}	-6.0×10^{-4}
1	B(^{16}O)	1	91.60	91.40	91.17
2	A(^{18}O)	3	91.31	91.13	90.97
3	B(^{16}O)	5.5	91.59	91.40	91.12
4	A(^{18}O)	7.5	91.40	91.20	91.01
5	B(^{16}O)	10.75	91.61	91.43	91.16
6	A(^{18}O)	12	91.42	91.22	91.02
7	B(^{16}O)	14	91.66	91.42	91.16
8	A(^{18}O)	15	91.43	91.24	91.04
Average of all Runs					
	$\langle \text{B}^{(16\text{O})} \rangle$	7.81	91.61	91.42	91.15
	$\langle \text{A}^{(18\text{O})} \rangle$	9.375	91.39	91.20	91.01
	$[\langle \text{B} \rangle - \langle \text{A} \rangle]$	-1.56	0.23	0.22	0.14
	Estimated drift rate (deg/h)*		0.006	0.005	0.003
	Drift correction (deg)†		0.009	0.008	0.005
	Corrected temp. difference (deg) ($\langle \text{B} \rangle - \langle \text{A} \rangle + \text{Drift correction}$)		0.24	<u>0.23</u>	<u>0.15</u>
	Corresponding value of α			0.023	0.015

*Slope from linear interpolation of runs 1-8 at one value of χ , after shifting sample A temperatures by $[\langle \text{B} \rangle - \langle \text{A} \rangle]$.

†Estimated drift rate \times average time difference of 1.56 hrs.

TABLE II. Superconducting transition temperature shift after second diffusion (sample B in ^{18}O and sample A in ^{16}O). Temperatures for three values of χ are given. The transition of B is now at lower temperature than A, confirming that the shift is due to an isotope effect.

Run	Sample	Time (hrs.)	Temp. (K) at which the χ vs. T curve crosses the indicated χ (emu/g).		
			$\chi = -4.5 \times 10^{-4}$	-8.0×10^{-4}	-14×10^{-4}
1	A(^{16}O)	1	91.20	91.04	90.81
2	B(^{18}O)	3	91.20	90.95	90.65
3	A(^{16}O)	6	91.38	91.13	90.90
4	B(^{18}O)	7.5	91.25	90.99	90.68
5	A(^{16}O)	9.5	91.42	91.19	90.91
6	B(^{18}O)	11	91.28	91.01	90.67
7	A(^{16}O)	12.5	91.44	91.23	90.91
8	B(^{18}O) 15		91.23	91.00	90.68
Average of all Runs					
	$\langle A(^{16}\text{O}) \rangle$	7.25	91.36	91.15	90.88
	$\langle B(^{18}\text{O}) \rangle$	9.13	91.24	90.99	90.67
	$[\langle A \rangle - \langle B \rangle]$	-1.88	0.12	0.16	0.21
	Estimated drift rate (deg/h)*		0.011	0.009	0.005
	Drift correction (deg)†		0.021	0.017	0.009
	Corrected temp. difference (deg) ($\langle A \rangle - \langle B \rangle + \text{Drift correction}$)		<u>0.14</u>	<u>0.18</u>	0.22
	Corresponding value of α		0.016	0.020	

*Slope from linear interpolation of runs 1-8 at one value of χ , after shifting sample B temperatures by $[\langle A \rangle - \langle B \rangle]$.

†Estimated drift rate \times average time difference of 1.88 hrs.

Figure Captions

Fig. 1 Reported values of α in the expression $T_c \propto M^{-\alpha}$. Our result: $\alpha = 0.019 \pm 0.005$ is consistent with the limits placed by Bourne *et al.*⁹ and by Battlogg *et al.*¹⁰, but are in conflict with the results claimed by Leary *et al.*⁸

Fig. 2 (a) Transition temperatures of two samples A and B broken from the same pellet, after isotopic substitution by gas phase diffusion. A contains ~88% ¹⁸O, while B has ~100% ¹⁶O. Several runs are plotted. The transition temperature of A is clearly ~0.2 K lower than B. Data points from Fig. 1 of Leary *et al.*⁸ are included for comparison. (b) Transitions of the same samples, but following re-diffusion with the opposite isotope (*i.e.* B in ¹⁸O and A in ¹⁶O). Now the ¹⁸O fraction in B is ~83% greater than in A, and the transition temperature of B is lower, confirming that the difference is due to the isotope effect.

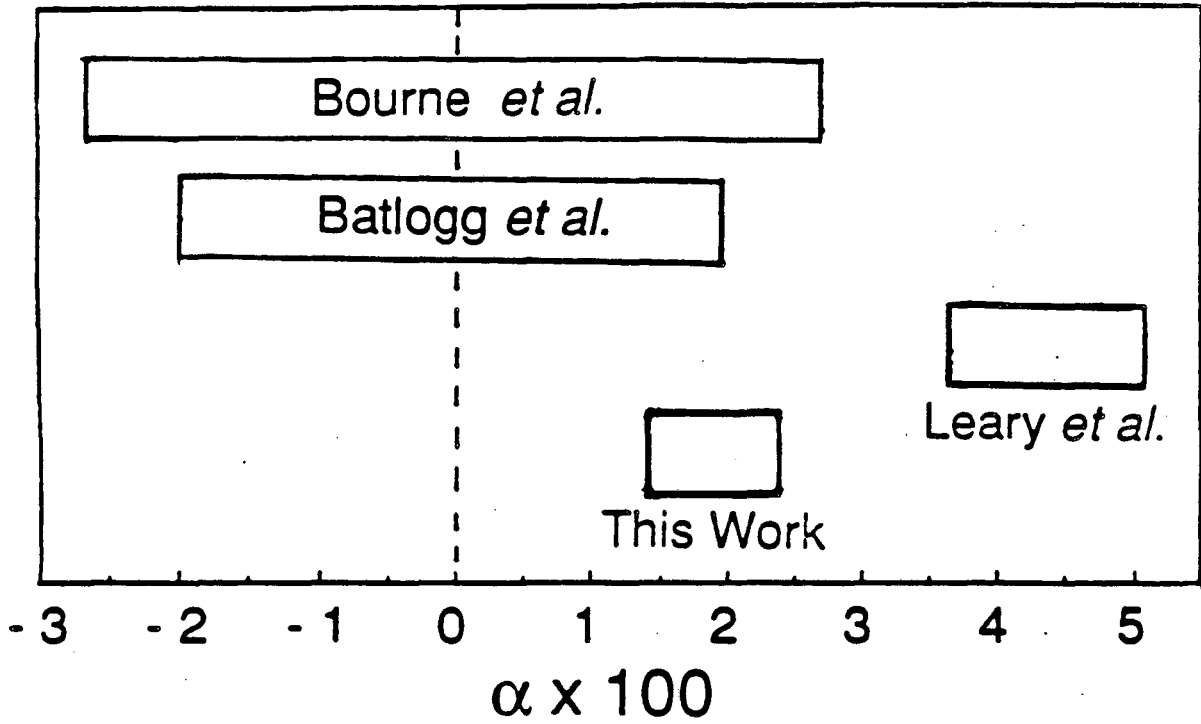


FIGURE 1

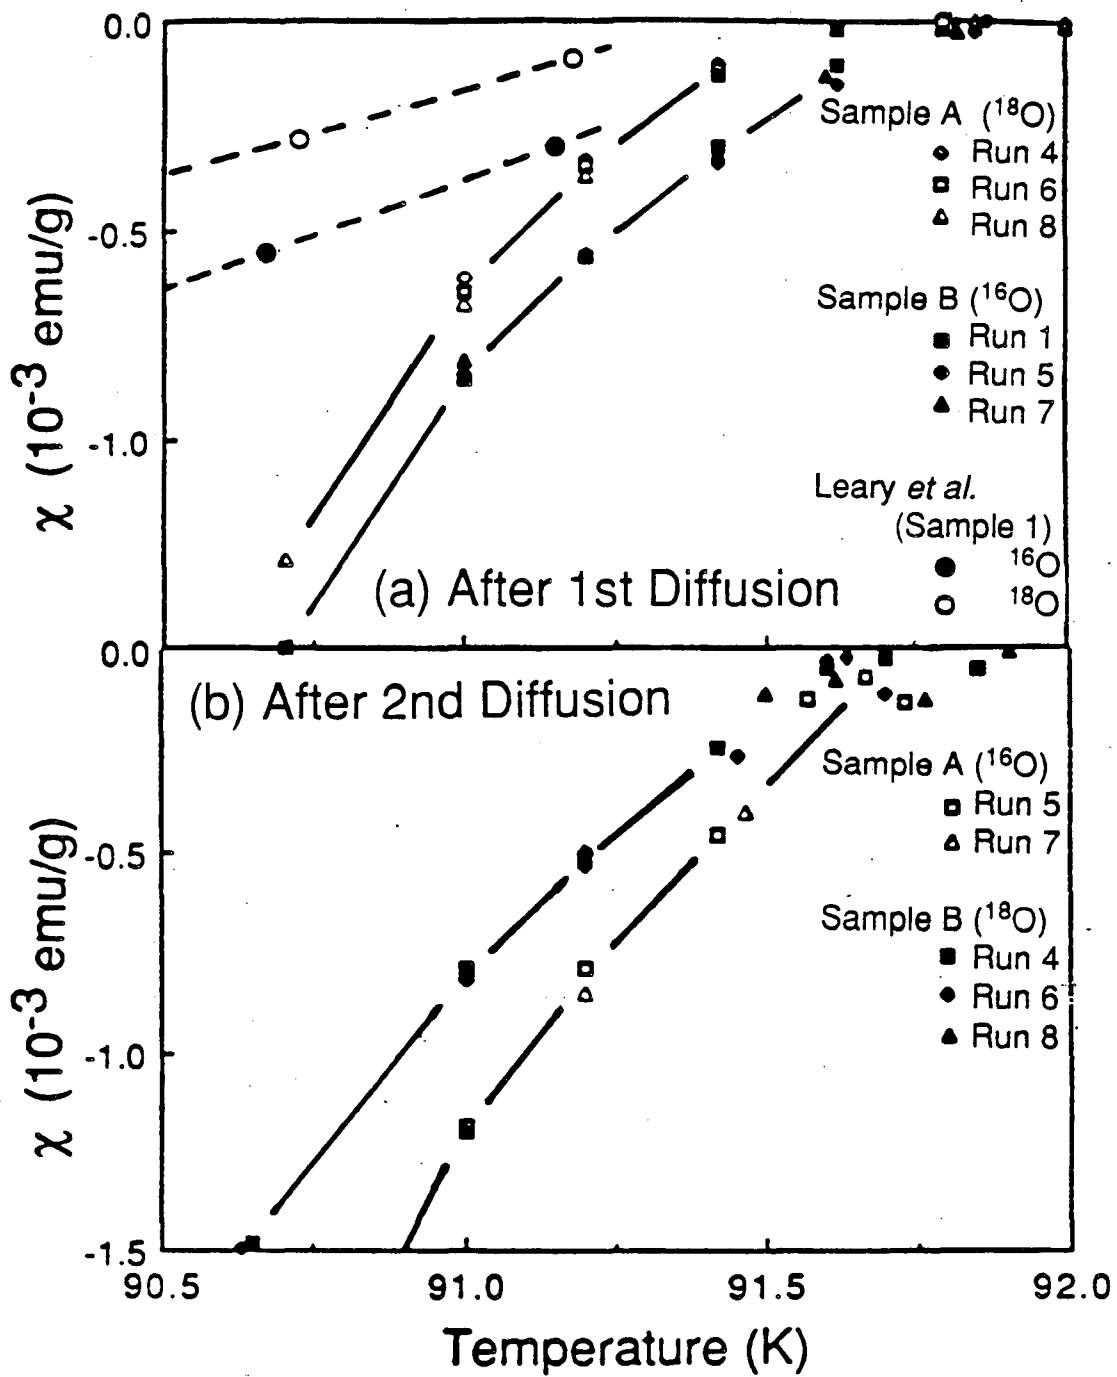


FIGURE 2

*LAWRENCE BERKELEY LABORATORY
TECHNICAL INFORMATION DEPARTMENT
UNIVERSITY OF CALIFORNIA
BERKELEY, CALIFORNIA 94720*