

UC Santa Barbara

UC Santa Barbara Previously Published Works

Title

Generation of a Ni₃ Phosphinidene Cluster from the Ni(0) Synthon, Ni(η^3 -CPh₃)₂

Permalink

<https://escholarship.org/uc/item/6cq1x1ks>

Journal

Organometallics, 39(8)

ISSN

0276-7333

Authors

Touchton, Alexander J

Wu, Guang

Hayton, Trevor W

Publication Date

2020-04-27

DOI

10.1021/acs.organomet.0c00095

Peer reviewed

Generation of a Ni₃ Phosphinidene Cluster from the Ni(0) Synthone, Ni(η³-CPh₃)₂

Alexander J. Touchton, Guang Wu, Trevor W. Hayton*

Department of Chemistry and Biochemistry, University of California, Santa Barbara, California 93106, United States

ABSTRACT: Reaction of NiCl₂ in THF with 2 equiv of Li(CPh₃) at -25 °C results in formation of Ni(η³-CPh₃)₂ (**1**) in moderate yield. Complex **1** was fully characterized, which included analysis by X-ray crystallography. In the solid-state, **1** features an η³ binding mode of its trityl ligands, resulting in a structure that is reminiscent of the archetypal Ni(II) organometallic, *bis*(η³-allyl)nickel. In addition, complex **1** has proved to be excellent Ni(0) synthon. For example, reaction of **1** with excess CO results in formation of Ni(CO)₄ along with Gomberg's dimer. Similarly, reaction of **1** with 4 equiv of PPh₃ results in formation of Ni(PPh₃)₄ (**2**). Presumably, its ability to function as a Ni(0) source is derived from the relatively high stability of the trityl radical, which results in weak Ni-C bonds that are susceptible to homolytic cleavage. Finally, reaction of **1** with 2 equiv of PPh₃, in an attempt to form a larger Ni cluster, resulted in formation of Ni₃(μ₃-PPh)(μ-PPh₂)₂(PPh₃)₃ (**3**) in moderate yield. Its phosphide and phosphinidene ligands are derived from the formal reduction of the PPh₃ ligand.

Introduction

The field of atomically precise nanoclusters (APNCs) has experienced a rapid expansion in the past decade.¹ However, most of this work has been restricted to APNCs of the coinage metals (Cu, Ag, Au).¹ In contrast, limited progress has been made towards the synthesis of APNCs of the other transition metals. Part of this shortfall can be ascribed to the high air-sensitivity that is expected for APNCs of Fe, Co, and Ni, which makes their isolation more challenging.^{1b,2} The lack of a general synthetic route to these materials also plays a role. For example, while group 11 APNCs are typically made by reaction of a metal halide precursor with a supporting ligand and a strong reducing agent, such as NaBH₄, similar reactions with Ni or Co have only resulted in the isolation of M(II)-containing clusters. For example, we demonstrated that reaction of CoCl₂ with PhCH₂CH₂SH and excess NaBH₄ resulted in formation of the Co(II)-containing cluster, [Co₁₀(SCH₂CH₂Ph)₁₆Cl₄], as the only isolated product.² Similarly, reaction of NiCl₂ with PhCH₂CH₂SH and excess NaBH₄ results only in isolation of an Ni(II) thiolate cluster.^{1b,3} The apparent difficulty of generating M(0) in these reactions points to the need for a fundamentally new strategy for APNC formation, one in which M(0) can be easily generated under mild conditions. Accordingly, we sought to find a transition metal M(0) synthon that could reliably deliver M(0) equivalents during APNC synthesis.


A survey of the literature reveals that *bis*(trityl)nickel, Ni(CPh₃)₂, may serve our purposes. This complex was reported in 1966 by Wilke and Schott and was formed by reaction of 2 equiv of Na(CPh₃) with NiBr₂ in diethyl ether at -78 °C.^{5d} Importantly, Wilke demonstrated its utility as a Ni(0) synthon by reaction with 4 equiv of PPh₃, which resulted in formation of Ni(PPh₃)₄. Presum-

ably, Ni(CPh₃)₂ functions as a good Ni(0) synthon because the relatively high stability of the trityl radical results in weak Ni-C bonds, which are susceptible to homolytic cleavage. Several other transition metal trityl complexes have also proven to be good sources of metal-centered radicals, including Re(CO)₄(η³-CPh₃) and L^{Me}Fe(η¹-CPh₃) (L^{Me} = {(2,6-*i*-Pr₂C₆H₃)NC(Me)}₂CH), providing further support for this concept.⁴ However, Ni(CPh₃)₂ was not fully characterized and its structure was never determined by X-ray crystallography. The latter point is significant because there is some uncertainty concerning the bonding mode of the trityl ligand in Ni(CPh₃)₂, with Wilke suggesting an η¹ binding mode, and other authors suggesting an η³ binding mode.⁵

Herein, we report the synthesis and characterization of *bis*(η³-trityl)nickel (**1**) and demonstrate its utility as a Ni(0) synthon during the preparation of the Ni phosphinidene cluster, [Ni₃(μ₃-PPh)(μ-PPh₂)₂(PPh₃)₃] (**3**).

Results and Discussion

Reaction of a suspension of NiCl₂ in THF with 2 equiv of Li(CPh₃) at -25 °C results in formation of Ni(η³-CPh₃)₂ (**1**), which can be isolated as a purple powder in 46% yield after work-up (Scheme 1). While similar yields were reported by Wilke and Schott in their preparation of **1**, we found it necessary to modify the reported work-up. In particular, its low solubility in benzene (see below) made the reported work-up (recrystallization from benzene) impractical. Instead, we found that washing the crude reaction mixture with hexanes, followed by washing with a 1:1 (v:v) solution of MeCN and H₂O, gave spectroscopically pure material in acceptable yields.

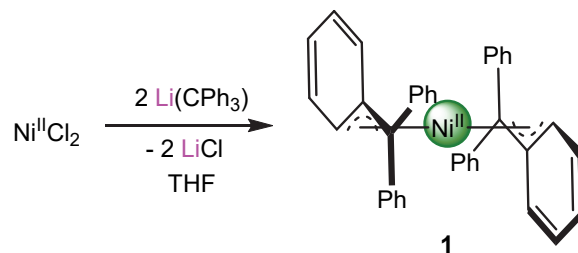

Scheme 1. Synthesis of Ni(η³-CPh₃)₂ (**1**)

As a solid, **1** is stable in air for several months. However, solutions of **1** in THF or CH₂Cl₂ are quite sensitive, quickly losing their purple hue on exposure to air. Complex **1** is insoluble in hexanes, acetonitrile, diethyl ether, methanol, and water, and very sparingly soluble in ethyl acetate and acetone. It is somewhat more soluble in benzene, toluene, and THF (~1 mg/mL in each). The highest solubility is observed in CH₂Cl₂ and CHCl₃ (~2 mg/mL). However, it does slowly decompose in these solvents, concomitant with formation of Gomberg's dimer and small amounts of triphenylmethane.

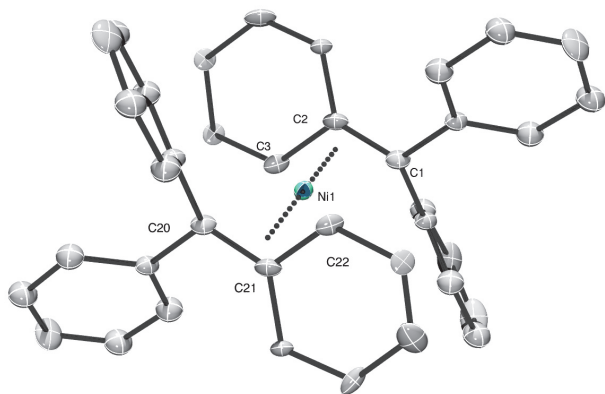


Figure 1. ORTEP drawing of one independent molecule of **1**. Shown with 50% probability thermal ellipsoids. All hydrogen atoms are omitted for clarity. Selected bond lengths (Å): Ni1-C1 = 2.05(2), Ni1-C2 = 2.01(2), Ni1-C3 = 2.10(2), Ni1-C20 = 2.08(2), Ni1-C21 = 2.03(2), Ni1-C22 = 2.04(2).


Complex **1** crystallizes in the monoclinic space group, Pn , with two independent molecules in the asymmetric unit (Figure 1). The crystal was twinned and weakly diffracting, which reduced the precision of the resulting metrical parameters; nonetheless, the connectivity of **3** was unambiguously confirmed. Each trityl ligand in **1** adopts an η^3 binding mode, resulting in a structure that is reminiscent of the archetypal Ni(II) organometallic, *bis*(η^3 -allyl)nickel.⁶ Its Ni-C distances range from 2.01(2) to 2.10(1) Å (av. Ni-C = 2.05(7) Å), while the C-C bonds within the allyl unit range from 1.40(2) to 1.48(2) Å (av. $C_{\text{allyl}}-C_{\text{allyl}}$ = 1.44(8) Å). These values are similar to those reported for the only other structurally characterized Ni(trityl) complex CpNi(η^3 -trityl), as well as (acac)Pd(η^3 -trityl).^{5b} A handful of other trityl complexes have also been structurally characterized, including recently $L^{\text{Me}}\text{Fe}(\eta^1\text{-CPh}_3)$, which features an η^1 trityl binding mode,^{4b} and $[\text{Ti}(\text{CO})_4(\eta^5\text{-CPh}_3)]$, which features an η^5 trityl binding mode.⁸

The ^1H NMR spectrum of **1** in CD_2Cl_2 at room temperature exhibits several very broad resonances in the aromatic region, indicative of a fluxional η^3 -trityl ligand.^{5b} On cooling the NMR sample to -40 °C, however, these resonances sharpen considerably, decoalescing into five distinct peaks (Figure S2-S3). Doublets at 6.24 and 6.57 ppm are assignable to the ortho protons of the coordinated and free phenyl groups, respectively. A triplet at 6.99 ppm is assignable to the para protons of the coordinated phenyl groups, a multiplet at


7.05 ppm is assignable to overlapping meta resonances of free and bound phenyl groups, and a triplet at 7.23 ppm is assignable to the para protons of the free phenyl groups. The pattern and relative ratios of these peaks implies that interconversion of coordinated and free phenyl groups via an η^1 -trityl intermediate is slower than the NMR time scale at this temperature.^{4a,9} However, the observation that the two ortho protons of the coordinated phenyl group are still magnetically equivalent at this temperature suggests that suprafacial exchange of the η^3 -trityl ligand is still occurring.^{5b,9-10} Cooling the sample to -79 °C only led to slight broadening of this resonance, suggesting that the barrier to suprafacial exchange is very low.

To test the efficacy of **1** as a Ni(0) synthon, we probed its reaction with CO. Thus, addition of CO (1 atm) to a CD_2Cl_2 solution of **1** resulted in an immediate color change from purple to colorless (Scheme 2). A solution-phase IR spectrum of this sample revealed the presence of a strong absorption band at 2040 cm^{-1} , which is assignable to the T_2 stretching mode of $\text{Ni}(\text{CO})_4$ (cf. $\nu(\text{C}=\text{O}) = 2043\text{ cm}^{-1}$).¹¹ Moreover, a $^{13}\text{C}\{^1\text{H}\}$ NMR spectrum of this sample featured a resonance at 192 ppm, matching the reported value for $\text{Ni}(\text{CO})_4$.¹² Finally, examination of ^1H NMR spectrum confirmed the presence of Gomberg's dimer (**5**), as indicated by the presence of diagnostic multiplets at 6.22 and 5.96 ppm, along with a singlet at 5.11 ppm.¹³ Small amounts of Ph_3CH , as indicated by a singlet at 5.55 ppm, are also present in the reaction mixture.¹⁴

Scheme 2. Reaction of **1** with CO and Ph_3P

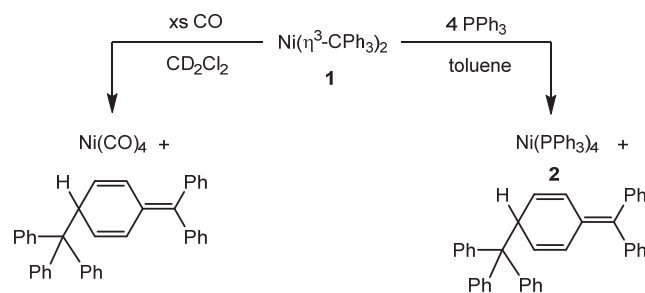

Similarly, addition of 4 equiv of PPh_3 to a suspension of **1** in toluene resulted in a gradual color change to red-orange (Scheme 2). Work-up of this solution resulted in the isolation of $\text{Ni}(\text{PPh}_3)_4$ (**2**) as a brown microcrystalline solid in 70% yield. Similar results were reported by Wilke.^{5d} A $^{31}\text{P}\{^1\text{H}\}$ NMR spectrum of **2** features a single broad resonance at 18 ppm, consistent with the spectrum previously reported for this material.¹⁵ In addition, the generation of Gomberg's dimer during the formation of **2** was confirmed by *in situ* spectroscopic monitoring of the reaction of **1** with 4 equiv of PPh_3 in toluene- d_8 (Figure S9).¹³

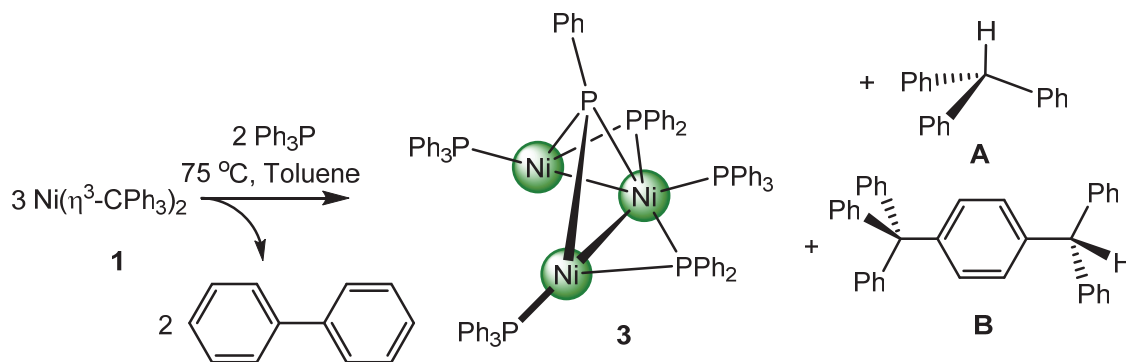

Scheme 3. Formation of $\text{Ni}_3(\mu_3\text{-PPh})(\mu\text{-PPh}_2)_2(\text{PPh}_3)_3$ (**3**) upon thermolysis of $\text{Ni}(\eta^3\text{-CPh}_3)_2$ (**1**).

After establishing the suitability of **1** as an Ni(0) synthon, we explored its ability to generate an APNC. Previously, we demonstrated that lowering the metal: Ph_3P ratio in the synthesis of phosphine-ligated Cu APNCs resulted in isolation of larger clusters.¹⁶

Thus, we performed the reaction of **1** with only 2 equiv of PPh_3 in toluene. Heating of this reaction mixture to 75 °C for 15 h resulted in formation of a brown solution from which the novel nickel phos-

phosphinidene complex, $[\text{Ni}_3(\mu_3\text{-PPh})(\mu\text{-PPh}_2)_2(\text{PPh}_3)_3]$ (**3**), can be isolated in 38% yield as a deep brown crystalline solid after work-up (Scheme 3). Complex **3** is insoluble in hexanes, sparingly soluble in diethyl ether, and soluble in THF, toluene, and 1,2-dimethoxyethane. The synthesis of **3** mirrors that of the recently reported Ni_{12} cluster, $[\text{Ni}_{12}(\text{PMe})_{10}(\text{PEt}_3)_8]$, which is formed by reaction of $\text{Ni}(1,5\text{-COD})_2$ with $(\text{PMe})_5$ and PEt_3 .¹⁷

Complex **3** crystallizes in the triclinic space group P-1 as a toluene solvate, $\mathbf{3}\cdot 2\text{C}_7\text{H}_8$. Its solid-state molecule structure is shown in Figure 2. In the solid state, **3** features three Ni centers ligated by a triply-bridged phosphinidene ligand, two doubly-bridged phosphide ligands, and three phosphine ligands (one bound to each Ni center). The phosphinidene and phosphide ligands are evidently derived from reduction of PPh_3 (see below). The Ni-Ni bond lengths are 2.451(1) and 2.4442(9) Å. These distances are consistent with those expected for formal single Ni-Ni bonds (formal shortness ratio = 0.99, 0.98, respectively).¹⁸ The Ni-P bond lengths for the bridging phosphide (av. Ni-P = 2.18 Å, range = 2.139(1)-2.219(1) Å) and phosphinidene (av. Ni-P = 2.16 Å, range = 2.097(1)-2.263(1) Å) moieties are consistent with those of other clusters bearing bridging $[\text{RP}]^2-$ or $[\text{R}_2\text{P}]^-$ ligands.¹⁹ For example, the Ni phosphinidene complex, $[\text{Ni}_8(\text{CO})_8(\mu_4\text{-PPh})_6]$ features an average Ni-P bond length of 2.183 Å,^{19h} while the Ni phosphide complex, $[\text{Ni}_2(\mu\text{-PPh}_2)_2(\text{PCy}_3)_2]$ features an average Ni-P bond length of 2.16 Å.^{19k} If the Ni-Ni bonds are ignored, the central Ni center features a tetrahedral geometry ($\tau_4 = 0.96$),²⁰ whereas the two outer Ni centers display trigonal planar geometries ($\Sigma(\angle\text{P-Ni}_2\text{-P}) = 359.3^\circ$, $\Sigma(\angle\text{P-Ni}_3\text{-P}) = 360.0^\circ$). The average Ni oxidation state in **3** is +1.33, but given its short Ni-Ni bonds, and its diamagnetism (see below), the valence electrons are clearly strongly coupled and delocalized over all three Ni centers.

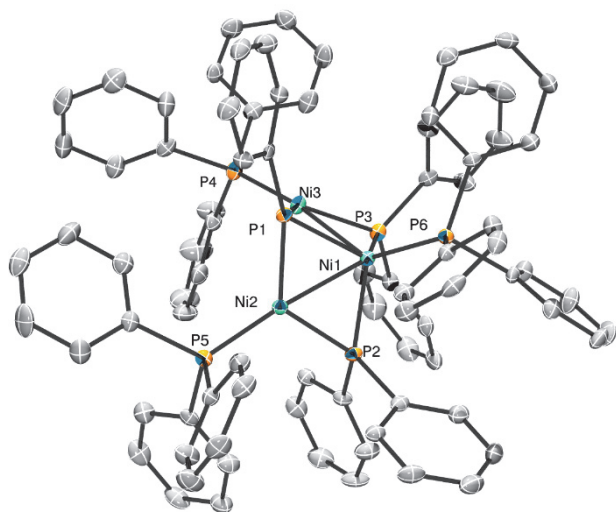


Figure 2. ORTEP drawing of $\mathbf{3}\cdot 2\text{C}_7\text{H}_8$. Shown with 50% probability thermal ellipsoids. Hydrogen atoms and toluene solvate molecules are omitted for clarity. Selected bond distance (Å) and angles ($^\circ$): Ni1-Ni2 = 2.451(1), Ni1-Ni3 = 2.4442(9) Å, av. Ni-PPh₂ = 2.18(6) and av. Ni-PPh = 2.16(5), $\Sigma(\angle\text{P-Ni}_2\text{-P}) = 359.3^\circ$, $\Sigma(\angle\text{P-Ni}_3\text{-P}) = 360.0^\circ$.

The $^{31}\text{P}\{^1\text{H}\}$ NMR spectrum of **3** in C_6D_6 is consistent with its solid state molecular structure. In particular, it features resonances at 34.1 (1P), 41.7 (2P), 122.4 (2P), and 487.5 ppm (1P) (Figure 3), which are assignable to the two unique Ph_3P environments, the phosphide environment, and phosphinidene environment, respectively. The phosphinidene resonances appears as a triplet of triplets ($^2J_{\text{PP}} = 208$ Hz, 43 Hz) due to coupling to two equivalent phosphide

ligands and two equivalent PPh_3 ligands. The other ^{31}P resonances are complicated multiplets. The ^{31}P chemical shifts for the $\mu_3\text{-PPh}$ and $\mu\text{-PPh}_2$ ligands in **3** are similar to those observed for other clusters bearing bridging $[\text{PPh}]^2-$ ligands^{19e} or $[\text{PPh}_2]^-$ ligands.^{19j, 21} The ^1H NMR spectrum of **3** in C_6D_6 features multiplets at 7.45 and 7.25 ppm, which are assignable to the *ortho* protons of the inequivalent phenyl groups of the $[\text{PPh}_2]^-$ ligands (one phenyl group is below the Ni₃ plane and one phenyl group is above the Ni₃ plane), indicating the stereochemical rigidity of the cluster skeleton. Finally, the ESI-MS of **3** in THF acquired in positive ion mode further supports the proposed formulation. The two major peaks at 1440.2716 *m/z* and 1178.1591 *m/z* are ascribable to $[\text{M}]^+$ (calcd. 1440.1964 *m/z*) and $[\text{M-PPh}_3]^+$, respectively (Figures S23-S25).

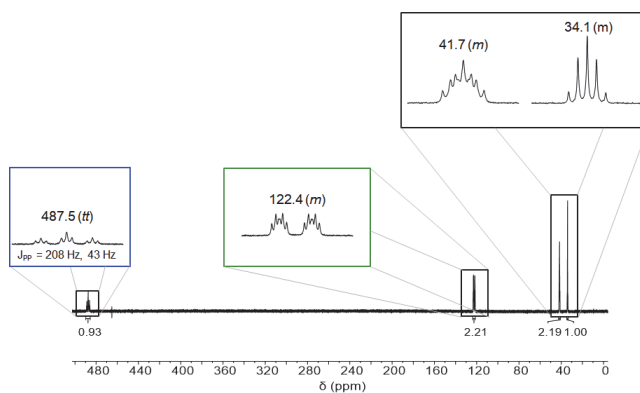


Figure 3. $^{31}\text{P}\{^1\text{H}\}$ NMR spectrum of **3** in benzene-*d*₆ at room temperature.

To better understand the reaction stoichiometry, we sought to identify the organic by-products present in the reaction mixture. A ^1H NMR spectrum of the crude mixture, recorded in benzene-*d*₆, reveals the presence of biphenyl, as indicated by resonances at 7.46, 7.21, and 7.13 ppm (Scheme 3, Figure S14). This conclusion was further confirmed by inspection of $^{13}\text{C}\{^1\text{H}\}$ NMR spectrum of the same sample (Figure S15). Curiously, though, we do not observe any resonances assignable to Gomberg's dimer. Instead, we observe singlets at 5.43 and 5.38 ppm in the ^1H NMR spectrum, which can be ascribed to triphenylmethane (**A**), and 1-(diphenylmethyl)-4-(trityl)benzene (**B**). These assignments were further corroborated by the $^{13}\text{C}\{^1\text{H}\}$ NMR spectrum of this sample (Figure S15). Both **A** and **B** are known Gomberg's dimer decomposition products.²² Also observed in the ^1H NMR spectrum are singlets at 3.82 and 3.78 ppm, which are also likely Gomberg's dimer decomposition products, but which remain unidentified. Given the elevated temperature of this transformation it is likely that Gomberg's dimer is initially formed, but undergoes a subsequent thermal decomposition.

To rationalize our observations and explain the formation of **3**, we propose that **1** initially reacts with PPh_3 to form $\text{Ni}(\text{PPh}_3)_n$ and Gomberg's dimer. Subsequent oxidative addition of a P-C bond across the Ni center, followed by dimerization and reductive elimination of biphenyl would provide the known phosphide-bridged bimetallic, $\text{Ni}_2(\mu\text{-PPh}_2)_2(\text{PPh}_3)_3$ (**4**).^{19g} Addition of another equivalent of $\text{Ni}(\text{PPh}_3)_n$, and one more oxidative addition/reductive elimination step would provide **3**. In support of this proposed mechanism, we note that oxidative addition of a P-C bond in PPh_3 at Ni(0), with elimination of biphenyl, has been reported previously.²³ The conversion of a PPh_2 ligand to a PPh ligand, via P-C oxidative addition, is also known.^{19b} To further support our proposed mechanistic sequence, we monitored the thermolysis of **2** by ^1H and $^{31}\text{P}\{^1\text{H}\}$ NMR spectroscopies in toluene-*d*₈ after heating at 40 $^\circ\text{C}$ for 19 h and then 80 $^\circ\text{C}$ for 25 h. After 19 h at 40 $^\circ\text{C}$, the $^{31}\text{P}\{^1\text{H}\}$

NMR spectrum revealed resonances tentatively assigned to complex **4** (Figure S16). However, upon further heating these signals disappear, concomitant with the appearance of signals assignable to **3**. Significantly, this experiment confirms that Ni(PPh₃)₄ is a viable precursor to complex **3**.

Conclusions

In summary, we have completed the characterization of Ni(CPh₃)₂, confirming that it features an η³ binding mode of its trityl ligands. Moreover, we have demonstrated that Ni(CPh₃)₂ is a good source of Ni(0) via its reactions with CO and PPh₃. Indeed, Ni(CPh₃)₂ offers several attractive features that are not found in other common Ni(0) synthons,²⁴ such as Ni(1,5-cod)₂ and Ni(CO)₄. For example, Ni(1,5-cod)₂ is highly air-sensitive and somewhat light sensitive,²⁵ while CO displacement reactions in Ni(CO)₄ become more difficult as the total number of CO ligands decreases.^{25a} In contrast, Ni(CPh₃)₂ is both air and water stable as a solid, while loss of both trityl ligands appears to be facile, judging by its rapid reaction with CO. Thus, we suggest that Ni(CPh₃)₂ will be a good precursor for not only APNC formation, but also for Ni(0)-catalyzed cross couplings.²⁶ That said, we note that our efforts to form a large Ni APNCs using Ni(CPh₃)₂ were thwarted by the facile oxidative addition of the P-C bonds of PPh₃. This result demonstrates the high reactivity of the “Ni(0)” formed from Ni(CPh₃)₂ and also suggest that successful formation of large, Ni(0)-containing APNCs will require the use of co-ligands that are particularly resistant to reduction.

ASSOCIATED CONTENT

Supporting Information

Experimental, spectroscopic, and crystallographic details for complexes **1** and **3**.

This material is available free of charge via the Internet at <http://pubs.acs.org>.

AUTHOR INFORMATION

Corresponding Author

*E-mail for T.W.H.: hayton@chem.ucsb.edu.

ORCID

Alexander J. Touchton: 0000-0002-3369-4702

Trevor W. Hayton: 0000-0003-4370-1424

Notes

The authors declare no competing financial interests.

ACKNOWLEDGMENT

We thank the National Science Foundation (CHE 1764345) for financial support of this work. This research made use of the 400 MHz NMR Spectrometer of the UCSB Chemistry Department, an NIH SIG (1S10OD012077-01A1). The MRL Shared Experimental Facilities are supported by the MRSEC Program of the National Science Foundation under award NSF DMR 1720256; a member of the NSF-funded Materials Research Facilities Network. A. J. T. thanks the Mellichamp Academic Initiative in Sustainability at UCSB for a summer fellowship.

REFERENCES

1. (a) Jin, R.; Zeng, C.; Zhou, M.; Chen, Y., Atomically Precise Colloidal Metal Nanoclusters and Nanoparticles: Fundamentals and Opportunities. *Chem. Rev.* **2016**, *116*, 10346; (b) Cook, A. W.; Hayton, T. W., Case Studies in Nanocluster Synthesis and Characterization: Challenges and Opportunities. *Acc. Chem. Res.*

2018, *51*, 2456; (c) Du, X.; Jin, R., Atomically Precise Metal Nanoclusters for Catalysis. *ACS Nano* **2019**, *13*, 7383; (d) Fang, J.; Zhang, B.; Yao, Q.; Yang, Y.; Xie, J.; Yan, N., Recent advances in the synthesis and catalytic applications of ligand-protected, atomically precise metal nanoclusters. *Coord. Chem. Rev.* **2016**, *322*, 1; (e) Jin, R., Atomically precise metal nanoclusters: stable sizes and optical properties. *Nanoscale* **2015**, *7*, 1549; (f) Zeng, C.; Chen, Y.; Das, A.; Jin, R., Transformation Chemistry of Gold Nanoclusters: From One Stable Size to Another. *J. Phys. Chem. Lett.* **2015**, *6*, 2976.

2. Cook, A. W.; Wu, G.; Hayton, T. W., A Re-examination of the Synthesis of Monolayer-Protected Co_x(SCH₂CH₂Ph)_m Nanoclusters: Unexpected Formation of a Thiolate-Protected Co(II) T3 Supertetrahedron. *Inorg. Chem.* **2018**, *57*, 8189.

3. Kagalwala, H. N.; Gottlieb, E.; Li, G.; Li, T.; Jin, R.; Bernhard, S., Photocatalytic hydrogen generation system using a nickel-thiolate hexameric cluster. *Inorg. Chem.* **2013**, *52*, 9094.

4. (a) Crocker, L. S.; Mattson, B. M.; Heinekey, D. M.; Schulte, G. K., Synthesis and characterization of (η³-trityl)tetracarbonylrhenium thermal precursor for generation of the pentacarbonylrhenium radical. *Inorg. Chem.* **1988**, *27*, 3722; (b) MacLeod, K. C.; DiMucci, I. M.; Zovinka, E. P.; McWilliams, S. F.; Mercado, B. Q.; Lancaster, K. M.; Holland, P. L., Masked Radicals: Iron Complexes of Trityl, Benzophenone, and Phenylacetylene. *Organometallics* **2019**, *38*, 4224.

5. (a) Jolly, P. W.; Wilke, G., Chapter IV - Nickel Hydride, Nickel Alkyl, and Nickel Aryl Complexes. In *The Organic Chemistry of Nickel*, Jolly, P. W.; Wilke, G., Eds. Academic Press: 1974; pp 139; (b) Sonada, A.; Mann, B. E.; Maitlis, P. M., Preparation and fluxional behaviour of α,1,2-η-triphenylmethylpalladium and -platinum complexes. *J. Chem. Soc., Chem. Commun.* **1975**, 108; (c) Seyferth, D.; King, R. B., *Annual Surveys of Organometallic Chemistry*. Elsevier Publishing Company: 1967; Vol. 3; (d) Wilke, G.; Schott, H., Bistritylnickel and Tritylnickel Chloride. *Angew. Chem. Int. Ed.* **1966**, *5*, 583.

6. (a) Goddard, R.; Krueger, C.; Mark, F.; Stansfield, R.; Zhang, X., Effect upon the hydrogen atoms of bonding an allyl group to a transition metal. A theoretical investigation and an experimental determination using neutron diffraction of the structure of bis(η³-allyl)nickel. *Organometallics* **1985**, *4*, 285; (b) Wilke, G.; Bogdanović, B., Bis-π-allyl-nickel. *Angew. Chem.* **1961**, *73*, 756; (c) Bönemann, H.; Bogdanović, B.; Wilke, G., cis- and trans-Bis-(π-allyl)nickel Systems. *Angew. Chem. Int. Ed.* **1967**, *6*, 804.

7. (a) Pasykiewicz, S.; Pietrzykowski, A.; Bukowska, L.; Słupecki, K.; Jerzykiewicz, L. B.; Urbańczyk-Lipkowska, Z., Reactions of nickelocene with diphenylmethyl- and triphenylmethyl-lithium. *J. Organomet. Chem.* **2000**, *604*, 241; (b) Sonoda, A.; Bailey, P. M.; Maitlis, P. M., Crystal and molecular structures of pentane-2,4-dionato-(α, 1,2-η-tri-phenylmethyl)-palladium and -platinum. *J. Chem. Soc., Dalton Trans.* **1979**, 346.

8. Fischer, P. J.; Ahrendt, K. A.; Young, V. G.; Ellis, J. E., Trityltitanium Complexes. X-ray Structural Characterization of [Ti(CO)₄{η⁵-C(4-C₆H₄R)₃}]⁻ (R = H, OCH₃). *Organometallics* **1998**, *17*, 13.

9. (a) Cotton, F. A.; Marks, T. J., Stereochemically nonrigid organometallic molecules. XX. Proton nuclear magnetic resonance study of the fluxional behavior of some substituted (1,2,7-trihaptobenzyl)(pentahaptocyclopentadienyl)dicarbonyl compounds of molybdenum and tungsten. *J. Am. Chem. Soc.* **1969**, *91*, 1339; (b) Becker, Y.; Stille, J. K., The dynamic η¹- and η³-benzylbis(triethylphosphine)palladium(II) cations. Mechanisms of interconversion. *J. Am. Chem. Soc.* **1978**, *100*, 845.

10. (a) Carmona, E.; Paneque, M.; Poveda, M. L., Synthesis and characterization of some new organometallic complexes of nickel(II) containing trimethylphosphine. *Polyhedron* **1989**, *8*, 285; (b) Wasilke, J.-C.; Ziller, J. W.; Bazan, G. C.,

Trimethylphosphine-bis(benzyl)nickel: Synthesis and Characterization. *Adv. Synth. Catal.* **2005**, *347*, 405.

11. Crawford Jr, B. L.; Cross, P. C., The vibrational spectrum and thermodynamic properties of nickel carbonyl. *J. Chem. Phys.* **1938**, *6*, 525.

12. Bramley, R.; Figgis, B. N.; Nyholm, R. S., ¹³C and ¹⁷O n.m.r. spectra of metal carbonyl compounds. *Trans. Faraday Soc.* **1962**, *58*, 1893.

13. Lankamp, H.; Nauta, W. T.; MacLean, C., A new interpretation of the monomer-dimer equilibrium of triphenylmethyl- and alkylsubstituted-diphenyl methyl-radicals in solution. *Tetrahedron Lett.* **1968**, *9*, 249.

14. Attempts to quantify the amount of Gomberg's dimer formed in the reaction were thwarted by the formation of several unidentified Gomberg's dimer decomposition products.

15. Mynott, R.; Mollbach, A.; Wilke, G., A proof of the existence of Ni[P(C₆H₅)₃]₄ in solution. *J. Organomet. Chem.* **1980**, *199*, 107.

16. Nguyen, T. A. D.; Jones, Z. R.; Goldsmith, B. R.; Buratto, W. R.; Wu, G.; Scott, S. L.; Hayton, T. W., A Cu₂₅ Nanocluster with Partial Cu(0) Character. *J. Am. Chem. Soc.* **2015**, *137*, 13319.

17. Doud, E. A.; Butler, C. J.; Paley, D. W.; Roy, X., Nickel Phosphinidene Molecular Clusters from Organocyclophosphine Precursors. *Chem. Eur. J.* **2019**, *25*, 10840.

18. (a) Pauling, L., Atomic Radii and Interatomic Distances in Metals. *J. Am. Chem. Soc.* **1947**, *69*, 542; (b) Eisenhart, R. J.; Rudd, P. A.; Planas, N.; Boyce, D. W.; Carlson, R. K.; Tolman, W. B.; Bill, E.; Gagliardi, L.; Lu, C. C., Pushing the Limits of Delta Bonding in Metal–Chromium Complexes with Redox Changes and Metal Swapping. *Inorg. Chem.* **2015**, *54*, 7579.

19. (a) Cook, S. L.; Evans, J.; Gray, L. R.; Webster, M., The preparation and crystal structure of Fe₃(CO)₉(μ₃-PPh)₂. *J. Organomet. Chem.* **1982**, *236*, 367; (b) Maclaughlin, S. A.; Carty, A. J.; Taylor, N. J., Hydrogénation of phosphido bridged ruthenium clusters. A view of P—C bond activation and cleavage in the coordinatively unsaturated molecule Ru₃(CO)₉(μ₂-PPh₂)(μ₂-H): conversion of μ₂-PPh₂ to μ₃-PPh. *Can. J. Chem.* **1982**, *60*, 87; (c) Lower, L. D.; Dahl, L. F., Synthesis and structural characterization of a new type of metal cluster system, octacarbonylhexakis(μ₄-phenylphosphido)octanickel, containing a completely bonding metal cube. A transition metal analog of cubane, C₈H₈. *J. Am. Chem. Soc.* **1976**, *98*, 5046; (d) Fenske, D.; Basoglu, R.; Hachgenei, J.; Rogel, F., Novel Clusters of Cobalt and Nickel with Organophosphorus Ligands. *Angew. Chem. Int. Ed.* **1984**, *23*, 160; (e) Fenske, D.; Hachgenei, J.; Rogel, F., [Ni₈(μ₄-PPh)₆(PPh₃)₄] and [Ni₉(μ₄-PPh)₆(PPh₃)₄]; Cluster with Coordinatively Unsaturated Ni-Atoms. *Angew. Chem. Int. Ed.* **1984**, *23*, 982; (f) Coleman, J. M.; Dahl, L. F., Molecular Structures of [(C₆H₅)₂PCoC₃H₅]₂ and [C₆H₅]₂PNiC₃H₅]₂. An Assessment of the Influence of a Metal-Metal Bond on the Molecular Geometry of an Organometallic Ligand-Bridged Complex. *J. Am. Chem. Soc.* **1967**, *89*, 542; (g) Lu, Z.; Abbina, S.; Sabin, J. R.; Nemykin, V. N.; Du, G., Unexpected Formation of Chiral Pincer CNN Nickel Complexes with β-Diketiminato Type Ligands via C–H Activation: Synthesis, Properties, Structures, and Computational Studies. *Inorg. Chem.* **2013**, *52*, 1454; (h) Lower, L. D.; Dahl, L. F., Synthesis and structural characterization of a new type of metal cluster system, octacarbonylhexakis(μ₄-phenylphosphido)octanickel, containing a

completely bonding metal cube. A transition metal analog of cubane, C₈H₈. *J. Am. Chem. Soc.* **1976**, *98*, 5046; (i) Rieck, D. F.; Gavney, J. A.; Norman, R. L.; Hayashi, R. K.; Dahl, L. F., Synthesis, chromatographic separation, and stereophysical analysis of the homologous [Ni_{12-x}(PMe)_x(CO)_{24-3x}]²⁻ series (x = 2, 3, 4) containing noncentered Ni_{12-x}P_x icosahedral cages and the [Ni₁₀(μ₅-PMe)₂(μ₄-PMe)₅(CO)₁₀]²⁻ dianion containing a structurally unprecedented heptacapped pentagonal prismatic metal cage: structural, spectroscopic, and electrochemical consequences due to replacement of Ni(CO)₃ fragments with electronically equivalent (isolobal) PME fragments. *J. Am. Chem. Soc.* **1992**, *114*, 10369; (j) Beck, R.; Shoshani, M.; Krasinkiewicz, J.; Hatnean, J. A.; Johnson, S. A., Synthesis and chemistry of bis(triisopropylphosphine) nickel(i) and nickel(0) precursors. *Dalton Trans.* **2013**, *42*, 1461; (k) Haehnel, M.; Hansen, S.; Schubert, K.; Arndt, P.; Spannenberg, A.; Jiao, H.; Rosenthal, U., Synthesis, Characterization and Reactivity of Group 4 Metallocene Bis(diphenylphosphino)acetylene Complexes—A Reactivity and Bonding Study. *J. Am. Chem. Soc.* **2013**, *135*, 17556; (l) Keşanlı, B.; Gardner, D. R.; Scott, B.; Eichhorn, B. W., Two new bimetallic phosphido carbonyl complexes of nickel(0): [Ni₂(CO)₂(PPh₃)₂(μ-CO)(μ-PPh₂)]⁻ and [Ni₂(CO)₄(μ-PPh₂)₂]²⁻. *J. Chem. Soc., Dalton Trans.* **2000**, 1291.

20. Yang, L.; Powell, D. R.; Houser, R. P., Structural variation in copper(i) complexes with pyridylmethylamide ligands: structural analysis with a new four-coordinate geometry index, τ⁴. *Dalton Trans.* **2007**, 955.

21. Chen, Y.; Sui-Seng, C.; Zargarian, D., Tetraphenylborate as a Novel Bridging Ligand in a Zwitterionic Nickel(I) Dimer. *Angew. Chem. Int. Ed.* **2005**, *44*, 7721.

22. (a) Eisch, J. J.; Yu, K.; Rheingold, A. L., 6,12-Diphenyldibenzo[b,f][1,5]diazocine as an Electron-Capture Agent: Efficient Mechanistic Probe for SET Processes and Reagent for the Oxidative Dimerization of Benzylic Organometallics. *Eur. J. Org. Chem.* **2012**, *2012*, 3165; (b) Hiroshi, T.; Toshikazu, N.; Niichiro, T., The Transformation of the Triphenylmethyl Radical into the Triphenylmethyl Cation in the Sulfur Dioxide - Oxygen System. *Bull. Chem. Soc. Jpn.* **1970**, *43*, 1747; (c) Chen, C.; Lee, H.; Jordan, R. F., Synthesis, Structures, and Ethylene Polymerization Behavior of Bis(pyrazolyl)borate Zirconium and Hafnium Benzyl Complexes. *Organometallics* **2010**, *29*, 5373.


23. Fahey, D. R.; Mahan, J. E., Reversible oxidative addition of triphenylphosphine to zero-valent nickel and palladium complexes. *J. Am. Chem. Soc.* **1976**, *98*, 4499.

24. Nattmann, L.; Saeb, R.; Nöthling, N.; Cornella, J., An air-stable binary Ni(0)–olefin catalyst. *Nat. Catal.* **2020**, *3*, 6.

25. (a) Tolman, C. A., Phosphorus ligand exchange equilibria on zerovalent nickel. Dominant role for steric effects. *J. Am. Chem. Soc.* **1970**, *92*, 2956; (b) Dander, J. E.; Weires, N. A.; Garg, N. K., Benchtop Delivery of Ni(cod)₂ using Paraffin Capsules. *Org. Lett.* **2016**, *18*, 3934.

26. Tasker, S. Z.; Standley, E. A.; Jamison, T. F., Recent advances in homogeneous nickel catalysis. *Nature* **2014**, *509*, 299.

Reaction of NiCl_2 with 2 equiv of $\text{Li}(\text{CPh}_3)$ in THF results in formation of $\text{Ni}(\eta^3\text{-CPh}_3)_2$, an air- and water-stable source of nickel(0).

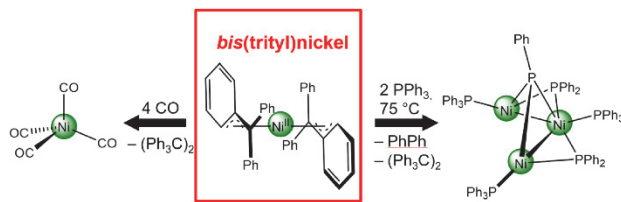

- ✓ Convenient source of $\text{Ni}(0)$
 - ✓ Air-stable as a solid
 - ✓ Inexpensive synthesis
-