

UC Irvine

UC Irvine Previously Published Works

Title

Low-temperature magnetism in YbBiPt

Permalink

<https://escholarship.org/uc/item/6f30q1cf>

Journal

Physical Review B, 46(5)

ISSN

2469-9950

Authors

Amato, A
Canfield, PC
Feyerherm, R
et al.

Publication Date

1992-08-01

DOI

10.1103/physrevb.46.3151

Copyright Information

This work is made available under the terms of a Creative Commons Attribution License, available at <https://creativecommons.org/licenses/by/4.0/>

Peer reviewed

Low-temperature magnetism in YbBiPt

A. Amato

*Institut für Mittelenergiephysik der Eidgenössische Technische Hochschule Zürich,
CH-5232 Villigen PSI, Switzerland*

P. C. Canfield

Los Alamos National Laboratory, Los Alamos, New Mexico 87545

R. Feyherm

*Institut für Mittelenergiephysik der Eidgenössische Technische Hochschule Zürich,
CH-5232 Villigen PSI, Switzerland*

Z. Fisk

Los Alamos National Laboratory, Los Alamos, New Mexico 87545

F. N. Gyax

*Institut für Mittelenergiephysik der Eidgenössische Technische Hochschule Zürich,
CH-5232 Villigen PSI, Switzerland*

R. H. Heffner

Los Alamos National Laboratory, Los Alamos, New Mexico 87545

D. E. MacLaughlin*

Kamerlingh Onnes Laboratorium, University of Leiden, 2300 RA Leiden, The Netherlands

H. R. Ott

Laboratorium für Festkörperphysik, Eidgenössische Technische Hochschule Hönggerberg, CH-8093 Zürich, Switzerland

A. Schenck

*Institut für Mittelenergiephysik der Eidgenössische Technische Hochschule Zürich,
CH-5232 Villigen PSI, Switzerland*

J. D. Thompson

Los Alamos National Laboratory, Los Alamos, New Mexico 87545

(Received 13 April 1992)

Positive-muon (μ^+) spin-relaxation experiments have been carried out in a pressed-powder sample of the low-carrier-density heavy-electron system YbBiPt. Spatially inhomogeneous and disordered static Yb magnetism is observed below ~ 0.5 K, with a strongly reduced Yb moment of $\sim 0.1\mu_B$ over $\sim 50\%$ of the sample volume at $T=0.06$ K. Substantial μ^+ spin-lattice relaxation, rarely observed in heavy-electron systems, suggests anomalously slow Yb spin fluctuations. Our data are reminiscent of μ^+ behavior in spin glasses, and raise the question of whether the large low-temperature specific heat in YbBiPt is due in part to low-lying magnetic excitations.

The RBiPt (R =rare earth) series of ternary intermetallic compounds exhibits a rather unique evolution from insulating to weak metallic behavior with increasing rare-earth atomic number.¹ Among these materials YbBiPt is of particular interest. Measurements of the specific heat c_p is flux-grown single crystals of this compound² yield an enormous Sommerfeld coefficient $\gamma=c_p/T\approx 8$ Jmol⁻¹K⁻² below ~ 0.4 K, suggestive of an extremely massive itinerant-electron state. A low characteristic temperature is indicated by an entropy release of $R\ln 2$ between zero and 1 K. A cusp in the ac susceptibility at 0.4 K indicates some sort of low-temperature magnetic phase which seems to coexist with the heavy-electron state. The specific heat of crushed powders of YbBiPt (Ref. 3) is

nearly the same as in unstrained material above 0.5 K, but below this temperature the c_p/T ratio is reduced by approximately 50% and there is no clear evidence for a magnetic phase transition.

These results indicate that YbBiPt is situated on the boundary between magnetic and heavy-electron behavior with respect to the Yb spin degrees of freedom. Questions are raised concerning (1) the stability of the Yb moment, (2) the nature of a heavy-electron state which can evolve from a low-carrier-density metal at high temperatures, and (3) the competition between Kondo singlet formation and Rudermann-Kittel-Kasuya-Yosida interactions.

This paper presents the results of positive-muon spin rotation (μ^+ SR) experiments which bear on the above

questions. Like other magnetic resonance techniques, μ^+ SR provides a microscopic probe of local static and dynamic magnetic behavior in solids.⁴ In the time-differential μ^+ SR method used in these studies spin-polarized positive muons (μ^+) are implanted into the sample, and the subsequent precession and relaxation of the μ^+ polarization is monitored. In high transverse applied field H_{\perp} (applied field H_0 perpendicular to the μ^+ polarization p_{μ}) the relaxation rate is usually determined by the inhomogeneous distribution of static local fields at μ^+ sites. In high longitudinal field H_{\parallel} ($H_0 \parallel p_{\mu}$) the relaxation is due to thermal fluctuations of the local fields (spin-lattice relaxation),^{4,5} and in zero applied field both dynamic and static relaxation components can be observed.^{5,6} Zero to high field crossover occurs when $|H_0|$ is of the order of the static local field distribution width ΔH_L . One complication associated with the technique is the fact that the number and location of muon stopping sites may not be known.

Polycrystals of YbBiPt were prepared by the flux-growth technique.⁷ They were crushed, mixed with a small amount of GE 7031 varnish, and pressed to form a pellet with $\sim 80\%$ of the theoretical density. The μ^+ SR experiments were carried out at the Low Temperature Facility of the Paul Scherrer Institute, Villigen, Switzerland, over the temperature range 0.06–300 K.

Figure 1 shows the observed time-differential relaxation function $G_{ZF}(t)$ in zero applied field for $T=0.06$ K. There is no sign of a well-defined precession frequency or frequencies, indicating that static YB magnetism, if present, is either spatially disordered or incommensurate. The two-component structure evident in Fig. 1 is observed for $T \lesssim 20$ K. Good fits were obtained to a sum of fast and slow components of the form $G_{ZF}(t) = A_f g_f(t) + A_s \exp(-\lambda_s t)$, where A_f and A_s are the amplitudes of

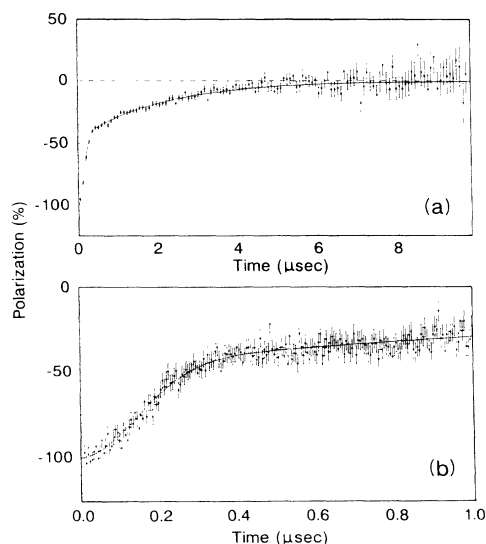


FIG. 1. Zero-field time-differential μ^+ SR histogram in Yb-BiPt, $T=0.060$ K. (a) Time range 0–8 μ s. The two-component structure is easily recognizable. (b) Time range 0–10 μ s, showing early part of the relaxation function. The Gaussian nature of the fast component is evident.

the fast and slow components, respectively, and λ_s is the exponential rate of the slow component. The form $g_f(t)$ of the fast component was observed to change abruptly from Gaussian [$g_f = \exp(-\sigma_f^2 t^2)$] below 0.5 K (cf. Fig. 1) to exponential [$g_f = \exp(-\lambda_f t)$] above this temperature. The relaxation rates and the component amplitudes A_f and A_s were varied for best fit, with the total amplitude $A_f + A_s$ held at a value obtained from weak transverse-field calibration runs.

The temperature dependence of A_f and A_s is given in Fig. 2. With increasing temperature A_f decreases monotonically (with a corresponding increase of A_s). By ~ 0.5 K half the weight of the fast component has been transferred to the slow component. This is near the temperature at which the Gaussian to exponential crossover occurs, and where c_p/T of the crushed sample shows a maximum.³ Above 30 K $A_f \approx 0$.

The temperature dependence of the fast-component Gaussian relaxation rate σ_f below 0.5 K is given in Fig. 3(a). Measurement of the fast-component exponential relaxation rate λ_f above 0.5 K was only possible below ~ 0.7 K, due to the small values of A_f for higher temperatures (Fig. 2); in this limited temperature range $\lambda_f \approx 3 \mu\text{s}^{-1}$. The slow-component exponential relaxation rate λ_s is given in Fig. 3(b). Assuming that the relaxation is in the motionally narrowed limit, the observed decrease in λ_s with increasing temperature up to ~ 1 K [Fig. 3(b)] indicates that the μ^+ local-field fluctuation rate increases with temperature over this range. The rapid decrease of λ_s above 100 K probably signals the onset of μ^+ diffusion.

Measurements in a longitudinal field $H_{\parallel} = 5$ kOe between 0.1 and 1.06 K revealed substantial μ^+ spin-lattice relaxation. An example for $T=0.06$ K is given in Fig. 4. Observable spin-lattice relaxation is rare in heavy-electron and related systems, and indicates low-frequency fluctuations of an appreciable Yb moment. The exponential form $G_{\parallel}(t) = A_{\parallel} \exp(-\lambda_{\parallel} t)$ gave good fits to the data. The amplitude A_{\parallel} was reduced to $\sim 0.4(A_f + A_s)_{ZF}$ (cf. Fig. 4), independent of temperature, and the relaxation rate λ_{\parallel} varied only slightly, from 0.75(5) μs^{-1} at 0.1 K to 1.0(1) μs^{-1} at 1.06 K.

Interpretation of these data depends on knowledge of the number of μ^+ stopping sites, so we begin by consider-

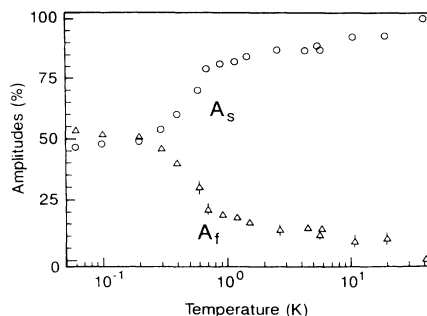


FIG. 2. Temperature dependence of zero-field μ^+ SR fast- and slow-component amplitudes in YbBiPt. Δ : fast-component amplitude A_f . \circ : slow-component amplitude A_s . Relative values of A_f and A_s are measures of the volume fractions of “frozen-spin” and “paramagnetic” domains, respectively.

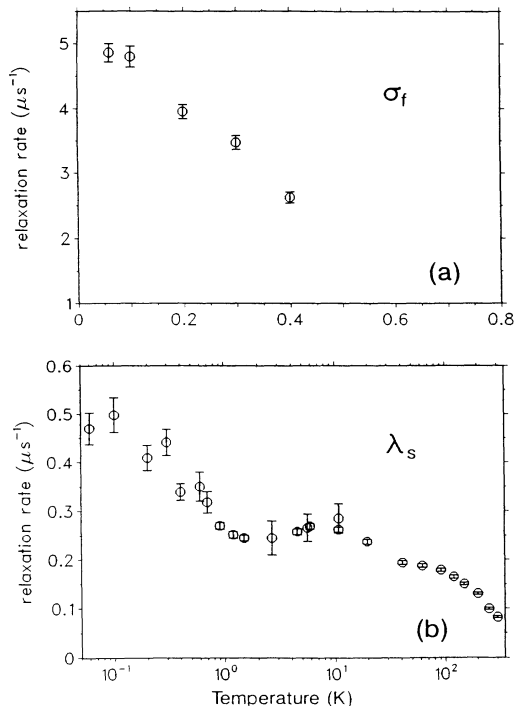


FIG. 3. Temperature dependence of zero-field fast- and slow-component μ^+ SR relaxation rates in YbBiPt. (a) Fast-component Gaussian relaxation rate $\sigma_f = \sigma_{KT}$ below 0.5 K. (b) Slow-component exponential relaxation rate λ_s . The fast-component exponential relaxation rate $\lambda_f \approx 3 \mu\text{s}^{-1}$ between 0.5 and 0.7 K is not shown.

ing this question. μ^+ SR was carried out in a transverse field $H_{\perp} = 2.9$ kOe at temperatures above 2.5 K. These measurements, which will be reported elsewhere in more detail, yielded a single signal with asymmetric broadening typical of an anisotropic Knight shift powder pattern. There is therefore only one μ^+ site, and this site has lower than tetrahedral symmetry. Comparing these data with simulated μ^+ powder spectra, we tentatively identify the muon site as an off-center position shifted 0.4 \AA from the $(\frac{1}{2}, \frac{1}{2}, \frac{1}{2})$ point toward a nearest-neighbor Bi in the fcc MgAgAs (half-Heusler) structure.

The existence of two μ^+ SR signal components in zero field then suggests the existence of two different magnetic

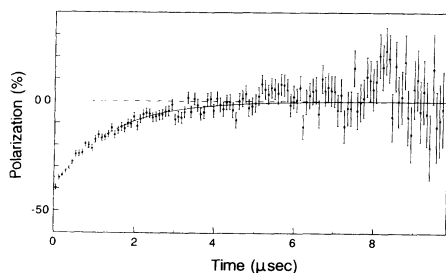


FIG. 4. Time-differential μ^+ SR histogram in YbBiPt, longitudinal field $H_{\parallel} = 5$ kOe, temperature 0.06 K. Note the reduced amplitude compared to the zero-field histograms of Fig. 1.

environments or domains. The size of these domains is unknown, except that they must be somewhat larger than a few unit cell volumes. The fast Gaussian component below 0.5 K must originate from “frozen-spin” domains characterized by a static or quasistatic field component distribution with zero mean and rms width $\Delta H_L = \sigma_f / \gamma_{\mu}$, where γ_{μ} is the μ^+ gyromagnetic ratio. This result rules out a nonmagnetic ground state for $\sim 50\%$ of our sample. A Gaussian distribution is expected for a regular lattice of randomly oriented moments,^{6,8} but not for an incommensurate periodic spin arrangement.

For random moment orientations the zero-field μ^+ SR signal should be given by the static Kubo-Toyabe (KT) function⁶ $G_{KT}(t) = \frac{1}{3} + \frac{2}{3}(1 - \sigma_{KT}^2 t^2) \exp(-\frac{1}{2} \sigma_{KT}^2 t^2)$. The short-time behavior of $G_{KT}(t)$ is Gaussian, in agreement with our data, with $\sigma_f = \sigma_{KT}$. We do not observe the typical KT recovery to $\frac{1}{3}$ at long times, which indicates that the recovery signal is damped by spin-lattice relaxation.

The static disordered magnetism in frozen-spin domains indicated by the Gaussian form of the rapid component is not likely to be due to lattice defects, given the sharp x-ray Bragg lines in our YbBiPt samples. The observed value of σ_f at low temperatures corresponds to $\Delta H_L \approx 60$ Oe. Assuming dipolar coupling to a muon at the site described above, a standard Van Vleck second-moment calculation yields $\sim 0.1 \mu_B$ for the static Yb moment. This is consistent with the absence of a nuclear Schottky term in the specific heat,² which would not be observed above ~ 50 mK for this moment value.

The abrupt crossover at 0.5 K of the fast component from a Gaussian to an exponential form signals the loss of a static spin component and onset of strong thermal fluctuations in the μ^+ local field in the corresponding domains. (We will continue to use the label “frozen-spin” for these domains even though there is no static spin component above 0.5 K.) In the motionally narrowed limit^{5,6} $\lambda_f = 2\sigma_{KT}^2 \tau_c$, where τ_c is the correlation time of the spin fluctuations. With $\sigma_{KT} = 5 \mu\text{s}^{-1}$ from the low-temperature data, we obtain $\tau_c \approx 2 \times 10^{-7}$ s between 0.5 and 0.7 K.

The slow zero-field component is exponential over the full temperature range 0.06–300 K. This indicates the absence of static Yb magnetism and motionally narrowed relaxation by spin fluctuations in the corresponding “paramagnetic” domains, for which we obtain $t_c \approx 10^{-8}$ s at low temperatures. For a system obeying ordinary spin dynamics with a characteristic energy scale $k_B T_0$, an order-of-magnitude estimate of τ_c is $(k_B T_0 / \hbar)^{-1} \sim 10^{-11}$ s if we take $T_0 \sim 0.5$ K. The observed correlation times are very much longer than this in both paramagnetic and frozen-spin domains.

The relaxation in a longitudinal field of 5 kOe also indicates the presence of two components, viz., the observed signal and an unobserved fraction. The latter is probably a nonrelaxing constant background due to frozen-spin domains.⁹ Unlike the behavior in zero field, however, the volume fraction of frozen-spin domains in 5 kOe appears to be temperature independent between 0.1 and 1 K. In addition λ_{\parallel} is larger than λ_s in zero field, which can be understood only if τ_c increases with increasing field. Thus

the presence of an external field $H \sim k_B T_0 / \mu_B$, where $T_0 \approx 0.5$ K as estimated above, seems to alter the microscopic behavior of the sample considerably. The magnetoresistance of YbBiPt is also found to be very sensitive to small ($\lesssim 5$ kOe) magnetic fields.²

Several conclusions can be drawn from these data.

(1) The observed two-component form of the μ^+ relaxation function suggests an inhomogeneous distribution of Yb magnetism over two kinds of domains. Similar behavior has been reported in the heavy-electron compounds CeAl₃ (Ref. 10) and URu₂Si₂ (Ref. 11), where it is regarded as an intrinsic property.

(2) Disordered static magnetism, with a Yb moment much less than the free-ion value, sets in abruptly below 0.5 K over about half of the sample. This temperature corresponds to the maximum in the specific heat observed in other crushed-power samples.³ The sharp transition precludes the attribution of the more continuous temperature dependence of the frozen-spin volume fraction (Fig. 2) to a distribution of transition temperatures. Taken as a whole the data suggest a percolative process, which attains the percolation threshold at ~ 0.5 K.

(3) The Yb moment of $\sim 0.1 \mu_B$ deduced from our measurements is 40 times smaller than the free-ion value, and is also much smaller than Yb crystal electric field (CEF) Γ_6 or Γ_7 doublet ground-state moments.¹² Weak-moment static magnetism has also been observed in several heavy-electron systems with higher carrier densities.¹³

(4) The rapid μ^+ spin-lattice relaxation rates yield Yb spin correlation times which are anomalously long [$\tau_c \sim 10^3 - 10^4 (k_B T_0 / \hbar)^{-1}$] in both kinds of domains.

The enormous low-temperature specific-heat γ in YbBiPt has been attributed to itinerant heavy-electron behavior.² Our μ^+ SR observation of slow spin fluctuations and static magnetism in this compound raises the alternative possibility that a high density of low-lying magnetic excitations yields the large γ . This is the case for spin glasses, where a large temperature-linear term is found in the specific heat¹⁴ (although never as large as in the present case) and where μ^+ SR experiments [e.g., in AgMn (Ref. 15)] have confirmed the presence of a wide distribution of spin fluctuation rates. μ^+ SR relaxation behavior is qualitatively similar in YbBiPt and spin glasses.

Our observation of differentiated types of magnetic domain may also shed light on the observed reduction³ of γ in powdered YbBiPt. We surmise that strain introduced by powdering creates the two types of domain (paramagnetic and frozen spin), one of which gives little or no contribution to the low-temperature γ . At high temperatures the paramagnetic domains dominate. The increase with decreasing temperature of the relative volume fraction of the frozen-spin domains might be due to a percolative process; the observed static spin freezing at ~ 0.5 K could then signal the formation of an infinite cluster. Domains might be induced by strain dependence of the Kondo temperature, with paramagnetic and frozen-spin domains corresponding to regions where Kondo compensation or magnetic interactions, respectively, characterize the ground state.

Further μ^+ SR experiments using unstrained YbBiPt are currently in progress to address these issues. The association between the large γ and static Yb magnetism would be strengthened by observation of such magnetism over the entire sample volume, particularly if the magnetism were disordered. If no static magnetism is observed in unstrained samples the large γ must be due solely to heavy itinerant electrons. (The strain-induced domain picture for reduction of γ would of course not hold if domain structure is also observed in unstrained high- γ samples.) In either case the strain sensitivity of the magnetic and thermal properties underscores the very delicate balance between heavy-electron formation and magnetism in this system.

We acknowledge with thanks the expert help of C. Baines, D. Herlach, and the accelerator crew of PSI during the experiments, and have benefited from discussions with A. Lacerda, W. P. Beyermann, E. A. Knetsch, and J. A. Mydosh. Work at UC Riverside was supported in part by NSF Grants No. DMR-8814783 and No. DMR-9114911, and the UC Riverside Academic Senate Committee on Research. Research at Leiden was supported financially by the Netherlands NWO and FOM. Work at Los Alamos was performed under the auspices of the U.S. Department of Energy. The financial support of the Schweizerische Nationalfonds is gratefully acknowledged.

*Permanent address: University of California, Riverside, CA 92521-0413.

¹P. C. Canfield *et al.*, J. Appl. Phys. **70**, 5800 (1991).

²Z. Fisk *et al.*, Phys. Rev. Lett. **67**, 3310 (1991).

³A. Lacerda *et al.* (unpublished).

⁴For a description of the μ SR technique, see A. Schenck, *Muon Spin Rotation Spectroscopy* (Hilger, Bristol, 1985).

⁵See, for example, C. P. Slichter, *Principles of Magnetic Resonance*, 3rd ed. (Springer-Verlag, Berlin, 1990).

⁶R. Kubo and T. Toyabe, in *Magnetic Resonance and Relaxation*, edited by R. Blinc (North-Holland, Amsterdam, 1967), p. 810; see also R. S. Hayano *et al.*, Phys. Rev. B **20**, 850 (1979).

⁷P. C. Canfield and Z. Fisk, Philos. Mag. B (to be published).

⁸Spin-lattice relaxation yields an exponential relaxation function, as does the static distribution of local fields in a dilute

spin glass [R. E. Walstedt and L. R. Walker, Phys. Rev. B **9**, 4857 (1974)].

⁹Alternatively, the invisible component might reflect extremely rapid dynamics (short correlation times) leading to undetectably slow μ^+ relaxation. This seems unlikely, given the static component observed in zero field.

¹⁰S. Barth *et al.*, Phys. Rev. B **39**, 11 695 (1989).

¹¹G. M. Luke *et al.*, Bull. Am. Phys. Soc. **37** (1), 60 (1992).

¹²K. Sugawara, J. Phys. Soc. Jpn. **42**, 1161 (1977).

¹³See, for example, D. E. MacLaughlin, in *Encyclopedia of Physics*, 2nd ed., edited by R. G. Lerner and G. L. Trigg (VCH, New York, 1991), p. 484, and references therein.

¹⁴L. E. Wenger and P. M. Keesom, Phys. Rev. B **11**, 3497 (1975).

¹⁵D. E. MacLaughlin *et al.*, Phys. Rev. Lett. **51**, 927 (1983).