

UC Irvine

UC Irvine Previously Published Works

Title

Magnetoresistance and upper critical magnetic field of UBe13 under pressure

Permalink

<https://escholarship.org/uc/item/6j27m137>

Journal

Journal of Magnetism and Magnetic Materials, 63(C)

ISSN

0304-8853

Authors

Willis, JO
Thompson, JD
Smith, JL
[et al.](#)

Publication Date

1987

DOI

10.1016/0304-8853(87)90636-6

Copyright Information

This work is made available under the terms of a Creative Commons Attribution License, available at <https://creativecommons.org/licenses/by/4.0/>

Peer reviewed

MAGNETORESISTANCE AND UPPER CRITICAL MAGNETIC FIELD OF UBe_{13} UNDER PRESSURE

J O WILLIS, J D THOMPSON,* J L SMITH and Z FISK

Materials Science and Technology Division, Mail Stop G730, Los Alamos National Laboratory, Los Alamos, NM 87545, USA

**Physics Division, Los Alamos National Laboratory, Los Alamos, NM 87545, USA*

We have investigated the effects of pressure on the magnetoresistance and the upper critical magnetic field of the heavy electron compound UBe_{13} . Both the superconducting transition temperature and the upper critical field decrease under hydrostatic pressure. The low temperature magnetoresistance remains large and negative under pressure. The temperature region over which the resistivity has a T^2 temperature dependence increases with both magnetic field and with pressure. At a fixed magnetic field, the coefficient of the T^2 term in the resistivity decreases strongly with pressure. UBe_{13} is found to have a pressure independent intrinsic residual resistivity of $18 \mu\Omega\text{cm}$.

UBe_{13} [1] is one of the three heavy electron superconductors characterized by large values of the dc susceptibility at zero temperature and of the electronic specific heat coefficient γ ($=C/T$), which taken together imply electron masses of several hundred times the free electron value. This intermetallic compound is superconductive below $T_c = 0.9$ K and has extremely large values of $B'_{c2} \equiv -dB_{c2}/dT|_{T=T_c}$ of 42 T/K or possibly larger, and extrapolated values of $B_{c2}(T=0)$ in excess of 9 T [2]. Such values reflect the large electron mass and the high normal state resistivity at T_c of about $130 \mu\Omega\text{cm}$. UBe_{13} also exhibits a very large negative magnetoresistance, amounting to 35% at T_c^+ and 5 T [2].

In addition to the striking response of UBe_{13} in both the normal and superconducting state to magnetic fields, the effects of impurity substitution are unique [3, 4]. Dilute thorium substitutions for uranium show a nonmonotonic depression of T_c with concentration. A second large anomaly appears in the specific heat data well below T_c and then vanishes again as the Th concentration is increased. In general, impurity substitutions may effect both the interatomic spacing and the number of conduction electrons. In contrast, hydrostatic pressure may be used to vary the interatomic spacing with no other perturbing effects. Because of the many interesting

and unusual properties of UBe_{13} noted above, we have here investigated the effects of pressure on T_c , B'_{c2} , and $\rho(T, B)$ of UBe_{13} . Pressure has been shown to reduce the C/T value by 30% at pressures of about 9 kbar [5]. Recent measurements above 1 K at Los Alamos [6] show that the position and magnitude of the 2.5 K resistivity peak in UBe_{13} both show a strong positive correlation with pressure. In addition, for pressures greater than ≈ 9 kbar, the resistivity exhibited a T^2 temperature dependence over a limited temperature interval above 1 K that increased with pressure. Such temperature dependences had only been observed previously below 1 K in the presence of a large magnetic field ($B > 3$ T) [7].

In this work we have measured the magnetoresistance and the upper critical magnetic field of polycrystalline UBe_{13} between 0 and 9 T, at pressures from 0 to 19 kbar, and at temperatures down to approximately 150 mK, below which thermal equilibrium times in the self-clamped Cu-Be cell employed became excessive. The measurements were performed using a conventional four-terminal ac resistance technique with transport currents of 0.07 A/cm^2 or smaller to avoid joule heating effects. The transport current was roughly parallel to the applied magnetic field. The pressures were determined from the T_c of a tin manometer.

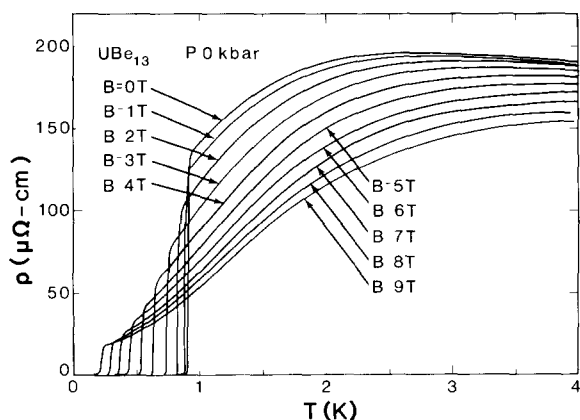


Fig 1 Resistivity versus temperature for UBe_{13} at zero pressure and at the magnetic field values indicated

Results are shown for representative pressures of 0 and 19 kbar in figs 1 and 2, respectively, where it is immediately apparent that for $T < 4$ K the resistivity at 19 kbar is strongly depressed relative to its zero pressure value. The superconducting transition temperature T_c was found to decrease at the rate of about 16 mK/kbar. This value is slightly larger than that found previously by ac susceptibility measurements [8] on a polycrystalline sample with a T_c of 0.85 K versus the present value of 0.905 K. The upper critical magnetic field $B_{c2}(T)$ is strongly depressed by pressure, as seen in fig 3. We have extrapolated the critical field

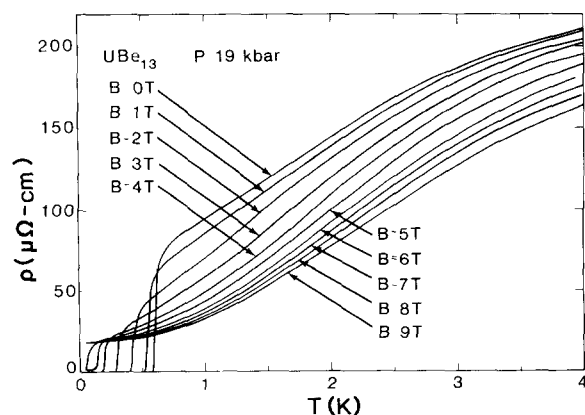


Fig 2 Resistivity versus temperature for UBe_{13} at 19 kbar and at the magnetic field values indicated

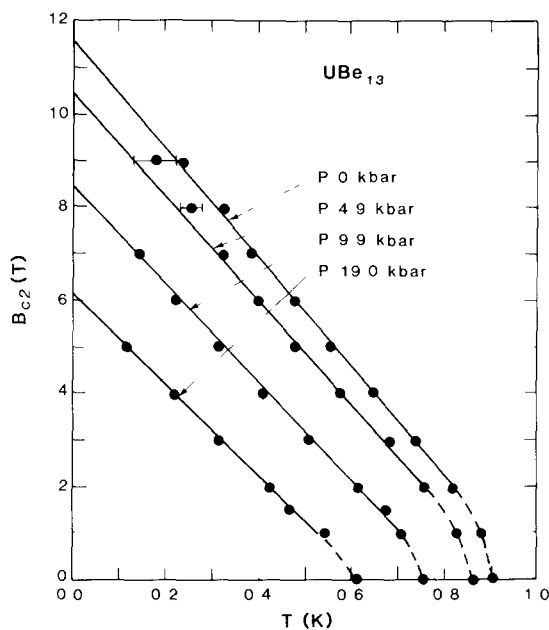


Fig 3 Upper critical magnetic field versus temperature for UBe_{13} at the pressure values indicated. The lines are only a guide to the eye.

linearly to $T = 0$ as there is no evidence that $B_{c2}(T)$ approaches the temperature axis with zero slope, as has been noted previously [2]. The values of $B_{c2}(0)$ so obtained decrease linearly with pressure at the rate of 0.29 T/kbar, with a $P = 0$ value of 11.5 T, somewhat larger than that reported previously [2, 9]. Additionally, we find that B'_{c2} decreases dramatically with pressure in correspondence to the large decrease in C/T [5] and the normal state resistivity at T_c .

Examining now the normal state properties, we observe that the large negative magnetoresistance persists at 19 kbar. As is evident from figs 1 and 2, the magnetoresistance is a complex function of temperature and magnetic field, and it cannot be determined explicitly below T_c ($B = 0$). The normal state resistivity is decreased with both pressure and magnetic field, and we find an intrinsic resistivity ρ_0 of $18 \mu\Omega\text{cm}$ that is independent of pressure. This is an important result in that previous measurements above 1 K [6] exhibited a tendency toward a constant ρ_0 but were not able to extract a precise value.

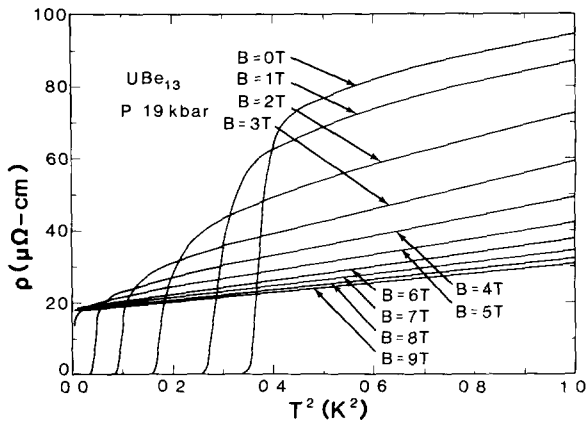


Fig 4 Resistivity versus temperature-squared for UBe_{13} at 19 kbar and at the magnetic field values indicated

Fig 4 shows the resistivity versus temperature-squared for UBe_{13} at 19 kbar. There are large regions over which the temperature dependence is indeed quadratic at the higher fields, with the coefficient A in $\rho = \rho_0 + AT^2$ decreasing for fields of 3 T and larger. There may be smaller ranges over which a T^2 dependence occurs at lower fields, but they are somewhat obscured by a high temperature tail of the superconducting transition. The coefficient A has a value of about $13 \mu\Omega\text{cm}/\text{K}^2$ at 19 kbar and $B = 9 \text{ T}$, which is much lower than the value of $34 \mu\Omega\text{cm}/\text{K}^2$ for the same field at $P = 0$. If A is assumed to be proportional to $1/T_f^2$ where T_f is the Fermi temperature of the heavy mass state, then these results would suggest that the highest attained pressure and magnetic field have increased the degeneracy temperature by roughly a factor of 3 to 4 relative to ambient conditions. Indeed, the region over which a T^2 dependence in ρ is observed at 9 T increases from less than 1 K at $P = 0$, to 1.4 K at $P = 9.9 \text{ kbar}$, and to 2 K at $P = 19 \text{ kbar}$.

In conclusion, we find strong effects of pressure on the superconducting transition temperature, on the upper critical magnetic field, the resistance, and the magnetoresistance of UBe_{13} . The results suggest the depression of the mass of the heavy electrons with pressure and with magnetic field and the increase in temperature of the regime in which UBe_{13} exhibits Fermi liquid-like effects, notably a quadratic temperature dependence of the resistivity at low temperatures. Finally our results point to an intrinsic, pressure independent, impurity dominated residual resistivity for UBe_{13} of $18 \mu\Omega\text{cm}$ in the high magnetic field limit.

This work was performed under the auspices of the US Department of Energy.

References

- [1] H R Ott, H Rudigier, Z Fisk and J L Smith, Phys Rev Lett 50 (1983) 1595
- [2] M B Maple, J W Chen, S E Lambert, Z Fisk, J L Smith, H R Ott, J S Brooks and M J Naughton, Phys Rev Lett 54 (1985) 477
- [3] J L Smith, Z Fisk, J O Willis, B Batlogg and H R Ott, J Appl Phys 53 (1984) 1996
- [4] H R Ott, H Rudigier, Z Fisk and J L Smith, Phys Rev B31 (1985) 1651
- [5] J A Olsen, R A Fisher, N E Phillips, G R Stewart and A L Giorgi, Bull Am Phys Soc 31 (1986) 648
- [6] J D Thompson, M W McElfresh, J O Willis, Z Fisk, J L Smith and M B Maple, Bull Am Phys Soc 31 (1986) 445
- [7] G Remenyi, D Jaccard, J Floquet, A Briggs, Z Fisk, J L Smith and H R Ott, submitted to J de Phys
- [8] J W Chen, S E Lambert, M B Maple, Z Fisk, J L Smith and H R Ott, Proc 17th Intern Conf on Low Temp Phys eds U Eckern, A Schmid, W Weber and H Wuehl (North-Holland, Amsterdam, 1984) p 325
- [9] U Rauchschwalbe, U Ahlheim, F Steglich, D Rainer and J J M Franse, Z Phys B60 (1985) 379