

Lawrence Berkeley National Laboratory

Recent Work

Title

HIGH-TEMPERATURE HEAT CONTENT OF HAFNIUM

Permalink

<https://escholarship.org/uc/item/7b3606q3>

Authors

Hawkins, Donald T.

Onillon, Marc

Orr, Raymond L.

Publication Date

1963-03-01

University of California

Ernest O. Lawrence
Radiation Laboratory

TWO-WEEK LOAN COPY

*This is a Library Circulating Copy
which may be borrowed for two weeks.
For a personal retention copy, call
Tech. Info. Division, Ext. 5545*

HIGH-TEMPERATURE HEAT CONTENT OF HAFNIUM

Berkeley, California

DISCLAIMER

This document was prepared as an account of work sponsored by the United States Government. While this document is believed to contain correct information, neither the United States Government nor any agency thereof, nor the Regents of the University of California, nor any of their employees, makes any warranty, express or implied, or assumes any legal responsibility for the accuracy, completeness, or usefulness of any information, apparatus, product, or process disclosed, or represents that its use would not infringe privately owned rights. Reference herein to any specific commercial product, process, or service by its trade name, trademark, manufacturer, or otherwise, does not necessarily constitute or imply its endorsement, recommendation, or favoring by the United States Government or any agency thereof, or the Regents of the University of California. The views and opinions of authors expressed herein do not necessarily state or reflect those of the United States Government or any agency thereof or the Regents of the University of California.

UNIVERSITY OF CALIFORNIA

Lawrence Radiation Laboratory
Berkeley, California

Contract No. W-7405-eng-48

HIGH-TEMPERATURE HEAT CONTENT OF HAFNIUM

Donald T. Hawkins, Marc Onillon, and Raymond L. Orr

March 1963

HIGH-TEMPERATURE HEAT CONTENT OF HAFNIUM

DONALD T. HAWKINS, MARC ONILLON, AND RAYMOND L. ORR
Lawrence Radiation Laboratory and Department of Mineral Technology,
University of California, Berkeley

The difficulty of obtaining hafnium of sufficient purity has contributed to a relative lack of reported thermodynamic data for this element. Existing low temperature heat capacity data do not extend above 200°K, making necessary a considerable extrapolation in order to obtain values of the standard thermodynamic properties at 298.15°K (5). The only reported high-temperature thermal value is the single heat content measurement of Adenstedt (1) at 373°K.

Interest in hafnium as a high temperature refractory metal having a large neutron absorption cross section, plus the availability of a sample of satisfactorily pure material, made it desirable to determine the high temperature thermal properties of hafnium by means of heat content measurements. This paper reports the results of such measurements in the range between 298° and 1346°K.

EXPERIMENTAL

The hafnium used was obtained from the Lawrence Radiation Laboratory, Livermore, which also supplied the results of chemical and spectrographic analyses. The sample contained 2.8 wt. % (5.3 at. %) Zr and less than a total of 0.055 wt. % of remaining impurities, principally 0.020% Fe, 0.010% Ni, and 0.008% O.

Heat content measurements were made using a diphenyl ether

Bunsen-type drop calorimeter. The apparatus and experimental procedures have been described in detail previously (4, 8) and will be mentioned only briefly here. The specimen, consisting of 1.3703 grams of hafnium enclosed in 0.6245 grams of platinum foil, was heated in an argon atmosphere in a vertical tube furnace to a measured temperature, then dropped into the calorimeter. Heat from the specimen entered a surrounding chamber containing liquid and solid diphenyl ether at its melting point, 300.0°K, melting some of the solid isothermally. The resulting increase in volume was measured by displacement of mercury from the bottom of the calorimeter chamber into a horizontal calibrated capillary tube. The heat effect was obtained from the measured volume change using the calibration factor determined by Jessup (6) and routinely checked throughout the measurements by dropping a solid platinum specimen in the calorimeter (8). Corrections were made for the heat content of the platinum capsule, the heat lost during the drop, and the small difference between the calorimeter temperature, 300°K, and the standard reference temperature, 298.15°K.

The results were corrected for the Zr content of the sample by assuming the Kopp-Neumann rule of additive heat capacities to apply throughout the measured range. Heat contents of Zr tabulated by Kelley (7) were used to 1135°K, the α (hcp)- β (bcc) transformation temperature, above which values for α -Zr were extrapolated. Hafnium itself does not undergo the α - β transition until it reaches $2023 \pm 20^\circ\text{K}$ (3). Starting with the runs at 984°K and continuing at higher temperatures, the specimen gained small amounts of weight, presumably because of oxygen absorption. The

total increase in weight, reached at the highest temperature runs (1346°K), was 0.0036 grams, amounting to 0.26% by weight. The relative amounts of the absorbed oxygen in the surface oxide layer and in solution were not known; neither were the partial molar properties of oxygen dissolved in hafnium. Correction for the absorbed oxygen was thus based on known heat content values (7) for HfO_2 , the only stoichiometric oxide known to be formed by hafnium. After completion of the high temperature runs, two final runs (marked with asterisks in Table I) were repeated at a lower temperature, 837°K, in order to check the method of correction. The results, after correction, were in excellent agreement with the values found before oxidation had occurred.

RESULTS

The experimental results are listed in Table I and are shown plotted in terms of the function $(H_T^\circ - H_{298.15}^\circ) / (T - 298.15)$ in Figure 1 along with the single result of Adenstedt (1). The measurements are fitted within an average deviation of 0.4% by the analytical expression

$$H_T^\circ - H_{298.15}^\circ = 5.607 T + 0.911 \times 10^{-3} T^2 - 1753 ,$$

which results from the straight line shown in Figure 1. The selected curve joins smoothly in both C_p and (dC_p/dT) with the low temperature C_p data of Burk, Estermann, and Friedberg (2) as extrapolated to 298.15°K by Hultgren, Orr, Anderson, and Kelley (5).

Smoothed values of the thermal properties of hafnium corresponding

to the selected curve are tabulated in Table II. Values of the free energy function are based on $S_{298.15}^{\circ} = 10.50 \pm 0.5$ as given by Hultgren et al. (5).

ACKNOWLEDGMENTS

The sample and analyses were provided by Mr. Ray Bedford. The work was conducted with support from the U. S. Air Force Office of Scientific Research and from the U. S. Atomic Energy Commission through the Inorganic Materials Research Division of the Lawrence Radiation Laboratory.

LITERATURE CITED

- (1) Adenstedt, H.K., Trans. ASM 44, 949 (1952).
- (2) Burk, D.L., Estermann, I., Friedberg, S.A., Z. physik. Chem. (Frankfurt) 16, 183 (1958).
- (3) Deardorff, D.K., Kato, H., Trans. AIME 215, 876 (1959).
- (4) Hultgren, Ralph, Newcomb, Peter, Orr, Raymond L., Warner, Linda, Phys. Chem. Metallic Solns., Natl. Phys. Lab. Symposium No. 9, Vol. 1, Paper 1H, HMSO, London, 8 pp. (1959).
- (5) Hultgren, Ralph, Orr, Raymond L., Anderson, P.D., Kelley, Kenneth K., "Selected Values of Thermodynamic Properties of Metals and Alloys," p. 120, John Wiley and Sons, Inc., New York, 1963 (in press).
- (6) Jessup, R.S., J. Res. Nat. Bur. Standards 55, 317 (1955).
- (7) Kelley, K.K., U. S. Bur. Mines Bull. 584, 1960.
- (8) Kendall, W.B., Orr, R.L., Hultgren, R., THIS JOURNAL 7, 516 (1962).

Table I. Experimental Results

<u>T, °K</u>	<u>$H_T^\circ - H_{298.15}^\circ$ cal. /g. atom</u>	<u>T, °K</u>	<u>$H_T^\circ - H_{298.15}^\circ$ cal. /g. atom</u>
338.86	241	837.15*	3604
341.72	274	837.25*	3589
341.86	286	841.35	3572
342.15	279	841.75	3605
389.96	562	842.25	3595
392.53	597	842.45	3587
392.90	582	920.05	4188
398.28	612	920.15	4140
398.40	617	920.95	4125
486.65	1193	983.51	4637
486.65	1205	983.78	4645
486.78	1166	983.87	4639
492.71	1236	1109.70	5593
492.71	1234	1109.79	5585
576.55	1801	1109.88	5505
576.65	1781	1182.82	6164
576.75	1795	1187.07	6141
589.05	1873	1187.07	6170
687.82	2557	1187.61	6173
687.93	2524	1271.23	6827
697.26	2623	1272.07	6846
697.71	2610	1306.48	7138
697.71	2596	1306.98	7136
790.95	3257	1346.23	7448
791.65	3262	1346.48	7493

* Runs made to confirm method of correcting for oxygen absorption
(see text).

Table II. Thermal Properties of Hafnium

<u>T, °K</u>	<u>$H_T^\circ - H_{298.15}^\circ$</u> cal. /g. atom	<u>cal. /deg. g. atom</u>		
		<u>Cp</u>	<u>$S_T^\circ - S_{298.15}^\circ$</u>	<u>$\frac{F_T^\circ - H_{298.15}^\circ}{T}$</u>
298.15	0	6.15	0.00	10.50
300	11	6.15	0.04	10.50
400	640	6.34	1.83	10.74
500	1280	6.52	3.26	11.21
600	1940	6.70	4.47	11.74
700	2620	6.88	5.52	12.28
800	3320	7.06	6.45	12.80
900	4030	7.25	7.29	13.31
1000	4770	7.43	8.06	13.80
1100	5520	7.61	8.78	14.26
1200	6290	7.79	9.45	14.71
1300	7080	7.98	10.08	15.14
1350	7480	8.07	10.38	15.34

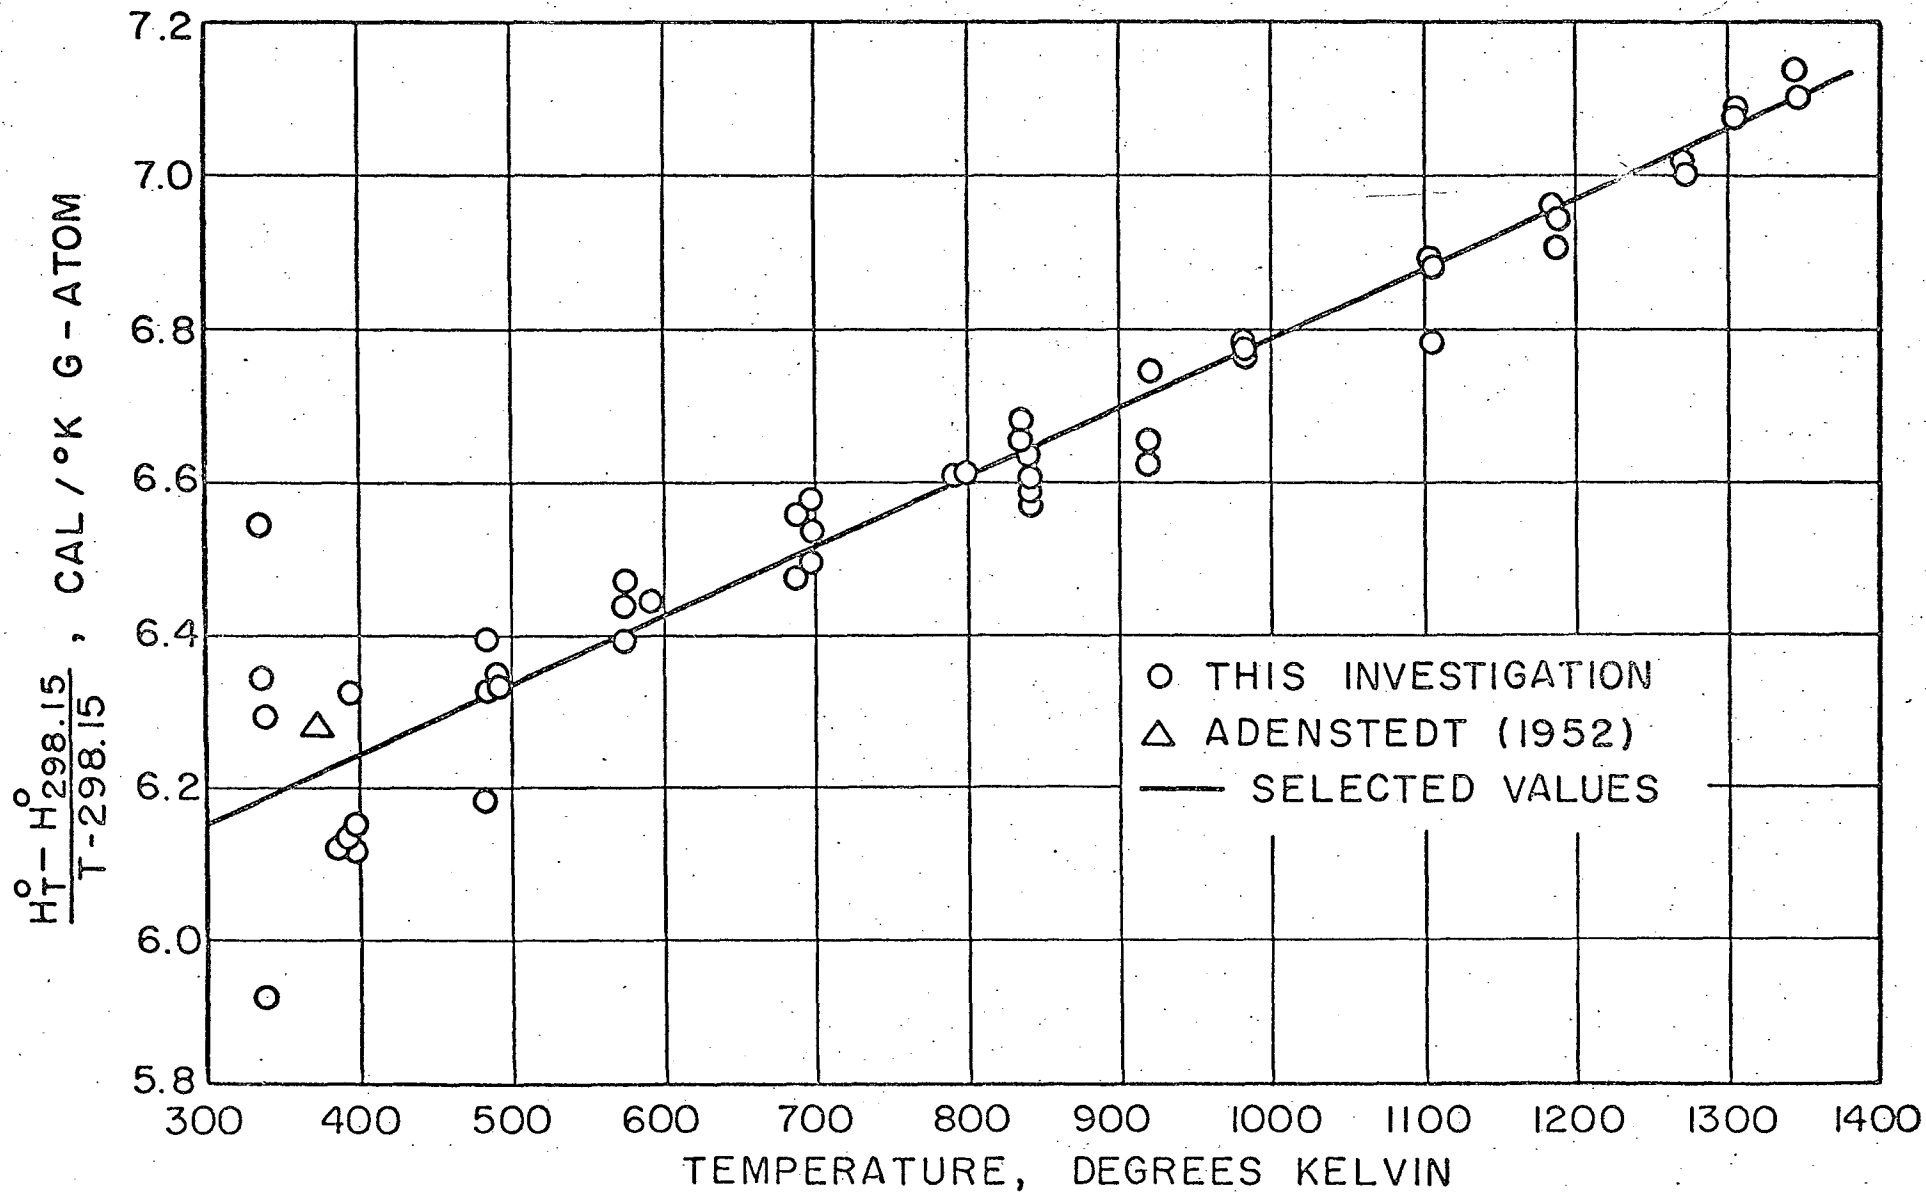


Figure 1. Heat content of hafnium expressed in terms of the function
 $\frac{(H_T^0 - H_{298.15}^0)}{(T - 298.15)}$.

