

UC Berkeley

UC Berkeley Previously Published Works

Title

Large bandgap of pressurized trilayer graphene

Permalink

<https://escholarship.org/uc/item/04c853gs>

Journal

Proceedings of the National Academy of Sciences of the United States of America,
116(19)

ISSN

0027-8424

Authors

Ke, Feng
Chen, Yabin
Yin, Ketao
et al.

Publication Date

2019-05-07

DOI

10.1073/pnas.1820890116

Peer reviewed



Large bandgap of pressurized trilayer graphene

Feng Ke^{a,1}, Yabin Chen^{b,1}, Ketao Yin^{c,1}, Jiejuan Yan^{a,d}, Hengzhong Zhang^a, Zhenxian Liu^e, John S. Tse^c, Junqiao Wu^b, Ho-kwang Mao^{a,2}, and Bin Chen^{a,2}

^aCenter for High Pressure Science and Technology Advanced Research, 201203 Shanghai, China; ^bDepartment of Materials Science and Engineering, University of California, Berkeley, CA 94720; ^cDepartment of Physics and Engineering Physics, University of Saskatchewan, Saskatoon, SK S7N 5E2, Canada; ^dAdvanced Light Source, Lawrence Berkeley National Laboratory, Berkeley, CA 94720; and ^eInstitute of Materials Science, Department of Civil and Environmental Engineering, The George Washington University, Washington, DC 20052

Contributed by Ho-kwang Mao, March 14, 2019 (sent for review December 12, 2018; reviewed by Xi Ling and Alexander V. Soldatov)

Graphene-based nanodevices have been developed rapidly and are now considered a strong contender for postsilicon electronics. However, one challenge facing graphene-based transistors is opening a sizable bandgap in graphene. The largest bandgap achieved so far is several hundred meV in bilayer graphene, but this value is still far below the threshold for practical applications. Through in situ electrical measurements, we observed a semiconducting character in compressed trilayer graphene by tuning the interlayer interaction with pressure. The optical absorption measurements demonstrate that an intrinsic bandgap of 2.5 ± 0.3 eV could be achieved in such a semiconducting state, and once opened could be preserved to a few GPa. The realization of wide bandgap in compressed trilayer graphene offers opportunities in carbon-based electronic devices.

graphene | two-dimensional materials | high pressure | electrical transport | bandgap opening

The remarkable physical properties of graphene, such as high carrier mobility, flexibility, and mechanical strength make it a wonder of materials science (1–8). For example, the very high carrier mobility of graphene of $10,000 \text{ cm}^2 \text{ V}^{-1} \text{ s}^{-1}$ has promoted potential applications in high-speed integrated electronic devices. However, unlike silicon semiconductor, the main challenge for graphene-based transistors is the gapless character of graphene (9–19) that results in an impossible on/off field-effect transition and a low $I_{\text{on}}/I_{\text{off}}$ ratio (18, 19). Considerable efforts have been made to increase the bandgap of graphene, using quantum confinement by patterning graphene in the form of a quantum dot (20), nanoribbon (21, 22), and nanomesh (23), or symmetric breaking and selective control of the carrier concentration in graphene layers by an external electric field (9–17). However, these efforts have disappointed as the maximum bandgap opening ever achieved was only several hundred meV in bilayer graphene. Promisingly, a bandgap of ~ 1 eV was recently opened in nanoporous graphene (24).

Pioneering studies indicated that the electronic structure of few-layer graphene was highly sensitive to interlayer van der Waals coupling (25–27). Breaking the inversion symmetry of Bernal-stacked bilayer graphene has been shown to open a gap and the possibility of tuning the gap energy. The electronic structure of graphene can also be modified by interlayer hybridization, as exemplified in graphene/h-BN and graphene/SiC multilayers (28–32). We pursued an alternate approach of tuning the interlayer hybridization of few-layer graphene with pressure to modulate the electronic structure. The graphene sample on a different substrate has quite different pressure response (33–36). Furthermore, the behavior of graphene on a substrate at high pressure differs drastically from that of freestanding graphene (37), indicating that substrates obscure the intrinsic properties of graphene significantly.

In our study, we directly transferred the graphene sample onto a diamond surface for measurements to avoid the influence of the substrate. However, pressurizing few-layer graphene and in situ examining the change of the electronic structure, taking the electrical measurements as an example, presents many technical difficulties from preparation of defect-free graphene flakes, the

placing of microelectrodes on a tiny piece of atomic layer sample to ensure good contacts in a diamond anvil cell, and the prevention of ultrathin samples from damage under pressure. First, we developed a microwiring technique for in situ high-pressure electrical transport measurements on nanomaterials with only a few layers. A semimetal-to-semiconductor transition was observed in compressed trilayer graphene. Systematic electrical and absorption measurements provide compelling evidence that a large intrinsic bandgap of 2.5 ± 0.3 eV was achieved in mechanically exfoliated Bernal-stacked trilayer graphene under compression.

Results and Discussion

The critical experimental step is the fabrication of probing electrodes with ohmic contact that are suitable for electrical measurements on nanomaterials at high pressure. For this purpose, we used an advanced experimental technique of patterning Ti/Au film as probing electrodes on the diamond culet with an electron beam deposition method. The electrodes were then extended with platinum foils ($\sim 2 \mu\text{m}$ in thickness) by careful hand-wiring to ensure stability under compression (Fig. 1). More experimental details on our sample preparation, transfer, and identification of the Bernal stacking order can be found in *SI Appendix*. The resistances of trilayer graphene at ~ 0.5 GPa measured by two- and four-terminal electrodes were ~ 1.1 k Ω and $\sim 300 \Omega$ (*SI Appendix*, Fig. S2), respectively. These values are comparable with previously reported results (14), indicating the good quality of the graphene sheet and contacts.

The pressure response of the Bernal-stacked trilayer graphene resistance was investigated at ambient temperature (Fig. 2A).

Significance

The remarkable physical properties of graphene make it a marvel of materials science. However, the gapless character of graphene makes it impossible to be a strong contender for postsilicon electronics. Opening a sizable bandgap in graphene is hence highly desired. We developed a microwiring technique for high-pressure electrical measurement on nanomaterials with only a few layers. Through in situ electrical and absorption studies we demonstrate that an intrinsic bandgap of 2.5 eV is achievable in compressed Bernal-stacked trilayer graphene. The realization of a wide bandgap in compressed graphene stimulates explorations for the practical application of carbon-based electronic devices.

Author contributions: F.K., H.-k.M., and B.C. designed research; F.K., Y.C., K.Y., and J.Y. performed research; F.K., Y.C., K.Y., H.Z., Z.L., J.S.T., J.W., H.-k.M., and B.C. analyzed data; and F.K., Y.C., K.Y., J.Y., H.Z., Z.L., J.S.T., J.W., H.-k.M., and B.C. wrote the paper.

Reviewers: X.L., Boston University; and A.V.S., Luleå University of Technology.

The authors declare no conflict of interest.

Published under the [PNAS license](#).

¹F.K., Y.C., and K.Y. contributed equally to this work.

²To whom correspondence may be addressed. Email: maohk@hpstar.ac.cn or chenbin@hpstar.ac.cn.

This article contains supporting information online at www.pnas.org/lookup/suppl/doi:10.1073/pnas.1820890116/-DCSupplemental.

Published online April 19, 2019.

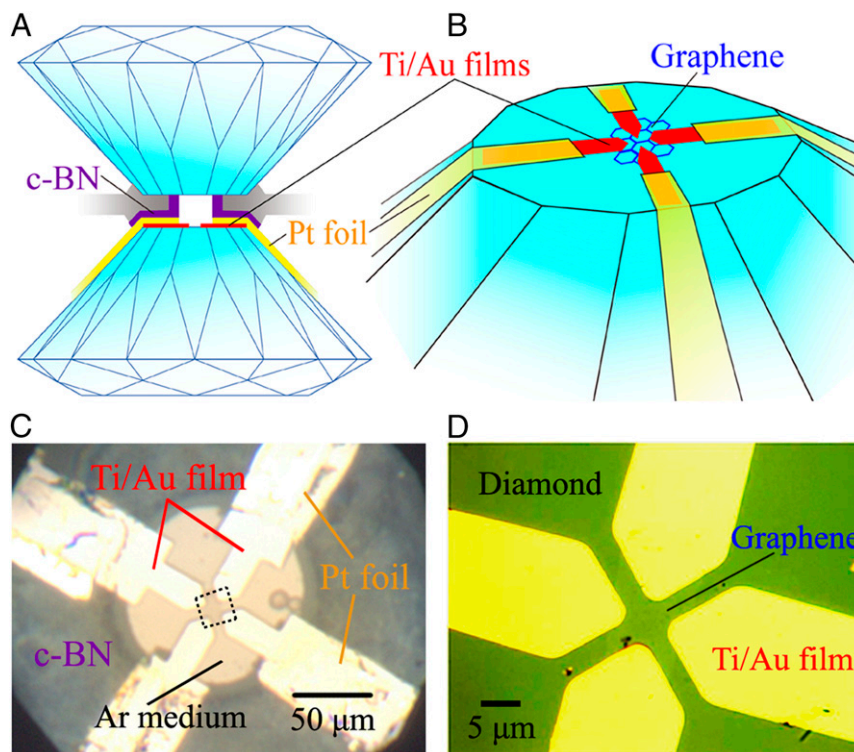


Fig. 1. Four-terminal nanodevice of trilayer graphene with Van der Pauw configuration on a diamond culet. (A) Illustration of a cross-sectional view of the designed microcircuit. (B) A perspective view of the designed microwiring setup. (C) Top view of the trilayer graphene sample and probing electrodes in a diamond anvil cell. Daphne 7373 or Argon pressure media were loaded for repeating high-pressure measurements. (D) Optical microscope image of trilayer graphene and Ti/Au film electrodes on the diamond surface.

Below 30.1 GPa, the resistance of trilayer graphene varies smoothly with pressure. A break in the trend and a sudden increase in the resistance is observed at about 33.0 GPa. The resistance increases dramatically by more than three orders of magnitudes upon further compression to 59.0 GPa. Above 59.0 GPa, the resistance jumps out

of the measurable range of the instrument. This observation is a strong indication of bandgap opening.

The sheet resistance of Bernal-stacked trilayer graphene was also investigated as a function of temperature at pressures to check the opening of bandgap (Fig. 2 B and C). At low pressures

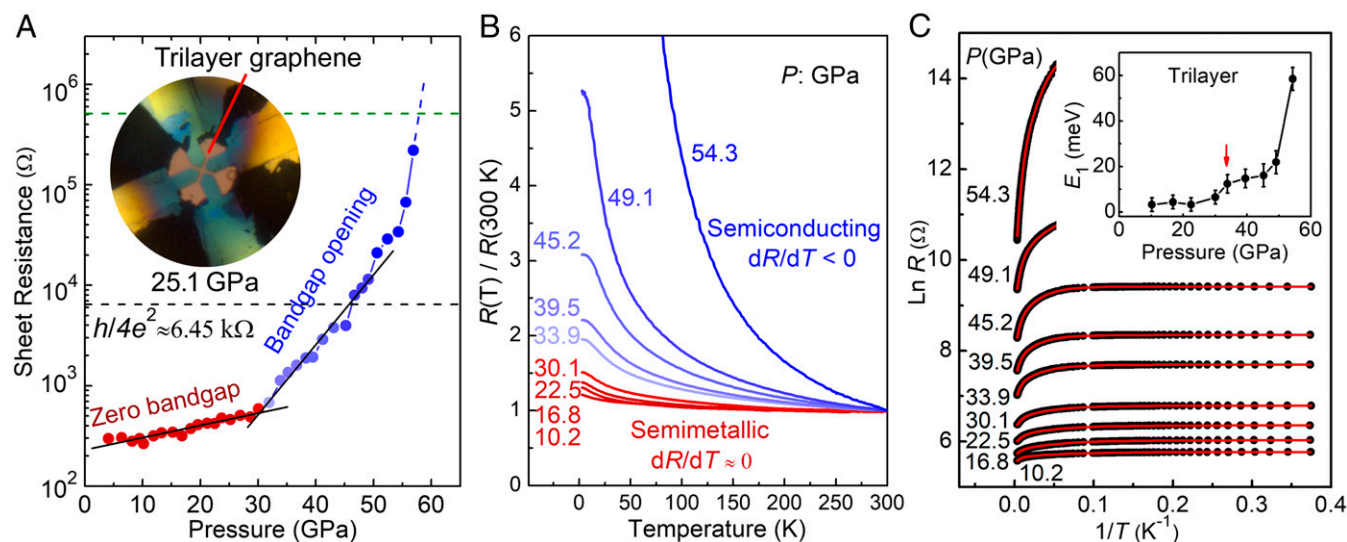


Fig. 2. Sheet resistances of trilayer graphene as functions of pressure and temperature. (A) Resistance–pressure curves of trilayer graphene measured at room temperature (300 K). The solid black lines are guides for the eyes. The black dashed line denotes the resistance quantum, $h/4e^2 \sim 6.45 \text{ k}\Omega$, above which, a disordered conductor would behave as an insulator at low temperatures due to Anderson localization. (B) R - T curves at representative pressures showing the semimetallic–semiconducting transition. (C) Arrhenius plots of the resistance. The solid red lines are fitted to Eq. 1. (Inset) The pressure dependence of the obtained activation energy E_1 is shown. The uncertainties are from the fitting errors and the selection of the critical temperature of these three transport processes.

(<30.1 GPa), the resistance (R) shows a weak temperature dependence ($dR/dT \approx 0$), indicative of a semimetallic character. Surprisingly, at 33.9 GPa, the resistance becomes strongly temperature dependent and increases significantly with decreasing temperature ($dR/dT < 0$). The temperature dependence of resistance becomes even more pronounced at higher pressure up to 54.3 GPa, exhibiting a typical semiconducting behavior.

The temperature dependence of compressed trilayer graphene resistance shows linear trend in the high-temperature range (200–300 K, *SI Appendix, Fig. S3*), suggesting Arrhenius-like thermally activated conduction. With decreasing temperature, the slope decreases continuously, suggesting another thermally activated conduction process. Below 30 K, the $\ln R$ vs. $1/T$ curves become nearly T -independent, which indicates an alternative conduction mechanism, such as various-range hopping. Such a conduction process was also observed in gapped bilayer graphene (38, 39). Assuming the variable range hopping to be of Mott type, the low-temperature resistance should be proportional to $\exp[-(T_0/T)^{1/3}]$. Hence, we fitted the R - T curves with the following equation (38):

$$R(T)^{-1} = R_1^{-1} \exp[-E_1/2k_B T] + R_2^{-1} \exp[-E_2/2k_B T] + R_3^{-1} \exp[-(T_3/T)^{1/3}], \quad [1]$$

where E_1 , E_2 , T_3 , R_1 , R_2 , and R_3 are the two activation energies, hopping energy, and related resistance coefficients, respectively. Our fitted results match the R - T curves well in the whole temperature range (Fig. 2C). The extracted activation energy E_1 varies smoothly with pressure up to 30.1 GPa, followed by a sharp increase above 33.9 GPa (Fig. 2C, *Inset*), consistent with the onset pressure of the R - P curve.

The gap opening of compressed Bernal-stacked trilayer graphene was further confirmed with infrared-visible-UV (IR-vis-UV) absorption experiments. At ambient conditions (*SI Appendix, Fig. S4*), a pronounced and asymmetric peak due to excitonic resonance at the photon energy of 4.6 eV is observed in the absorbance pattern of trilayer graphene, similar to that previously reported in mono- and few-layer graphene (40, 41). The transmittance of $(95.5 \pm 0.5)\%$ at 1.5 eV is comparable

with that of suspended trilayer graphene (40, 41). All measurements confirm that the absorption is associated with the intrinsic properties of trilayer graphene.

Pressurized Bernal-stacked trilayer graphene was studied with laboratory and synchrotron IR absorption spectroscopy (photon energy range: 0.2 ~ 1.0 eV, Fig. 3 and *SI Appendix, Fig. S5*). The absorbance of trilayer graphene [$A = -\log(T_s)$, where T_s is the transmittance of sample] varies smoothly with the loading pressure until 26.1 GPa, when it drops suddenly and approaches zero at higher pressure. This observation indicates that the bandgap of compressed trilayer graphene has been opened and is larger than 1.0 eV, the maximum photon energy of IR radiation used in the measurements.

The bandgap energy of pressurized trilayer graphene cannot be accurately determined from the above IR experiments. Therefore, to track the bandgap evolution precisely, we measured the vis-UV transmittance spectra in trilayer graphene under pressure within the energy range of 1.4 ~ 4.9 eV (Fig. 4B). Below 28.3 GPa, the absorption spectra show no significant change with compression. The main feature is a small blue-shift of the excitonic resonance peak at about 4.6 eV with increasing pressure. At 28.3 GPa, a transition is clearly identified from the absorbance measured with radiation energy of 1.5 eV. As shown in Fig. 4D, the absorbance of trilayer graphene varies smoothly initially up to 25.9 GPa. A sudden drop in the absorbance is observed at 28.3 GPa, followed by a continuous reduction with further compression up to 51.5 GPa. The absorption result suggests that the bandgap is larger than 1.5 eV. The result also agrees well with the optical microscopy observation under white transmitted light where the trilayer graphene becomes increasingly transparent above 28.3 GPa (Fig. 4A). All of the evidence confirms the large intrinsic bandgap in pressurized trilayer graphene. The experimental results suggest that a broad pressure range is needed to make the semimetallic trilayer transform to the semiconducting state completely, i.e., the ratio of semimetallic/semiconducting states is pressure dependent. Such a mixed phase is also observed in compressed substrate-supported two-layer graphene (33, 34). During decompression, the semiconducting phase remains unchanged down to a few GPa, but almost returns to its original state when quenched to ambient pressure, as shown

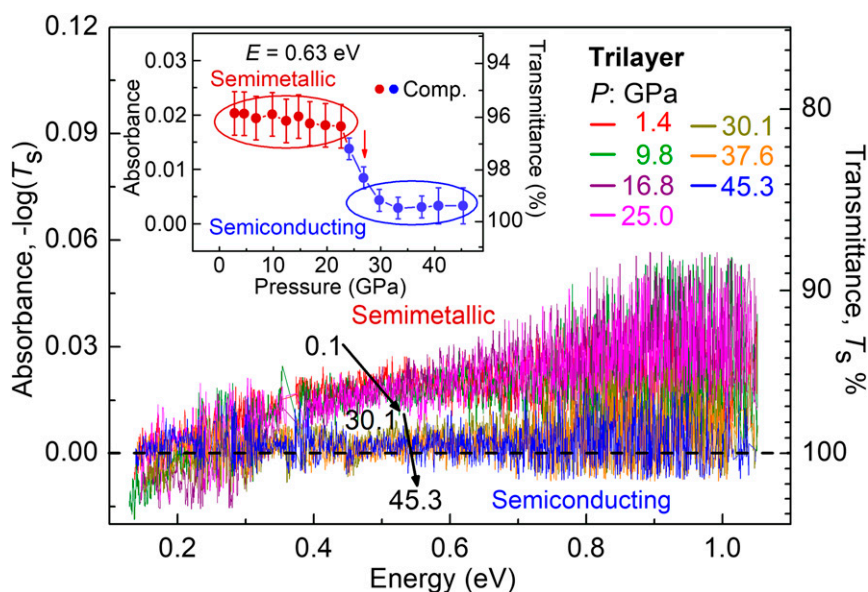


Fig. 3. IR results of trilayer graphene under compression showing the bandgap opening. (*Inset*) The pressure dependence of trilayer graphene absorbance at radiation energy of 0.63 eV. The absorbance data at around 0.33 eV are removed due to the influence of C–H bonding absorption in the Daphne 7373 pressure medium.

10 GPa, far from the semimetallic–semiconducting transition pressure of 33.9 GPa. Hence, we believe strain/stress induced by the quasi-hydrostatic conditions may affect the onset pressure of the semimetallic–semiconducting transition but does not play a key role in opening of such a large bandgap in trilayer graphene.

Recently, a diamond-like carbon film was observed in two-layer graphene followed by sp^2 - sp^3 rehybridization through nanoindentation and compression methods (33, 34). Previous experimental and theoretical results also demonstrated that graphite transformed into an sp^3 -bonded carbon phase (48–56) under cold compression, although the structure of the high-pressure phase is still controversial. In addition, the value of the bandgap opened in trilayer graphene is comparable with that of the high-pressure transparent phase of graphite (*SI Appendix, Fig. S8*). Hence, we infer that the opening of the bandgap is caused by sp^2 - sp^3 rehybridization in pressurized trilayer graphene. Further study is needed to understand the structural evolution of trilayer graphene under compression.

In conclusion, through electrical, IR and vis-UV absorption measurements, we observed an intrinsic bandgap of 2.5 ± 0.3 eV in pressurized Bernal-stacked trilayer graphene by tuning the interlayer coupling with pressure. The high-pressure semiconducting phase could be preserved to a few GPa. The achieved bandgap of

2.5 ± 0.3 eV is much larger than previously reported values of several hundred meV. The bandgap of compressed trilayer graphene is larger than silicon (1.1 eV) under ambient conditions. However, the reverse engineering of fabricating a narrower gap graphene sheet is, in principle, comparatively easier. This study may stimulate explorations of practical graphene-based electronic devices.

Materials and Methods

Trilayer graphene flakes were mechanically exfoliated from bulk graphite on Si/SiO_2 surface. In situ high-pressure electrical measurements were conducted in a PPMS-9 system with a temperature range of 2–300 K. High-pressure IR absorption measurements were conducted at Beamline 1.4.3 of the Advanced Light Source, Lawrence Berkeley National Laboratory and the Infrared Lab of National Synchrotron Light Source II at Brookhaven National Laboratory. Vis-UV absorption measurements were conducted on a customized Vis-UV microscope system with a photon energy of 1.4–4.9 eV. More details about the experiments and calculations can be found in *SI Appendix*.

ACKNOWLEDGMENTS. We thank Dr. Hongwei Sheng, Dr. Xiao-Jia Chen, and Dr. Lin Wang for their helpful discussion and technical support. The authors acknowledge the funding support of National Science Associated Funding (Grant U1530402). The device fabrication partly done in Berkeley was supported by the US NSF Grant DMR-1708448.

- Novoselov KS, et al. (2004) Electric field effect in atomically thin carbon films. *Science* 306:666–669.
- Schwierz F (2010) Graphene transistors. *Nat Nanotechnol* 5:487–496.
- Novoselov KS, et al. (2005) Two-dimensional gas of massless Dirac fermions in graphene. *Nature* 438:197–200.
- Novoselov KS, et al. (2012) A roadmap for graphene. *Nature* 490:192–200.
- Zhang Y, Tan Y-W, Stormer HL, Kim P (2005) Experimental observation of the quantum Hall effect and Berry's phase in graphene. *Nature* 438:201–204.
- Novoselov KS, et al. (2006) Unconventional quantum Hall effect and Berry's phase of 2π in bilayer graphene. *Nat Phys* 2:177–180.
- McCann E, Fal'ko VI (2006) Landau-level degeneracy and quantum Hall effect in a graphite bilayer. *Phys Rev Lett* 96:086805.
- Geim AK, Novoselov KS (2007) The rise of graphene. *Nat Mater* 6:183–191.
- Zhang Y, et al. (2009) Direct observation of a widely tunable bandgap in bilayer graphene. *Nature* 459:820–823.
- Mak KF, Lui CH, Shan J, Heinz TF (2009) Observation of an electric-field-induced band gap in bilayer graphene by infrared spectroscopy. *Phys Rev Lett* 102:256405.
- Han MY, Özyilmaz B, Zhang Y, Kim P (2007) Energy band-gap engineering of graphene nanoribbons. *Phys Rev Lett* 98:206805.
- Castro EV, et al. (2007) Biased bilayer graphene: Semiconductor with a gap tunable by the electric field effect. *Phys Rev Lett* 99:216802.
- Oostinga JB, Heersche HB, Liu X, Morpurgo AF, Vandersypen LMK (2008) Gate-induced insulating state in bilayer graphene devices. *Nat Mater* 7:151–157.
- Taychatanapat T, Jarillo-Herrero P (2010) Electronic transport in dual-gated bilayer graphene at large displacement fields. *Phys Rev Lett* 105:166601.
- Ohta T, Bostwick A, Seyller T, Horn K, Rotenberg E (2006) Controlling the electronic structure of bilayer graphene. *Science* 313:951–954.
- Wang F, et al. (2008) Gate-variable optical transitions in graphene. *Science* 320:206–209.
- Li ZQ, et al. (2009) Band structure asymmetry of bilayer graphene revealed by infrared spectroscopy. *Phys Rev Lett* 102:037403.
- Hunt B, et al. (2013) Massive Dirac fermions and Hofstadter butterfly in a van der Waals heterostructure. *Science* 340:1427–1430.
- Li X, Wang X, Zhang L, Lee S, Dai H (2008) Chemically derived, ultrasmooth graphene nanoribbon semiconductors. *Science* 319:1229–1232.
- Ponomarenko LA, et al. (2008) Chaotic Dirac billiard in graphene quantum dots. *Science* 320:356–358.
- Wang X, Dai H (2010) Etching and narrowing of graphene from the edges. *Nat Chem* 2:661–665.
- Wang X, et al. (2008) Room-temperature all-semiconducting sub-10-nm graphene nanoribbon field-effect transistors. *Phys Rev Lett* 100:206803.
- Bai J, Zhong X, Jiang S, Huang Y, Duan X (2010) Graphene nanomesh. *Nat Nanotechnol* 5:190–194.
- Moreno C, et al. (2018) Bottom-up synthesis of multifunctional nanoporous graphene. *Science* 360:199–203.
- Ohta T, et al. (2007) Interlayer interaction and electronic screening in multilayer graphene investigated with angle-resolved photoemission spectroscopy. *Phys Rev Lett* 98:206802.
- Park C, et al. (2015) Electronic properties of bilayer graphene strongly coupled to interlayer stacking and an external electric field. *Phys Rev Lett* 115:015502.
- Guo Y, Guo W, Chen C (2008) Tuning field-induced energy gap of bilayer graphene via interlayer spacing. *Appl Phys Lett* 92:243101.
- Ramasubramanian A, Naveh D, Towle E (2011) Tunable band gaps in bilayer graphene-BN heterostructures. *Nano Lett* 11:1070–1075.
- Varchon F, et al. (2007) Electronic structure of epitaxial graphene layers on SiC: Effect of the substrate. *Phys Rev Lett* 99:126805.
- Zhou SY, et al. (2007) Substrate-induced bandgap opening in epitaxial graphene. *Nat Mater* 6:770–775.
- Woods CR, et al. (2014) Commensurate-incommensurate transition in graphene on hexagonal boron nitride. *Nat Phys* 10:451–456.
- Hao Y, et al. (2016) Oxygen-activated growth and bandgap tunability of large single-crystal bilayer graphene. *Nat Nanotechnol* 11:426–431.
- Martins LGP, et al. (2017) Raman evidence for pressure-induced formation of diamondene. *Nat Commun* 8:96.
- Gao Y, et al. (2018) Ultrahard carbon film from epitaxial two-layer graphene. *Nat Nanotechnol* 13:133–138.
- Nicolle J, Machon D, Poncharal P, Pierre-Louis O, San-Miguel A (2011) Pressure-mediated doping in graphene. *Nano Lett* 11:3564–3568.
- Machon D, et al. (2018) Raman scattering studies of graphene under high pressure. *J Raman Spectrosc* 49:121–129.
- Soldatov AV, You S, Mases M, Novoselov KS (2012) Freestanding graphene monolayer at high hydrostatic pressure. *Graphene 2012, Abstract Book of the Conference* (Graphene 2012, Brussels), p 172.
- Zou K, Zhu J (2010) Transport in gapped bilayer graphene: The role of potential fluctuations. *Phys Rev B Condens Matter Phys* 82:081407.
- Cao Y, et al. (2016) Superlattice-induced insulating states and valley-protected orbits in twisted bilayer graphene. *Phys Rev Lett* 117:116804.
- Nair RR, et al. (2008) Fine structure constant defines visual transparency of graphene. *Science* 320:1308.
- Mak KF, Shan J, Heinz TF (2011) Seeing many-body effects in single- and few-layer graphene: Observation of two-dimensional saddle-point excitons. *Phys Rev Lett* 106:046401.
- Tauc J, Grigorovici R, Vancu A (1966) Optical properties and electronic structure of amorphous germanium. *Phys Status Solidi* 15:627–637.
- Kawazoe H, et al. (1997) P-type electrical conduction in transparent thin films of CuAlO_2 . *Nature* 389:939–942.
- Kuriyama K, Katoh T (1988) Optical band gap of the filled tetrahedral semiconductor LiZnP . *Phys Rev B Condens Matter* 37:7140–7142.
- Ponomarenko LA, et al. (2011) Tunable metal-insulator transition in double-layer graphene heterostructures. *Nat Phys* 7:958–961.
- Ni ZH, et al. (2008) Uniaxial strain on graphene: Raman spectroscopy study and band-gap opening. *ACS Nano* 2:2301–2305.
- Monteverde U, et al. (2015) Under pressure: Control of strain, phonons and bandgap opening in rippled graphene. *Carbon* 91:266–274.
- Utsumi W, Yagi T (1991) Light-transparent phase formed by room-temperature compression of graphite. *Science* 252:1542–1544.
- Wang Y, Panzik JE, Kiefer B, Lee KKM (2012) Crystal structure of graphite under room-temperature compression and decompression. *Sci Rep* 2:520.
- Patterson JR, Kudryavtsev A, Vohra YK (2002) X-ray diffraction and nanoindentation studies of nanocrystalline graphite at high pressures. *Appl Phys Lett* 81:2073–2075.
- Yagi T, Utsumi W, Yamakata Ma, Kikegawa T, Shimomura O (1992) High-pressure in situ x-ray-diffraction study of the phase transformation from graphite to hexagonal diamond at room temperature. *Phys Rev B Condens Matter* 46:6031–6039.
- Li Q, et al. (2009) Superhard monoclinic polymorph of carbon. *Phys Rev Lett* 102:175506.
- He C, et al. (2012) New superhard carbon phases between graphite and diamond. *Solid State Commun* 152:1560–1563.
- Niu H, et al. (2012) Families of superhard crystalline carbon allotropes constructed via cold compression of graphite and nanotubes. *Phys Rev Lett* 108:135501.
- Wang JT, Chen C, Kawazoe Y (2011) Low-temperature phase transformation from graphite to sp^3 orthorhombic carbon. *Phys Rev Lett* 106:075501.
- Amsler M, et al. (2012) Crystal structure of cold compressed graphite. *Phys Rev Lett* 108:065501.