



# Lawrence Berkeley Laboratory

UNIVERSITY OF CALIFORNIA

RECEIVED  
LAWRENCE  
BERKELEY LABORATORY

## Materials & Molecular Research Division

MAR 5 1981

LIBRARY AND  
DOCUMENTS SECTION

Submitted to the Journal of Low Temperature Physics


THERMOELECTRIC GENERATION OF CHARGE IMBALANCE AT  
A SUPERCONDUCTOR-NORMAL METAL INTERFACE

D.J. Van Harlingen

January 1981

**TWO-WEEK LOAN COPY**

*This is a Library Circulating Copy  
which may be borrowed for two weeks.  
For a personal retention copy, call  
Tech. Info. Division, Ext. 6782.*

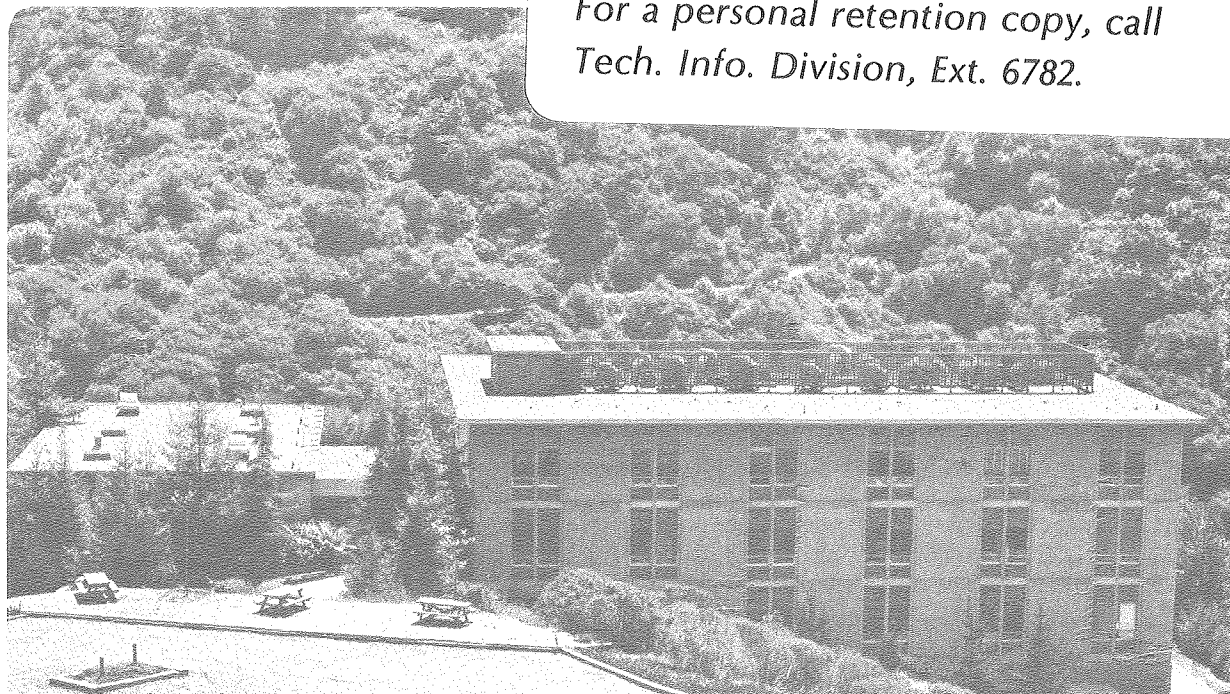

*LBL-12029  
ca*

## DISCLAIMER

This document was prepared as an account of work sponsored by the United States Government. While this document is believed to contain correct information, neither the United States Government nor any agency thereof, nor the Regents of the University of California, nor any of their employees, makes any warranty, express or implied, or assumes any legal responsibility for the accuracy, completeness, or usefulness of any information, apparatus, product, or process disclosed, or represents that its use would not infringe privately owned rights. Reference herein to any specific commercial product, process, or service by its trade name, trademark, manufacturer, or otherwise, does not necessarily constitute or imply its endorsement, recommendation, or favoring by the United States Government or any agency thereof, or the Regents of the University of California. The views and opinions of authors expressed herein do not necessarily state or reflect those of the United States Government or any agency thereof or the Regents of the University of California.

THERMOELECTRIC GENERATION OF CHARGE IMBALANCE  
AT A SUPERCONDUCTOR-NORMAL METAL INTERFACE

D. J. Van Harlingen

Department of Physics, University of California, and  
Materials and Molecular Research Division, Lawrence  
Berkeley Laboratory, Berkeley, California 94720

The thermoelectric voltage produced across a superconductor-normal metal-superconductor (SNS) sandwich by an applied heat current has been measured in Pb-Cu-PbBi and In-Al-Sn as a function of temperature. The observed divergence of the thermoelectric voltage near  $T_c$  is attributed to a charge imbalance region decaying into the superconductor from the NS interface over the quasiparticle diffusion length  $\lambda_{Q^*}$ . The charge imbalance is generated by thermoelectrically driven quasiparticle currents in the superconductor. It contributes a voltage per unit heat power given by  $V_S/P = \lambda_{Q^*} S/\kappa A$ , where  $A$  is the sample cross-sectional area, and  $S$  and  $\kappa$  are the thermopower and the thermal conductivity of quasiparticles in the superconductor. For Pb and In, we find the measured thermopower in the superconducting state to be slowly-varying with temperature near  $T_c$  and consistent in magnitude with normal state values. This result is in agreement with theoretical predictions of thermoelectric effects in superconductors but contrary to previous experimental results obtained by other methods.

## I. INTRODUCTION

The idea that the quasiparticles in a superconductor are driven by a temperature gradient, first proposed by Ginzburg<sup>1</sup>, has been widely discussed recently<sup>2-4</sup> and is generally accepted. However, experimental investigations of the thermoelectric effect have yielded conflicting results. Theoretically, it is predicted that the thermoelectric coefficient  $L_T$  describing the quasiparticle current  $\vec{J}_n = L_T(-\vec{\nabla}T)$  should be continuous with the value of  $L_T$  in the normal state at  $T=T_c$  and roll-off smoothly to zero as  $T$  decreases. Instead, measurements of the thermoelectrically-generated magnetic flux in bimetallic superconducting rings<sup>4-6</sup> have suggested that  $L_T$  diverges weakly at  $T_c$  as  $(T_c-T)^{-1/2}$ , becoming several orders of magnitude larger than the normal state coefficient. On the other hand, investigations of the polarity asymmetry of the critical current in clean superconducting point contacts with a temperature gradient<sup>3,7</sup> have observed no thermoelectric current at all.

In this paper, we report the observation of a thermoelectric voltage in excess of the contribution from the normal metal region in superconductor-normal-superconductor (SNS) sandwiches with an applied uniform heat current. We attribute the excess voltage to a charge imbalance region generated by thermoelectric currents in the superconductors. Measurement of the temperature dependence of the excess voltage enables a determination of the thermoelectric coefficient  $L_T$  in the superconducting state near the transition temperature. For superconducting Pb and In, we find  $L_T$  to be slowly-varying and consistent with expected normal state values at  $T_c$ , in agreement with theories of thermoelectricity in superconductors<sup>8</sup>.

## II. THEORETICAL DESCRIPTION

We begin by describing the mechanism for the generation of charge imbalance at an NS interface by thermoelectric currents, first suggested by Artemenko and Volkov<sup>9</sup>. A charge imbalance exists in a superconductor whenever the quasiparticle distribution  $f_k$  is perturbed from equilibrium in such a way that the net charge per unit volume of the quasiparticles,  $Q^*$  is non-zero. In order to conserve total electronic charge, the condensate charge must then compensate by a shift of the pair chemical potential  $\mu_s$  from its equilibrium value. As discussed by Waldram<sup>10</sup>, Pethick and Smith<sup>11</sup>, and others, the difference in chemical potentials may be related to  $Q^*$  by

$$Q^* \equiv \sum_k q_k f_k = -2N(0)e(\mu_s - \mu_n), \quad (1)$$

where  $N(0)$  is the single spin electronic density of states and  $q_k$  is the charge of the quasiparticle in the state  $\vec{k}$ . In our notation,  $q_k$  varies from an electron charge  $e$  for  $k \gg k_F$  to a hole charge  $-e$  for  $k \ll k_F$ , where  $k_F$  is the Fermi wavevector. The quantity  $\mu_n$  in Eq. (1) is the quasiparticle chemical potential, which depends only on the number of electrons and the temperature; it should not be confused with the effective potential  $\mu_n$  of Pethick and Smith<sup>11</sup> used to model the non-equilibrium quasiparticle distribution.

Like the conduction electrons in a normal metal, the quasiparticles in a superconductor respond to external fields according to the transport equation

$$\vec{J}_n = \frac{\sigma}{e} (-\vec{\nabla}\phi_n) + L_T(-\vec{\nabla}T), \quad (2)$$

where  $\sigma$  is the electrical conductivity and  $\phi_n$  the electrochemical potential of the quasiparticles. The electrical driving force on the quasiparticles  $(-\vec{\nabla}\phi_n) = e\vec{E} - \vec{\nabla}\mu_n$  depends on the electric field  $\vec{E}$  and the quasiparticle chemical potential  $\mu_n$ . On the other hand, in order that the supercurrent is not accelerated, the London equations require that the electrical driving force on the pairs vanish in steady-state so that  $(-\vec{\nabla}\phi_s) = e\vec{E} - \vec{\nabla}\mu_s = 0$ , where  $\phi_s$  is the pair electrochemical potential. Thus, we may also write Eq. (2) in the form

$$\vec{J}_n = \frac{\sigma}{e} \vec{\nabla}(\mu_s - \mu_n) + L_T(-\vec{\nabla}T) = \frac{\sigma}{2N(0)e^2} (-\vec{\nabla}Q^*) + L_T(-\vec{\nabla}T). \quad (3)$$

We see that a charge imbalance gradient, as well as a temperature gradient, drives a quasiparticle current in a superconductor. In a configuration for which  $\vec{\nabla} \times \vec{J}_n = 0$ , the Meissner effect exists in a superconductor even in a non-equilibrium state<sup>4</sup>. The normal current  $\vec{J}_n$  is then locally cancelled by a counterflow of supercurrent  $\vec{J}_s = -\vec{J}_n$  in order to exclude the magnetic field except within a penetration depth of the surface.

The steady-state charge imbalance is determined from the Boltzmann equation by requiring

$$\frac{dQ^*}{dt} = -\vec{\nabla} \cdot \vec{J}_n - \frac{Q^*}{\tau_{Q^*}} = 0. \quad (4)$$

Charge imbalance is created at the rate  $\vec{\nabla} \cdot \vec{J}_n$  and decays with the characteristic relaxation time  $\tau_{Q^*}$ . Combining Eqs.(3) and (4), we obtain differential equations for  $J_n$  and  $Q^*$ :

$$\vec{J}_n - (\lambda_{Q^*})^2 \vec{\nabla}(\vec{\nabla} \cdot \vec{J}_n) = L_T(-\vec{\nabla}T), \quad (5)$$

$$Q^* - (\lambda_{Q^*})^2 \nabla^2 Q^* = \tau_{Q^*} L_T \nabla^2 T. \quad (6)$$

Here  $\lambda_{Q^*}$  is the usual quasiparticle diffusion length characterizing the spatial decay of charge imbalance given by

$$\lambda_{Q^*} = \left( \frac{\sigma \tau Q^*}{2N(0)e^2} \right)^{1/2} = \left( \frac{1}{3} v_F \ell \tau Q^* \right)^{1/2}, \quad (7)$$

where  $\ell$  is the mean free path and  $v_F$  is the Fermi velocity.

We consider a perfect normal metal-superconductor (NS) interface with an applied uniform heat current density  $\vec{U} = U\hat{x}$ , as shown in Fig. 1(a). We assume that the superconductor is near its transition temperature  $T_c$  so that the dominant heat flow is by quasiparticle conduction; the temperature gradients in N and S are then each uniform (although not necessarily equal). In the normal metal, under open circuit conditions a uniform electrochemical potential gradient  $(-\vec{\nabla}\phi) = eS_N(\vec{\nabla}T)_N$  is established preventing any electric current flow. This is the usual thermoelectric voltage which depends on the normal metal thermopower  $S_N \equiv (L_T)_N/\sigma_N$ , and the temperature gradient  $(\vec{\nabla}T)_N$  in N. The currents and fields in the superconductor are obtained by solving Eqs. (5) and (6) in one-dimension, requiring  $\vec{J}_n = \vec{J}_s = 0$  at the interface ( $x=0$ ) and noting that in this case  $\nabla^2 T = 0$ . We find

$$\vec{J}_n(x) = L_T(-\vec{\nabla}T) (1 - e^{-x/\lambda_{Q^*}}), \quad (8)$$

$$Q^*(x) = 2N(0)e^2 \lambda_{Q^*} S \nabla T e^{-x/\lambda_{Q^*}}, \quad (9)$$

where  $S = L_T/\sigma$  is the corresponding thermopower of the superconductor. The quasiparticle current, plotted in Fig. 1(b), has the value  $L_T(-\vec{\nabla}T)$  well inside the superconductor and falls to zero at the interface over the length  $\lambda_{Q^*}$ . The current reduction is caused by the build-up of charge imbalance near the interface, decaying exponentially into the superconductor with the same length  $\lambda_{Q^*}$  as shown in Fig. 1(c). It should be emphasized again

that the quasiparticle current is accompanied by an equal and opposite supercurrent so that the net current is zero everywhere.

A charge imbalance proportional to  $\vec{\nabla}T$  is thus generated near an NS interface by thermoelectric currents when heat flows into the superconductor. By symmetry, heat extraction creates an imbalance of the opposite sign. We should note that the interaction of the superfluid counterflow with the temperature gradient also produces a uniform charge imbalance in the superconductor proportional to  $(\nabla T)^2$ , as discussed by Sacks<sup>12</sup>, Entin-Wohlman and Orbach<sup>13</sup>, and looked for by Falco<sup>14</sup>. Because of coupling between charge and energy modes, the charge imbalance created by this mechanism scales with the elastic scattering time  $\tau_{imp}$  rather than with the charge imbalance relaxation time  $\tau_{Q^*} \gg \tau_{imp}$  of Eq. (4), and hence is much smaller than the effect considered here. As is clear from Eq. (6), a non-uniform temperature gradient ( $\nabla^2 T \neq 0$ ) can also create an additional  $Q^*$ , an effect which has been commented on by Tinkham<sup>15</sup>. In particular, at the interface of a superconductor and an insulator (or another superconductor far below its transition temperature), heat enters the superconductor as phonons and is transferred to the quasiparticle distribution over a phonon diffusion length,  $\lambda_{ph}$ . For  $x \lesssim \lambda_{ph}$ ,  $\nabla^2 T \neq 0$  and the expressions for  $\vec{J}_n$  and  $Q^*$  are modified slightly from those derived for the NS interface. Since  $\lambda_{ph} \ll \lambda_{Q^*}$ , the difference is negligible unless heat is deliberately injected or extracted along the length of the superconductor.

Previous investigations of thermoelectric effects in superconductors have relied on discriminating between the counterbalancing normal and superfluid components of the current in the bulk of a superconductor. In this experiment, we detect the charge imbalance thermoelectrically generated



near an NS interface. Consider a normal metal sample sandwiched between two superconductors, S and S', as illustrated in Fig. 2. We assume that  $T \lesssim T_{cS} \ll T_{cS'}$ , so that we may ignore any non-equilibrium effects at the NS' interface.

We plot the spatial variations of the electrochemical potentials in the presence of an applied heat current density U. In the normal region, the potential varies linearly due to the uniform thermoelectric field. In S', far below its transition temperature,  $\phi_n = \phi_s$  is constant. However, in S, from Eq. (9),  $\phi_n = Q^*/2N(0)e$  decays exponentially from the NS interface with characteristic length  $\lambda_{Q^*}$  while  $\phi_s$  drops to zero within a coherence length of the interface. The difference in potentials results from the charge imbalance in S.

The voltage across the SNS' sandwich is the sum of the thermoelectric voltage of the normal region

$$V_N = L_N S_N (\nabla T)_N, \quad (10)$$

where  $L_N$  is the thickness, and a contribution from the charge imbalance region in the superconductor given by Eq. (9):

$$V_S = \frac{Q^*(0)}{2N(0)e} = \lambda_{Q^*} S \nabla T. \quad (11)$$

Since the total heat flow P through the sample is uniform, we may write the voltage in the additive form

$$V = \left[ \left( \frac{L_N}{A} \right) \frac{S_N}{\kappa_N} + \left( \frac{\lambda_{Q^*}}{A} \right) \frac{S}{\kappa} \right] P, \quad (12)$$

where A is the cross-sectional area and  $\kappa_N = P/A(\nabla T)_N$  and  $\kappa = P/A\nabla T$  are the thermal conductivities of N and S respectively. The effect of the charge imbalance is to add to the thermoelectric voltage an amount equivalent to a length  $\lambda_{Q^*}$  of a normal metal characterized by the coefficients S and  $\kappa$ .

In the absence of pair-breaking mechanisms, the charge imbalance relaxation time near  $T_c$  is given by <sup>11,16</sup>

$$\tau_{Q^*} = \left( \frac{4k_B T_c}{\pi \Delta} \right) \tau_E = \left( \frac{0.73k_B T_c}{\Delta(0)} \right) \tau_E (1-t)^{-1/2}, \quad (13)$$

where  $\tau_E$  is the inelastic electron-phonon scattering time at the Fermi level for  $T=T_c$ . The second form is obtained by assuming a BCS superconductor for which  $\Delta(t) \sim 1.74\Delta(0)(1-t)^{1/2}$ . Thus, according to Eq. (7),  $\lambda_{Q^*}$  diverges weakly as  $(1-t)^{-1/2}$  near  $T_c$ . This divergence provides a signature for separating out the thermoelectric charge imbalance contribution from the total measured thermoelectric voltage, allowing determination of the transport coefficients in the superconducting state.

It is interesting to compare Eq. (12) with the expression for the voltage generated in the SNS' sandwich by an applied electric current  $I$ , derived and experimentally verified by Hsiang and Clarke<sup>17</sup>

$$V = \left[ \left( \frac{L_N}{A} \right) \rho_N + \left( \frac{\lambda_{Q^*}}{A} \right) \rho \right] Z(t) I. \quad (14)$$

Here  $\rho_N$  and  $\rho$  are the electrical resistivities of the normal metal and of the quasiparticles in the superconductor respectively, and  $Z(t)$  is a universal function of reduced temperature equal to unity at  $t=1$  and falling off rapidly as  $t$  decreases.<sup>18</sup> Charge flow across the NS interface produces a charge imbalance that decays as in Fig. 1(c) and adds resistance equivalent to a section of length  $\lambda_{Q^*}$  of the superconductor being normal. The factor  $Z(t)$  expresses the fraction of the total current  $I$  that enters S as quasiparticle current, the rest entering as supercurrent via Andreev reflection processes<sup>10,19</sup> at the NS interface. In the case considered here of an applied heat current, the excess quasiparticle charge responsible for the charge imbalance is

injected into the region near the NS interface by the thermoelectric currents inside the superconductor rather than by any charge flow across the interface. Ignoring variations of the energy gap of the superconductor with temperature, there is no energy threshold for quasiparticle injection as in Andreev reflection, and the factor  $Z(t)$  is absent in the thermoelectric voltage, Eq. (12).

### III. EXPERIMENTAL RESULTS

We have measured the thermoelectric voltage across SNS' sandwiches composed of Pb-Cu-PbBi and In-Al-Sn. The component metals are selected to have low mutual solubilities so that sharp NS interfaces are formed instead of broad intermetallic alloy regions. Two different superconductors are used in each sandwich, with  $T_{CS} < T_{CS}'$ , so that the divergent contribution of only the NS interface to the thermoelectric voltage will be detected. This enables determination of the thermoelectric coefficient of the S components, Pb and In.

The samples were formed by casting 3 mm dia., 2 mm thick discs of superconductor onto both sides of a thin normal metal plate. The Cu plates, 0.2 mm thick, were spark cut from 99.999% pure polycrystalline copper and oxygen-annealed to remove paramagnetic impurities that elevate the normal state thermopower<sup>20</sup>. Following chemical polishing to remove surface imperfections and oxides, the Pb and PbBi (eutectic) were melted onto opposite sides into a pyrex-bead mold. The In-Al-Sn sandwiches were formed in a similar manner, using 0.5 mm thick Al cut from 99.999% pure, nominally RRR=10,000 aluminum stock.

Figure 3 shows the experimental configuration. The sample was mounted inside a vacuum can, soldered to a copper block that was connected

to the  $^4\text{He}$  bath through a weak thermal link. A heater on the block enabled the sample temperature to be elevated above bath temperature and electronically regulated, while a heater at the isolated end provided the heat flow through the sample. The temperature of the NS interface was measured by a Ge thermometer placed on the normal metal; the Andreev thermal boundary resistance<sup>19</sup> between N and S is negligible near  $T_c$ . The sample was connected in a potentiometric circuit using an rf SQUID as a null detector. By measuring the current  $I_S$  applied to the calibrated standard resistor  $R_S \approx 3 \times 10^{-6}$ , we determined the thermoelectric voltage across the composite sample with a resolution of  $10^{-14}$  V. The resistance of the SNS' sandwich could also be measured in this configuration by applying a current  $I$  through the sample.

In Fig. 4(a) we plot the measured resistance of a Pb-Cu-PbBi sandwich as a function of temperature. At low temperatures, the resistance is slowly varying, but as  $T$  is increased,  $R$  exhibits a divergence at the Pb transition temperature,  $T_c = 7.2\text{K}$ . We attribute the divergence to the excess resistance of the charge imbalance region in the Pb. To extract the contribution from the superconductor,  $R_S$ , we first fit the resistance to a polynomial below 4K, over which range the charge imbalance contribution is negligible. Since the Cu is expected to be in the residual resistance regime at these temperatures, the appreciable temperature dependence of the resistance indicates that the NS and NS' interfaces are not perfectly metallic<sup>21</sup>, probably containing patches of oxides. The excess resistance above the parameterized fit, extrapolated to higher temperatures as shown in Fig. 4(a), is identified with  $R_S$ .

Theoretically,  $R_S$  is given by the second term in brackets in Eq. (14). Using Eqs. (7) and (13), we may separate out the explicit temperature dependence in the expression

$$R_S = \frac{1}{A} \left( \frac{0.73k_B T_C}{2N(0)e^2 \Delta(0)} \right)^{\frac{1}{2}} (\rho \tau_E)^{\frac{1}{2}} [Z(t)(1-t)^{-\frac{1}{4}}]. \quad (15)$$

In this equation, all of the parameters except  $\rho$  may be directly measured or obtained from the literature. Hence, in Fig. 4(b) we plot  $R_S$  vs.  $[Z(t)(1-t)^{-\frac{1}{4}}]$ ; the inset shows the universal function  $Z(t)$ . From the slope, we find  $\rho = 3.1 \times 10^{-8} \Omega\text{-cm}$ , using the calculated value<sup>22</sup> of  $\tau_E = 2.3 \times 10^{-11}$  sec. This corresponds to a quasiparticle diffusion length given by  $\lambda_{Q^*} = \lambda_{Q^*}(0)(1-t)^{-\frac{1}{4}}$ , where  $\lambda_{Q^*}(0) = 2.7 \mu\text{m}$ .

In Fig. 5(a), we plot the thermoelectric voltage per unit power across the Pb-Cu-PbBi sandwich vs. temperature. The negative bump in the thermoelectric voltage centered at 4K is characteristic of the thermopower of Cu<sup>20</sup>; the bump arises from the Kondo effect caused by magnetic impurities. Near  $T_C$ , however, we observe a negative divergence of the measured voltage, evidence for charge imbalance generation by the thermoelectric currents in the Pb. By subtracting the extrapolated curve drawn in Fig. 5(a), we again separate the contribution attributed to the superconductor,  $V_S$ , which we identify with the second term of Eq. (12).

In order to isolate the explicit temperature dependence of  $\lambda_{Q^*}$ , we may write

$$V_S/P = \left( \frac{\lambda_{Q^*}(0)}{A} \right) \frac{S}{\kappa} [(1-t)^{-\frac{1}{4}}]. \quad (16)$$

We use the value of  $\lambda_{Q^*}(0) = 2.7 \mu\text{m}$  obtained from the SNS' resistance, and estimate the thermal conductivity of the Pb from the measured electrical resistivity assuming the Wiedemann-Franz law,  $\kappa/\sigma T = L_0$ , where  $L_0$  is the Lorenz number ( $L_0 = 2.45 \times 10^{-8} \text{V}^2/\text{K}^2$ ). The only unknown coefficient is the thermoelectric power of the Pb,  $S$ , which we determine by plotting  $V_S/P$  vs.  $(1-t)^{-1/2}$  in Fig. 5(b). It is important to note that the proportionality of  $V_S/P$  to the expected temperature variation of  $\lambda_{Q^*}$  indicates that  $S$  is itself not strongly temperature dependent. A divergence of  $S \sim (1-t)^{-1/2}$  in the superconducting state had been suggested by bimetallic ring experiments.<sup>4</sup> From the slope of the curve in Fig. 5(b), we deduce a value of  $S = -7.8 \times 10^{-7} \text{V/K}$  near  $T_c$ .

In our configuration, we were unable to measure the normal state thermopower of the Pb section of the sample directly. However, pure Pb in the normal state<sup>23</sup> has a thermopower  $S_N = -2.2 \times 10^{-7} \text{V/K}$ , within a factor of 4 of our measured value. Since the addition of even small amounts of impurities may change the magnitude of the thermopower by as much as an order of magnitude, the results are consistent with the thermopower of the normal and superconducting states being continuous at  $T_c$ . Certainly, the coefficient measured by this technique does not deviate by several orders of magnitude (smaller or larger) from the expected normal state value, as has been observed previously.

Measurements on In-Al-Sn sandwiches near the In transition (3.4K) yield similar results. In Fig. 6, we plot the resistance  $R$  and thermoelectric voltage  $V/P$  vs.  $T$  for an In-Al-Sn sample. From the divergence of  $R$  near  $T_c$  we obtain  $\rho = 9.8 \times 10^{-7} \Omega\text{-cm}$ , which gives a diffusion length  $\lambda_{Q^*}(0) = 1.2 \mu\text{m}$ ,

assuming the calculated value<sup>22</sup>  $\tau_E = 1.0 \times 10^{-10}$  sec. for In. Despite  $\tau_E$  being longer in In than in Pb, we obtain a shorter  $\lambda_{Q^*}$  due to the higher resistivity. This we presume to be caused by substantial alloying of the Al into In. The divergence of V/P is evident only very near  $T_C$ , arising from the nearly linear normal metal thermopower of the Al. The excess thermoelectric voltage is found to increase roughly as  $(1-t)^{-1/4}$ , suggesting a slowly-varying superconducting state thermopower  $S = -1.1 \times 10^{-7}$  V/K. This is in good agreement with measured values<sup>4</sup> of the thermopower for normal state indium at  $T_C$  ( $\sim 4 \times 10^{-7}$  to  $3 \times 10^{-8}$  V/K).

#### IV. CONCLUSION

We have observed the charge imbalance generated at NS interfaces by thermoelectrically-driven quasiparticle currents in superconducting Pb and In. The charge imbalance, detected as an excess voltage in the presence of an applied heat current through the sample, exhibits the temperature variation of  $\lambda_{Q^*} \sim (1-t)^{-1/4}$  near  $T_C$ . We conclude, therefore, that the thermoelectric coefficient  $L_T$  (or  $S$ ) in the superconducting state is slowly-varying over the range of our measurement,  $T = 0.9$  to  $0.999 T_C$ . The measured magnitudes in Pb and In are in reasonable agreement with typical normal state thermopower values for the metals at their transition temperatures.

Further experiments are being conducted to eliminate some of the uncertainties in the measurements. First of all, it is necessary to fabricate better NS interfaces, eliminating oxide barriers and reducing alloying. Secondly, because of the extreme sensitivity of the thermopower of metals to impurities and defects, it is essential to make a direct measurement of the normal state thermopower in the sample used so that a direct comparison between the normal and superconducting state values can be made.

## ACKNOWLEDGEMENTS

I am grateful to the Cavendish Laboratory at Cambridge University, England, for their warm hospitality during the experimental stages of this work, and to Professor John R. Waldram for many illuminating discussions. I further acknowledge the National Science Foundation for a NATO Postdoctoral Fellowship and Thomas R. Lemberger for a critical reading of the manuscript. This work was supported in part by the Division of Materials Science, Office of Basic Energy, U.S. Department of Energy under contract No. W-7405-Eng. 48.



## REFERENCES

1. V. L. Ginzburg, Zh. Eksp. Teor. Fiz. 14, 177 (1944) [Sov. Phys. JETP 8, 148 (1944)].
2. C. M. Falco and J. C. Garland, in Non-equilibrium Superconductivity, Phonons, and Kapitza Boundaries, edited by K. E. Gray (Plenum Press, New York, 1981), chap. 16.
3. A. A. J. Matsinger, R. de Bruyn Ouboter, and H. van Beeken, Physica (Utrecht) B 93, 63 (1978).
4. D. J. Van Harlingen, D. F. Heidel, and J. C. Garland, Phys. Rev. B 21, 1842 (1980).
5. C. M. Pegrum, A. M. Guénault, and G. R. Pickett, in Low Temperature Physics-LT14, edited by M. Krusius and M. Vuorio (North-Holland, Amsterdam, 1975), Vol. II, p. 513.
6. C. M. Falco, Solid State Commun. 19, 623 (1976).
7. N. K. Welker and F. D. Bedard, in SQUID: Superconducting Quantum Interference Devices and their Applications, edited by H. D. Hahlbohm and H. Lübbig (Walter de Gruyter, New York, 1977), p. 200.
8. Yu. M. Gal'perin, V. L. Gurevich, and V. I. Kozub, Zh. Eksp. Teor. Fiz. 66, 1387 (1974) [Sov. Phys. JETP 39, 680 (1975)].
9. S. N. Artemenko and A. F. Volkov, Zh. Eksp. Teor. Fiz. 70, 1051 (1976) [Sov. Phys. JETP 43, 548 (1976)].
10. J. R. Waldram, Proc. R. Soc. (London) A 345, 231 (1975).
11. C. J. Pethick and H. Smith, Ann. Phys. 119, 133 (1979).
12. R. A. Sacks, J. Low Temp. Phys. 34, 393 (1979).
13. O. Entin-Wohlman and R. Orbach, Phys. Rev. B 22, 4271 (1980).
14. C. M. Falco, Phys. Rev. Lett. 39, 661 (1977).
15. M. Tinkham, Phys. Rev. B 22, 2594 (1980).

16. A. Schmid and G. Schön, *J. Low Temp. Phys.* 20, 207 (1975).
17. T. Y. Hsiang and J. Clarke, *Phys. Rev. B* 21, 945 (1980).
18. J. Clarke, U. Eckern, A. Schmid, G. Schön, and M. Tinkham, *Phys. Rev. B* 20, 3933 (1979).
19. A.F. Andreev, *Zh. Eksp. Teor. Fiz.* 46, 182 (1964) [*Sov. Phys. JETP* 19, 1228 (1964)].
20. E. R. Rumbo, *Phil. Mag.* 19, 689 (1969).
21. G. L. Harding, A. B. Pippard, and J. R. Tomlinson, *Proc. R. Soc. (London)* A 340, 1 (1974).
22. S. B. Kaplan, C. C. Chi, D. N. Langenberg, J. J. Chang, S. Jafarey, and D. J. Scalapino, *Phys. Rev. B* 14, 4854 (1976).
23. J. W. Christian, J. P. Jan, W. P. Pearson, and I. M. Templeton, *Proc. R. Soc. (London)* A 245, 213 (1958).

## FIGURE CAPTIONS

- Fig. 1 (a) At a normal metal-superconductor interface, an applied heat current  $\vec{U}$  generates an electrochemical potential gradient  $\vec{\nabla}\phi_n$  in the normal metal and counterflowing normal and supercurrents  $\vec{J}_n = -\vec{J}_s$  in the superconductor. (b) Spatial variation of quasiparticle current near the NS interface. (c) Spatial decay of the thermoelectrically-generated charge imbalance  $Q^*$ .
- Fig. 2 Spatial variations of the pair ( $\phi_s$ ) and quasiparticle ( $\phi_n$ ) electrochemical potentials in the SNS' sandwich shown at the top. The measured voltage  $V$  includes the normal thermoelectric voltage  $V_N$  plus the charge imbalance contribution  $V_S$ . Here,  $T_{CS} \ll T_{CS}'$ .
- Fig. 3 Schematic drawing of the experimental configuration used to measure the thermopower and resistance of SNS' sandwiches.
- Fig. 4 (a) The temperature dependence of the resistance  $R$  of a Pb-Cu-PbBi sandwich showing the divergence at  $T_c = 7.2K$ . The solid line is a polynomial fit to the region below 4K. (b) The contribution to the resistance from the charge imbalance region  $R_S$  vs.  $Z(t)(1-t)^{-1/4}$ , where  $Z(t)$  is shown in the inset.
- Fig. 5 (a) Plot of the measured thermoelectric voltage per unit power  $V/P$  vs.  $T$  for a Pb-Cu-PbBi sample. The solid curve is characteristic of the normal thermopower of Cu. (b) Fit of the charge imbalance contribution  $V_S/P$  to the temperature dependence of  $\lambda_{Q^*} \sim (1-t)^{-1/4}$ .
- Fig. 6 (a) The temperature dependence of the resistance  $R$  vs.  $T$  for an In-Al-Sn sample. (b) Thermoelectric voltage vs.  $T$  for the same sample. Both exhibit a divergence at the indium transition temperature  $T_c = 3.4K$ .



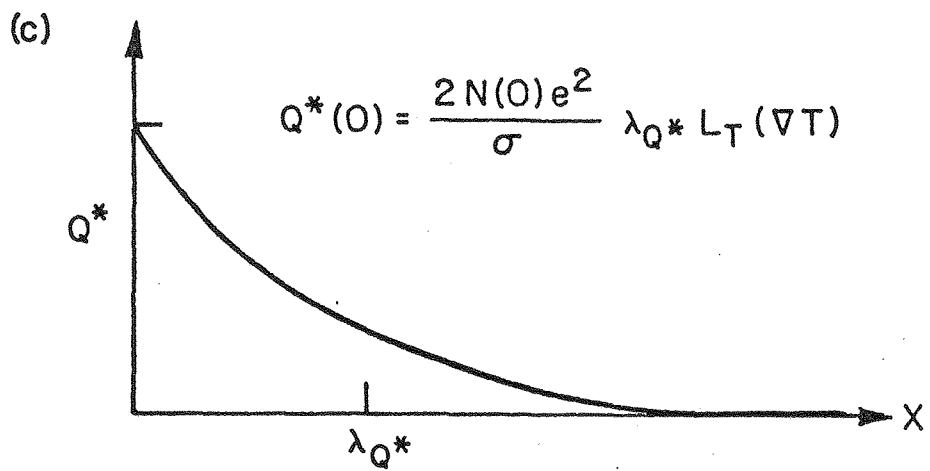
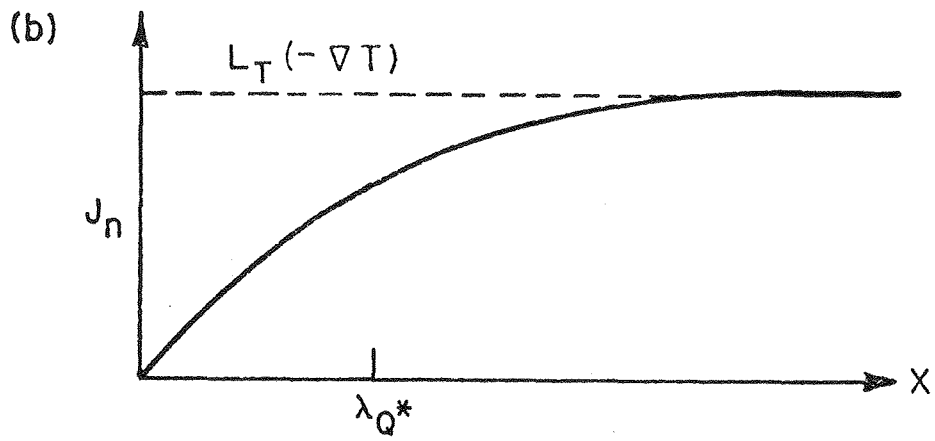
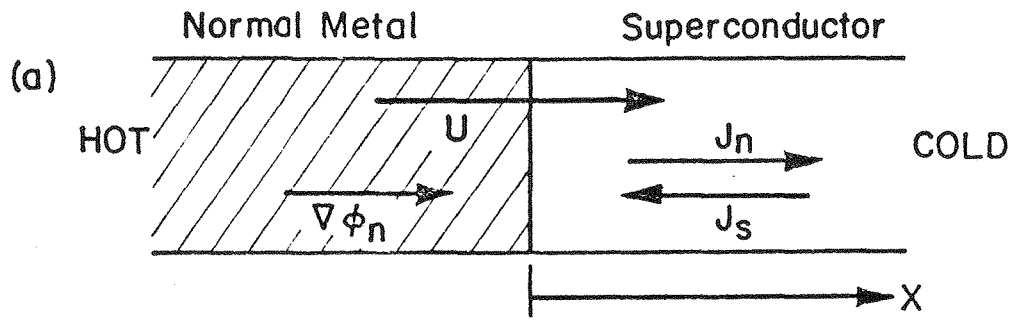



Fig. 1



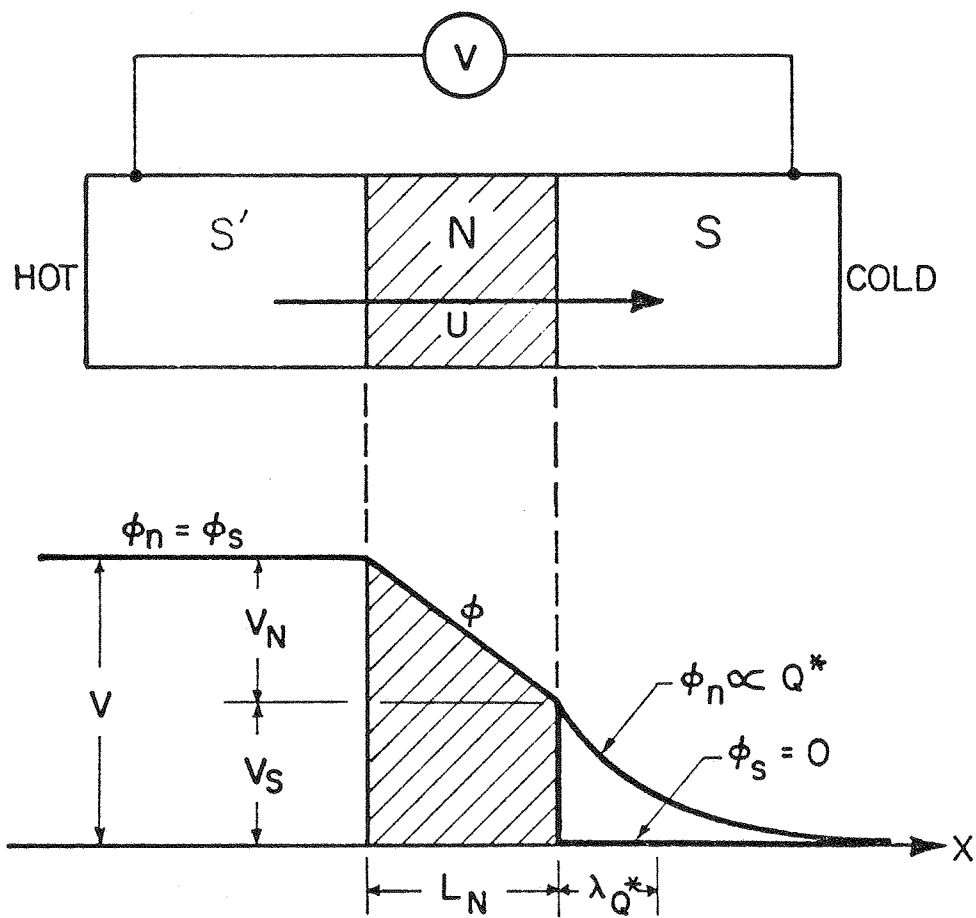


Fig. 2





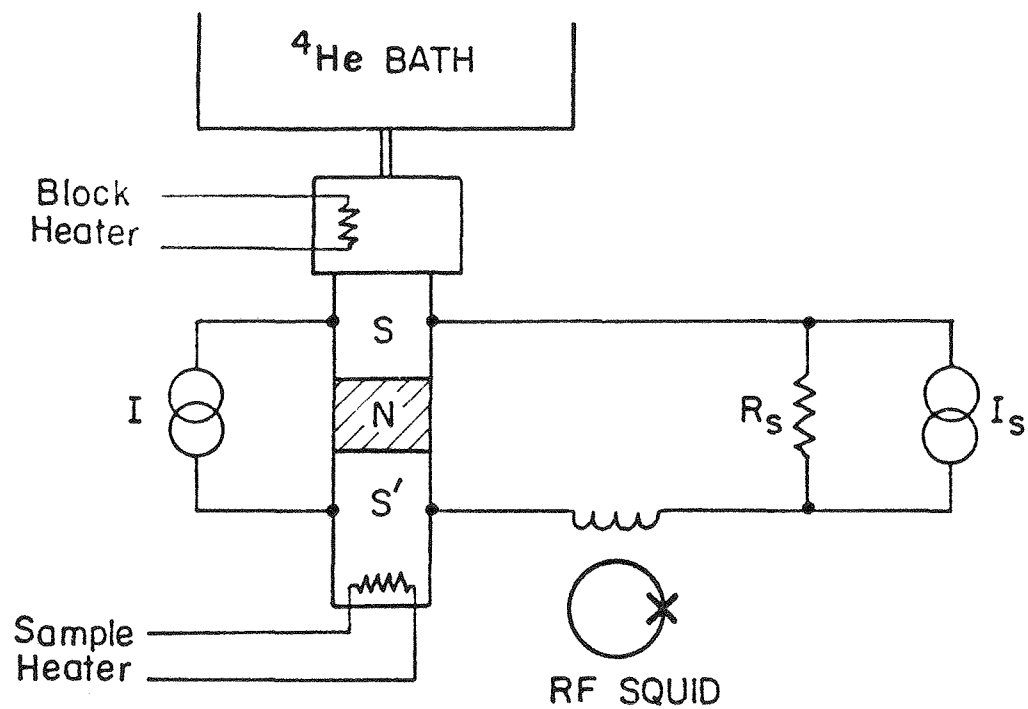


Fig. 3



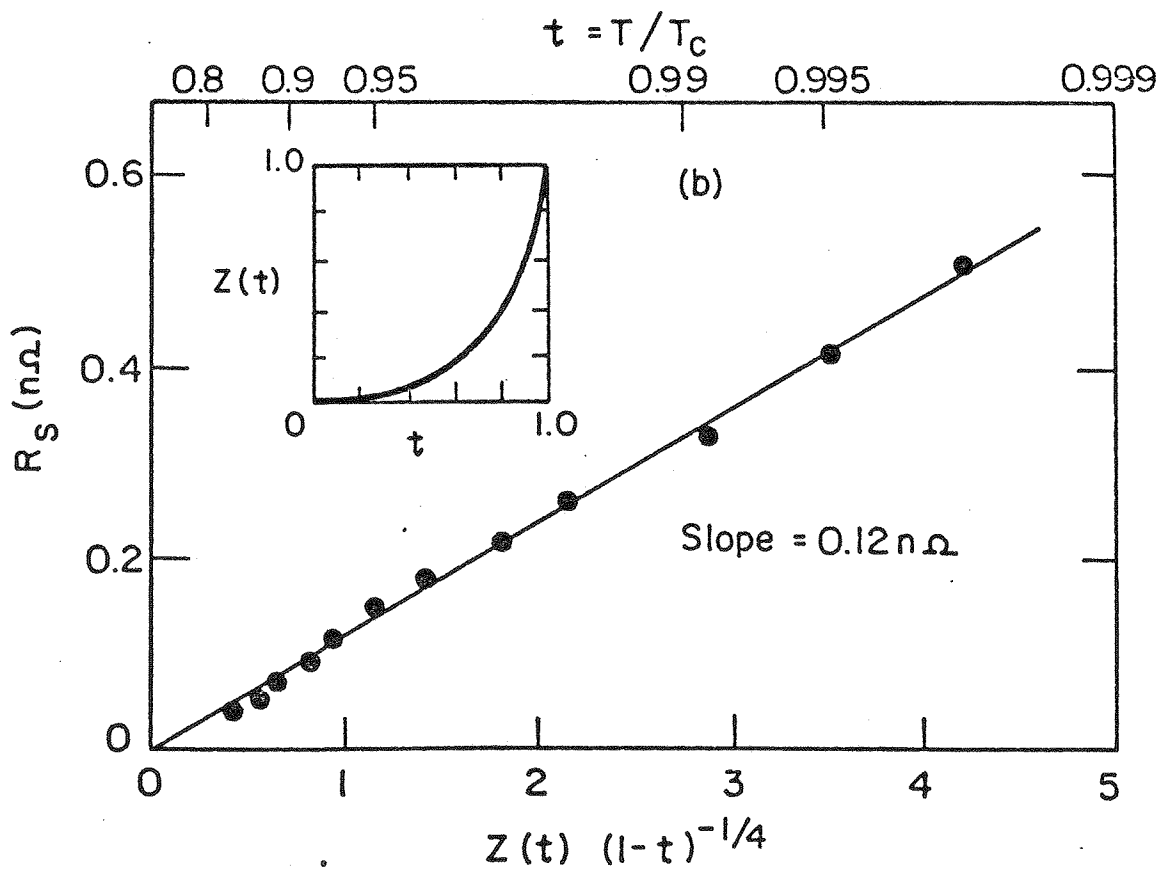
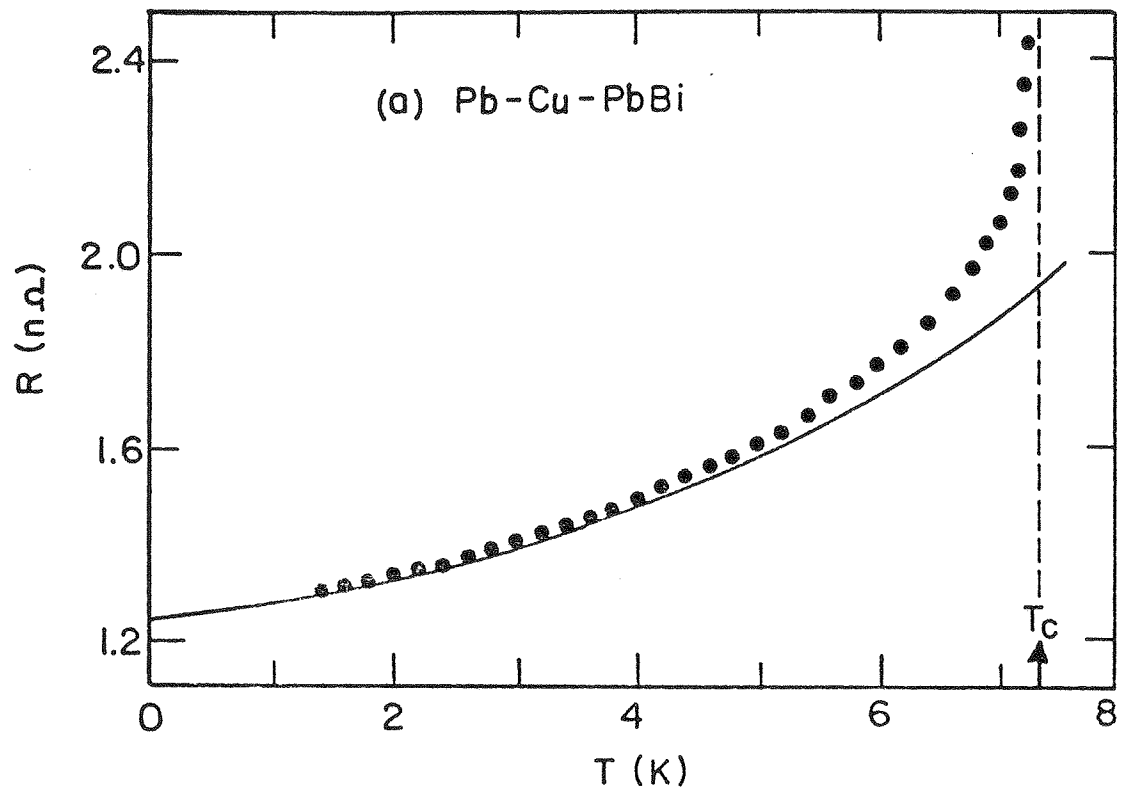


Fig. 4



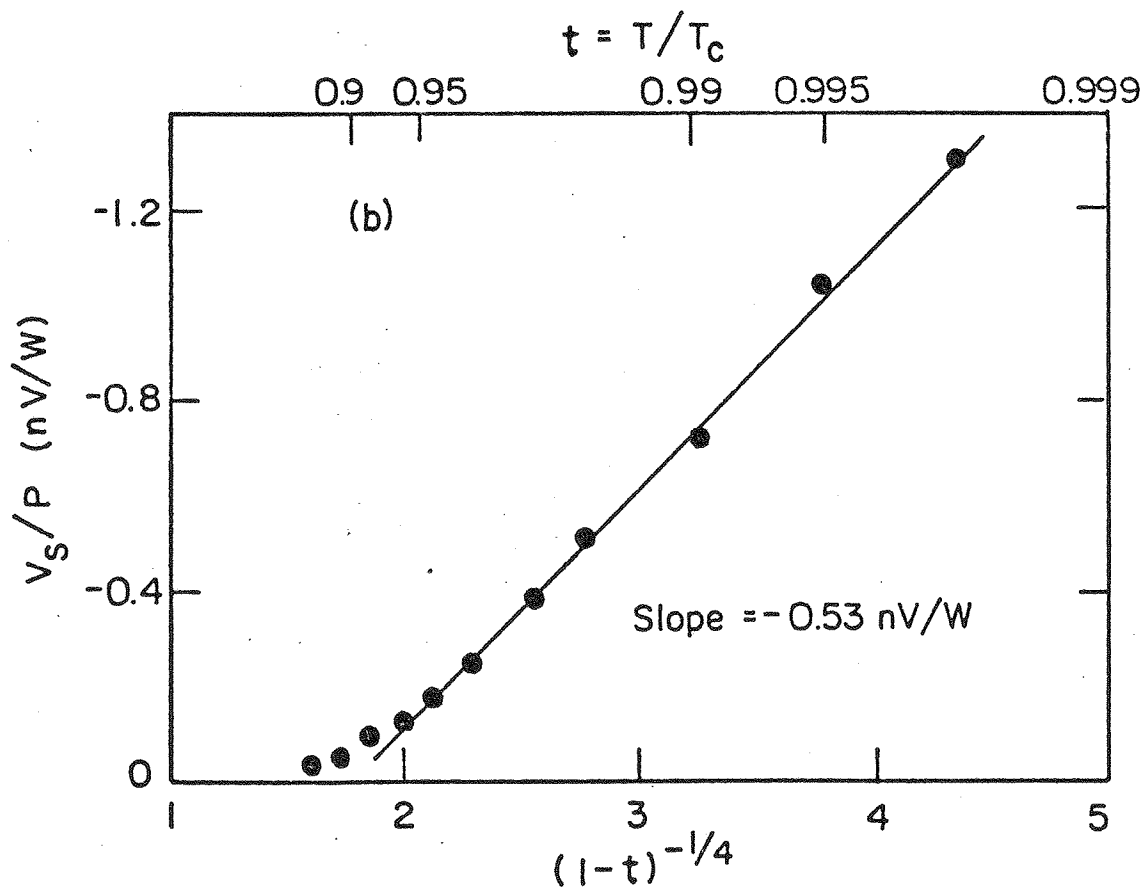
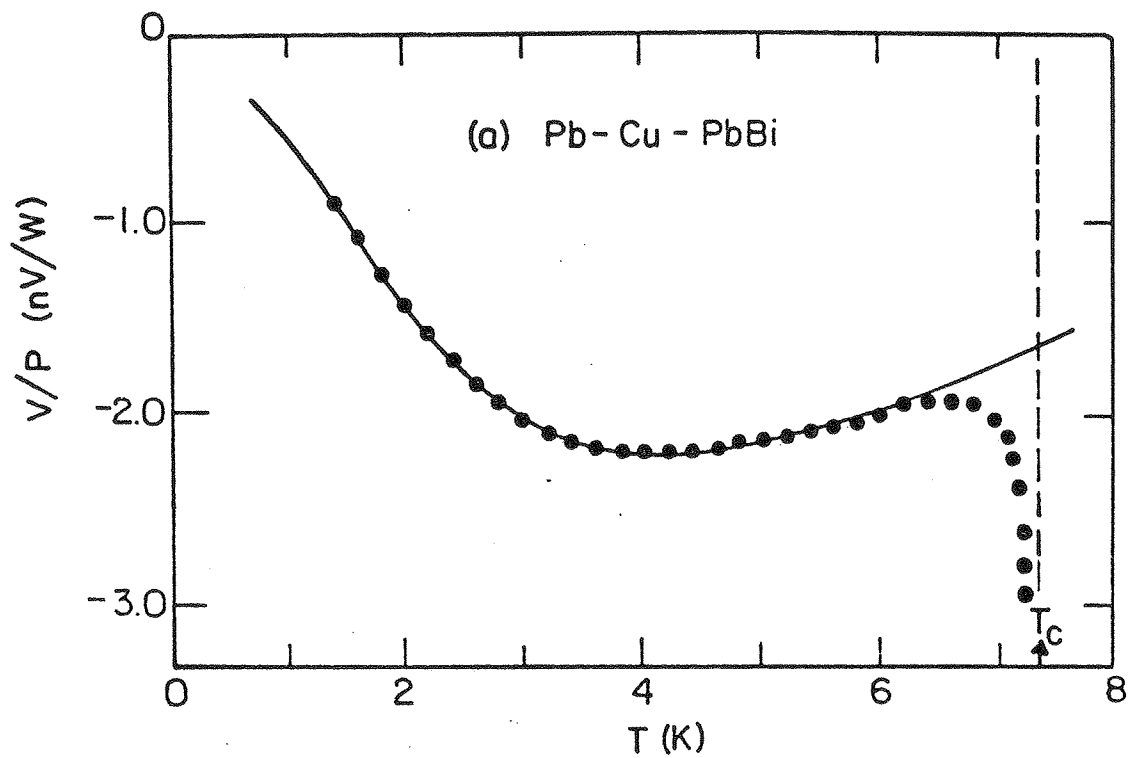


Fig. 5




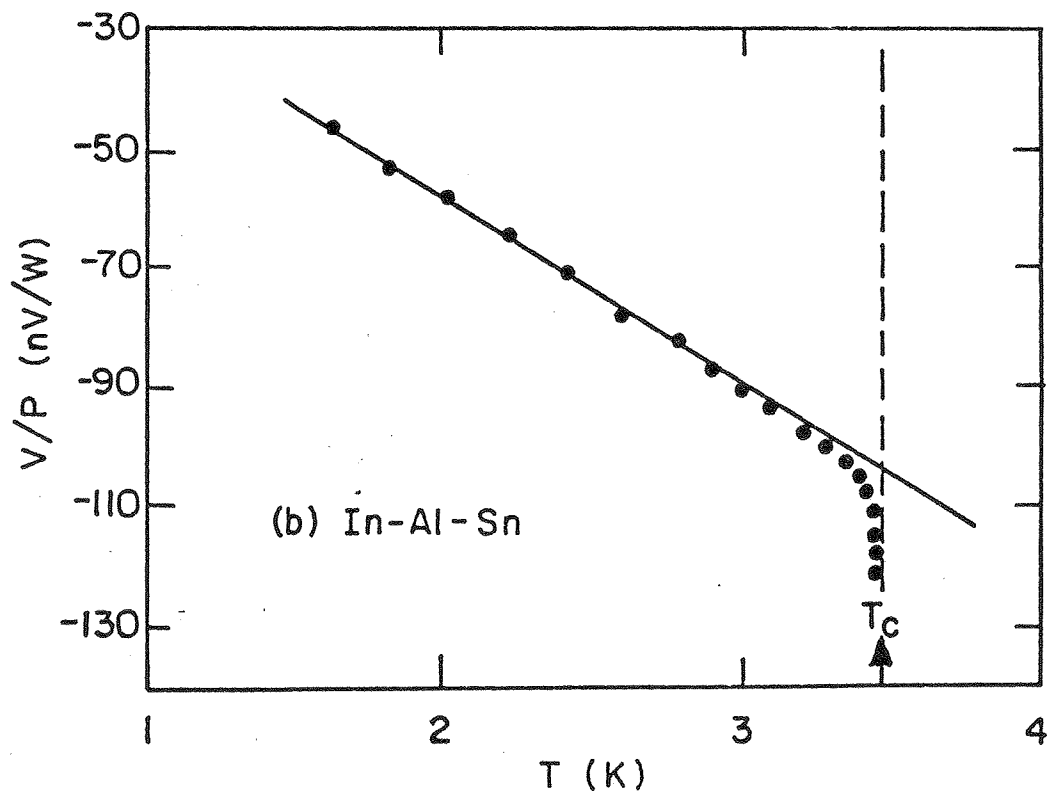


Fig. 6

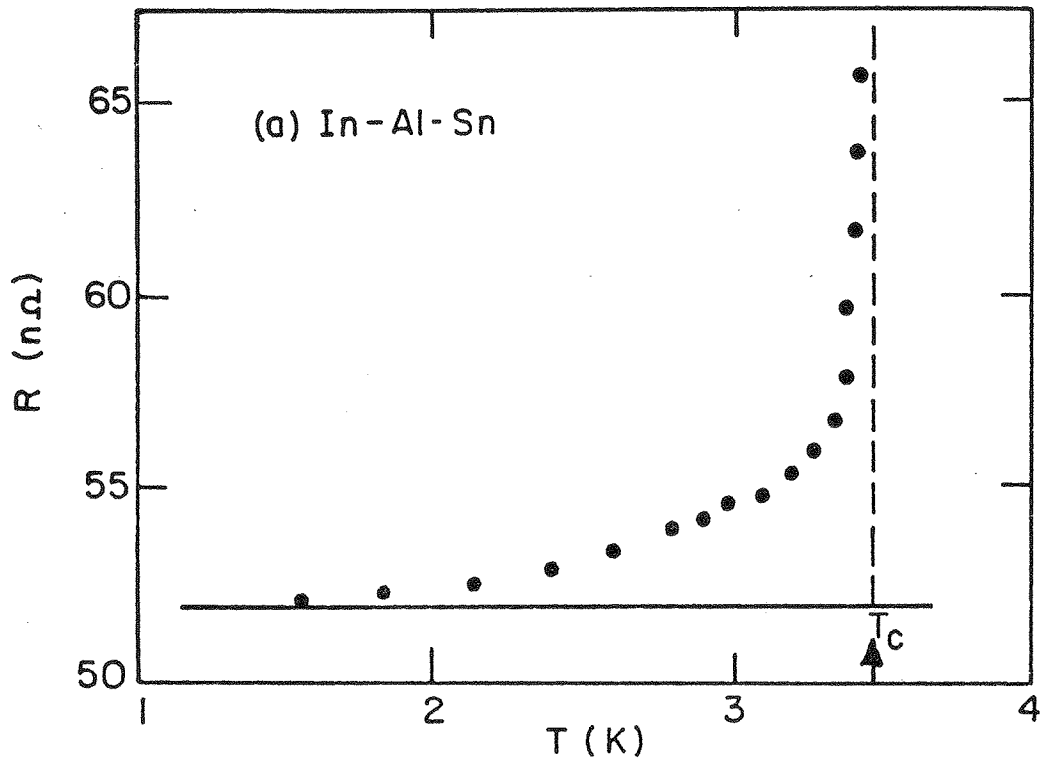