

# Lawrence Berkeley National Laboratory

## LBL Publications

### Title

CORRELATION OF CYCLOHEXENE REACTIONS ON PLATINUM CRYSTAL SURFACES OVER 10-ORDERS OF MAGNITUDE PRESSURE RANGE: VARIATIONS OF STRUCTURE SENSITIVITY, RATES, AND REACTION PROBABILITIES

### Permalink

<https://escholarship.org/uc/item/0b8299tf>

### Author

Davis, S.M.

### Publication Date

1979-09-01



# Lawrence Berkeley Laboratory

UNIVERSITY OF CALIFORNIA

## Materials & Molecular Research Division

RECEIVED  
LAWRENCE  
BERKELEY LABORATORY

Submitted to the Journal of Catalysis

NOV 16 1979

LIBRARY AND  
DOCUMENTS SECTION

CORRELATION OF CYCLOHEXENE REACTIONS ON PLATINUM  
CRYSTAL SURFACES OVER 10-ORDERS OF MAGNITUDE PRESSURE  
RANGE: VARIATIONS OF STRUCTURE SENSITIVITY, RATES, AND  
REACTION PROBABILITIES

S. M. Davis and G. A. Somorjai

September 1979

### For Reference

Not to be taken from this room



LBL-9869 c.1

## **DISCLAIMER**

This document was prepared as an account of work sponsored by the United States Government. While this document is believed to contain correct information, neither the United States Government nor any agency thereof, nor the Regents of the University of California, nor any of their employees, makes any warranty, express or implied, or assumes any legal responsibility for the accuracy, completeness, or usefulness of any information, apparatus, product, or process disclosed, or represents that its use would not infringe privately owned rights. Reference herein to any specific commercial product, process, or service by its trade name, trademark, manufacturer, or otherwise, does not necessarily constitute or imply its endorsement, recommendation, or favoring by the United States Government or any agency thereof, or the Regents of the University of California. The views and opinions of authors expressed herein do not necessarily state or reflect those of the United States Government or any agency thereof or the Regents of the University of California.

LBL 9869

CORRELATION OF CYCLOHEXENE REACTIONS ON PLATINUM CRYSTAL  
SURFACES OVER 10-ORDERS OF MAGNITUDE PRESSURE RANGE:

Variations of Structure Sensitivity, Rates, and  
Reaction Probabilities

S.M. Davis and G.A. Somorjai

Materials and Molecular Research Division, Lawrence Berkeley Laboratory,  
and Department of Chemistry, University of California, Berkeley, CA 94720

September 1979

Prepared for the U.S. Department of Energy  
under contract W-7405-ENG-48

Abstract

The hydrogenation and dehydrogenation of cyclohexene have been studied in the  $10^{-7}$  to  $10^2$  torr pressure range. The reaction of cyclohexene in excess hydrogen over the Pt(223) stepped platinum crystal surface at 25-150°C predominantly produces benzene at low pressures ( $\sim 10^{-7}$  torr) and cyclohexane at high pressures ( $\sim 10^2$  torr). While the low pressure reactions are structure sensitive and proceed on the clean metal surface, the high pressure reaction is apparently structure insensitive due to the continuous presence of a near monolayer of carbonaceous species. Widely differing coverages of reactive, weakly adsorbed hydrogen influence the reversal in selectivity between high and low pressures. The catalytic efficiency (reaction probability) decreases markedly with increasing pressure.

## Introduction

The reactions of cyclohexene at low total pressures ( $10^{-8}$ - $10^{-5}$  Torr) over platinum crystal surfaces have been investigated extensively (1-3). The hydrogenation and dehydrogenation reactions are structure sensitive as indicated by the striking variations in catalytic behavior which exist between crystal surfaces of different atomic structure. At much higher pressures ( $10$ - $10^3$  Torr) over silica supported platinum catalysts, Boudart and coworkers (4) have convincingly shown that cyclohexene hydrogenation is structure insensitive. The change of the reaction rate dependence on surface structure as the pressure is increased indicates that the reaction mechanism has changed. In order to explore how the reaction mechanism was altered we have investigated the catalyzed hydrogenation and dehydrogenation of cyclohexene over 10-orders of magnitude pressure range, from  $10^{-8}$ - $10^2$  Torr. Our catalyst was a Pt(223) single crystal of surface area of about  $1\text{ cm}^2$ . The atomic surface structure of this sample consists of terraces of (111) orientation that are 5 atoms wide, separated by steps, one atom in height and of (100) orientation. The structure and composition of the surface was monitored by low energy electron diffraction (LEED) and Auger electron spectroscopy (AES) before and after the reaction studies, in situ, in the reaction chamber.

Our results indicate that at low reactant pressures the reaction occurs on an initially clean platinum surface and the kinetics are characteristic of the uncovered metal. The catalyst deactivates rapidly however, due to the build-up of a monolayer of carbonaceous deposit on the metal surface. Platinum in the presence of this carbon-containing overlayer is quite active however, at high reactant pressures. At high pressures the deposit builds up within seconds and steady state rates are obtained in its presence. It appears that while the

hydrogenation and dehydrogenation of cyclohexene are structure sensitive on the clean platinum surface these reactions are structure insensitive in the presence of this carbonaceous deposit. This explains in part, the pressure dependence of the structure sensitivity of these reactions.

The turnover numbers increase by four to six orders of magnitude for the dehydrogenation and hydrogenation reactions, respectively, as the reactant pressure is increased from  $10^{-8}$  to  $10^2$  Torr. The reaction probabilities however, decrease by orders of magnitude with increasing pressure. Thus, the platinum surface becomes much less efficient to catalyze the surface reactions at high pressures.

## Experimental

High and low pressure experiments were performed in a UHV apparatus equipped with electron optics for LEED and Auger electron spectroscopy, an argon ion-sputter gun, a quadrupole mass analyzer, and an internal isolation cell which operates as a micro-batch reactor ( $V = 160 \text{ cm}^3$ ) in the  $10^{-4}$ -1 atm pressure range (5). The high pressure enclosure was attached to an external gas recirculation loop which was fitted with an isolable Wallace & Tiernan gauge, metering valves for gas admission and mass spectral analysis, a gear pump for gas circulation, and a gas chromatograph sampling valve. Research grade hydrogen (Matheson) and cyclohexene (Matheson "Spectroquality", 99.5+ mol%) were mixed in the circulation loop before expansion into the isolation cell.

Turnover frequencies for the batch reactions were calculated from the slopes of initially linear product accumulation versus reaction time curves. Reaction rates did not depend on the recirculation rate, and initial rates were reproducible to within about  $\pm 10\%$ . At  $150^\circ\text{C}$  and 77 Torr ( $1 \text{ Torr} = 133 \text{ N m}^{-2}$ ) the maximum hydrogenation rate of  $33 \text{ molec site}^{-1} \text{ sec}^{-1}$  represented a cyclohexene conversion rate of  $\sim 4\% \text{ min}^{-1}$ ; however, total conversion after 100 minutes of reaction never exceeded  $\sim 75\%$  as a result of self-poisoning. The sample was cooled to  $25^\circ\text{C}$  before evacuating the reaction mixture and then flashed to the reaction temperature prior to Auger analysis. The pumpdown time required for Auger analysis was about 3 minutes. Detailed procedures followed for low pressure flow reactions, crystal preparation and cleaning, and surface characterization have been described previously (2,3).



## Results and Discussion

### The Build-up of the Carbonaceous Overlayer:

The product accumulation as a function of reaction time for the stepped platinum crystal surface is shown in Figure 1 for a total pressure of 77 Torr. At temperatures below  $\sim 100^\circ\text{C}$ , self-poisoning does not occur at 77 Torr or is slow and largely reversible at  $10^{-6}$  Torr (2). After reactions at these low temperatures most ( $\sim 80\%$  or more at  $25^\circ\text{C}$ ) of the adsorbate that accumulates on the surface can be reversibly desorbed at  $\sim 120^\circ\text{C}$  as molecular benzene. At higher temperatures self-poisoning becomes rapid and irreversible. Between 0.4 and 1.1 monolayer of disordered carbonaceous material is deposited during the first 10-200 seconds of the reaction essentially independent of the cyclohexene pressure. This overlayer is strongly chemisorbed and decomposes on further heating with the evolution of hydrogen and only traces of benzene. The overlayer coverage depends significantly on the reaction temperature increasing from  $\sim 0.4$  at  $25^\circ\text{C}$  and  $10^{-6}$  Torr to  $\sim 1.1$  at  $150^\circ\text{C}$  and 77 Torr ( $C_{273}/Pt_{237} = 2.8$  corresponds to monolayer coverage for this surface (6)). In Figure 2 the rate of the dehydrogenation reaction as a function of time is shown at low pressures along with the build-up of the carbonaceous deposit with time. The overall rate of self-poisoning at low pressures correlates closely with the build-up of the carbon containing irreversibly chemisorbed overlayer. The rapid self-poisoning at  $150^\circ\text{C}$  demonstrates that the irreversibly chemisorbed overlayer is particularly effective in blocking sites that catalyze dehydrogenation. The reaction rates at low pressures were obtained before the build-up of the deposit. The catalytic activity observed at low pressures is therefore characteristic of the clean metal surface. At high pressures, the initially clean surface rapidly becomes covered with a monolayer of reversibly and irreversibly chemisorbed species. The catalytic behavior is then characteristic of an extensively precovered platinum surface.

In Figure 3 the initial turnover frequencies obtained for the hydrogenation reaction as a function of temperature over the stepped crystal surface are compared with those reported by Segal et al (4) for dispersed platinum. The two sets of data agree well supporting the view (4) that the reaction at high pressures is structure insensitive. The apparent activation energy for hydrogenation is  $5.0 \pm 0.5$  kcal/mole on the stepped surface at 77 Torr.

The transition of the active platinum surface from being clean to continuously covered by the carbonaceous deposit is accompanied by a change from structure sensitive to structure insensitive catalytic behavior for the hydrogenation of cyclohexene. A change in mechanism is also indicated by the changing apparent activation energy for this reaction. It is less than 1 kcal/mole at low pressures while it is 5 kcal/mole at high pressures. Similarly, the apparent activation energy for the dehydrogenation of cyclohexene is at least 8 kcal/mole at 77 Torr, while it is near zero at low pressures in the same temperature regime. A more pronounced increase in apparent activation energy with increasing pressure has also been observed during cyclohexane hydrogenolysis and dehydrogenation (7). The apparent activation energy for metal-catalyzed hydrocarbon reactions always appears to increase with increasing reactant pressures (8).

The Hydrogenation and Dehydrogenation Rates of Cyclohexene Over Ten Orders of Magnitude Pressure Range:

The turnover frequencies and reaction probabilities at 150°C for the hydrogenation and dehydrogenation of cyclohexene in excess hydrogen are summarized in Figure 4. All the results were obtained on the stepped Pt(223) crystal face. The error bars at low pressures span the range of structure sensitivity for 2-6 different platinum crystal faces. Overall, the turnover numbers for hydrogenation and dehydrogenation vary by factors of  $10^7$  and  $10^4$ , respectively, for a  $10^9$ -fold increase in the cyclohexene pressure. The fraction

of reacting molecules dehydrogenating to benzene decreases from 94-100% at low pressures to just over 1% at a total pressure of 77 Torr. The dehydrogenation reaction probability - that is, the fraction of incident cyclohexene molecules converted to benzene - declines steadily from  $\sim 0.05$  at  $10^{-7}$  Torr to less than  $10^{-6}$  at 77 Torr. In contrast, the hydrogenation probability varies by only two orders of magnitude ( $\sim 10^{-3}$ - $10^{-5}$ ) over the entire range of pressure, surprisingly exhibits a minimum at a total pressure of  $10^{-2}$ - $10^{-1}$  Torr, and thereafter increases with increasing total pressure. In the pressure range of increasing reaction probability the hydrogenation rate is 1.3 order with respect to total pressure.

The enormous decline in the dehydrogenation probability with increasing pressure is mainly associated with the lengthy mean reaction time which is required for the dehydrogenation and desorption processes to occur. The 2-5 minute induction period observed before appreciable benzene desorption in our low pressure experiments (cf. Fig 2)(1-3) indicates that the mean reaction time is on the order of 10 sec at  $150^{\circ}\text{C}$  and certainly no shorter than  $10^{-1}$  sec. When the cyclohexene pressure is  $10^{-7}$  Torr, the dehydrogenation probability is high ( $\sim 0.05$ ) because the time required for adsorption, surface reaction, and product transport away from the surface is short in comparison to the time between collisions of the reactant molecules with the surface (ca.  $10^{-14}$  sec  $\text{cm}^2$  at  $10^{-7}$  Torr). At higher pressures the dehydrogenation efficiency decreases rapidly as the inter-collision period becomes much shorter than the mean reaction time. Under these conditions, most of the adsorption sites are continuously blocked from incident cyclohexene molecules by carbonaceous deposits.

In order to assure that thermodynamic equilibrium considerations do not influence the rate data that are shown in Figure 4, the equilibrium constants and conversion concentrations of cyclohexane and benzene were calculated at low pressures ( $\sim 10^{-7}$  Torr) and high pressures (77 Torr) at two temperatures,

25°C and 150°C. These data along with turnover frequencies are listed in Table 1. It can be seen that at 150°C there are no thermodynamic boundary conditions that influence the rates reported in Figure 4 with the exception of the low pressure hydrogenation rate.

There could be another reason, in addition to the presence of the carbonaceous deposit, for the change of hydrogenation mechanism and reversal in selectivity at higher pressures. Reactive, weakly adsorbed hydrogen ( with heats of adsorption in the range of 8-10 kcal/mole ) is identifiable on platinum only at pressures exceeding  $\sim 10^{-1}$  Torr (9-12). At about this pressure the cyclohexene hydrogenation probability begins to increase, and hydrogenation becomes the prevailing reaction pathway. While weakly adsorbed hydrogen hydrogenates benzene readily (10,13), studies by Basset *et al.* (10) indicate that strongly chemisorbed hydrogen (  $-\Delta H_a \geq 15$  kcal/mole ) does not add to benzene at all, or at least not at an easily accessible rate. More general considerations (8) suggest that at pressures of practical application this new type of weakly adsorbed hydrogen is responsible for most, perhaps all, metal-catalyzed hydrogenation reactions. Reversibly chemisorbed hydrogen must also be present under low pressure reaction conditions. However, the surface concentration,  $\sigma$ , at  $10^{-6}$  Torr will be exceedingly small because its residence time,  $\tau = \tau_0 e^{-\Delta H_a/RT} = 10^{-8} - 10^{-5}$  sec, is short compared to the period between  $H_2$  collisions with the surface (  $1/F \approx 10^{-15}$  sec  $cm^2$  at  $10^{-6}$  Torr ), so that  $\sigma = F\tau$  is less than  $\sim 10^{10} cm^{-2}$ , ie. less than  $10^{-3}\%$  of a monolayer. At high pressures the steady state concentration of weakly adsorbed hydrogen will become appreciable as a result of the increased  $H_2$  flux, and as a consequence, hydrogenation will become kinetically facile.

#### Acknowledgement

This work was supported by the Division of Materials Sciences, Office of Basic Energy Sciences, U.S. Department of Energy and the Petroleum Research Fund administered by the American Chemical Society.

References

1. D.W. Blakely and G.A. Somorjai, J. Catal., 42, 181 (1976).
2. S.M. Davis and G.A. Somorjai, Surface Sci., in press.
3. C.E. Smith, J.P. Biberian, and G.A. Somorjai, J. Catal., 57, 426 (1979).
4. E. Segal, R.J. Madon, and M. Boudart, J. Catal., 52, 45 (1978).
5. J.C. Hemminger, R. Carr, and G.A. Somorjai, Chem. Phys. Lett., 57, 100 (1978).
6. J.P. Biberian and G.A. Somorjai, Appl. Surface Sci., 2, 253 (1979).
7. W.D. Gillespie and G.A. Somorjai, to be published.
8. S.M. Davis and G.A. Somorjai, to be published in Catal. Rev.
9. M. Primet, J.M. Basset, M.V. Mathieu, and M. Prettre, J. Catal., 28, 368 (1973).
10. J.M. Basset, G. Dalmai-Imelik, M. Primet, and R. Mutin, J. Catal., 37, 22 (1975).
11. L.T. Dixon, R. Barth, R.J. Kokes, and J.W. Gryder, J. Catal., 37, 376 (1975).
12. J.D. Clewly, J.F. Lynch, and T.B. Flanagan, J. Catal., 36, 291 (1975).
13. P.C. Aben, J.C. Platteeuw, and B. Southamer, Proc. 4<sup>th</sup> Internat. Congr. Catalysis, Moscow, 1968, paper I-3.
14. D.R. Stull, E.F. Westrum, and G.C. Sinke, The Chemical Thermodynamics of Organic Compounds, Wiley & Sons Inc., New York, 1969.

Table I: Equilibrium Constants and Turnover Frequencies for Cyclohexene Reactions at High and Low Pressures over Pt(223)


Reaction	T (°C)	TN <sup>a</sup> low P	TN <sup>a</sup> high P	logK <sub>p</sub> <sup>b</sup>	C <sub>eq</sub> <sup>a</sup> (%) low P	C <sub>eq</sub> <sup>a</sup> (%) high P
Hydrogenation	25	3-8x10 <sup>-6</sup>	2.8	13.08	99.9	99.9
	150	3-8x10 <sup>-6</sup>	33	6.95	0.8	99.9
Dehydrogenation	25	2x10 <sup>-4</sup>	-	-3.96	99.9	0.2
	150	4x10 <sup>-4</sup>	0.4	0.65	99.9	99.7

a) Turnover frequencies (uncertainty  $\pm 10\%$ ) and equilibrium conversions referred to initial pressures of 6x10<sup>-8</sup> Torr C<sub>6</sub>H<sub>10</sub> and 6x10<sup>-7</sup> Torr H<sub>2</sub> at low P; 7 Torr C<sub>6</sub>H<sub>10</sub> and 70 Torr H<sub>2</sub> at high P (1 Torr = 133 N m<sup>-2</sup>).

b) Referred to ideal gas state at 1 atm (14).

Figure Captions


1. Product accumulation versus reaction time for cyclohexene hydrogenation over Pt(223) at several temperatures. Rapid sampling was facilitated by the combined use of a mass spectrometer and gas chromatograph.
2. A comparison at 150°C of the cyclohexene dehydrogenation rate over Pt(223) at low pressures with the simultaneous build-up of the irreversibly chemisorbed carbonaceous overlayer. A  $C_{273}/Pt_{237}$  ratio of 2.8 corresponds to monolayer coverage.
3. Arrhenius plot for cyclohexene hydrogenation over Pt(223). For comparison, the results of Segal, Madon, and Boudart (4) are included for  $P_{HC} = 13$  Torr and  $P_{H_2} = 76$  Torr.
4. Correlation of cyclohexene reaction rates and reaction probabilities over 10-orders of magnitude pressure range. The reactions were performed at 150°C over the stepped Pt(223) crystal surface with  $H_2/HC = 10$ .

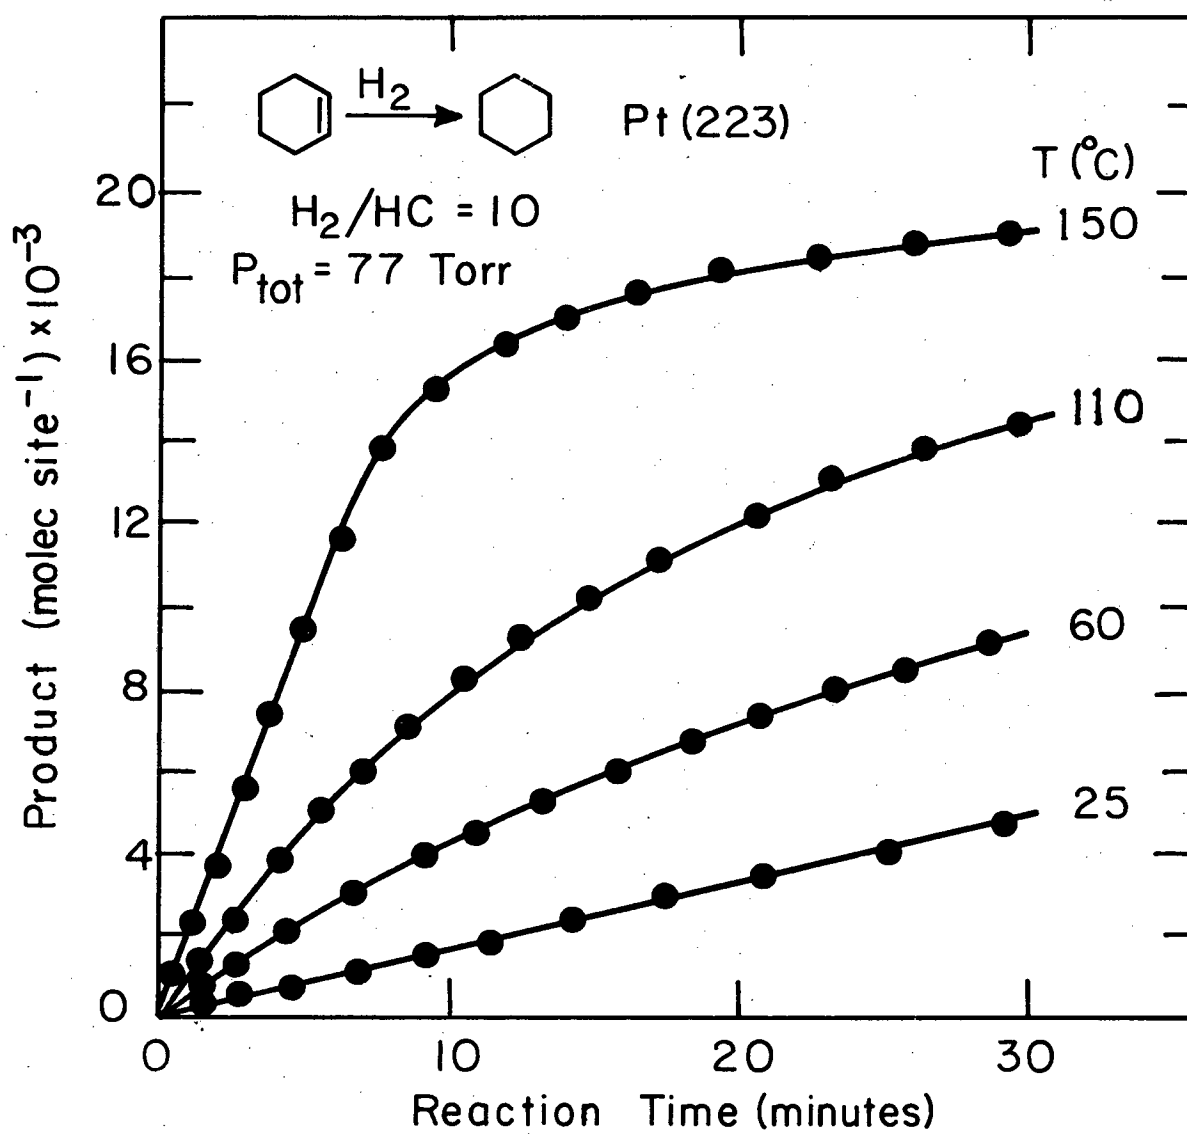

XBL797-6700


Fig.1



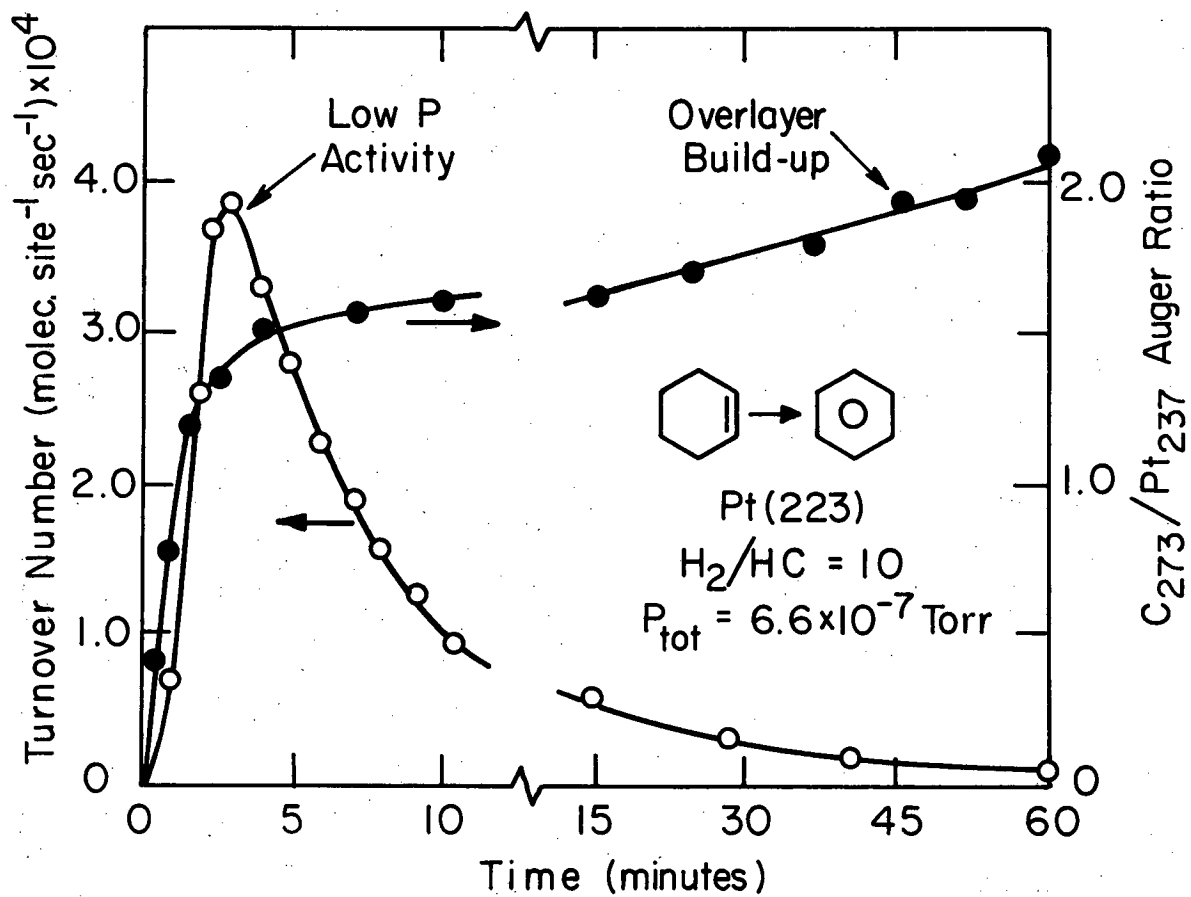


XBL 798-6750

Fig.2

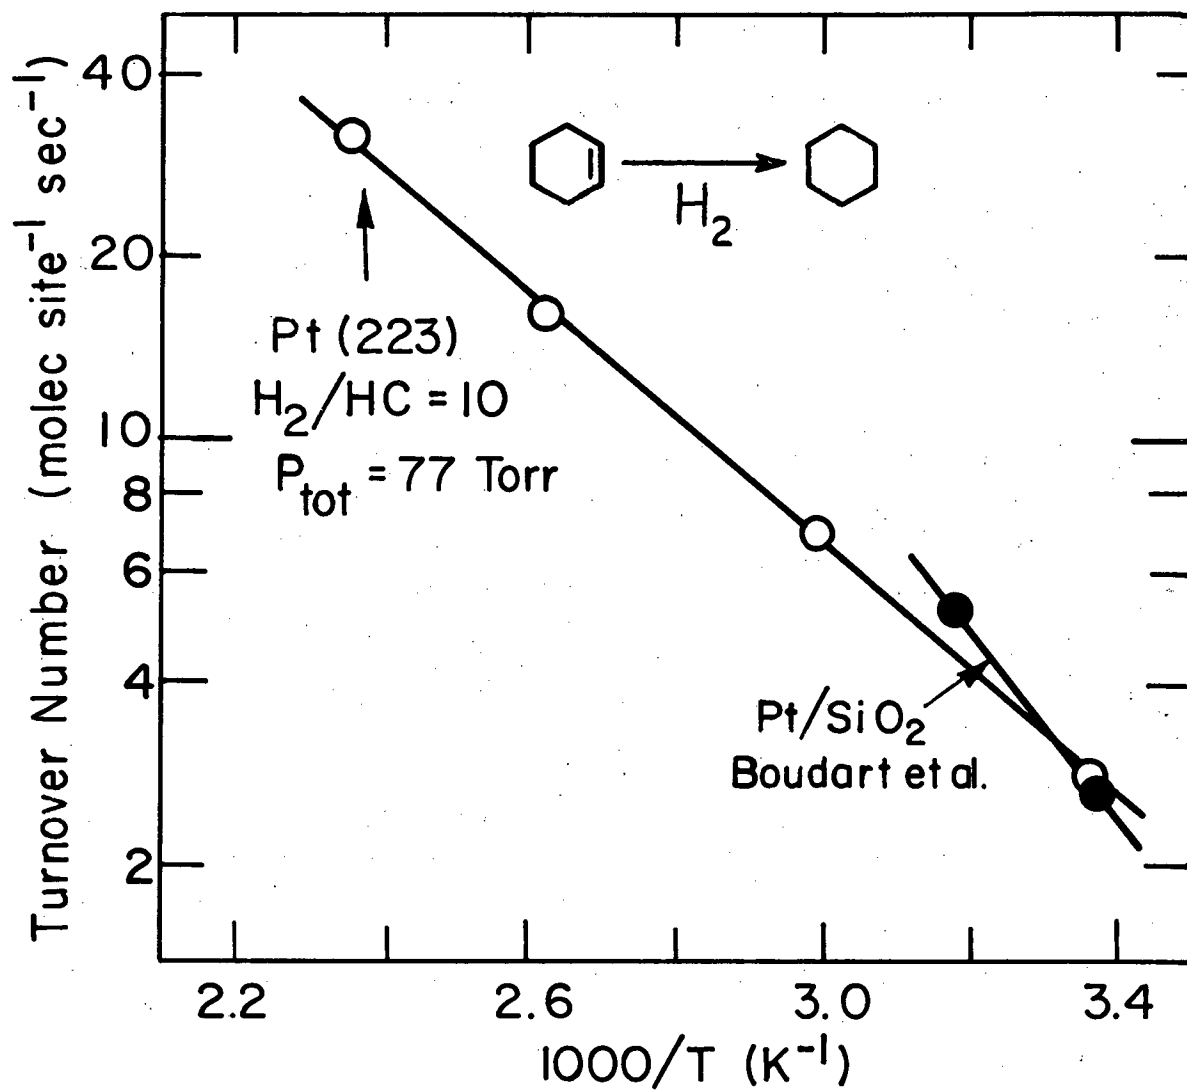

XBL797-6699

Fig.3

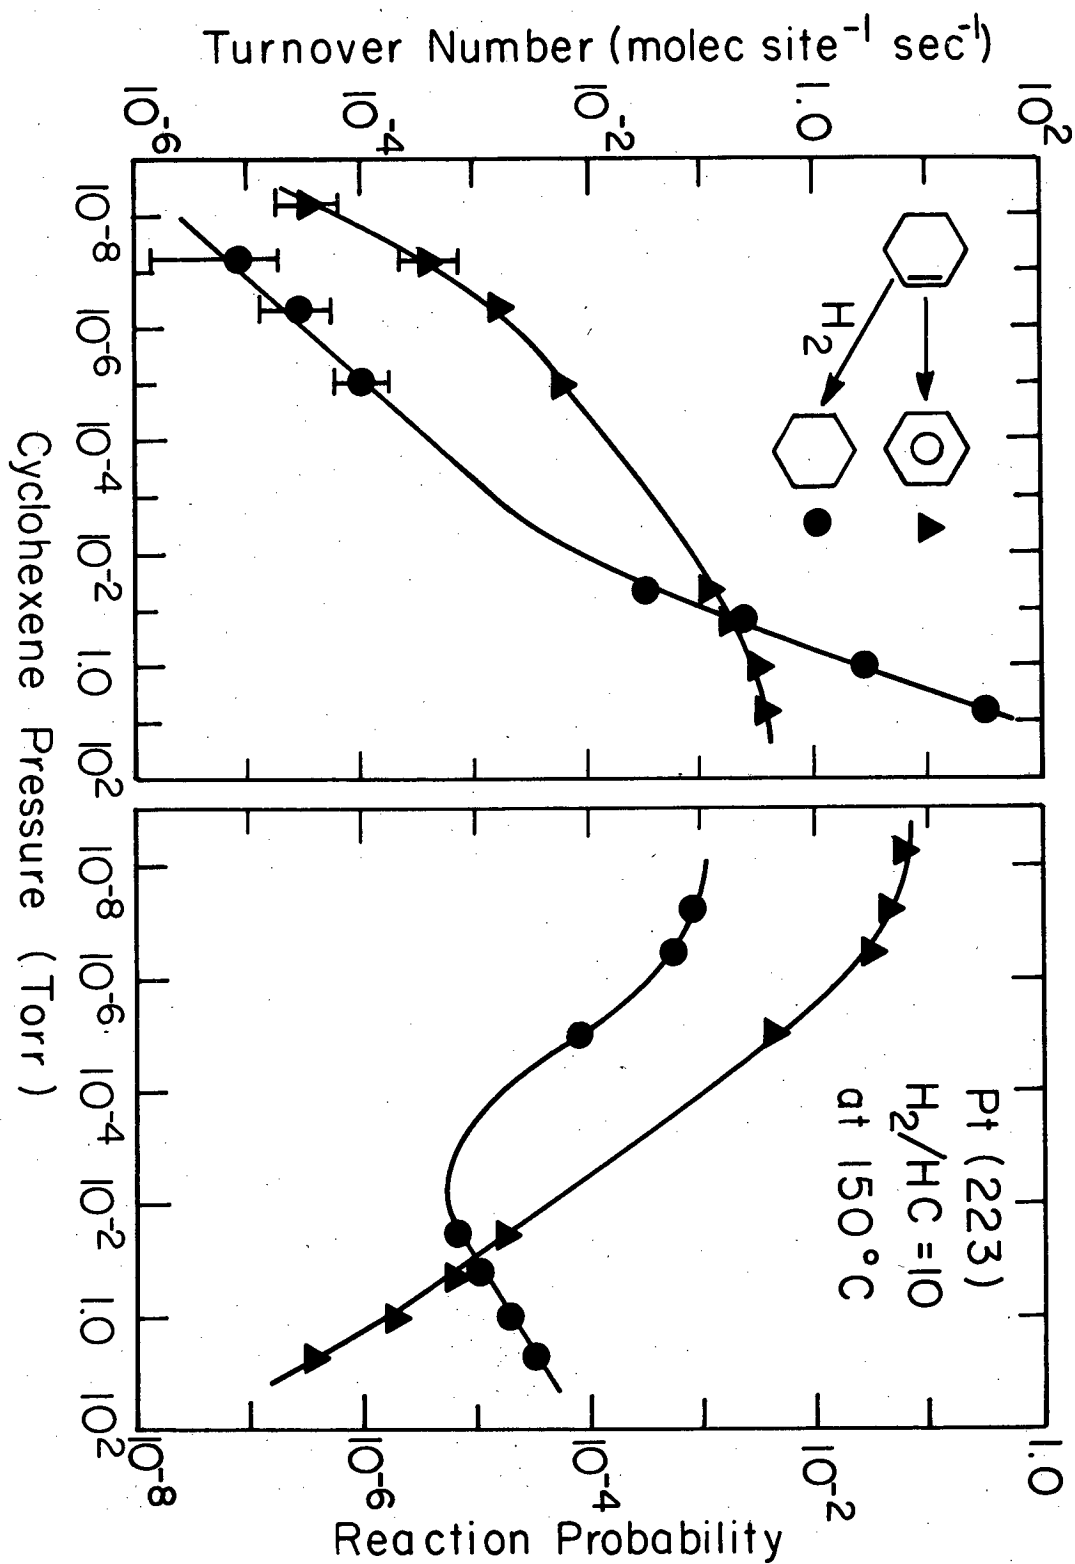

XBL 797-6698

Fig.4

This report was done with support from the Department of Energy. Any conclusions or opinions expressed in this report represent solely those of the author(s) and not necessarily those of The Regents of the University of California, the Lawrence Berkeley Laboratory or the Department of Energy.

Reference to a company or product name does not imply approval or recommendation of the product by the University of California or the U.S. Department of Energy to the exclusion of others that may be suitable.

TECHNICAL INFORMATION DEPARTMENT  
LAWRENCE BERKELEY LABORATORY  
UNIVERSITY OF CALIFORNIA  
BERKELEY, CALIFORNIA 94720