

Lawrence Berkeley National Laboratory

LBL Publications

Title

The Source, Origin and Propagation of Quenches Measured in Superconducting Dipole Magnets

Permalink

<https://escholarship.org/uc/item/0v4202jr>

Authors

Caspi, S

Hassenzahl, W V

Publication Date

1982-11-01

e.2



Lawrence Berkeley Laboratory

UNIVERSITY OF CALIFORNIA

RECEIVED
LAWRENCE

BERKELEY LABORATORY

Accelerator & Fusion Research Division

FEB 18 1983

LIBRARY AND
DOCUMENTS SECTION

Presented at the 1982 Applied Superconductivity Conference, Knoxville, TN, November 28-December 3, 1982; and to be published in the Proceedings


THE SOURCE, ORIGIN AND PROPAGATION OF QUENCHES MEASURED IN SUPERCONDUCTING DIPOLE MAGNETS

S. Caspi and W.V. Hassenzahl

November 1982

TWO-WEEK LOAN COPY

This is a Library Circulating Copy which may be borrowed for two weeks. For a personal retention copy, call Tech. Info. Division, Ext. 6782.

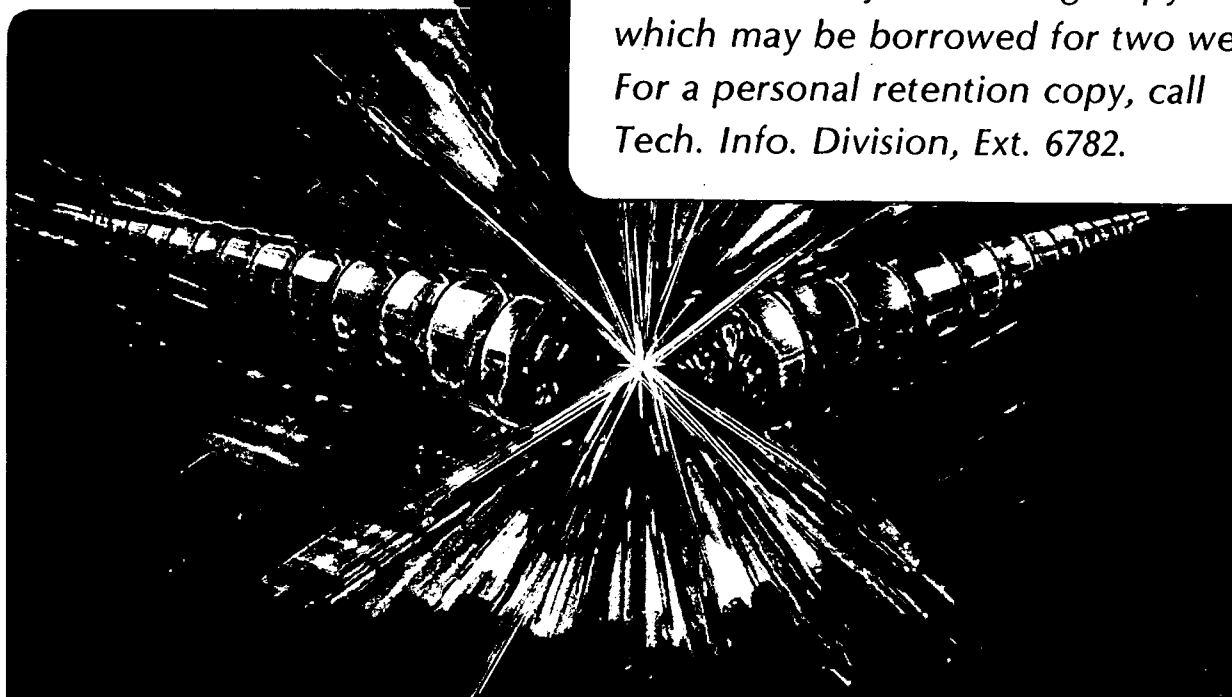

LBL-14390
e.2

DISCLAIMER

This document was prepared as an account of work sponsored by the United States Government. While this document is believed to contain correct information, neither the United States Government nor any agency thereof, nor the Regents of the University of California, nor any of their employees, makes any warranty, express or implied, or assumes any legal responsibility for the accuracy, completeness, or usefulness of any information, apparatus, product, or process disclosed, or represents that its use would not infringe privately owned rights. Reference herein to any specific commercial product, process, or service by its trade name, trademark, manufacturer, or otherwise, does not necessarily constitute or imply its endorsement, recommendation, or favoring by the United States Government or any agency thereof, or the Regents of the University of California. The views and opinions of authors expressed herein do not necessarily state or reflect those of the United States Government or any agency thereof or the Regents of the University of California.

THE SOURCE, ORIGIN AND PROPAGATION OF QUENCHES MEASURED
IN SUPERCONDUCTING DIPOLE MAGNETS*

S. Caspi and W. V. Hassenzahl

November 1982

Accelerator and Fusion Research Division
Lawrence Berkeley Laboratory
University of California
Berkeley, California 94720

*This work was supported by the Director, Office of Energy Research, Office of High Energy and Nuclear Physics, High Energy Physics Division, U. S. Dept. of Energy, under Contract No. DE-AC03-76SF00098.

of the 1st layer. The highest field in the D-7H coil is in the innermost turn of the inner layer at the end of the coil. The retaining rings in both cases are tapered on the inside and slip over collets to provide a circumferential compressive load on the windings. The magnitude of the loads were chosen to ensure compression in the coil at all operating levels. There is some evidence that in D-8A the inner layer was not under compression at the highest operating currents.

Quenches in the Coils

A total of approximately 200 quenches were observed in the dipoles described above. The voltages across various coil sections were recorded by a data acquisition system and permanently stored for later analysis. A typical quench in the D-8A magnet is shown in Figs. 2a, 2b and 2c. In Fig. 2a the measured voltage across the three inner turns of the north pole is plotted as a function of time. The ordinate, which has units of Ohms, is the measured voltage divided by the quench current, 3100A. A voltage spike, which is ascribed to conductor motion, is followed by a resistive rise as the quench propagates through the coil.

The structure in the resistive rise can be attributed to three effects. The first is axial propagation of the normal region along the conductor in the straight sections. The second is propagation around the ends, and the third is propagation from turn to turn. (No layer-to-layer propagation was detected prior to enabling the energy extraction circuit.)

The electrical response of the inner turn of the south pole, which remained superconducting, is shown in Fig. 2b. A quiescent period before the initiating voltage spike is followed by a rather noisy period.

Figure 2c shows the raw acoustic emission signal during a quench from a sensor on one of the end rings. The signal is quiescent until the voltage spike of Fig. 2a. At that time a large acoustic burst is observed. This burst is followed by a noisy period that extends beyond the record and probably until well after the current has been reduced to zero by the external protection circuit.

The progression of the quench can be observed in greater detail by looking at short sections of the coil. Figure 3 shows the voltages across sections of the innermost turns of D-7H during a quench. The quench begins in section 6, at one end of the magnet, and progresses towards both straight sections. The slope of the section 6 signal decreases twice (see arrows A and B), as the normal region propagates past a voltage tap. The final slope shows a resistive rise in the section as a result of heating only.

The resistance of the two adjacent sections, 5 and 7, which was initially zero increases as the normal region propagates into them. Note that the initiation of the resistive rise in these sections corresponds to the inflections in the signal for section 6 (see arrows A and B). Both sections 5 and 7 are observed to be completely normal before the protection circuit is engaged at time = 0, about 38 ms after the quench began.

The locations of most quenches in the two dipoles D-8A and D-7H are shown in Figs. 4a and 4b. Each quench is numbered and enclosed in a box. The quenches in D-8A are almost all in the straight sections, the high field region for this coil. All the

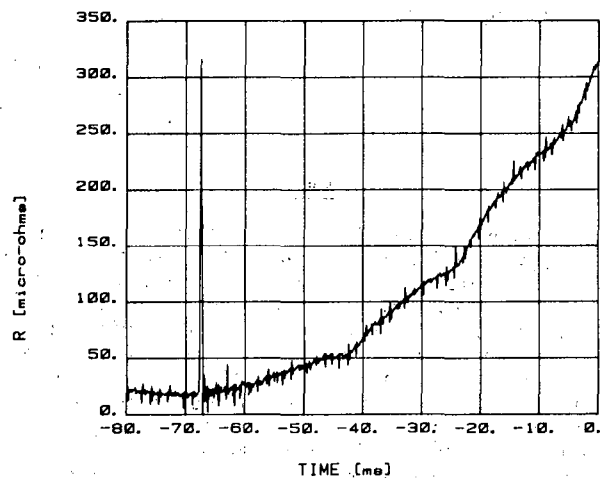


Fig. 2a. Signal observed across a normal going region of the "north pole" of D-8A during a quench.

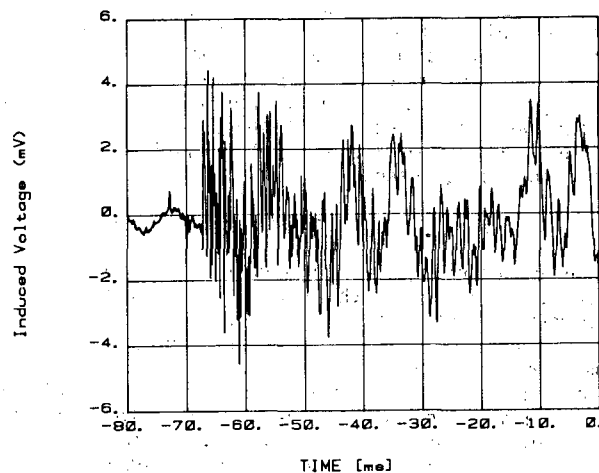


Fig. 2b. Signal observed across the "south" pole of D-8A during the quench shown in Fig. 2a.

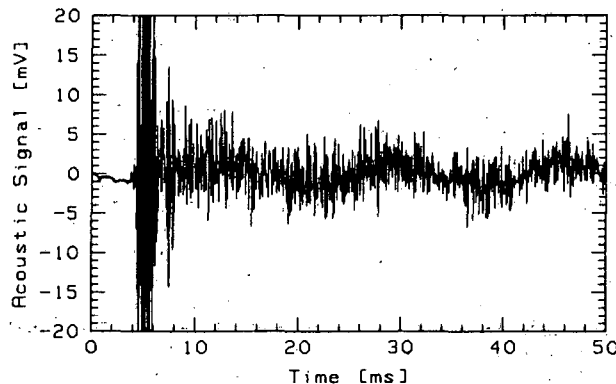


Fig. 2c. Acoustic emission observed during a quench in D-8A.

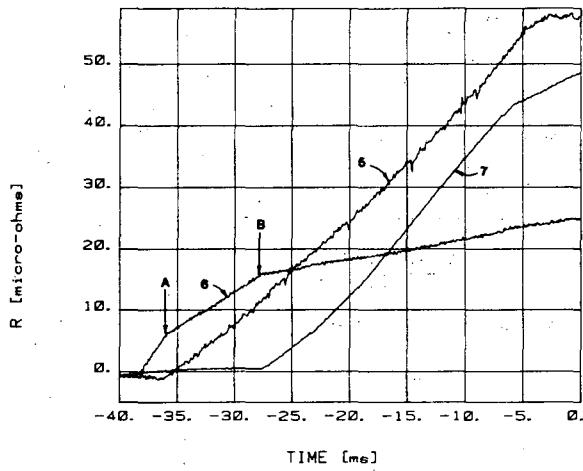


Fig. 3. Normal zone propagation and resistive rise prior to energy extraction. The numbers on the curves correspond to the sections shown in Fig. 4b.

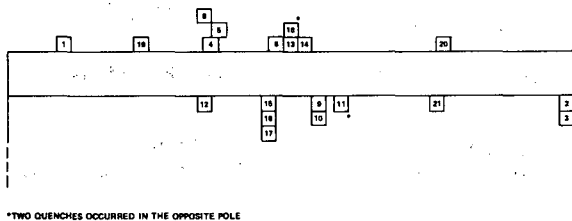


Fig. 4a. Points of quench origin in the innermost turns of the 1st layer of D-8A.

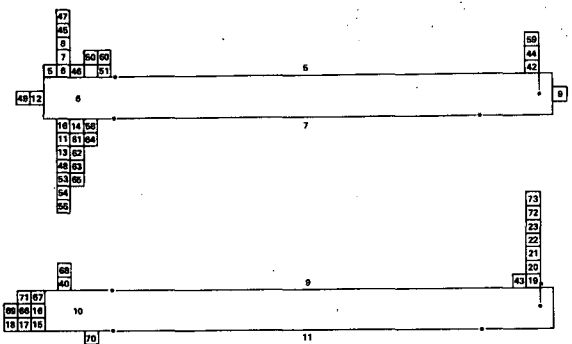


Fig. 4b. Points of quench origin in the inner layer of D-7H. The sequential quench number of these quenches whose origins could be determined precisely are given in the boxes.

quenches in D-7H are at or very near the ends, the high field region.

The voltage response of the coil segments, such as the detailed data of Fig. 3, allows us to calculate the quench propagation velocity. The D-7H magnet was tested in both He I at 4.4 K and He II at 1.8 K and the measured axial quench propagation velocities are shown in Fig. 5a. Velocities between 10 and 70 m/s were observed at both 1.8 and 4.4 K. The limiting value, ~70 m/s, was at a current corresponding almost exactly to the critical current at the bath temperature. Theoretically the velocity

should be infinite at the critical current. However, in this coil the fields in the straight sections, where the velocity was measured are about 10% below those at the ends where the quenches start. The measured quench velocities are plotted in Fig. 5b as a function of the ratio of critical current. The velocities in He I and He II nearly overlap when plotted this way.

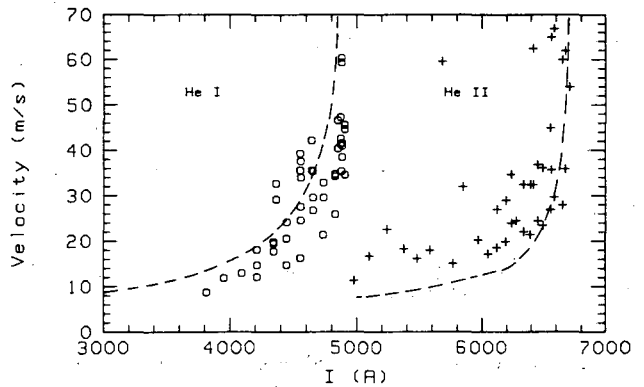


Fig. 5a. Axial quench propagation velocity in D-7H as a function of quench current. The dashed lines are calculated with the program QUENCH.

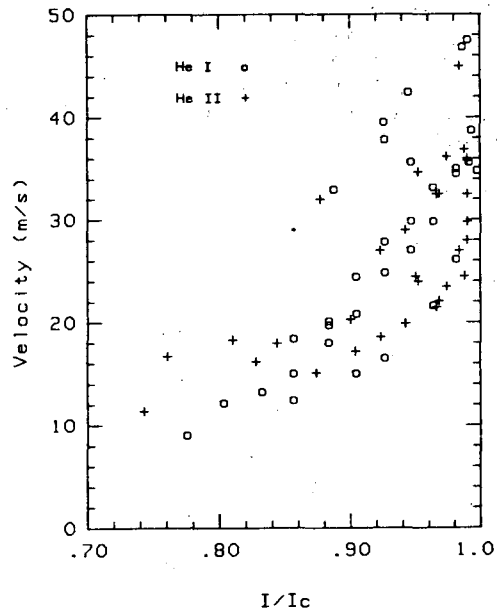


Fig. 5b. Axial quench propagation velocities in D-7H as a function of normalized quench current, quench current divided by short sample current.

The dashed curves of velocities in Fig. 5a were calculated using the program QUENCH with the actual conductor and coil geometry. The calculated velocities depend on the quantity of helium in the conductor cross section. The curves shown in Fig. 5a, which seem to fit the data are based on 3% helium in the conductor cross section, which is within the range of our estimate based on conductor and insulation compaction.

The maximum temperatures in the D-8A coil calculated by the program QUENCH are shown in Fig. 6

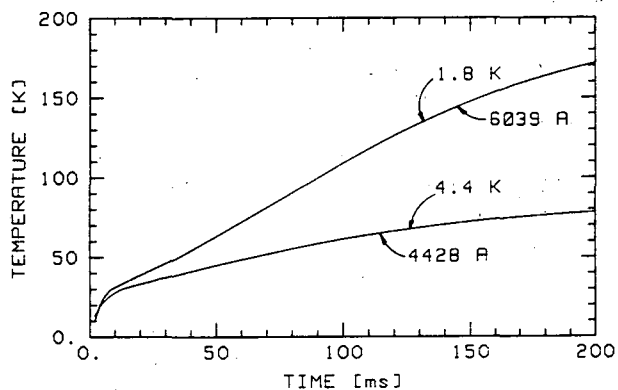


Fig. 6. Temperature response during a quench calculated using the program QUENCH.

for quenches at 90% of critical current. The initial shape of the curve, which appears to have some inflection depends strongly on the helium specific heat, which is assumed to be effectively zero above 20 K. The final temperature, however, is almost independent of the helium contribution.

The turn-to-turn quench propagation is shown in Fig. 7. The time to propagate to the second turn correspond to velocities that are about a factor of 200 less than the axial velocities. Following Wilson⁵ this corresponds to the transverse thermal conductivity being about 40,000 times less than the axial thermal conductivity.

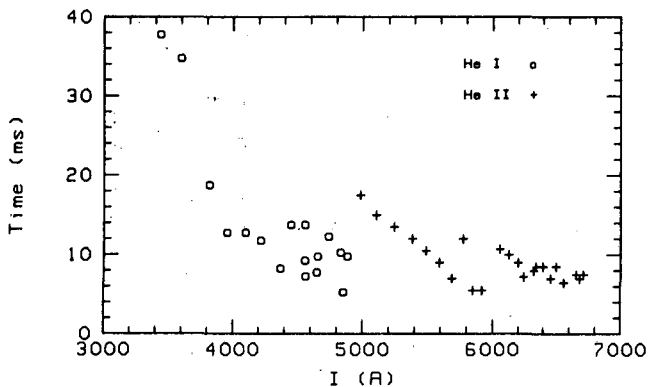


Fig. 7. Transverse quench propagation: transit time from 1st to 2nd turn vs. current.

Quench Initiation

The energy released during the initial voltage spike in some of the quenches in D-8B, a coil that is essentially identical to D-8A except that aluminum rings were used, are presented in Table III. The values of energy indicated are an integral of the product of voltage and current for the duration of the spike and do not reflect any estimate of the distribution of this energy in the coil and the electrical circuit. The quenches in He I were generally triggered by events involving energies about 100 times smaller than those that triggered the quenches in He II. Small disturbances were observed to cause quenches at 4.4 K both before and after the 1.8 K tests. Thus it is evident that the lower energy

events must have occurred in He II but they did not cause quenches. The resolution of the detection system before quench #28 was too low to determine the energy released in the precursor. Because the apparatus was only capable of monitoring the coil during a quench, nonquench causing events were not monitored and the maximum safe disturbance cannot be determined.

TABLE III: Energy release in a quench causing event in dipole D-8B.

Quench Number	Current (A)	Temperature (K)	Energy (J)
28	3650	1.75	4.5
31	4075	1.75	6.8
32	4194	1.8	5.1
34	4100	1.8	9.8
43	2910	4.4	0.03
45	2878	4.4	0.11

References

1. S. Caspi, "D-8A-Test Results," LBL Internal Report, SUMAG-58, 1981.
2. S. Caspi, "D-7H-Test Results," LBL Report 14796, 1982.
3. W. Hassenzahl, "Quench - Modifications and Documentation," CEN SACLAY Report SUPRA/78-61 CEN, 1978.
4. M. Garber and W. B. Sampson, "Quench Properties of High Current Superconductors," IEEE Trans. Magn. MAG-15, 77, 1981.
5. M. N. Wilson, "Computer Simulation of the Quenching of a Superconducting Magnet," Rutherford High Energy Lab., Report RHEL/M 151.

This report was done with support from the Department of Energy. Any conclusions or opinions expressed in this report represent solely those of the author(s) and not necessarily those of The Regents of the University of California, the Lawrence Berkeley Laboratory or the Department of Energy.

Reference to a company or product name does not imply approval or recommendation of the product by the University of California or the U.S. Department of Energy to the exclusion of others that may be suitable.

TECHNICAL INFORMATION DEPARTMENT
LAWRENCE BERKELEY LABORATORY
UNIVERSITY OF CALIFORNIA
BERKELEY, CALIFORNIA 94720