

Lawrence Berkeley National Laboratory

Recent Work

Title

RELEASE OF VOLATILE FISSION PRODUCTS FROM UO₂

Permalink

<https://escholarship.org/uc/item/1sx7z371>

Author

Prussin, S.G.

Publication Date

1983-10-01

c.2



Lawrence Berkeley Laboratory

UNIVERSITY OF CALIFORNIA

RECEIVED
LAWRENCE

BERKELEY LABORATORY

JAN 17 1984

LIBRARY AND
DOCUMENTS SECTION

Materials & Molecular Research Division

To be presented at the American Nuclear Society
Topical Meeting on Fission Product Behavior and
Source Term Research, Snowbird, UT, July 15-19, 1984


RELEASE OF VOLATILE FISSION PRODUCTS FROM UO₂

S.G. Prussin, D.R. Olander, P. Goubeault, and
D. Bayen

October 1983

TWO-WEEK LOAN COPY

*This is a Library Circulating Copy
which may be borrowed for two weeks.
For a personal retention copy, call
Tech. Info. Division, Ext. 6782.*

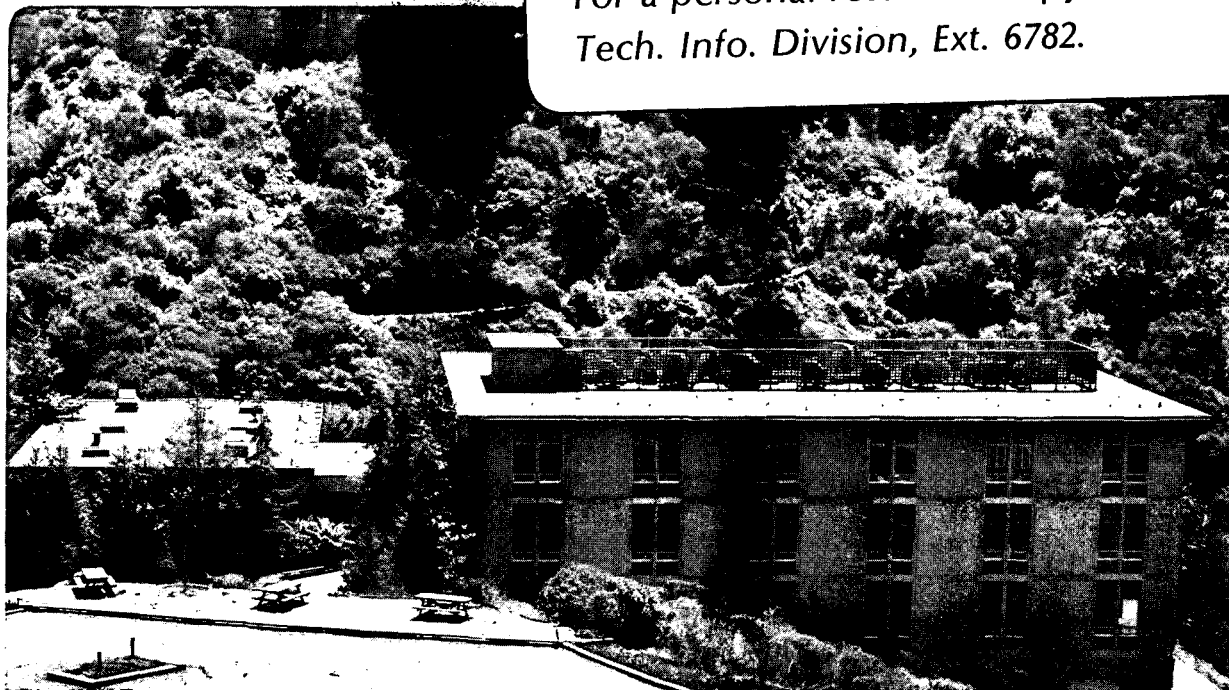

LBL-16893
c.2

DISCLAIMER

This document was prepared as an account of work sponsored by the United States Government. While this document is believed to contain correct information, neither the United States Government nor any agency thereof, nor the Regents of the University of California, nor any of their employees, makes any warranty, express or implied, or assumes any legal responsibility for the accuracy, completeness, or usefulness of any information, apparatus, product, or process disclosed, or represents that its use would not infringe privately owned rights. Reference herein to any specific commercial product, process, or service by its trade name, trademark, manufacturer, or otherwise, does not necessarily constitute or imply its endorsement, recommendation, or favoring by the United States Government or any agency thereof, or the Regents of the University of California. The views and opinions of authors expressed herein do not necessarily state or reflect those of the United States Government or any agency thereof or the Regents of the University of California.

RELEASE OF VOLATILE FISSION PRODUCTS FROM UO_2

By S. G. Prussin, D. R. Olander, P. Goubeault and D. Bayen

Material and Molecular Research Division
Lawrence Berkeley Laboratory, and
Department of Nuclear Engineering
University of California
Berkeley, California

Submitted for presentation at the ANS Topical Meeting on Fission Product Behavior and Source Term Research, Snowbird, Utah, July 1984

This work was supported by the Director, Office of Energy Research, Office of Basic Energy Sciences, Materials Sciences Division of the U.S. Department of Energy under Contract No. DE-AC03-76SF00098.

The diffusion of rare gases in UO_2 has been the subject of a large number of experimental investigations. Lawrence (1) has reviewed the literature through 1977 and has identified variables which appear to exert large effects on the release of rare gases. These include stoichiometry, density and form of the solid, burnup and conditions under which annealing was accomplished (i.e., in vacuum, or in the presence of reactive or inert gases). At 1400°C , the scatter band of the data reviewed by Lawrence covers over four orders of magnitude. By critical assessment of the data, Matzke (2) has estimated the uncertainty in xenon diffusivity at 1400°C at zero burnup as plus-or-minus a factor of ten.

Very few diffusion data exist on iodine and none for cesium or tellurium. Friskney and Turnbull (3) studied in-pile release of iodine and Peehs et al. (4) examined iodine and cesium behavior in post-irradiation anneal experiments. The amount of iodine released from a fuel sample was evaluated by measuring the activity of ^{131}I or ^{133}I trapped by a charcoal filter in ref. 3 or by a liquid-nitrogen cooled surface in ref. 4.

In our experiments, post-irradiation anneal of lightly-irradiated UO_2 was used to measure the release kinetics of the volatile fission products Xe, I, and Te. As the last three are chemically very reactive, it is quite difficult to insure complete collection of material release by means of a gas-sweeping technique. To avoid this difficulty, we measured the fraction of a particular fission product retained in a specimen by gamma-ray spectroscopy before and following an anneal. The method is based on the assumption (proven experimentally) that once released, no fission products return to the specimen. Thus the fractional release is one

minus the fraction retained.

By appropriate selection of reactor irradiation and cooling times, the gamma-ray spectrum obtained with a Ge(Li) detector exhibits well-separated peaks by which each of these fission products can be assayed. Iodine behavior was determined by following the intensity of the 365-keV photopeak from decay of ^{131}I . Xenon removal was obtained from the change in intensity of the 81-keV transition in decay of ^{133}Xe . Tellurium release was followed by measurements of the intensity of the 773-keV photopeak in decay of 2.3-hr ^{132}I after the specimen was allowed to decay sufficiently to attain secular equilibrium with the 78-hr ^{132}Te .

Anneals were conducted in flowing hydrogen at temperatures between 1400 - 1700°C. The water content of the hydrogen was controlled to \sim 100 ppm (monitored by a moisture meter) to assure perfect stoichiometry of the UO_2 . As a test of the reliability of the method, no release of neptunium was detected, as would be expected at these temperatures. Both single crystal and conventional pellet specimens were tested.

The results, which up to now have been interpreted by the Booth equivalent sphere model, indicate that the diffusion coefficient of iodine is about twice as large as that of xenon, and that of tellurium nearly 10 times that of xenon. All three specimens exhibit activation energies of \sim 130 kcal/mole. The result for xenon at 1400°C is 10^{-13} cm^2/s , which is in the middle of the range of most likely values estimated by Matzke(2). The iodine diffusivities are considerably different from those reported by Friskney and Turnbull(3) obtained by in-pile release tests. They report approximately equal diffusivities of xenon and iodine, and both exhibited very low activation energies. The present data on tellurium is the first diffusivity in UO_2 reported

for this element. Tests for two different annealing periods suggests that the fractional release is proportional to the square root of the annealing time, indicating a diffusional process. Comparison of the data from polycrystal and single crystal specimens gave equivalent sphere radii (in the Booth model) of $200 \pm 100 \mu\text{m}$. This result is considerably larger than the equivalent sphere radius of $\sim 60 \mu\text{m}$ found by Friskney and Turnbull(3), or the grain size in the polycrystalline specimens ($\sim 10 \mu\text{m}$), and suggests restricted grain boundary diffusion. However, release from the polycrystals was always nearly an order of magnitude larger than that from single crystals (after accounting for different surface-to-volume ratios), so it is clear that grain boundaries in UO_2 do not simply act as fission product traps which open up only upon linkage of gas bubbles formed on them. This behavior is assumed in most fuel performance codes (5,6) and while such an approach may be adequate at high burnup, it is clearly inappropriate for short irradiations. For the very short irradiations used here, neither inter- or intragranular bubbles are present. The release kinetics are direct measures of combined lattice-grain boundary diffusional processes.

Current efforts include the measurement of concentration profiles of fission products in annealed slabs of UO_2 . This is accomplished by assay of the intensity of characteristic gamma ray peaks as successive layers (a few tens of microns each) of the specimen are removed by precision grinding. According to the Booth model, no concentration gradient of the diffusing species should be observed over dimensions large compared to the average grain size. However, more physically realistic migration models which include combined grain boundary and lattice diffusion predict

nonuniform concentration profiles. The distribution measurement will thus provide crucial information for modeling the basic release process.

REFERENCES

1. G. T. Lawrence, J. Nucl. Mater., 71 (1978) 195.
2. H. J. Matzke, "Gas Release Mechanisms in UO_2 ", Consultants Symposium on Rare Gases in Metals and Ionic Solids, Harwell, U.,. (1979).
3. C. A. Friskeny, J. A. Turnbull, J. Nucl. Mater., 79 (1979) 184.
4. M. Peehs and G. Kaspar, High Temp.-High Press., to be published.
5. J. Rest, Nucl. Technol. 61 (1983) 33.
6. R. J. White and M. O. Tucker, J. Nucl. Mater. 118 (1983).

This report was done with support from the Department of Energy. Any conclusions or opinions expressed in this report represent solely those of the author(s) and not necessarily those of The Regents of the University of California, the Lawrence Berkeley Laboratory or the Department of Energy.

Reference to a company or product name does not imply approval or recommendation of the product by the University of California or the U.S. Department of Energy to the exclusion of others that may be suitable.

TECHNICAL INFORMATION DEPARTMENT
LAWRENCE BERKELEY LABORATORY
UNIVERSITY OF CALIFORNIA
BERKELEY, CALIFORNIA 94720