

Lawrence Berkeley National Laboratory

LBL Publications

Title

Absence of detectable spin and orbital pumping from Ni to Nb by out-of-plane ferromagnetic resonance

Permalink

<https://escholarship.org/uc/item/1zx3h4wp>

Journal

Applied Physics Letters, 128(5)

ISSN

0003-6951

Authors

Bakare, Omolara A

Street, Galen T

Abdizadeh, Sachli

et al.

Publication Date

2026-02-02

DOI

10.1063/5.0301792

Copyright Information

This work is made available under the terms of a Creative Commons Attribution License, available at <https://creativecommons.org/licenses/by/4.0/>

Peer reviewed

Absence of detectable spin and orbital pumping from Ni to Nb by out-of-plane ferromagnetic resonance

Omola A. Bakare,^{1, a)} Galen T. Street,¹ Sachli Abdizadeh,¹ Rachel E. Maizel,¹ Christoph Klewe,² and Satoru Emori^{1, 3, b)}

¹⁾ *Department of Physics, Virginia Tech, Blacksburg, VA, USA*

²⁾ *Advanced Light Source, Lawrence Berkeley National Laboratory, Berkeley, CA, USA*

³⁾ *Academy of Integrated Science, Virginia Tech, Blacksburg, VA, USA*

(Dated: 16 September 2025)

Excited ferromagnets can pump spin angular momentum, along with possibly orbital angular momentum. Among elemental ferromagnets, Ni has been proposed to exhibit substantial orbital pumping relative to spin pumping. Here, we search for a signature of orbital pumping by Ni, specifically by comparing out-of-plane ferromagnetic resonance in heterostructures without Ni (FeV/Nb) and with Ni (FeV-Ni/Nb). The FeV/Nb series shows a clear increase in Gilbert damping with the Nb sink thickness, attributed to spin pumping from FeV to Nb. Surprisingly, the FeV-Ni/Nb series exhibits no such damping increase, revealing no significant spin or orbital pumping from Ni to Nb. Our results offer a fresh perspective on angular-momentum transfer in Ni-based heterostructures, suggesting that the interpretation of some strong orbitronic effects may require further consideration.

A flow of angular momentum can exert a torque on the magnetization, thereby controlling the digital states of nanomagnetic memories^{1,2}. In addition to the flow of spin angular momentum, recent studies suggest that the flow of orbital angular momentum may play a critical role³⁻⁵. For example, torques due to orbital Hall effects in some metals, such as Ti and Nb, are reportedly an order of magnitude stronger than those due to spin Hall effects⁶⁻¹⁰. However, distinguishing spin- and orbital-current effects is fundamentally a challenge¹¹⁻¹³, hindering the design of spin/orbitronic devices. Coexisting charge-spin conversion processes in nanomagnetic metal heterostructures^{11,12,14-16} further complicate the interpretation of spin/orbital torque experiments.

An alternative approach is to examine spin/orbital *pumping*, which does not introduce any net charge current in the studied heterostructure¹⁷⁻²⁵. A precessing magnetization in the source material, consisting of spin and orbital moments^{23,26}, produces nonequilibrium spin and orbital accumulations at the interface. These accumulations propagate as spin and orbital currents [Fig. 1(a,b)] and ultimately decay in the adjacent sink material. The decays of spin and orbital currents result in an additional loss of nonequilibrium angular momentum from the ferromagnetic source, manifesting as an enhancement of Gilbert damping^{19-21,27}. Thus, the spin or orbital decay (diffusion) length can be deduced from Gilbert damping vs sink thickness^{19-21,27}: the damping first increases with increasing sink thickness as more spin or orbital current decays, and then saturates beyond the diffusion length.

Here, we test the hypothesis, motivated by the

theoretical predictions of Go *et al.*¹⁷, that the ferromagnetic source dictates the nature of spin/orbital pumping. According to Ref. 17, the magnitude of orbital pumping may be only a few percent relative to spin pumping for Fe, but it may exceed 10% for Ni. Hence, we might expect the Gilbert damping enhancement as a function of sink thickness to differ between an Fe-based source [Fig. 1(a,c,e)] and a Ni-based source [Fig. 1(b,d,f)]. Assuming substantial orbital pumping from Ni, if the orbital decay length is much greater than the spin decay length^{9,10,28}, we might observe a gradual increase in Gilbert damping due to orbital pumping over a wide sink thickness range, on top of a sharper increase due to spin pumping [Fig. 1(d)]. On the other hand, if the orbital decay length is much shorter than the spin decay length²⁹⁻³², the observed damping might first increase sharply at small sink thicknesses due to orbital pumping, followed by a more gradual increase due to spin pumping [Fig. 1(f)].

We compare the Gilbert damping of two types of heterostructure, as illustrated in Fig. 1:

1. an Fe₇₀V₃₀ source interfaced with a Nb sink (FeV/Nb);
2. a bilayer source of Fe₇₀V₃₀ and Ni, with Ni interfaced with a Nb sink (FeV-Ni/Nb).

Instead of elemental Fe, we chose Fe₇₀V₃₀ with a reduced saturation magnetization^{33,34} to facilitate reliable quantification of spin/orbital pumping with out-of-plane ferromagnetic resonance (FMR)^{20,21}. A single-layer source of Ni with high intrinsic Gilbert damping (damping parameter ~ 0.03) would obscure small damping enhancements from pumping³⁵. As such, we instead chose FeV-Ni, in which thin Ni is exchange-coupled to low-damping FeV, ensuring a large FMR signal-to-noise ratio^{33,34} and precise quantification of damping enhancements from the Ni/Nb

^{a)} Electronic mail: obakare@vt.edu

^{b)} Electronic mail: semori@vt.edu

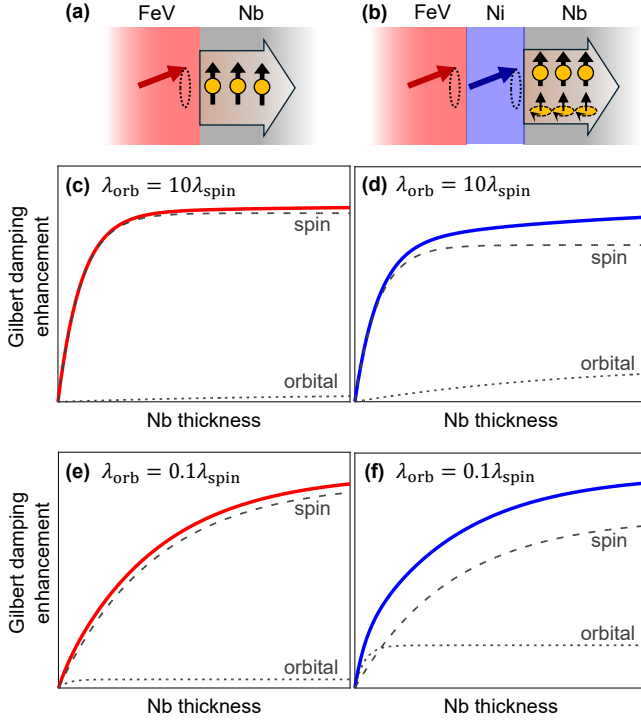


FIG. 1. (a,d) Schematics of heterostructures with different sources of pumping: (a) FeV hypothesized with predominantly spin pumping; (b) Ni (coherently coupled to FeV) hypothesized with sizable orbital pumping relative to spin pumping. (c-f) Hypothesized schematics of Gilbert damping enhancement vs Nb sink thickness where: (c,d) the orbital diffusion length λ_{orb} is an order of magnitude greater than the spin diffusion length λ_{spin} with the (c) FeV source and (d) Ni source; (e,f) λ_{orb} is an order of magnitude less than λ_{spin} with the (e) FeV source and (f) Ni source.

interface. Nb has attracted much attention for its potentially large orbital Hall effect^{6,8,36}, such that it is an interesting prototypical metal for investigating spin/orbital transport. Our study focuses on Nb as the sink instead of Ti (another interesting metal in orbitronics^{9,10}) because Nb has a lower reactivity with residual gases in the deposition chamber.

In this letter, we demonstrate that the observed behavior for FeV/Nb is consistent with the hypothesized predominance of spin pumping. Surprisingly, our observation for FeV-Ni/Nb completely deviates from our hypothesis [Fig. 1(b,d,f)]; we find no resolvable signature of spin or orbital pumping in FeV-Ni/Nb, as the Gilbert damping enhancement remains essentially zero. Our findings imply minimal angular momentum transport between Ni and Nb, e.g., an order of magnitude smaller than between FeV and Nb, pointing to the need to re-examine reports of robust orbital transport in Ni/Nb and similar metal heterostructures.

All samples were deposited by magnetron sputtering on Si substrates with 50-nm-thick thermally grown SiO_2 , unless otherwise noted. The base pressure before

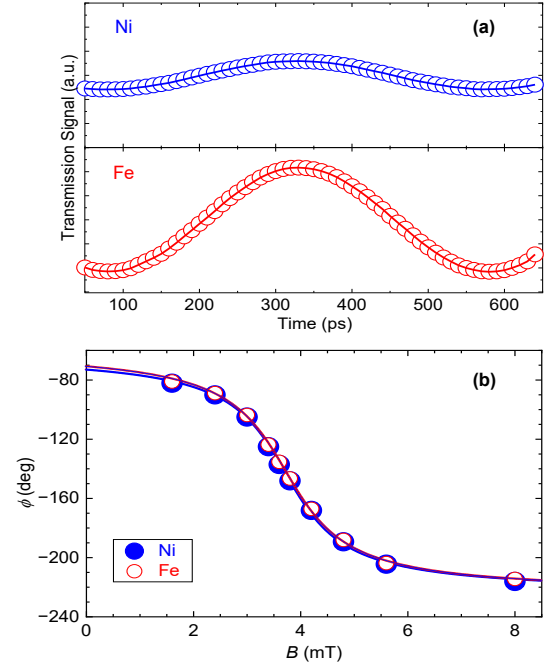


FIG. 2. (a) Time traces of XFMR signals acquired at 2 GHz under an in-plane applied field of 3.7 mT and (b) field dependence of the precessional phase ϕ at the Ni and Fe L_3 edges in FeV-Ni ($t_{\text{Nb}} = 0$).

deposition was $\lesssim 8 \times 10^{-8}$ Torr. The Ar sputtering gas pressure was 3 mTorr. The FeV/Nb series has the stack structure of substrate / Ti(3) / Cu(3) / $\text{Fe}_{70}\text{V}_{30}$ (20) / Nb(t_{Nb}) / TiO_x (3), where the values in parentheses denote thicknesses in nm. The Nb thickness t_{Nb} varies from 0 to 40 nm. The Ti/Cu seed layer enables smooth textured growth of the subsequent polycrystalline film layers, yielding narrower FMR linewidths (higher signal-to-noise ratios)³⁷. The TiO_x capping layer (naturally oxidized, passivated Ti upon exposure to ambient air) protects the underlying layers from oxidation.

The FeV-Ni/Nb series has the same stack structure as FeV/Nb, except that 4-nm-thick Ni is inserted between FeV and Nb. The Ni thickness of 4 nm was chosen to be greater than the spin decay length of ≈ 2 -3 nm [Refs. 38, 39] and less than the ferromagnetic exchange length of ≈ 8 nm [Ref. 40]. It is also sufficiently thick for the layer-resolved x-ray magnetic circular dichroism (XMCD) measurement, detailed below, but still much thinner than the 20-nm-thick FeV layer that dominates the large-signal FMR dynamics.

Verification of the coupling between FeV and Ni under FMR requires a layer-resolved measurement. To this end, we separately acquired time traces of the precessing magnetizations of FeV and Ni through XMCD at Beamline 4.0.2 at the Advanced Light Source. The details of this dynamic XMCD method, also known as x-ray FMR or XFMR, are found in Refs. 41 and 42. In brief, we conducted dynamic XMCD measurements on an FeV-Ni sample with $t_{\text{Nb}} = 0$ nm, grown on Ce-

doped $\text{Y}_3\text{Al}_5\text{O}_{12}$ (YAG) substrates for luminescence yield detection of XMCD⁴³. The signals at the Fe L_3 edge (from FeV) and the Ni L_3 edge were measured under an in-plane applied quasistatic field and a microwave excitation of 2 GHz. The time traces in Fig. 2(a), acquired at the resonance field ($B_{\text{res}} \approx 3.7$ mT), reveal sinusoidal oscillations of the excited Fe and Ni moments with a period of 500 ps. Quick visual inspection suggests that the Fe and Ni precess in phase, consistent with the coherent coupling of the magnetizations in FeV and Ni. We fit the B dependence of the precessional phase ϕ [Fig. 2(b)] with $\phi = \phi_0 + \arctan(\Delta B/(B - B_{\text{res}}))$. The baseline phases ϕ_0 for Fe and Ni are within $\approx 1^\circ$ of each other, which can be accounted for by the 3-ps timing jitter of the master oscillator of the beamline. The deviation between Fe and Ni for the obtained FMR linewidth ΔB and resonance field B_{res} are also within the field reading uncertainty of ± 0.2 mT at the beamline.

Thus, our quantitative dynamic XMCD results confirm rigid coupling between resonantly excited magnetizations of the FeV and Ni layers. This is reasonable considering the direct interface between the FeV and Ni layers, along with the 4-nm Ni layer thickness under the ferromagnetic exchange length of ≈ 8 nm [Ref. 40]. While this measurement was performed in the in-plane geometry due to experimental constraints, we expect this strong ferromagnetic exchange to enforce coherent precession in the out-of-plane FMR geometry as well. This is because the ferromagnetic exchange interaction, which is the primary mechanism for this coupling, is isotropic and does not depend on the direction of the applied field.

Spin/orbital pumping occurs across the interface between the source and the sink. Therefore, in FeV-Ni/Nb, pumping into Nb must originate from the magnetization dynamics of Ni in direct contact with Nb, rather than the dynamics of FeV away from Nb. Any spin current pumped from FeV largely decays within the first ≈ 2 -3 nm of Ni^{38,39}, rather than propagating through the 4-nm-thick Ni layer. Orbital transport from FeV through Ni is less clear, but orbital pumping by FeV is plausibly just a few percent relative to spin pumping¹⁷ and can be neglected.

We evaluate our hypothesis that FeV-Ni/Nb could display substantial orbital pumping from Ni to Nb, distinct from FeV/Nb with limited orbital pumping. For this purpose, we conducted broadband FMR spectroscopy, using a flip-chip coplanar-waveguide setup with the quasistatic field applied *out of the film plane*. Crucially, this out-of-plane configuration eliminates extrinsic non-Gilbert two-magnon relaxation⁴⁴, thereby enabling reliable quantification of the Gilbert damping parameter^{20,21} emerging from spin/orbital pumping. Our electromagnet with a maximum field of 2 T is sufficient to saturate FeV(-Ni), with a demagnetizing field of $\mu_0 M_s \approx 1.1$ T, completely out of plane. Each FMR spectrum is fit with a Lorentzian derivative to extract the resonance field B_{res} and the half-width-at-half-maximum FMR linewidth ΔB [Refs. 33, 38].

The slope of ΔB vs f [Fig. 3(a,c)] permits straightforward quantification of the Gilbert damping parameter α via

$$\Delta B = \Delta B_0 + \frac{h}{g\mu_B} \alpha f, \quad (1)$$

where h is Planck's constant, $g \approx 2.1$ is the g -factor (derived from the f dependence of B_{res} as shown in the Supplementary Material), and μ_B is the Bohr magneton. The zero frequency linewidth ΔB_0 , capturing the broadening of the FMR linewidth from magnetic inhomogeneity⁴⁵, is $\Delta B_0 = 0.06$ mT for FeV/Nb and 0.2 mT for FeV-Ni/Nb. We apply Eq. 1 to data at $f \geq 10$ GHz to quantify α . Below 10 GHz (or $B \lesssim 1.4$ T), ΔB exhibits a slightly shallower slope with decreasing f due to incomplete saturation; our analysis in the Supplementary Material presents fits accounting for the nonlinearity of these low-frequency data points, which yield α nearly identical to the values in Fig. 3(c,d).

As shown in Fig. 3(a), FeV interfaced with Nb exhibits a noticeably steeper slope in ΔB vs f , i.e., greater Gilbert damping, compared to FeV without Nb. With increasing t_{Nb} , α increases from ≈ 0.0026 at $t_{\text{Nb}} = 0$ to a saturated level of ≈ 0.0032 [Fig. 3(c)]. This trend is consistent with the pumping of angular momentum from the FeV source to the adjacent Nb sink in which the angular momentum decays [Fig. 1(a)].

Further insights can be gained by fitting the t_{Nb} dependence of α with a diffusion model. We remark that no established theoretical model exists yet for orbital diffusion. Nevertheless, since spin pumping likely overwhelmingly dominates over orbital pumping from an Fe-based source¹⁷, we analyze the t_{Nb} thickness dependence of α in FeV/Nb with the spin diffusion model^{21,27},

$$\alpha = \alpha_{\text{no-sink}} + \frac{g\mu_B \hbar}{2e^2 M_s t_M} \left[\frac{1}{G_{\uparrow\downarrow}} + 2\rho_{\text{Nb}} \lambda_d \coth\left(\frac{t_{\text{Nb}}}{\lambda_d}\right) \right]^{-1}, \quad (2)$$

with the saturation magnetization $M_s = 900$ kA/m and the magnetic source thickness $t_M = 20$ nm. The thickness dependent resistivity of Nb is modeled as $\rho_{\text{Nb}} = 1.5 \times 10^{-7} \Omega\text{m} + 1.4 \times 10^{-15} \Omega\text{m}^2/t_{\text{Nb}}$ [Ref. 46]. The free parameters of the fit here are the spin-mixing conductance $G_{\uparrow\downarrow}$ and the spin diffusion length λ_d . We obtain $G_{\uparrow\downarrow} = (5.8 \pm 2.1) \times 10^{14} \Omega^{-1}\text{m}^{-2}$ ($g_{\uparrow\downarrow} = (h/e^2)G_{\uparrow\downarrow} = 15 \pm 5 \text{ nm}^{-2}$), in line with typical values of ferromagnet/nonmagnetic-metal interfaces^{47,48}; $\lambda_d = 5.5 \pm 1.0$ nm is similar to ≈ 3 nm [Ref. 8] and ≈ 8 nm [Ref. 20] reported by others.

We also evaluate the *effective* spin-mixing conductance $G_{\text{eff}}^{\uparrow\downarrow}$, which is directly proportional to the saturated Gilbert damping enhancement $\Delta\alpha$, as given by^{19,47}

$$G_{\text{eff}}^{\uparrow\downarrow} = \frac{2e^2 M_s t_M}{g\mu_B \hbar} \Delta\alpha. \quad (3)$$

FeV/Nb exhibits $\Delta\alpha \approx 0.0006$, corresponding to an effective spin-mixing conductance of $G_{\text{eff}}^{\uparrow\downarrow} \approx 3 \times 10^{14}$

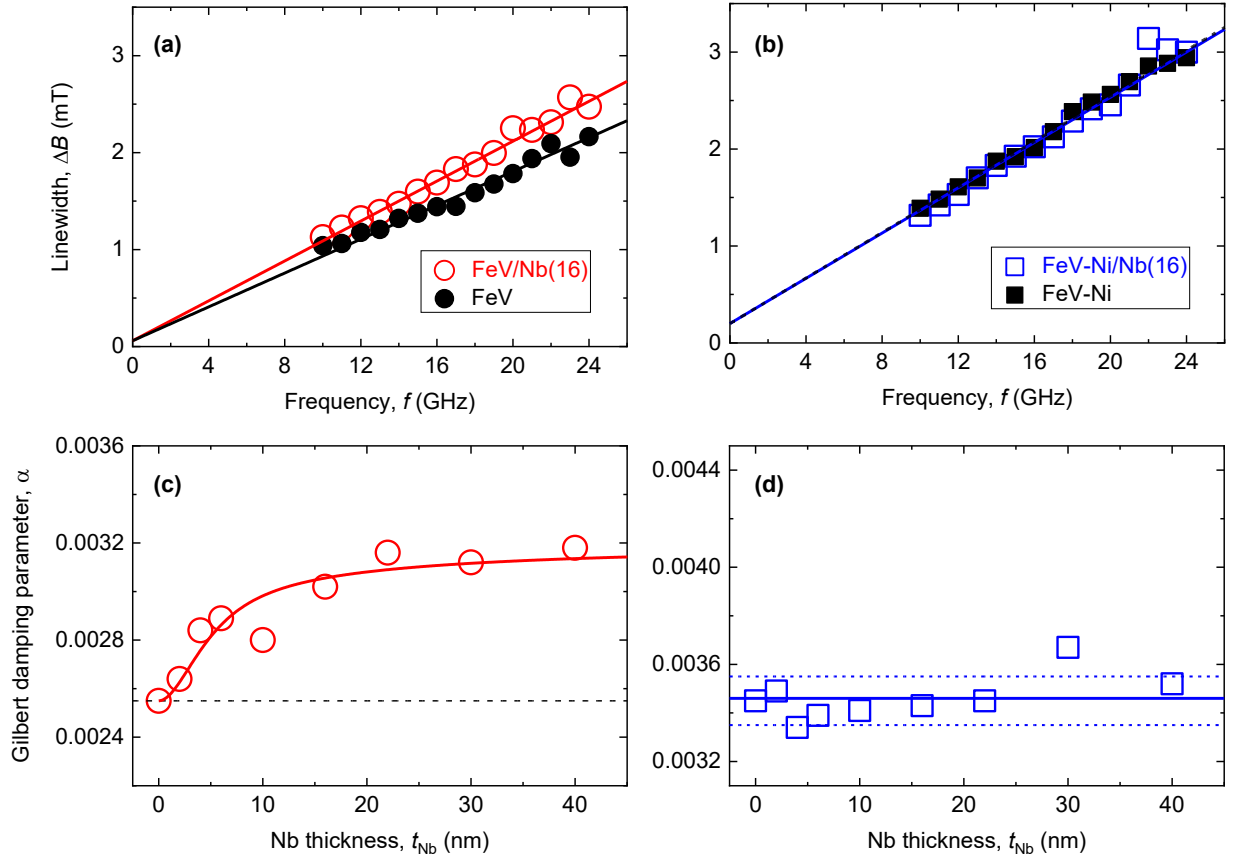


FIG. 3. (a,b) Half-width-at-half-maximum FMR linewidth ΔB as a function of frequency f for (a) FeV/Nb and (b) FeV-Ni/Nb, measured with the samples magnetized out-of-plane. The linear fits are used to quantify the Gilbert damping parameter α with Eq. 1. (c,d) Gilbert damping parameter α plotted against the Nb thickness for (c) FeV/Nb and (d) FeV-Ni/Nb. The horizontal dashed line in (c) denotes $\alpha_{\text{no-sink}}$ for FeV ($t_{\text{Nb}} = 0$). In (d), the solid line denotes the average value of α over all FeV-Ni/Nb samples, whereas the dashed lines denote the standard deviation.

$\Omega^{-1}\text{m}^{-2}$ ($g_{\text{eff}}^{\uparrow\downarrow} \approx 7 \text{ nm}^{-2}$). These values are again in line with reasonable values for ferromagnet/normal-metal interfaces⁴⁷. Overall, the conventional framework of spin pumping (e.g., Eqs. 2 and 3) reasonably captures our experimental results for FeV/Nb.

The observed trend for FeV-Ni/Nb is qualitatively different, as seen in Fig. 3(b,d), which constitutes the key results of our work. FeV-Ni with and without a Nb layer exhibit nearly identical slopes in ΔB vs f [Fig. 3(b)]. As summarized in Fig. 3(d), the Gilbert damping parameter of FeV-Ni/Nb remains essentially constant with t_{Nb} : FeV-Ni with no Nb exhibits $\alpha_{\text{no-sink}} \approx 0.0035$, and α remains at that value within the scatter of ± 0.0001 for all FeV-Ni/Nb samples. This lack of detectable enhancement of α with the addition of Nb indicates no significant pumping from Ni to Nb.

As confirmed by our dynamic XMCD experiment [Fig. 2], FeV and Ni magnetizations precess together coherently. Therefore, Ni is not just a passive sink of angular momentum, but also an active source that can pump angular momentum into adjacent layers. The constant damping parameter of $\alpha = 0.0035 \pm 0.0001$ for

FeV-Ni/Nb, about 35% higher than that of FeV, may be due to mutual angular momentum pumping between ferromagnetic FeV and Ni⁴⁹. The origin of this t_{Nb} -independent elevated damping in FeV-Ni remains the subject of a future study.

The key finding here is that spin/orbital pumping from Ni to Nb is so small that it is below our present detection limit. We take the scatter in α of 0.0001 to be the upper limit of $\Delta\alpha$ for FeV-Ni/Nb. With $t_{\text{M}} = 24 \text{ nm}$ and $M_{\text{s}} = 870 \text{ kA/m}$ in Eq. 3, the effective mixing conductance at the Ni/Nb interface would be $G_{\text{eff}}^{\uparrow\downarrow} < 0.5 \times 10^{14} \Omega^{-1}\text{m}^{-2}$ ($g_{\text{eff}}^{\uparrow\downarrow} < 1 \text{ nm}^{-2}$). This estimated angular-momentum transmission across Ni/Nb is an order of magnitude weaker than transmission across FeV/Nb.

The absence of resolvable spin and orbital pumping from Ni to Nb, in contrast to pronounced pumping from FeV to Nb, is a striking finding. It highlights that the composition of the ferromagnetic source can have a dramatic impact on the efficiency of angular-momentum transfer into an adjacent metal. This finding is consistent with early computational predictions that

the matching of electronic band states at the Fermi energy between the ferromagnetic and nonmagnetic metals greatly impacts the strength of spin pumping⁴⁸. It is possible that a significant band mismatch exists at the Ni/Nb interface and suppresses angular-momentum transfer in our samples. However, the extent of the band mismatch at this interface, along with its precise correlation with angular-momentum pumping (or the lack thereof), remains an open question. Further theoretical work is warranted to identify the exact mechanism responsible for the suppression of significant pumping.

Our findings underscore the potential complexity of prior studies that aim to detect angular-momentum transport electrically from lateral voltage signals, which can have coexisting contributions from both the ferromagnetic and nonmagnetic metals^{14–16}. While our Gilbert damping measurements show minimal angular-momentum pumping from Ni to Nb, prior electrical measurements may be influenced by other coexisting phenomena. For example, electrically detected pumping can include signals like rectification, thermoelectric effects, and inverse spin-Hall signals originating from within the ferromagnet itself^{50–52}, potentially augmented by asymmetric interfaces^{53,54}. Similarly, electrically detected torque measurements can be influenced by “self-torques” generated inside the ferromagnet with asymmetric interfacial and bulk properties^{54–56}. In general, disentangling angular-momentum transfer between the two materials from other coexisting effects is challenging with these voltage detection methods.

Our method here monitors angular-momentum dissipation through Gilbert damping in the out-of-plane FMR configuration. It does not rely on lateral voltage measurements, so it is free of complications that hamper electrically detected pumping and torque measurements. Our approach may provide a complementary – and potentially more reliable – view of angular-momentum transport in magnetic heterostructures. While we did not find significant orbital pumping in Ni/Nb, we do not universally rule out the existence of orbital pumping in other systems. Critical insights into orbital pumping may be gained through future studies that quantify Gilbert damping enhancement with high precision, particularly in heterostructures with ferromagnetic sources possessing different spin/orbital characteristics.

In summary, we have attempted to find a signature of orbital pumping from Ni to Nb. Specifically, we have compared FMR results of heterostructures without Ni (FeV/Nb) and with Ni (FeV-Ni/Nb). The FeV and Ni magnetizations in FeV-Ni are confirmed to be coupled coherently, boosting the precession amplitude of Ni for spin/orbital pumping. Out-of-plane broadband FMR measurements allow for straightforward quantification of Gilbert damping. We observe an increase and saturation of damping with Nb thickness in FeV/Nb, which is consistent with spin pumping from FeV to

Nb. However, no detectable change in damping is observed for FeV-Ni/Nb. This surprising observation implies minimal spin and orbital pumping from Ni to Nb. The absence of detectable pumping here suggests the need to reconsider angular momentum transport in heterostructures consisting of Ni interfaced with Nb (and perhaps other similar transition metals). While our study does not rule out orbital pumping in general, it highlights the current challenge in uncovering this phenomenon in metallic multilayers.

Supplementary Material: The Supplementary Material presents the quantification of the g -factor and different protocols of fitting the frequency dependence of the out-of-plane FMR linewidth.

ACKNOWLEDGMENTS

O.A.B., R.E.M, and S.E. were supported by the National Science Foundation (NSF) under Grant No. ECCS-2144333. G.T.S. and S.A.K. were supported by the NSF under Grant No. ECCS-2236160. This research used resources of the Advanced Light Source, a U.S. DOE Office of Science User Facility under Contract No. DE-AC02-05CH11231. SE also thanks support by the Luther and Alice Hamlett Junior Faculty Fellowship.

DATA AVAILABILITY

The data that support the findings of this study are available from the corresponding authors upon reasonable request.

- ¹A. Brataas, A. D. Kent, and H. Ohno, *Nature Materials* **11**, 372 (2012).
- ²A. Manchon, J. Železný, I. M. Miron, T. Jungwirth, J. Sinova, A. Thiaville, K. Garello, and P. Gambardella, *Review of Modern Physics* **91**, 035004 (2019).
- ³D. Go, D. Jo, H.-W. Lee, M. Kläui, and Y. Mokrousov, *Europhysics Letters* **135**, 37001 (2021).
- ⁴P. Wang, F. Chen, Y. Yang, S. Hu, Y. Li, W. Wang, D. Zhang, and Y. Jiang, *Advanced Electronic Materials*, 2400554 (2024).
- ⁵R. Burgos Atencia, A. Agarwal, and D. Culcer, *Advances in Physics: X* **9**, 2371972 (2024).
- ⁶S. Dutta and A. A. Tulapurkar, *Physical Review B* **106**, 184406 (2022).
- ⁷A. Bose, F. Kammerbauer, R. Gupta, D. Go, Y. Mokrousov, G. Jakob, and M. Kläui, *Physical Review B* **107**, 134423 (2023).
- ⁸F. Liu, B. Liang, J. Xu, C. Jia, and C. Jiang, *Physical Review B* **107**, 054404 (2023).
- ⁹H. Hayashi, D. Jo, D. Go, T. Gao, S. Haku, Y. Mokrousov, H.-W. Lee, and K. Ando, *Communications Physics* **6**, 32 (2023).
- ¹⁰Y.-G. Choi, D. Jo, K.-H. Ko, D. Go, K.-H. Kim, H. G. Park, C. Kim, B.-C. Min, G.-M. Choi, and H.-W. Lee, *Nature* **619**, 52 (2023).
- ¹¹D. Lee, D. Go, H.-J. Park, W. Jeong, H.-W. Ko, D. Yun, D. Jo, S. Lee, G. Go, J. H. Oh, *et al.*, *Nature Communications* **12**, 6710 (2021).
- ¹²G. Sala and P. Gambardella, *Physical Review Research* **4**, 033037 (2022).
- ¹³S. Han, H.-W. Ko, J. H. Oh, H.-W. Lee, K.-J. Lee, and K.-W. Kim, *Physical Review Letters* **134**, 036305 (2025).

- ¹⁴A. Davidson, V. P. Amin, W. S. Aljuaid, P. M. Haney, and X. Fan, *Physics Letters A* **384**, 126228 (2020).
- ¹⁵D. Go, F. Freimuth, J.-P. Hanke, F. Xue, O. Gomonay, K.-J. Lee, S. Blügel, P. M. Haney, H.-W. Lee, and Y. Mokrousov, *Physical Review Research* **2**, 033401 (2020).
- ¹⁶K.-W. Kim, B.-G. Park, and K.-J. Lee, *npj Spintronics* **2**, 8 (2024).
- ¹⁷D. Go, K. Ando, A. Pezo, S. Blügel, A. Manchon, and Y. Mokrousov, *Physical Review B* **111**, L140409 (2025).
- ¹⁸A. Pezo, D. Go, Y. Mokrousov, H. Jaffrès, and A. Manchon, *Physical Review B* **111**, 134424 (2025).
- ¹⁹Y. Tserkovnyak, A. Brataas, G. E. Bauer, and B. I. Halperin, *Reviews of Modern Physics* **77**, 1375 (2005).
- ²⁰C. T. Boone, H. T. Nembach, J. M. Shaw, and T. J. Silva, *Journal of Applied Physics* **113**, 153906 (2013).
- ²¹C. T. Boone, J. M. Shaw, H. T. Nembach, and T. J. Silva, *Journal of Applied Physics* **117**, 223910 (2015).
- ²²E. Santos, J. Abrão, D. Go, L. De Assis, Y. Mokrousov, J. Mendes, and A. Azevedo, *Physical Review Applied* **19**, 014069 (2023).
- ²³S. Ding, H. Wang, W. Legrand, P. Noël, and P. Gambardella, *Nano Letters* **24**, 10251 (2024).
- ²⁴H. Hayashi, D. Go, S. Haku, Y. Mokrousov, and K. Ando, *Nature Electronics* **7**, 646 (2024).
- ²⁵H. Wang, M.-G. Kang, D. Petrosyan, S. Ding, R. Schlitz, L. J. Riddiford, W. Legrand, and P. Gambardella, *Physical Review Letters* **134**, 126701 (2025).
- ²⁶S. Emori, R. E. Maizel, G. T. Street, J. L. Jones, D. A. Arena, P. Shafer, and C. Klewe, *Applied Physics Letters* **124**, 122404 (2024).
- ²⁷P. M. Haney, H.-W. Lee, K.-J. Lee, A. Manchon, and M. D. Stiles, *Physical Review B* **87**, 174411 (2013).
- ²⁸I. Lyalin, S. Alikhah, M. Berritta, P. M. Oppeneer, and R. K. Kawakami, *Physical Review Letters* **131**, 156702 (2023).
- ²⁹K. D. Belashchenko, G. G. Baez Flores, W. Fang, A. A. Kovalev, M. van Schilfgaarde, P. M. Haney, and M. D. Stiles, *Physical Review B* **108**, 144433 (2023).
- ³⁰M. Rang and P. J. Kelly, *Physical Review B* **109**, 214427 (2024).
- ³¹S. Urazhdin, *Physical Review B* **108**, L180404 (2023).
- ³²X. Ning, A. Pezo, K.-W. Kim, W. Zhao, K.-J. Lee, and A. Manchon, *Physical Review Letters* **134**, 026303 (2025).
- ³³D. A. Smith, A. Rai, Y. Lim, T. Q. Hartnett, A. Sapkota, A. Srivastava, C. Mewes, Z. Jiang, M. Clavel, M. K. Hudait, *et al.*, *Physical Review Applied* **14**, 034042 (2020).
- ³⁴M. Arora, E. K. Delczeg-Czirjak, G. Riley, T. Silva, H. T. Nembach, O. Eriksson, and J. M. Shaw, *Physical Review Applied* **15**, 054031 (2021).
- ³⁵M. A. Schoen, J. Lucassen, H. T. Nembach, T. Silva, B. Koopmans, C. H. Back, and J. M. Shaw, *Physical Review B* **95**, 134410 (2017).
- ³⁶N. Keller, A. Bose, N. Soya, E. Hauth, F. Kammerbauer, R. Gupta, H. Hayashi, H. Kashiki, G. Jakob, S. Krishnia, *et al.*, *Nano Letters* (2025), 10.1021/acs.nanolett.5c02641.
- ³⁷E. R. Edwards, H. T. Nembach, and J. M. Shaw, *Physical Review Applied* **11**, 054036 (2019).
- ³⁸Y. Lim, S. Wu, D. A. Smith, C. Klewe, P. Shafer, and S. Emori, *Applied Physics Letters* **121**, 222403 (2022).
- ³⁹K.-H. Ko and G.-M. Choi, *Journal of Magnetism and Magnetic Materials* **510**, 166945 (2020).
- ⁴⁰G. S. Abo, Y.-K. Hong, J. Park, J. Lee, W. Lee, and B.-C. Choi, *IEEE Transactions on Magnetics* **49**, 4937 (2013).
- ⁴¹C. Klewe, P. Shafer, J. Shoup, C. Kons, Y. Pogoryelov, R. Knut, B. Gray, H.-M. Jeon, B. Howe, O. Karis, *et al.*, *Applied Physics Letters* **122**, 132401 (2023).
- ⁴²C. Klewe, Q. Li, M. Yang, A. T. N'Diaye, D. M. Burn, T. Hesjedal, A. I. Figueroa, C. Hwang, J. Li, R. J. Hicken, *et al.*, *Synchrotron Radiation News* **33**, 12 (2020).
- ⁴³C. Piamonteze, Y. W. Windsor, S. R. Avula, E. Kirk, and U. Staub, *Synchrotron Radiation* **27**, 1289 (2020).
- ⁴⁴M. Hurben and C. Patton, *Journal of Applied Physics* **83**, 4344 (1998).
- ⁴⁵C. K. Mewes and T. Mewes, *Handbook of Nanomagnetism: Applications and Tools*, 71 (2015).
- ⁴⁶K.-R. Jeon, C. Ciccarelli, A. J. Ferguson, H. Kurebayashi, L. F. Cohen, X. Montiel, M. Eschrig, J. W. Robinson, and M. G. Blamire, *Nature Materials* **17**, 499 (2018).
- ⁴⁷L. Zhu, D. C. Ralph, and R. A. Buhrman, *Physical Review Letters* **123**, 057203 (2019).
- ⁴⁸M. Zwierzycki, Y. Tserkovnyak, P. J. Kelly, A. Brataas, and G. E. Bauer, *Physical Review B* **71**, 064420 (2005).
- ⁴⁹Y. Li, W. Cao, V. P. Amin, Z. Zhang, J. Gibbons, J. Sklenar, J. Pearson, P. M. Haney, M. D. Stiles, W. E. Bailey, V. Novosad, A. Hoffmann, and W. Zhang, *Physical Review Letters* **124**, 117202 (2020).
- ⁵⁰L. Bai, P. Hyde, Y. Gui, C.-M. Hu, V. Vlaminc, J. Pearson, S. Bader, and A. Hoffmann, *Physical Review Letters* **111**, 217602 (2013).
- ⁵¹H. Schultheiss, J. E. Pearson, S. D. Bader, and A. Hoffmann, *Physical Review Letters* **109**, 237204 (2012).
- ⁵²A. Tsukahara, Y. Ando, Y. Kitamura, H. Emoto, E. Shikoh, M. P. Delmo, T. Shinjo, and M. Shiraishi, *Physical Review B* **89**, 235317 (2014).
- ⁵³L. Chen, M. Decker, M. Kronseder, S. Wimmer, F. Wimmer, M. Schreiber, J. Repp, T. Schulthess, B. Koopmans, and C. Back, *Nature Communications* **7**, 13802 (2016).
- ⁵⁴K.-W. Kim and K.-J. Lee, *Physical Review Letters* **125**, 207205 (2020).
- ⁵⁵W. Wang, T. Wang, V. Amin, Y. Lee, S. Oh, Y. Chen, A. Kim, B. Kim, S. Oh, D. Lee, K. Lee, J. Lee, J. Hong, J. Park, H. Kim, K. Lee, H. Lee, P. Haney, H. Lee, J. Koh, and B. Jung, *Nature Nanotechnology* **14**, 819 (2019).
- ⁵⁶R. E. Maizel, S. Wu, P. P. Balakrishnan, A. J. Grutter, C. J. Kinane, A. J. Caruana, P. Nakarmi, B. Nepal, D. A. Smith, Y. Lim, *et al.*, *Physical Review Applied* **22**, 44052 (2024).