

# Lawrence Berkeley National Laboratory

## LBL Publications

### Title

Stability of 124 and 247 Superconductors

### Permalink

<https://escholarship.org/uc/item/2rr0n3cw>

### Authors

Morris, D E

Asmar, N G

Wei, J Y T

et al.

### Publication Date

1988-11-01



# Lawrence Berkeley Laboratory

UNIVERSITY OF CALIFORNIA


## Physics Division

Submitted to Nature

### Stability of 124 and 247 Superconductors

D.E. Morris, N.G. Asmar, J.Y.T. Wei, and J.E. Post

November 1988

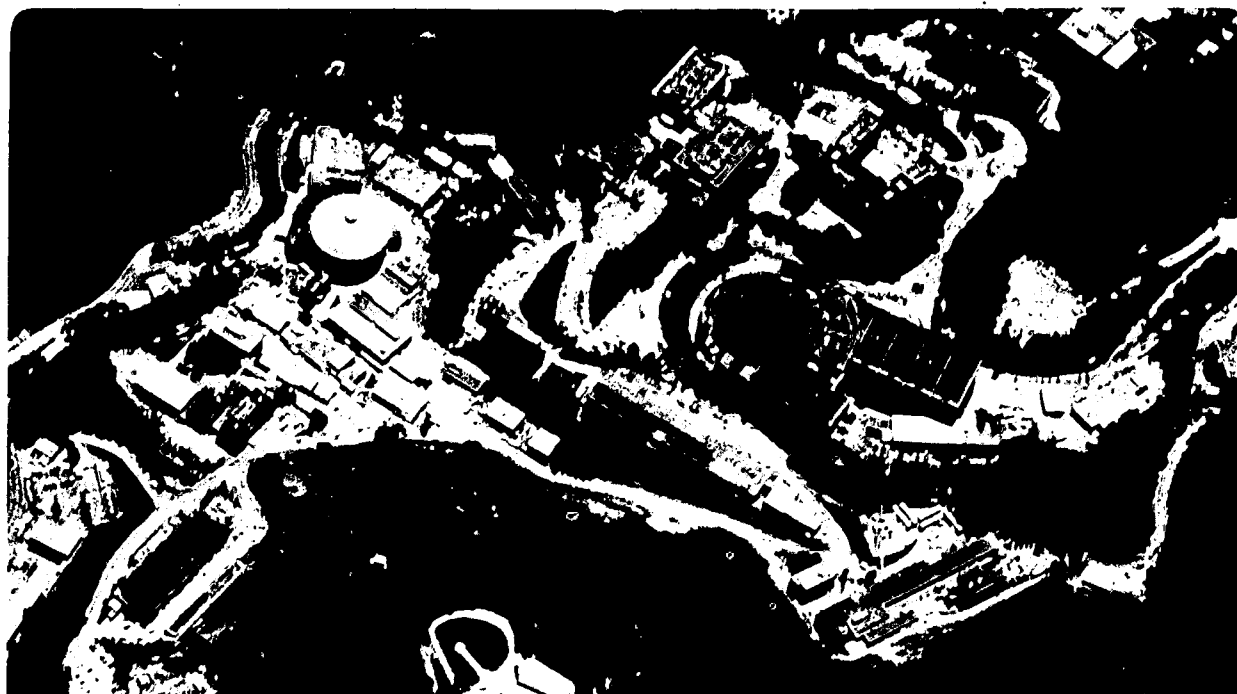

LOAN COPY  
Circulates  
for 2 weeks  
Bldg. 50 Library  
Copy 2

LBL-26250

## **DISCLAIMER**

This document was prepared as an account of work sponsored by the United States Government. While this document is believed to contain correct information, neither the United States Government nor any agency thereof, nor the Regents of the University of California, nor any of their employees, makes any warranty, express or implied, or assumes any legal responsibility for the accuracy, completeness, or usefulness of any information, apparatus, product, or process disclosed, or represents that its use would not infringe privately owned rights. Reference herein to any specific commercial product, process, or service by its trade name, trademark, manufacturer, or otherwise, does not necessarily constitute or imply its endorsement, recommendation, or favoring by the United States Government or any agency thereof, or the Regents of the University of California. The views and opinions of authors expressed herein do not necessarily state or reflect those of the United States Government or any agency thereof or the Regents of the University of California.

# Stability of 124 and 247 superconductors

D. E. Morris, N. G. Asmar, J. Y. T. Wei,  
Physics Division, Lawrence Berkeley Laboratory,  
University of California, Berkeley, CA 94720, and

J. E. Post,  
Smithsonian Institution, National Museum of Natural History,  
Washington DC 20560

## Abstract

The 124 phase  $\text{YBa}_2\text{Cu}_4\text{O}_8$  is synthesized by solid state reaction at  $930\text{--}980^\circ\text{C}$  in  $P(\text{O}_2) \geq 35$  atm. while the 123 phase  $\text{YBa}_2\text{Cu}_3\text{O}_{7-\delta}$  is formed at  $P(\text{O}_2) \leq 5$  atm. At intermediate  $P(\text{O}_2)$  the 247 phase  $\text{Y}_2\text{Ba}_4\text{Cu}_7\text{O}_{15-x}$  is favored. In high  $P(\text{O}_2)$ , 124 is the only phase formed for a wide range of starting stoichiometries. When Dy or Ho (ionic radii close to Y) or Er (smaller) are substituted, the pressure ranges are similar. For the larger (lighter) rare earths Eu and Gd, higher pressures are required. Oxygen is more tightly bound in 124 than in 123, and slow cooling is not needed to optimize  $T_c$ . Oxygen is reversibly lost when 247 is heated, but much less than in 123. The  $T_c$  of 247 is 40-50 K, half that of 123 or 124. Synthesis of the 124 and 247 phases is relatively easy since very high oxygen pressures are not required; this may have considerable practical importance.

The 123, 124, and 247 phases of Y-Ba-Cu-O along with their rare earth analogues offer three isostructural families with incremental variations in lattice parameters and superconducting properties. For this reason, the rare earth 124 and 247 compounds may be helpful in testing theories of high temperature superconductivity. In earlier work<sup>6</sup>, we prepared the rare earth analogues  $RBa_2Cu_4O_8$  ( $R = Nd, Sm, Eu, Gd, Dy, Ho, Er, Tm$ ) with the 124 structure using high pressure oxygen  $P(O_2) \approx 100$  atm. These compounds exhibit varying  $T_C$ 's correlated with the  $R$  ion radius and lattice parameters. We have now prepared the 247 rare earth analogues  $R_2Ba_4Cu_7O_{15-x}$  ( $R = Eu, Gd, Dy, Ho, Er$ ), using appropriate oxygen pressures.

The '124' superconductor  $YBa_2Cu_4O_8$  has a more stable oxygen content than '123' ( $YBa_2Cu_3O_{7-\delta}$ ), and its superconducting  $T_C \approx 81$  K, is high enough to be useful. Its structure is similar to that of 123 but with a double Cu-O 'ribbon' in place of the single Cu-O chain<sup>1,2</sup>. Unfortunately, 124 was difficult to synthesize, so it has not been studied extensively. It was first identified as an intergrowth<sup>3</sup> in 123, and subsequently prepared as a distinct phase<sup>4</sup> and as majority phase<sup>5</sup> in epitaxial thin films. Recently,  $YBa_2Cu_4O_8$  has been synthesized in bulk in pressurized oxygen<sup>6,7</sup>, but very high oxygen pressure was thought to be necessary<sup>7</sup>. We have discovered that single phase 124 can be prepared at 930-980°C by the simple

solid state reaction method at moderate oxygen pressure, ~35 atm. There is no need for slow cooling or oxygen annealing of 124 to optimize its superconducting properties; this may have considerable practical importance.

124 is the only phase formed over a wide range of starting stoichiometries, when the oxygen pressure is sufficient. The 123 phase is stable only up to a few atm., and the '247' phase  $Y_2Ba_4Cu_7O_{15-x}$  is favored at intermediate pressures. 247, which consists of 123 and 124 blocks alternating along the *c* axis, was also considered difficult to synthesize in bulk<sup>6,8,9</sup>. This phase is also a superconductor, but surprisingly,  $T_C \approx 40-50$  K, much lower than for 123 ( $T_C \approx 93$  K) or 124 ( $T_C \approx 81$  K). When rare earths are substituted for yttrium, the pressure ranges for the different phases shift somewhat. We have investigated synthesis conditions of all three phases in the R-Ba-Cu-O (R = Y, Eu, Gd, Dy, Ho, Er) systems, by varying  $P(O_2)$  and starting stoichiometry. It has been reported<sup>7</sup> that the 123 phase  $YBa_2Cu_3O_{7-\delta}$  is stable up to ~200 atm., with the 124 and 247 phases co-existing at higher pressures. Our results show that this is not the case.

Samples were prepared by solid state reaction of  $Y_2O_3$  or a rare earth oxide  $R_2O_3$  (R = Nd, Sm, Eu, Gd, Er, Dy, Ho, Er, or Tm) (all 99.9%), with BaO(99.99%) and CuO(99.99%). In the first series of experiments, starting stoichiometry (cation ratio) was 1:2:4. All ingredients were fine powders (-325 mesh), which were ground

together in a mortar and pestle and pressed into 6 mm tablets at 3500 kg/cm<sup>2</sup>. The samples were wrapped individually in Au foil and calcined for 8 hr in O<sub>2</sub> at pressures between 4 and 100 bar (1 bar ... 0.1 Mpa = 0.987 atm) in a commercially available externally heated high pressure oxygen furnace<sup>10</sup>. The calcining temperature was 930°C or 980°C, followed by slow cooling<sup>11</sup> to room temperature. Each sample was then re-ground, pressed and fired under the same conditions to maximize homogeneity.

The samples were examined by X-ray powder diffraction (XRD). The patterns (Fig. 1) indicated that in addition to one or more of the superconducting phases, most samples contained some CuO and BaO, as well as small quantities of the 'green phase' R<sub>2</sub>BaCuO<sub>5</sub>. The three superconducting phases were distinguished by their characteristic low angle powder diffraction peaks. The [0 0 2] peak of the 124 phase is found at d spacing ≈ 13.6 Å, clearly distinct from the position of the [0 0 1] peak of 123 at 11.7 Å and the [0 0 4] peak of 247 at 12.55 Å (Fig 2 and Ref 6). This method is quite sensitive, because the low angle reflections from the rare earth compounds are quite strong.

The preliminary phase diagram determined from the XRD studies is given in Figure 3. We find that the 123 phase in the Y-Ba-Cu-O system is stable only up to a few atm. At high pressure (> 30 bar) the stable phase is 124, while 247 is formed at intermediate

pressure. A similar pattern is found in the rare earth substituted systems, but the ranges of pressure over which the 123, 247, or 124 phase are formed depend on the radius of the R ion. In the Dy and Ho systems the pressure ranges correspond closely to those of the Y system. These three ions have nearly the same radii and their 124 and 247 compounds have nearly the same lattice parameters<sup>6</sup>. The  $T_C$ 's of their 124 phases are also similar<sup>6</sup>. The lighter rare earth ions (with larger radii) require somewhat higher pressures for synthesis of 247 and of 124. This accounts for our inability to synthesize single phase  $\text{EuBa}_2\text{Cu}_4\text{O}_8$  and  $\text{GdBa}_2\text{Cu}_4\text{O}_8$  at 100 bar (Fig 3 and Ref 6). When the  $P(\text{O}_2)$  is not optimal for 247, ordering of the alternating 123 and 124 blocks is imperfect. The disorder is indicated by broadening of the low angle XRD peak (Fig 2b). Samples which contained two phases according to XRD (Fig 2d) showed two transitions, giving 'stepped' susceptibility curves (Fig 4e).

The orthorhombic distortion in 124 is smaller<sup>6</sup> than in 123, and we find that it is still smaller in the 247 compounds. The distortion varies inversely with rare earth ion radius in 247 compounds in the same manner as in 124 and 123. The  $T_C$  of the 247 compounds also varies inversely with rare earth radius, as found earlier for the 124 series<sup>6</sup>. Details will be published elsewhere<sup>12</sup>.

Superconducting diamagnetic transitions were measured on a SQUID magnetometer in fields of 3-8 oe. Y-Ba-Cu-O samples containing 123



exhibited Meissner flux expulsion at 93K, as opposed to 81 K for those containing 124. Our value of  $T_c \approx 40-50$  K for the slow cooled<sup>10</sup> 247 compound agrees with Ref 7, but not with the value  $\sim 86$ K given in Ref 9 for the resistive transition of an oxidized ribbon of metallic precursors. Some 123 or 124 in their samples may have been responsible.


The oxygen in 124 is more tightly bound than in 123 (Refs 6 and 7). No reversible weight loss was observed upon heating  $YBa_2Cu_4O_8$  at  $50^\circ\text{C}/\text{min}$  in a Perkin-Elmer TG-7 thermogravimetric analyzer to  $\sim 800^\circ\text{C}$  in 1 atm  $O_2$  (Fig 5), demonstrating that the 'ribbon' oxygen in 124 is more tightly bound than is the 'chain' oxygen in 123. However, heating to higher temperatures caused irreversible loss. A sample of 124 which was quenched from  $\sim 950^\circ\text{C}$  to  $100^\circ\text{C}$  within 5 minutes showed  $T_c$  and transition width substantially the same as for slow cooled samples (Fig 4), confirming that cooling rate is not critical for the 124 phase, in contrast to 123.

A second series of experiments, in which the starting cation ratio was varied over a wide range, showed that only the 124 phase is formed at  $P(O_2) = 100$  atm. The synthesis temperature was  $930^\circ\text{C}$ . With Y:Ba:Cu ratios of 1:2:3, 1:2:3.5, 1:2:4, and 1:2:5, the 124 phase alone, without 123 or 247, was detected by low angle XRD. At still greater CuO content (1:2:6), and in samples richer in Ba (Y:Ba:Cu ratios 1:3:4, 1:3:5, 1:3:6), no low angle peaks appeared.

These experiments indicate that 124 is the stable phase in high  $P(O_2)$  over a considerable range of starting compositions.

It is worth noting that all these cation ratios (except 1:2:3) lie within the "region of partial melting" shown in Ref 13 for the  $Y_2O_3$ -Ba-CuO phase diagram at 950-1000°C and one atm. An attempt was made to grow single crystals of 1-2-4 by a melt-reaction of a Cu-O rich mixture. The Y:Ba:Cu starting stoichiometry was 2:6:15. After reacting at 980°C and 70 bar for 24 h and slow cooling at 3°C/h to 900°C, no melting or crystal growth was observed. To explore this further, Y-Ba-Cu-O with 1:2:4 cation ratio was reacted in  $P(O_2) = 100$  bar at 1000°C. Again, no melting was seen.


With the above information it is easy to understand why the 124 phase is more stable than 123 in high pressure oxygen at elevated temperatures ( $T \approx 900$ -1000°C), and the reverse is true at lower oxygen pressures. As is well known, 123 loses oxygen rapidly and reversibly upon heating above ~400°C (Ref 14 and Fig 5). At synthesis temperature  $T \approx 950$ °C in 1 atm oxygen, the stoichiometry is about  $YBa_2Cu_3O_{6.35}$  (Ref 15). Therefore, the synthesis reaction is:



and oxygen is evolved during the synthesis. When the compound is slowly cooled after synthesis, it absorbs ~0.3  $O_2$  from its

surroundings to form  $\text{YBa}_2\text{Cu}_3\text{O}_{6.95}$ , the well known 123 superconductor. If the compound is quenched from synthesis temperature, the oxygen content will remain low, yielding the non-superconducting semiconductor  $\text{YBa}_2\text{Cu}_3\text{O}_{6.35}$ . In retrospect, the momentous discovery<sup>16</sup> of superconducting  $\text{YBa}_2\text{Cu}_3\text{O}_{6.95}$  was made because of the extraordinarily high oxygen diffusivity<sup>14</sup>, which enabled the semiconducting compound to oxidize during cooling.

In contrast, when synthesis is carried out under  $P(\text{O}_2) > 30$  bar, the reaction proceeds as:



We see that oxygen is taken up during the synthesis, and the 124 compound is fully oxidized during formation. The thermodynamic stability of 124 under these conditions is indicated by the fact that it forms in preference to 123 even when the starting cation ratio is 1:2:3.

At lower temperatures, the difference in oxygen content of 123 and 124 (compared to their constituent oxides) is smaller and the oxygen pressure required to stabilize the 1-2-4 phase should be lower. Furthermore, diffusion of the cations is much slower than the oxygen. This may explain the formation of 1-2-4 in thin films prepared with the appropriate stoichiometry and processed at lower

temperatures<sup>4,5</sup>. At still lower temperature (<400°C) the excess oxygen content of both 123 and 124 is the same (relative to their constituent oxides), and it is not clear at present which compound is thermodynamically more stable at ambient temperature and pressure.

The stability of 247 at intermediate oxygen pressures can also be understood. Only the oxygen in the single chains in the 123 blocks is expected to be weakly bound, while the oxygen in the 1-2-4 blocks will be more tightly bound. Consequently, the oxygen loss on heating 247 should be only about half that of the 123 compound at the same temperature and oxygen partial pressure. Therefore, the oxygen content of 247 at high temperatures should be intermediate between that of 123 and 124. This was confirmed by TGA measurements (Figure 5) which showed a reversible oxygen loss from  $Y_2Ba_4Cu_7O_{15-x}$  which is much smaller than for  $YBa_2Cu_3O_{7-\delta}$ , which is shown for comparison.

The 124 superconductor may be technologically useful because of its greater thermal stability. Since no oxygen is lost or gained during heating or cooling, the thermal expansion parameters should be better behaved than 123, and no tetragonal-orthorhombic phase transition is expected during cooling from synthesis temperature. The orthorhombic distortion of 124 is only half that of 123 (Ref 6), which may also be helpful in minimizing thermal stresses.

It is well known that when 123 is processed above ~940°C in one

atm  $O_2$ , non-superconducting phases form at the grain boundaries<sup>17</sup>. This is a handicap in producing high density ceramic 123, since the sintering temperature cannot be increased. Note that the 123 compound at  $T \geq 950^\circ C$  and  $P(O_2) = 1$  atm contains less oxygen than do the green phase  $Y_2BaCuO_5$  and other decomposition products of 123 (e.g.  $BaCuO_2$ ). One might attempt to stabilize the 123 phase up to higher temperatures by heating in high  $P(O_2)$  to increase the oxygen content to above 6.5, which is higher than that of the decomposition products. Unfortunately, our results show that the 123 phase is not stable under those conditions and will gradually convert into 124. The inhibition of melting in elevated  $P(O_2)$  (see above) will prevent densification by liquid phase sintering. However, it may be possible to prepare dense 124 material with enhanced  $J_c$  by sintering in high  $P(O_2)$  at significantly higher temperatures.

Another technique for making high density ceramic material is hot isostatic pressing (HIP). If 123 is synthesized, sealed in an Ag, Au or Pt container and HIPed, a large internal oxygen pressure will develop as the compound loses oxygen, and the 123 will convert slowly to 124 plus excess Yttrium and Barium oxides. Then the oxygen pressure inside the sample container will fall to a value (~ 5-30 bar) just sufficient to sustain the stability of the 124 phase, which has absorbed the rest of the oxygen released from the 123 compound. A more practical procedure would be to prepare 124, and then HIP it. The conversion of 124 into 123 will be stopped by the

rising internal  $O_2$  pressure.

The most important use for the 124 compound may be as a precursor for preparation of 123. After synthesis of single phase 124, and high temperature processing for densification, subsequent thermal treatment in air or vacuum would remove enough oxygen to cause the 124 to convert into 123 plus excess  $CuO$ , which may migrate to the grain boundaries. However, the diffusion of the cations is much slower than of the oxygen, so if the low  $P(O_2)$  treatment is done at low temperature, or for a short time, the  $Cu$  will not reach the grain boundaries, but will be left within the 123 grains as  $CuO$  'islands'. These intragranular non-superconducting islands may be effective as flux pinning centers to increase  $J_c$ .

The authors thank Daphne Ross for assistance with X-ray diffraction, N. A. Crocker, J. H. Nickel, R. L. Sid, M. T. Tran, and W. E. Vinje for laboratory assistance, and G. W. Smith for useful advice. D. E. M. wishes to express appreciation for the encouragement of R. A. Muller and P. J. Oddone. This research was supported in part by the U. S. Department of Energy under Contract No. DE-AC03-76SF00098.

## References

- <sup>1</sup>P. Marsh, et al. Nature 334, 141 (1988).
- <sup>2</sup>R. M. Hazen, L. W. Finger and D. E. Morris, preprint, to appear in Appl. Phys. Lett.
- <sup>3</sup>M.P.A.Viegers, et al., J. Mater. Res. 2, 743 (1987); J. Narayan, et al. Appl. Phys. Lett. 51, 940 (1987); H. W. Zandbergen, et al., Nature 331, 596 (1988); T. Kogure, et al., Physica C 156, 35 (1988).
- <sup>4</sup>A. F. Marshall, et al., Phys. Rev. B 37, 9353 (1988).
- <sup>5</sup>J. Kwo, et al., Appl. Phys. Lett. 52, 1625 (1988); K. Char et al., Phys. Rev. B 38, 834 (1988); M. L. Mandich, et al., Phys. Rev. B 38, 5031 (1988);
- <sup>6</sup>D. E. Morris, et al., Lawrence Berkeley Lab Report LBL-26221 (Sept 1988); to appear in Phys. Rev. B. 1 April, 1989.
- <sup>7</sup>J. Karpinski, et al., Nature 336, 660 (1988)
- <sup>8</sup>J. Karpinski, et al., Physica C 153-155, 830 (1988); P. Bordet, et al., Nature 334, 596 (1988).
- <sup>9</sup>T. Kogure, et al., Physica C 156, 45 (1988).
- <sup>10</sup>Morris Research, 1862 Euclid #240, Berkeley CA 94709, USA.
- <sup>11</sup>50 min to 700°C, 50 min to 600°C, 100 min to 500°C, 100 min to 400°C, furnace cool.
- <sup>12</sup>Morris et al. Lawrence Berkeley Lab Report LBL-26735 (Jan. 1989); to be published.
- <sup>13</sup>L. F. Schneemeyer, et al., Nature 328, 601 (1987).
- <sup>14</sup>D.E.Morris, et al, Proc.of MRS Spring Meeting-Symp. S, Vol EA-11, p.209 (Mtl. Res. Soc, Pittsburgh, PA, 1987).
- <sup>15</sup>P. K. Gallagher, Adv. Ceram. Mater. 2, 632 (1987); K. Kishio, et al., Jpn. J. Appl. Phys. 26, L1228 (1987); E. D. Specht, et al., Phys. Rev. B 37, 7426 (1988).
- <sup>16</sup>M. K. Wu, et al., Phys. Rev. Lett. 58, 908 (1987)
- <sup>17</sup>D. Shi, et al, Mater. Lett. 6, 217 (1988); T. Aselage and K. Keefer, J. Mater. Res. 3, 1279 (1988); K. G. Frase & D. R. Clarke, in "Ceramic Superconductors" ed D. R. Clarke & D. W. Johnson.

### Figure captions

Fig. 1. X-ray powder diffraction patterns for the 124 and 247 phases in the Dy-Ba-Cu-O system. Each pattern shows a single phase, except for additional peaks identified as CuO.

Fig 2. Low angle X-ray powder diffraction curves taken with Cu  $k\alpha$  radiation: (a) Dy-Ba-Cu-O synthesized in 34 bar  $O_2$ ; the peak at d spacing = 13.6 Å indicates the 124 phase. (b) Dy-Ba-Cu-O synthesized in 17 bar  $O_2$ ; the peak at 12.55 Å indicates the 247 phase. (c) Dy-Ba-Cu-O synthesized in 5 bar  $O_2$ ; the peak at 11.7 Å indicates the 123 phase. (d) Eu-Ba-Cu-O processed in 100 bar  $O_2$ . The two peaks at 13.6 Å and 12.55 Å indicate that the sample contains both 124 and 247 phases. Note the broadening of the 12.55 Å peak, indicating imperfect order in the sequence of alternating 123 and 124 layers or presence of extra 123 or 124 layers.

Fig. 3. Pressure ranges for thermodynamic stability of the 123, 247, and 124 phases:  $RBa_2Cu_3O_{7-\delta}$ ,  $R_2Ba_4Cu_7O_{15-x}$ , and  $RBa_2Cu_4O_8$  ( $R = Y, Eu, Gd, Dy, Ho, Er$ ) at 930-980°C, as determined from the position of the low angle X-ray peak. For each rare earth system, the phases present are indicated as a function of oxygen pressure during synthesis. The fraction of each phase between 0 and 1.0 is plotted on the vertical axis. In all cases, the 123 phase is stable up to 5-15 bar, the 124 phase is stable above 35-200 bar



depending on the R ion radius, and the 247 phase is stable at intermediate oxygen pressures.

Fig. 4. Meissner flux expulsion curves for (a)  $\text{YBa}_2\text{Cu}_3\text{O}_{7-\delta}$ , (b)  $\text{Y}_2\text{Ba}_4\text{Cu}_7\text{O}_{15-x}$ , and (c)  $\text{YBa}_2\text{Cu}_4\text{O}_8$ , all slow cooled. Curve (d) is for  $\text{YBa}_2\text{Cu}_4\text{O}_8$  synthesized under the same conditions as (c) ( $T = 980^\circ\text{C}$ ,  $P[\text{O}_2] = 70 \text{ atm}$ ), but rapidly cooled in  $\sim 5 \text{ min}$  to  $100^\circ\text{C}$ ; the  $T_c$  was unaffected. Curve (e) is for a Eu-Ba-Cu-O sample processed at 34 bar. Note the two 'steps' at  $\sim 37 \text{ K}$  and  $\sim 60 \text{ K}$ . Meissner curves for  $\text{RBa}_2\text{Cu}_4\text{O}_8$  ( $R = \text{Nd, Sm, Eu, Gd, Dy, Ho, Er}$ ) were published in Ref 6, and curves for  $\text{R}_2\text{Ba}_4\text{Cu}_8\text{O}_{15-x}$  ( $R = \text{Y, Eu, Gd, Dy, Ho, Er}$ ) are given in Ref 12.

Fig 5. Thermogravimetric (oxygen loss) curves for 124, 123, and 247 phases of Y-Ba-Cu-O up to  $800^\circ\text{C}$ . Heating and cooling rates were  $30 \text{ deg/min}$ . (a)  $\text{YBa}_2\text{Cu}_4\text{O}_8$  - oxygen content remains nearly constant, with a small irreversible weight loss at high temp. (b)  $\text{YBa}_2\text{Cu}_3\text{O}_{7-\delta}$  - oxygen loss is large and nearly reversible. (c)  $\text{Y}_2\text{Ba}_4\text{Cu}_7\text{O}_{15-x}$  - oxygen loss at  $800^\circ\text{C}$  is much smaller than for 123, and is partially reversible. The oxygen loss appears to begin at a higher temperature ( $\sim 500^\circ\text{C}$ ) than in 123 ( $\sim 400^\circ\text{C}$ ).

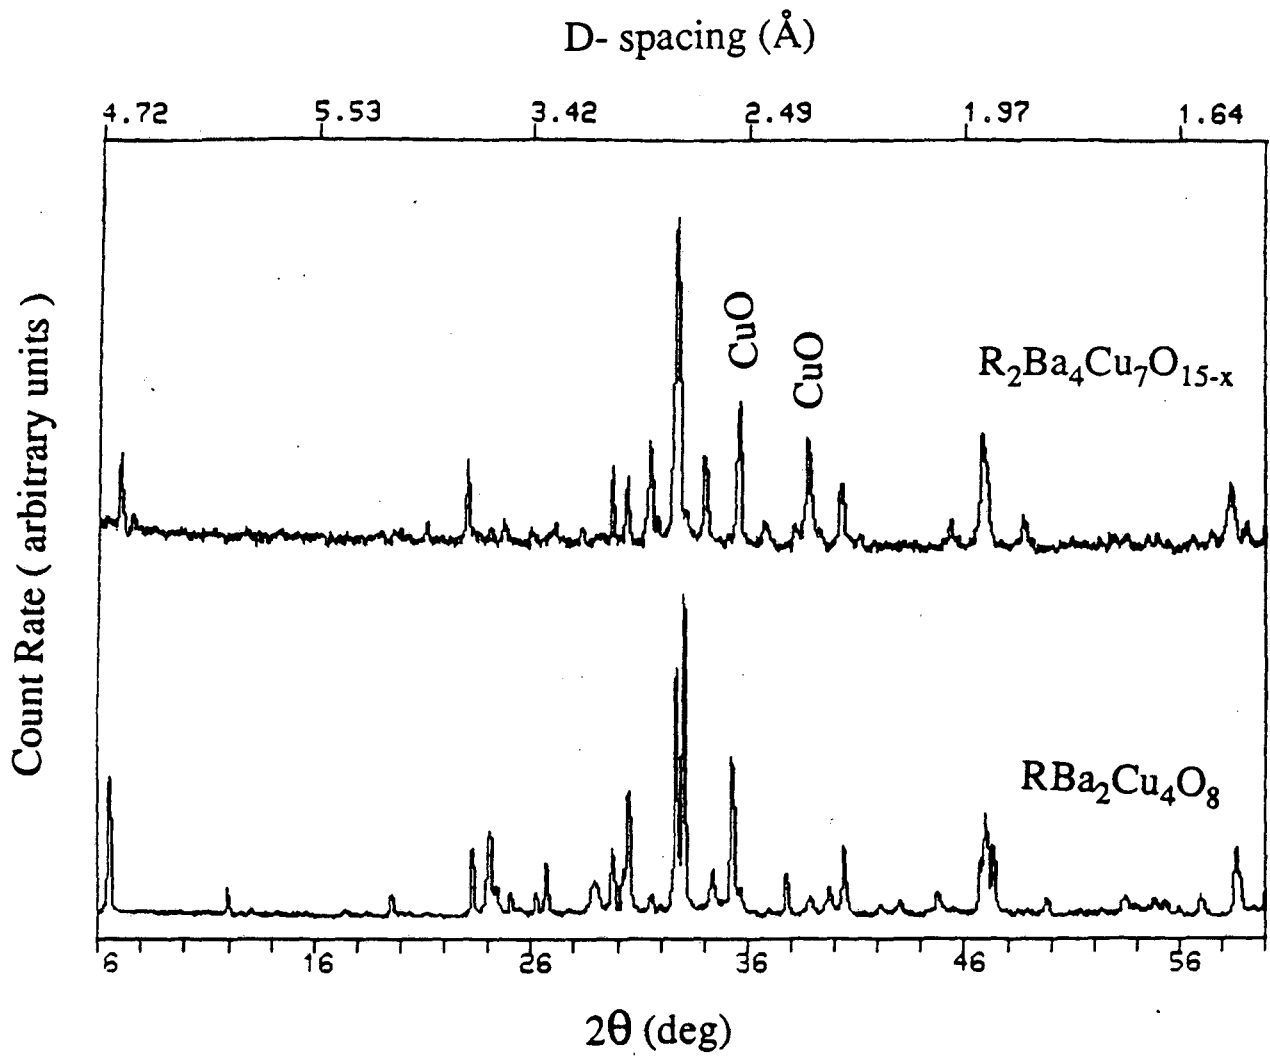


Fig. 1

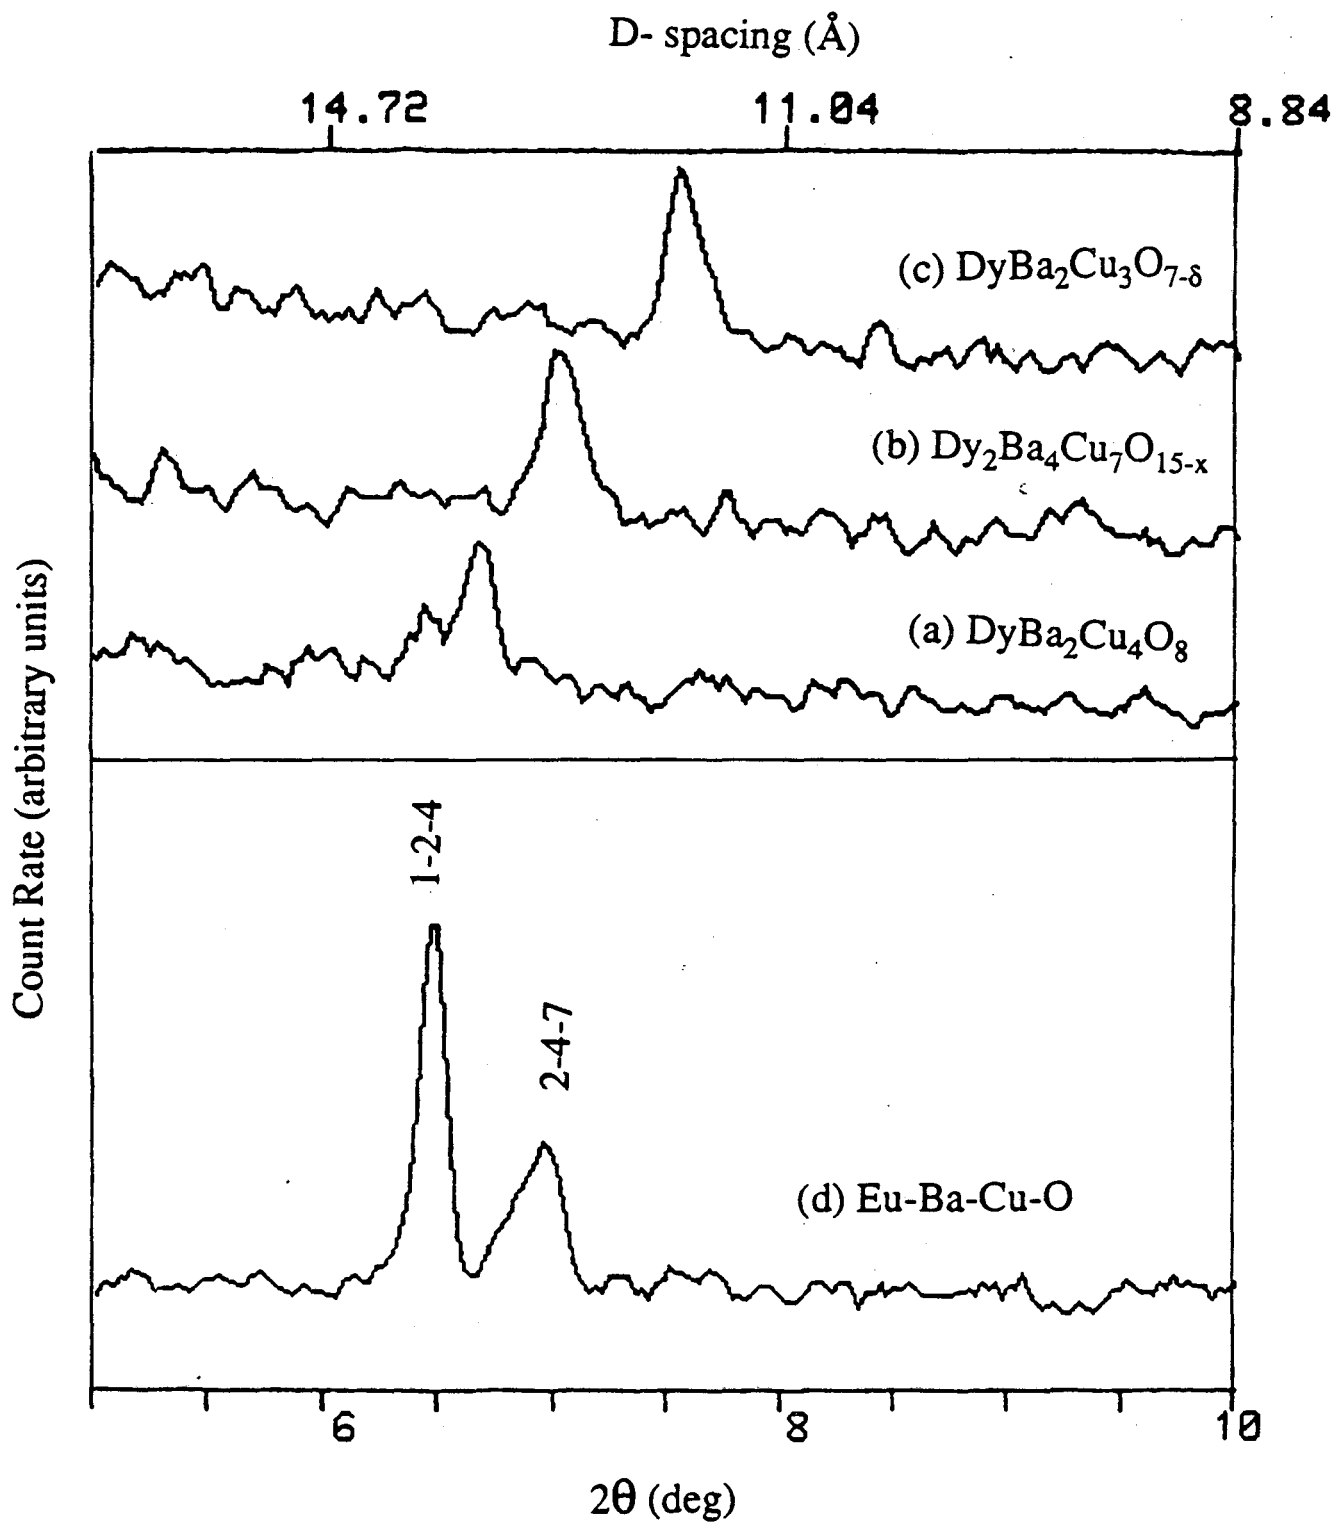


Figure 2

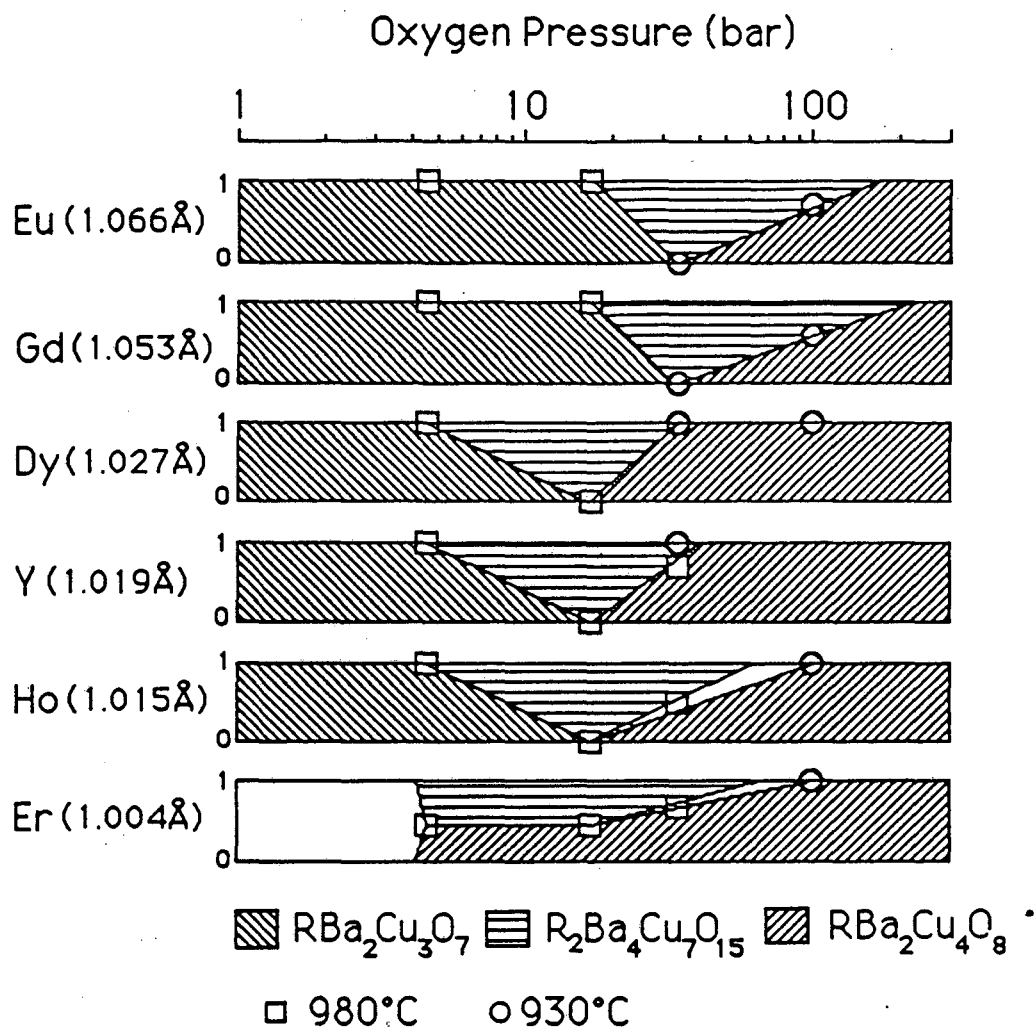


Fig. 3

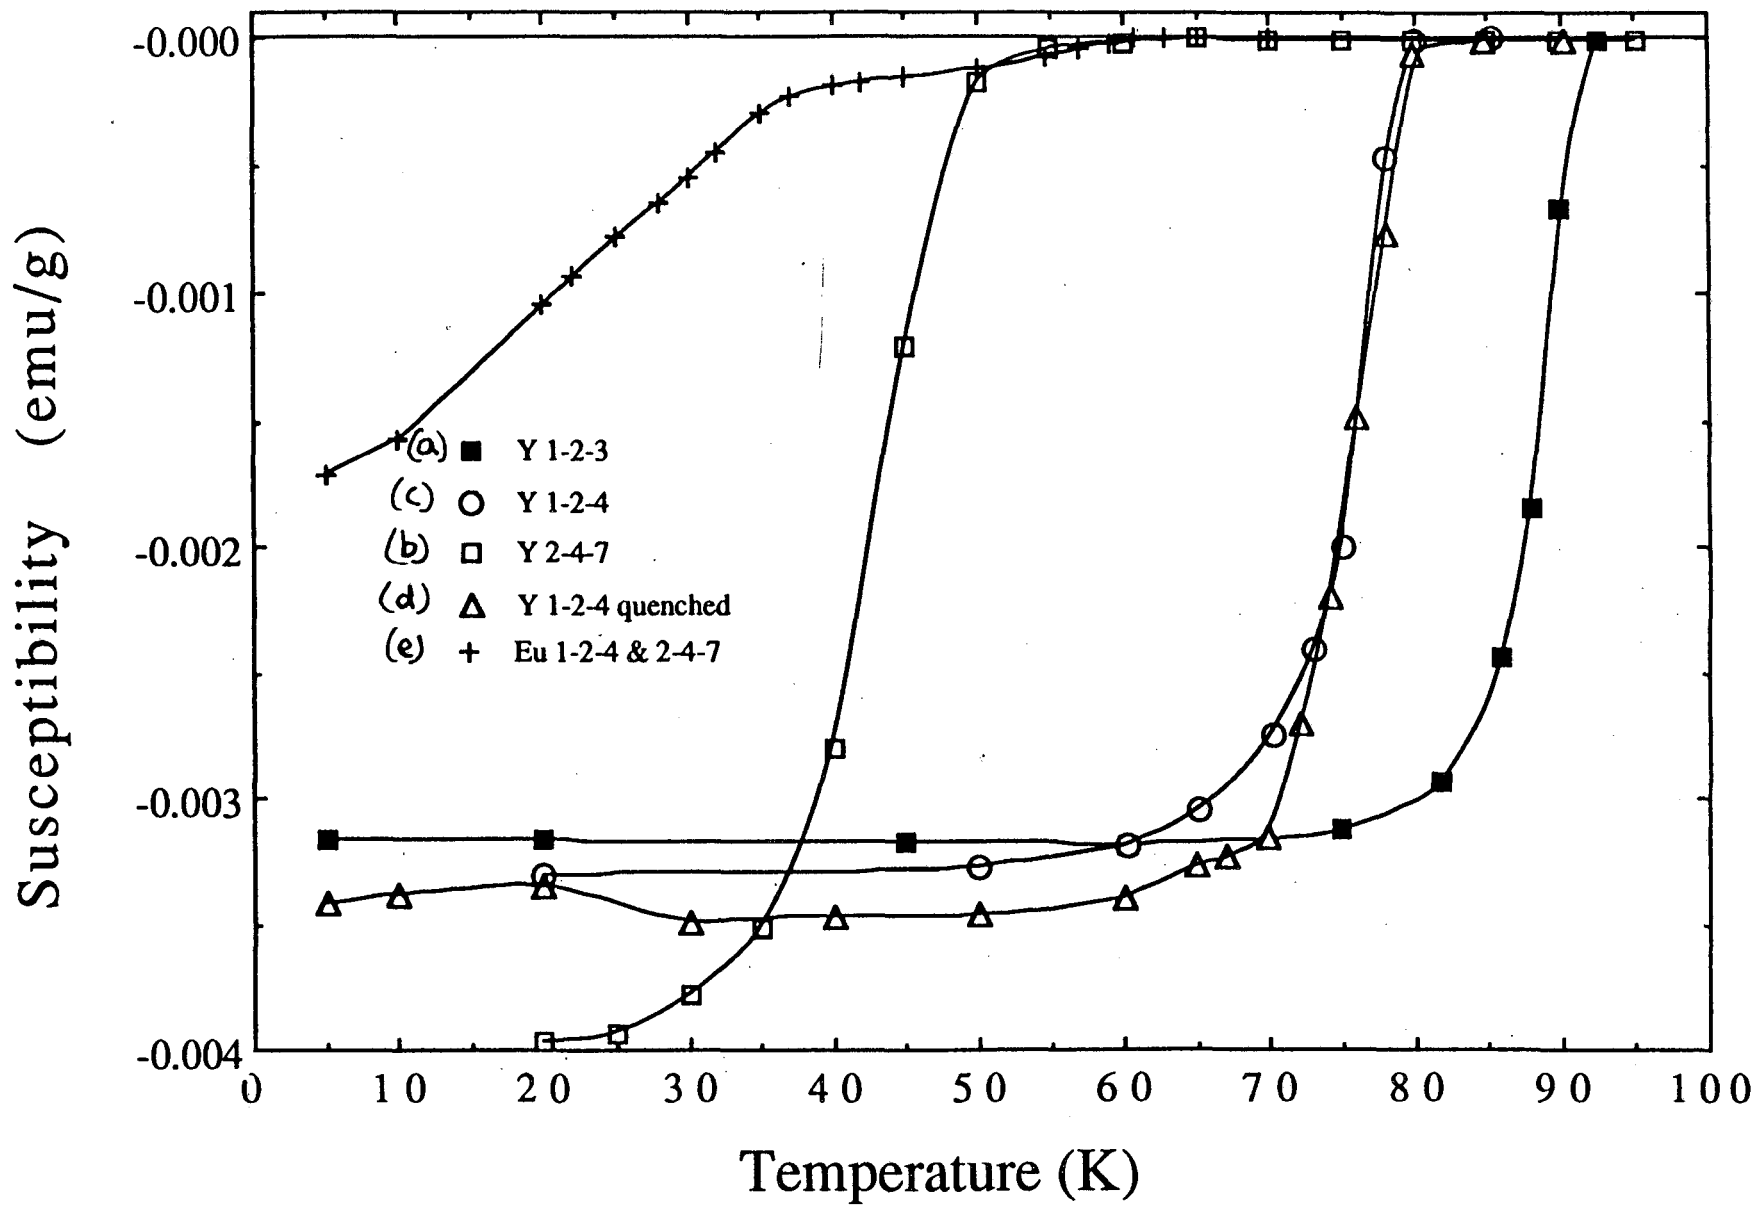


Figure 4

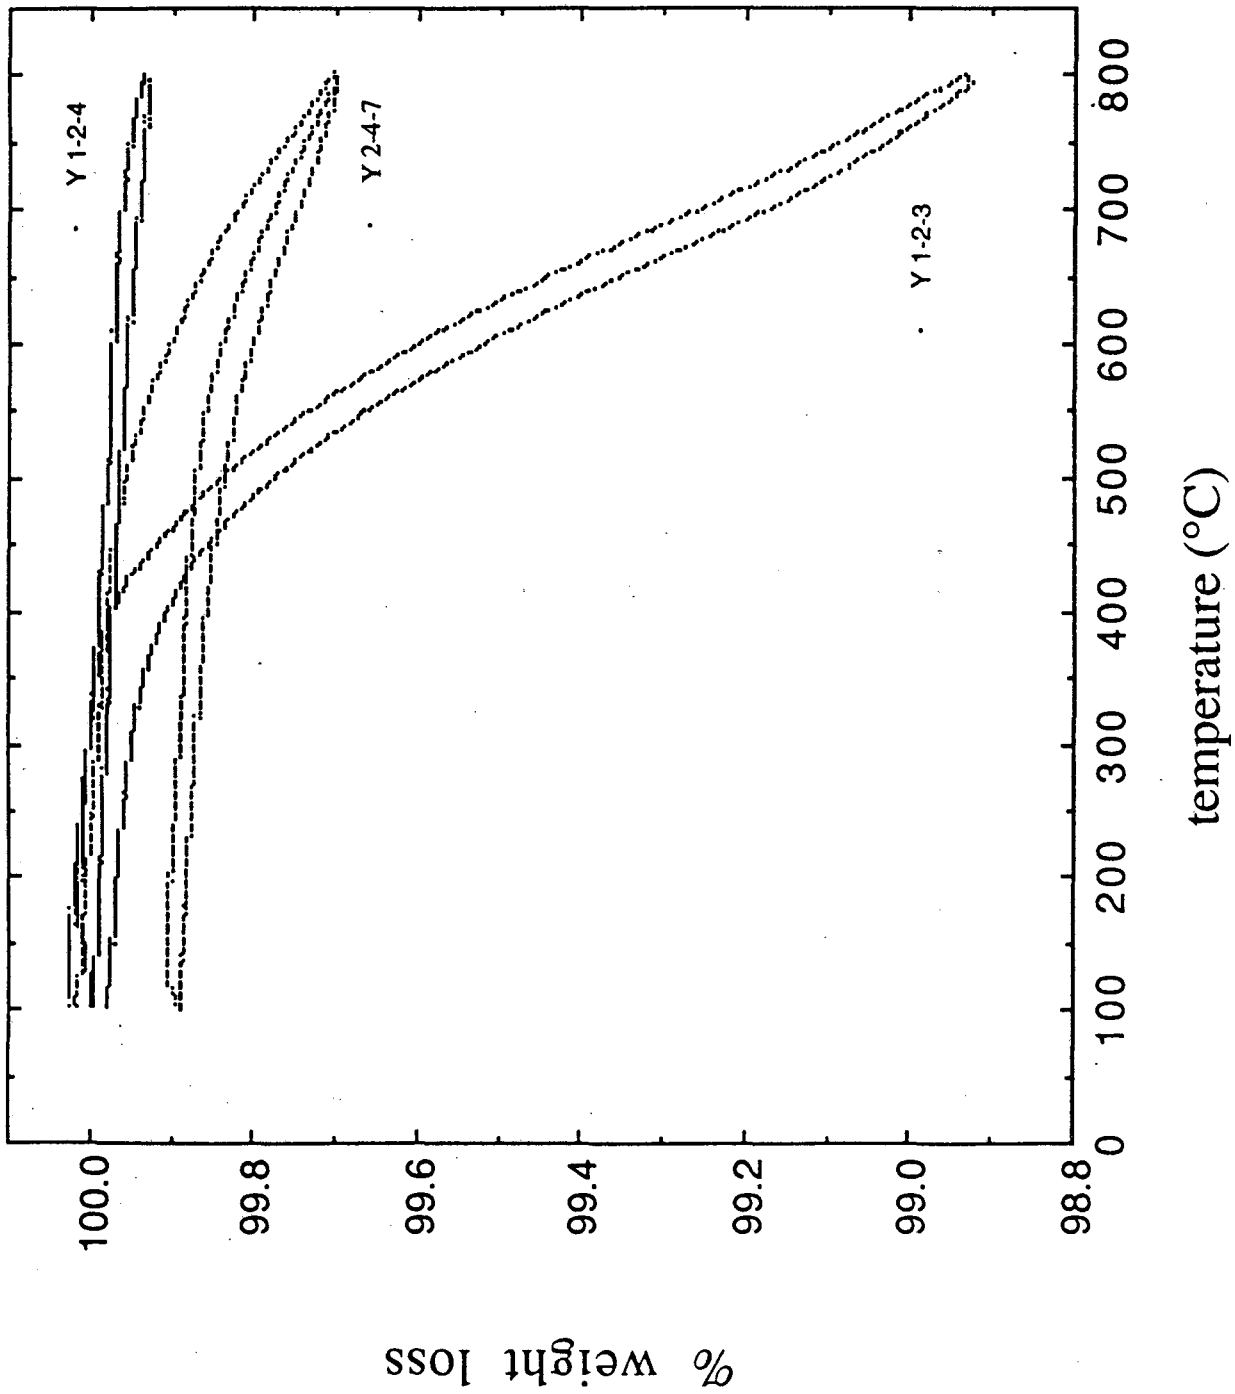


Figure 5

LAWRENCE BERKELEY LABORATORY  
TECHNICAL INFORMATION DEPARTMENT  
1 CYCLOTRON ROAD  
BERKELEY, CALIFORNIA 94720