

**UCLA**

**UCLA Previously Published Works**

**Title**

Bubble Transport in Three-Dimensional Gravity Driven Flow, Part II. Numerical Results

**Permalink**

<https://escholarship.org/uc/item/2sq7v904>

**Journal**

Journal of Non-Crystalline Solids, 336(2)

**Authors**

Pilon, Laurent  
Viskanta, Raymond

**Publication Date**

2004

Peer reviewed

# Bubble Transport in Three-Dimensional Laminar Gravity Driven Flow - Numerical Results

Laurent Pilon<sup>1</sup> and Raymond Viskanta<sup>2</sup>

<sup>1</sup> Mechanical and Aerospace Engineering Department  
University of California, Los Angeles - Los Angeles, CA 90095, USA  
Phone: +1 (310)-206-5598, Fax: +1 (310)-206-4830  
E-mail: pilon@seas.ucla.edu

<sup>2</sup> Heat Transfer Laboratory  
School of Mechanical Engineering  
Purdue University  
West Lafayette, IN 47907, USA

September 16, 2003

# ABSTRACT

This paper is the second part of a study on bubble transport, growth and shrinkage in three-dimensional gravity driven flow. Sample calculations with applications to glass melting furnaces are presented. First, a consistent set of thermophysical properties of the most common composition [74 SiO<sub>2</sub>-16 Na<sub>2</sub>O-10 CaO (mol.%)] of soda-lime silicate glass or similar compositions over the temperature range of 1000 to 2000 K is reported. The population balance equation is solved for the bubble density function using the backward method of characteristics. The zeroth to third order moments, i.e, number of bubbles, average radius, molar gas fraction, interfacial area, and void fraction are computed by numerical integration. Results for both transient and steady state operations are presented and analysed. Two cases are considered (1) bubbles containing only CO<sub>2</sub> and (2) bubbles containing a diffusing gas (O<sub>2</sub>) and a non-diffusing gas (CO<sub>2</sub>). The feasibility of such complex calculation is demonstrated and is in qualitative agreement with reported results.

**Keywords:** defects in glass, soda-lime silicate glass, population balance theory, glass properties, glass refining, bubbles.

## NOMENCLATURE

$A$	Parameters of the initial bubble size distribution
$A_i$	Liquid/gas interfacial area concentration
$B$	Parameters of the initial bubble size distribution
$D$	Diffusion coefficient
$f_1$	Bubble density function
$f_v$	Volumetric gas fraction
$g$	Specific gravity
$M$	Molecular mass
$N$	Total number of bubbles per unit volume of glassmelt
$p_0$	Atmospheric pressure
$p$	Pressure
$r$	Bubble radius
$r_0$	Initial bubble radius
$r_{min}$	Minimum bubble radius
$\dot{r}$	Rate of change of bubble radius
$R$	Universal gas constant = $8.314J/molK$
$S$	Solubility of the gas species in the molten glass
$T$	Temperature
$t$	Time
$W$	Glass tank width (see Figure 1)
$w_r$	Vertical upward velocity of the bubble relative to the glassmelt

$\vec{x}$	Spatial or external coordinates
$x$	Longitudinal location (see Figure 1)
$x$	Spanwise location (see Figure 1)
$z$	Local depth within the glassmelt (see Figure 1)

### Greek symbols

$\alpha$	Parameter
$\epsilon_1, \epsilon_2$	Arbitrarily small constants for convergence criteria
$\eta$	Parameters of the initial bubble size distribution
$\gamma$	Gas molar fraction in the bubbles
$\sigma$	Surface tension
$\rho$	Density
$\mu$	Kinematic viscosity

### Subscripts

<i>batch</i>	Refers to the glassmelt/batch interface
$CO_2$	Refers to the carbon dioxide
$i$	Index of the gas species
$I, J, K$	Refers to indices of the scalar nodes of the staggered grid
$O_2$	Refers to the oxygen
$\infty$	Refers to the bulk of the glassmelt

### Notation

$\bar{X}$	Average value of variable X with respect to bubble radius
-----------	---

# 1 Introduction

The first part of the study [1] presents a comprehensive model of bubble growth, shrinkage, and transport in three-dimensional gravity driven flow. Previous studies computed the dissolved gas concentration in the melt by neglecting the source term due to the diffusion of gases in and out of the bubbles [2–6]. This simplification implies that the dissolved gas concentrations and the number of bubbles in discretized groups can be computed consecutively and independently. In the present study, these parameters are intimately coupled, i.e.,  $C_{\infty,i}$ ,  $r$ ,  $\gamma_i$ , and  $f_1$  are computed iteratively until converged solutions for all the variables are obtained. Considering refining reactions that are complete and irreversible enables one to compute the refining agent concentration  $[M^{k+}]$  independently.

The input parameters governing the problem are: (1) the thermophysical properties of the molten glass, (2) the physicochemical properties of gases dissolved in the molten glass, (3) the refining reactions characteristics, (4) the partial pressure of gases at the combustion space/glassmelt or foam interfaces, and (5) the three-dimensional flow and temperature fields of the molten glass. Two sample calculations are presented and discussed in detail for the following physical situations : (1) bubbles contain only  $\text{CO}_2$  that diffuse out of the bubbles, and (2) bubbles containing both  $\text{CO}_2$  and  $\text{O}_2$  but with only  $\text{O}_2$  diffusing in and out of the bubbles.

The main interest of this paper is to demonstrate the feasibility of the calculations by presenting sample results and trends observed in the two-phase flow. Consequently, some simplifications in the model formulation have been made to make the calculations more economical. These include neglecting the effect of bubbles on the liquid flow and thermal

structures and assuming that the bubble velocity is the same as that of the glassmelt except in the vertical direction where buoyancy is accounted for. These simplifications are justified by the fact that bubbles and the void fraction are small and by the inability to validate the numerical results at present due to the lack of experimental data. The study also aims at assessing the effect of the gas diffusion in and out of the bubbles on the concentration of dissolved gases in the glassmelt and neglected in previous studies [2–7].

## 2 Physicochemical Properties

The thermophysical properties are important input parameters and their appropriate specification is a major concern in modeling glass melting furnaces and bubble behavior [8, 9]. Up to now, no reported simulation of glass melting furnaces has used a consistent set of thermophysical properties for a given glass composition. The assessment of the bubble transport and foam formation models depends strongly on the accuracy of the molten glass thermophysical properties (e.g., viscosity, density, surface tension, thermal diffusivity, and expansion coefficient), the refining reaction characteristics as well as the diffusion coefficient, and the solubility of each gas dissolved in the molten glass. These thermophysical properties depend on many parameters such as the glass composition, the temperature, the dissolved gas partial pressure, and the composition and pressure of the atmosphere [10]. According to Kawachi and Kawase [5] reliable data and measurement methods are not yet available for some of the thermophysical properties needed. The purpose of this work is neither to develop an extensive database nor to provide new experimental results or measurement methods. Instead, its specific aim is to collect and assess the available data for soda-lime

silicate glass. Particular attention was paid to the properties of the most common composition [74 SiO<sub>2</sub>-16 Na<sub>2</sub>O-10 CaO (mol.%)] of soda-lime silicate glass or similar compositions over the temperature range of 1000 to 2000 K. The thermophysical properties of the molten glass have been previously reported [11] and need not be reproduced. Discussion of the gas physicochemical properties used as input parameters to the numerical simulations is included in the next subsection and is limited to oxygen and carbon dioxide gases. Additional data for nitrogen, water vapor, and sulfure dioxide are given in Ref. [12].

## 2.1 Surface Tension

The surface tension depends on the temperature, the bulk glass composition, the atmosphere composition, and the ions dissolved in the melt such as the sulfate [13]. The effect of all those parameters are discussed in detail by Schulze [10]. In brief, surface tension decreases with increasing temperature and the fraction of CaO and Na<sub>2</sub>O. The surface tension of the system 74 SiO<sub>2</sub>-16 Na<sub>2</sub>O-10 CaO (mol.%) soda-lime silicate glass/air is given by [10, 14],

$$\sigma(T) = 321.7 - 0.04 \times (T - 1173.15) \quad \text{in mN/m} \quad (1)$$

The above expression is assumed to be independent of the gas, i.e., Equation (1) is used for both carbon dioxide/ and oxygen/soda-lime silicate glass systems. However, it has been observed experimentally that the surface tension of soda-lime silicate glass was reduced by the presence of gases having a non-zero dipole moment in the atmosphere [15]. Water vapor has been identified as having the most significant effect on the surface tension. At temperatures larger than 600°C, however, the effect of water vapor has been considered to be negligible [10, 13]. The effect of the atmosphere on the surface tension is of great importance



in the formation of glass foam [13,16], and even a small surface tension depression can have a significant effect on the foam thickness as shown experimentally by Ghag *et al.* [17] for water+78% glycerine solution. Unfortunately, no data is reported in the literature for the change of surface tension with water vapor pressure at high temperatures; therefore, this effect will not be considered further.

## 2.2 Gas Diffusion Coefficient in the Glassmelt

The most extensive diffusion measurements have been made for fused silica, since this glass is one of the most permeable to gases. Unfortunately, for other types of glass, a few measurements concerning gases other than helium and hydrogen are available [18]. The variation of the diffusion coefficient of the gas species “i” in a glassmelt as a function of temperature is known to follow an Arrhenius type of law [19]:

$$D_i = D_{0,i} \exp(-\Delta H_{D,i}/RT) \quad (2)$$

where  $D_{0,i}$  and  $\Delta H_{D,i}$  are empirically determined constants.

Diffusion coefficient of oxygen in the molten glass varies significantly from one type of glass to another as shown by Doremus [20]. Very often the soda-lime silicate glass composition was not available even though it is well known that the gas diffusion coefficients and solubilities can depend significantly on the glass composition. A fit of the experimental data presented by Terai and Oishi [21] gives the following expression for the diffusion coefficient of oxygen in 71.7 SiO<sub>2</sub>-15.5 Na<sub>2</sub>O-12.8 CaO (mol.%) soda-lime silicate glass:

$$D_{O_2} = 3.2 \times 10^{-6} \exp(-21076/T) \quad (3)$$

A fit of data reported by Doremus [20] for a commercial soda-lime silicate glass leads to the following expression:

$$D_{O_2} = 1.14 \times 10^{-3} \exp(-24946/T) \quad (4)$$

Unfortunately, the composition of the glass studied by Doremus [20] is unknown and it is believed to contain other elements such as MgO and Al<sub>2</sub>O<sub>3</sub> [19]. The discrepancies among experimental data are assumed to be due the differences in the glass compositions. It was decided to use the data reported by Terai and Oishi [21] since they cover a wider range of temperatures, and the glass studied has a very similar composition to that of interest in the present study, i.e., 74 SiO<sub>2</sub>-16 Na<sub>2</sub>O-10 CaO (mol.%).

The only additional information available in the literature concerning the diffusion coefficient of carbon dioxide in soda-lime silicate glass is the following expression proposed by Nemec and Muhlbauer [22]

$$D_{CO_2} = 7.95 \times 10^{-9} \exp[-11332/(T - 473.4)] \quad (5)$$

### 2.3 Gas Solubility in the Glassmelt

Gases can dissolve in the glassmelt by physical and/or chemical dissolution. Physical dissolution consists of occupying free spaces in the network of the molten glass. Physical solubility is higher for small gas molecules and increases slightly with temperature [10]. Gases can also dissolve chemically, i.e., they react chemically and create bonds with the glass structure.

Solubility is the amount of dissolved gas per unit mass of melt per unit of applied pressure and is expressed in many different units. The common unit is the volume of gas at standard temperature and pressure (STP, 0°C and 1 atm) per unit volume of material exposed at one

atmosphere of gas ( $\text{m}^3 \text{ (STP)}/\text{m}^3\text{atm}$ ). It can also be expressed in  $\text{kg}/\text{m}^3\text{Pa}$ . Doremus [18] pointed out that these definitions contain implicitly a temperature dependence since the applied pressure follows the ideal gas law,  $P=nRT/V$ . Instead, Doremus [18] suggested the use of ‘‘Ostwald solubility’’ defined as the ratio of the concentration of the gas in the material  $C_i$  and the concentration of the gas in the surrounding atmosphere  $C_g$ ,

$$S_{i,Os} = \frac{C_i}{C_g} \quad (6)$$

In the present work, however, solubility will be expressed in moles of gas per unit volume of liquid phase per unit external partial pressure of the gas ( $\text{mol}/\text{m}^3\text{Pa}$ ) as used in the most common form of the Henry’s law. The relationships between the different units for solubility are:

$$1[\text{mol}/\text{m}^3\text{Pa}] = \frac{1}{RT_{STP}}[\text{m}^3(\text{STP})/\text{m}^3\text{atm}] = \frac{1}{RT}S_{i,Os} \quad (7)$$

where  $R$  is the universal gas constant ( $=8.314\text{J}/\text{molK}$ ),  $T$  is the temperature, and  $T_{STP}$  is the temperature at the standard atmosphere ( $=273.15\text{K}$ ). In the following sections the solubility is expressed in  $\text{mol}/\text{m}^3\text{Pa}$  and is assumed to follows an Arrhenius type of law:

$$S_i = S_{i,0}exp(\Delta H_{S,i}/RT) \quad (8)$$

where  $S_{0,j}$  and  $\Delta H_{S,i}$  are constants determined experimentally.

The solubility of oxygen depends strongly on the glass composition [23]. The presence of suitable elements of variable valence such as antimony oxide or arsenic can increase the solubility [23]. The only collected data concerning the solubility of oxygen in soda-lime silicate is [23],

$$S_{O_2} = 2.2 \times 10^{-4} \quad \text{in mol}/\text{m}^3\text{Pa} \quad (9)$$

An expression of solubility of carbon dioxide is available in the literature and compares well with reported experimental data [22]:

$$S_{CO_2} = 3.45 \times 10^{-6} \exp(3840/T) \quad \text{in mol/m}^3\text{Pa} \quad (10)$$

## 2.4 Refining Reactions

The present study is concerned with antimony pentoxide used as the refining agent and decomposing according to the reaction  $Sb_2O_5 \rightleftharpoons Sb_2O_3 + O_2 \uparrow$ . Kawachi and Kawase [4, 5] and Kawachi and Kato [24] showed that the rate of the backward reaction can be neglected in the production of TV-panel glass. Therefore, the refining reaction can be considered as irreversible with only the decomposition of  $Sb_2O_5$  taking place. Reaction rate constants and order of the refining reaction involving antimony oxide in TV-panel glass can be found in the literature [24]. The same refining reaction characteristics were assumed to hold also for soda-lime silicate glasses. Antimony oxide is considered for the following reasons: the refining reaction produces only oxygen whose concentration in the glassmelt has to be computed, and the reaction is complete and irreversible so that refining agent concentration can be computed independently from the dissolved gas concentrations  $C_{\infty,i}$  and the bubble density function  $f_1$ . Treatment of equilibrium refining reactions, such as these involving sodium sulphate  $Na_2SO_4$ , would consist of including the computation of the refining agent concentration into the iterative scheme for the dissolved gas concentrations and the bubble density function to account for their interdependence. In addition, when sodium sulfate is used as a refining agent both oxygen and sulfur dioxide  $SO_2$  are generated during the refining process. Then, they dissolve in the glassmelt and can diffuse in and out of the bubbles [13, 25]. Therefore,

concentrations of both oxygen and sulfure oxide dissolved in the molten glass and their molar fractions in the bubbles should be computed along with those of carbon dioxide. The bubbles are then characterized by six independent variables (e.g.,  $x, y, z, r, \gamma_{CO_2}, \gamma_{O_2}$ ) making the numerical scheme quite involved. Such a situation falls beyond the scope of the present study whose main objective is to demonstrate the feasibility of the calculations.

Finally, it has not been possible to find the diffusion coefficient of the refining agent in soda-lime silicate glass.

## 3 Results and Discussion

### 3.1 Model Glass Tank and Parameters

The same glass melting tank as that used for three-dimensional flow and thermal structures of molten glass was considered [11, 26]. It is a rectangular bath 15.85 m long, 7.315 m wide, and 1.03 m deep (see Figure 1). The molten glass exits the tank through a throat having a cross-sectional area of  $0.386 \times 0.802 \text{ m}^2$  which is located at the bottom and in the middle of the front wall. The raw batch material leading to a glassmelt of composition of 74 SiO<sub>2</sub>-16 Na<sub>2</sub>O-10 CaO (mol.%) is introduced into the tank at a rate  $\dot{m}_b$  of 356 tons/day (or 4.12 kg/s) in the form of a loose blanket covering the entire width of the tank. Since about 200 kg of gases are produced per ton of batch introduced [27], the corresponding glass production rate (pull rate)  $\dot{m}_{pull}$  is 297 tons/day (or 3.347 kg/s) of molten glass.

The simulations consider an oxy-fuel furnace burning methane and oxygen at stoichiometric conditions at atmospheric pressure according to reaction  $\text{CH}_4 + 2\text{O}_2 \rightarrow 2\text{H}_2\text{O} + \text{CO}_2$ .

Thus, the partial pressures of oxygen and carbon dioxide at the glassmelt/combustion space interface are taken as 0.0 and  $p_0/3$ , respectively.

The energy  $\Delta H_{melt}$  required to bring the batch from room temperature (320 K) to clear molten glass and the melting temperature  $T_{melt}$  were taken equal to 2200 kJ/kg and 1450 K, respectively [28]. A linear decrease of the glassmelt velocity at the batch/glassmelt interface from 0.2 cm/s where the batch enters the furnace to zero at the tip of the batch blanket was chosen to simulate the fact that the batch blanket becomes thinner and less compact from the loading end to the tip. The maximum batch velocity of 0.2 cm/s was computed based on the pull rate of 4.12 kg/s for a batch blanket covering the entire width and having a density of 1400 kg/m<sup>3</sup> and a thickness of 20 cm. Moreover, from previous work [26] based on the momentum equation for a batch blanket at rest projected onto the vertical axis, a depth of 10.4 cm of the batch blanket was assumed to be submerged under the free glass surface.

The heat losses between the glassmelt and the ambient surroundings through the walls were computed assuming 1-D heat conduction through the refractories and cooling of the walls by natural convection using an ambient temperature of 320 K. The construction of the sidewall refractories were considered to be the same, with an overall heat transfer coefficient of 3.86 W/m<sup>2</sup>K. At the bottom of the tank the overall heat transfer coefficient equals 3.89 W/m<sup>2</sup>K and that at the back and front wall is equal to 5.57 W/m<sup>2</sup>K.

The net heat flux incident from the combustion space and reaching the surface of the batch and of the molten glass is assumed to have the longitudinal profile shown in Figure 2, where the parameters  $q''_{max}$  and  $q''_0$  are the maximum heat flux and the heat flux at the back wall ( $x = 0$  m), respectively. The distance from the back wall to the location of the maximum heat flux is  $L_{max}$  and the distance where the heat flux vanishes is  $L_0$ . They were assumed

to be equal to 7.5 m and 13.84 m, respectively. Such a heat flux profile was chosen based on industrial practices [11]. The three-dimensional flow and thermal structures of the molten glass for the above conditions have been presented and discussed in details in Ref. [11, 26] and need not be repeated here. Only the temperature, velocity, and streamlines at midplane in the longitudinal direction are reproduced in Figure 3. One can see that a part of the pull current flows directly from under the batch along the bottom of the tank to the throat as experimentally observed by Zhiqiang and Zhihao [29]. Thus the product quality is expected to be degraded due to the shorter residence time of the glassmelt in the tank.

### 3.2 Analysis of the Results

The calculations yield the value of the bubble density function  $f_1$ , the bubble radius  $r$ , and the molar fraction of each gas contained in the bubbles  $\gamma_i$  at each scalar nodes as well as the concentration(s) of gas(es) dissolved in the melt. The amount of information obtained from the computer program is very large and not easily interpretable unless it is reduced to physical quantities. Therefore, for a better interpretation of the computational results the bubble density function  $f_1$  and the bubble radius  $r$  were converted into more physical and understandable local variables such as the total number of bubbles  $N$ , the interfacial area concentration  $A_i$ , the volume fraction of the gas phase  $f_v$ , the average bubble radius  $\bar{r}$  and the average carbon dioxide molar fraction  $\bar{\gamma}_{CO_2}$  at each scalar grid point  $(x_I, y_J, z_K)$ . For bubbles containing a single gas or a diffusing and a non-diffusing gas, only one independent internal variable ( $r$ ) is considered and  $N$ ,  $A_i$ ,  $f_v$ ,  $\bar{r}$ , and  $\bar{\gamma}_{CO_2}$  are defined, respectively, as

$$0^{th} \text{ moment} \quad N(x, y, z) = \int_0^\infty f_1(x, y, z, r) dr \quad (11)$$

$$1^{st} \text{ moment} \quad \bar{r}(x, y, z) = \left[ \int_0^\infty r f_1(x, y, z, r) dr \right] / N(x, y, z) \quad (12)$$

$$1^{st} \text{ moment} \quad \bar{\gamma}_{CO_2}(x, y, z) = \left[ \int_0^\infty \gamma_{CO_2} f_1(x, y, z, r) dr \right] / N(x, y, z) \quad (13)$$

$$2^{nd} \text{ moment} \quad A_i(x, y, z) = \int_0^\infty 4\pi r^2 f_1(x, y, z, r) dr \quad (14)$$

$$3^{rd} \text{ moment} \quad f_v(x, y, z) = \int_0^\infty \frac{4\pi r^3}{3} f_1(x, y, z, r) dr \quad (15)$$

In the case of single component gas bubbles  $\bar{\gamma}_{CO_2}(x, y, z, r) = 1$ . If several diffusing gases are treated, additional internal variables have to be considered and the above integrals become multiple integrals with respect not only to variable  $r$  but also to other internal variables  $\gamma_i$ . Note also that, unlike discretized formulations previously suggested [3], which divide the bubble size distribution in groups and solve the population balance equation for the number of bubbles in each group, the present formulation and the associated method of solution compute directly the bubble density function  $f_1$  enabling accurate predictions of any moments of the density function and in particular the zero (N), first ( $\bar{r}$  and  $\bar{\gamma}_{CO_2}$ ), second ( $A_i$ ), and third ( $f_v$ ) order moments. The above single integrals are computed numerically using the Simpson's rule of integration for unequally spaced data [30].

### 3.3 Numerical Method

In order to validate the numerical implementation of the backward method of characteristics, computations of the bubble radius and density function for simple physical situations having closed-form analytical solutions have been performed [31]. Very good agreement between numerical predictions and analytical solutions for  $r$ , and  $f_1$  have been reported for one and two dimensional flows and transient and steady-state situations [31].

Numerical difficulties arise due to the fact that many key variables (e.g., the pressure



inside the bubbles  $p_b$ ) are functions of  $1/r$  which tend to infinity as the bubble radius decreases. However, extremely small bubbles cannot be physically treated in the same manner as macroscale bubbles due, for example, to gas rarefaction effects, and the limits of the concept of surface tension at very small scale. To avoid the numerical problems and account for physical limitations of the model, bubbles are considered to disappear when their radius becomes less than  $1.0 \mu\text{m}$  as suggested by Kawachi and Kawase [5]. Then, the bubble radius  $r$  and the bubble density function  $f_1$  are arbitrarily set to  $1.0 \mu\text{m}$  and zero, respectively, corresponding effectively to a sink term in the bubble population balance equation.

The grid sensitivity study for the spatial discretization has been previously performed for the velocity and temperature fields [11]. The entire glass bath was discretized using the  $66 \times 39 \times 25$  staggered grid used for computing the glassmelt flow and thermal structures [11, 26]. The same grid was used for the refining agent concentration and the concentrations of gases dissolved in the molten glass. The steady state was estimated to be reached when the residual for these variables fell below an arbitrarily small constant  $\epsilon_1$ . The steady-state for the bubble density function  $f_1$ , the bubble radius  $r$ , and the gas molar fraction  $\gamma_{CO_2}$  is assumed to be reached when the maximum relative variation of the predicted variables between two consecutive iterations over the computational domain fall under an arbitrarily small constant  $\epsilon_2$ , i.e.,

$$\text{Max} \left[ \frac{|X_{I,J,K}^{(n-1)} - X_{I,J,K}^{(n)}|}{|X_{I,J,K}^{(n-1)}|} \right] \leq \epsilon_2 \quad \text{for} \quad 1 \leq I \leq 66, 1 \leq J \leq 39, \text{ and } 1 \leq K \leq 25 \quad (16)$$

where  $n$  denotes the iteration number,  $X$  is the general symbol for  $r$ ,  $f_1$ , and  $\gamma_{CO_2}$ , while  $I, J, K$  are the indices for the scalar nodes of the staggered grid in the  $x$ -,  $y$ -, and  $z$ -directions, respectively. Numerical results for  $C_{\infty, i}$ ,  $r$ ,  $f_1$ , and  $\gamma_{CO_2}$  at steady state were found to be

independent of  $\epsilon_1$  and  $\epsilon_2$  provided that  $\epsilon_1 \leq 10^{-5}$  and  $\epsilon_2 \leq 4. \times 10^{-3}$ .

Moreover, in order to reduce computational time and still provide adequately accurate results, grid sensitivity studies have been conducted to choose the suitable number of points taken on the initial bubble density function that gives grid-independent numerical results for  $N$ ,  $A_i$ ,  $\bar{r}$ ,  $\bar{\gamma}_{CO_2}$ ,  $f_v$ , and  $C_{\infty,CO_2}$ . Numerical sensitivity tests have been made with 6, 11, and 22 points on the initial bubble density function as represented in Figure 4. For all simulations, the results  $N$ ,  $A_i$ ,  $\bar{r}$ , and  $f_v$ , for the same simulated time differed by less than 1.5% between 11 and 22 points. Therefore, 11 points on the initial distribution are sufficient to obtain a solution independent of the number of points considered on the initial distribution. The time step was proven to have no influence on the final results as long as at least two consecutive points on the pathlines are contained in any elementary computational volume of the  $66 \times 39 \times 25$  staggered grid.

Unfortunately, no experimental data for full scale industrial glass melters are available to quantitatively validate the numerical results. Comparison with numerical results reported in the literature [3, 5, 6] were made when available. Such comparison with results for the local number of bubbles obtained by Balkanli and Urgan [3] may be misleading since, as pointed out in the first part of the study [1], the boundary conditions used, the expression for the time rate of change of bubble radius, the decoupling of the gas concentration and the bubble population balance equations are questionable. Moreover, the method of solution based on the discretized formulation cannot predict accurately the other moments of the bubble density function such as  $\bar{r}$ ,  $\bar{\gamma}_{CO_2}$ ,  $A_i$ , and  $f_v$  [32, 33]. The next two sections present results of sample calculations for the physical situations when bubbles contain only  $CO_2$  and when bubbles contain both  $CO_2$  as a non-diffusing gas and  $O_2$  as a diffusing gas, respectively.

### 3.4 Bubbles Containing a Single Gas

Previous studies solving the bubble population balance equation have been concerned only with carbon dioxide bubbles and have neglected the coupling between the concentration of gas dissolved in the molten glass and the bubble population balance equation [3]. This assumption has been made for the sake of simplicity but has not been justified on physically or numerically sound arguments. However, the gas contained in single component gas bubbles can only diffuse out of the bubbles since the gas concentration at the bubble/glassmelt interface at equilibrium  $C_{e,i}$  given by the Henry's law is always larger than the gas solubility in the glassmelt [Ref. [1], Equation (27)]. Bubbles shrink due to gas diffusion while they can grow or shrink due to pressure changes; therefore, the presence of bubbles may be a significant source for the gas dissolved in the molten glass and decoupling the gas concentration and the bubble density function may not be appropriate. This section presents and discusses the results when carbon dioxide is the only diffusing gas considered. It represents a limiting case of practical applications since even when no refining agent is added to the batch, water vapor generated in the combustion space, which has a large diffusion coefficient and solubility in the glassmelt [19], dissolves in the melt and diffuses in the bubbles. The situation considered is highly idealized in order to (1) show the feasibility of the calculations, (2) compare with similar simulations previously reported in the literature [2, 3, 7], and (3) assess the effect of bubbles on the concentration of gases dissolved in the molten glass that was neglected in previous studies [2, 4–6].

The size distribution of bubbles generated by fusion/melting of the raw materials and

used as a boundary condition is assumed to follow a gamma distribution defined as

$$f_1(\vec{x}_{batch}, r, t) = Ar^\eta \exp(-Br) \quad (17)$$

the three constants  $A$ ,  $B$ , and  $\eta$  are positive and real numbers determined from experimentally measured quantities such as the radius  $r_{max}$  at which the density function reaches a maximum, the total number of bubbles per unit volume of liquid  $N$ , and the volumetric void fraction  $f_v$ . These quantities can be related to the constants  $A$ ,  $B$ , and  $\eta$  by

$$r_{max} = \left(\frac{\eta}{B}\right), \quad N = \frac{A\Gamma(\eta + 1)}{B^{\eta+1}}, \quad \text{and} \quad f_v = \frac{4\pi A\Gamma(\eta + 4)}{3B^{\eta+4}} \quad (18)$$

where  $\Gamma(z)$  is the gamma function [ $\Gamma(z) = \int_0^\infty e^{-t}t^{z-1}dt$ ] which has been tabulated by Abramowitz and Stegun [34]. Based on experimental results reported in the literature [5, 35, 36],  $r_{max}$ ,  $N$ , and  $f_v$  under the batch were taken to be 98  $\mu\text{m}$ , 2,240 bubbles per cubic centimeter of glass, and 4%, respectively, leading to constants  $A=3.23 \times 10^{26} \text{ m}^{-7}$ ,  $B = 3.05 \times 10^4 \text{ m}^{-1}$ , and  $\eta=3$ . The corresponding average bubble radius and interfacial area concentration are 112  $\mu\text{m}$  and 609  $\text{m}^2/\text{m}^3$  of glass, respectively. Note that the problem of conservation of the total number of bubbles raised in the first part of the study is not of concern here since the bubble growth/shrinkage rate is very small, owing to the small diffusion coefficient and solubility of carbon dioxide in the glassmelt and due to the small temperature and viscosity gradients, i.e.,  $\partial w_r / \partial r \approx 0.0$  [see Equation (59) in Ref.pilon2003-1], as checked and confirmed numerically.

First, numerical simulation for the  $\text{CO}_2$  concentration in the glassmelt neglecting the presence of bubbles has been performed. Figure 5a shows the concentration of carbon dioxide dissolved in the glass bath obtained at the midplane. The figure reveals a fairly uniform carbon dioxide concentration along the glass bath with a sharp concentration gradient close

the glass free surface. The relatively uniform carbon dioxide concentration can be explained by the good mixing caused by advective currents and indicates that advection dominates over diffusion [7]. The dominance of advection over diffusion explains also the sharp concentration gradient under the glassmelt surface since in this region the molten glass flows parallel the free surface and transport of carbon dioxide in the normal direction (z-direction) takes place only by diffusion. The lower concentration at the surface of the glass bath is due to the fact that solubility decrease exponentially with temperature [see Equation (10)]. The temperatures at the glass free surface are larger than those under the batch by about 250K [26]. Thus, the CO<sub>2</sub> concentration imposed at the glassmelt/combustion space interface is much smaller than that imposed at the glassmelt/batch interface. Overall, numerical predictions of the CO<sub>2</sub> concentration agree well with those reported by Balkanli and Ungan [7]. However, these authors while using the same boundary conditions and the same expression for the carbon dioxide solubility as those of the present study did not mention the partial pressure of carbon dioxide at the glassmelt/combustion space interface used in their numerical simulations. The value of 0.001 kg/m<sup>3</sup> they reported at the glass surface tends to indicate that they imposed a very small partial pressure of CO<sub>2</sub> at the glassmelt/combustion space interface, whereas it should be fairly large since CO<sub>2</sub> and water vapor are the main products of the combustion.

Second, the CO<sub>2</sub> concentration is computed by accounting for the source term owing to CO<sub>2</sub> diffusion out of the bubbles. A converged solution was obtained after two full successive calculations for the CO<sub>2</sub> concentration  $C_{\infty,CO_2}$  in the glassmelt and the bubble radius  $r$  and density function  $f_1$ . Figure 5b shows the concentration of carbon dioxide dissolved in the glass bath at the midplane, while Figure 5c shows the relative difference in the CO<sub>2</sub> concen-

tration between Figures 5a and 5b. It indicates that accounting for gas diffusion out of the bubbles as a source term for carbon dioxide dissolved in the glassmelt does not significantly change the numerical results and the CO<sub>2</sub> concentration increases by less than 2% in most of the glass bath when diffusion out of the bubble is accounted for. Similar spatial distribution of iso-concentration lines can be obtained by shifting the concentration by +0.003 kg/m<sup>3</sup>. For example, the 0.185 kg/m<sup>3</sup> iso-concentration line when the presence of bubbles is neglected has a profile similar to the 0.188 kg/m<sup>3</sup> concentration line when the presence of bubbles is accounted for.

Finally, note that supersaturation (up to 50 %) of the glassmelt with CO<sub>2</sub> occurs under the batch and at the bottom of the tank (see Figure 6). This could lead to heterogeneous bubble nucleation if a large enough amount of undissolved sand grains is present in this region. Bubble nucleation could then result in secondary foam formation in the region beyond the batch tip as commonly observed in industrial glass melting furnaces [13]. Then, secondary foam would be generated not only by bubbles rising from the glassmelt but also from bubbles generated due to oversaturation of the glassmelt and nucleation at the unmelted sand grain surface. However, it is beyond the scope of the present study to investigate such a complex phenomena.

The hypothetical situation in which bubbles would be injected at the batch/glassmelt interface at time  $t=0$ s and would grow or shrink and be transported in the glassmelt by advection currents has been simulated. Figure 7 shows a series of iso-concentration lines for the total number of bubbles per unit volume of glass  $N$  at midplane for 1, 2, 3, and 4 hours after the beginning of injection. The iso-concentration lines propagates with the glass flow from under the batch to the front wall and then move up toward the free surface

before sinking again under the batch. It clearly shows the transport of bubbles by convective currents from under the batch to the refining section and the throat. It also demonstrates the capability of the computer program based on the backward method of characteristics to simulate transient problems. Convergence to steady state is very slow owing to the complexity of the flow field, the small velocities of the glassmelt, and the slow transport phenomena taking place in the glassmelt. In industrial glass melting furnaces, it is estimated that it can take up to two days for the a glassmelt fluid particle to flow from under the batch to throat corresponding to 320,000 time steps to be computed for each points taken on the initial bubble size distribution (see Figure 4).

Numerical results for the total number of bubbles at steady-state at different cross-sections in the longitudinal direction are shown in Figure 8. One can observe the predominance of the bubble transport in the longitudinal direction and no significant changes in the profile of the total number of bubbles from the midplane ( $y/W=0.5$ ) to the side wall ( $y=W=0.01$ ) are evident. Moreover, the total number of bubbles entrapped in the glass melt is large and relatively uniform due to the small diffusion coefficient of  $\text{CO}_2$  in the glassmelt and the good mixing provided by convection currents.

The steady-state numerical results for the total number of bubbles  $N$ , the average bubble radius  $\bar{r}$ , the interfacial area concentration  $A_i$ , and the void fraction  $f_v$ , respectively at the midplane ( $z/W=0.5$ ) are presented in Figures 9a to 9d and correspond to a simulated time of 48 hours. As one can see,

- a large number of bubbles remain in the glassmelt including near the glassmelt free surface,

- the average bubble radius decreases slightly as the bubbles are transported by the convection currents from under the batch to the refining section owing to the small diffusion coefficient of CO<sub>2</sub> in the glassmelt,
- A large bubble concentration gradient exist near the free surface since only large bubbles escape to the free glassmelt surface. Indeed, the glassmelt flowing near the free surface from the hot spot toward the batch prevents the smallest bubbles from reaching the surface. These bubbles are too small for the buoyancy force to overcome the strong convection currents in the horizontal plane near the surface of the molten glass. Thus, small bubbles get trapped in the first recirculation loop located in the first half of the tank and significantly fewer bubbles are trapped in the second recirculation loop located closed to the front wall.
- Finally, Figures 9a and b indicate that a large number of bubbles with an average diameter between 70 and 100  $\mu\text{m}$  are transported from the batch through the submerged throat as they are carried by advection when the glassmelt is being pulled. Note also that the average bubble diameter increases near the throat. This is attributed to gas expansion due to the increase of the bubble temperature as they rise back to the glassmelt surface after being carried along the bottom of the tank. This results in a poor glass quality and productivity but was expected given the glassmelt flow pattern discussed earlier. It is, therefore, interesting to investigate the impact of the refining agent on the bubble behavior since refining gases diffuse in the bubbles to enable the bubbles to rise to the glassmelt surface by buoyancy before reaching the throat.



### 3.5 Bubbles Containing Two Different Gases

Bubble growth in the glassmelt can only be due to the diffusion of gases such as oxygen, water vapor, and sulfur oxide that have a large diffusion coefficient and a large enough solubility [37]. Bubble growth is obtained by adding refining agents to the batch that produce such gases. The present example is limited to the important practical situations when antimony pentoxide  $\text{Sb}_2\text{O}_5$  is added to the raw batch materials as a refining agent. The refining agent concentration is needed to compute the oxygen concentration dissolved in the glassmelt and diffusing in and out of the bubbles. It can be computed independently from the other variables since refining reactions are assumed to be irreversible and complete. However, since the diffusion coefficient of the refining agent and the reaction rate constants of the refining reaction involving antimony oxide in soda-lime silicate glass could not be obtained from the literature, the refining agent concentration has not been computed. Instead, the oxygen concentration dissolved in the glassmelt was assumed to be equal to saturation at the local temperature and pressure everywhere in the glass bath. This can be justified by the fact that oxygen is supplied in great amount during the melting of batch. Thus, its concentration in the glassmelt under the batch should be uniform as shown for  $\text{CO}_2$ . Furthermore, unlike  $\text{CO}_2$ , oxygen is also generated by refining reactions in the refining section of the tank where the temperatures are large allowing refining reactions to occur. Finally, convection currents produce good mixing that leads to uniform oxygen concentration in the glassmelt similar to that observed for carbon dioxide. The same sharp concentration gradient at the glassmelt/combustion space interface observed for  $\text{CO}_2$  is expected for  $\text{O}_2$  since the boundary condition for the oxygen concentration is  $C_{\infty, \text{O}_2} = 0.0$  at the glassmelt/combustion space

interface. This concentration gradient is neglected since it is very sharp and highly localized to a small depth in the glassmelt.

In the case under consideration, both carbon dioxide and oxygen dissolved in the glassmelt or contained in the bubbles have to be considered. Carbon dioxide is generated during the melting of calcium carbonate while oxygen is released by the decomposition of nitrates such as  $\text{NaNO}_3$  and of the refining agent [25]. For a typical soda-lime silicate glass batch without refining agent, experimental analysis of gases released during batch melting and fusion [38,39] indicate that significantly more (at least 15 times)  $\text{CO}_2$  is generated than other gases. But, oxygen is generated by refining reactions. Therefore, as a first order approximation, bubbles located under the batch are assumed to contain both  $\text{CO}_2$  and  $\text{O}_2$  at equal molar fraction, i.e.,  $\gamma_{\text{CO}_2} = \gamma_{\text{O}_2} = 0.5$ , at the batch/glassmelt interface. Since the diffusion coefficient and solubility of carbon dioxide are at least one order of magnitude smaller than those of oxygen [37,40,41] over the temperature range 1000 K to 2000 K, carbon dioxide is treated as a non-diffusing gas and only oxygen is assumed to diffuse in and out of the bubbles. This assumption has the advantage of simplifying the numerical algorithm by avoiding two-dimensional numerical integration from scattered data points for the amount of gas diffusing from the glassmelt to the bubbles  $\dot{m}_{diff}$  [see part I, equation (17)]. Such integration would require bivariate interpolation and smooth surface fitting onto an equally space fixed grid for initial values given at irregularly distributed points [42,43], before performing the double integration by repeated one-dimensional numerical integration using Simpson's rule [30].

Moreover, the number of moles of carbon dioxide contained in the bubbles remain constant while the  $\text{CO}_2$  molar fraction changes due to oxygen diffusion. The  $\text{CO}_2$  molar fraction

in the bubbles at location  $z$  having radius  $r$  and temperature  $T$  is expressed as

$$\gamma_{CO_2} = 1 - \gamma_{O_2} = \frac{T(p_0 + 2\sigma/r_0)}{T_{melt}(p_0 + \rho_\infty gz + 2\sigma/r)} \left(\frac{r_0}{r}\right)^3 \gamma_{CO_2}^0 \quad (19)$$

The initial bubble radius of a point of the initial bubble density function under the batch is  $r_0$ . The initial bubble temperature equals the batch melting temperature  $T_{melt}$  taken as 1450 K. Finally, the initial molar fraction of  $CO_2$  in the bubbles is given by  $\gamma_{CO_2}^0$  while the bubbles are assumed to be initially located in the plane  $z=0$  m. Since  $CO_2$  is assumed not to diffuse in or out of the bubbles, the bubbles can shrink until the molar fraction of  $CO_2$  becomes unity and the bubble radius reaches its minimum  $r_{min}$ , which can be determined by solving the following equation

$$(p_0 + \rho_\infty gz)r_{min}^3 + 2\sigma r_{min}^2 - (p_0 r_0^3 + 2\sigma r_0^2) \frac{T}{T_{melt}} \gamma_{CO_2}^0 = 0 \quad (20)$$

Figures 10a to 10d show the numerical results for the total number of bubbles per unit volume of glass N, the average bubble radius  $\bar{r}$ , the average molar fraction of  $CO_2$ , the interfacial area concentration  $A_i$ , and the volumetric gas fraction  $f_v$ . As one can see, most of the bubbles are located under the batch where the interfacial area concentration and the void fraction are the largest. Compared with the case when only  $CO_2$  is considered one can conclude that (1) less and smaller bubbles are present in the glassmelt and particularly near the glassmelt surface and at the throat, (2) bubbles are more located around the batch blanket and do not cover the entire glassmelt surface, (3) the average diameter of bubbles leaving the tank at the throat is between 10 and 60  $\mu\text{m}$  compared with 70 to 100  $\mu\text{m}$  when only  $CO_2$  is considered, (4) the average  $CO_2$  molar fraction (not plotted here) increases relatively quickly as bubbles move away from the batch blanket and is almost uniform across the glass bath. This can be explained by the fact that oxygen diffuses out of the bubbles

much faster than carbon dioxide ( $D_{O_2} > D_{CO_2}$ ). Therefore, the main mechanism of refining is bubble dissolution or absorption. Similar results have been also obtained numerically by Kawachi and Iwatsubo [6] for similar simulated conditions when the hot spot was located at about 2/3 of the total furnace length and the concentration of oxygen dissolved in the glassmelt was large and almost uniform.

## 4 Conclusions

This paper presents numerical results for sample calculations of bubble transport, growth or shrinkage in three-dimensional laminar gravity driven flow based on the model presented in details in the first part with applications to glass melting furnaces. The following conclusions can be drawn:

- The present study demonstrate the feasibility of solving the bubble population balance equation in three-dimensional laminar gravity driven flow for both transient and steady-state situations using the backward method of characteristics.
- Detail calculations of the bubble density function enables one to compute any  $m^{th}$  order moments of the density function and in particular, the total number of bubble, the average bubble radius, the average gas molar fraction, the interfacial area concentration and the void fraction.
- Due to the small liquid velocities and the slow diffusion process, the calculation time of the current computer program is excessive and constitutes a limitation to its use. This issue could be easily addressed by parallelizing the computation of the solution of

the population balance equation. Indeed, solution of the population balance equation for two different points on the initial bubble density function is currently performed successively on a single microprocessor computer even though they are independent. Therefore, they should be performed in parallel on a multiprocessors computer with as many microprocessors as points taken on the initial bubble density function. This measure will divide the current computational time by the number of microprocessors used.

- Bubble nucleation at the sand grain surface may be significant and should be modeled since oversaturation of the glassmelt with carbon dioxide and oxygen appear to be important. To do so, the density function of unmelted sand grains is needed in order to know the number of nucleation sites. It could be computed by the same method as that presented here for the bubble density function. A different expression for the growth rate  $\dot{r}$  will have to be used and is already available in the literature [44, 45].
- Nucleation at the refractory walls has been neglected for the sake of simplicity. However, it could be easily accounted for by modeling of heterogeneous nucleation at the refractory walls and by computing the transport of the generated bubbles in a similar manner to that presented above. Finally, the solution is obtained by adding the density functions for bubbles injected from under the batch or from the refractory walls based on the superposition principle.
- It shows that considering the oxygen diffusion in and out of the bubbles has a significant effect on the number and size of bubbles leaving and remaining in the glassmelt. More realistic simulations should include detailed computation of the refining reaction and

gas concentrations dissolved in the glassmelt provided that all the thermophysical properties needed be available.

## References

- [1] L. Pilon, A.G. Fedorov, D. Ramkrishna, and R. Viskanta, “Bubble transport and generation in glass melting furnaces. part I. mathematical formulation”, *Journal of Non Crystalline Solids*, (submitted for publication), 2003.
- [2] B. Balkanli and A. Urgan, “Numerical simulation of bubble behaviour in glass melting tanks. Part 3. bubble trajectories”, *Glass Technology*, vol. 37, no. 4, pp. 137–142, 1996.
- [3] B. Balkanli and A. Urgan, “Numerical simulation of bubble behaviour in glass melting tanks. Part 4. bubble number density distribution”, *Glass Technology*, vol. 3, no. 5, pp. 164–168, 1996.
- [4] S. Kawachi and Y. Kawase, “Evaluation of bubble removing performance in a TV glass furnace. Part 1. mathematical formulation”, *Glastechnische Berichte*, vol. 71, no. 4, pp. 83–91, 1998.
- [5] S. Kawachi and Y. Kawase, “Evaluation of bubble removing performance in a TV glass furnace. Part 2. verification using real furnace data”, *Glastechnische Berichte*, vol. 71, no. 5, pp. 111–119, 1998.
- [6] S. Kawachi and Y. Iwatsubo, “Diagnosis and treatment of bubbles in glass production using a numerical simulator”, *Glastechnische Berichte*, vol. 72, no. 7, pp. 207–213, 1999.

- [7] B. Balkanli and A. Ungan, “Numerical simulation of bubble behaviour in glass melting tanks. Part 2. gas concentration”, *Glass Technology*, vol. 37, no. 3, pp. 101–105, 1996.
- [8] R. G. C Beerkens and H. De Wall, “Mechanism of oxygen diffusion in glassmelts containing variable-valence ions”, *Journal of the American Ceramic Society*, vol. 73, no. 7, pp. 1857–1861, 1990.
- [9] M. Cable and J.R. Frade, “Theoretical analysis of the dissolution of multi-component gas bubbles”, *Glastechnische Berichte*, vol. 60, no. 11, pp. 355–362, 1987.
- [10] H. Scholze, *Glass nature, structure and properties, 3rd. Edition*, Springer-Verlag, Berlin, 1991.
- [11] L. Pilon, G. Zhao, and R. Viskanta, “Three-dimensional flow and thermal structures in glass melting furnaces. Part I. Effects of the heat flux distribution”, *Glass Science and Technology*, vol. 75, no. 2, pp. 55–68, 2002.
- [12] L. Pilon, *Interfacial and transport phenomena in closed-cell foams*, PhD thesis, Purdue University, West Lafayette, IN, USA, 2002.
- [13] P. R. Laimbock, *Foaming of glass melts*, PhD thesis, Technical University of Eindhoven, Eindhoven, The Netherlands, 1998.
- [14] A. Dietzel, “Praktische bedeutung von berechnung der oberflächenspannung von gläsern, glasuren und emails”, *Sprechsaal*, vol. 75, pp. 82–85, 1942.
- [15] N. M. Parikh, “Effect of atmosphere on surface tension of glass”, *Journal of the American Ceramic Society*, vol. 41, pp. 18–22, 1958.

- [16] A. G. Fedorov and L. Pilon, “Glass foam: formation, transport properties, and heat, mass, and radiation transfer”, *Journal of Non-Crystalline Solids*, vol. 311, pp. 154–173, 2002.
- [17] S. S. Ghag, P. C. Hayes, and H-G Lee, “Physical model studies on slag foaming”, *ISIJ International*, vol. 38, pp. 1201–1207, 1998.
- [18] R. H. Doremus, *Glass science*, John Wiley & Sons, New York, NY, 1994.
- [19] N. P. Bansal and R. H. Doremus, *Handbook of glass properties*, Academic Press, Inc., 1986.
- [20] R. H. Doremus, “Diffusion of oxygen from contracting bubbles in molten glass”, *Journal of the American Ceramic Society*, vol. 43, pp. 655–661, 1960.
- [21] R. Terai and Y. Oishi, “Self-diffusion of oxygen in soda-lime silicate glass”, *Glastechnische Berichte*, vol. 50, pp. 68–73, 1977.
- [22] L. Nemeč and M. Mühlbauer, “Verhalten von gasblasen in der glasschmelze bei konstanter temperatur”, *Glastechnische Berichte*, vol. 54, pp. 99–108, 1981.
- [23] M. Cable, “A study of refining. Part 2. Mechanisms of refining”, *Glass Technology*, vol. 2, no. 2, pp. 60–70, 1961.
- [24] S. Kawachi and M. Kato, “Evaluation of reaction rate of refining agents”, *Glastechnische Berichte*, vol. 72, no. 6, pp. 182–187, 1999.
- [25] J. E. Shelby, *Handbook of gas diffusion in solids and melts*, ASM International, Materials Park, OH, 1996.



- [26] L. Pilon, G. Zhao, and R. Viskanta, “Three-dimensional flow and thermal structures in glass melting furnaces. Part II. Effects of the presence of batch and bubbles”, *Glass Science and Technology*, vol. 75, no. 3, pp. 115–124, 2002.
- [27] C. Madivate, F. Müller, and W. Wilsmann, “Calculation of the theoretical energy requirement for melting technical silicate glasses”, *Journal of the American Ceramic Society*, vol. 81, pp. 3300–3306, 1998.
- [28] C. Madivate, “Calculation of the theoretical energy requirement for melting technical silicate glasses”, *Journal of the American Ceramic Society*, vol. 81, pp. 3300–3306, 1998.
- [29] Y. Zhiqiang and Z. Zhihao, “Basic flow pattern and its variation in different types of glass tank furnaces”, *Glastechnische Berichte*, vol. 70, pp. 165–172, 1997.
- [30] J. D. Hoffman, *Numerical Methods for Engineers and Scientists*, McGraw Hill, New York, NY, 1998.
- [31] L. Pilon and R. Viskanta, “Modified method of characteristics for solving the population balance equation”, *International Journal for Numerical Methods in Fluids*, vol. 42, pp. 1211–1236, 2003.
- [32] S. Kumar and D. Ramkrishna, “On the solution of population balance equation by discretization - III nucleation, growth, and aggregation of particles”, *Chemical Engineering Science*, vol. 52, no. 4, pp. 4659–4679, 1997.
- [33] D. Ramkrishna, *Population Balances*, Academic Press, San Diego, CA, 2000.

- [34] M. Abramowitz and I. A. Stegun, *Handbook of mathematical functions*, Dover Publications, New York, 1965.
- [35] A. Urgan, W.H. Turner, and R. Viskanta, “Effect of gas bubbles on three-dimensional circulation in a glass melting tank”, *Glastechnische Berichte*, vol. 56K, pp. 125–129, 1983.
- [36] M. Cable and A. A. Naqvi, “The refining of a soda-lime-silica glass with antimony”, *Glass Technology*, vol. 16, no. 1, pp. 2–11, 1975.
- [37] M. Cable and C. G. Rasul, “Spontaneous bubble formation in silicate melts at high temperatures: II, effect of we atmospheres and behavior of mixed alkali glasses”, *Journal of the American Ceramic Society*, vol. 50, no. 10, pp. 528–531, 1967.
- [38] J. Mukerji, A. K. Nandi, and K.D. Sharma, “Reaction in container glass batch”, *Ceramic Bulletin*, vol. 59, pp. 790–793, 1980.
- [39] F. Kramer, “Gasprofilmessugen zur bestimmung der gasabgabe beim glasschmeltprozeß”, *Glastechnische Berichte*, vol. 53, no. 7, pp. 177–188, 1980.
- [40] M. C. Weinberg, P. I. K. Onorato, and D. R. Uhlmann, “Behavior of bubbles in glassmelts: I, dissolution of a stationary bubble containing a single gas”, *Journal of the American Ceramic Society*, vol. 63, pp. 175–180, 1980.
- [41] J. I. Ramos, “Behavior of multicomponent gas bubbles in glass melts”, *Journal of the American Ceramic Society*, vol. 69, no. 2, pp. 149–154, 1986.

- [42] H. Akima, “A method of bivariate interpolation and smooth surface fitting for values given at irregularly distributed points”, *ACM Transactions on Mathematical Software*, vol. 4, no. 2, pp. 148–159, 1978.
- [43] H. Akima, “On estimating partial derivatives for bivariate interpolation of scattered data”, *Rocky Mountain Journal of Mathematics*, vol. 14, pp. 41–52, 1984.
- [44] M. K. Choudhary, “Dissolution of polydisperse silica grains in glass melts - analysis”, *Journal of the American Ceramic Society*, vol. 73, pp. 3053–3058, 1990.
- [45] A. Ungan, R. U. Payli, and B. Balkanli, “Numerical model of polydispersed silica grain dissolution in glass melting furnaces”, *Journal of the American Ceramic Society*, vol. 77, no. 7, pp. 1921–1927, 1994.

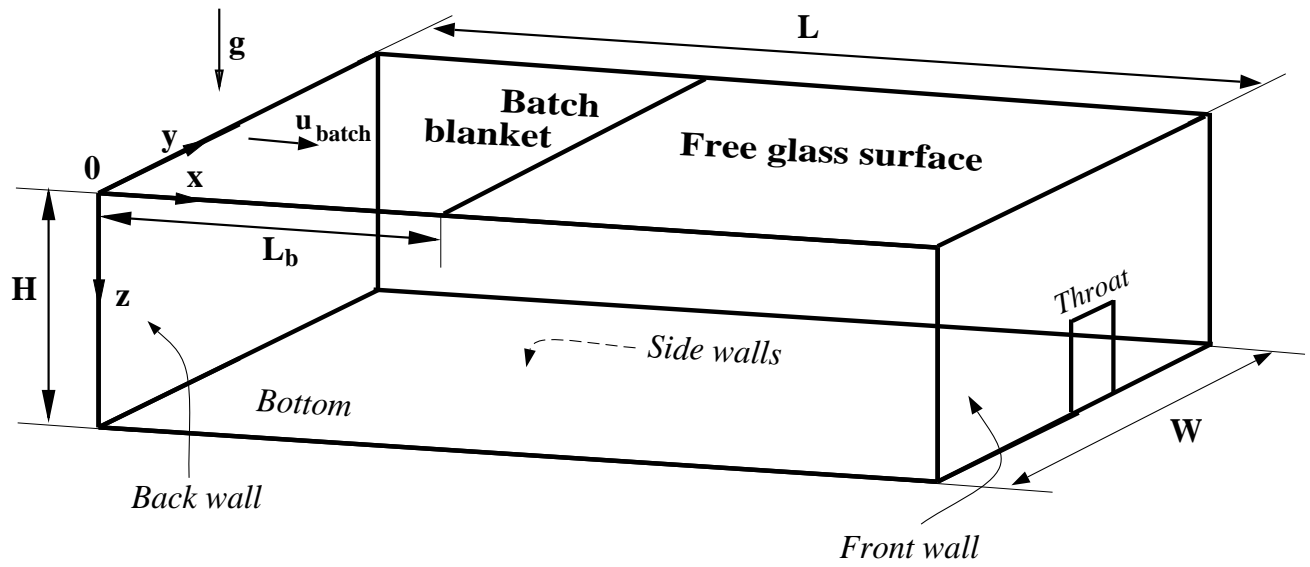


Figure 1: Schematic of the modeled glass melting tank and the associated systems of coordinates.

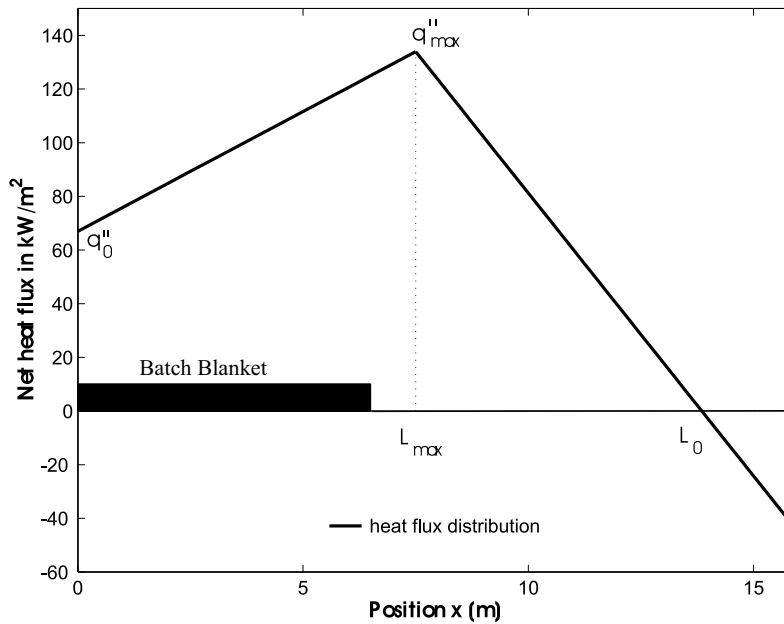


Figure 2: Heat flux distribution used as the boundary condition at the glassmelt/combustion space interface.

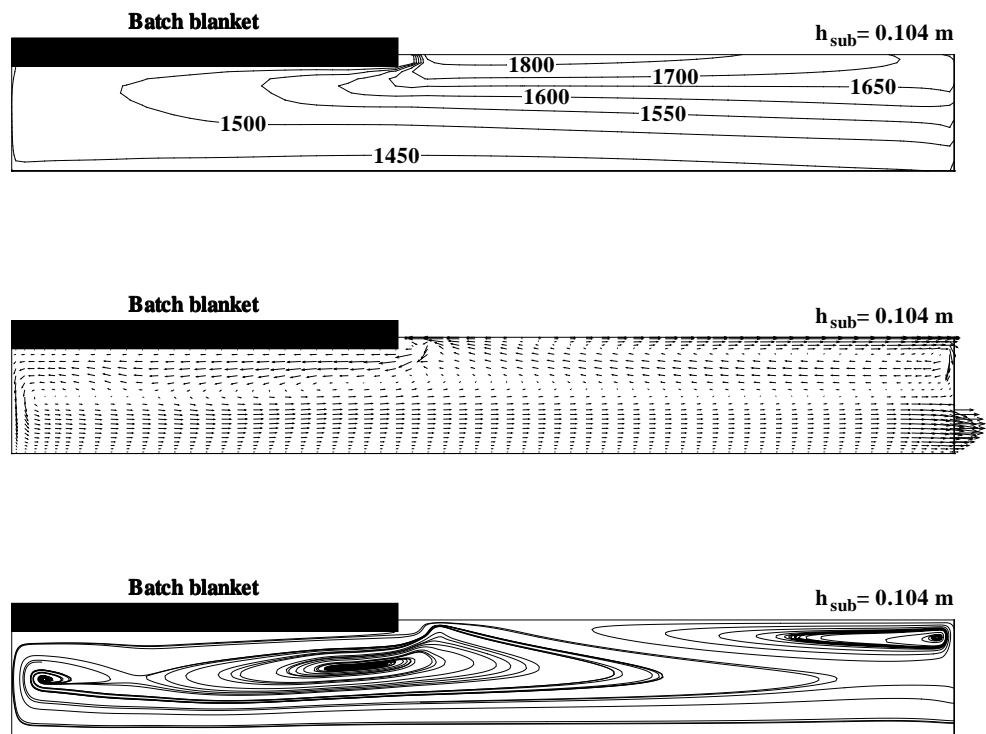


Figure 3: Flow field used as input parameter with from top to bottom (top) velocity field, (center) temperature field, and (bottom) streamtraces at the tank midplane.

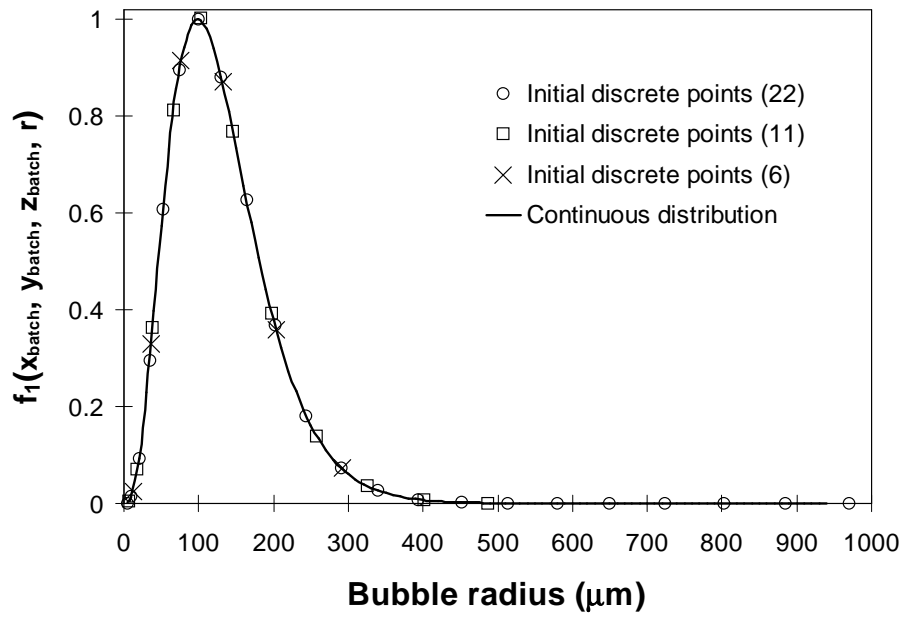


Figure 4: Initial bubble density function under the batch and arbitrary discrete set of points chosen for the simulations [Equation (17)].

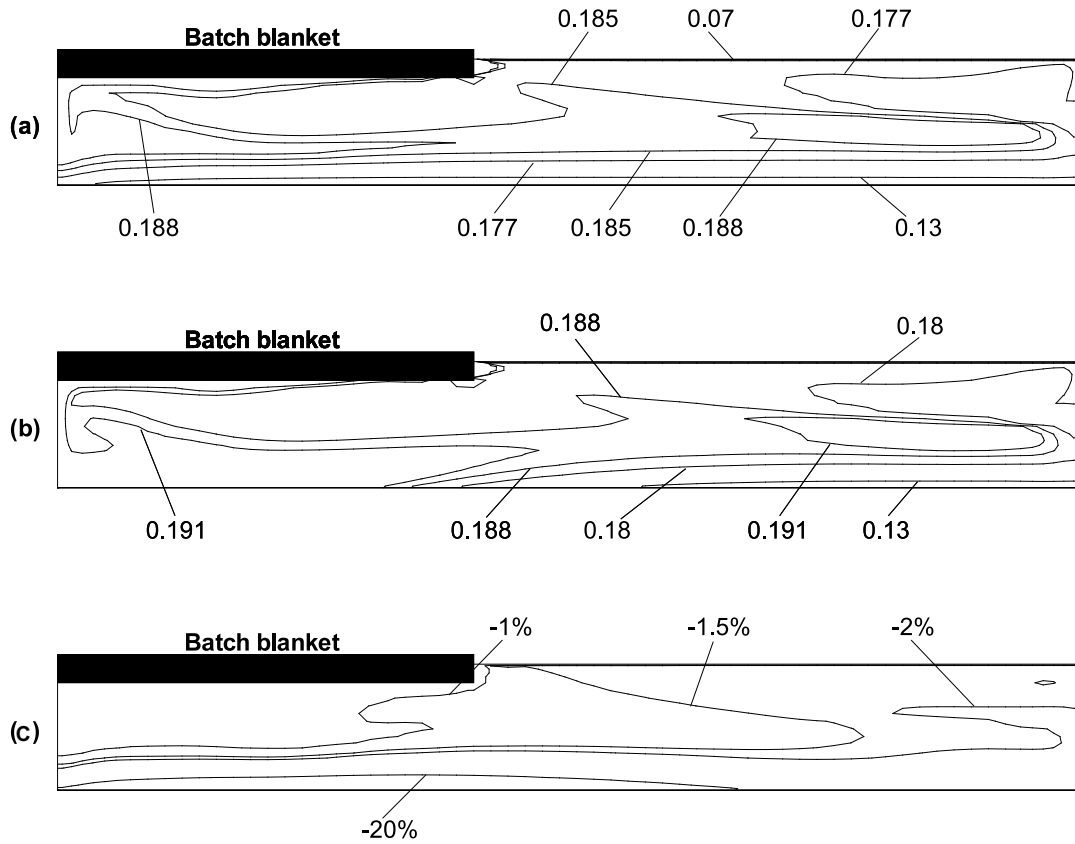


Figure 5: Dissolved CO<sub>2</sub> gas iso-concentration lines at midplane in kg/m<sup>3</sup> (a) without accounting for the presence of bubbles and (b) with accounting for the source term due to gas diffusion in and out of bubbles, and (c) relative difference (in %) between the local CO<sub>2</sub> concentrations in (a) and in (b).

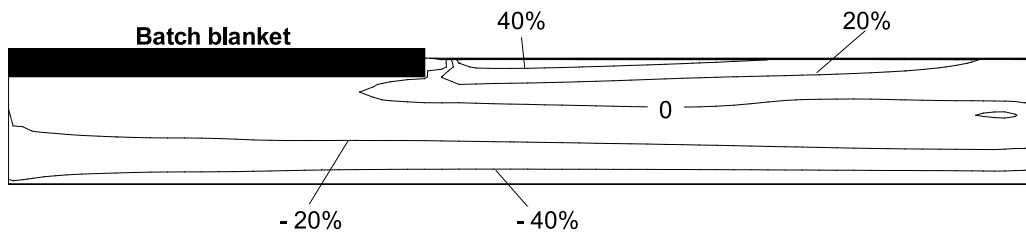


Figure 6: Relative difference between the local CO<sub>2</sub> saturation and CO<sub>2</sub> concentration (in %) at midplane accounting for the source term due to gas diffusion in and out of bubbles (negative values correspond to supersaturation).



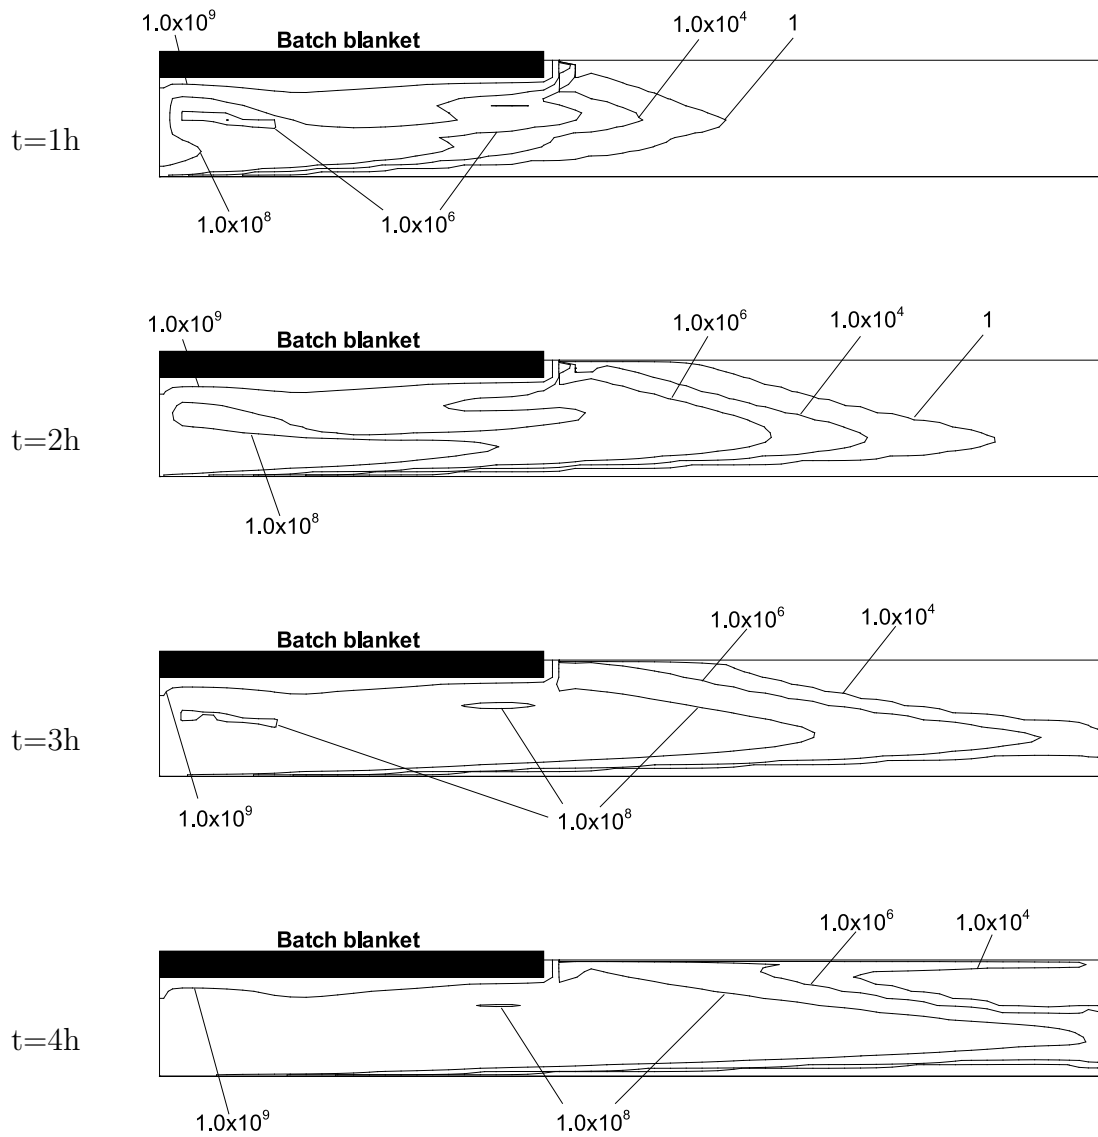


Figure 7: Evolution of iso-concentration lines with time for the total number of bubbles  $N$  (in  $\#/m^3$ ) at midplane.

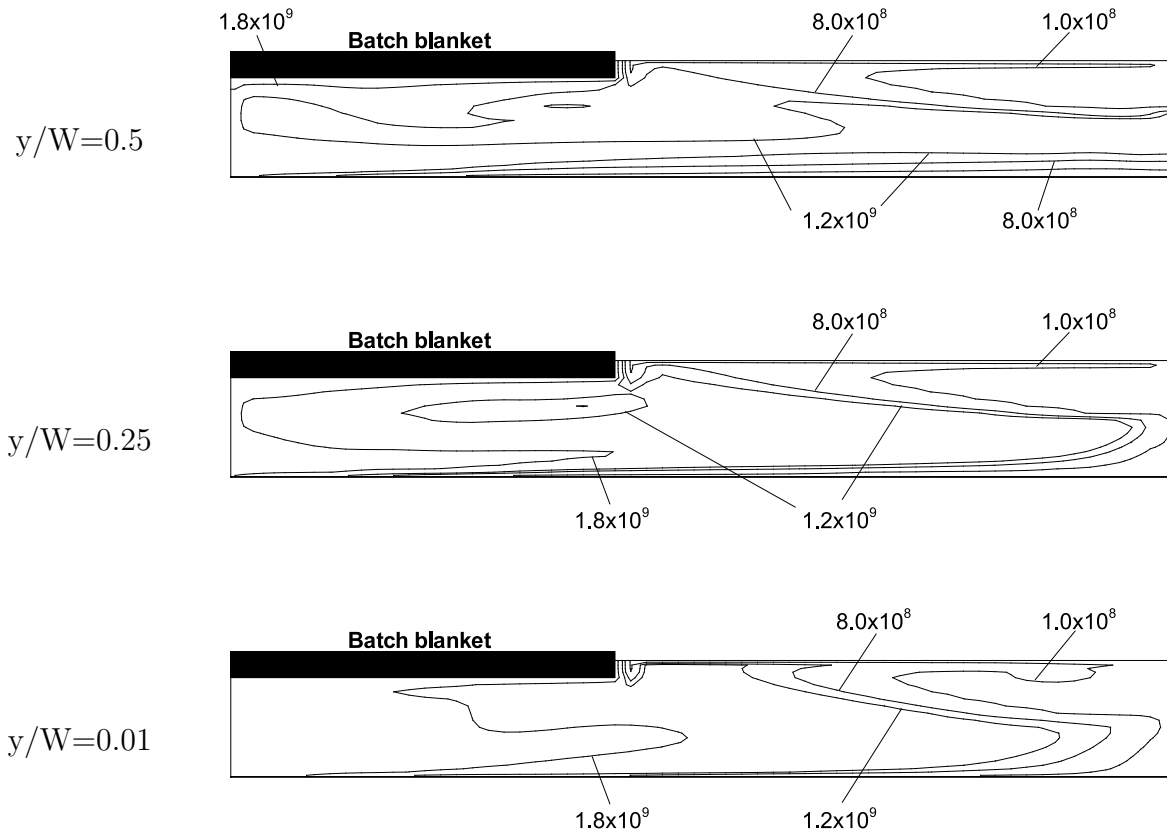


Figure 8: Steady-state iso-concentration lines for the total number of bubbles  $N$  (in  $\#/m^3$ ) at midplane  $y/W = 0.5$  (top), at  $y/W=0.25$  (center), and  $y/W=0.01$  (bottom).

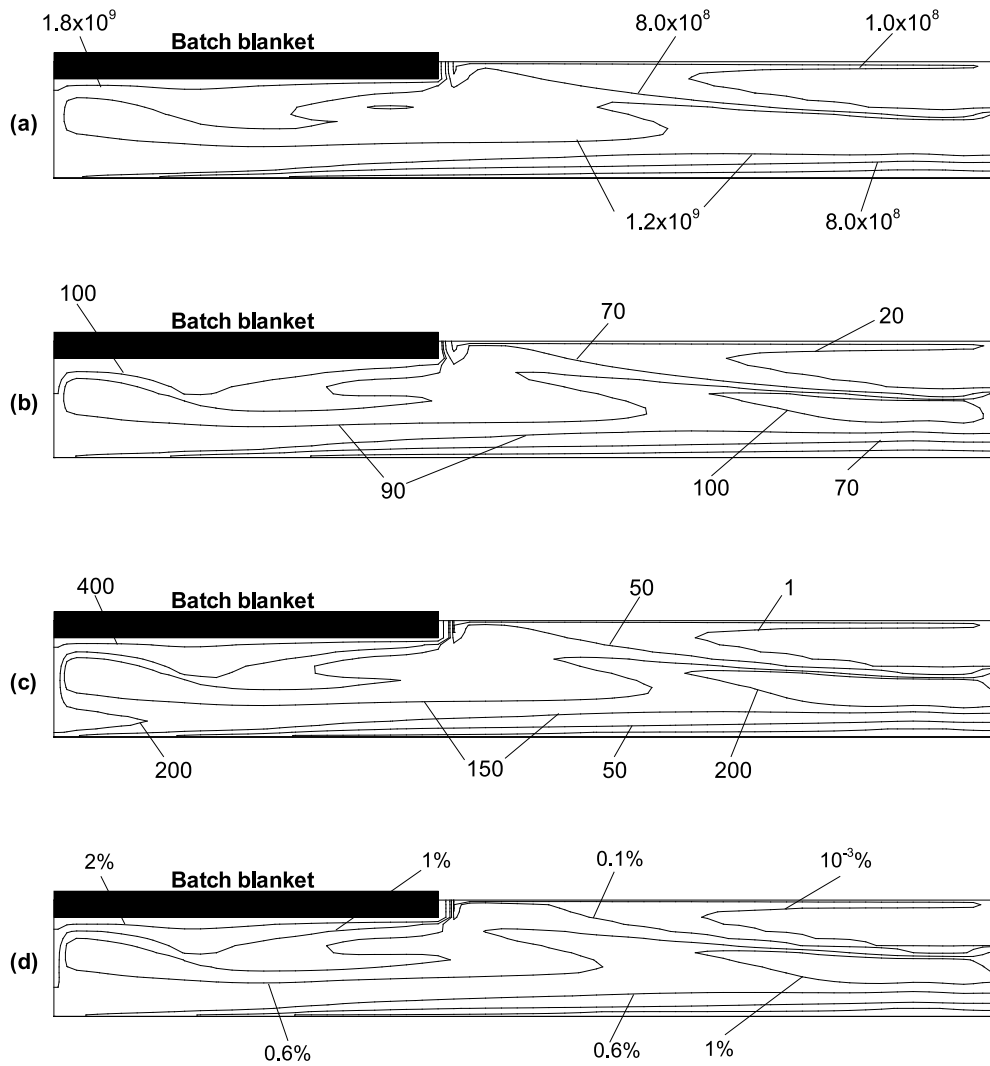


Figure 9: Iso-concentration lines at midplane for (a)  $N$  (in  $\#/m^3$ ), (b)  $\bar{r}$  (in  $\mu m$ ), (c)  $A_i$  (in  $m^2$  of interface /  $m^3$  of glassmelt), (d)  $f_v$  (in  $m^3$  of gas in bubbles /  $m^3$  of glassmelt) at midplane.

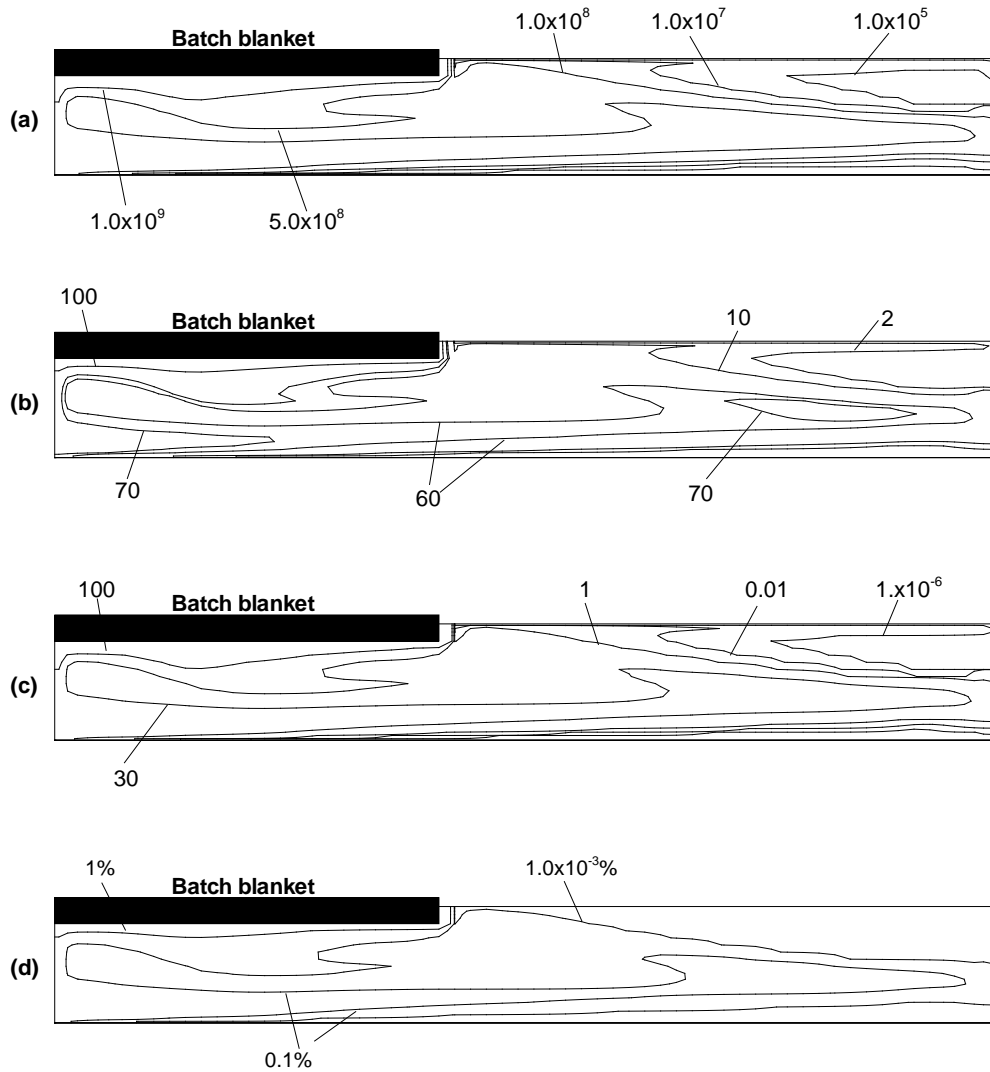


Figure 10: Iso-concentration lines at midplane for (a)  $N$  (in  $\#/m^3$ ), (b)  $\bar{r}$  (in  $\mu\text{m}$ ), (c)  $A_i$  (in  $\text{m}^2$  of interface /  $\text{m}^3$  of glassmelt), (d)  $f_v$  (in  $\text{m}^3$  of gas in bubbles /  $\text{m}^3$  of glassmelt).