

Lawrence Berkeley National Laboratory

Recent Work

Title

Origination of the "Linear" Term in the Specific Heat of $\text{YBa}_{2}\text{Cu}_{3}\text{O}_{7}$

Permalink

<https://escholarship.org/uc/item/3118w8tg>

Authors

Phillips, N.E.

Fisher, R.A.

Gordon, J.E.

et al.

Publication Date

1989-07-01



Lawrence Berkeley Laboratory

UNIVERSITY OF CALIFORNIA

Materials & Chemical Sciences Division

Presented at the Conference on Materials and Mechanisms of Superconductivity, High-Temperature Superconductors, Stanford, CA, July 23-28, 1989, and to be published in Physica C

Origin of the "Linear" Term in the Specific Heat of $\text{YBa}_2\text{Cu}_3\text{O}_7$

N.E. Phillips, R.A. Fisher, J.E. Gordon, and S. Kim

July 1989



Prepared for the U.S. Department of Energy under Contract Number DE-AC03-76SF00098.

1 LOAN COPY 1
1 Circulates 1
1 for 2 weeks 1

Bldg: 50 Library.

LBL-27541

Copy 2

DISCLAIMER

This document was prepared as an account of work sponsored by the United States Government. While this document is believed to contain correct information, neither the United States Government nor any agency thereof, nor the Regents of the University of California, nor any of their employees, makes any warranty, express or implied, or assumes any legal responsibility for the accuracy, completeness, or usefulness of any information, apparatus, product, or process disclosed, or represents that its use would not infringe privately owned rights. Reference herein to any specific commercial product, process, or service by its trade name, trademark, manufacturer, or otherwise, does not necessarily constitute or imply its endorsement, recommendation, or favoring by the United States Government or any agency thereof, or the Regents of the University of California. The views and opinions of authors expressed herein do not necessarily state or reflect those of the United States Government or any agency thereof or the Regents of the University of California.

ORIGIN OF THE "LINEAR" TERM IN THE SPECIFIC HEAT OF $\text{YBa}_2\text{Cu}_3\text{O}_7$ *

Norman E. Phillips, R. A. Fisher, J. E. Gordon[†], and S. Kim

Materials and Chemical Sciences Division, LBL, University of California, Berkeley, CA 94720, USA

We report measurements of the specific heat, C , of a number of samples of YBCO, and interpret the results as showing the existence of localized magnetic moments on the YBCO lattice that suppress the transition to the superconducting state. Both the extent of the transition [as measured, for example, by the "jump" in C at T_c , $\Delta C(T_c)$] and the magnitude of the low-temperature "linear" term in C , $\gamma(0)T$, are correlated with the concentration of these moments in the way expected for pair-breaking centers: $\gamma(0)$ increases and $\Delta C(T_c)/T_c$ decreases, both linearly, with increasing moment concentration. The contribution to $\gamma(0)$ associated with these pair-breaking centers, together with that previously recognized as arising from impurity phases, accounts completely for the observed $\gamma(0)$. We are not aware of other results that are inconsistent with these correlations, and conclude that there is no contribution to $\gamma(0)$ that is an intrinsic property of the superconducting state in YBCO.

There is reliable evidence that impurity phases which contain Cu^{2+} moments that order near 10K, most notably BaCuO_2 , contribute both to the high temperature susceptibility, χ , and to the zero field "linear" term, $\gamma(0)T$, in the low temperature specific heat of YBCO.¹ However, the experimental correlation between $\gamma(0)$ and χ , when combined with the fact that $\gamma(0)$ is rarely found to be $< -4\text{mJ/mole}\cdot\text{K}^2$, suggests there is a contribution to $\gamma(0)$ which is intrinsic to the superconducting state.

Most YBCO samples show an upturn in C/T at low temperatures which is converted to a Schottky-like anomaly by the application of a magnetic field.² These effects are evidence for Cu^{2+} moments which order below 1K in zero field. In the following we show evidence that these moments are located in the YBCO lattice and provide a pair-breaking mechanism that suppresses the superconducting transition, simultaneously reducing $\Delta C(T_c)$ and increasing $\gamma(0)$. The sum of this contribution to $\gamma(0)$ and that from impurity phases accounts completely for the observed value of $\gamma(0)$ and leads to the conclusion that there is no contribution intrinsic to the superconducting state. Nevertheless, allowing for the possibility of such an intrinsic contribution, γ_0 , we write, $\gamma(0) = \gamma_0 + n_1\gamma_1 + n_2\gamma_2$, γ_1 and γ_2 are the molal contributions to $\gamma(0)$ due to the impurity phase and to the Cu^{2+} moments in the YBCO lattice, and n_1 and n_2 are the number of moles of impurity phase and lattice moments, respectively. n_2 can be determined from the Schottky peak, and $n = n_1 + n_2$ from the high temperature

*Supported by the Director, Office of Energy Research, Office of Basic Energy Sciences, Materials Sciences Division of the U.S. Dept. of Energy under Contract DE-AC03-76SF00098, and by an EXXON Education Grant from the Research Corporation.

[†]Permanent Address: Physics Dept., Amherst College, Amherst, MA 01002,

measurements. A statistical analysis of the data on a number of YBCO samples gives $\gamma_0 = 0.1 \pm 0.8 \text{ mJ/K}^2 \cdot \text{mole}$, thereby indicating that superconducting YBCO has no intrinsic linear term. The analysis also gives $\gamma_1 = 106$ and $\gamma_2 = 1370 \text{ mJ/K}^2 \cdot \text{mole}$. Fig. 1 shows plots of $\gamma(0)$ and its components, $n_1\gamma_1$ and $n_2\gamma_2$ versus n , n_1 , and n_2 , respectively. The $\gamma(0)$ points have an rms deviation of 34% from the straight-line fit with non-zero intercept, while the other two plots have rms deviations of 14% from lines which pass through the origin.

The fraction of superconducting material can be inferred from the specific heat in various ways. Fig. 2 demonstrates the consistency of $\Delta C(T_c)/T_c$ with two other such measures, ΔS and $d\gamma/dH$. Fig. 3 shows the dependence of $\Delta C(T_c)/T_c$ and $n_2\gamma_2$ on n_2 . The decrease of $\Delta C(T_c)$ and the increase of $\gamma(0)$ (as manifested in the change of $n_2\gamma_2$ with n_2) are signatures of the operation of a pair-breaking mechanism, which provides a physical basis for understanding the n_2 -dependent contribution to $\gamma(0)$. Extrapolation of $\gamma_2 n_2$ to the value of n_2 at which $\Delta C(T_c)$ goes to zero provides an estimate of the normal-state value of γ , $\gamma = 14 \text{ mJ/K}^2 \cdot \text{mole}$. Together with the maximum value of $\Delta C(T_c)/T_c$, its value at $n_2 = 0$, this gives $\Delta C(T_c)/\gamma T_c = 6$ for the fully superconducting state. That ratio is substantially larger than the BCS weak-coupling limit, 1.43, and provides a measure of strong-coupling effects.

REFERENCES


1. A.P. Ramirez, et al. Mater. Res. Soc. Symp. 99 (1987) 459. R. Kuentzler, et al., Solid State Commun. 65 (1988) 1529. D. Eckert, et al., J. Low Temp. Phys. 73 (1988) 241.
2. R.A. Fisher et al., J. Superconductivity 1 (1988) 231.
3. C.-S. Jee, J. Superconductivity 1 (1988) 63.

FIGURE CAPTIONS

Fig. 1. $\gamma(0)$, $n_1\gamma_1$, and $n_2\gamma_2$ [$\gamma(0) = n_1\gamma_1 + n_2\gamma_2$] vs. $n = n_1 + n_2$, n_1 , and n_2 , respectively. The straight lines represent least-squares fits.


Fig. 2. Intercomparison of three measures of the fraction of superconducting material: ΔS , $d\gamma/dH$, and $\Delta C(T_c)/T_c$. $\Delta S = \int_{T'}^{T_c} [C(H=0) - C(T)]/T \, dT$, where T' is the temperature at which $C(H=0) = C(T)$. $d\gamma/dH$ is the field derivative of $\gamma(H)$ in the mixed state. The straight lines represent least-squares fits.

Fig. 3. $\Delta C(T_c)/T_c$ and $n_2\gamma_2$ vs. n_2 . The straight lines represent least-squares fits. $\Delta C(T_c)/T_c = 84(1 - 99n_2)$, $\gamma_2 = 1370$, $\gamma_1 = 106 \text{ mJ/K}^2 \cdot \text{mole}$.

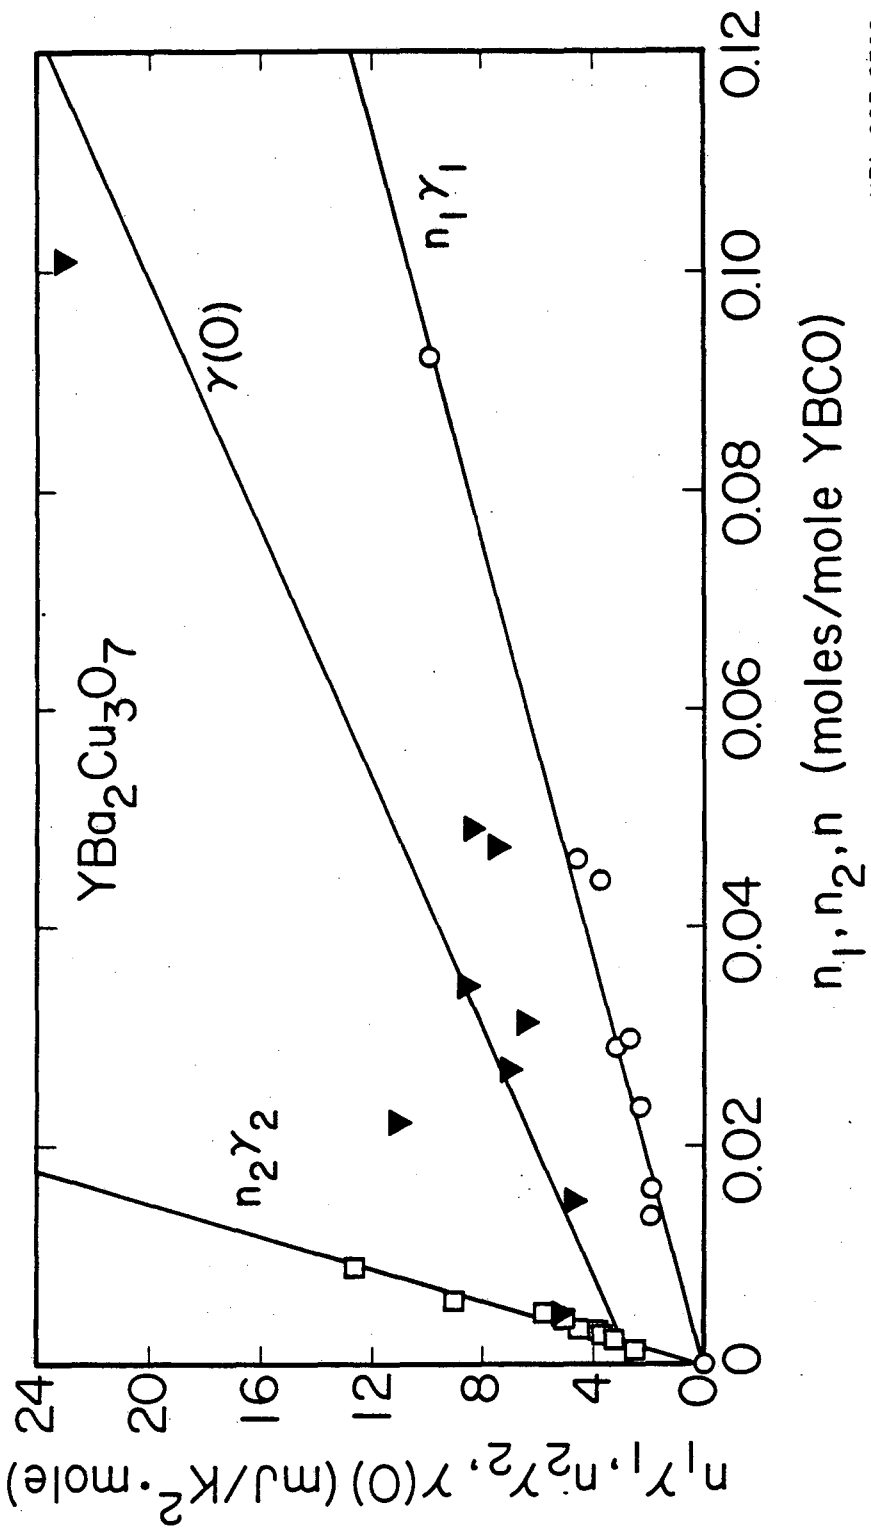


XBL 897-2700

FIG 1

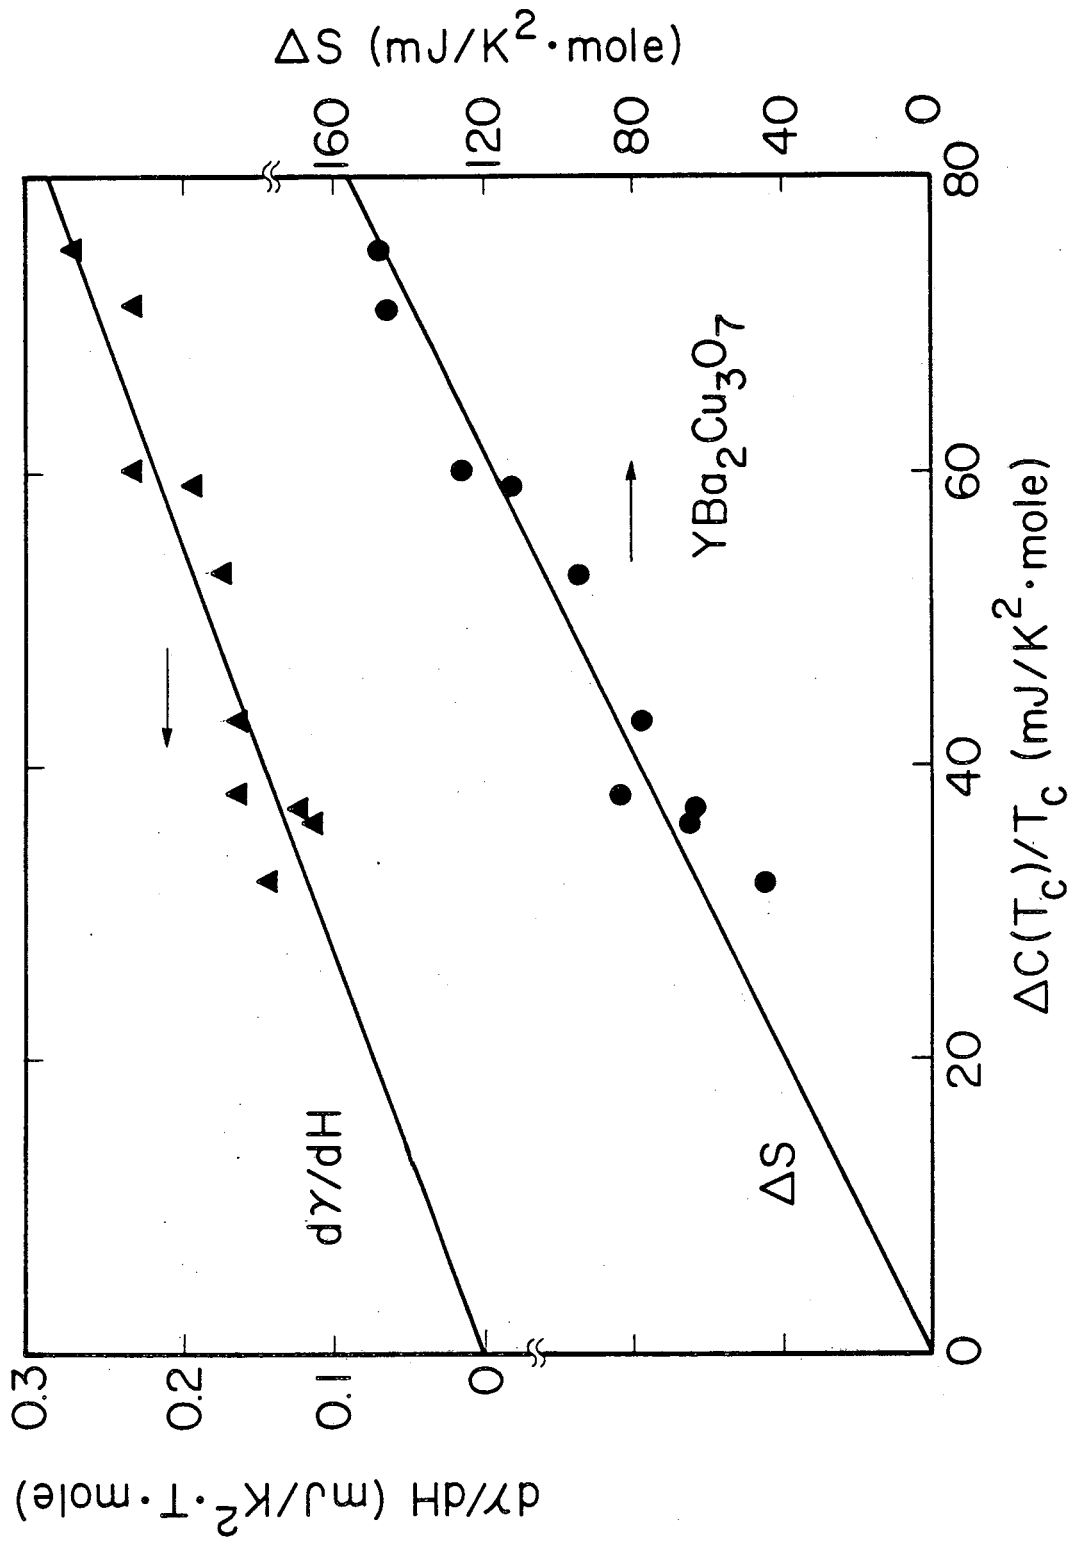

XBL 897-2702

FIG 2

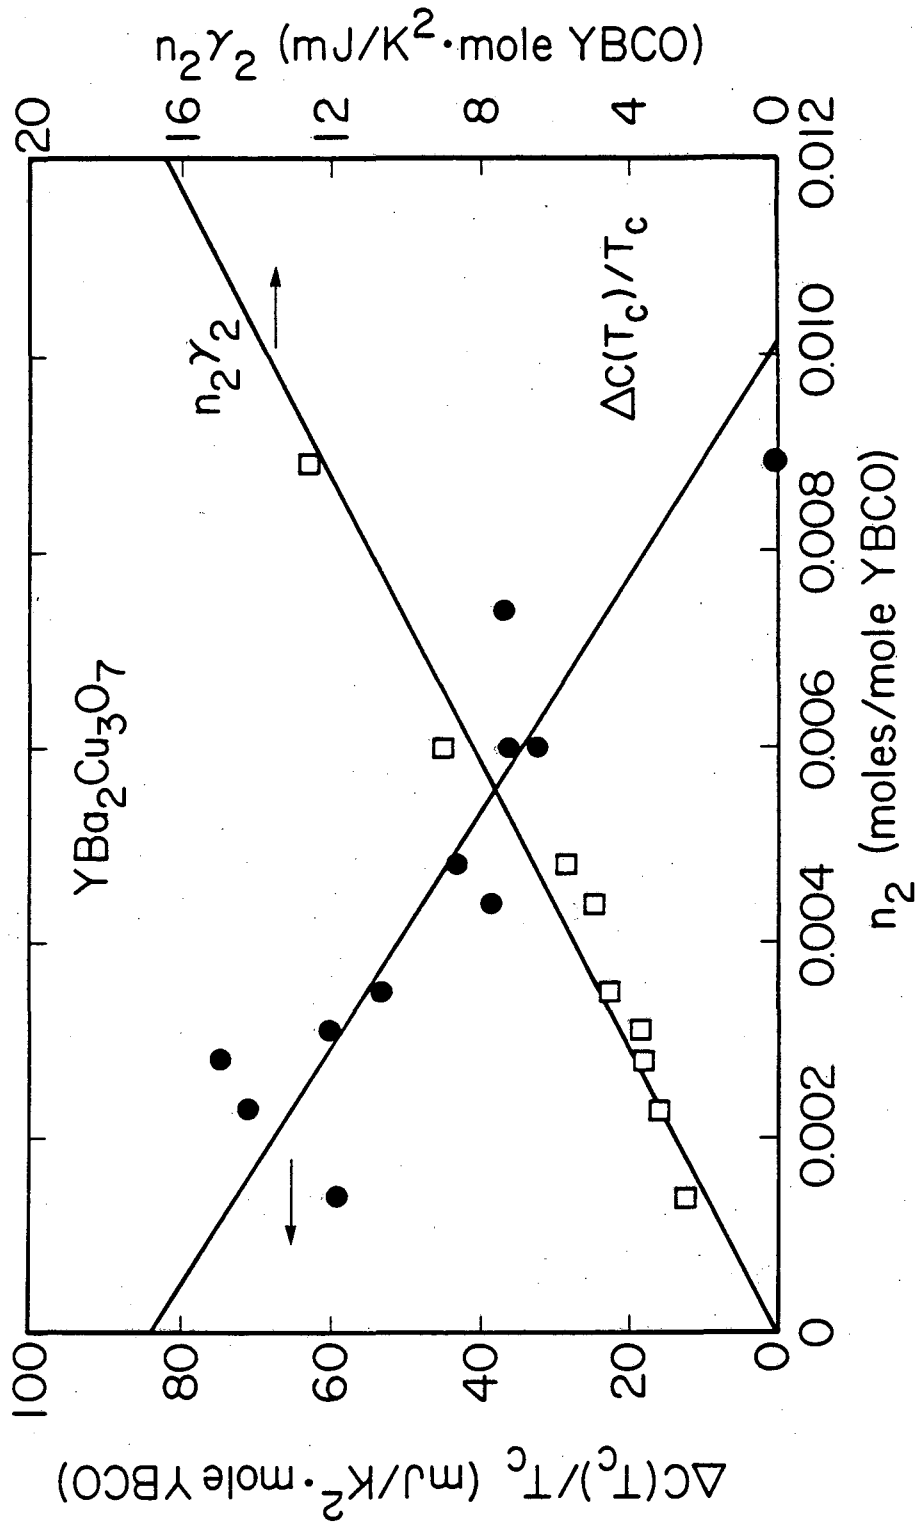

XBL 897-2701

FIG 3

LAWRENCE BERKELEY LABORATORY
TECHNICAL INFORMATION DEPARTMENT
1 CYCLOTRON ROAD
BERKELEY, CALIFORNIA 94720