

Lawrence Berkeley National Laboratory

LBL Publications

Title

Geometrical Frustration and Defect Formation in Growth of Colloidal Nanoparticle Crystals on a Cylinder: Implications for Assembly of Chiral Nanomaterials

Permalink

<https://escholarship.org/uc/item/33020316>

Journal

ACS Applied Nano Materials, 4(10)

ISSN

2574-0970

Authors

Tanjeem, Nabila
Wilkin, William H
Beller, Daniel A
[et al.](#)

Publication Date

2021-10-22

DOI

10.1021/acsnm.1c02126

Copyright Information

This work is made available under the terms of a Creative Commons Attribution-NonCommercial License, available at <https://creativecommons.org/licenses/by-nc/4.0/>

Peer reviewed

Geometrical Frustration and Defect Formation in Growth of Colloidal Nanoparticle Crystals on a Cylinder: Implications for Assembly of Chiral Nanomaterials

Nabila Tanjeem,[†] William H. Wilkin,[‡] Daniel A. Beller,[¶] Chris H. Rycroft,^{†,§} and
Vinothan N. Manoharan^{*,†,‡}

[†]*Harvard John A. Paulson School of Engineering and Applied Sciences, Harvard
University, Cambridge, MA 02138, USA*

[‡]*Department of Physics, Harvard University, Cambridge, MA 02138, USA*

[¶]*Department of Physics, University of California, Merced, CA 95343, USA*

[§]*Computational Research Division, Lawrence Berkeley Laboratory, Berkeley, CA 94720,
USA*

E-mail: vnm@seas.harvard.edu

Abstract

Using a combination of experiment and simulation, we study how two-dimensional (2D) crystals of colloidal nanoparticles grow on cylindrical substrates. The cylindrical geometry allows us to examine growth in the absence of Gaussian curvature but in the presence of a closure constraint – the requirement that a crystal loop back onto itself. In some cases, this constraint results in structures that have been observed previously in theory and nonequilibrium packing experiments: chiral crystals and crystals with linear defects known as “line slips.” More generally, though, the structures we see differ from

those that have been observed: the line slips are kinked and contain partial vacancies. We show that these structures arise because the cylinder changes how the crystal grows. After a crystal wraps around the cylinder and touches itself, it must grow preferentially along the cylinder axis. As a result, crystals with a chiral line-slip tend to trap partial vacancies. Indeed, we find that line slips that are less aligned with the cylinder axis incorporate more partial vacancies on average than ones that are more aligned. These results show that crystal growth on a cylinder is frustrated by the closure requirement, a finding that may shed some light on the assembly of biological nanosystems such as tobacco mosaic virus and might inform ways to fabricate chiral optical nanomaterials.

Keywords

colloidal crystallization, defects, frustration, crystal growth, self-assembly

1 Introduction

The morphology of a crystal depends on how it nucleates and grows. Consequently, the structure of a real crystal often differs from an idealized equilibrium structure or ground state.¹ The connection between morphology and growth was first made by Steno² in the 17th century, long before the atomic theory. In the 1950s, Frank and coworkers³ elucidated the relationships between crystal growth rates, thermal fluctuations, and atomic-scale structural features, including steps and defects. More recently, experiments on colloidal nanoparticles, which permit both structural details and growth⁴⁻⁸ to be directly visualized, have led to a new understanding of crystal growth.

In particular, colloidal systems have revealed that curved substrates can fundamentally alter crystal growth. Most studies have focused on the role of the substrate's Gaussian curvature, the product of its two principal curvatures. Owing to Gaussian curvature, large 2D crystals of colloidal spheres on a spherical substrate must incorporate topological defects.⁹⁻¹⁵

When these defects are energetically costly, the crystal alters its growth to avoid them. For example, 2D crystals composed of particles with short-ranged attractions grow isotropically on a flat surface but anisotropically on a sphere.^{16–19}

Here we explore how a cylindrical substrate affects the growth of 2D crystals of colloidal nanoparticles. At first glance, one would not expect a cylindrical substrate to modify how such a crystal grows in the same way that a spherical substrate does: a cylinder has zero Gaussian curvature (because the curvature is zero along one direction), and hence a crystal on a cylinder need not incorporate topological defects. Furthermore, a colloidal crystal on a cylinder – as opposed to one on a sphere – does not accrue stress as it grows. In other words, it would seem to have no way to “know” that it is on a curved surface.

However, this argument neglects one important feature of a cylindrical crystal: when it grows sufficiently large, it must meet itself, forming a closed loop. We show how this “closure constraint” affects how the crystal grows. On a plane, crystals do not have to contend with a closure constraint, and therefore we observe different patterns of growth and structure than are seen in planar crystals. On a sphere, crystals do contend with a closure constraint, and the effects of this closure constraint on spherical crystals have been studied in simulation.^{20,21} But for a sphere it is difficult to separate the effects of the global closure constraint from the local effects of Gaussian curvature, which leads to stress in a growing crystal. By examining a system with zero Gaussian curvature, we explore how closure alone might affect growth.

To this end, we first study the crystal morphologies and defects and then show what they reveal about growth. Most previous work on the morphologies of cylindrical crystals focuses only on idealized structures: densest packings and ground states. This problem dates back to (at latest) the 1830s, with Louis and Auguste Bravais’s mathematical analysis²² of phyllotaxis, the arrangement of leaves around a plant stem. More recently, Pickett and coworkers²³ showed that for certain values of the size ratio r – the ratio of the cylinder diameter to sphere diameter – the densest packings of hard spheres *inside* a cylinder are chiral crystals. They also found that between size ratios corresponding to these commen-

urate crystals, the densest packings incorporate linear defects now known as “line slips,” which consist of two parallel lines of spheres in which each sphere touches only five others. These defects have zero net Burgers vector.²⁴ Mughal and coworkers related these results to packings *on the surface of* a cylinder²⁵ (the phyllotactic problem) and showed that as the size ratio increases, the densest packings vary between achiral hexagonal packings, chiral hexagonal packings, and chiral hexagonal packings with line slips.²⁶ Later simulations by Wood and coworkers²⁴ showed that line slips can also occur in the ground states of particles with long-range attractions.

Our study differs in two ways from these theoretical studies and from the few experimental studies of sphere packings inside cylinders.^{27–30} First, we focus on *how* cylindrical crystals grow, and not just on their structures. Second, the interactions between our nanoparticles are comparable to the thermal energy $k_B T$, so that nanoparticles in a growing crystal can rearrange. In these two respects, the crystallization process we study is much more similar to a the self-assembly of a biological nanosystem than it is to phyllotactic growth. Thus, at the end of the paper, we compare our system to tobacco mosaic virus (TMV), which also self-assembles at finite temperature and forms a cylindrical structure.

As we shall show, the closure constraint fundamentally alters the way the crystal grows, as evidenced by the random incorporation of a new type of defect (the partial vacancy) into the line slips. We find that crystals with highly helical line-slips are more frustrated than crystals with less helical line-slips. This result raises the question of how nanomaterials can be designed that avoid this frustration. The comparison with TMV suggests a potential approach to make chiral nanomaterials.

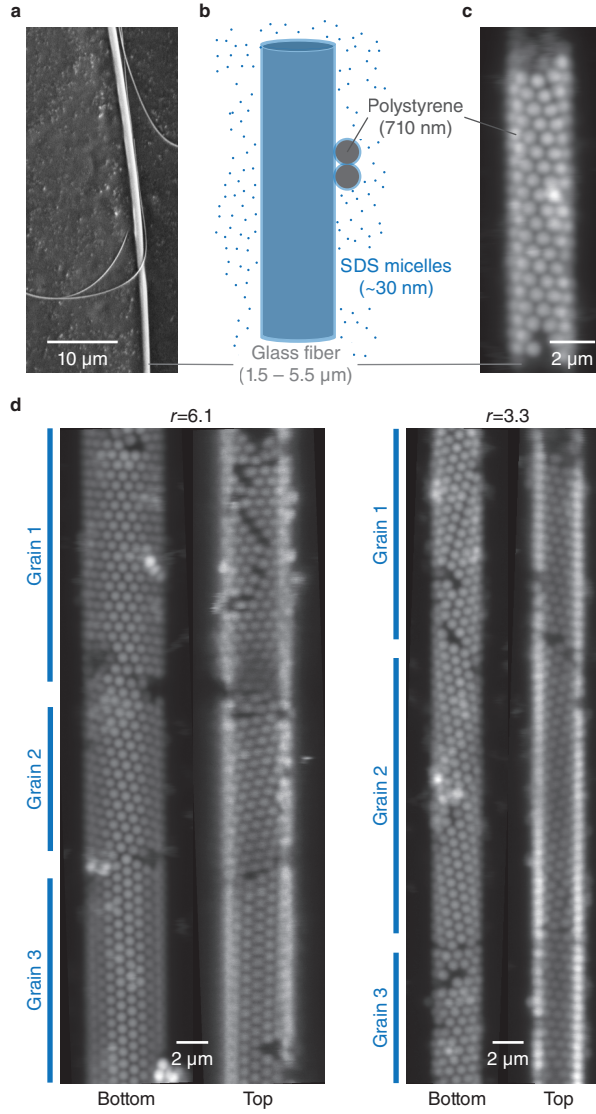


Figure 1: **Formation of colloidal crystals on a cylinder.** **a**, Scanning electron micrograph of an optical fiber tapered from an original diameter of $125\ \mu\text{m}$ to about $200\ \text{nm}$ at its thinnest part. Both thick and thin segments in the image belong to the same fiber. We examine crystals that form where the fiber diameter is between 1.5 and $5.5\ \mu\text{m}$. **b**, Polystyrene colloidal nanoparticles with an average diameter of $710\ \text{nm}$ are attracted to the fiber through a depletion interaction mediated by SDS micelles with an effective diameter of $30\ \text{nm}$.^{31,32} This effective diameter is larger than the physical diameter of $4\ \text{nm}$ because it accounts for electrostatic interactions. Blue shaded regions denote the volume excluded to the micelles. We adjust the concentration of colloidal nanoparticles (0.25% w/v) and SDS (33.6 – $34\ \text{mM}$) in solution to prevent the formation of multiple crystal layers, large clusters of particles, or kinetic instabilities. **c**, Projection of a stack of confocal microscope images of a colloidal crystal formed on the surface of a cylinder. **d**, Confocal microscope images of crystals assembled on two cylinders with different size ratios r . Because the objective is below the cylinder, images of the top and sides of the cylinder are distorted by lensing through the glass fiber (see Fig. S2 for details of experimental setup). The blue lines denote the approximate boundaries of different crystal grains that wrap around the cylinder. These grains are identified by the consistent chiral angle found on both sides of the cylinder.

2 Results and Discussion

2.1 Single crystals form on and wrap around a cylindrical fiber

In our experimental system, 2D colloidal crystals self-assemble on the surface of a hard cylinder, driven by a short-ranged depletion interaction^{33–35} between the particles and between the nanoparticles and cylinder. We fabricate cylinders by simultaneously heating and pulling a silica optical fiber.^{36–38} This method results in a tapered cylinder with a diameter d of a few micrometers and with a smooth surface for crystal growth (Fig. 1a).

We introduce a depletion interaction between polystyrene nanoparticles (diameter $D = 710$ nm) and between the nanoparticles and the cylinder using sodium dodecyl sulfate (SDS) micelles (Fig. 1b). Because the interaction between nanoparticles is isotropic, a 2D crystal of such particles can bend freely and conform to the cylinder surface, which has no Gaussian curvature but does have non-zero mean curvature. The potential-well depth is a few $k_B T$ (see Supporting Information) and the interaction range is approximately the effective diameter of the depletant micelles, or about 4% of the polystyrene nanoparticle size at the SDS concentration we use (Fig. 1b).^{31,32} With such a weak and short-ranged attraction, isolated dislocations or disclinations do not occur.¹⁷ Because only nanoparticles very close to one another interact, we refer to the attraction between two neighboring nanoparticles as a “bond.” Furthermore, we choose the SDS concentration so that the crystals grow slowly and kinetic instabilities are avoided (Supporting Information).

Immediately after preparing the sample, we see multiple crystallites growing on the cylinder. In 3–5 hours, the cylinder is almost entirely covered with crystallites (Fig. 1c; for comparison, Fig. S5 shows crystallization on a flat surface). To study the closure of individual crystallites, we limit our observations to size ratios $r = d/D$ between 2 and 6, in which case multiple grains form along the length of the cylinder, each of which wraps completely around the cylinder (Fig. 1d and Fig. S6). The cylinder is slightly tapered, allowing us to investigate growth at different size ratios. But because the diameter of the fiber changes

negligibly along a single grain, we can consider the substrate to be cylindrical rather than conical on the scale of the grain (Supporting Information).

2.2 At long times, some crystals form dense packings but most contain kinks

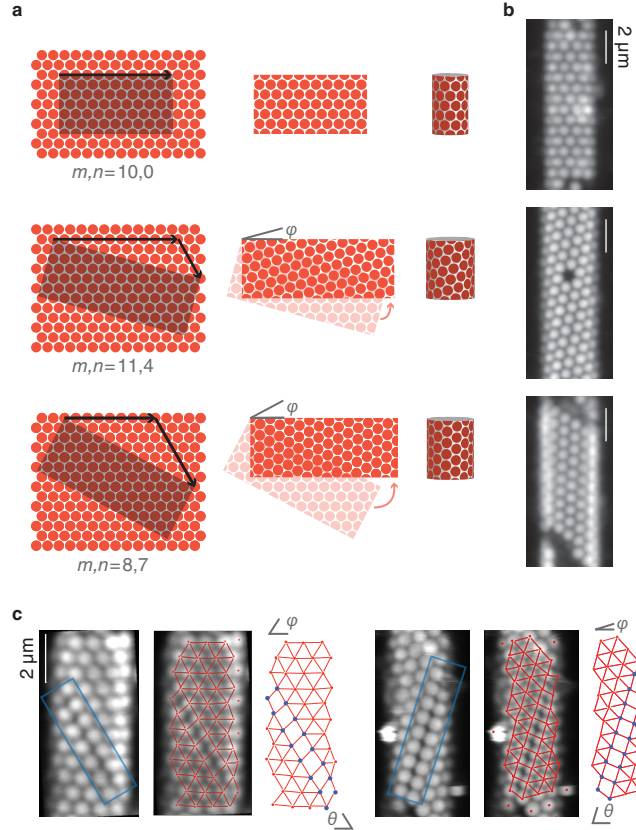


Figure 2: **Some, but not all, of the observed crystals have structures corresponding to densest packings on a cylinder.** **a**, Diagrams showing construction of commensurate cylindrical crystals. When the side length of the dark rectangle is commensurate with an integer linear combination (m, n) of the lattice vectors \mathbf{v}_1 and \mathbf{v}_2 (dark arrows show the vectors $m\mathbf{v}_1$ and $n\mathbf{v}_2$), the resulting segment of the lattice (middle column) can wrap perfectly around a cylinder with circumference $\|m\mathbf{v}_1 + n\mathbf{v}_2\|$. As shown in the middle and right columns, the integers m and n determine the chiral angle ϕ . An achiral crystal results from $(m, n) = (10, 0)$, whereas chiral crystals result from $(11, 4)$ and $(8, 7)$. **b**, Confocal microscope images of three crystals grown on the same tapered fiber. The chiral angles are $\phi = 0^\circ$ (top), 16.3° (middle), and 27.6° (bottom). The resulting configurations are close to the corresponding diagrams in **a**. **c**, Confocal images and bond (interaction) networks of two line-slip defects (blue boxes) with different helicity. The helicity of a line slip is determined by the angle θ between the line slip and the azimuthal direction on the cylinder. Blue circles show the particles that form the line slip. Images of both sides of the cylinders shown in panels **b** and **c** are shown in Fig. S7.

We first describe the structures of the cylindrical crystals that we observe at long times

(several hours). We find that some, but not all, have structures corresponding to the densest packings predicted in previous theoretical studies: commensurate crystals and crystals with line slips. We discuss the geometry of these structures because it is essential for understanding the growth process and how it can lead to non-ground-state structures.

Some of the crystals we observe in our experiment are commensurate – the only defects being vacancies – and some of these are chiral. Mathematical models of phyllotaxis^{25,39,40} show that commensurate crystals can appear for integer values of the chiral indices m and n (Fig. 2a). These indices determine the size ratio and chiral angle of the crystal. We characterize the chiral angle of the observed crystals, which is easier to measure than m and n (Fig. 2b). We find that crystals with different helicity can spontaneously assemble on different parts of the cylinder.

We also observe straight line-slip defects in some of the crystals (Fig. 2c). Such defects have been observed previously in macroscopic systems^{26,29} but not, to our knowledge, in a self-assembled system. They follow a helical path around the cylinder that is also parallel to one of the lattice vectors of the crystal.

The line-slip defects that we observe are stable for the duration of our experiments (up to 18 h), though vacancies do appear and disappear during that time. The stability is expected because line slips cannot disappear unless the crystal unwraps and rewraps, as shown in previous simulations and theoretical studies.^{24,25} On a flat surface, defects similar to line slips can occur between two grains with similar orientations (Fig. S8), but these defects disappear when the grains translate. On a cylinder, the line-slip defect occurs within the same grain, and thus translation along the line slip corresponds to a rotation of the crystal. However, rotating the crystal would change its circumference, which would require it to either penetrate or detach from the cylinder, both of which are energetically prohibitive.

We find, however, that most crystals do not adopt ground-state structures, even at long times. Instead, they contain a new type of defect not previously seen in simulation or experiment: kinked line-slips (Fig. 3a). The kinks contain gaps that we call “partial vacancies”

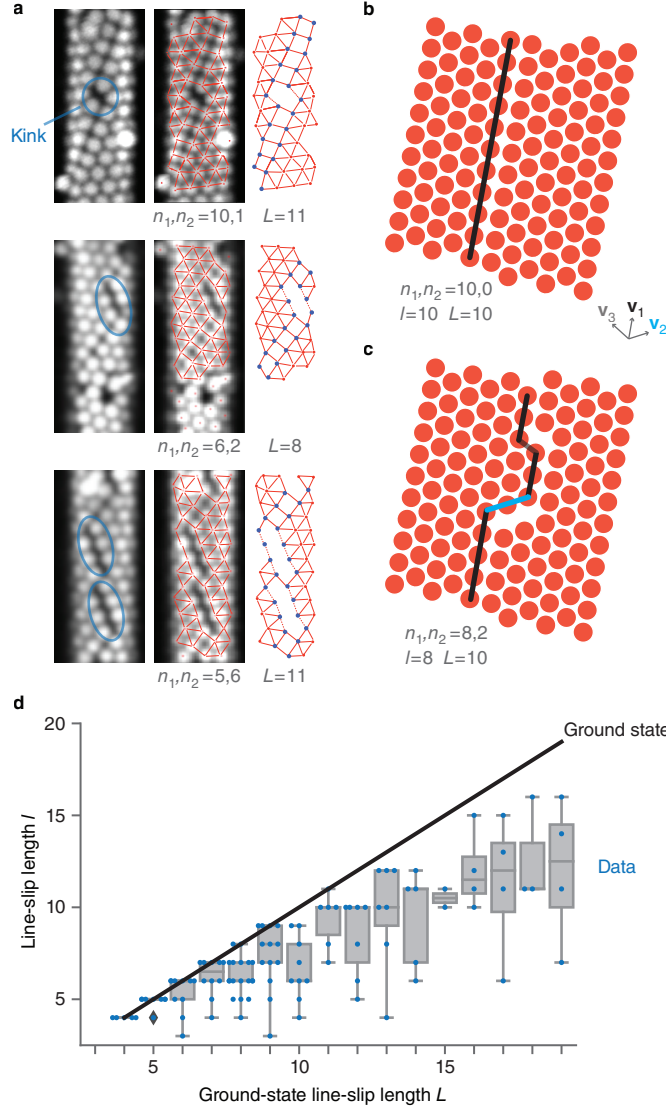


Figure 3: **Most crystals with line-slip defects have kinks and are not ground-state structures.** **a**, Confocal images and bond networks of three kinked line-slip defects, with the kinks circled in blue. We characterize each defect by counting the number of steps (particle center-to-center distances) from its starting to ending point. n_1 is the number of steps taken along \mathbf{v}_1 , the lattice direction aligned with the line slip, and n_2 along \mathbf{v}_2 . Two parameters characterize the geometry: the line-slip length $l = n_1$, which is the number of particles in the line slip that have five neighbors, and the ground-state length $L = n_1 + n_2$, which is the length if all the partial vacancies were to exit the line slip. Images of both sides of the cylinders are shown in Fig. S7. **b**, Diagram of a line-slip defect in its ground state. $L = l$ because there are no kinks. **c**, Diagram of a line-slip defect with kinks. Because of the kinks, $l < L$. **d**, Plot of l as a function of L for ground states (black line) and experiment (blue dots). To find l from experiment, we measure n_1 and n_2 from images of 116 crystals. The experimental data is shown as a box-and-whisker plot with data points in blue. The box extends from the lower to upper quartile and the whiskers show the range of the data at each L .

because they are smaller than a nanoparticle. We find that kinked line-slips emerge in crystals with different chiral angles and with a variety of numbers of partial vacancies, as shown in Fig. 3a. We characterize the different kinked structures using two length scales, as shown in Fig. 3b,c. Quantification of these length scales for the observed structures (Fig. 3d) illustrates two points. First, most of the line-slips are kinked, and the proportion of line slips that are in the ground state decreases with increasing line-slip length. Second, for a given line-slip length, the number of partial vacancies can vary.

This variation shows that the partial vacancies do not affect the commensurability of the crystal with the cylindrical constraint. In fact, kinked line-slips can in principle convert to straight line-slips when partial vacancies move into the grain boundaries – or, equivalently, when multiple nanoparticles move in a direction parallel to the line slip. Such a relaxation does not require a change in cylinder circumference; instead, the excess void space can be absorbed by the grain boundaries. Thus, a kink can be viewed as an excitation of a straight line-slip. Kinked line-slips would therefore not have been observed in previous simulations on cylindrical crystals²⁴ that examined only the ground states.

2.3 Kinked line-slips form during growth

Having shown that defects arise that do not change the commensurability constraint, we now turn to what these defects reveal about the growth process. To understand why the kinked line-slips occur so frequently in our experiments, we watch line slips form in experiment (Fig. 4a and Movie S1). We find that kinked line-slips tend to form when two parallel line-slips grow, trapping partial vacancies in between. These observations suggest a mechanism for the formation of partial vacancies (Fig. 4b).

We also find that, once formed, most kinked defects do not relax into straight line-slips on the timescale of the experiment (Fig. S9), although the kinks and grain boundaries do fluctuate (Fig. S10). Hence, in contrast to crystals that close without a line slip (Fig. S11 and Movie S2), crystals with kinked line-slips appear to result when partial vacancies are

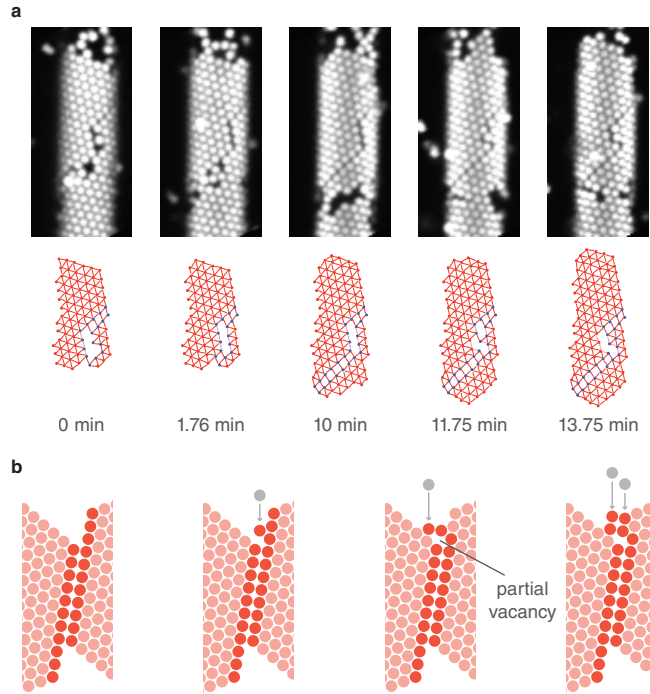


Figure 4: **Kinked line-slips form during growth of the crystal.** **a**, Confocal images and bond networks showing the formation of a kinked line-slip defect. At 0 min, a line-slip defect begins to form when the crystal wraps around the cylinder. At 1.76 min, another line slip starts to form in parallel, leaving partial vacancies between the two. The line slips continue to grow until 10 min, after which we observe fluctuations in the kinked shape but not in the number of partial vacancies. Not all particles are shown in the bond network diagrams. **b**, Diagrams illustrating a mechanism for kink formation. The growing line slip is shown by the dark red particles. In the second diagram, a particle that attaches to the crystal prevents the line slip from growing. In the third diagram, another particle attaches and traps a partial vacancy. In the fourth diagram, additional particles attach and continue the line slip, which is now kinked.

kinetically trapped during crystal growth. Brownian-dynamics simulations of particles interacting on a cylinder through a short-range potential that approximates the experimental depletion attraction (Supporting Information and Movie S3) show that kinks arise during growth and not afterward (Fig. 5a–d and Movie S4).

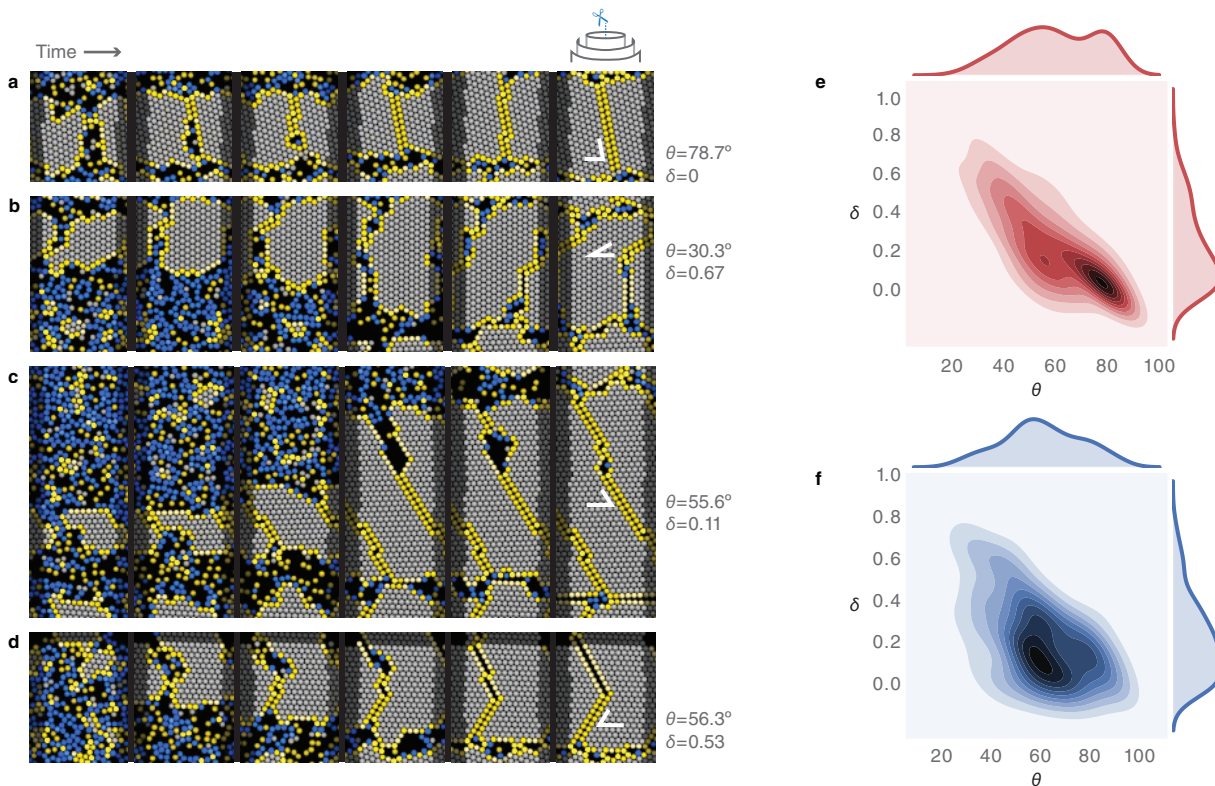


Figure 5: Line slips that are more aligned with the cylinder axis are less kinked. **a–d**, Renderings of the simulated growth of four crystals with line slips. In each image the crystal is shown cut and unwrapped, such that the entire circumference of the cylinder (same for all four crystals) is visible. The line-slip angle θ and parameter $\delta = (L - l)/L$ are shown at right for each crystal, and particles in the line slip and grain boundaries are shown in yellow. In **a**, the line slip is nearly aligned with the cylinder axis. It forms kinks but eventually rearranges into a straight line-slip. In **b**, the line slip makes a larger angle with the axis. The crystal, however, grows preferentially in the axial direction and consequently traps partial vacancies, resulting in a larger value of δ . In **c** and **d**, the line slips have angles between those of **a** and **b**, and their values of δ also lie between those of **a** and **b**. **e**, Contour plot showing probability distribution (kernel density estimate) of kinked line-slip defects as a function of δ and θ for 79 simulated crystals with fixed r . **f**, Same type of plot as **e**, but showing data from 116 crystals found in experiment with varying r . The correlation coefficient in the experiment (-0.49) is smaller than that of simulation (-0.77), likely because the experimental data are not taken at a single size ratio. The data points used to create the kernel density estimates in panels **e** and **f** are shown in Fig. S12.

The observation that these new defects arise during growth is the first clue that the cylindrical geometry affects the growth process itself. The second clue is that the parameter $\delta = (L - l)/L$, the number of partial vacancies per unit length of the total defect, is inversely

correlated with the line-slip angle θ in both simulation (Fig. 5e) and experiment (Fig. 5f). Thus, line slips that are less aligned with the cylinder axis have more partial vacancies on average. This result was unexpected to us because the partial vacancies neither reduce the energy of the crystal, nor do they change the commensurability of the crystal with its substrate.

2.4 The cylindrical geometry affects the growth process

We make sense of the negative correlation between the line-slip angle and the density of partial vacancies as follows. On a flat plane, near equilibrium, a crystalline grain grows isotropically. The same should be true of a crystal on a cylinder *until* the grain wraps around the cylinder and the crystal touches itself. At this point, growth along the azimuthal direction of the cylinder is hindered, and the flux of particles arriving at the crystal is no longer isotropic. A line slip that is aligned with the cylinder axis can continue to grow without kinks after it meets itself (Fig. 6a) because of symmetry: the two other faces of the crystal make the same angle with the cylinder axis, and therefore particles can attach to them at the same rates (Fig. 6b). By contrast, a line slip that is less aligned with the cylinder axis faces a challenge when it meets itself (Fig. 6c) because the other two faces make different angles with the line slip. Continuing the line slip without defects requires particles to attach to both faces at the same rates (Fig. 6d), but the broken symmetry makes this scenario unlikely: the larger the angle between the cylinder axis and the face corresponding to the line slip, the higher the probability that particles land on this face and trap partial vacancies by the mechanism of Fig. 4b.

Although this simple picture of the growth dynamics ignores effects such as diffusion of partial vacancies, it does describe the dynamics seen in simulations. To quantify these dynamics, we measure the lengths of all three faces of the crystal as a function of time. These lengths are related to the rates at which particles attach to faces – for example, the length of face 1 increases when particles attach to faces 2 and 3 – but are easier to measure. We find

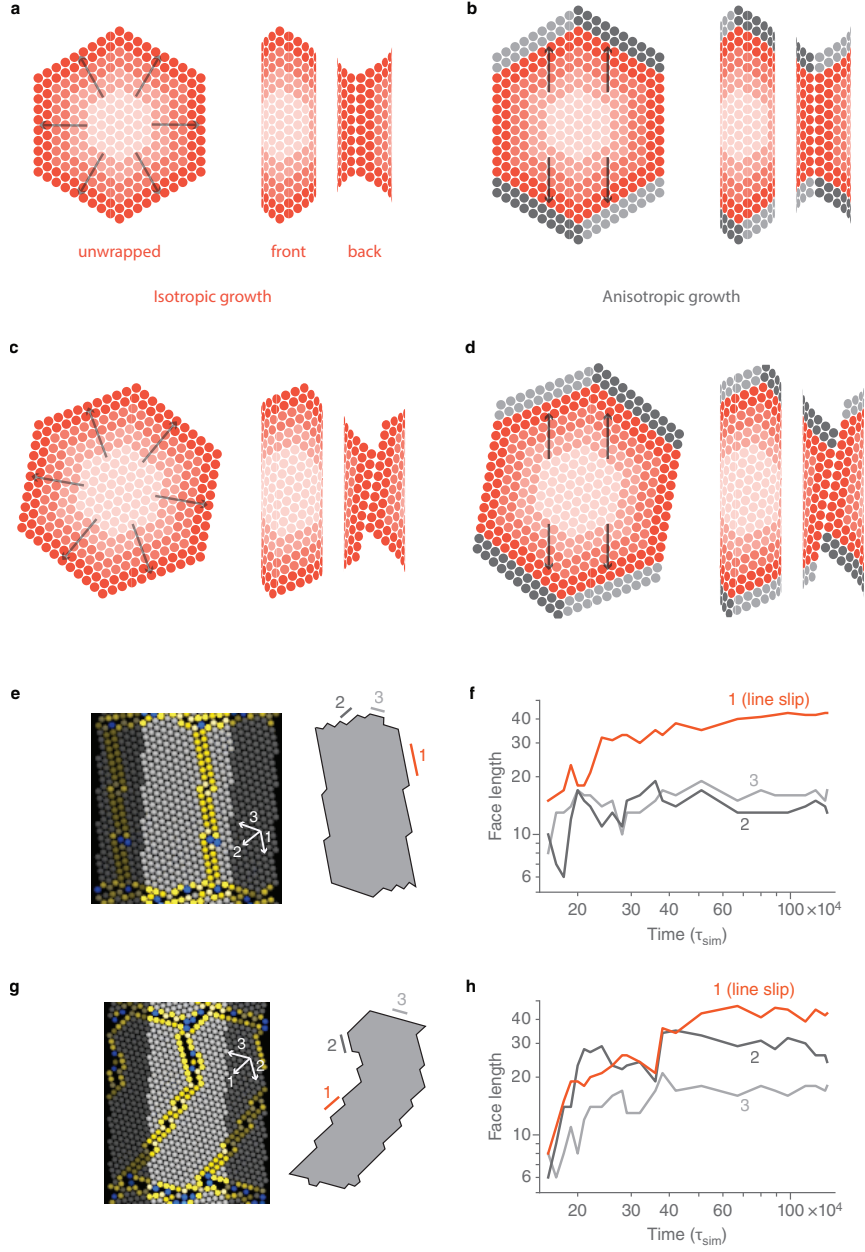


Figure 6: **Kinks result from anisotropic growth after a crystal meets itself.** **a**, Illustrations of a crystal growing on a cylinder. Darker colors correspond to later stages of growth. The crystal grows isotropically until it wraps and meets itself, forming a line slip. **b**, The crystal must then grow along the cylinder axis. Gray circles indicate particles that attach to the two exposed faces of the crystal to continue the line slip. **c** and **d**, Same as **a** and **b**, but for a line slip that is less vertical. For the line slip to remain straight, the growth on the light and dark gray faces must be the same. But because these two faces make different angles with the average growth direction (along the axis), partial vacancies can become trapped by the mechanism of Fig. 4b. **(e)** Rendering of a nearly vertical line-slip ($\theta \approx 80^\circ$) found in simulation. Diagram at right shows the area of the crystal (shaded region) and three faces. **f**, Lengths of the three faces as a function of time. The lengths are comparable until $2 \times 10^5 \tau_{\text{sim}}$ (where $\tau_{\text{sim}} = 180$ ms), at which point face 1 (aligned with the line slip and closely aligned with the crystal axis) starts to dominate. **g** and **h**, Same as **e** and **f**, but for a less vertical line slip ($\theta \approx 45^\circ$). Because face 2 is nearly aligned with the cylinder axis, it competes with face 1, and the line slip becomes kinked.

that for a crystal with a line slip that is nearly aligned with the cylinder axis (Fig. 6e and Movie S5), the lengths of the faces are approximately the same at short times, indicating isotropic growth (Fig. 6f). At longer times, the growth becomes anisotropic, with the face aligned with the line slip (face 1) growing much longer than the other two (faces 2 and 3). The disparity between the length of the face 1 and the lengths of faces 2 and 3 indicates that relatively few particles attach *to* face 1. As a result, the crystal incorporates few partial vacancies. A crystal with a line slip that is misaligned with the cylinder axis (Fig. 6g and Movie S6) also shows approximately isotropic growth at short times (Fig. 6h), but at longer times, the face aligned with the line slip (face 1) competes with face 2, which is more closely aligned with the cylinder axis. As a result, the crystal traps several partial vacancies.

2.5 Conclusion

We have shown how the closure constraint changes how a crystal composed of nanoparticles grows on a cylindrical substrate. The crystal grows approximately isotropically (as shown by our simulations) until it meets itself, at which point it must grow preferentially along the cylinder axis. As a result, the larger the angle between the line slip and the cylinder axis, the more partial vacancies the crystal incorporates.

These results have both fundamental and practical implications for nanomaterials. From the fundamental perspective, they show that a closure constraint alone can frustrate crystal growth. This is a different type of geometric frustration^{15,41} from the more well-studied form arising from Gaussian curvature.^{41,42} It does not occur in planar 2D crystals, where there is no closure constraint. It manifests only when the crystal size becomes comparable to the circumference, which is why the defects, partial vacancies, occur only where the crystal meets itself.

From a practical perspective, our results show that some ground-state cylindrical crystals are harder to make than others. In particular, it is difficult to grow a dense crystal having a line slip that is tightly wound about the axis, owing to the mismatch between the line slip

and the growth direction. Thus, self-assembly may be an inefficient way to make certain chiral nanomaterials, which have applications in sensors⁴³ and optical metamaterials.⁴⁴ Indeed, existing self-assembly routes to such nanostructures rely on templates such as TMV capsids^{44,45} and DNA origami rods⁴⁶ that guide nanoparticles into a prescribed helicity. An interesting question is whether there are conditions under which nonspecific substrates, like the fibers we use, can template the formation of large, single crystals with prescribed helicity and line-slip structure.

To address this question, it is useful to examine self-assembled cylindrical nanosystems that are not frustrated. Single-wall carbon nanotubes,^{47,48} for example, can adopt diameters corresponding to commensurate crystals, and microtubules can adopt straight line-slips (called “seams”⁴⁹) because these structures do not form around a cylindrical template. However, in systems like ours, the nanoparticles must satisfy the closure constraint while simultaneously adhering to a template. There are several systems in biology that face a similar set of competing constraints.⁴⁰

Of these, tobacco mosaic virus (TMV) has a particularly interesting way to satisfy both the closure and adhesion constraints. The coat proteins of TMV self-assemble into a cylindrical capsid around the viral RNA, even *in vitro*⁵⁰ – indeed, the TMV capsid is the structure that first inspired the term “self-assembly”.⁵¹ However, the assembly pathway differs from that in our system. The coat proteins first assemble into disks,⁵² and a single site on the RNA nucleates the formation of the cylindrical capsid from these disks.⁵³ During nucleation and assembly, the disks “dislocate”,^{52,54} or shear, to form helical structures, thereby reducing their diameter and adhering to the RNA.

Thus in TMV the proteins *first* satisfy the closure constraint by forming disks and *afterward* adhere to the RNA template. They maintain the closure constraint during the dislocating process. By contrast, the nanoparticles in our system first adhere to the template, then form crystals that must close. Our results show that even a single crystal can be frustrated by the closure constraint; therefore the control over nucleation that the RNA

provides may not be as important to eliminating frustration in TMV as the sequential nature of the assembly. This assembly pathway might have evolved in part to prevent the formation of line slips or partial vacancies that would expose the RNA to degradation by nucleases. There are, of course, other differences between our system and TMV. For example, the interactions between coat proteins are longer-ranged in TMV, which might help vacancies exit by allowing dislocations to form and glide helically to relax stresses.^{55,56} But the most striking difference is that the assembly is staged in a way that allows for both closure and adhesion. Engineering a similarly staged process may permit the directed self-assembly of nanoparticles into prescribed chiral crystals with high yield.

Another question for future work is why the kinked line-slips take so long to relax. Understanding their relaxation dynamics – and how those dynamics slow with increasing interaction strength and line-slip size – might reveal more about the relatively simple but unexplored form of geometric frustration imposed by a cylindrical surface.

3 Methods

See Supporting Information for all details of the experimental and computational methods.

Acknowledgement

We thank Smarak Maity, Amirhassan Shams-Ansari, and Michael Burek for help with the fabrication of the cylinders; Guangnan Meng and Sandra Nakasone for help with experimental protocols; and Frans Spaepen, Adil Mughal, David Nelson, Michael Moshe, Rodrick Kuate Defo, and L. Mahadevan for helpful discussions. This work was supported by the Harvard MRSEC under National Science Foundation grant nos. DMR-1420570 and DMR-2011754. C. H. Rycroft was partially supported by the Applied Mathematics Program of the U.S. DOE Office of Science Advanced Scientific Computing Research under contract number DE-AC02-05CH11231.

Supporting Information Available

The following files are available free of charge.

- Supporting information document: includes detailed Materials and Methods, Figs. S1 to S12, and Table S1
- Movie S1: Confocal images showing a crystal on a cylinder forming a kinked line-slip defect. Snapshots of this movie are shown in Fig. 4 of the manuscript.
- Movie S2: Confocal images showing a crystal on a cylinder without any defects. Snapshots of this movie are presented in Fig. S11.
- Movie S3: Rendering of crystal growth on a cylinder from a Brownian-dynamics simulation. The four images are of the same cylinder taken from four azimuthal angles at 90° intervals.
- Movie S4: Rendering of crystal growth on a cylinder from a Brownian-dynamics simulation, showing the cylinder cut and unwrapped. Snapshots of this movie are presented in Fig. 5 of the manuscript.
- Movie S5: Renderings of Brownian-dynamics simulation showing the growth of a crystal with a line slip that is nearly aligned with the cylinder axis.
- Movie S6: Renderings of Brownian-dynamics simulation showing the growth of a crystal with a line slip that is misaligned with the cylinder axis.

References

- (1) Sunagawa, I. Growth and Morphology of Crystals. *Forma* **1999**, *14*, 147–166.
- (2) Steno, N. *De solido intra solidum naturaliter contento dissertationis prodromus*; 1669; English translation by John Garrett Winter, “The prodromus of Nicolaus Steno’s disser-

- tation concerning a solid body enclosed by process of nature within a solid; an English version with an introduction and explanatory notes,” MacMillan (London), 1916.
- (3) Burton, W. K.; Cabrera, N.; Frank, F. C. The growth of crystals and the equilibrium structure of their surfaces. *Philosophical Transactions of the Royal Society of London. Series A, Mathematical and Physical Sciences* **1951**, *243*, 299–358.
 - (4) Palberg, T. Colloidal crystallization dynamics. *Current Opinion in Colloid & Interface Science* **1997**, *2*, 607–614.
 - (5) Skjeltorp, A. T. Visualization and characterization of colloidal growth from ramified to faceted structures. *Physical Review Letters* **1987**, *58*, 1444–1447.
 - (6) de Villeneuve, V. W. A.; Dullens, R. P. A.; Aarts, D. G. A. L.; Groeneveld, E.; Scherff, J. H.; Kegel, W. K.; Lekkerkerker, H. N. W. Colloidal Hard-Sphere Crystal Growth Frustrated by Large Spherical Impurities. *Science* **2005**, *309*, 1231–1233.
 - (7) Savage, J. R.; Dinsmore, A. D. Experimental Evidence for Two-Step Nucleation in Colloidal Crystallization. *Physical Review Letters* **2009**, *102*.
 - (8) Ganapathy, R.; Buckley, M. R.; Gerbode, S. J.; Cohen, I. Direct Measurements of Island Growth and Step-Edge Barriers in Colloidal Epitaxy. *Science* **2010**, *327*, 445–448.
 - (9) Schreiner, W.; Kratky, K. W. Computer simulation of hard-disc packings with spherical boundary conditions. *Journal of the Chemical Society, Faraday Transactions 2: Molecular and Chemical Physics* **1982**, *78*, 379–389.
 - (10) Bowick, M.; Cacciuto, A.; Nelson, D. R.; Travesset, A. Crystalline Order on a Sphere and the Generalized Thomson Problem. *Physical Review Letters* **2002**, *89*, 185502.
 - (11) Bausch, A. R.; Bowick, M. J.; Cacciuto, A.; Dinsmore, A. D.; Hsu, M. F.; Nelson, D. R.; Nikolaidis, M. G.; Travesset, A.; Weitz, D. A. Grain Boundary Scars and Spherical Crystallography. *Science* **2003**, *299*, 1716–1718.

- (12) Lipowsky, P.; Bowick, M. J.; Meinke, J. H.; Nelson, D. R.; Bausch, A. R. Direct visualization of dislocation dynamics in grain-boundary scars. *Nature Materials* **2005**, *4*, 407.
- (13) García, N. A.; Register, R. A.; Vega, D. A.; Gómez, L. R. Crystallization dynamics on curved surfaces. *Physical Review E* **2013**, *88*, 012306.
- (14) Guerra, R. E.; Kelleher, C. P.; Hollingsworth, A. D.; Chaikin, P. M. Freezing on a sphere. *Nature* **2018**, *554*, 346–350.
- (15) Grason, G. M. Perspective: Geometrically frustrated assemblies. *The Journal of Chemical Physics* **2016**, *145*, 110901.
- (16) Schneider, S.; Gompper, G. Shapes of crystalline domains on spherical fluid vesicles. *Europhysics Letters (EPL)* **2005**, *70*, 136–142.
- (17) Meng, G.; Paulose, J.; Nelson, D. R.; Manoharan, V. N. Elastic Instability of a Crystal Growing on a Curved Surface. *Science* **2014**, *343*, 634–637.
- (18) Vega, D. A.; Lorenzana, J.; Gómez, L. R.; García, N. A.; Vitelli, V. Phase nucleation in curved space. *Nature Communications* **2015**, *6*, 6856.
- (19) Köhler, C.; Backofen, R.; Voigt, A. Stress Induced Branching of Growing Crystals on Curved Surfaces. *Physical Review Letters* **2016**, *116*, 135502.
- (20) Luque, A.; Reguera, D.; Morozov, A.; Rudnick, J.; Bruinsma, R. Physics of shell assembly: Line tension, hole implosion, and closure catastrophe. *The Journal of Chemical Physics* **2012**, *136*, 184507.
- (21) Michaels, T. C. T.; Bellaiche, M. M. J.; Hagan, M. F.; Knowles, T. P. J. Kinetic constraints on self-assembly into closed supramolecular structures. *Scientific Reports* **2017**, *7*, 12295.

- (22) Bravais, L.; Bravais, A. Essai sur la disposition des feuilles curvisériées. *Annales des sciences naturelles. Botanique* **1837**, *7*, 42–110.
- (23) Pickett, G. T.; Gross, M.; Okuyama, H. Spontaneous Chirality in Simple Systems. *Physical Review Letters* **2000**, *85*, 3652–3655.
- (24) Wood, D. A.; Santangelo, C. D.; Dinsmore, A. D. Self-assembly on a cylinder: a model system for understanding the constraint of commensurability. *Soft Matter* **2013**, *9*, 10016.
- (25) Mughal, A.; Chan, H. K.; Weaire, D. Phyllotactic Description of Hard Sphere Packing in Cylindrical Channels. *Physical Review Letters* **2011**, *106*, 115704.
- (26) Mughal, A.; Chan, H. K.; Weaire, D.; Hutzler, S. Dense packings of spheres in cylinders: Simulations. *Physical Review E* **2012**, *85*, 051305.
- (27) Lohr, M. A.; Alsayed, A. M.; Chen, B. G.; Zhang, Z.; Kamien, R. D.; Yodh, A. G. Helical packings and phase transformations of soft spheres in cylinders. *Physical Review E* **2010**, *81*, 040401.
- (28) Wu, G.; Cho, H.; Wood, D. A.; Dinsmore, A. D.; Yang, S. Confined Assemblies of Colloidal Particles with Soft Repulsive Interactions. *Journal of the American Chemical Society* **2017**, *139*, 5095–5101.
- (29) Winkelmann, J.; Haffner, B.; Weaire, D.; Mughal, A.; Hutzler, S. Simulation and observation of line-slip structures in columnar structures of soft spheres. *Physical Review E* **2017**, *97*, 059902.
- (30) Ouahjji, S.; van Ravensteijn, B. G. P.; Fernández-Rico, C.; Lacina, K. S.; Philipse, A. P.; Petukhov, A. V. Wet-Chemical Synthesis of Chiral Colloids. *ACS Nano* **2018**, *12*, 12089–12095.

- (31) Iracki, T. D.; Beltran-Villegas, D. J.; Eichmann, S. L.; Bevan, M. A. Charged Micelle Depletion Attraction and Interfacial Colloidal Phase Behavior. *Langmuir* **2010**, *26*, 18710–18717.
- (32) Tulpar, A.; Subramanian, V.; Ducker, W. Decay Lengths of Double-Layer Forces in Solutions of Partly Associated Ions. *Langmuir* **2001**, *17*, 8451–8454.
- (33) Asakura, S.; Oosawa, F. On Interaction between Two Bodies Immersed in a Solution of Macromolecules. *The Journal of Chemical Physics* **1954**, *22*, 1255–1256.
- (34) Asakura, S.; Oosawa, F. Interaction between particles suspended in solutions of macromolecules. *Journal of Polymer Science* **1958**, *33*, 183–192.
- (35) Binder, K.; Virnau, P.; Statt, A. Perspective: The Asakura Oosawa model: A colloid prototype for bulk and interfacial phase behavior. *The Journal of Chemical Physics* **2014**, *141*, 140901.
- (36) Tong, L.; Gattass, R. R.; Ashcom, J. B.; He, S.; Lou, J.; Shen, M.; Maxwell, I.; Mazur, E. Subwavelength-diameter silica wires for low-loss optical wave guiding. *Nature* **2003**, *426*, 816–819.
- (37) Tong, L.; Lou, J.; Ye, Z.; Svacha, G. T.; Mazur, E. Self-modulated taper drawing of silica nanowires. *Nanotechnology* **2005**, *16*, 1445–1448.
- (38) Tong, L.; Mazur, E. Glass nanofibers for micro- and nano-scale photonic devices. *Journal of Non-Crystalline Solids* **2008**, *354*, 1240–1244.
- (39) van Iterson, G. *Mathematische und mikroskopisch-anatomische Studien über Blattstellungen nebst Betrachtungen über den Schalenbau der Miliolinen.*; Fischer: Jena, 1907.
- (40) Erickson, R. O. Tubular Packing of Spheres in Biological Fine Structure. *Science* **1973**, *181*, 705–716.

- (41) Sadoc, J.-F.; Mosseri, R. *Geometrical Frustration*; Collection Alea-Saclay: Monographs and Texts in Statistical Physics; Cambridge University Press: Cambridge, 1999.
- (42) Bowick, M. J.; Giomi, L. Two-dimensional matter: order, curvature and defects. *Advances in Physics* **2009**, *58*, 449–563.
- (43) Cecconello, A.; Besteiro, L. V.; Govorov, A. O.; Willner, I. Chiroplasmonic DNA-based nanostructures. *Nature Reviews Materials* **2017**, *2*, 1–19.
- (44) Kobayashi, M.; Tomita, S.; Sawada, K.; Shiba, K.; Yanagi, H.; Yamashita, I.; Uraoka, Y. Chiral meta-molecules consisting of gold nanoparticles and genetically engineered tobacco mosaic virus. *Optics Express* **2012**, *20*, 24856–24863.
- (45) Dujardin, E.; Peet, C.; Stubbs, G.; Culver, J. N.; Mann, S. Organization of Metallic Nanoparticles Using Tobacco Mosaic Virus Templates. *Nano Letters* **2003**, *3*, 413–417.
- (46) Kuzyk, A.; Schreiber, R.; Fan, Z.; Pardatscher, G.; Roller, E.-M.; Högele, A.; Simmel, F. C.; Govorov, A. O.; Liedl, T. DNA-based self-assembly of chiral plasmonic nanostructures with tailored optical response. *Nature* **2012**, *483*, 311–314.
- (47) Iijima, S.; Ichihashi, T. Single-shell carbon nanotubes of 1-nm diameter. *Nature* **1993**, *363*, 603–605.
- (48) Bethune, D. S.; Kiang, C. H.; Vries, M. S. d.; Gorman, G.; Savoy, R.; Vazquez, J.; Beyers, R. Cobalt-catalysed growth of carbon nanotubes with single-atomic-layer walls. *Nature* **1993**, *363*, 605–607.
- (49) Kikkawa, M.; Ishikawa, T.; Nakata, T.; Wakabayashi, T.; Hirokawa, N. Direct visualization of the microtubule lattice seam both in vitro and in vivo. *Journal of Cell Biology* **1994**, *127*, 1965–1971.
- (50) Fraenkel-Conrat, H.; Williams, R. C. Reconstitution of Active Tobacco Mosaic Virus

- from Its Inactive Protein and Nucleic Acid Components. *Proceedings of the National Academy of Sciences of the United States of America* **1955**, *41*, 690–698.
- (51) Caspar, D. L. D.; Klug, A. Physical Principles in the Construction of Regular Viruses. *Cold Spring Harbor Symposia on Quantitative Biology* **1962**, *27*, 1–24.
- (52) Butler, P. J. G. Assembly of Tobacco Mosaic Virus Particle. *Nature* **1971**, *233*, 25–27.
- (53) Butler, P. J. G. Self-assembly of tobacco mosaic virus: the role of an intermediate aggregate in generating both specificity and speed. *Philosophical Transactions of the Royal Society of London. Series B: Biological Sciences* **1999**, *354*, 537–550.
- (54) Klug, A. The Tobacco Mosaic Virus Particle: Structure and Assembly. *Philosophical Transactions: Biological Sciences* **1999**, *354*, 531–535.
- (55) Harris, W. F. Dislocations in Tobacco Mosaic Virus. *Nature* **1972**, *240*, 294–297.
- (56) Beller, D. A.; Nelson, D. R. Plastic deformation of tubular crystals by dislocation glide. *Physical Review E* **2016**, *94*, 033004.

TOC Graphic

