

Lawrence Berkeley National Laboratory

Recent Work

Title

An X-Ray Study of the Rare-Earth Oxide Systems: CeIV-NdIII, CeIV-PrIII, CeIV-PrIV, and PrIV-NdIII

Permalink

<https://escholarship.org/uc/item/3mb884wm>

Author

McCullough, J.D.

Publication Date

1949-06-16

UNIVERSITY OF
CALIFORNIA

*Radiation
Laboratory*

TWO-WEEK LOAN COPY

*This is a Library Circulating Copy
which may be borrowed for two weeks.
For a personal retention copy, call
Tech. Info. Division, Ext. 5545*

BERKELEY, CALIFORNIA

C.2

UCRL-376

DISCLAIMER

This document was prepared as an account of work sponsored by the United States Government. While this document is believed to contain correct information, neither the United States Government nor any agency thereof, nor the Regents of the University of California, nor any of their employees, makes any warranty, express or implied, or assumes any legal responsibility for the accuracy, completeness, or usefulness of any information, apparatus, product, or process disclosed, or represents that its use would not infringe privately owned rights. Reference herein to any specific commercial product, process, or service by its trade name, trademark, manufacturer, or otherwise, does not necessarily constitute or imply its endorsement, recommendation, or favoring by the United States Government or any agency thereof, or the Regents of the University of California. The views and opinions of authors expressed herein do not necessarily state or reflect those of the United States Government or any agency thereof or the Regents of the University of California.

INSTALLATION	NO. COPIES
Argonne National Laboratory	8
Armed Forces Special Weapons Project	1
Atomic Energy Commission, Washington	2
Battelle Memorial Institute	1
Brookhaven National Laboratory	4
Bureau of Ships	1
Carbide and Carbon Chemicals Corporation (K-25 Plant)	4
Carbide and Carbon Chemicals Corporation (Y-12 Plant)	4
Columbia University (Failla)	1
Dow Chemical Company	1
General Electric Company, Richland	6
Hanford Operations Office	1
Iowa State College	1
Kellex Corporation	2
Knolls Atomic Power Laboratory	4
Los Alamos	3
Massachusetts Institute of Technology (Gaudin)	1
Massachusetts Institute of Technology (Kaufmann)	1
Mound Laboratory	3
National Advisory Committee for Aeronautics	1
National Bureau of Standards	2
Naval Radiological Defense Laboratory	1
NEPA Project	1
New Brunswick Laboratory	1
New York Operations Office	2
North American Aviation, Inc.	1
Oak Ridge National Laboratory	12
Patent Branch, Washington	1
Sylvania Electric Products, Inc.	1
Technical Information Branch, ORE	15
UCLA Medical Research Laboratory (Warren)	1
University of California Radiation Laboratory	4
University of Rochester	2
Western Reserve University (Friedell)	1
Westinghouse Electric Corporation	2
	<u>97</u>

INFORMATION DIVISION
Radiation Laboratory
Univ. of California
Berkeley, California

An X-ray Study of the Rare-earth Oxide Systems: $\text{Ce}^{\text{IV}}\text{-Nd}^{\text{III}}$,
 $\text{Ce}^{\text{IV}}\text{-Pr}^{\text{III}}$, $\text{Ce}^{\text{IV}}\text{-Pr}^{\text{IV}}$, and $\text{Pr}^{\text{IV}}\text{-Nd}^{\text{III}}$.

By J. D. McCullough*

Department of Chemistry and Radiation Laboratory
University of California, Berkeley, California

Abstract

An X-ray study of the oxide systems $\text{Ce}^{\text{IV}}\text{-Nd}^{\text{III}}$, $\text{Ce}^{\text{IV}}\text{-Pr}^{\text{III}}$, $\text{Ce}^{\text{IV}}\text{-Pr}^{\text{IV}}$, and $\text{Pr}^{\text{IV}}\text{-Nd}^{\text{III}}$ has been carried out with the following results:

1. Solid solutions with the fluorite structure are formed in all cases and lattice constants have been determined as a function of composition. For the oxide systems $\text{M}^{\text{IV}}\text{-M}^{\text{III}}$ there is an upper solubility limit varying from 50 to 67 atomic per cent of the trivalent metal.

2. Praseodymium is readily oxidized to Pr^{IV} in the presence of Ce^{IV} , with but more difficulty in the presence of Nd^{III} .

3. In no case is there evidence for the oxidation of Pr beyond the +4 state, even under oxygen pressures as high as 50 atmospheres.

* Present address: Department of Chemistry, University of California
Los Angeles 24, California

An X-ray Study of the Rare-earth Oxide Systems: $\text{Ce}^{\text{IV}}-\text{Nd}^{\text{III}}$,
 $\text{Ce}^{\text{IV}}-\text{Pr}^{\text{III}}$, $\text{Ce}^{\text{IV}}-\text{Pr}^{\text{IV}}$, and $\text{Pr}^{\text{IV}}-\text{Nd}^{\text{III}}$

By J. D. McCullough⁽¹⁾

(1) Present address: Department of Chemistry, University of California
Los Angeles 24, California

This study was undertaken with the object of learning more about the behavior of the oxides of praseodymium, in particular the unusual properties of Pr_6O_{11} and the relationships of this oxide to Pr_2O_3 and to PrO_2 . It has also been of interest to observe the effects of Nd^{III} and Ce^{IV} on the tendency of Pr^{III} to be oxidized to Pr^{IV} (or beyond) in the oxide systems.

Materials. The starting materials employed in most of the present study were commercial preparations of CeO_2 , Pr_6O_{11} and Nd_2O_3 obtained from the Rohr and Haas Company, Philadelphia; the Research Chemicals Company, Burbank, California and from the Maywood Chemical Works, Maywood, New Jersey, respectively. Spectrographic analysis showed these oxides to be 99.5%, 99.5%, and 98.5% pure from the standpoint of the metal content. The more critical samples, including most of those higher than 80% in praseodymium were prepared by use of column purified praseodymium. Spectrographic analysis of this material indicated no detectable amounts of other rare-earths or of the metals La, Sc, Y, Fe, Al, and Ca. Certain of the cerium-rich samples were prepared from cerium oxalate obtained from Prof. F. H. Spedding. The only impurities detected in a spectrographic analysis of this material were 0.017% each of Nd and La.

In order to convert the starting materials to substances of definite composition in weighable form, they were strongly ignited in air. Since

there was some doubt regarding the exact composition of the oxide of praseodymium resulting from air ignition, it was finally heated to approximately 1400° C. for 2 hours in high vacuum. This procedure yielded a pale green powder which was shown by means of its X-ray diffraction pattern to be the A (hexagonal) form of Pr_2O_3 .

Procedure. Stock solutions of the three rare-earths were prepared by dissolving weighed samples of the oxides in nitric acid. The dissolution of CeO_2 was hastened by the addition of hydrogen peroxide. Mixtures of the three pairs of rare-earths having the compositions shown in the tables were prepared by measuring appropriate volumes of the stock solutions. Each mixed solution was added quickly with stirring to an excess of freshly prepared aqueous ammonia. The resulting precipitates were collected on sintered glass, oven dried, then ignited in air in platinum crucibles for 2 hours at 800° C. Each sample was then ground in an agate mortar and heated in high vacuum for 3 hours at 1400° C. This treatment was found to convert praseodymium to Pr^{III} and cerium to Ce^{IV} while neodymium remained in the trivalent state. X-ray powder patterns were prepared of all samples in this state with the exception of some of the Pr-Nd and Ce-Pr mixtures. The Ce-Pr and Pr-Nd mixtures were then reheated in small open crucibles in a furnace at 600° C. for 16 hours, after which X-ray powder patterns were again prepared. Finally, most of the praseodymium-containing samples were heated in sealed quartz tubes (Figure 1) under an oxygen pressure of approximately 50 atmospheres. The oxygen was generated by decomposing a weighed sample of dry sodium chlorate in the tube after sealing, the approximate pressure being estimated from the volume of the tube

and the weight of sodium chlorate taken. After decomposition of the sodium chlorate by local application of heat, the tubes were placed in a furnace for 48 hours at 300° C. This treatment has been found to convert Pr_6O_{11} to PrO_2 and presumably converts all praseodymium in the mixtures to Pr^{IV} . This assumption is substantiated by the nature of the solid-solution diagrams shown in Figures 2, 3, and 4. X-ray powder patterns were prepared for all of the oxygen treated samples.

X-ray Diffraction. Powder diffraction photographs were prepared by use of copper radiation filtered through nickel foil. The camera was of the cylindrical back-reflection type with an effective diameter of 9.013 cm. The lattice constants given are based on the X-ray wavelengths: $\text{CuK}\alpha = 1.5418 \text{ \AA}$, $\text{CuK}\alpha_1 = 1.5405 \text{ \AA}$, and $\text{CuK}\alpha_2 = 1.5445 \text{ \AA}$.

Table I

Lattice Constants for Solid Solutions of Cerium and Neodymium Oxides

($\text{CeO}_2 - \text{Nd}_2\text{O}_3$)

Sample No.	Atomic Per Cent Nd	Lattice Constant ($\text{\AA}$) (Fluorite Structure)
1	0	5.411 $\pm$ 0.001
2	5.7	5.421 $\pm$ 0.001
3	12.5	5.433 $\pm$ 0.002
4	30.0	5.459 $\pm$ 0.003
5	41.7	5.473 $\pm$ 0.003
6	53.0	5.494 $\pm$ 0.004
7	74.1	5.505 $\pm$ 0.004
8	82.8	5.505 $\pm$ 0.006

Table II

Lattice Constants for Solid Solutions of Praseodymium and Cerium Oxides

Sample No.	Atomic Per Cent Pr	Lattice Constants ($\text{\AA}$) (Fluorite Structure)		
		Heated in Vacuum	Heated in Air	Heated in Oxygen
1	0.0	5.411 ± 0.001	5.411 ± 0.001	5.411 ± 0.001
2	14.5	5.442 ± 0.002	5.407 ± 0.001	
3	25.3	5.460 ± 0.002	5.405 ± 0.001	5.406 ± 0.001
4	35.6	5.481 ± 0.003		
5	48.5	5.508 ± 0.003	5.402 ± 0.002	
6	52.5	5.511 ± 0.002		5.402 ± 0.001
7	53.1	5.510 ± 0.002	5.400 ± 0.002	
8	65.3	5.52 ± 0.01	5.398 ± 0.002	
9	77.5		5.398 ± 0.005 5.465 ± 0.005	
10	87.2	5.558 ± 0.002	5.40 ± 0.01 5.465 ± 0.003	5.397 ± 0.003
11	91.9		5.468 ± 0.003	
12	94.4		5.468 ± 0.002	
13	97.0		5.468 ± 0.002	
14	100.0	5.570 ± 0.002	5.468 ± 0.001	5.394 ± 0.002

* Two phases, fluorite type plus "C" type Pr_2O_3 ** One phase, "C" type (cubic) Pr_2O_3 . Cell constant given is one-half of true value.
Pure Pr_2O_3 also crystallizes as "A" (hexagonal) type.

Table III

Lattice Constants for Solid Solutions of Praseodymium and Neodymium Oxides.

Sample No.	Atomic Per Cent Pr	Lattice Constants ($\text{\AA}$) (Fluorite Structure)	
		Heated in Air	Heated in Oxygen
1	28.2	5.49 ± 0.01	5.50 ± 0.01
2	44.0	5.490 ± 0.004	5.502 ± 0.005
3	55.9	5.490 ± 0.004	5.477 ± 0.003
4	79.7	5.468 ± 0.003	5.436 ± 0.006
5	96.6	5.468 ± 0.002	5.402 ± 0.004
6	100.0	5.468 ± 0.001	5.394 ± 0.002

* Shows two phases, the non-fluorite phase being unidentified but probably rich in Nd_2O_3 .

Results and Discussion. The experimental data are given in Tables I, II, and III, and are shown graphically in Figures 2, 3, and 4. It is seen that in the single-phase regions, the oxide systems $\text{Ce}^{\text{IV}}\text{-Nd}^{\text{III}}$, $\text{Ce}^{\text{IV}}\text{-Pr}^{\text{IV}}$, $\text{Ce}^{\text{IV}}\text{-Pr}^{\text{III}}$, and $\text{Pr}^{\text{IV}}\text{-Nd}^{\text{III}}$ show a nearly linear relationship between the lattice constant, a_0 , and the composition in terms of the atomic per cent of the total rare-earth metal present in the trivalent form. In Figure 5, the oxide systems $\text{Ce}^{\text{IV}}\text{-La}^{\text{III}}$ (2), $\text{Ce}^{\text{IV}}\text{-Pr}^{\text{III}}$, $\text{Ce}^{\text{IV}}\text{-Nd}^{\text{III}}$, and $\text{Pr}^{\text{IV}}\text{-Nd}^{\text{III}}$ are shown together for

(2) Zintl, E. and Croatto, U., Z. anorg. allg. Chem. 242, 79 (1939)

comparison purposes. The relative slopes of the lines are in keeping with the relative radii of the cations involved. Exact computation of these slopes from the ionic radii is complicated by the variable coordination number of the cation (8 in CeO_2 and 6 in the cubic M_2O_3 structure) and by the lattice defects caused by unoccupied anion sites.

As indicated in the tables, a number of the samples show two (or possibly more) phases, but in all such cases at least one phase is of the fluorite type. In the $\text{Ce}^{\text{IV}}\text{-Nd}^{\text{III}}$ oxide system, a second phase, presumably rich in Nd_2O_3 , is indicated at a composition corresponding to 70 atomic per cent of Nd from the standpoint of the metal content. This second phase is definitely not of the A or C type of Nd_2O_3 , and has not as yet been characterized. In the $\text{Ce}^{\text{IV}}\text{-Pr}^{\text{III}}$ and the $\text{Pr}^{\text{IV}}\text{-Nd}^{\text{III}}$ oxide systems, saturation of the fluorite structure is indicated at 50 atomic per cent and 56 atomic per cent of the trivalent metal respectively. On this same basis, saturation is reached in the $\text{Ce}^{\text{IV}}\text{-La}^{\text{III}}$ system at 60 atomic per cent of La^{III} .

In the $\text{Ce}^{\text{IV}}\text{-Pr}^{\text{III}}$ oxide system the second phase produced above 50 atomic per cent of Pr^{III} is the C-type cubic M_2O_3 structure. Above approximately 85 atomic per cent of Pr^{III} , the C-type phase is the only one present. The lattice constants in Table II for the C phase are given as one-half of the true values in order to be on a basis comparable to the fluorite phases. Pure Pr_2O_3 also crystallizes in the hexagonal A form of rare-earth sesquioxide.

The behavior of Pr_6O_{11} is of particular interest. This oxide results when any other oxide of praseodymium or salts such as the nitrate or oxalate are strongly heated in air. The lattice constant of Pr_6O_{11} is quite reproducible under widely different methods of preparation with a value of $5.462 \pm$

0.001 Å. This figure is at variance with the literature values of 5.499 and 5.536 kX^{(3), (4)} but is the result of the measurement of diffraction photographs

(3) Goldschmidt, V. M., Ulrich, F., and Barth, T., Strukturbericht I, 198

(4) Goldschmidt, V. M. Strukturbericht I, 198

of over twenty samples prepared in this laboratory, including column purified material. The solubility of Pr_2O_3 and PrO_2 in the Pr_6O_{11} phase is apparently too small to alter the lattice constant appreciably and the composition Pr_6O_{11} appears to be an isolated point in the praseodymium-oxygen system.

The individuality of the Pr_6O_{11} phase is also indicated by the praseodymium-rich, air-ignited samples in the Ce-Pr and the Pr-Nd oxide systems. In the Ce-Pr oxide system, (Table II), the Pr_6O_{11} phase with unaltered lattice constant persists until the praseodymium content has dropped below 77.5%. As the cerium content increases, a new fluorite type phase appears which is probably a solid system of CeO_2 in PrO_2 . Samples No. 9 and No. 10 both show an unaltered Pr_6O_{11} phase plus the solid solution phase. As one proceeds from Sample No. 14 to Sample No. 9, the intensities of the lines due to the Pr_6O_{11} phase diminish in relative intensity and the lines become broader and more diffuse while the opposite effects are noted for the solid solution. By the time the praseodymium content has dropped to 65%, only the solid solution phase remains. Judging by the lattice constant of the solid solution which is presumably in equilibrium with Pr_6O_{11} , its composition is approximately 75% PrO_2 and 25% CeO_2 . That the

solid solution is in equilibrium with Pr_6O_{11} is indicated by the fixed value of its lattice constant while the Pr_6O_{11} phase is still present. After the Pr_6O_{11} phase disappears, the lattice constant of the solid solution varies as indicated by the air-ignited values for Samples No. 1-8 in Table II. The failure of the lines of the solid solution to appear on the photographs of Samples No. 11-13 is believed to be due to an extremely small particle size. This is indicated by the broadening of the lines on the pattern for Sample No. 10 and to a lesser degree on that for Sample No. 9.

The behavior of Pr_6O_{11} is similar in the air-ignited samples of the Pr-Nd oxide system. Neodymium in amounts up to 20% does not alter the lattice constant of the Pr_6O_{11} phase. In this case a second phase does not appear on the films but there is considerable diffuse scattering in evidence. When the praseodymium content is reduced below 65%, the behavior on air-ignition is not reproducible unless the conditions are carefully controlled. All of the samples reported in Table III were ignited in a furnace simultaneously.

Pure PrO_2 is readily prepared by heating any lower oxide in oxygen gas at a pressure of approximately 50 atmospheres and a temperature of approximately 300°C . The range of temperature and oxygen pressure over which the change may be accomplished was not determined in this study but is under investigation by others in this laboratory. The lattice constant of PrO_2 was found in the present study to have the reproducible value of $5.394 \pm 0.002 \text{ \AA}$ and is also at variance with the literature values of 5.373 and 5.40 kX. (4)(5)

(5) Scherrer and Polacios, Strukturbericht II, 259

Several attempts to prepare a single phase with a composition between Pr_6O_{11} and PrO_2 were made by heating intimate mixtures of the two oxides in sealed quartz tubes. No such phase appears to exist, the usual result of the attempts being the two starting materials with unaltered lattice constants. Incomplete oxidation of Pr_6O_{11} with oxygen gas was also found to yield the two phases Pr_6O_{11} and PrO_2 , each with its characteristic lattice constant.

There has been some speculation regarding an oxidation state of +5 for praseodymium. Prandtl and Rieder⁽⁶⁾ have reported that praseodymium is oxidized

(6) Prandtl, W. and Rieder, G., Z. anorg. allg. Chem. 238, 225 (1938).

beyond the +4 state when in the presence of a trivalent rare-earth. Yttrium was the trivalent element actually used in their work in order to eliminate the possibility of any oxidation other than that of praseodymium. Marsh⁽⁷⁾, in attempting to repeat the work of Prandtl and Rieder, was able to oxidize

(7) Marsh, J. K., Jour. Chem. Soc. (1946) 5

praseodymium only to the +4 state in the presence of Y_2O_3 . The present work offers good evidence indicating that praseodymium is oxidized to, but not beyond the +4 state. The dotted line on Figure 4 represents a prediction of the lattice constants for the $\text{Pr}^{\text{IV}}\text{-Nd}^{\text{III}}$ oxide system as a function of composition. The slope of this line was taken equal to that for the $\text{Ce}^{\text{IV}}\text{-Pr}^{\text{III}}$ oxide system (Figure 3) because of the similarities in relationships involved in the two systems. It is significant that the experimental points for the oxidized samples in the Pr-Nd oxide system are close to this predicted line. This

indicates that the praseodymium in the samples is oxidized completely to the +4 state, but not beyond, even in the presence of trivalent neodymium and at oxygen pressures of approximately 50 atmospheres.

It is also interesting to note that in the portion of the Ce-Pr oxide system below 65% praseodymium, that element is easily oxidized to the +4 state on being heated in air. Evidently the presence of Ce^{IV} makes the oxidation of praseodymium to the +4 state easier than when alone or when trivalent neodymium is present. This may be due to the identity of the crystal structure of PrO_2 to that of CeO_2 .

Acknowledgment. The author is indebted to Mrs. Lee Jackson and Mrs. Carol Dauben for preparing and measuring some of the powder photographs, to Mr. J. Conway for the spectrographic analyses, to Mr. R. C. Lilly and Mr. D. C. Stewart for the column purification of praseodymium and to Dr. B. B. Cunningham for many helpful discussions.

This paper is based on work performed under the auspices of the Atomic Energy Commission at the Radiation Laboratory, University of California.

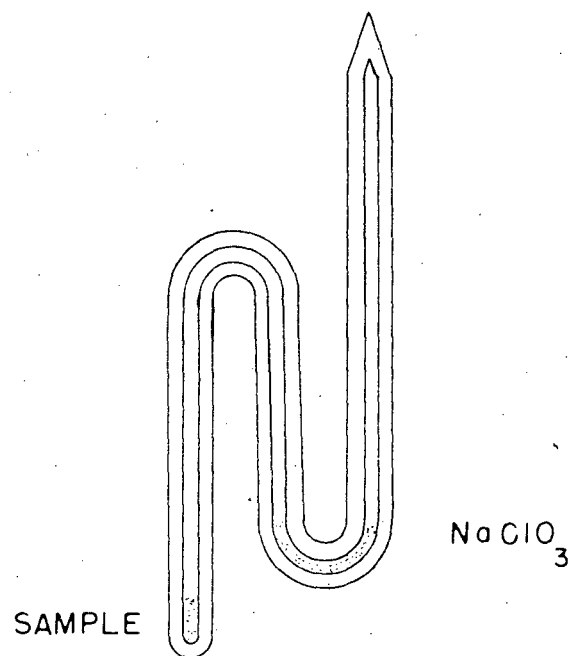


FIG. 1 QUARTZ TUBE FOR
OXIDATION OF PRASEODYMIUM SAMPLES

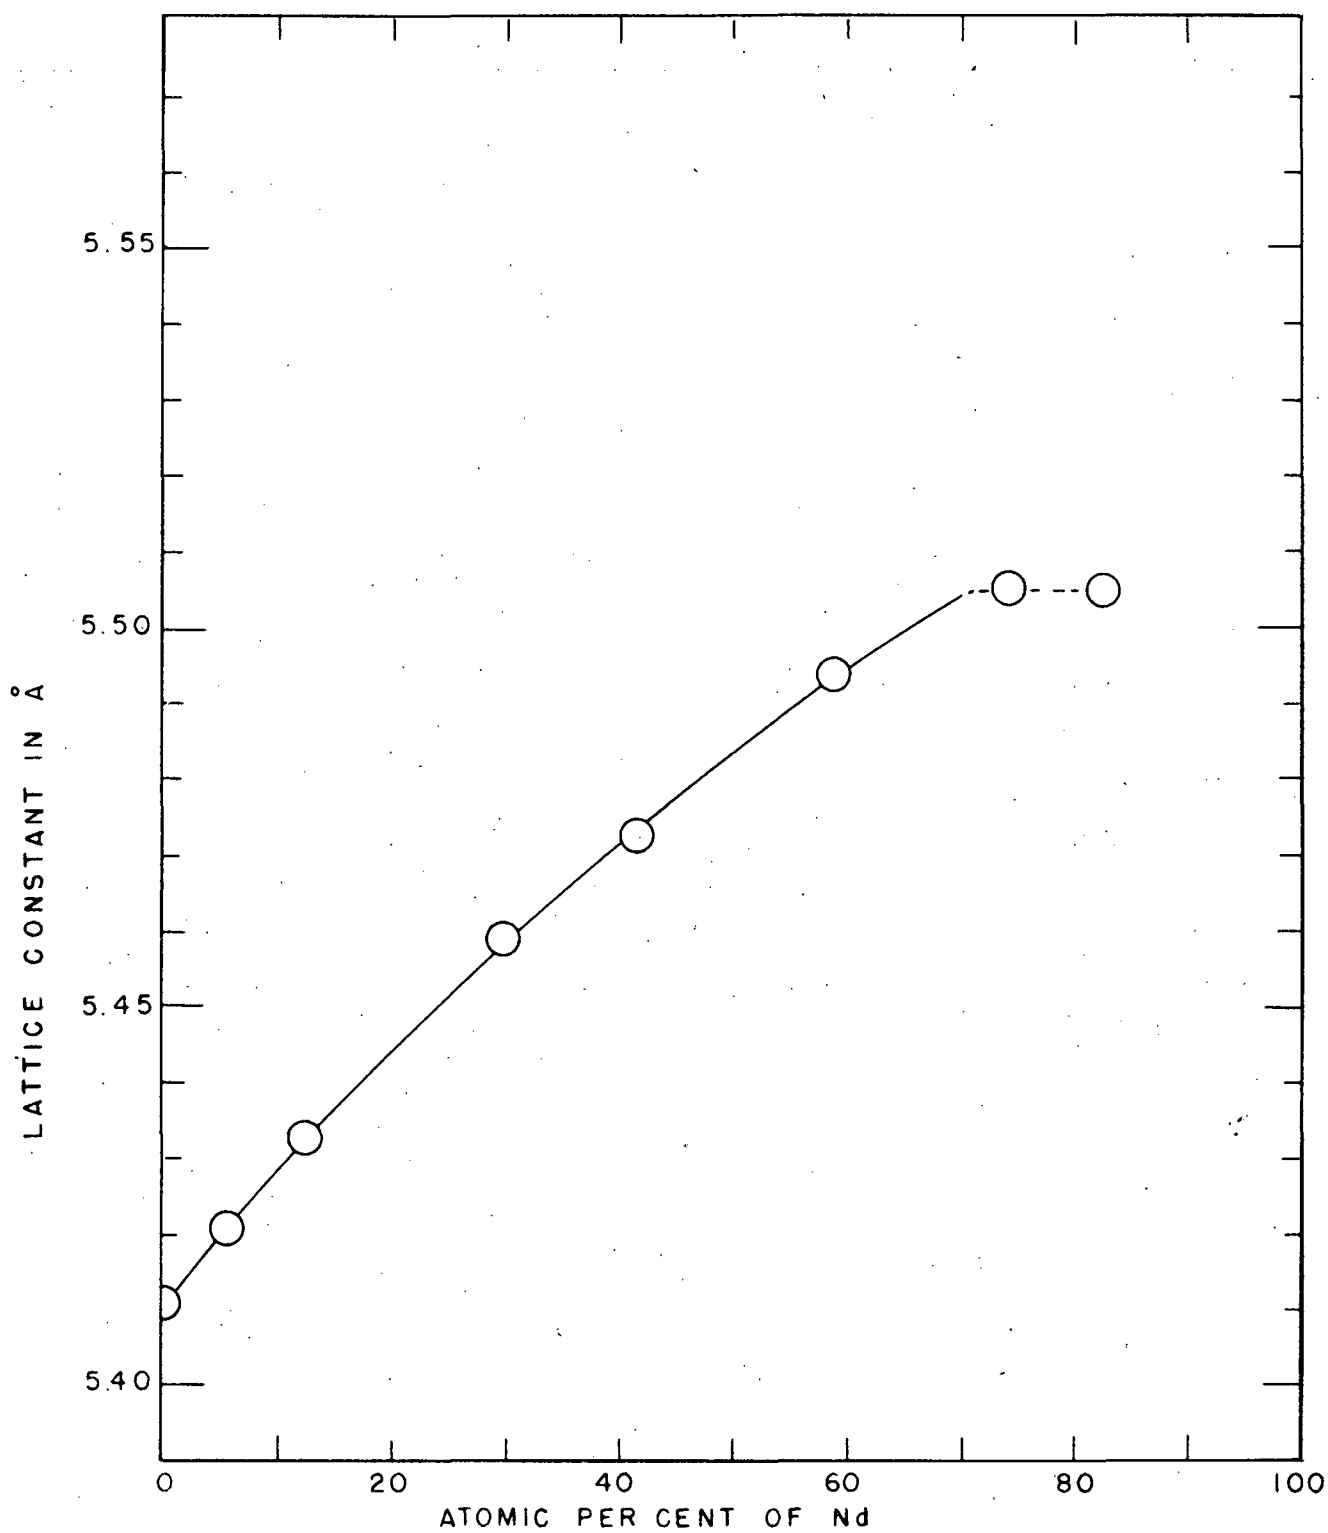


FIG. 2 LATTICE CONSTANTS FOR SOLID SOLUTIONS IN THE CERIC OXIDE - NEODYMIUM OXIDE SYSTEM WITH FLUORITE-TYPE STRUCTURE.

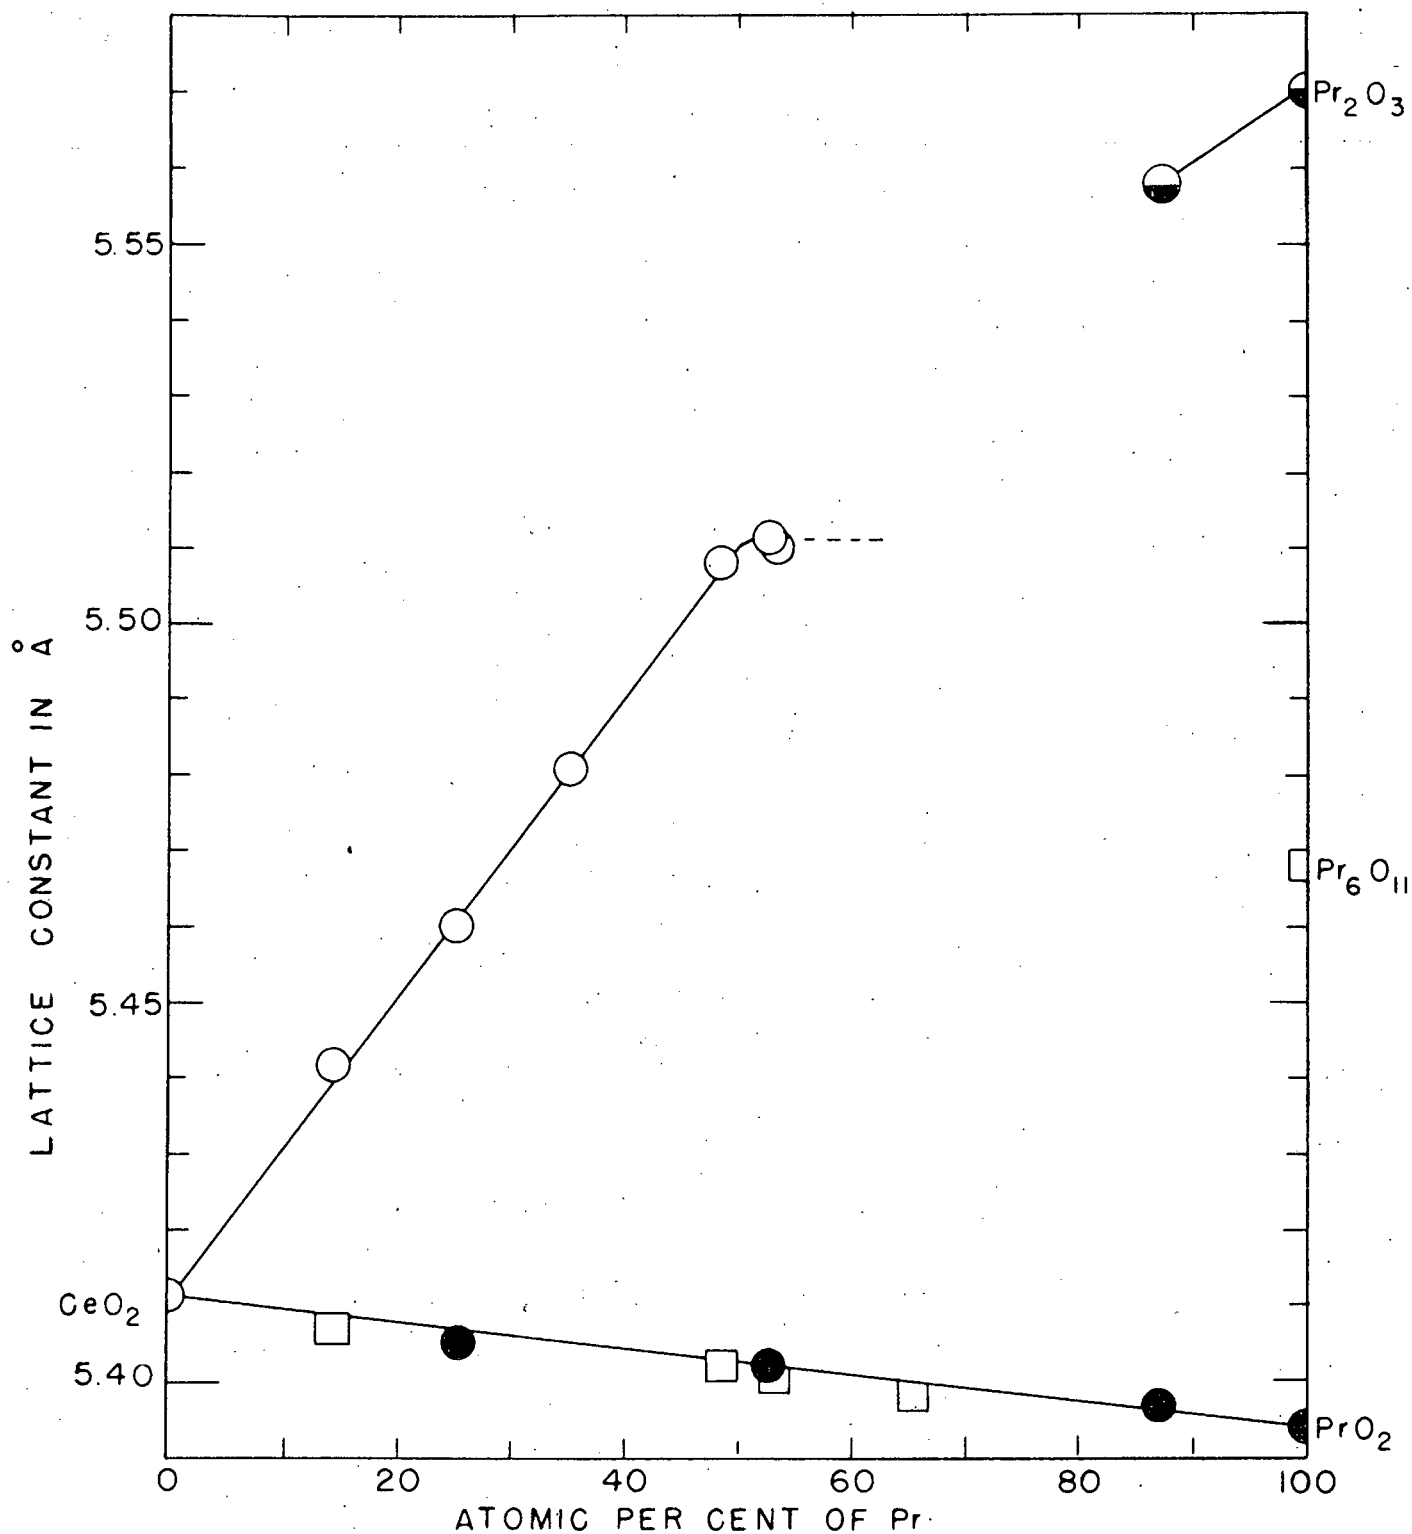


FIG. 3 LATTICE CONSTANTS FOR SOLID SOLUTIONS IN THE CERIC OXIDE-PRASEODYMIUM OXIDE SYSTEMS.

- LEGEND:
- HEATED IN VACUUM. FLUORITE-TYPE PHASE.
 - HEATED IN OXYGEN. FLUORITE-TYPE PHASE.
 - ◐ HEATED IN VACUUM. C-TYPE PHASE.
 - HEATED IN AIR. FLUORITE-TYPE PHASE.

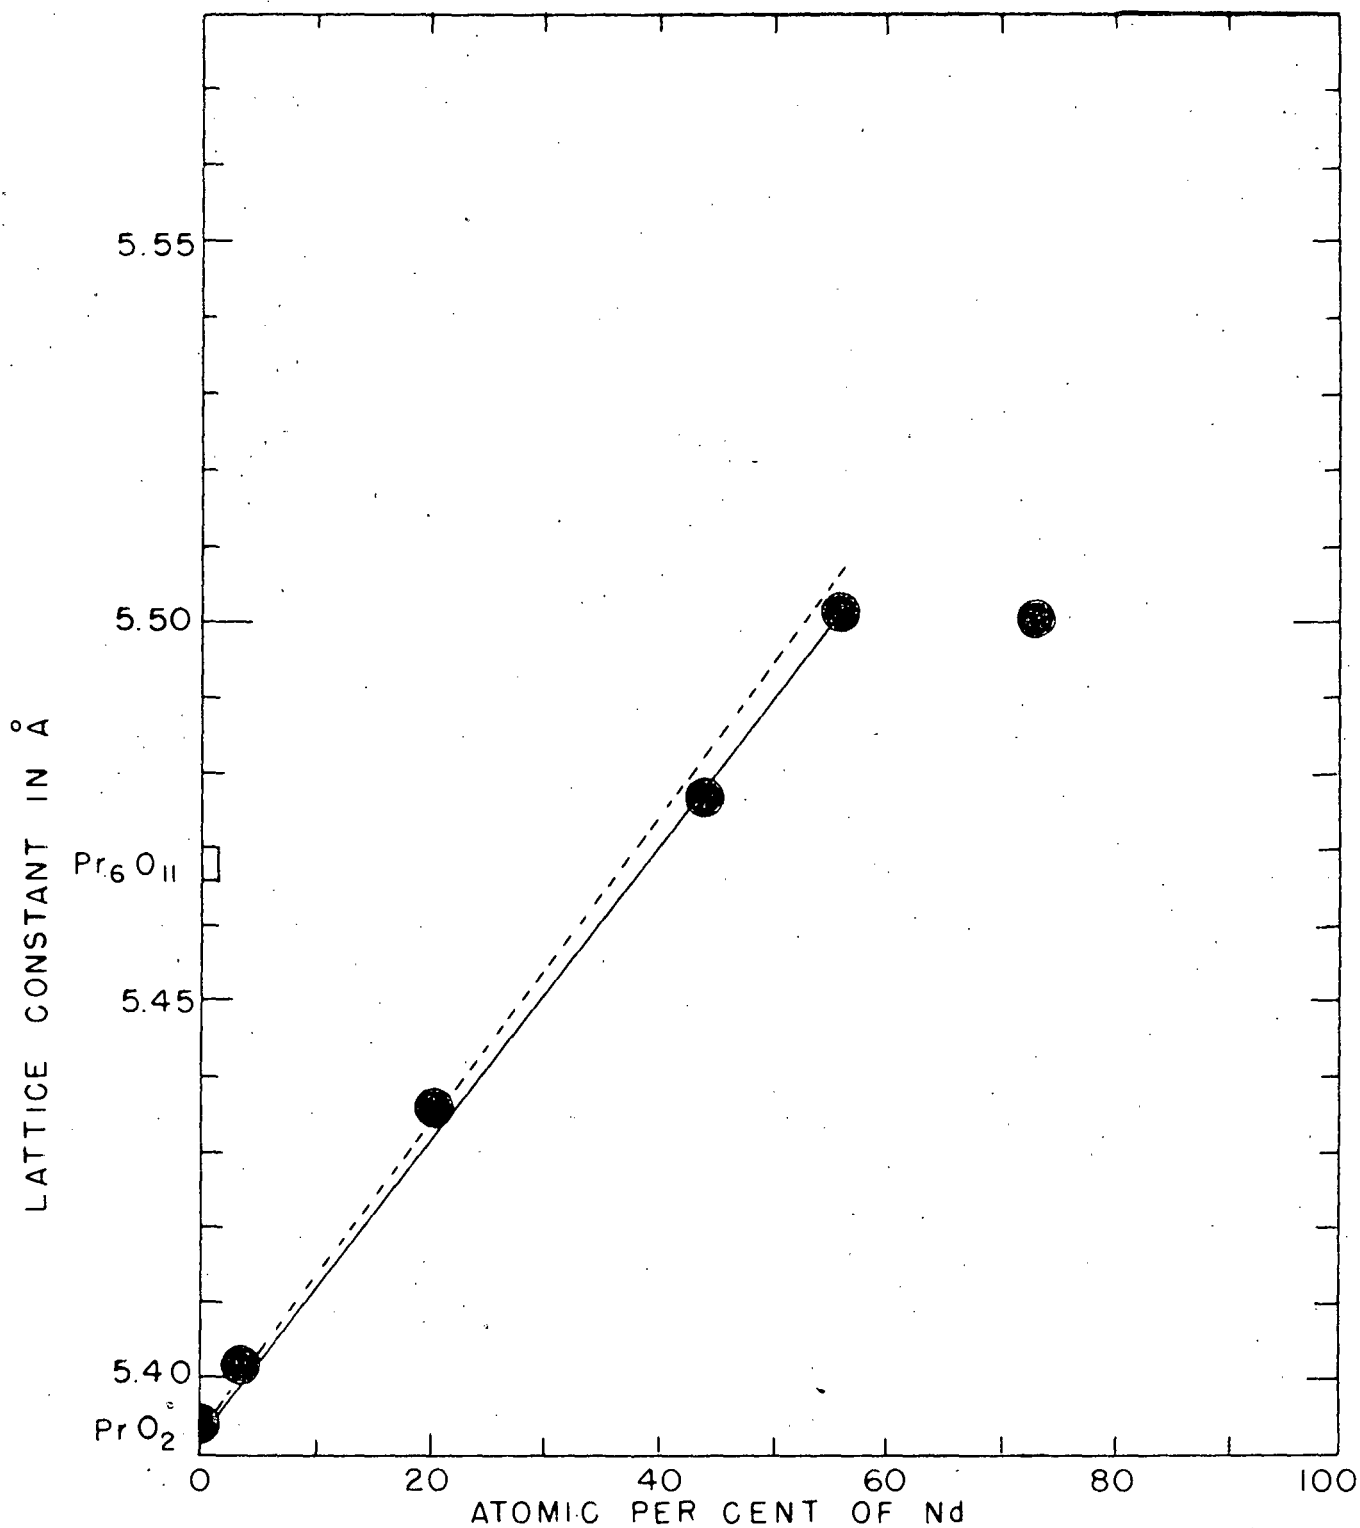


FIG. 4 LATTICE CONSTANTS FOR SOLID SOLUTIONS IN THE PRASEODYMIUM OXIDE-NEODYMIUM OXIDE SYSTEM.

LEGEND: ● HEATED IN OXYGEN, FLUORITE-TYPE PHASE
□ HEATED IN AIR, FLUORITE-TYPE PHASE.

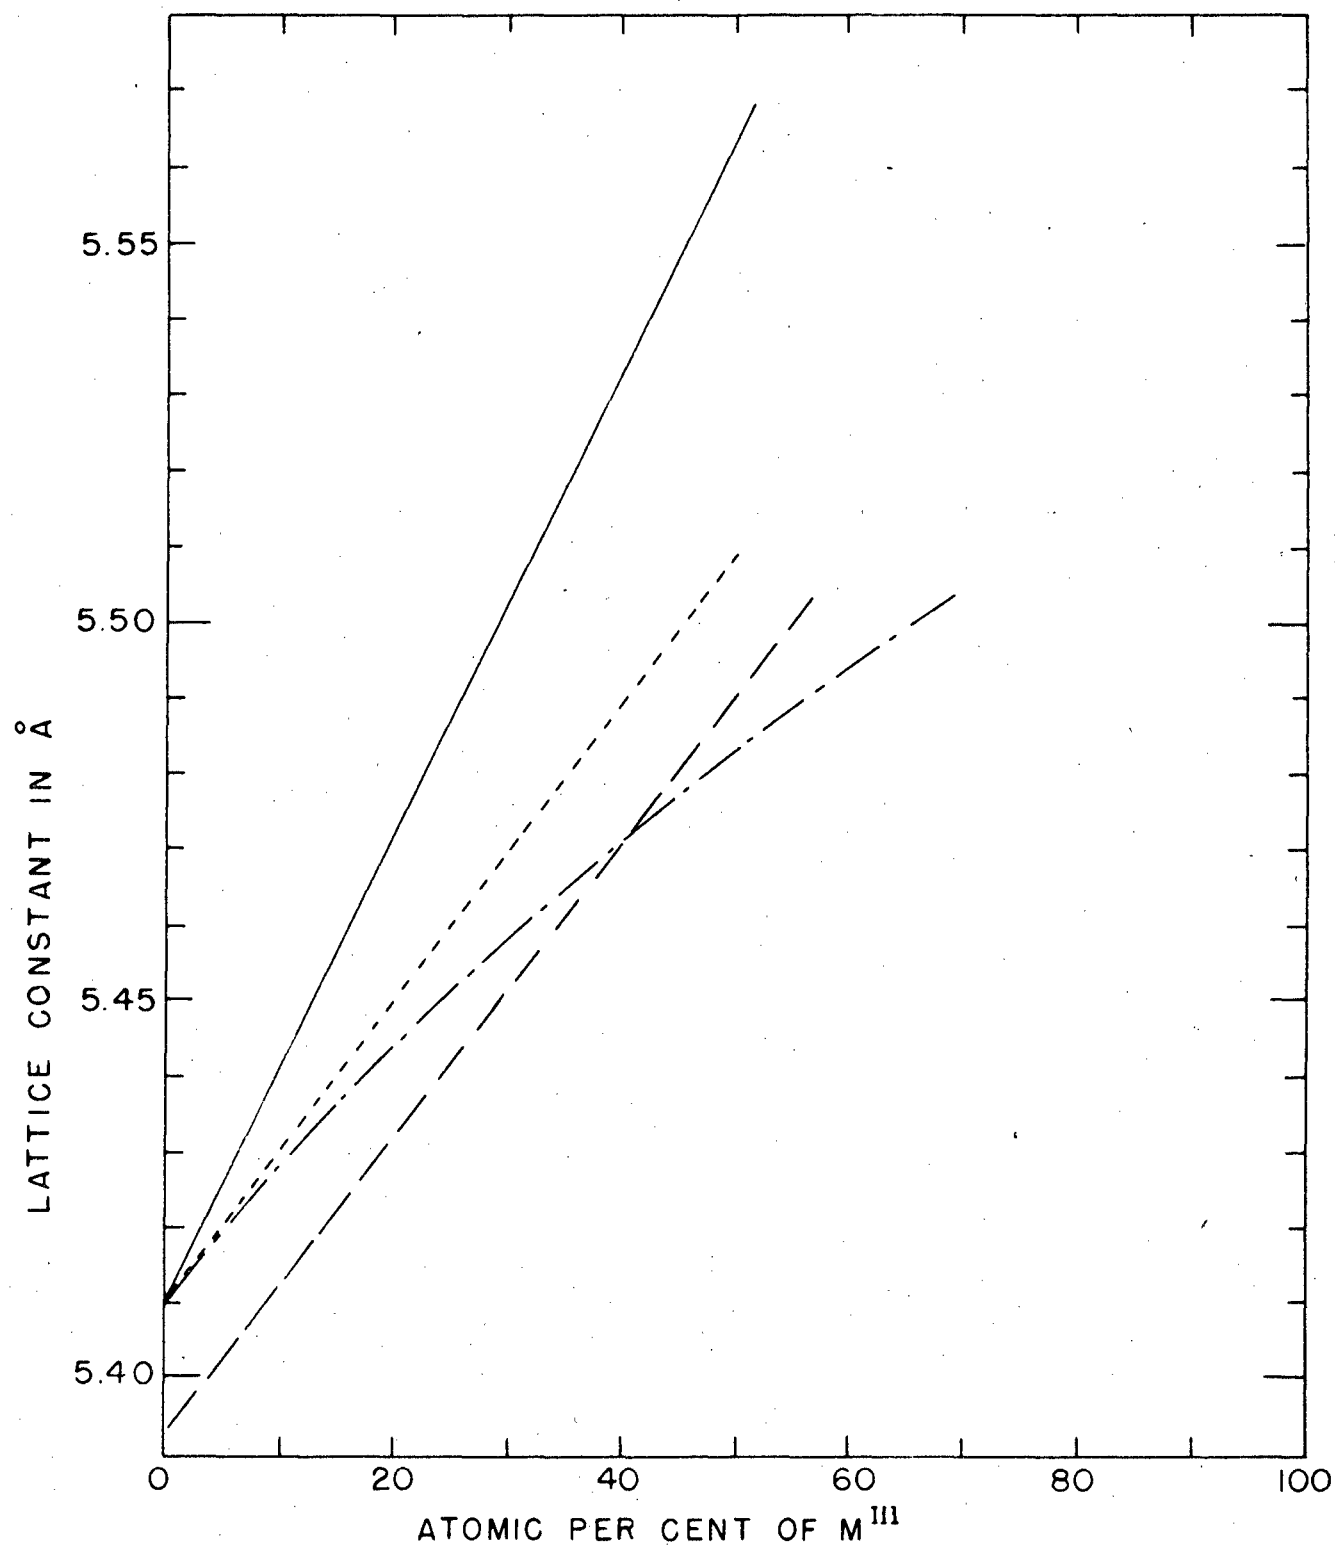


FIG. 5 COMPARISON OF SOLID SOLUTIONS IN RARE EARTH OXIDE SYSTEMS

LEGEND: ————— $\text{CeO}_2 - \text{La}_2\text{O}_3$
 - - - - - $\text{CeO}_2 - \text{Pr}_2\text{O}_3$
 - · - · - $\text{CeO}_2 - \text{Nd}_2\text{O}_3$
 - - - - - $\text{PrO}_2 - \text{Nd}_2\text{O}_3$