

Lawrence Berkeley National Laboratory

Lawrence Berkeley National Laboratory

Title

Source fabrication and lifetime for Li⁺ ion beams extracted from alumino-silicate sources

Permalink

<https://escholarship.org/uc/item/3xw4q5bs>

Author

Roy, Prabir

Publication Date

2012-04-18

Peer reviewed

Source fabrication and lifetime for Li⁺ ion beams extracted from alumino-silicate sources

Prabir K. Roy,* Wayne G. Greenway, and Joe W. Kwan

Lawrence Berkeley National Laboratory (LBNL), One Cyclotron Road, Berkeley, California, CA-94720, USA

(Dated: April 27, 2012)

A space-charge-limited beam with current densities (J) exceeding 1 mA/cm² have been measured from lithium alumino-silicate ion sources at a temperature of $\sim 1275^\circ$ C. At higher extraction voltages, the source appears to become emission limited with $J \geq 1.5$ mA/cm², and J increases weakly with the applied voltage. A 6.35 mm diameter source with an alumino-silicate coating, ≤ 0.25 mm thick, has a measured lifetime of ~ 40 hours at $\sim 1275^\circ$ C, when pulsed at 0.05 Hz and with pulse length of ~ 6 μ s each. At this rate, the source lifetime was independent of the actual beam charge extracted due to the loss of neutral atoms at high temperature. The source lifetime increases with the amount of alumino-silicate coated on the emitting surface, and may also be further extended if the temperature is reduced between pulses.

I. INTRODUCTION

Low-mass ions, such as lithium (Li⁺), have an energy loss peak (dE/dx) at a suitable kinetic energy [1] for heating targets to electron-volt temperatures for studies of warm dense matter (WDM) [2]. The Heavy Ion Fusion Sciences (HIFS) program [3] at Lawrence Berkeley National Laboratory will carry out WDM experiments using Li⁺ ion beam with energy 1.2 - 3 MeV to achieve volumetric heating up to 0.1 - 1 eV. Experiments will be carried out at the Neutralized Drift Compression Experiment-II (NDCX-II) facility [4, 5]. The conceptual design of NDCX-II was presented by A. Friedman *et al.* in Ref. [6] using a 10.9 cm diameter source of lithium ions (Li⁺). A Li⁺ ion beam can be produced by thermionic emission from the alumino-silicates compounds β -spodumene and β -eucryptite [7–9] at above 1200^o C. This type of ion source is also being used in magnetically confined fusion experiments for plasma diagnostics [10–14]. Table I shows Li⁺ current density data presented by several authors [7, 9, 11, 13, 15, 16]. Unfortunately, crucial details of the source fabrication and emission characterization are not always published. Krupnik *et al.* [15] demonstrated beam current density of 4 mA/cm² at 1400^o C to 1500^o C. However, this temperature range is near sintering (melting) of the lithium alumino-silicate compound and emission at this temperature is unstable due to the phase transitions of the compound. There is also concern about de-lamination of fragments from the substrate depending on the size of the ion source. This article describes preparation of lithium β -eucryptite compound, typical current density and lifetime, and variation of lifetime with temperature and mass of the alumino-silicate. These results reflect recent experimental work to characterize lithium alumino-silicate ion sources.

The total lithium ion charge produced by a source depends on the beam pulse length and extraction voltage, and on the ratio of the emitted alkali ions and neutral

atoms. In general, for a pulsed ion source, the total beam charge per pulse is

$$Q = J_b A \tau, \quad (1)$$

where Q is the charge of the beam pulse, J_b is the beam current density (assumed uniform), A is the emission area, and τ is the pulse duration. The total charge available (Q_a) by a source is,

$$Q_a = \left(\frac{M_s \eta}{m_i} \right) e, \quad (2)$$

where M_s is the mass of lithium β -eucryptite compound (in g) that is used to fabricate a source, η is the concentration of lithium atom by weight within the total compound, m_i is the mass of the ion, (for Li⁷, $m_i = 1.16 \times 10^{-23}$ g), and e is the ion charge. Therefore, the theoretical lifetime of a source for complete extraction (neglecting emission of neutrals) is related to the compound mass by

$$T_{\text{life}} = \left(\frac{M_s \eta}{m_i} \right) \left(\frac{e}{I_b} \right), \quad (3)$$

where $I_b = J_b A$ is the beam current for the source surface area A . For example, 0.4 mg lithium alumino-silicate compound that has a 5.56% concentration of lithium atom can provide a beam current (I_b) of 25 μ A with a lifetime of 3.4 hours.

In comparison with potassium alumino-silicate, the lithium alumino-silicate has much shorter lifetime and the coating is more difficult to make. In order to achieve a good coating, it is necessary to melt alumino-silicate into the porous tungsten substrate during the sintering (melting) process. In fact, the variation of the amount of absorbed material may affect the lifetime. Also, fabricating a source with a thick coating is problematic due to the nature of anisotropic thermal-expansion coefficients of the lithium alumino-silicate resulting in material stresses. There are surface cracks if the material is too thick and the material occasionally flakes off from the substrate surface. Figure 1(a) and Fig. 1(b) show 500 times and 2000 times magnified tungsten substrate surfaces, respectively; Fig. 1(c) shows a cracked and partially flaking

* PKRoy@lbl.gov

source surface, and Fig. 1(d) shows a smooth surface of a coated substrate. The magnified images were taken with a 15 kV electron microscope.

TABLE I. Li^+ current density measured by various groups.

Density (mA/cm^2)	Temp. ($^\circ\text{C}$)	Ref.
1 (β -eucryptite)	≈ 1230	[7]
0.02 (β -spodumene)	≈ 1200	[9]
1.5 (β -eucryptite)	≈ 1200	[11]
1 (β -eucryptite)	≈ 1300	[13]
4 (β -eucryptite)	≈ 1500	[15]
1.5 (β -eucryptite)	≈ 1275	[16]

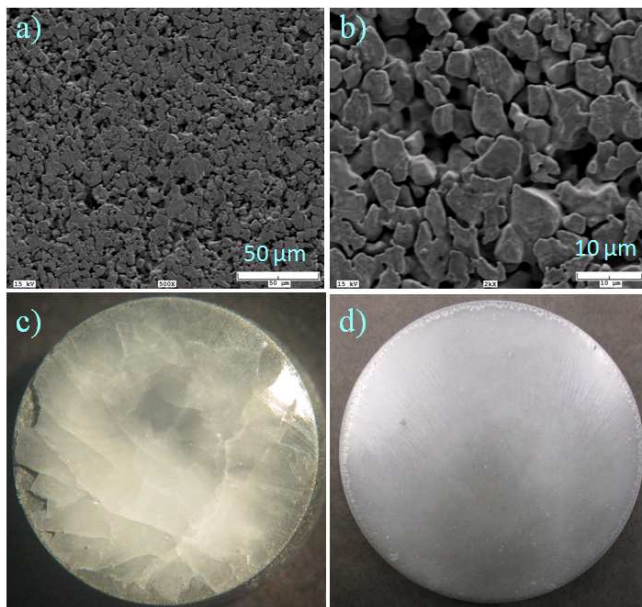


FIG. 1. (a) 70% to 80% dense an enlarged tungsten substrate surface shown 500 times magnified, (b) same surface shown 2000 times magnified, (c) source surface with cracks and flakes, and (d) an example of a smooth source surface.

II. PREPARATION OF LITHIUM

β -EUCRYPTITE ALUMINO-SILICATE SOURCE

There are several steps to prepare a lithium alumino-silicate source: (1) produce the chemical compound, (2) grind the compound into powder, (3) apply a “green coating”, (4) sinter the material to form a hard surface layer.

A. Preparing powder, coating and drying process

A mixture of Li_2CO_3 , Al_2O_3 , and SiO_2 is prepared following the stoichiometric ratio for β -eucryptite type source [7], and calcined at 600°C for one hour to drive off

CO_2 . This temperature has been chosen after testing several samples at different temperatures (400 to 1200°C) and analyzing under electron microscope to detect carbon. The resulting carbon-free calcined powder is ground to obtain a homogeneous mixture, and then heated to 1200°C to form $\text{Li}_2\text{O}-\text{Al}_2\text{O}_3-2\text{SiO}_2$ leucite crystalline phase. This β -eucryptite crystalline compound is ground to particulate size in the range of $100\ \mu\text{m}$, ready for use in coating. For example, in making a $0.63\ \text{cm}$ diameter Li^+ source, we use $0.037\ \text{gm}$ of $\leq 37\ \mu\text{m}$ alumino silicate powder. After mixing the powder with several drops of de-ionized water, the mixture is agitated for several minutes in an ultrasonic cleaner to break up the clumps. A 70-80% density tungsten button is used as substrate after it has been clean fired at 1700°C for one hour in a vacuum furnace. Just before coating, the surface of the tungsten button is wetted with de-ionized water, and then a small amount of alumino-silicate suspended in plenty of de-ionized water is allowed to be self-absorbed into the porous tungsten substrate to “prime” the surface. The next step is to spread alumino-silicate paste on the substrate surface and build that up to the desired thickness. A Teflon spatula can be used to create a smooth finish. The coated tungsten button is placed into a vacuum oven for drying. The oven temperature is set to 100°C with rise rate of $2^\circ\text{C}/\text{minute}$ starting from room temperature. Drying takes about an hour.

B. Vacuum furnace melting procedure

The furnace is first backfilled with Argon and a small amount of Hydrogen (negative 677 millibar pressure of 96% Argon plus 4% Hydrogen). The idea of using a partial pressure of inert gas was to minimize lithium vapor loss. The following temperature cycle was used in sintering the alumino-silicate sources. At first the system is heated to $\sim 80^\circ\text{C}$ at a ramp rate of $2^\circ\text{C}/\text{minute}$. After that, the temperature is increased at $5^\circ\text{C}/\text{min}$ until 200°C , followed by $10^\circ\text{C}/\text{min}$ to 1400°C . The peak temperature is held steady for 5 minutes, and then ramping down at $7^\circ\text{C}/\text{min}$ to room temperature. After cooling to room temperature, the furnace is slowly backfilled with argon to atmospheric pressure.

III. BEAM CURRENT DENSITY OF A PULSED BEAM

Several $0.63\ \text{cm}$ diameter lithium-alumino silicate ion sources were installed successively in an ion diode for testing. The distance between the source surface and the mid-plane of the extraction electrode was $1.48\ \text{cm}$. The extraction pulse voltage could be varied from $1\ \text{kV}$ to $10\ \text{kV}$. A tungsten filament coil was used to heat up the source to desire temperatures. The beam current was measured by a Faraday cup. A negative biased electrode in the cup was used to suppress unwanted electrons from

entering the positively biased collector. The positively biased collector also functions to suppress secondary electrons once the beam impinges on the collector plate. The pulsed was at 0.05 Hz and with pulse length of $\sim 6 \mu\text{s}$ each. The ion diode configuration was described in an earlier article [16] with the diagnostic details and identification of the elements. Figure 2 shows the measured beam current density as a function of the extraction voltage ranging from 0.5 kV to 10 kV for source temperatures set from 1220° C to 1300° C. The source temperature was measured using a disappearing filament-type brightness pyrometer with null-balance, lamp-current measuring circuit [17], calibrated with emissivity of tungsten. The pyrometer is sensitive to the brightness at $\lambda = 0.65$ microns. The “brightness temperature” measured using the pyrometer is affected by the emissivity of the alumino-silicate material. We note that the emissivity of the alumino-silicate at $\lambda=0.65$ microns may not be the same as tungsten.

The space-charge limited current density of an ion gun is defined by the Child-Langmuir law: $J(\chi, V, d) = \chi \frac{V^{3/2}}{d^2}$, where $\chi = \frac{4\epsilon_0}{9} \sqrt{\frac{2e}{m_i}}$, and d is the effective distance between source and extraction electrode. Thus, in the space-charge limited regime, the beam current is determined by the ion mass and the geometry of the ion gun, and is linearly proportional to $V^{3/2}$. Figure 2 shows that a space-charge limited current density of 1 mA/cm² can be obtained when the sources were operated at or above 1275° C with a 2.52 kV extraction bias. At higher extraction voltages, the source appears to become emission limited with $J \geq 1.5$ mA/cm², and J varies weakly on the applied voltage.

IV. SOURCE LIFETIME AS A FUNCTION OF TEMPERATURE AND LITHIUM MASS DEPOSITED

Two of the approximately 0.25 mm thick button sources were operated at a temperature of $\simeq 1265$ ° C to extract 5 to 6 μs beam pulses with $V=1.75$ kV. The pulses were repeated at a rate of 0.05 Hz until emission of the sources was significantly reduced. Figure 3 shows lifetime data from the sources when the beam was extracted on the space-charge limited regime. A uniform current density profile was observed for a duration of 30 to 40 hours after 10 to 15 hours of initial operation. It is speculated that the initial ≈ 15 hours was affected by contamination while the heat and pulsed extraction voltage gradually removed the contamination. It was observed that the lifetime varied from source to source even when the operating temperature, pulsed voltage and pressure of the chamber were not significantly altered. One possibility for the variation of source lifetime is due to the variation in the mass of alumino-silicate deposited on the sources. Therefore a separate experiment was set up to measure the lifetime of the ion source as a function of temperature and mass of Li alumino-silicate used. In

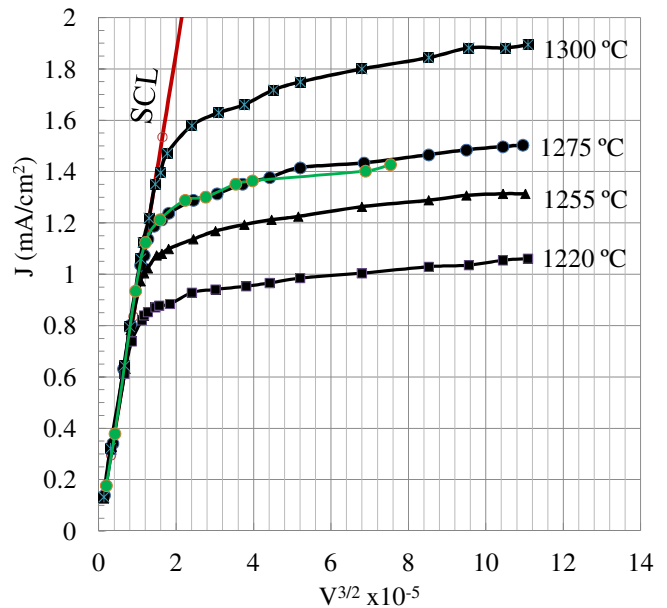


FIG. 2. Measured Li^+ beam current density (J) plotted versus $V^{3/2}$, with V in volts. Data in the dotted line at 1275° C (green) demonstrates reproducibility of beam emission from a different source prepared under similar conditions. The red line shows the space-charge limited (SCL) current density according to the Child-Langmuir law.

this set up, a narrow molybdenum foil with an embossed spherical depression at the center is used as the source substrate and simultaneously as a heater ribbon. A small amount of alumino-silicate material is deposited in the depression of pocket to form an emitting surface.

A. Preparation of pocket source and experimental setup

Figure 4 shows the experiment setup including the molybdenum ribbon. All the ribbons used were 0.075 mm thick, 4.9 mm wide, and 5 cm long. The pocket was accurately made, always has the same diameter of 2.1 mm regardless of depth. There were five different pocket depths: 0.25 mm, 0.43 mm, 0.50 mm, 0.63 mm, and 0.75 mm. The ribbons were cleaned with de-ionized water in ultrasonic cleaner. After being air-dried, the pockets of the ribbons were lightly blasted with aluminum oxide powder (“sand blasted”) to create a rough surface for anchoring alumino-silicate material when sintered (melted). The pockets of the ribbons were filled up with lithium alumino-silicate paste. Following the procedure given in Sec. II, the ribbons were dried in an air-furnace at $\approx 100^0$ C for a couple of hours, and then sintered in the vacuum furnace at 1400^0 C. The mass of alumino-silicate deposited was determined by measuring the weight of the ribbon with and without the alumino-silicate. A biased conducting plate, located at a distance of 4 mm from the source surface, was used as a collec-

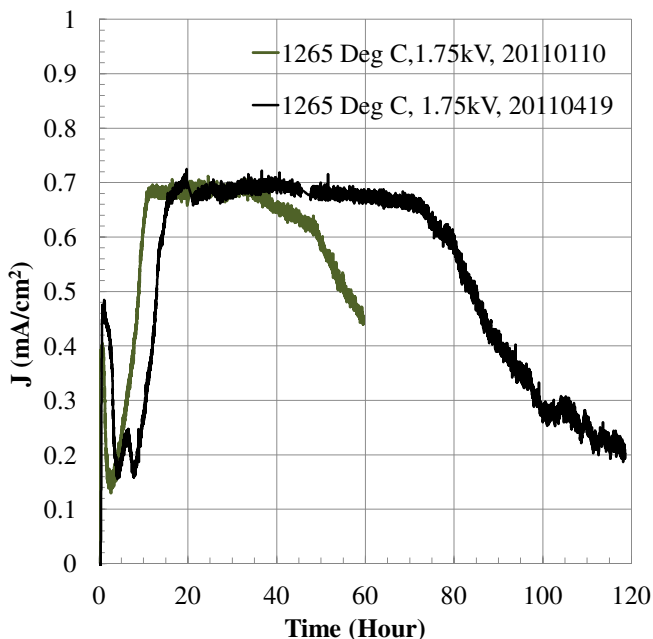


FIG. 3. Measured Li^+ beam current density (J) of pulsed source versus time. The thickness of sintered aluminosilicate was about 0.25 mm, but not kept constant. The source surface temperature of $\simeq 1265^\circ\text{C}$ and extraction voltage of $V \simeq 1.75\text{ kV}$ were unchanged during the data collection.

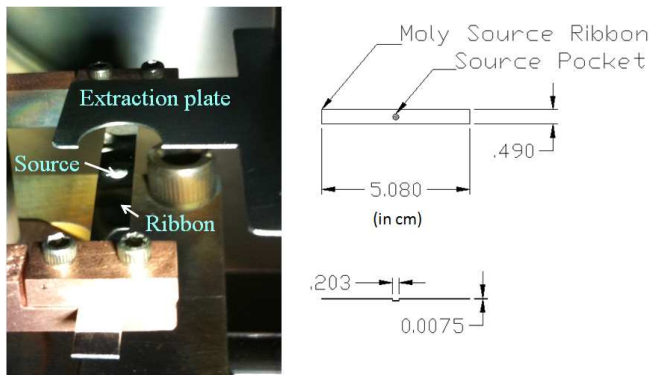


FIG. 4. Setup of a continuous beam extraction system. The ribbon location with a source pocket is indicated. The extraction plate was 4 mm above the source surface during the beam measurements. The cut-way aperture with the extraction plate is to measure temperature, and far enough from the beam trajectories.

tor to measure current (I_c). With the source at ground potential, the bias of the collector was set at negative 120 V to ensure space-charge limited emission. In this simple diode set up, secondary electrons coming off the collector plate are not suppressed and therefore the measured collector current will include secondary electron current. Fortunately, the secondary electron coefficient is very low [18] at 120 eV ion energy such that the collector current can be expected to be not more than a few percent higher than the actual beam current.

B. Lifetime variation with duty factor

The lifetimes of three ribbon sources were measured by varying their duty factors. The vacuum in the chamber was at $\sim 10^{-6}$ Torr. There were 3 cases: (A) continuously on for beam extraction, (B) pulsed on for 5 minutes followed by off for 10 minutes, (C) pulsed on for 5 minutes followed by off for 20 minutes. Thus the corresponding duty factors are 1, 0.33 and 0.2. The amount of aluminosilicate used was ~ 6.9 mg in case A, and ~ 5.8 mg in both case B and C. The surface area of each of the sources was 3.14 mm^2 . For all sources, during on time the temperature was held at 1265°C and the applied extraction voltage was 120 V, whereas during off time the temperature was reduced to 850°C with the extraction voltage turned off. The experiment continued until the sources were nearly depleted. As shown in Fig. 5, after a short initial period the beam current in all 3 cases reached the same level (over $60\ \mu\text{A}$) which persisted for many hours depending on the duty factor. The elapsed time to depletion of case A was ~ 16 hours (from the time the current has approached maximum to the time when the current decreased to $\sim 50\%$). For cases B and C, the corresponding elapsed time to depletion was ~ 29 hrs and ~ 49 hrs. Note that if lifetime is defined as the useful beam time, which is the product of elapsed time and the duty factor, then the measured lifetime for these cases A, B, and C are 16 hrs, 9.6 hrs, and 9 hrs, respectively. Since case A has a higher aluminosilicate mass than cases B and C, the lifetime comparison should be further normalized by their weights (see next section). The corresponding normalized ratio is 1 : 0.71 : 0.67.

C. Source lifetime depending on the mass of lithium aluminosilicate deposited

Five sources with different mass of lithium aluminosilicate deposited were measured to compare their lifetime. The other parameters of the experiment such as the distance between the source to collector plate (4 mm gap), the operating temperature, the beam extraction voltage, and the vacuum pressure (10^{-6} Torr) were all unchanged. The emitting surface area of the sources varied between 3.14 mm^2 to 4.15 mm^2 due to an error during the source fabrication process. All of the sources were operated at $\sim 1265^\circ\text{C}$ and the beams were extracted, continuously, with 120 V, until the beams current signal was reduced to a minimum detectable level relative to the peak current. The beam current density was expected to have little variation with mass because the space-charge limited current density should be depend only on the surface area and be independent of the source mass deposited insofar as there remain sufficient ions to be emitted. This is consistent with results shown in Fig. 6 where the measured beam current density (J) is plotted against the deposited source mass for a given area and operating temperature. Figure 7 shows the lifetime variation with

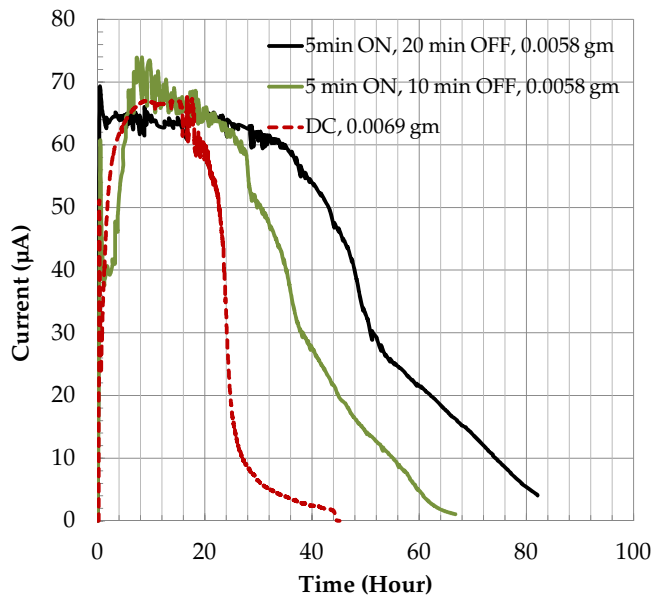


FIG. 5. The beam current versus lifetime of three sources with different duty factors. During on time, the temperature was at $\sim 1265^\circ\text{C}$ and an extraction voltage of 120 V, and during off time, the temperature was at $\sim 800^\circ\text{C}$ and zero extraction voltage. The surface of each of the sources was 3.14 mm^2 .

the mass density of lithium alumino-silicate deposited. The lifetime of the alumino-silicate is measured from the time beam current has transitioned from cleaning phase to operational mode to the time where the beam current has decreased to $\sim 50\%$ of its current at the transition level. As expected, the lifetime increases almost linearly with the lithium alumino-silicate mass deposited in the source.

The theoretically available charge can be calculated from the known mass of lithium in the β -eucryptite mixture. Figure 8 shows comparison of the calculated and measured time-integrated charge extracted from the sources. As expected, the extracted charge of the sources was proportional to the mass of the deposited alumino-silicate material. The difference between the measured charge and the theoretical limit is within about 10%.

V. CONCLUSION

In this paper, the procedures used to fabricate lithium alumino-silicate sources were discussed. Typically, a well made source would have glassy-type surface and the substrate surface fully coated without defects. Previously, it was observed that if a source surface was not glassy-type, the emission density could be as low as $1/3 - 2/3$ of that with glassy-type surface. Here, a space-charge-limited emission with current densities exceeding 1 mA/cm^2 was obtained from 0.64 cm diameter lithium alumino-silicate ion sources when operating at $\sim 1275^\circ\text{C}$.

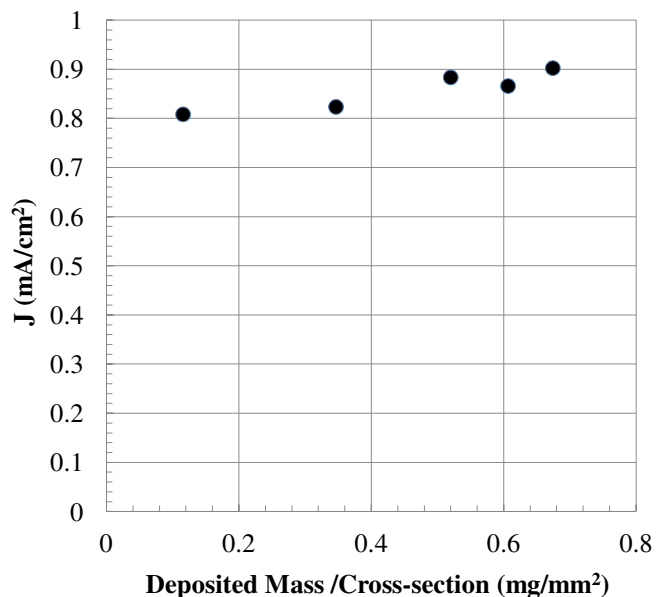


FIG. 6. Current density versus mass variation. The sources were operated at 1265°C . The surface area of the sources varied between 3.14 mm^2 to 4.15 mm^2 .

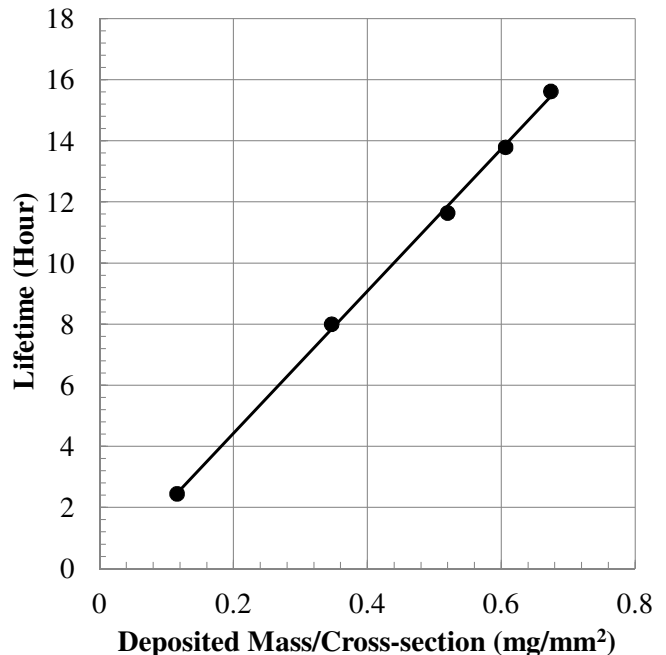


FIG. 7. The source lifetime as a function of alumino-silicate mass deposited.

The lifetime of a thin coated (on a tungsten substrate) lithium alumino-silicate source was between 30 to 40 hours when pulsed at 0.05 Hz and with pulse length of $\sim 6\text{ }\mu\text{s}$ each, i.e., a duty factor of 3×10^{-7} , at an operating temperature of $\geq 1275^\circ\text{C}$. A longer lifetime time, nearly ≥ 100 hours was reported recently [16] for similar sources. This time variation could be due to the variation

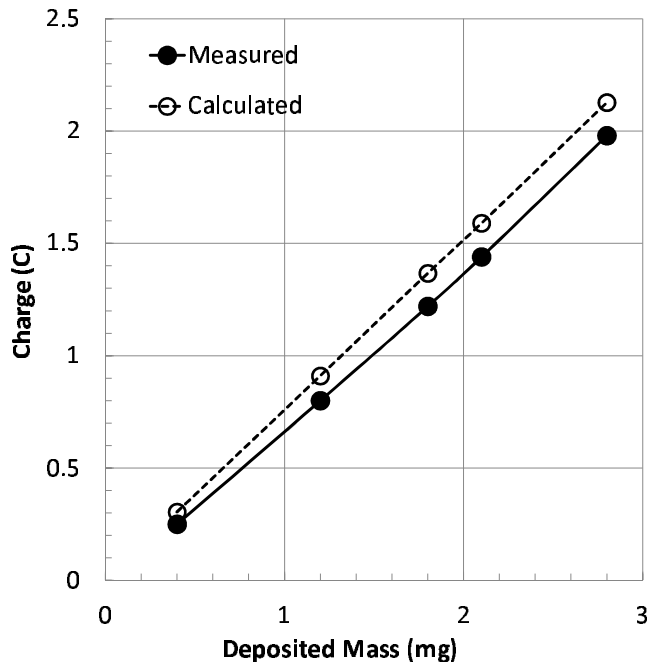


FIG. 8. Calculated and measured total extracted charge of sources with 0.4 mg, 1.2 mg, 1.8 mg, 2.1 mg, and 2.8 mg of alumino-silicate material deposited.

of amount of lithium alumino-silicate mass deposition on

the substrate surface as demonstrated in Fig. 7. Nevertheless, the total beam charge extracted during the 40 - 100 hrs with such low duty factor pulsed mode was very small. In comparison, the beam charge that was extracted in ~ 16 hrs lifetime when operated in dc mode was near the theoretical limit of the amount of lithium ions contained in the mass of alumino-silicate. This discrepancy suggested that the loss of lithium as neutral vapor was at a similar rate as the ion current extraction when the ion source temperature was at 1265°C . Thus the lifetime of a lithium ion source depends mostly on the total elapse time that the source is kept at high temperature. Consequently, one way to extend the useful lifetime is to momentarily reduce the operating temperature during the idle time between pulses. This could be a practical method if the pulse rate is very slow as once or twice per minute. A laser pulsed heating technique [19] could be useful in the heating system.

ACKNOWLEDGMENTS

The authors wish to thank A. Friedman, D. P. Grote, S. M. Lidia, S. M. Lund, B. G. Logan, W. M. Sharp and W. L. Waldron for useful discussions. T. M. Lipton, M. R. Dickinson, and T. E. Katayanagi provided valuable technical assistance. This work was performed under the auspices of the U.S. Department of Energy by LBNL under Contract DE-AC02-05CH11231.

-
- [1] J. J. Barnard, J. Armijo, R. M. More, A. Friedman, I. Kaganovich, B. G. Logan, M. M. Marinak, G. E. Penn, A. B. Sefkow, P. Santhanam, P. Stoltz, S. Veitser and J. S. Wurtele, *Nucl. Instrum. Methods Phys. Res., A* **577**, 275 (2007).
- [2] F. M. Bieniosek, J.J. Barnard, A. Friedman, E. Henestroza, J.-Y. Jung, M.A. Leitner, S. Lidia, B.G. Logan, R.M. More, P.A. Ni, P.K. Roy, P.A. Seidl, W.L. Waldron: Ion-beam-driven warm dense matter experiments, *The Sixth Int. Conf. on Inertial Fusion Sciences and Applications*, San Francisco CA, (2009).
- [3] B. G. Logan, F. M. Bieniosek, C. M. Celata, J. Coleman, W. Greenway, E. Henestroza, J. W. Kwan, E. P. Lee, M. Leitner, P. K. Roy, P. A. Seidl, J.-L. Vay, W. L. Waldron, S. S. Yu, J. J. Barnard, R. H. Cohen, A. Friedman, D. P. Grote, M. Kireeff Covo, A. W. Molvik, S. M. Lund, W. R. Meier, W. Sharp, R. C. Davidson, P. C. Efthimion, E. P. Gilson, L. Grisham, I. D. Kaganovich, H. Qin, A. B. Sefkow, E. A. Startsev, D. Welch, and C. Olson, *Nucl. Instrum. Methods Phys. Res., A* **577**, 1 (2007).
- [4] J. W. Kwan, A. Faltens, J. Y. Jung, E. P. Lee, M. Leitner, B. G. Logan, W. L. Waldron, A. Friedman, *Bulletin of the American Physical Society*, **54(15)**, 192 (2009).
- [5] W. M. Sharp, A. Friedman, D. P. Grote, R. H. Cohen, S. M. Lund, M. Leitner, J.-L. Vay, W. L. Waldron, *Bulletin of the American Physical Society*, **54(15)**, 211 (2009).
- [6] A. Friedman, J. J. Barnard, R. H. Cohen, D. P. Grote, S. M. Lund, W. M. Sharp, A. Faltens, E. Henestroza, J.-Y. Jung, J. W. Kwan, E. P. Lee, M. A. Leitner, B. G. Logan, J.-L. Vay, W. L. Waldron, R. C. Davidson, M. Dorf, E. P. Gilson, and I. D. Kaganovich, *Phys. of Plasma*, **17**, 056704 (2010).
- [7] J. P. Blewett and E. J. Jones, *Phy. Review*, **50**, 464 (1936).
- [8] S. K. Allison and M. Kamegai, *Rev. Sci. Intrum.*, **32**, 1090 (1961).
- [9] R. K. Feeney, W. E. Sayle II, and J. W. Hooper, *Rev. Sci. Intrum.*, **47**, 964 (1976).
- [10] D. M. Thomas, W. P. West, and K. McCormicks, *Rev. Sci. Intrum.*, **59(8)**, 1735 (1988).
- [11] D. M. Thomas, *Rev. Sci. Intrum.*, **66(1)**, 806 (1995).
- [12] J. Vukanic and I. Terzic, *Nucl. Instrum. Methods*, **111**, 117 (1973).
- [13] K. McCormick, S. Fiedler, G. Kocsis, and J. Zoletnik, *Fusion Eng. and Design*, **34-35**, 125 (1997).
- [14] G. Anda, G. Petravich, S. Zoletnik, S. Bato, *Nucl. Instrum. Methods Phys. Res.*, **74**, 715 (2005).
- [15] L.I. Krupnik et al., *IEEE Trans Plasma Sci.*, **36** 1536 (2008).
- [16] P. K. Roy, W. G. Greenway, J. W. Kwan, P. A. Seidl, W. L. Waldron, and J. K. Wu, *Rev. Sci. Intrum.*, **82**, 013304 (2011).
- [17] Optical Pyrometer made by Leeds and Northrup, UK.
- [18] P. M. Waters, *Phy. Review*, **111** (4), 1053 (1958).

- [19] P. A. Ni, J. W. Kwan, P. K. Roy, and W. L. Waldron, *Rev. Sci. Instrum.*, **82**, 023304 (2011).

DISCLAIMER

This document was prepared as an account of work sponsored by the United States Government. While this document is believed to contain correct information, neither the United States Government nor any agency thereof, nor the Regents of the University of California, nor any of their employees, makes any warranty, express or implied, or assumes any legal responsibility for the accuracy, completeness, or usefulness of any information, apparatus, product, or process disclosed, or represents that its use would not infringe privately owned rights. Reference herein to any specific commercial product, process, or service by its trade name, trademark, manufacturer, or otherwise, does not necessarily constitute or imply its endorsement, recommendation, or favoring by the United States Government or any agency thereof, or the Regents of the University of California. The views and opinions of authors expressed herein do not necessarily state or reflect those of the United States Government or any agency thereof or the Regents of the University of California.