

UC Berkeley

UC Berkeley Previously Published Works

Title

Durable, Ultrathin, and Antifouling Polymer Brush Coating for Efficient Condensation Heat Transfer.

Permalink

<https://escholarship.org/uc/item/4ch2b65m>

Journal

ACS Applied Materials and Interfaces, 16(1)

Authors

Lam, Cheuk

Donati, Matteo

Regulagadda, Kartik

et al.

Publication Date

2024-01-10

DOI

10.1021/acsami.3c17293

Peer reviewed

Durable, Ultrathin, and Antifouling Polymer Brush Coating for Efficient Condensation Heat Transfer

Shuai Li, Cheuk Wing Edmond Lam, Matteo Donati, Kartik Regulagadda, Emre Yavuz, Till Pfeiffer, Panagiotis Sarkiris, Evangelos Gogolides, Athanasios Milionis, Dimos Poulikakos,* Hans-Jürgen Butt, and Michael Kappl*



Cite This: *ACS Appl. Mater. Interfaces* 2024, 16, 1941–1949



Read Online

ACCESS |



Metrics & More




Article Recommendations



Supporting Information

ABSTRACT: Heat exchangers are made of metals because of their high heat conductivity and mechanical stability. Metal surfaces are inherently hydrophilic, leading to inefficient filmwise condensation. It is still a challenge to coat these metal surfaces with a durable, robust, and thin hydrophobic layer, which is required for efficient dropwise condensation. Here, we report the nonstructured and ultrathin (~ 6 nm) polydimethylsiloxane (PDMS) brushes on copper that sustain high-performing dropwise condensation in high supersaturation. Due to the flexible hydrophobic siloxane polymer chains, the coating has low resistance to drop sliding and excellent chemical stability. The PDMS brushes can sustain dropwise condensation for up to ~ 8 h during exposure to 111 °C saturated steam flowing at $3 \text{ m}\cdot\text{s}^{-1}$, with a 5 – 7 times higher heat transfer coefficient compared to filmwise condensation. The surface is self-cleaning and can reduce the level of bacterial attachment by 99%. This low-cost, facile, fluorine-free, and scalable method is suitable for a great variety of heat transfer applications.

KEYWORDS: dropwise condensation, heat transfer, transition, wetting, polydimethylsiloxane, durability

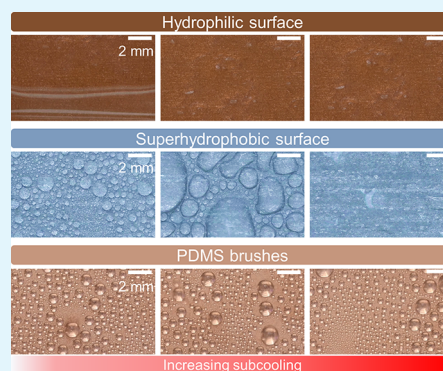

1. INTRODUCTION

Water vapor condensation is ubiquitous in nature and everyday life.^{1,2} It plays an important role in a variety of applications involving heat and mass transfer,^{3–5} e.g., for water harvesting,^{6–8} water desalination, power generation, and thermal management. Most heat transfer devices are manufactured from metals with high thermal conductivity, e.g., $\sim 398 \text{ W}\cdot\text{m}^{-1}\cdot\text{K}^{-1}$ for copper. However, the metals are hydrophilic and easily wetted by condensation from steam, leading to a stable liquid film covering the surface.^{9,10} During this so-called “filmwise condensation” mode, the liquid film hinders heat transfer because of its significant thermal resistance. By applying a low-adhesion or hydrophobic polymer coating on the metal surface,^{11–13} the condensate can nucleate, grow, coalesce, and easily slide away from the surface in the form of distinct droplets. This condensation mode is called “dropwise condensation”.¹⁴ It can show a performance enhancement of up to 1 order of magnitude compared to filmwise condensation, thanks to the periodic condensate removal, which leaves an accessible surface for fresh droplet nucleation.^{4,15}

On the other hand, these polymeric coatings usually have very low thermal conductivities on the order of 0.1 – $0.5 \text{ W}\cdot\text{m}^{-1}\cdot\text{K}^{-1}$.¹⁶ A thick polymer coating increases the thermal resistance, leading to an inefficient heat transfer process. For example, the state-of-the-art coatings, e.g., superhydrophobic

surfaces,^{17–20} and lubricant-infused surfaces,^{21–25} usually have a large thickness ranging from micrometer to millimeter (Figure 1a, Tables S1 and S2, Supporting Information). It can lead to a significantly high thermal resistance of more than $10^{-5} \text{ m}^2\cdot\text{K}\cdot\text{W}^{-1}$ on a copper substrate,^{26–28} compromising the heat transfer benefits from the dropwise condensation mode. To reduce the thermal resistance, ultrathin polymer brushes (ideally at the nanoscale level), such as polydimethylsiloxane (PDMS) brushes,^{29–36} can be grafted onto the metal substrate. The coatings are ultrathin (~ 6 nm) with low thermal resistance ($<10^{-7} \text{ m}^2\cdot\text{K}\cdot\text{W}^{-1}$, Figure S1, Supporting Information) and able to repel water drops with low contact angle hysteresis ($<10^\circ$).

Achieving a small coating thickness usually comes at the cost of compromised robustness. Despite the nanoscale thickness, PDMS brushes are promising alternative materials compared to superhydrophobic and lubricant-infused surfaces due to the absence of micro- or nanoscale rough surface topography,

Received: November 17, 2023

Revised: November 28, 2023

Accepted: November 28, 2023

Published: December 20, 2023



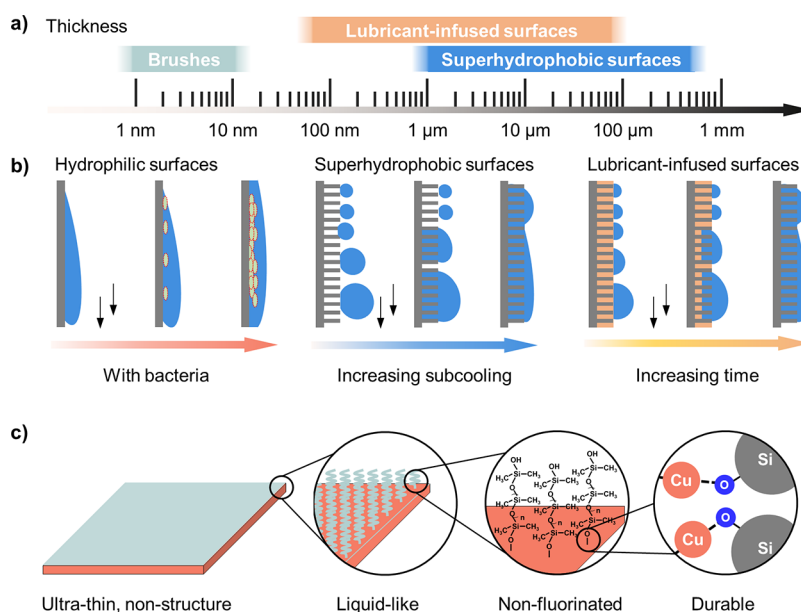


Figure 1. Overview. (a) Summarized coating thickness of brushes, superhydrophobic surfaces, and lubricant-infused surfaces. (b) Schematic showing the limitations of hydrophilic surfaces, superhydrophobic surfaces, and lubricant-infused surfaces with the accumulation of bacteria, increasing subcooling, and increasing time, respectively. (c) Surface characteristics of PDMS brushes.

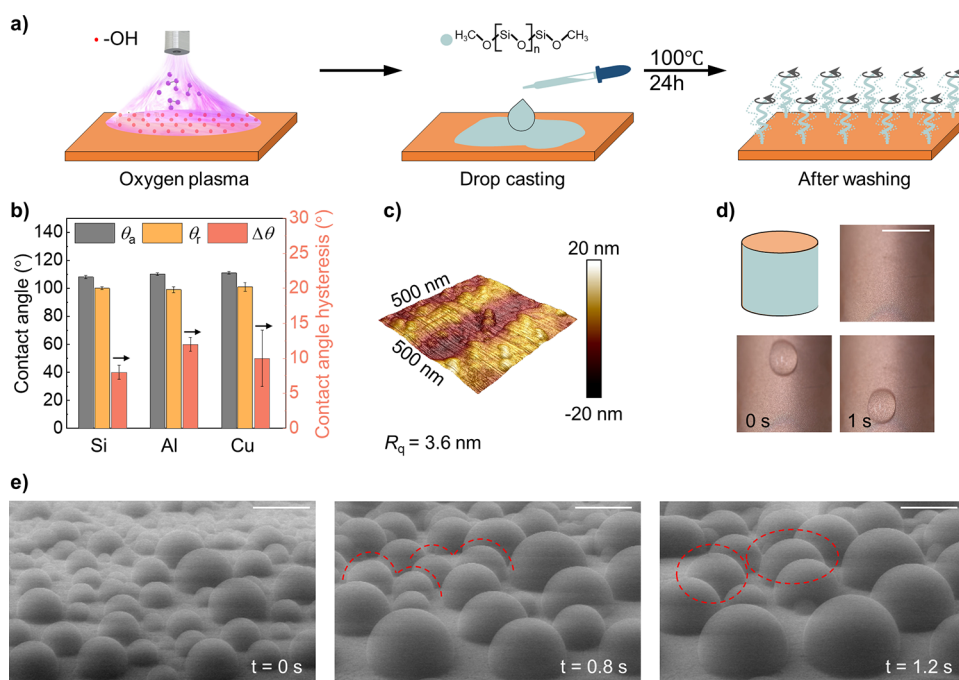


Figure 2. Preparation and characterization of PDMS brushes. (a) Fabrication of PDMS brushes via the drop-casting method. (b) Wetting properties (advancing and receding contact angles, contact angle hysteresis) of water on PDMS brushes-coated silicon wafer, aluminum, and copper substrates. (c) Surface morphology of PDMS brushes on the copper substrate. (d) Time-lapsed photographs of a water drop sliding on a PDMS brushes-coated copper cylinder (diameter: 24 mm). Tilt angle: 25°. Scale bar: 10 mm. (e) Time-lapsed photographs of water condensation and drop coalescence on PDMS brushes by environmental scanning electron microscopy. Scale bar: 20 μ m.

which typically is prone to damage,³⁷ as well as the good adhesion to the substrate due to strong covalent grafting. On the contrary, for superhydrophobic surfaces, the superhydrophobicity relies on vapor cushions within the micro/nanostructures (Cassie state).^{38–40} At elevated supersaturation, impalement of the micro/nanostructures by water will occur (Wenzel state);⁴¹ thus, the surface loses its superhydrophobicity, leading to filmwise condensation (Figure 1b).^{42,43} For lubricant-infused surfaces, although studies have

shown their excellent liquid repellency, and heat transfer coefficient up to 5 times higher compared to filmwise condensation,²⁶ they still face the issue of gradual lubricant depletion in the long term (Figure 1b).⁴⁴

Another problem in condensation applications is the contamination on the surface, e.g., biofouling, which can be a major issue that limits the heat transfer efficiency in industrial applications, e.g., condenser tubes,^{45,46} and heat exchangers.⁴⁷ Microorganisms, such as bacteria, can attach to the surface of

the condenser fins and tubes, acting as defects,⁴⁸ and continue expanding to form a fouling layer that can affect the heat transfer. This fouling layer can reduce the efficiency of the condenser by acting as an insulator, increasing the resistance to heat transfer and obstructing the departure of water. Although this problem is more relevant to the cooling side (the internal part of condenser tubes), it is not rare that the external part of the condenser tubes faces the problem of contamination. For example, in atmospheric water harvesting applications,^{49,50} dust or microorganisms may attach to the surface during environmental exposure. Under ambient conditions, bacteria can easily grow and form a fouling layer. Therefore, antifouling is a very desirable property of coatings for heat transfer applications. Finally, the green chemistry of the polymeric coating material is also essential. With continuous use, coating degradation is inevitable, and biopersistent elements can be released into the environment, especially in processes that involve open systems. Specifically, hydrophobic surfaces sustaining dropwise condensation are usually made with long-chain perfluorinated polymers, which are not environmentally friendly, and their byproducts during degradation tend to bioaccumulate.⁵¹

Here, we study the condensation of water on PDMS brushes (Figure 1c) under harsh experimental conditions. Because of their strong covalent bond with the substrate (Figure S2, Supporting Information) and the absence of rough surface microfeatures, PDMS brushes are stable even at challenging, high subcooling values and steam pressures. We experimentally demonstrate the coating resilience with an accelerated endurance test characterized by exposure to superheated steam at 111 °C and 1.42 bar with a shear velocity of 3 m·s⁻¹. Under the aforementioned conditions, the PDMS brushes can sustain dropwise condensation for at least 8 h and show a heat transfer coefficient that is 5 times greater than that of filmwise condensation. We also show that the PDMS brushes can effectively repel bacteria such as *Escherichia coli* and *Staphylococcus aureus*, reducing the attachment by 99%. With all these merits, PDMS brushes are promising to open a new avenue to enhance practical heat transfer performance by sustainable and effective means.

2. RESULTS AND DISCUSSION

2.1. Preparation and Characterization of PDMS Brushes.

PDMS brushes were prepared by a drop-casting and annealing method as described by Krumpfer and McCarthy for silicon wafers (Figure 2a and Methods).^{52–56} Briefly, a PDMS liquid drop (molecular weight of 11,740 g·mol⁻¹) was deposited onto an oxygen-plasma-activated copper surface, followed by heating. The grafting process of PDMS brushes onto the surface is initiated by siloxane hydrolysis. Then, the silanol-terminated chain can be covalently bonded onto the hydroxyl group on the copper (Figure S3, Supporting Information).^{29,57,58} The resulting PDMS coating on copper is smooth with root-mean-square roughness of 3.6 ± 0.5 nm in an area of 500 × 500 nm² (Figure 2c). This value is mainly related to the roughness of the pristine copper substrate (3.0 nm ± 0.7 nm). The cost of the coating is estimated to be less than 10 USD per m² (Table S3, Supporting Information).

The coated surface is hydrophobic with a water advancing contact angle of 111° ± 1° and a contact angle hysteresis of 10° ± 4° (Figure 2b). PDMS brushes could also be easily applied on a variety of materials, such as silicon and aluminum, leading to similarly improved wetting properties: water

advancing contact angle and contact angle hysteresis on silicon and aluminum substrates are 108° ± 1°, 8° ± 1°, and 110° ± 1°, 12° ± 1°, respectively. In addition, PDMS brushes can be applied on curved surfaces. As shown in Figure 2d and Video S1 (Supporting Information), a water drop slides off on a PDMS-coated cylinder copper surface (diameter: 24 mm) within 1 s.

The thickness and grafting density of PDMS brushes were analyzed by atomic force microscopy (AFM) force spectroscopy (Figure S4, Supporting Information), giving a coating thickness of $d = 6 \pm 1$ nm. It has been reported recently that lubricant thickness could be optimized for an efficient condensation process on lubricant-infused surfaces utilizing drop coarsening due to merging by lateral capillary forces.⁵⁹ Such a mechanism cannot work for the much thinner PDMS brush coatings, but their orders of magnitude smaller thickness leads to a negligible thermal resistance, which is even more beneficial for heat transfer. Following the equation $\Gamma = (d\rho N_A)/M_w$, the grafting density Γ of our PDMS brushes was estimated as 0.3 ± 0.05 chains·nm⁻², where ρ and N_A represent mass density and Avogadro constant, respectively.⁶⁰

The water condensation dynamics on PDMS brushes are first studied at the microscale, in situ, using an environmental scanning electron microscope (ESEM, FEI Quanta 650 FEG). As shown in Figure 2e, the droplets maintain spherical cap shapes. While growing, the droplets easily coalesce without visible contact line pinning, suggesting the excellent droplet mobility and water repellency of PDMS brushes for tiny condensing droplets. When considering superhydrophobic surfaces, it can be challenging to repel tiny droplets because the superhydrophobicity relies on the empty space within structures.^{19,61,62} At high subcooling values, if the droplet size is comparable to or smaller than the size of the surface features, droplets may stay pinned inside these features, and this may cause coalescence at early growth stages with other droplets and consequently lead to the formation of filmwise condensation.^{39–43,63}

As a primary durability test for the PDMS brushes, we used drop sliding measurement in a custom-built device, as reported before.⁶⁴ A needle connected with a peristaltic pump generated a series of water drops (each 45 μL). The stage was tilted at 50°, and a high-speed camera (FASTCAM MINI UX100, see Methods for details) was attached to the stage to capture videos. After continuously sliding thousands of water drops over the surface, PDMS brushes still exhibit good hydrophobicity (Videos S2–S5, Supporting Information). The velocity of drops 1 and 5000 was $0.08 \text{ m}\cdot\text{s}^{-1} \pm 0.02 \text{ m}\cdot\text{s}^{-1}$ and $0.10 \text{ m}\cdot\text{s}^{-1} \pm 0.02 \text{ m}\cdot\text{s}^{-1}$, respectively (Figure S5, Supporting Information). The corresponding dynamic advancing contact angle and contact angle hysteresis for drop 1 and drop 5000 were $130^\circ \pm 3^\circ$, $66^\circ \pm 7^\circ$, and $126^\circ \pm 3^\circ$, $56^\circ \pm 6^\circ$, respectively. The larger value of dynamic contact angle hysteresis compared to the static contact angle hysteresis shown in Figure 2b is attributed to the substantially higher drop velocity.⁶⁵

2.2. Condensation Heat Transfer Performance at Low Pressure.

The condensation heat transfer performance of PDMS brushes was tested with a custom-built condensation chamber under low saturation vapor pressure (30 mbar, steam temperature 24 °C) (Figure S6, Supporting Information, and methods for details).^{5,26} These conditions are comparable to industrial condensers' operation parameters. The steam was

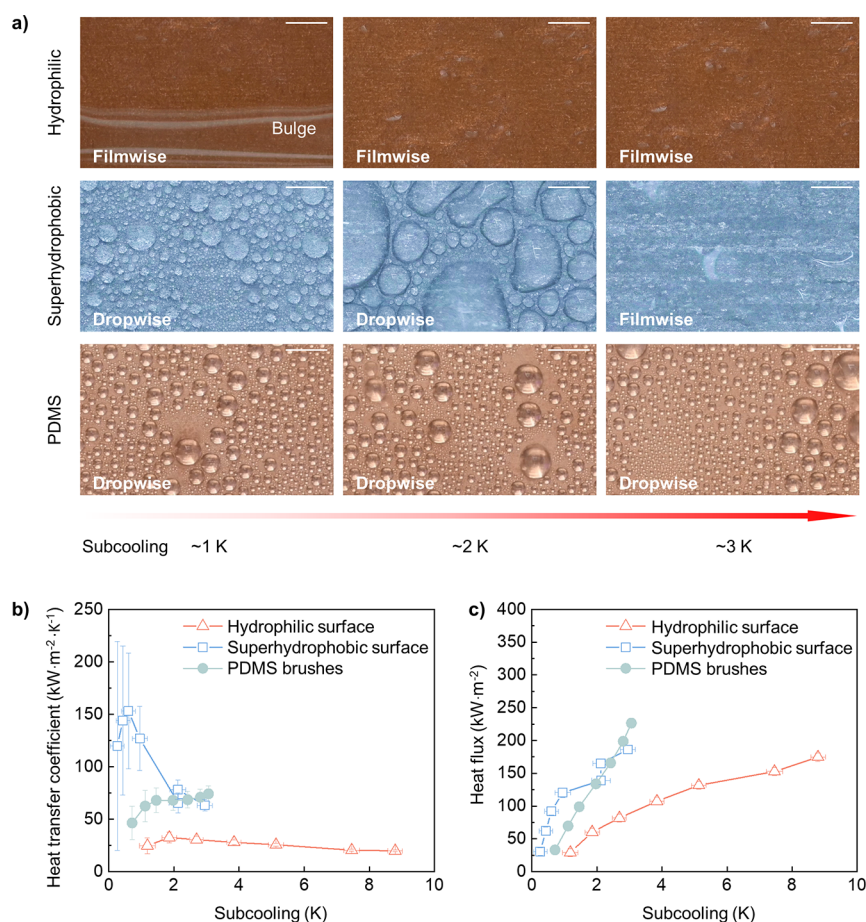


Figure 3. Condensation heat transfer performance at a low steam pressure (30 mbar). (a) Optical images of hydrophilic surface, superhydrophobic surface, and PDMS brushes surface at different subcooling (1, 2, and 3 K) under steady-state condensation. Scale bar: 2 mm. (b) Heat transfer coefficients of the three vertically placed surfaces at different subcooling. Steam pressure: 30 mbar; steam flow rate: $\sim 4.6 \text{ m}\cdot\text{s}^{-1}$; steam flow direction: horizontal. (c) Corresponding heat flux of the three surfaces at different subcooling. Data for superhydrophobic surface from our recent work.⁶⁶

generated from an electric boiler and flowed horizontally across the sample, where the flow speed was $\sim 4.6 \text{ m}\cdot\text{s}^{-1}$.

With increased subcooling, the dropwise condensation mode on PDMS brushes was maintained (Figure 3a, Videos S6–S8, Supporting Information), without a change of the circular drop shape. On our superhydrophobic reference surface (see Experimental Section for details),⁶⁶ dropwise condensation was observed at subcooling $< 1 \text{ K}$. Superhydrophobic surfaces are known for their jumping dropwise condensation mode only at low subcooling.^{17,67} However, the drops show an irregular shape at subcooling of 2 K and finally turn into a liquid film at 3 K. The filmwise condensation is due to the flooding at high subcooling values because the surface remains superhydrophobic after condensation upon drying. Filmwise condensation on the superhydrophobic surface still allows higher heat transfer compared to that on the conventional hydrophilic surface. The reason is the difference in the wetting situation. On the conventional hydrophilic surface, a thick liquid film is formed, leading to large thermal resistance.

It can be recognized from the bulge formed at the bottom of the hydrophilic surface (Figure 3a and Video S6). On the superhydrophobic surface, filmwise condensation leads to flooding of the surface structure, which then acts as a wicking layer. Therefore, film thickness is reduced to the order of the structure thickness of the superhydrophobic surface layer, and

no bulge is visible at the lower end. This leads to a lower thermal resistance of the superhydrophobic layer during filmwise condensation (Figure 3a and Video S7). The different condensation modes for these three surfaces highlight the ability of PDMS brushes to sustain dropwise condensation over a wide range of subcooling values.

This stability of dropwise condensation is also reflected in the trend of the heat transfer coefficient as a function of subcooling (Figure 3b). Although the superhydrophobic surface shows better heat transfer performance than PDMS brushes at low subcooling, the performance on the superhydrophobic surface decreases and approaches that for filmwise condensation around a subcooling of 2–3 K. Figure 3c plots the heat fluxes of the three surfaces. At subcooling of 3 K, PDMS brushes exhibit a heat flux of $233 \text{ kW}\cdot\text{m}^{-2}\cdot\text{K}^{-1}$, which is 20% higher than that of the superhydrophobic surface. It should be noted that we cannot measure the heat transfer coefficient at higher subcooling ($> 3 \text{ K}$) for these better-performing surfaces due to their efficiency. Nevertheless, it is reasonable to predict that PDMS brushes can still maintain dropwise condensation at higher subcooling values or condensation rates, due to the absence of micro and nanostructures that can eventually get flooded with water.

2.3. Condensation Heat Transfer Performance at High Pressure. To quantitatively evaluate condensation

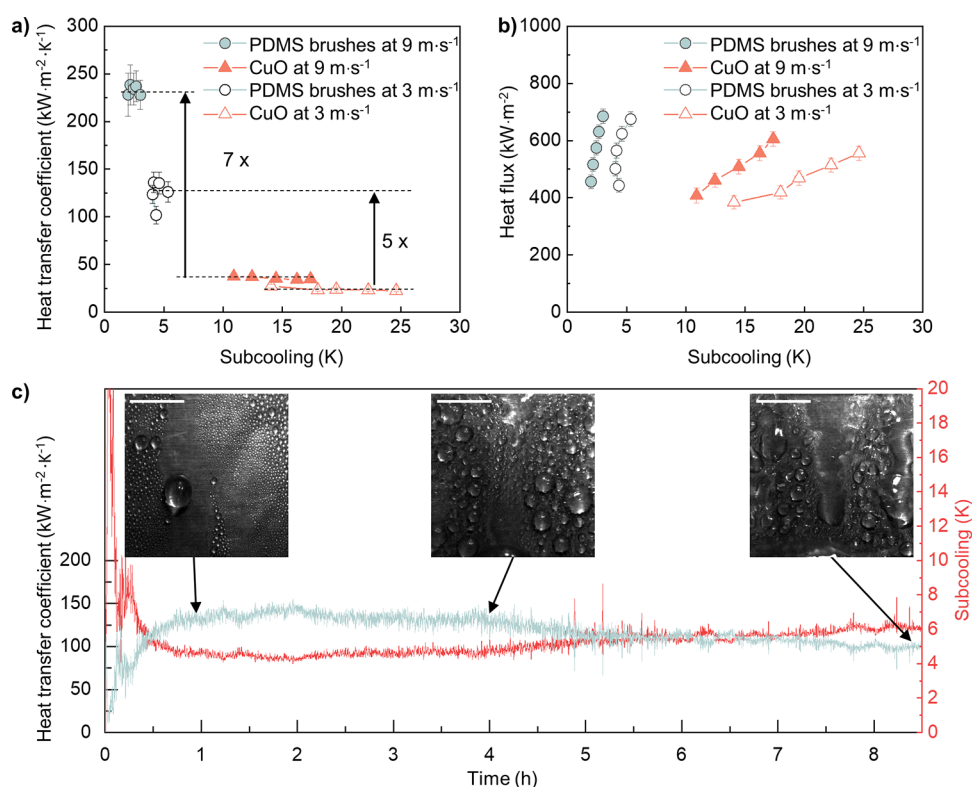


Figure 4. Condensation heat transfer performance at high pressure. (a) Heat transfer coefficients of vertically placed PDMS brushes and hydrophilic CuO at different subcooling values. Steam temperature: 111 °C; steam pressure: 1.42 bar; steam flow rate: 3 and 9 m·s⁻¹. Dashed lines mark the average values. (b) Corresponding heat flux of the two surfaces at different subcooling. (c) Heat transfer coefficient of PDMS brushes within ~8 h and corresponding subcooling values. Inset: High-speed photographs of condensed drops. Scale bar: 5 mm.

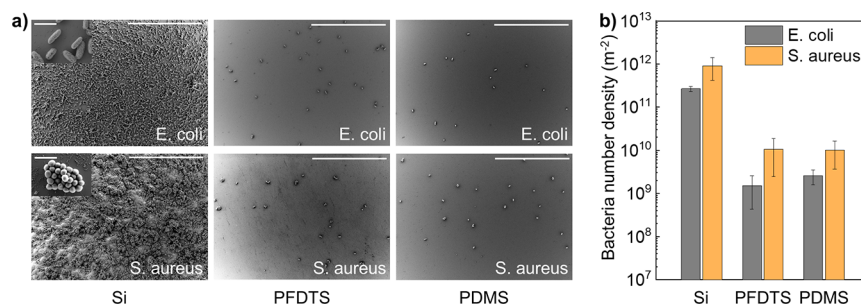


Figure 5. Antifouling performance of PDMS brushes. (a) SEM images of *E. coli* (rod-shaped, top three images) and *S. aureus* (spherical-shaped, bottom three images) on silicon wafer, PFDTs, and PDMS brushes surface. Scale bar: 50 and 2 μm (inset). (b) Number density of attached bacteria on three surfaces.

heat transfer performance in harsh conditions, the PDMS brush surface was tested in a high-pressure flow chamber where the steam pressure and temperature were 1.42 bar and 111 °C, respectively (Figure S7, Supporting Information).⁵ The experiment is conducted in a flow condensation environment, while the steam flowed vertically with velocities of 3 or 9 m·s⁻¹. As shown in Figure 4a,b, PDMS brushes exhibited a higher heat transfer coefficient at both steam velocities. At 3 m·s⁻¹, the average heat transfer coefficient reached 125 kW·m⁻²·K⁻¹, which is ~5 times higher than that on a bare CuO reference surface (filmwise condensation). Due to enhanced advection, the heat transfer performance was better on both surfaces at a steam flow rate of 9 m·s⁻¹. On PDMS brushes, the heat transfer coefficient reaches 233 kW·m⁻²·K⁻¹, which is ~7 times higher than that on the CuO surface.

To test the coating durability under condensation, we focused on the PDMS brushes with a steam flow rate of 3 m·s⁻¹ for an extended period (~8 h). The heat transfer coefficient and corresponding subcooling were continuously measured over 8 h, while condensation rates were recorded at several intervals (Figure 4c and Video S9, Supporting Information). In the first 0.5 h, the system had to stabilize. The heat transfer coefficient increased and oscillated initially. After ~0.5 h, the experimental conditions were stable, and the surface exhibited a heat transfer coefficient of ~121 kW·m⁻²·K⁻¹. Up until 7 h, dropletwise condensation remained the dominant mode. Afterward, an increase in the departure droplet sizes was observed, and localized filmwise condensation islands appeared (~30% area shows filmwise condensation). However, the heat transfer coefficient remained as high as 103 kW·m⁻²·K⁻¹ at 8.8 h, which is still more than 4 times higher than that of filmwise

condensation. Such accelerated durability test proves that the ultrathin PDMS brushes sustain efficient dropwise condensation in harsh conditions for ~ 8 h, showing its potential for practical applications where the conditions are much milder.⁶⁸ The filmwise condensation, in the end, may be related to the oxidation process of copper, which degrades the wettability of PDMS coating.^{67,69} It should be noted that even after degradation, the wetting properties of the coating can be restored by applying a bit of PDMS oil (Figure S8, Supporting Information). Moreover, as a perspective of future impacts, although PDMS brush coating is grafted on the flat substrate here, it may also be used to modify the structured surface to further enhance condensation.⁷⁰

2.4. Antifouling Test. We further measured the antifouling property by immersing the substrate in solutions containing *Escherichia coli* (*E. coli*) and *Staphylococcus aureus* (*S. aureus*), respectively. Both *E. coli* and *S. aureus* are commonly found bacteria. *E. coli* is Gram-negative and rod-shaped, while *S. aureus* is Gram-positive and spherically shaped. After 1 day of culture at 37 °C, the samples are taken out and washed gently to remove the floating bacteria. Scanning electron microscopy (SEM) images showed a significantly reduced bacterial number on PFDTs and PDMS surfaces when compared to those on the uncoated surface (Figures S9 and S10, Supporting Information). Specifically, the attached *E. coli* number density was $(2.7 \pm 0.3) \times 10^{11} \text{ m}^{-2}$ on Si surfaces, $(1.5 \pm 1.1) \times 10^9 \text{ m}^{-2}$ on PFDTs surfaces, and $(2.6 \pm 1.0) \times 10^9 \text{ m}^{-2}$ on PDMS surfaces (Figure 5b). For *S. aureus*, the number density on the three surfaces were $(9.1 \pm 4.9) \times 10^{11} \text{ m}^{-2}$, $(1.1 \pm 0.8) \times 10^{10} \text{ m}^{-2}$, and $(1.0 \pm 0.6) \times 10^{10} \text{ m}^{-2}$, respectively. The calculated antibacterial efficiency (i.e., the ratio of reduced bacterial amount on the surface to the total amount on the Si surface) reached $\sim 99\%$ on both PFDTs and PDMS surfaces, showing the comparable antifouling property of the PDMS surface to the conventional fluorinated PFDTs surface. A quick anticontamination test showed that the PDMS brushes can effectively repel adhesive materials such as chalk powder and chili sauce, revealing its self-cleaning properties (Figure S10 and Videos S10–S11, Supporting Information).

3. CONCLUSIONS

We demonstrate that the low-cost, flat, antifouling, and nonfluorinated PDMS brush coating can sustain high-performing dropwise condensation at extreme conditions, e.g., high subcooling value, and high steam shear flow and temperature. The PDMS brushes consist of siloxane polymer chains, where one side is covalently grafted onto the substrate and the other side is free and flexible. The coating is thin (thickness of 6 nm) and water-repellent (advancing contact angle of $\sim 110^\circ$ and contact angle hysteresis of $\sim 10^\circ$ on copper). The experimental results show that PDMS brushes on copper substrate exhibit dropwise condensation and ~ 3 – 7 times higher heat transfer coefficients compared to that of filmwise condensation formation on pristine copper substrates in the low (30 mbar) and high (1.4 bar) pressure chambers. The PDMS brushes also exhibit excellent durability in high-pressure environments, which is confirmed by the 8-h condensation test under harsh conditions of 1.4 bar steam pressure and 3 m s^{-1} steam velocity. Additionally, PDMS brushes can effectively repel 99% of bacteria, e.g., *E. coli* and *S. aureus*. Therefore, PDMS brushes are promising candidates for developing a low-cost, environment-friendly, and effective coating for condensation heat transfer applications.

4. EXPERIMENTAL SECTION

4.1. Surface Preparation. PDMS brushes are prepared by drop-casting. First, the substrates (silicon, aluminum, or copper) were washed in acetone, 2-propanol, and deionized water with ultrasonication for 10 min, respectively. Then, they are treated with an oxygen plasma (Diener Electronic Femto, 120 W, $6 \text{ cm}^3 \cdot \text{min}^{-1}$ oxygen flow rate) for 5 min. Afterward, several drops of PDMS (polydimethylsiloxane, 100 cSt, Thermo Scientific) are applied on the substrate, which is then covered by spontaneous wetting. After full spreading, the substrates were put in the oven at 100 °C for 24 h and washed with acetone afterward to remove any unbound residue. This preparation method is repeated twice. PFDTs surfaces are prepared via chemical vapor deposition in a vacuum desiccator. Twenty μL of 1H,1H,2H,2H-perfluorodecyltrimethoxysilane is added before the desiccator is vacuumed below 20 mbar. The reaction lasts for 4 h. Hydrophilic CuO surfaces are prepared by immersing oxide-free pristine copper in boiling water for 30 min. The superhydrophobic surfaces are fabricated as described before.⁶⁶ Briefly, after the cleaning process, the substrates are immersed into a 9.25% V/V aqueous solution of hydrochloric acid for 10 min to fabricate microstructures. Then they are immersed in boiling water for 5 min to fabricate nanostructures on top of microstructures through the boehmitage process. Finally, the substrates are coated with a thin hydrophobic film through C_4F_8 plasma deposition.

4.2. Surface Characterization. Advancing and receding contact angles are measured using a goniometer (OCA35, Dataphysics). The volume of sessile water was gradually ($1 \mu\text{L} \cdot \text{s}^{-1}$) increased from 5 to 20 μL and decreased back to 5 μL . The contact angles were determined by fitting an ellipse to the contour images. The surface morphology was measured using Dimension Icon AFM (Bruker) in tapping mode. Reflective aluminum Si cantilevers (OLTESPA-R3) with a spring constant of $\sim 2 \text{ N} \cdot \text{m}^{-1}$ were used. The thickness of the brush layer was measured using an AFM instrument (JPK Nanowizard 4) in force mapping mode. Force–distance curves were recorded with a grid of 16×16 points on an area of $1 \times 1 \mu\text{m}^2$. For the observation of condensation using an environmental scanning electron microscope (ESEM) (Quanta 650 FEG, FEI), the samples were placed on a custom-made copper platform, which was cooled with a recirculating chiller and maintained at ~ 2 °C. The drop velocity and dynamic contact angles on the surface were determined by analyzing videos of drop sliding via a MATLAB program (DSAFM). The videos were recorded using a high-speed camera (FASTCAM MINI UX100, Photron with a Titan TL telecentric lens, 0.268x, 1 in. C-Mount, Edmund Optics) at a frame rate of 500 FPS. Briefly, the edge position of the drops was detected, after the drop images were corrected by subtracting the background from the original images and tilting according to the background image. The drop velocities were calculated by the displacement from each frame. Dynamic advancing and receding contact angles were determined by applying a fourth-order polynomial fit to the drop contour in each image.

4.3. Condensation Heat Transfer Measurements. We used two custom-made experimental setups for the condensation tests similar to our recent work.^{5,26} The chambers are evacuated first before the introduction of steam. An electric boiler was used to generate steam from deionized water. Condensation tests were performed with saturated steam at a pressure of 1.42 bar or 30 mbar. The samples were mounted on a copper block. Several temperature sensors inside the copper block were used to determine the condensation heat flux (q'') through the surface by following the equation $q'' = k_c A_c / A_e \cdot dT/dx$. Here, k_c is the thermal conductivity of the copper cooler, A_c is the cross-sectional area of the cooler, A_e is the area of the exposed condensing surface, and dT/dx is the constant thermal gradient along the array. dT/dx was computed from a least-squares linear fit of the temperatures measured with the temperature sensor array. In the low-pressure (30 mbar) chamber, the surface temperature was measured by two temperature sensors attached to the surface. Videos were recorded with a DSLR (D7500, Nikon) and a macro lens (AF Micro-Nikkor 200 mm f/4D IF-ED, Nikon). In the high-pressure chamber

(1.42 bar), the surface temperature was estimated by using a thermocouple placed inside the substrate. The videos were recorded by using a high-speed camera (FASTCAM Mini UX100, 2000FPS) and the same lens. More details are in Figures S6 and S7, Supporting Information.

4.4. Antifouling Tests. To test the antifouling property, the samples ($1 \times 1 \text{ cm}^2$) are first sterilized by UV light (366 nm) for 15 min. Then, the samples are placed in a sterile 24-well plate, and each well includes 2 mL of the bacteria test suspension (refer to Figure S11 in the Supporting Information for the preparation of bacterial suspension). The samples are incubated for 1 day at 37 °C before the medium is removed from the samples and gently washed 3 times with 1 mL saline solution (0.85% NaCl in Milli-Q water). Afterward, the bacteria is fixed by 1 mL glutaraldehyde (Sigma-Aldrich, 2.5% (v/v) in the saline solution) for 30 min at room temperature. Subsequently, the coatings are gently washed 3 times with the saline solution and dehydrated with a series of ethanol (30, 40, 50, 60, 70, 80, 90, 95, and 99.89%, 15 min each, last step twice). Lastly, the samples are dried under vacuum at room temperature overnight prior to SEM imaging. For bacterial number counting, more than 30 images are taken at random positions by scanning electron microscopy (SEM, LEO 1530 Gemini, Zeiss).

■ ASSOCIATED CONTENT

Data Availability Statement

The authors declare that the data supporting the findings of this study are available within the paper and its Supporting Information or from the corresponding author upon reasonable request.

SI Supporting Information

The Supporting Information is available free of charge at <https://pubs.acs.org/doi/10.1021/acsami.3c17293>.

Schematic of the thermal resistance network of PDMS brushes; bond dissociation energies; schematic showing the bonding process of PDMS brushes on the copper; water contact angles on PDMS brushes; estimation of the grafting density of PDMS brushes; water drop sliding velocity and contact angles on PDMS brushes coated copper plate; device for condensation heat transfer measurements at 30 mbar and 1.4 bar; durability test of PDMS-coated copper in hot water ($\sim 100 \text{ }^\circ\text{C}$) and its recovery; antifouling property of different surfaces; photographs showing the self-cleaning property of PDMS brushes; Schematic of bacterial suspension preparation; Thickness of the current state-of-the-art superhydrophobic surfaces; thickness of the current state-of-the-art lubricant infused surfaces; and cost estimation of PDMS brushes on a copper plate (PDF) Water drop slide off a PDMS-coated copper tube. Tilt angle: 25° (AVI)

Water drop sliding on PDMS brushes coated copper plate: 1st drop (AVI)

Water drop sliding on PDMS brushes coated copper plate: 100th drop (AVI)

Water drop sliding on PDMS brushes coated copper plate: 1000th drop (AVI)

Water drop sliding on PDMS brushes coated copper plate: 5000th drop (AVI)

Left: Steam condensation on a hydrophilic copper oxide surface. Right: real-time heat transfer coefficient and subcooling. Steam pressure: 30 mbar. Playback: 240× (MP4)

Left: Steam condensation on a superhydrophobic aluminium surface. Right: real-time heat transfer

coefficient and subcooling. Steam pressure: 30 mbar. Playback: 240× (MP4)

Left: Steam condensation on PDMS brushes coated copper surface. Right: real-time heat transfer coefficient and subcooling. Steam pressure: 30 mbar. Playback: 240× (MP4)

Steam condensation on PDMS brushes coated copper surface. Steam pressure: 1.4 bar. Playback: 0.1× (MP4)

Cleaning process of PDMS brushes coated copper plate being contaminated with chalk powder (AVI)

Cleaning process of PDMS brushes coated copper plate being contaminated with chili sauce (AVI)

■ AUTHOR INFORMATION

Corresponding Authors

Dimos Poulikakos – Department of Mechanical and Process Engineering, Laboratory of Thermodynamics in Emerging Technologies, ETH Zurich, 8092 Zurich, Switzerland; orcid.org/0000-0001-5733-6478; Email: dpoulikakos@ethz.ch

Michael Kappl – Max Planck Institute for Polymer Research, 55128 Mainz, Germany; orcid.org/0000-0001-7335-1707; Email: kappl@mpip-mainz.mpg.de

Authors

Shuai Li – Max Planck Institute for Polymer Research, 55128 Mainz, Germany; orcid.org/0009-0006-5656-4755

Cheuk Wing Edmond Lam – Department of Mechanical and Process Engineering, Laboratory of Thermodynamics in Emerging Technologies, ETH Zurich, 8092 Zurich, Switzerland; Present Address: Massachusetts Institute of Technology, Cambridge, Massachusetts 02139, United States; orcid.org/0000-0002-8782-8438

Matteo Donati – Department of Mechanical and Process Engineering, Laboratory of Thermodynamics in Emerging Technologies, ETH Zurich, 8092 Zurich, Switzerland; orcid.org/0000-0003-0197-0159

Kartik Regulagadda – Department of Mechanical and Process Engineering, Laboratory of Thermodynamics in Emerging Technologies, ETH Zurich, 8092 Zurich, Switzerland; orcid.org/0000-0002-5787-9234

Emre Yavuz – Max Planck Institute for Polymer Research, 55128 Mainz, Germany

Till Pfeiffer – Institute for Technical Thermodynamics, Technical University of Darmstadt, 64287 Darmstadt, Germany

Panagiotis Sarkiris – Institute of Nanoscience and Nanotechnology, NCSR “Demokritos”, 15341 Agia Paraskevi, Attiki, Greece

Evangelos Gogolides – Institute of Nanoscience and Nanotechnology, NCSR “Demokritos”, 15341 Agia Paraskevi, Attiki, Greece; orcid.org/0000-0002-1870-5629

Athanasios Milionis – Department of Mechanical and Process Engineering, Laboratory of Thermodynamics in Emerging Technologies, ETH Zurich, 8092 Zurich, Switzerland

Hans-Jürgen Butt – Max Planck Institute for Polymer Research, 55128 Mainz, Germany; orcid.org/0000-0001-5391-2618

Complete contact information is available at: <https://pubs.acs.org/doi/10.1021/acsami.3c17293>

Author Contributions

S.L., A.M., T.P., D.P., H.-J.B., and M.K. designed the research and experiments. S.L. and A.M. prepared the surface. S.L. carried out the experiments and characterization unless otherwise stated below. C.W.E.L. conducted the ESEM measurements. C.W.E.L., M.D., and K.R. conducted the condensation heat transfer measurements. P.S. and E.G. prepared the superhydrophobic surface for reference. S.L. and E.Y. conducted the antifouling measurements. S.L., C.W.E.L., M.D., K.R., E.Y., P.S., E.G., A.M., D.P., M.K., and H.-J.B. wrote the manuscript. All authors have given approval to the final version of the manuscript.

Funding

Open access funded by Max Planck Society.

Notes

The authors declare no competing financial interest.

ACKNOWLEDGMENTS

This project has received funding from the European Research Council (ERC) under the European Union's Horizon 2020 research and innovation programme (HARMoNIC, grant number 801229; Advanced grant DyanMo, No 883631). Shuai Li thanks the China Scholarship Council (CSC) for the financial support. Till Pfeiffer acknowledges the financial support by the German Research Foundation - Project number 265191195—SFB 1194; subproject C03.

REFERENCES

- (1) Zheng, Y.; Bai, H.; Huang, Z.; Tian, X.; Nie, F.-Q.; Zhao, Y.; Zhai, J.; Jiang, L. Directional Water Collection on Wetted Spider Silk. *Nature* **2010**, *463* (7281), 640–643.
- (2) Haechler, I.; Ferru, N.; Schnoering, G.; Mitridis, E.; Schutzius, T. M.; Poulikakos, D. Transparent Sunlight-Activated Antifogging Metamaterials. *Nat. Nanotechnol.* **2023**, *18*, 137.
- (3) Hou, Y.; Yu, M.; Chen, X. W.; Zuankai; Yao, S. Recurrent Filmwise and Dropwise Condensation on a Beetle Mimetic Surface. *ACS Nano* **2015**, *9* (1), 71–87.
- (4) Cho, H. J.; Preston, D. J.; Zhu, Y.; Wang, E. N. Nanoengineered Materials for Liquid–Vapour Phase-Change Heat Transfer. *Nat. Rev. Mater.* **2017**, *2* (2), 16092.
- (5) Donati, M.; Lam, C. W. E.; Milionis, A.; Sharma, C. S.; Tripathy, A.; Zendeli, A.; Poulikakos, D. Sprayable Thin and Robust Carbon Nanofiber Composite Coating for Extreme Jumping Dropwise Condensation Performance. *Adv. Mater. Interfaces* **2021**, *8* (1), No. 2001176.
- (6) Wang, X.; Zeng, J.; Li, J.; Yu, X.; Wang, Z.; Zhang, Y. Beetle and Cactus-Inspired Surface Endows Continuous and Directional Droplet Jumping for Efficient Water Harvesting. *J. Mater. Chem. A* **2021**, *9* (3), 1507–1516.
- (7) Dai, X. M.; Sun, N.; Nielsen, S. O.; Stogin, B. B.; Wang, J.; Yang, S. K.; Wong, T. S. Hydrophilic Directional Slippery Rough Surfaces for Water Harvesting. *Sci. Adv.* **2018**, *4* (3), No. eaaq0919. ARTN eaaq0919
- (8) Guo, Y.; Guan, W.; Lei, C.; Lu, H.; Shi, W.; Yu, G. Scalable Super Hygroscopic Polymer Films for Sustainable Moisture Harvesting in Arid Environments. *Nat. Commun.* **2022**, *13* (1), 2761.
- (9) Briggs, A.; Rose, J. Effect of Fin Efficiency on a Model for Condensation Heat Transfer on a Horizontal, Integral-Fin Tube. *Int. J. Heat Mass Transfer* **1994**, *37*, 457–463.
- (10) Browne, M.; Bansal, P. An Overview of Condensation Heat Transfer on Horizontal Tube Bundles. *Appl. Therm. Eng.* **1999**, *19* (6), 565–594.
- (11) Marto, P. J.; Looney, D. J.; Rose, J. W.; Wanniarachchi, A. S. Evaluation of Organic Coatings for the Promotion of Dropwise Condensation of Steam. *Int. J. Heat Mass Transfer* **1986**, *29* (8), 1109–1117.
- (12) Holden, K.; Wanniarachchi, A.; Marto, P.; Boone, D.; Rose, J. The Use of Organic Coatings to Promote Dropwise Condensation of Steam. *J. Heat Transfer-Trans. ASME* **1987**, *109* (3), 768–774.
- (13) Vemuri, S.; Kim, K.; Wood, B.; Govindaraju, S.; Bell, T. Long Term Testing for Dropwise Condensation Using Self-Assembled Monolayer Coatings of N-Octadecyl Mercaptan. *Appl. Therm. Eng.* **2006**, *26* (4), 421–429.
- (14) Schmidt, E.; Schurig, W.; Sellschopp, W. Versuche Über Die Kondensation von Wasserdampf in Film-und Tropfenform. *Technol. Mech. Thermodyn.* **1930**, *1* (2), 53–63.
- (15) Rose, J. W. Dropwise Condensation Theory and Experiment: A Review. *Proc. Inst. Mech. Eng. A: J. Power Energy* **2002**, *216* (2), 115–128.
- (16) Huang, C.; Qian, X.; Yang, R. Thermal Conductivity of Polymers and Polymer Nanocomposites. *Mater. Sci. Eng. R Rep.* **2018**, *132*, 1–22.
- (17) Miljkovic, N.; Enright, R.; Nam, Y.; Lopez, K.; Dou, N.; Sack, J.; Wang, E. N. Jumping-Droplet-Enhanced Condensation on Scalable Superhydrophobic Nanostructured Surfaces. *Nano Lett.* **2013**, *13* (1), 179–187.
- (18) Wen, R.; Xu, S.; Ma, X.; Lee, Y.-C.; Yang, R. Three-Dimensional Superhydrophobic Nanowire Networks for Enhancing Condensation Heat Transfer. *Joule* **2018**, *2* (2), 269–279.
- (19) Wang, D.; Sun, Q.; Hokkanen, M. J.; Zhang, C.; Lin, F. Y.; Liu, Q.; Zhu, S. P.; Zhou, T.; Chang, Q.; He, B.; et al. Design of Robust Superhydrophobic Surfaces. *Nature* **2020**, *582* (7810), 55–59.
- (20) Geyer, F.; D'Acunzi, M.; Sharifi-Aghili, A.; Saal, A.; Gao, N.; Kaltbeitzel, A.; Sloot, T. F.; Berger, R.; Butt, H. J.; Vollmer, D. When and How Self-Cleaning of Superhydrophobic Surfaces Works. *Sci. Adv.* **2020**, *6* (3), No. eaaw9727.
- (21) Wong, T. S.; Kang, S. H.; Tang, S. K.; Smythe, E. J.; Hatton, B. D.; Grinthal, A.; Aizenberg, J. Bioinspired Self-Repairing Slippery Surfaces with Pressure-Stable Omniphobicity. *Nature* **2011**, *477* (7365), 443–447.
- (22) Quéré, D. Non-Sticking Drops. *Rep. Prog. Phys.* **2005**, *68* (11), 2495–2532.
- (23) Smith, J. D.; Dhiman, R.; Anand, S.; Reza-Garduno, E.; Cohen, R. E.; McKinley, G. H.; Varanasi, K. K. Droplet Mobility on Lubricant-Impregnated Surfaces. *Soft Matter* **2013**, *9* (6), 1772–1780.
- (24) Guo, Z.; Boylan, D.; Shan, L.; Dai, X. Hydrophilic Reentrant Slips Enabled Flow Separation for Rapid Water Harvesting. *Proc. Natl. Acad. Sci. U. S. A.* **2022**, *119* (36), No. e2209662119.
- (25) Guo, Z.; Monga, D.; Shan, L.; Boylan, D.; Dai, X. Coarsening-Induced Disappearing Droplets Contribute to Condensation. *Droplet* **2022**, *1* (2), 170–181.
- (26) Tripathy, A.; Lam, C. W. E.; Davila, D.; Donati, M.; Milionis, A.; Sharma, C. S.; Poulikakos, D. Ultrathin Lubricant-Infused Vertical Graphene Nanoscaffolds for High-Performance Dropwise Condensation. *ACS Nano* **2021**, *15* (9), 14305–14315.
- (27) Khalil, K.; Soto, D.; Farnham, T.; Paxson, A.; Katmis, A. U.; Gleason, K.; Varanasi, K. K. Grafted Nanofilms Promote Dropwise Condensation of Low-Surface-Tension Fluids for High-Performance Heat Exchangers. *Joule* **2019**, *3* (5), 1377–1388.
- (28) Hou, Y.; Yu, M.; Shang, Y.; Zhou, P.; Song, R.; Xu, X.; Chen, X.; Wang, Z.; Yao, S. Suppressing Ice Nucleation of Supercooled Condensate with Bipilic Topography. *Phys. Rev. Lett.* **2018**, *120* (7), No. 075902.
- (29) Teisala, H.; Baumli, P.; Weber, S. A. L.; Vollmer, D.; Butt, H. J. Grafting Silicone at Room Temperature-A Transparent, Scratch-Resistant Nonstick Molecular Coating. *Langmuir* **2020**, *36* (16), 4416–4431.
- (30) Li, S.; Hou, Y.; Kappl, M.; Steffen, W.; Liu, J.; Butt, H. J. Vapor Lubrication for Reducing Water and Ice Adhesion on Poly-(Dimethylsiloxane) Brushes. *Adv. Mater.* **2022**, *34* (34), No. 2203242.
- (31) Zhao, X.; Khandoker, M. A. R.; Golovin, K. Non-Fluorinated Omniphobic Paper with Ultralow Contact Angle Hysteresis. *ACS Appl. Mater. Interfaces* **2020**, *12* (13), 15748–15756.
- (32) Khatir, B.; Shabani, S.; Golovin, K. Design and High-Resolution Characterization of Silicon Wafer-Like Omniphobic

Liquid Layers Applicable to Any Substrate. *ACS Appl. Mater. Interfaces* **2020**, *12* (28), 31933–31939.

(33) Monga, D.; Guo, Z.; Shan, L.; Taba, S. A.; Sarma, J.; Dai, X. Quasi-Liquid Surfaces for Sustainable High-Performance Steam Condensation. *ACS Appl. Mater. Interfaces* **2022**, *14* (11), 13932–13941.

(34) Li, S.; Diaz, D.; Kappl, M.; Butt, H.-J.; Liu, J.; Hou, Y. Enhanced Condensation Heat Transfer by Water/Ethanol Binary Liquids on Polydimethylsiloxane Brushes. *Droplet* **2022**, *1* (2), 214–222.

(35) Fazle Rabbi, K.; Ho, J. Y.; Yan, X.; Ma, J.; Hoque, M. J.; Sett, S.; Miljkovic, N. Polydimethylsiloxane-Silane Synergy Enables Dropwise Condensation of Low Surface Tension Liquids. *Adv. Funct. Mater.* **2022**, *32* (19), No. 2112837.

(36) Li, S.; Bista, P.; Weber, S. A. L.; Kappl, M.; Butt, H.-J. Spontaneous Charging of Drops on Lubricant-Infused Surfaces. *Langmuir* **2022**, *38* (41), 12610–12616.

(37) Tian, X.; Verho, T.; Ras, R. H. A. Moving Superhydrophobic Surfaces toward Real-World Applications. *Science* **2016**, *352* (6282), 142–143.

(38) Bormashenko, E. Y. *Wetting of Real Surfaces*; De Gruyter, 2013.

(39) Cassie, A. Contact angles. *Discuss. Faraday Soc.* **1948**, *3*, 11–16.

(40) Cassie, A. B. D.; Baxter, S. Wettability of Porous Surfaces. *Trans. Faraday Soc.* **1944**, *40*, 546–551. DOI: 10.1039/TF9444000546

(41) Wenzel, R. N. Surface Roughness and Contact Angle. *J. Phys. Colloid Chem.* **1949**, *53* (9), 1466–1467.

(42) Enright, R.; Miljkovic, N.; Al-Obeidi, A.; Thompson, C. V.; Wang, E. N. Condensation on Superhydrophobic Surfaces: the Role of Local Energy Barriers and Structure Length Scale. *Langmuir* **2012**, *28* (40), 14424–144232.

(43) Wen, R.; Lan, Z.; Peng, B.; Xu, W.; Yang, R.; Ma, X. Wetting Transition of Condensed Droplets on Nanostructured Superhydrophobic Surfaces: Coordination of Surface Properties and Condensing Conditions. *ACS Appl. Mater. Interfaces* **2017**, *9* (15), 13770–13777.

(44) Baumli, P.; D'Acunzi, M.; Hegner, K. I.; Naga, A.; Wong, W. S. Y.; Butt, H. J.; Vollmer, D. The Challenge of Lubricant-Replenishment on Lubricant-Impregnated Surfaces. *Adv. Colloid Interface Sci.* **2021**, *287*, No. 102329.

(45) Vishwakarma, V. Impact of Environmental Biofilms: Industrial Components and its Remediation. *J. Basic Microbiol.* **2020**, *60* (3), 198–206.

(46) Michels, H.; Kirk, W.; Tuthill, A. The Influence of Corrosion and Fouling on Steam Condenser Performance. *J. Mater. Energy Syst.* **1979**, *1* (3), 14–33.

(47) Bott, T. R. *Fouling of Heat Exchangers*; Elsevier, 1995.

(48) Tang, Y.; Yang, X.; Li, Y.; Lu, Y.; Zhu, D. Robust Micro-Nanostructured Superhydrophobic Surfaces for Long-Term Dropwise Condensation. *Nano Lett.* **2021**, *21* (22), 9824–9833.

(49) Ghosh, R.; Ray, T. K.; Ganguly, R. Cooling Tower fog Harvesting in Power Plants – A Pilot Study. *Energy* **2015**, *89*, 1018–1028.

(50) Wang, Y.; Gao, S.; Xu, W.; Wang, Z. NANOGENERATORS with Superwetting Surfaces for Harvesting Water/Liquid Energy. *Adv. Funct. Mater.* **2020**, *30* (26), No. 1908252.

(51) Suja, F.; Pramanik, B. K.; Zain, S. M. Contamination, Bioaccumulation and Toxic Effects of Perfluorinated Chemicals (PFCs) in the Water Environment: A Review Paper. *Water Sci. Technol.* **2009**, *60* (6), 1533–1544.

(52) Krumpfer, J. W.; McCarthy, T. J. Contact Angle Hysteresis: A Different View and a Trivial Recipe for Low Hysteresis Hydrophobic Surfaces. *Faraday Discuss.* **2010**, *146* (0), 103–111. DOI: 10.1039/B925045J.

(53) Krumpfer, J. W.; McCarthy, T. J. Rediscovering Silicones: “Unreactive” Silicones React with Inorganic Surfaces. *Langmuir* **2011**, *27* (18), 11514–11519.

(54) Milner, S. T. Polymer brushes. *Science* **1991**, *251* (4996), 905–914.

(55) Milner, S. T.; Witten, T. A.; Cates, M. E. Theory of the Grafted Polymer Brush. *Macromolecules* **1988**, *21* (8), 2610–2619.

(56) Eifert, A.; Paulssen, D.; Varanakkottu, S. N.; Baier, T.; Hardt, S. Simple Fabrication of Robust Water-Repellent Surfaces with Low Contact-Angle Hysteresis Based on Impregnation. *Adv. Mater. Interfaces* **2014**, *1* (3), No. 1300138.

(57) Hiemstra, T.; Van Riemsdijk, W. Multiple activated complex dissolution of metal (hydr) oxides: A Thermodynamic Approach Applied to Quartz. *J. Colloid Interface Sci.* **1990**, *136* (1), 132–150.

(58) Kugel, A.; Staflien, S.; Chisholm, B. J. Antimicrobial Coatings Produced by “Tethering” Biocides to the Coating Matrix: A Comprehensive Review. *Prog. Org. Coat.* **2011**, *72* (3), 222–252.

(59) Guo, Z.; Zhang, L.; Monga, D.; Stone, H. A.; Dai, X. Hydrophilic Slippery Surface Enabled Coarsening Effect for Rapid Water Harvesting. *Cell Rep. Phys. Sci.* **2021**, *2* (4), No. 100387.

(60) Sofia, S. J.; Premnath, V.; Merrill, E. W. Poly(ethylene oxide) Grafted to Silicon Surfaces: Grafting Density and Protein Adsorption. *Macromolecules* **1998**, *31* (15), 5059–5070.

(61) Deng, X.; Mammen, L.; Butt, H. J.; Vollmer, D. Candle Soot as a Template for a Transparent Robust Superamphiphobic Coating. *Science* **2012**, *335* (6064), 67–70.

(62) Lafuma, A.; Quéré, D. Superhydrophobic States. *Nat. Mater.* **2003**, *2* (7), 457–460.

(63) Papadopoulos, P.; Mammen, L.; Deng, X.; Vollmer, D.; Butt, H. J. How Superhydrophobicity Breaks Down. *Proc. Natl. Acad. Sci. U. S. A.* **2013**, *110* (9), 3254–3258.

(64) Li, X.; Bista, P.; Stetten, A. Z.; Bonart, H.; Schür, M. T.; Hardt, S.; Bodziony, F.; Marschall, H.; Saal, A.; Deng, X.; et al. Spontaneous Charging Affects the Motion of Sliding Drops. *Nat. Phys.* **2022**, *18* (6), 713–719.

(65) Dussan, E. On The Spreading of Liquids on Solid Surfaces: Static and Dynamic Contact Lines. *Annu. Rev. Fluid Mech.* **1979**, *11* (1), 371–400.

(66) Sarkiris, P.; Constantoudis, V.; Ellinas, K.; Lam, C. W. E.; Milionis, A.; Anagnostopoulos, J.; Poulikakos, D. A.; Gogolides, E. Topography Optimization for Sustainable Dropwise Condensation: The Critical Role of Correlation Length. *Adv. Funct. Mater.* **2023**, No. 2306756.

(67) Ma, J.; Sett, S.; Cha, H.; Yan, X.; Miljkovic, N. Recent Developments, Challenges, and Pathways to Stable Dropwise Condensation: A Perspective. *Appl. Phys. Lett.* **2020**, *116* (26), 260501.

(68) Béer, J. M. High efficiency electric power generation: The Environmental Role. *Prog. Energy Combust. Sci.* **2007**, *33* (2), 107–134.

(69) Yang, J. C.; Kolasa, B.; Gibson, J. M.; Yeadon, M. Self-Limiting Oxidation of Copper. *Appl. Phys. Lett.* **1998**, *73* (19), 2841–2843.

(70) Shan, L.; Guo, Z.; Monga, D.; Boylan, D.; Dai, X. Microchannel-Elevated Micromembrane for Sustainable Phase-Separation Condensation. *Joule* **2023**, *7* (1), 168–182.