

# UC Berkeley

## UC Berkeley Previously Published Works

### Title

Supramolecular assembly of blue and green halide perovskites with near-unity photoluminescence

### Permalink

<https://escholarship.org/uc/item/4t59495x>

### Journal

Science, 383(6678)

### ISSN

0036-8075

### Authors

Zhu, Cheng

Jin, Jianbo

Wang, Zhen

et al.

### Publication Date

2024-01-05

### DOI

10.1126/science.adi4196

Peer reviewed

# Supramolecular assembly of blue and green halide perovskites with near-unity photoluminescence

Cheng Zhu<sup>1,4,5‡</sup>, Jianbo Jin<sup>2‡</sup>, Zhen Wang<sup>1</sup>, Zhenpeng Xu<sup>1</sup>, Maria C. Folgueras<sup>1,4,5</sup>, Yuxin Jiang<sup>2,4</sup>, Can B. Uzundal<sup>2,4</sup>, Han K.D. Le<sup>2,4</sup>, Feng Wang<sup>3,4,5</sup>, Xiaoyu (Rayne) Zheng<sup>1</sup>, and Peidong Yang<sup>1,2,4,5\*</sup>

1 Department of Materials Science and Engineering, University of California, Berkeley, Berkeley, California 94720, United States

2 Department of Chemistry, University of California, Berkeley, Berkeley, California 94720, United States

3 Department of Physics, University of California, Berkeley, Berkeley, California 94720, United States

4 Materials Sciences Division, Lawrence Berkeley National Laboratory, Berkeley, California 94720, United States

5 Kavli Energy NanoScience Institute, Berkeley, California 94720, United States

‡ These authors contributed equally

\* Corresponding author. E-mail: p\_yang@berkeley.edu (P.Y.)

**One Sentence Summary:**

A crown ether-assisted assembly of  $[\text{Hf/ZrBr}_6]^{2-}$  emitting units enables near-unity blue and green emissions.

**Abstract:**

The metal-halide ionic octahedron is the optoelectronic unit for halide perovskites, and crown ether-assisted supramolecular assembly approach can pack various ionic octahedra into tunable symmetries. We demonstrate that near-unity photoluminescence quantum yield (PLQY) blue and green emission with the supramolecular assembly of Hf and Zr halide octahedral clusters.  $(18\text{C}6@K)_2\text{HfBr}_6$  powders showed blue emission with a near-unity PLQY (96.2%), and green emission was also achieved with  $(18\text{C}6@K)_2\text{ZrCl}_4\text{Br}_2$  powders at a PLQY of 82.7%. These highly emissive powders feature facile low-temperature solution-based synthesis conditions and maintain high PLQY in solution-processable semiconductor inks under ambient conditions and were used in thin-film displays and emissive 3D printed architectures that exhibited high spatial resolution.

## Main Text:

Blue and green emission with high photoluminescence quantum yield (PLQY) is at the forefront of solid-state lighting and color display research. Although Si and Zn co-doped GaN can exhibit a PLQY of 90% (1), these covalent semiconductors require high purity to prevent rapid nonradiative recombination at crystal structure defects (2-5) and rely on solid-state synthesis at elevated temperatures near 1000 °C (6). As an alternative to covalent semiconductors, ionic halide perovskites have received attention given their high optical absorption coefficient (7), tunable bandgap (8-10), high defect tolerance (11, 12), and efficient photo/electroluminescence (13, 14). For example, the blue and green emissive colloidal  $\text{CsPbCl}_x\text{Br}_{3-x}$  quantum dots have exhibited PLQY values  $\sim 80\%$  (15, 16). In addition, low-dimensional halide perovskites like the  $n = 1$  Ruddlesden-Popper phase  $(\text{C}_6\text{H}_5\text{CH}_2\text{NH}_3)_2\text{PbBr}_4$  show blue emission with a PLQY of 79% (17). Despite the remarkable optoelectronic properties of lead-based halide perovskites, the toxicity of lead and the complex colloidal synthesis complicate large-scale applications. Moreover, suitable ligands are still needed to prevent aggregation of these low-dimensional nanostructures during use (18).

Recent studies have revealed that the optoelectronic properties of halide perovskites stem from the  $[\text{MX}_6]^{n-}$  ( $\text{M} = \text{metal cation}$ ,  $\text{X} = \text{halide anion}$ ) fundamental building blocks in the crystal structure (19-21) and given the ionic nature and high chemical tunability of halide perovskite structures (22), different compositions and packing geometries of  $[\text{MX}_6]^{n-}$  could be explored for light-emission applications. The vacancy-ordered double perovskite ( $\text{A}_2\text{MX}_6$  phase) has been proposed to incorporate tetravalent metal cation octahedra, such as  $[\text{TeX}_6]^{2-}$  (23-25),  $[\text{SnX}_6]^{2-}$  (26, 27), and  $[\text{PtX}_6]^{2-}$  (28, 29). Although the  $[\text{PbX}_6]^{4-}$  octahedra are corner-shared in all three dimensions in the prototypical  $\text{CsPbX}_3$  structure (30), the  $[\text{MX}_6]^{2-}$  octahedra in the  $\text{A}_2\text{MX}_6$  phase are isolated because a vacancy occupies every other M-site in the crystal structure (23). A few  $[\text{MX}_6]^{n-}$  emitters as well as some non-octahedral emitters (31) with high PLQY ( $\sim 95\%$ ) have been identified with yellow emission, such as  $[\text{SnX}_6]^{4+}$  (32). However, emission of high PLQY with shorter wavelengths is still very rare. The isolated nature of the octahedra affects their optoelectronic properties, in that the strong coupling of the exciton with lattice vibrations greatly lowers the energy level of the exciton and forces it into transient self-trapped exciton (STE) states with a range of self-trapped energy levels (33, 34). As a result, the  $\text{A}_2\text{MX}_6$  systems generally have broadband emission with a large Stokes shift.

Although the  $\text{A}_2\text{MX}_6$  phase has been widely studied in various compositions, octahedra with  $\text{Hf}^{4+}/\text{Zr}^{4+}$  centers, especially  $[\text{HfBr}_6]^{2-}$  and  $[\text{ZrBr}_6]^{2-}$  octahedra, have rarely been the subject of research (35, 36), even though they have interesting optoelectronic properties.  $\text{Cs}_2\text{HfBr}_6$  crystals have a blue emission with the PL peak at 435 nm (35), and colloidal  $\text{Cs}_2\text{ZrBr}_6$  nanocrystals have been demonstrated to have a green emission with a PLQY of 45% (36). There are several reasons why they are less explored. Theoretical (37) and experimental studies (38) have shown that the  $\text{Hf}^{4+}$  and  $\text{Zr}^{4+}$  metal centers are extremely air- and moisture-sensitive in the  $\text{A}_2\text{MX}_6$  phase. Their synthesis requires the vertical Bridgman-Stockbarger method at  $\sim 1000^\circ\text{C}$  in sealed quartz ampoules (36, 39, 40). Finally, it is difficult to prepare high-purity samples that do not contain a secondary impurity such as  $\text{CsBr}$  (36). Thus, a new methodology is needed for the synthesis of more stabilized and purer solid phases containing the  $[\text{Hf}/\text{ZrBr}_6]^{2-}$  octahedra.

Recently, we proposed a general crown ether-assisted supramolecular assembly approach for tetravalent metal octahedra (41). Two crown ether@alkali metal complexes can sandwich a tetravalent metal octahedron into a (crown ether@A) $_2\text{MX}_6$  dumbbell structural unit. The composition of the dumbbell structural unit is highly tunable, with crown ether = 18-Crown-6 (18C6), 21-Crown-7 (21C7);  $\text{A} = \text{Cs}^+$ ,  $\text{Rb}^+$ ,  $\text{K}^+$ ;  $\text{M} = \text{Te}^{4+}$ ,  $\text{Sn}^{4+}$ ,  $\text{Se}^{4+}$ ,  $\text{Ir}^{4+}$ ,  $\text{Pt}^{4+}$ ,  $\text{Zr}^{4+}$ ,  $\text{Hf}^{4+}$ ,  $\text{Ce}^{4+}$ ;  $\text{X} = \text{Cl}^-$ ,  $\text{Br}^-$ ,  $\text{I}^-$ . In this work, we extended this general supramolecular assembly approach to  $[\text{HfBr}_6]^{2-}$  octahedra to achieve a structure with formula  $(18\text{C6}@\text{K})_2\text{HfBr}_6$  that features blue emission with near-unity (96.2%) PLQY. We also optimized the synthetic route by replacing the challenging high-temperature solid-state synthesis with a low-temperature

organic solution-based synthesis. Moreover, an efficient green emission was also achieved by tuning the composition of the (crown ether@A)<sub>2</sub>MX<sub>6</sub> dumbbell structural unit. (18C6@K)<sub>2</sub>ZrCl<sub>4</sub>Br<sub>2</sub> demonstrated green emission with 82.7% PLQY. By studying the photophysics of the supramolecular assembled samples, we could attribute the emission to self-trapped excitonic (STE) states and observed very strong electron-phonon coupling constant (represented by the Huang-Rhys parameter) > 90 for (18C6@K)<sub>2</sub>HfBr<sub>6</sub>. The supramolecular assembled samples had longer PL lifetimes (in the microsecond timescale) compared to other halide perovskite systems that reflected a low rate of nonradiative recombination.

The structural integrity and impressive optical properties of the supramolecular assembled solid powders were further maintained by generating a powder suspension in nonpolar organic solvents such as dichloromethane (DCM) to create an ink system. Polystyrene (PS) polymer was dissolved into the ink to further increase the solution processability. We used these inks to fabricate thin films through fast solvent evaporation. In combination with a digitally-controlled excitation source, the (18C6@K)<sub>2</sub>HfBr<sub>6</sub>/PS composite thin film could be used as a display with bright color contrast and fast response time. A solution-processable ink also allowed three-dimensional (3D) printing of the powders into various blue, green, and dual-color emitting structures.

### Crown Ether Assisted Supramolecular Assembly

We explored a supramolecular synthetic route in which 18C6 greatly increased the solubility of the KBr and HfBr<sub>4</sub> precursors in polar organic solvents for low-temperature solution-based synthesis. A clear precursor solution was obtained with acetonitrile (ACN) at 80°C with the concentration of 4 mM for 18C6 and KBr and 2 mM for HfBr<sub>4</sub>. Our previous study of the supramolecular assembly of tetravalent metal octahedra (41) indicated that a (18C6@K)<sub>2</sub>HfBr<sub>6</sub> dumbbell structural unit was formed in ACN. We grew (18C6@K)<sub>2</sub>HfBr<sub>6</sub> powders and single crystals using the anti-solvent crystallization method (39). K<sub>2</sub>HfBr<sub>6</sub> powders were also synthesized by using a modified solid-state synthesis method. We increased the purity and decreased the synthesis temperature to 200°C by combining mechanical forces with heat to facilitate solid-state diffusion. Details of the synthesis for (18C6@K)<sub>2</sub>HfBr<sub>6</sub> and K<sub>2</sub>HfBr<sub>6</sub> can be found in the Supplementary Materials.

The crystal structure of (18C6@K)<sub>2</sub>HfBr<sub>6</sub> was determined from single-crystal x-ray diffraction (SCXRD). (18C6@K)<sub>2</sub>HfBr<sub>6</sub> crystallized in the R3- [note this is 3 with an overbar] space group with lattice parameters of  $a = 14.1332 \text{ \AA}$  and  $c = 21.0189 \text{ \AA}$  (Fig. 1A and table S1). The (18C6@K)<sub>2</sub>HfBr<sub>6</sub> dumbbell structural unit belongs to the  $S_6$  point group, where two K<sup>+</sup> cations and the Hf<sup>4+</sup> cation sit on the  $S_6$  axis. The sixfold symmetry axis of the 18C6 and the  $S_6$  axis of O<sub>h</sub>-symmetric [HfBr<sub>6</sub>]<sup>2-</sup> octahedron were aligned (Fig. 1B). The K<sub>2</sub>HfBr<sub>6</sub> crystals were face-centered cubic (fcc) (Fig. 1C) (42, 43) in which the [HfBr<sub>6</sub>]<sup>2-</sup> ionic octahedra were charge balanced by the surrounding K<sup>+</sup> cations (Fig. 1D).

The purity of the (18C6@K)<sub>2</sub>HfBr<sub>6</sub> and K<sub>2</sub>HfBr<sub>6</sub> powders was investigated with powder x-ray diffraction (PXRD) (Fig. 1E). The PXRD pattern of the (18C6@K)<sub>2</sub>HfBr<sub>6</sub> powders matched with the calculated pattern generated from the single crystal structure with no visible diffraction peaks from impurities. The quality of the PXRD pattern for the K<sub>2</sub>HfBr<sub>6</sub> powders was much lower because of their extreme air sensitivity. The measurement had to be collected in 5 min with an inert atmosphere sample holder to prevent the degradation of the powders and measurement of the degradation product. Although the quality of the K<sub>2</sub>HfBr<sub>6</sub> PXRD pattern was not ideal, the most dominant peaks of the fcc K<sub>2</sub>HfBr<sub>6</sub> phase were still identifiable. Moreover, no HfBr<sub>4</sub> or KBr diffraction peaks were present (Fig. 1E), which showed that all the precursor materials transformed into the K<sub>2</sub>HfBr<sub>6</sub> phase. Raman spectrum of K<sub>2</sub>HfBr<sub>6</sub> further confirmed the presence of the [HfBr<sub>6</sub>]<sup>2-</sup> octahedra in the crystal structure (fig. S1).

The crown ether-assisted supramolecular approach was generalized to produce other emissive centers. For example, (18C6@K)<sub>2</sub>ZrBr<sub>6</sub> single crystals and powders were successfully synthesized by the same method, and the same crystal structure as (18C6@K)<sub>2</sub>HfBr<sub>6</sub> was obtained (fig. S2 and table S1). Figure S3 shows

that phase pure  $(18C6@K)_2ZrBr_6$  powders could be obtained with our established solution-based synthesis.  $K_2ZrBr_6$  powders were also synthesized with the same solid-state method as  $K_2HfBr_6$ .

The  $(18C6@K)_2Hf/ZrBr_6$  dumbbell building blocks were also the electronic units of the new crystal. To elucidate the effect of 18C6 on the electronic structures of the assembled  $[HfBr_6]^{2-}$  octahedra, density functional theory (DFT) calculations were performed on  $(18C6@K)_2HfBr_6$  (Fig. 1F) and  $K_2HfBr_6$  (Fig. 1G) to determine their electronic band structures and partial electronic density of states (pDOS). The electronic bands of  $(18C6@K)_2HfBr_6$  were less dispersive compared to  $K_2HfBr_6$  because the  $[HfBr_6]^{2-}$  octahedra were more separated in  $(18C6@K)_2HfBr_6$ . The conduction band (CB) of  $(18C6@K)_2HfBr_6$  was composed of Hf 5d and Br 4p orbitals, as was the CB of  $K_2HfBr_6$ . However, the valence band (VB) compositions were quite different in these two materials. The VB of  $K_2HfBr_6$  was mainly composed of the Br 4p orbital, but 18C6 contributed to the VB of  $(18C6@K)_2HfBr_6$ . Thus, the 18C6 molecules were electronically coupled to the  $[HfBr_6]^{2-}$  octahedra, indicating that the entire  $(18C6@K)_2HfBr_6$  dumbbell building block became a new electronic unit. DFT calculations of  $(18C6@K)_2ZrBr_6$  showed that the contribution from 18C6 to the VB and that the band structures were more discrete than  $K_2ZrBr_6$  (fig. S4).

### Optical Characterization of the Blue and Green Emitters

Compared to  $K_2HfBr_6$ ,  $(18C6@K)_2HfBr_6$  had greatly enhanced emission intensity. Figure 2A shows the extremely bright blue emission of  $(18C6@K)_2HfBr_6$  powders under 254-nm ultraviolet (UV) excitation. The photoluminescence (PL) spectrum of  $(18C6@K)_2HfBr_6$  powders was measured at 275-nm excitation (Fig. 2B). The powders had a blue emission centered at 445 nm (2.79 eV), and the full-width at half-maximum (FWHM) was 0.73 eV. Photoluminescence excitation (PLE) spectra revealed a large Stokes shift (1.35 eV).

The emission intensity of the  $(18C6@K)_2HfBr_6$  powders was quantified with PLQY measurement, and a near-unity value of  $96.2 \pm 1.2\%$  was obtained for the  $(18C6@K)_2HfBr_6$  powders over 6 measurements from 2 batches of samples (fig. S5). The specific value for each measurement is shown in table S2. In contrast, the PLQY of  $K_2HfBr_6$  powders was 12.8% (fig. S6).  $K_2HfBr_6$  also had an even larger Stokes shift (1.42 eV) and broader emission, with a peak emission wavelength of 457 nm and an FWHM of 0.90 eV (fig. S7). The color purity of the emission from the  $[HfBr_6]^{2-}$  octahedra was also enhanced by the supramolecular approach. Figure S8 shows the emission color of  $(18C6@K)_2HfBr_6$  and  $K_2HfBr_6$  powders on the CIE 1931 chromaticity diagram.  $(18C6@K)_2HfBr_6$  had a much purer blue emission color than  $K_2HfBr_6$ .

The  $[ZrBr_6]^{2-}$  units enabled high-PLQY green emissions. Upon 290-nm excitation,  $(18C6@K)_2ZrBr_6$  had a PL peak at 547 nm, and the FWHM of the PL was 0.69 eV (fig. S9). For the same excitation wavelength, the PL peak of  $K_2ZrBr_6$  was at 560 nm, and the FWHM of the PL was 0.70 eV (fig. S10). The PLQY of  $(18C6@K)_2ZrBr_6$  was 49.8% (fig. S11), which was slightly greater than the PLQY of  $K_2ZrBr_6$  (46.3%) (fig. S12). Although the peak position of the PL spectrum was in the green region, simply analyzing the peak emission wavelength was insufficient given the broadness of the STE-based emission, as this crystal actually produced a yellow-green emission color (fig. S13).

Given the great chemical tunability of the dumbbell structural unit, an alloying approach at the halide site was proposed to achieve a purer green emission with near-unity PLQY emission. For  $CsPbX_3$  ( $X = Cl^-, Br^-, I^-$ ) nanocrystals, the emission color can be easily controlled by tuning the halide composition (44); introducing  $Cl^-$  in the halide site may generate a shorter wavelength emission color. By carefully tuning the  $KCl/KBr$  and  $ZrCl_4/ZrBr_4$  precursor ratio in the synthesis, the  $Cl^-/Br^-$  ratio in the obtained  $(18C6@K)_2ZrX_6$  dumbbell structural unit can be precisely controlled. As expected, a larger  $Cl^-/Br^-$  ratio created a more blue-shifted PL (figs. S14 and S15). For example,  $(18C6@K)_2ZrCl_3Br_3$  and  $(18C6@K)_2ZrCl_4Br_2$  had green emission with PL peaks at 534 nm and 530 nm, respectively. Increasing the  $Cl^-$  content to a composition of  $(18C6@K)_2ZrCl_{4.5}Br_{1.5}$  changed the PL color to the cyan (bluish-green) color. The established halide-site

alloying approach not only generated a purer green emission color, but also boosted the PLQY of the emission to near-unity. For the Cl<sup>-</sup>/Br<sup>-</sup> ratio from 1:1 to 2:1 to 3:1, the PLQYs were 69.1%, 82.7%, and 87.0%, respectively (figs. S16 and S17).

Because the 2:1 Cl<sup>-</sup>/Br<sup>-</sup> ratio composition had both pure-green emission color and high PLQY, we selected (18C6@K)<sub>2</sub>ZrCl<sub>4</sub>Br<sub>2</sub> for detailed studies of green emission. (18C6@K)<sub>2</sub>ZrCl<sub>4</sub>Br<sub>2</sub> single crystals were synthesized by controlling the Cl<sup>-</sup>/Br<sup>-</sup> precursor ratio to be 2:1. The formula of (18C6@K)<sub>2</sub>ZrCl<sub>4</sub>Br<sub>2</sub> was determined by SCXRD (Cl<sup>-</sup>:Br<sup>-</sup> = 4.3:1.7, fig. S18 and table S3) and energy-dispersive x-ray spectroscopy (EDX) elemental mapping (Cl<sup>-</sup>:Br<sup>-</sup> = 4.1:1.9) (fig. S19). The Cl and Br atoms were perfectly miscible in the crystal structure. PXRD of the (18C6@K)<sub>2</sub>ZrCl<sub>4</sub>Br<sub>2</sub> powders (fig. S20) also indicated that this composition was a phase-pure system. The (101) and (110) diffraction peaks of (18C6@K)<sub>2</sub>ZrCl<sub>4</sub>Br<sub>2</sub> were slightly shifted to larger 2θ values compared to the corresponding PXRD peaks of (18C6@K)<sub>2</sub>ZrBr<sub>6</sub>, suggesting smaller lattice constants (fig. S21).

Figure 2C shows the bright green emission of (18C6@K)<sub>2</sub>ZrCl<sub>4</sub>Br<sub>2</sub> powders under 302-nm UV lamp excitation. The PL spectrum of (18C6@K)<sub>2</sub>ZrCl<sub>4</sub>Br<sub>2</sub> powders was measured at 295-nm excitation (Fig. 2D). The green emission had a similar Stokes shift (1.36 eV versus 1.35 eV) and FWHM (0.80 eV versus 0.73 eV) to the blue emission of the (18C6@K)<sub>2</sub>HfBr<sub>6</sub> powders, suggesting similar emission properties of the Hf and Zr metal centers in the supramolecular assembly materials system. The PLQY of the emission from (18C6@K)<sub>2</sub>ZrCl<sub>4</sub>Br<sub>2</sub> powders was 82.7 ± 0.9%, which was determined through the measurement of 4 samples from 2 batches (table S4). Therefore, we achieved highly emissive powders with blue and green emission colors based on the supramolecular assembly approach. The blue and green colors of the emissions from (18C6@K)<sub>2</sub>HfBr<sub>6</sub> and (18C6@K)<sub>2</sub>ZrCl<sub>4</sub>Br<sub>2</sub>, respectively, are summarized in the CIE 1931 diagram (Fig. 2E).

Next, we conducted a comprehensive photophysics analysis to confirm and gain deeper insights into the STE emission mechanism that underlies these blue and green emissions. The distinctive features of STE emissions, including their large Stokes shift and broadband nature, are primarily attributed to the electron-phonon coupling effect. To unravel the STE emission mechanism, we performed low-temperature PL measurements to examine the electron-phonon coupling in (18C6@K)<sub>2</sub>HfBr<sub>6</sub>. With increasing temperatures, the PL peak gradually broadened, and the peak was slightly red-shifted, indicating greater phonon participation at higher temperatures (Fig. 3A). A small shoulder peak at ~ 550 nm was present that especially distinct at lower temperatures that we attribute to the Zr impurity in the HfBr<sub>4</sub> precursor (35). Inductively coupled atomic emission spectroscopy revealed a ~ 0.5 at% ZrBr<sub>4</sub> impurity in the as-obtained HfBr<sub>4</sub> precursor, and that there was ~ 0.6 at% Zr<sup>4+</sup> impurity in the synthesized (18C6@K)<sub>2</sub>HfBr<sub>6</sub> single crystals (table S5).

To deconvolve the emission from (18C6@K)<sub>2</sub>ZrBr<sub>6</sub> impurities, a two-peak Gaussian fitting was applied to the PL spectrum at each temperature. Figure S22 shows an example at 4 K. The FWHMs of the (18C6@K)<sub>2</sub>HfBr<sub>6</sub> peaks were obtained from the Gaussian fittings and summarized in table S6. The temperature dependence of the FWHM of the emission peak was modeled by using the theory of Toyozawa (45), which applies a configuration coordinate model to explain the broadening of the emission originating from electron-phonon coupling. The FWHM depends on the effective phonon energy  $E_{ph}$ , the temperature  $T$ , and the Huang-Rhys electron-phonon coupling parameter  $S$ : (46)

$$FWHM = 2.36\sqrt{S}E_{ph}\sqrt{\coth\frac{E_{ph}}{2k_B T}} \quad (1)$$

The relation between FWHM and temperature is shown in Figure 3B. Analyzing the data according to Eq. 1 yielded a coupling factor  $S_l = 92.2 \pm 3.6$  and an effective phonon energy  $E_{ph1} = 21.4 \pm 0.5$  meV. This phonon mode corresponded to the asymmetric stretching mode ( $E_g$ ) of the  $[\text{HfBr}_6]^{2-}$  octahedra, which was observed at 20.4 meV ( $164.5 \text{ cm}^{-1}$ ) in the Raman spectrum (fig. S23). However, this phonon mode was only responsible for STE formation up to 190 K. For temperatures  $> 190$  K, a higher energy phonon mode dominated STE formation.

Shifting the zero temperature of Eq. 1 by 190 K, a second fit could be obtained with a coupling factor  $S_2 = 108.8 \pm 12.4$  and an effective phonon energy  $E_{ph2} = 25.8 \pm 1.6$  meV. This phonon mode corresponded to the symmetric stretching mode ( $A_{1g}$ ) of the  $[\text{HfBr}_6]^{2-}$  octahedra at 25.1 meV ( $202.5 \text{ cm}^{-1}$ ). The large Huang-Rhys factor  $S$  in both scenarios indicated a very strong electron-phonon coupling in this material. For example,  $S$  for  $\text{CsPbX}_3$  ( $X = \text{Br}^-$  or  $\text{I}^-$ ) is  $< 1$  (47), and the  $S$  for double perovskite  $\text{Cs}_2\text{AgBiBr}_6$  is only  $\sim 12$  (48). Self-trapping exciton behavior is closely related to the octahedra packing dimensionality. Through our supramolecular approach, the  $[\text{HfBr}_6]^{2-}$  octahedra were more isolated by the bulky  $(18\text{C6@K})^+$  complexes, which led to stronger self-trapping with larger  $S$  values.

Excitation wavelength-dependent PL mapping of  $(18\text{C6@K})_2\text{HfBr}_6$  (Fig. 3C) showed that for excitation wavelengths  $< 285$  nm, a broad PL peak at 445 nm emerged. The PL peak position and shape were independent of the excitation wavelength  $< 285$  nm. Thus, for above bandgap excitation, the emission originated from the relaxation of the same excited state. However, for excitation wavelengths  $> 285$  nm, a much weaker PL peak at  $\sim 550$  nm replaced the previous PL peak that arose from the  $\sim 0.6$  at%  $(18\text{C6@K})_2\text{ZrBr}_6$  impurity, and 2D PLE mapping of  $(18\text{C6@K})_2\text{ZrBr}_6$  showed a single PL peak at  $\sim 550$  nm from 245-nm to 330-nm excitation (fig. S24).

Time-resolved PL (TRPL) studies on the supramolecular assembled single crystals revealed that the PL decay of the  $(18\text{C6@K})_2\text{ZrBr}_6$  could be mostly described by a mono-exponential decay profile on the microsecond  $\mu\text{s}$  time scale, with a PL lifetime of 6.80  $\mu\text{s}$  (Fig. 3D and table S7). In contrast,  $\text{Cs}_2\text{ZrBr}_6$  bulk crystal featured a triple-exponential PL decay, yielding decay time constants of 40 ns (8.9%), 0.99  $\mu\text{s}$  (24%), and 4.6  $\mu\text{s}$  (68%) (35). Additionally,  $\text{Cs}_2\text{ZrBr}_6$  nanocrystals showed a double-exponential PL decay with time constants at 0.78  $\mu\text{s}$  and 4.5  $\mu\text{s}$  (49). The PLQY was related to both the radiative and non-radiative decay rates ( $\text{PLQY} = k_{\text{rad}}/(k_{\text{rad}} + k_{\text{non-rad}})$ ), so a more sluggish radiative decay did not necessarily correlate to a lower PLQY. Remarkably, the PLQY of  $(18\text{C6@K})_2\text{ZrBr}_6$  powders (49.8%) was greater than that of  $\text{K}_2\text{ZrBr}_6$  powders (46.3%, from our measurement) and  $\text{Cs}_2\text{ZrBr}_6$  nanocrystals [ $\sim 44\%$ , from (49)]. This observation suggested that the nonradiative decay rate of the supramolecular sample was slower than that of the vacancy-ordered double perovskite phases and may indicate a lower defect density in our assembled crystals. The PL decay of  $(18\text{C6@K})_2\text{ZrCl}_4\text{Br}_2$  single crystal could also be fit with a single exponential function, with an even longer PL lifetime (12.1  $\mu\text{s}$ ) (Fig. 3D and table S8).  $\text{Cs}_2\text{ZrCl}_6$  had a slightly longer PL lifetime (7.5  $\mu\text{s}$ ) than  $\text{Cs}_2\text{ZrBr}_6$  (50). This result suggested that the supramolecular material system had a longer PL lifetime and slower non-radiative decay rate.

We also evaluate the photostability of these highly emissive blue and green emitters. Notably, previous research in the OLED community has utilized a xenon lamp to simulate solar irradiation, dissolving Ir-complexes in deuterated toluene for reference measurements of green and blue emission (51, 52). To ensure a fair comparison, we applied identical irradiation energy density ( $62 \text{ mW/cm}^2$ ) and temperature ( $35^\circ\text{C}$ ), and deuterated toluene was used to disperse the  $(18\text{C6@K})_2\text{HfBr}_6$  and  $(18\text{C6@K})_2\text{ZrCl}_4\text{Br}_2$  powders. Figure S25 shows the PL intensity decay of the  $(18\text{C6@K})_2\text{HfBr}_6$  and  $(18\text{C6@K})_2\text{ZrCl}_4\text{Br}_2$  samples under continuous irradiation. Both decay trends could be accurately described by the integrated rate law for the first-order reaction ( $\ln(I/I_0) = -kt$ ). The rate constants of photodegradation were estimated to be  $5.1 \times 10^{-3} \text{ h}^{-1}$  and  $3.0 \times 10^{-3} \text{ h}^{-1}$  for  $(18\text{C6@K})_2\text{HfBr}_6$  and  $(18\text{C6@K})_2\text{ZrCl}_4\text{Br}_2$ , respectively. Remarkably, even under stringent irradiation conditions, the PL intensities of  $(18\text{C6@K})_2\text{HfBr}_6$  and  $(18\text{C6@K})_2\text{ZrCl}_4\text{Br}_2$  decreased



to 80% after 43 hours and 73 hours, respectively. These findings underscore the superior photostability of the supramolecular assembled samples compared to most Ir-complexes, rivaling the best-reported green-emitting fac-[Ir(ppy)<sub>3</sub>] reference ( $k = 2.6 \times 10^{-3} \text{ h}^{-1}$ ) (51, 52). Previous studies on the photodegradation of the Ir-complexes, such as Ir(ppy)<sub>3</sub> and Ir(piq)<sub>3</sub>, have identified singlet oxygen attack and interaction of the excited-state molecule with its local environment as primary degradation pathways (53).

### Blue-Green Dual-Color Display and 3D-Printing

The high PLQY of the blue and green emission colors in the powders were preserved in thin films, which would enable various optoelectronic device applications (54-56). Because the powders were stable in nonpolar organic solvents, they could be evenly dispersed into solution to form inks. We used dichloromethane (DCM) because its low boiling point (39.6°C) leads to high volatility for drying films, and added polystyrene (PS) to create inks suitable for drop casting or spin coating by increasing the viscosity (57, 58) (Fig. 4A). The image of (18C6@K)<sub>2</sub>HfBr<sub>6</sub>/PS ink under a white lamp (Fig. 4B) shows that a uniform white suspension was achieved that exhibited a bright blue emission under 254-nm excitation. The emission was solely from the (18C6@K)<sub>2</sub>HfBr<sub>6</sub> powders in the ink, as the shape of the PL spectrum was the same as the PL shape of the powders (fig. S26). The solution PLQY was 90.8% (Fig. 4B and fig. S27), which was only 5.5% less than the powder PLQY. This reduction was expected because DCM and PS do not absorb strongly in the blue color wavelength region (fig. S28), and the suspended powders in the ink could cause losses through scattering. The (18C6@K)<sub>2</sub>ZrCl<sub>4</sub>Br<sub>2</sub>/PS ink also preserved the green emission of the (18C6@K)<sub>2</sub>ZrCl<sub>4</sub>Br<sub>2</sub> powders with a solution PLQY of 75.0% (Fig. 4C and fig. S29).

The inks could be drop casted under ambient conditions, and after rapid solvent evaporation, a uniform thin film forms (Fig. 4, A, D, and E). PXRD patterns of the (18C6@K)<sub>2</sub>HfBr<sub>6</sub>/PS composite (fig. S30) and (18C6@K)<sub>2</sub>ZrCl<sub>4</sub>Br<sub>2</sub>/PS composite (fig. S31) showed that the structural integrity of the powders was preserved in the PS matrix. Scanning electron microscopy (SEM) imaging of the (18C6@K)<sub>2</sub>HfBr<sub>6</sub> powders and (18C6@K)<sub>2</sub>HfBr<sub>6</sub>/PS composite thin film surface (fig. S32) indicated that the submicrometer-sized powders were uniformly dispersed. Cross-sectional SEM imaging of the thin film (fig. S33) proved the presence and uniformity of the powders across the thin film. Under UV irradiation, (18C6@K)<sub>2</sub>HfBr<sub>6</sub>/PS and (18C6@K)<sub>2</sub>ZrCl<sub>4</sub>Br<sub>2</sub>/PS composite thin films showed bright blue and green emission, respectively (Fig. 4, D and E). The shapes of the PL spectra of the thin films were the same as for the powders (figs. S25 and S34), and the PLQYs were 80.3% (fig. S35) and 69.0% (fig. S36) for blue- and green-emitting composites, respectively.

The stability of the air-sensitive Hf and Zr octahedral clusters was further enhanced in the PS polymer composite. Both Cs<sub>2</sub>HfBr<sub>6</sub> and Cs<sub>2</sub>ZrBr<sub>6</sub> double-perovskite structures are predicted to be thermodynamically unstable in the presence of water and oxygen (37), and we found that K<sub>2</sub>HfBr<sub>6</sub> and K<sub>2</sub>ZrBr<sub>6</sub> powders turn from a white to a brownish color after a few minutes of air exposure and became non-emissive. In contrast, the (18C6@K)<sub>2</sub>HfBr<sub>6</sub>/PS and (18C6@K)<sub>2</sub>ZrCl<sub>4</sub>Br<sub>2</sub>/PS composites maintained their blue and green emission colors, respectively, after 1 month of storage in the air (fig. S37). The air-stable PS polymers along with the hydrophobic crown ethers could greatly protect the air-sensitive Hf and Zr metal emission centers.

We explored display applications of the powder/PS composite thin films. A digital mirror device with pixel resolution of 2560 by 1440 sequentially patterned 250-nm UV light through projection optics onto the (18C6@K)<sub>2</sub>HfBr<sub>6</sub>/PS composite thin film with a spot size of 6.9 mm by 3.9 mm at a frame rate of 60 Hz (schematic of the process is illustrated in Fig. 4A). An emissive “Blue Cal Logo” was illuminated on the thin film with dimensions 3.8 mm in height and 4.7 mm in width (Fig. 4F). The logo exhibited high luminosity, characterized by sharply defined edges. To further demonstrate dynamically changing display luminescence, we illuminated the alphabet sequence (from A to Z) onto the thin film with a fast flipping rate (0.1 s per letter). A video of 2.6 s was recorded (movie S1). Although the duration of each letter was very short, the blue emission with the shape of the letters was sharp and bright, as illustrated in the snapshot photos (Fig.

4G). The size of the letters was only 3.1 mm in width and 3.9 mm in length, but every feature of the letters was clearly visible with similar emission intensity owing to the high uniformity of the thin film. Furthermore, the response time of the display should be fast since the PL decay rate of the  $(18\text{C6@K})_2\text{HfBr}_6$  powders was  $\sim 3$  orders of magnitude faster than the frame rate of the digital mirror device. The letters switch extremely fast, with no blurring, ghosting, or trailing effects.

These emissive powders could also be processed with high-resolution 3D printing technologies. After blending them uniformly into a monomer resin. Conventional resins for 3D printing typically use dyes as the photoabsorber to control the depth of UV penetration and, consequently, the printing resolution. However, dyes absorb light and also color the final printed parts. To avoid interference with our blue and green emitters, we developed a photo-absorber-free resin mainly comprised of photomonomer poly(ethylene glycol) diacrylate (PEGDA) but with a high content of photo inhibitor to control the printing resolution. The polymerized PEGDA resin exhibited minimal absorption within the visible spectrum, featuring a modest absorption peak from 355 to 425 nm (fig. S38A). Also, under 250-nm UV excitation, the resin exhibited significantly low emission intensity (fig. S38B). Hence, the emission colors in the blue and green range of our emitters remained largely unaffected.

Upon stirring and sonication, the powders were uniformly dispersed into the PEGDA resin. We exploited a multi-material digital light-printing method (59, 60) to achieve a 3D assembly of the blue and green emitters into complex macro- and micro-architectures. Under 405-nm structured UV light illumination, the resin rapidly converted into solid 3D structures (Fig. 5A). The PL spectra from the  $(18\text{C6@K})_2\text{HfBr}_6/\text{PEGDA}$  and the  $(18\text{C6@K})_2\text{ZrCl}_4\text{Br}_2/\text{PEGDA}$  composites were similar to that of the powders (figs. S38C, S38D, S39, and S40). The printed architectural models of the Eiffel Tower (Fig. 5B), after excitation at 254 nm, showed their respective blue and green colors (Fig. 5C). The dimensions of the two Eiffel Towers were within a few centimeters, with high-resolution spatial features (Fig. 5B). The submicrometer scale of these powders and a printing layer thickness of 40  $\mu\text{m}$  enabled even distribution throughout each layer and ensured a homogeneous emission color profile across the entire architectural construct.

A single 3D-printed structure could also manifest emissions in both blue and green by alternative resins during the printing procedure. An Eiffel Tower design characterized by blue emissions at its upper and lower segments, with green emissions in its central region is shown in Figure 5D, and a second-order hierarchical lattice structure (octet truss) was realized with one half radiating in blue and the other in green (Fig. 5E). Notably, a close-up view of the boundary between these blue- and green-emitting regions within the octet truss structure revealed the high precision in color transition without any color crossover on either side. Twisted (Fig. 5F and fig. S41) and conformal (Fig. 5G and fig. S42) octet truss architectures with dual emissions were also achieved with bright emissions and high structural accuracy.

Other complex topologies, such as cuboctahedron, tetrakaidecahedron, octet truss, and Menger sponge with the blue emitter embedded (Fig. 5H, figs S43 and S44), were also obtained to exhibit the variety of structures that could be printed with the light-emitting ink. These demonstrations served as a proof-of-concept for integrating emissive ionic powders with 3D printing technology. The potential applications of 3D-printed light-emitting structures are extensive and constantly evolving, ranging from intricate interior ambient lighting solutions to seamless integration into wearable devices.

## Discussion

We have demonstrated a supramolecular assembly strategy for achieving halide perovskite blue and green emitters with ultra-high PLQY. Specifically,  $(18\text{C6@K})_2\text{HfBr}_6$  warranted a blue emission with near-unity (96.2%) PLQY, and  $(18\text{C6@K})_2\text{ZrCl}_4\text{Br}_2$  showed a green emission with a PLQY of 82.7%. The emission of the supramolecular assembled samples originated from the STE emission, with strong electron-phonon coupling and microsecond PL lifetimes. The supramolecular approach is very promising for solution

processability. The  $(18C6@K)_2HfBr_6/PS$ -DCM ink maintained a high PLQY of  $> 90\%$ . Uniform thin films were fabricated from this ink through a drop-casting technique. The  $(18C6@K)_2HfBr_6/PS$  composite had blue emission with a PLQY of  $> 80\%$ , making it favorable for patterning, display and printing applications. The powders with blue and green emissions were also highly compatible with the 3D printing technology. The supramolecular assembly approach for halide perovskite building block catalyzes further investigation into the synthesis and characterization of supramolecular assembled functional materials, laying the foundation for substantial progress in the field.

## References and Notes:

1. M. A. Reshchikov, M. Foussekis, J. D. McNamara, A. Behrends, A. Bakin, A. Waag, Determination of the absolute internal quantum efficiency of photoluminescence in GaN codoped with Si and Zn. *J. Appl. Phys.* **111**, 073106 (2012). doi:10.1063/1.3699312
2. M. A. Reshchikov, R. Y. Korotkov, Analysis of the temperature and excitation intensity dependencies of photoluminescence in undoped GaN films. *Phys. Rev. B* **64**, 115205 (2001). doi:10.1103/PhysRevB.64.115205
3. A. K. Viswanath, J. I. Lee, D. Kim, C. R. Lee, J. Y. Leem, Exciton-phonon interactions, exciton binding energy, and their importance in the realization of room-temperature semiconductor lasers based on GaN. *Phys. Rev. B* **58**, 16333–16339 (1998). doi:10.1103/PhysRevB.58.16333
4. W. Shan, B. D. Little, A. J. Fischer, J. J. Song, B. Goldenberg, W. G. Perry, M. D. Bremser, R. F. Davis, Binding energy for the intrinsic excitons in wurtzite GaN. *Phys. Rev. B* **54**, 16369–16372 (1996). doi:10.1103/PhysRevB.54.16369
5. C. Hauswald, P. Corfdir, J. K. Zettler, V. M. Kaganer, K. K. Sabelfeld, S. Fernández-Garrido, T. Flissikowski, V. Consonni, T. Gotschke, H. T. Grahn, L. Geelhaar, O. Brandt, Origin of the nonradiative decay of bound excitons in GaN nanowires. *Phys. Rev. B* **90**, 19 (2014). doi:10.1103/PhysRevB.90.165304
6. M. Shibata, T. Furuya, H. Sakaguchi, S. Kuma, Synthesis of gallium nitride by ammonia injection into gallium melt. *J. Cryst. Growth* **196**, 47–52 (1999). doi:10.1016/S0022-0248(98)00819-7
7. W. Yina, T. Shi, Y. Yan, Unusual defect physics in CH<sub>3</sub>NH<sub>3</sub>PbI<sub>3</sub> perovskite solar cell absorber. *Appl. Phys. Lett.* **104**, 063903 (2014). doi: 10.1063/1.4864778
8. R. J. Sutton, G. E. Eperon, L. Miranda, E. S. Parrott, B. A. Kamino, J. B. Patel, M. T. Hörantner, M. B. Johnston, A.-A. Haghighirad, D. T. Moore, H. J. Snaith, Bandgap-tunable cesium lead halide perovskites with high thermal stability for efficient solar cells. *Adv. Energy Mater.* **6**, 1502458 (2016). doi: 10.1002/aenm.201502458
9. M. R. Filip, G. E. Eperon, H. J. Snaith, F. Giustino, Steric engineering of metal-halide perovskites with tunable optical band gaps. *Nat. Commun.* **5**, 5757 (2014). doi:10.1038/ncomms6757
10. L. Protesescu, S. Yakunin, M. I. Bodnarchuk, F. Krieg, R. Caputo, C. H. Hendon, R. X. Yang, A. Walsh, M. V. Kovalenko, Nanocrystals of cesium lead halide perovskites (CsPbX<sub>3</sub>, X = Cl, Br, and I): novel optoelectronic materials showing bright emission with wide color gamut. *Nano Lett.* **15**, 3692–3696 (2015). doi:10.1021/nl5048779
11. J. Kang, L.-W. Wang, High defect tolerance in lead halide perovskite CsPbBr<sub>3</sub>. *J. Phys. Chem. Lett.* **8**, 489–493 (2017). doi:10.1021/acs.jpcclett.6b02800
12. K. X. Steirer, P. Schulz, G. Teeter, V. Stevanovic, M. Yang, K. Zhu, J. J. Berry, Defect tolerance in methylammonium lead triiodide perovskite. *ACS Energy Lett.* **1**, 360–366 (2016). doi:10.1021/acsenergylett.6b00196
13. F. Deschler, M. Price, S. Pathak, L. E. Klintberg, D.-D. Jarausch, R. Higler, S. Hüttner, T. Leijtens, S. D. Stranks, H. J. Snaith, M. Atatüre, R. T. Phillips, R. H. Friend, High photoluminescence efficiency and optically pumped lasing in solution-processed mixed halide perovskite semiconductors. *J. Phys. Chem. Lett.* **5**, 1421–1426 (2014). doi:10.1021/jz5005285

14. F. D. Stasio, S. Christodoulou, N. Huo, G. Konstantato, Near-unity photoluminescence quantum yield in CsPbBr<sub>3</sub> nanocrystal solid-state films via postsynthesis treatment with lead bromide. *Chem. Mater.* **29**, 7663–7667 (2017). doi:10.1021/acs.chemmater.7b02834
15. J. Li, L. Gan, Z. Fang, H. He, Z. Ye, Bright tail states in blue-emitting ultrasmall perovskite quantum dots. *J. Phys. Chem. Lett.* **8**, 6002–6008 (2017). doi:10.1021/acs.jpcclett.7b02786
16. S. Wang, C. Bi, J. Yuan, L. Zhang, J. Tian, Original core–shell structure of cubic CsPbBr<sub>3</sub>@amorphous CsPbBr<sub>x</sub> perovskite quantum dots with a high blue photoluminescence quantum yield of over 80%. *ACS Energy Lett.* **3**, 245–251 (2018). doi:10.1021/acsenergylett.7b01243
17. X. Gong, O. Voznyy, A. Jain, W. Liu, R. Sabatini, Z. Piontkowski, G. Walters, G. Bappi, S. Nokhrin, O. Bushuyev, M. Yuan, R. Comin, D. McCamant, S. O. Kelley, E. H. Sargent, Electron–phonon interaction in efficient perovskite blue emitters. *Nat. Mater.* **17**, 550–556 (2018). doi:10.1038/s41563-018-0081-x
18. H. Luo, Y. Huang, H. Liu, B. Zhang, J. Song, Ionic liquid assisted pure blue emission CsPbBr<sub>3</sub> quantum dots with improved optical properties and alkyl chain regulated stability. *J. Chem. Eng.* **430**, 132790 (2022). doi:10.1016/j.cej.2021.132790
19. M. C. Folgueras, S. Louisia, J. Jin, M. Gao, A. Du, S. C. Fakra, R. Zhang, F. Seeler, K. Schierle-Arndt, P. Yang, Ligand-Free Processable Perovskite Semiconductor Ink. *Nano Lett.* **21**, 8856–8862 (2021). doi:10.1021/acs.nanolett.1c03308
20. J. Jin, M. C. Folgueras, M. Gao, S. Yu, S. Louisia, Y. Zhang, L. N. Quan, C. Chen, R. Zhang, F. Seeler, K. Schierle-Arndt, P. Yang, A new perspective and design principle for halide perovskites: ionic octahedron network (ION). *Nano Lett.* **21**, 5415–5421 (2021). doi:10.1021/acs.nanolett.1c01897
21. M. Gao, Y. Zhang, Z. Lin, J. Jin, M. C. Folgueras, P. Yang, The making of a reconfigurable semiconductor with a soft ionic lattice. *Matter* **4**, 3874–3896 (2019). doi:10.1016/j.matt.2021.09.023
22. J. S. Manser, M. I. Saidaminov, J. A. Christians, O. M. Bakr, P. V. Kamat., Making and breaking of lead halide perovskites. *Acc. Chem. Res.* **49**, 330–338 (2016). doi:10.1021/acs.accounts.5b00455
23. M. C. Folgueras, J. Jin, M. Gao, L. N. Quan, J. A. Steele, S. Srivastava, M. B. Ross, R. Zhang, F. Seeler, K. Schierle-Arndt, M. Asta, P. Yang, Lattice dynamics and optoelectronic properties of vacancy-ordered double perovskite Cs<sub>2</sub>TeX<sub>6</sub> (X = Cl<sup>-</sup>, Br<sup>-</sup>, I<sup>-</sup>) single crystals. *J. Phys. Chem. C* **125**, 25126–25139 (2021). doi:10.1021/acs.jpcc.1c08332
24. D. Ju, X. Zheng, J. Yin, Z. Qiu, B. Türedi, X. Liu, Y. Dang, B. Cao, O. F. Mohammed, O. M. Bakr, X. Tao, Tellurium-based double perovskites A<sub>2</sub>TeX<sub>6</sub> with tunable band gap and long carrier diffusion length for optoelectronic applications. *ACS Energy Lett.* **4**, 228–234 (2019). doi:10.1021/acsenergylett.8b02113
25. A. D. Nicholas, B. W. Walusiak, L. C. Garman, M. N. Huda, C. L. Cahill, Impact of noncovalent interactions on structural and photophysical properties of zero-dimensional tellurium(IV) perovskites. *J. Mater. Chem. C* **9**, 3271–3286 (2021). doi:10.1039/D0TC06000C
26. J. Zhou, J. Luo, X. Rong, P. Wei, M. S. Molochev, Y. Huang, J. Zhao, Q. Liu, X. Zhang, J. Tang, Z. Xia, Lead-free perovskite derivative Cs<sub>2</sub>SnCl<sub>6-x</sub>Br<sub>x</sub> single crystals for narrowband photodetectors. *Adv. Opt. Mater.* **7**, 1900139 (2019). doi:10.1002/adom.201900139
27. Z. Tan, Y. Chu, J. Chen, J. Li, G. J. G. Niu, L. Gao, Z. Xiao, J. Tang, Lead-free perovskite


- variant solid solutions  $\text{Cs}_2\text{Sn}_{1-x}\text{Te}_x\text{Cl}_6$ : bright luminescence and high anti-water stability. *Adv. Mater.* **32**, 2002443 (2022). doi:10.1002/adma.202002443
28. H. Yin, J. Chen, P. Guan, D. Zheng, Q. Kong, S. Yang, P. Zhou, B. Yang, T. Pullerits, K. Han, Controlling photoluminescence and photocatalysis activities in lead-free  $\text{Cs}_2\text{Pt}_x\text{Sn}_{1-x}\text{Cl}_6$  perovskites via ion substitution. *Angew Chem. Int. Ed.* **60**, 22693–22699 (2021). doi:10.1002/anie.202108133
  29. I. N. Douglas, J. V. Nicholas, B. G. Wybourne, Luminescence of  $\text{Pt}^{4+}$  in octahedral complexes. *J. Chem. Phys.* **48**, 1415 (1968). doi:10.1063/1.1668827
  30. C. Li, X. Lu, W. Ding, L. Feng, Y. Gao, Z. Guo, Formability of  $\text{ABX}_3$  (X = F, Cl, Br, I) halide perovskites. *Acta Cryst.* **B64**, 702–707 (2008). doi:10.1107/S0108768108032734
  31. Q. He, C. Zhou, L. Xu, S. Lee, Xi. Lin, J. Neu, M. Worku, M. Chaaban, B. Ma, Highly stable organic antimony halide crystals for X-ray scintillation. *ACS Materials Lett.* **2**, 633–638 (2020). doi:10.1021/acsmaterialslett.0c00133
  32. C. Zhou, H. Lin, Y. Tian, Z. Yuan, R. Clark, B. Chen, L. J. van de Burgt, J. C. Wang, Y. Zhou, K. Hanson, Q. J. Meisner, J. Neu, T. Besara, T. Siegrist, E. Lambers, P. Djurovich, B. Ma, Luminescent zero-dimensional organic metal halide hybrids with near-unity quantum efficiency. *Chem. Sci.* **9**, 586–593 (2018). doi:10.1039/C7SC04539E
  33. M. Li, Z. Xia. Recent progress of zero-dimensional luminescent metal halides. *Chem. Soc. Rev.* **50**, 2626–2662 (2021). doi:10.1039/D0CS00779J
  34. J. A. Steele, P. Puech, M. Keshavarz, R. Yang, S. Banerjee, E. Debroye, C. W. Kim, H. Yuan, N. H. Heo, J. Vanacken, A. Walsh, J. Hofkens, M. B. J. Roefsaers, Giant electron–phonon coupling and deep conduction band resonance in metal halide double perovskite. *ACS Nano* **12**, 8081–8090 (2018). doi:10.1021/acsnano.8b02936
  35. K. Saeki, Y. Fujimoto, M. Koshimizu, D. Nakauchi, H. Tanaka, T. Yanagida, K. Asai, Luminescence and scintillation properties of  $\text{Cs}_2\text{HfBr}_6$  and  $\text{Cs}_2\text{ZrBr}_6$  crystals. *J. Appl. Phys.* **57**, 030310 (2018). doi:10.7567/JJAP.57.030310
  36. A. Abfaltrer, J. Shamsi, D. J. Kubicki, C. N. Savory, J. Xiao, G. Divitini, W. Li, S. Macpherson, K. Gałkowski, J. L. MacManus-Driscoll, D. O. Scanlon, S. D. Stranks, Colloidal synthesis and optical properties of perovskite-inspired cesium zirconium halide nanocrystals. *ACS Materials Lett.* **2**, 1644–1652 (2020). doi:10.1021/acsmaterialslett.0c00393
  37. C. Kaewmeechai, Y. Laosiritaworn, A. P. Jaroenjittichai, DFT calculation on electronic properties of vacancy-ordered double perovskites  $\text{Cs}_2(\text{Ti}, \text{Zr}, \text{Hf})\text{X}_6$  and their alloys: Potential as light absorbers in solar cells. *Results Phys.* **25**, 104225 (2021). doi:10.1016/j.rinp.2021.104875
  38. W. Thomas, H. Elias, Darstellung von  $\text{HfCl}_4$  und  $\text{HfBr}_4$  durch umsetzung von hafnium mit geschmolzenen metallhalogeniden. *J. Inorg. Nucl. Chem.* **38**, 2227–2229 (1976). doi:10.1016/0022-1902(76)80199-6
  39. E. V. van Loef, G. Ciampi, U. Shirwadkar, L. S. Pandian, K. S. Shah, Crystal growth and scintillation properties of Thallium-based halide scintillators. *J. Cryst. Growth* **532**, 125438 (2020). doi:10.1016/j.jcrysgro.2019.125438
  40. S. Kodama, S. Kurosawa, K. Fujii, T. Murakami, M. Yashima, J. Pejchal, R. Král, M. Nikl, A. Yamaji, M. Yoshino, S. Toyoda, H. Sato, Y. Ohashi, K. Kamada, Y. Yokota, A. Yoshikawa, Single-crystal growth, structure and luminescence properties of  $\text{Cs}_2\text{HfCl}_3\text{Br}_3$ . *Opt. Mater.* **106**, 109942 (2020). doi:10.1016/j.optmat.2020.109942

41. C. Zhu, J. Jin, M. Gao, A. M. Oddo, M. C. Folgueras, Y. Zhang, C.-K. Lin, P. Yang, Supramolecular assembly of halide perovskite building blocks. *J. Am. Chem. Soc.* **144**, 12450–12458 (2022). doi:10.1021/jacs.2c04357
42. J. E. Saal, S. Kirklin, M. Aykol, B. Meredig, C. Wolverton, Materials design and discovery with high-throughput density functional theory: the open quantum materials database (OQMD). *JOM* **65**, 1501–1509 (2013). doi:10.1007/s11837-013-0755-4
43. S. Kirklin, J. E. Saal, B. Meredig, A. Thompson, J. W. Doak, M. Aykol, S. Rühl, C. Wolverton, The open quantum materials database (OQMD): assessing the accuracy of DFT formation energies. *Npj Comput. Mater.* **1**, 15010 (2015). doi:10.1038/npjcompumats.2015.10
44. Q. A. Akkerman, . D’Innocenzo, S. Accornero, A. Scarpellini, A. Petrozza, M. Prato, L. Manna, Tuning the optical properties of cesium lead halide perovskite nanocrystals by anion exchange reactions. *J. Am. Chem. Soc.* **137**, 10276–10281 (2015). doi:10.1021/jacs.5b05602
45. Y. Toyozawa. Further contribution to the theory of the line-shape of the exciton absorption band. *Prog. Theor. Phys.* **27**, 89–104 (1962). doi:10.1143/PTP.27.89
46. W. Stadler, D. M. Hofmann, H. C. Alt, T. Muschik, B. K. Meyer, E. Weigel, G. Müller-Vogt, M. Salk, E. Rupp, K. W. Benz, Optical investigations of defects in  $\text{Cd}_{1-x}\text{Zn}_x\text{Te}$ . *Phys. Rev. B.* **51**, 10619–10630 (1995). doi:10.1103/PhysRevB.51.10619
47. Y. Song, X. Zhang, L. Li, Z. Mo, J. Xu, S. Yu, X. Liu, J. Zhang, Temperature-dependent photoluminescence of cesium lead halide perovskite ( $\text{CsPbX}_3$ , X = Br, Cl, I) quantum dots. *Mater. Res. Express* **6**, 115064 (2019). doi:10.1088/2053-1591/ab4911
48. S. J. Zelewski, J. M. Urban, A. Surrente, D. K. Maude, A. Kuc, L. Schade, R. D. Johnson, M. Dollmann, P. K. Nayak, H. J. Snaith, P. Radaelli, R. Kudrawiec, R. J. Nicholas, P. Plochocka, M. Baranowski, Revealing the nature of photoluminescence emission in the metal-halide double perovskite  $\text{Cs}_2\text{AgBiBr}_6$ . *J. Mater. Chem. C* **7**, 8350–8356 (2019). doi:10.1039/C9TC02402F
49. V. Vaněček, J. Páterek, R. Král, M. Buryi, V. Babin, K. Zloužeová, S. Kodama, S. Kurosawa, Y. Yokota, A. Yoshikawa, M. Nikl,  $\text{Cs}_2\text{HfCl}_6$  doped with Zr: Influence of tetravalent substitution on scintillation properties. *J. Cryst. Growth* **573**, 126307 (2021). doi:10.1016/j.jcrysgro.2021.126307
50. K. Saeki, Y. Fujimoto, M. Koshimizu, T. Yanagida, K. Asai, Comparative study of scintillation properties of  $\text{Cs}_2\text{HfCl}_6$  and  $\text{Cs}_2\text{ZrCl}_6$ . *Appl. Phys. Express* **9**, 042602 (2016). doi:10.7567/APEX.9.042602
51. H.-H. Kuo, Z.-L. Zhu, C.-S. Lee, Y.-K. Chen, S.-H. Liu, P.-T. Chou, A. K.-Y. Jen, Y. Chi. Bis-tridentate iridium(III) phosphors with very high photostability and fabrication of blue-emitting OLEDs. *Adv. Sci.* **5**, 1800846 (2018). doi: 10.1002/advs.201800846
52. H.-H. Kuo, L.-Y. Hsu, J.-Y. Tso, W.-Y. Hung, S.-H. Liu, P.-T. Chou, K.-T. Wong, Z.-L. Zhu, C.-S. Lee, A. K.-Y. Jen, Y. Chi. Blue-emitting bis-tridentate Ir(III) phosphors: OLED performances vs. substituent effects. *J. Mater. Chem. C* **6**, 10486–10496 (2018). doi: 10.1039/c8tc03194k
53. S. Schmidbauer, A. Hohenleutner, B. König. Studies on the photodegradation of red, green and blue phosphorescent OLED emitters. *Beilstein J. Org. Chem.* **9**, 2088–2096 (2013). doi:10.3762/bjoc.9.245
54. W. Hui, L. Chao, H. Lu, F. Xia, Q. Wei, Z. Su, T. Niu, L. Tao, B. Du, D. Li, Y. Wang, H. Dong, S. Zuo, B. Li, W. Shi, X. Ran, P. Li, H. Zhang, Z. Wu, C. Ran, L. Song, G. Xing, X.


- Gao, J. Zhang, Y. Xia, Y. Chen, W. Huang., Stabilizing black-phase formamidinium perovskite formation at room temperature and high humidity. *Science* **371**, 1359–1364 (2021). doi:10.1126/science.abf7652
55. F. Mathies, T. Abzieher, A. Hochstuhl, K. Glaser, A. Colsmann, U. W. Paetzold, G. Hernandez-Sosa, U. Lemmer, A. Quintilla, Multipass inkjet printed planar methylammonium lead iodide perovskite solar cells. *J. Mater. Chem. A* **4**, 19207–19213 (2016). doi:10.1039/C6TA07972E
  56. S. Li, X. L. Xu, Y. Yang, Y. S. Xu, Y. Xu, H. Xia, Highly deformable high-performance paper-based perovskite photodetector with improved stability. *ACS Appl. Mater. Interfaces* **13**, 31919–31927 (2013). doi:10.1021/acsami.1c05828
  57. M. Kaseem, K. Hamad, Y. G. Ko, Fabrication and materials properties of polystyrene/carbon nanotube (PS/CNT) composites: a review. *Eur. Polym. J.* **79**, 36–62 (2016). doi:10.1016/j.eurpolymj.2016.04.011
  58. Y. Tu, L. Zhou, Y. Z. Jin, C. Gao, Z. Z. Ye, Y. F. Yang, Q. L. Wang, Transparent and flexible thin films of ZnO-polystyrene nanocomposite for UV-shielding applications. *J. Mater. Chem.* **20**, 1594–1599 (2010). doi:10.1039/B914156A
  59. H. Cui, D. Yao, R. Hensleigh, H. Lu, A. Calderon, Z. Xu, S. Davaria, Z. Wang, P. Mercier, P. Tarazaga, X. Zheng, Design and printing of proprioceptive three-dimensional architected robotic metamaterials. *Science*, **376**, 1287–1293 (2022). doi:10.1126/science.abn0090
  60. R. Hensleigh, H. Cui, Z. Xu, J. Massman, D. Yao, J. Berrigan, X. Zheng. Charge-programmed three-dimensional printing for multi-material electronic devices. *Nat. Electron.* **3**, 216–224 (2020). doi:10.1038/s41928-020-0391-2
  61. CrysAlisPro 1.171.39.45f.
  62. O. V. Dolomanov, L. J. Bourhis, R. J. Gildea, J. A. K. Howard, H. Puschmann, OLEX2: a complete structure solution, refinement and analysis program. *J. Appl. Crystallogr.* **42** 339–341 (2009). doi:10.1107/S0021889808042726
  63. G. M. Sheldrick, SHELXT-integrated space-group and crystal-structure determination. *Acta Crystallogr., Sect. A: Found. Adv.* **71**, 3–8 (2015). doi:10.1107/S2053273314026370
  64. G. M. Sheldrick, Crystal structure refinement with SHELXL. *Acta Crystallogr., Sect. C: Struct. Chem.* **71**, 3–8 (2015). doi:10.1107/S2053229614024218
  65. S. J. Clark, M. D. Segall, C. J. Pickard, P. J. Hasnip, M. I. J. Probert, K. Refson, M. C. Payne, First principles methods using CASTEP. *Z. Kristallogr.* **220**, 567–570 (2005). doi:10.1524/zkri.220.5.567.65075
  66. D. R. Hamann, M. Schlüter, C. Chiang, Norm-conserving pseudopotentials. *Phys. Rev. Lett.* **43**, 1494–1497 (1979). doi:10.1103/PhysRevLett.43.1494
  67. W. Kohn, L. J. Sham, Self-consistent equations including exchange and correlation effects. *Phys. Rev.* **140**, A1133–A1138 (1965). doi:10.1103/PhysRev.140.A1133




Figures:

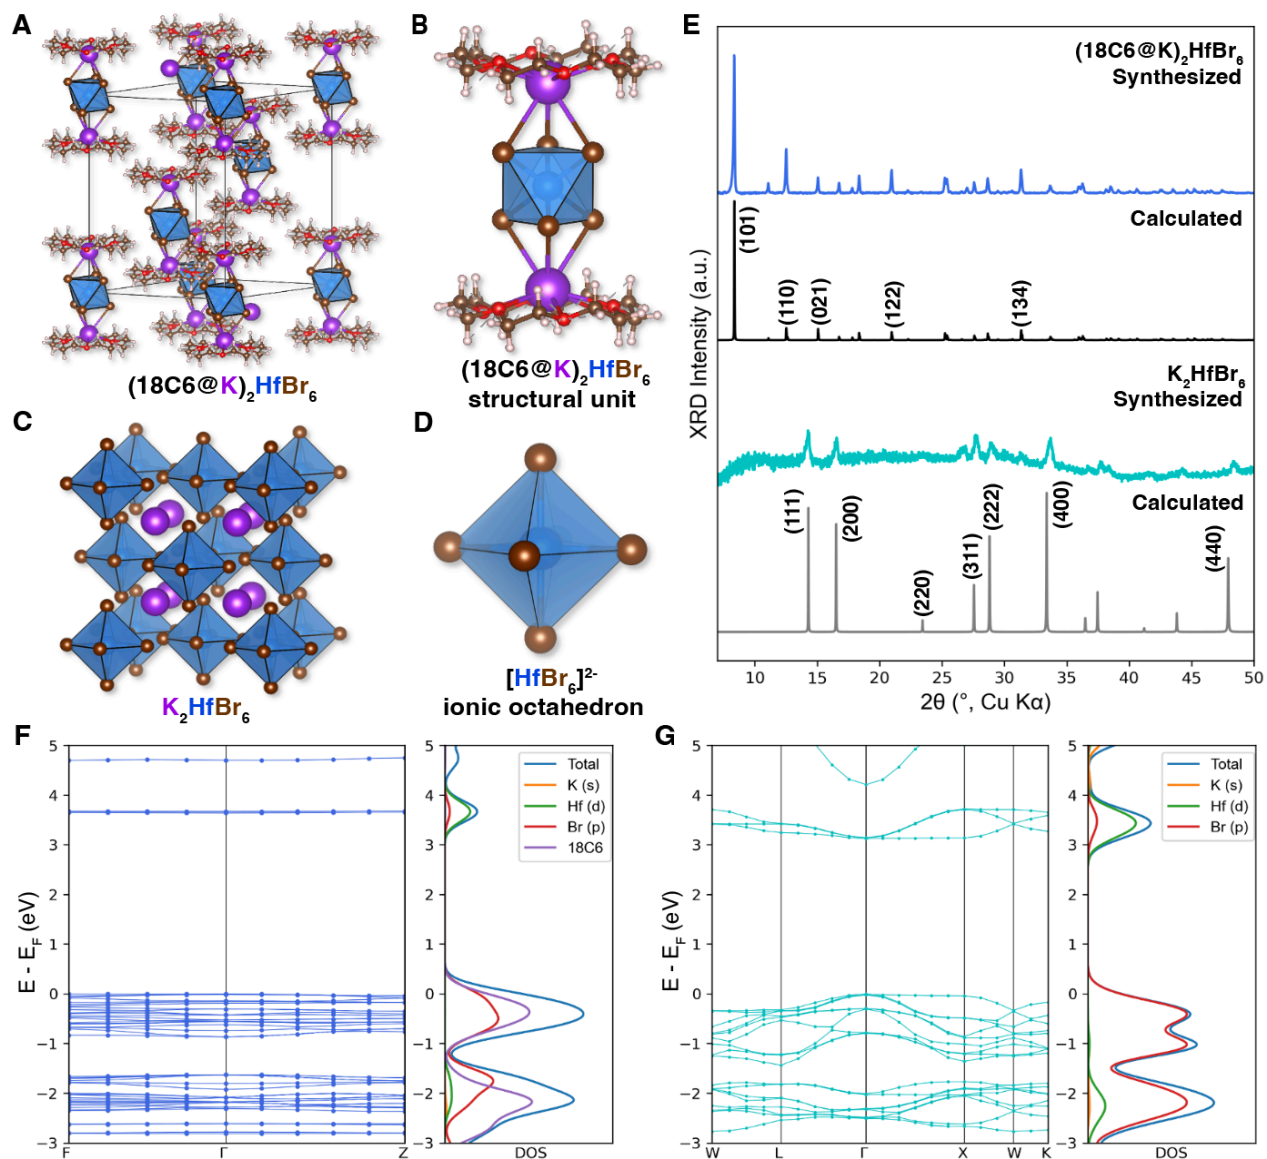


**Fig. 1. Two assemblies of the  $[HfBr_6]^{2-}$  ionic octahedron.** (A) The rhombohedral unit cell and (B) the dumbbell-shaped structural unit of  $(18C6@K)_2HfBr_6$ . (C) The  $Fm-3m$  unit cell (from OQMD database (36, 37)) and (D) the isolated  $[HfBr_6]^{2-}$  ionic octahedron building block of  $K_2HfBr_6$ . (E) The powder x-ray diffraction (PXRD) patterns for synthesized  $(18C6@K)_2HfBr_6$  and  $K_2HfBr_6$  powders and the calculated diffraction patterns.  $K_2HfBr_6$  showed quite poor PXRD quality because of its poor stability during measurement. Band structure and corresponding total partial density of states (pDOS) of (F)  $(18C6@K)_2HfBr_6$  and (G)  $K_2HfBr_6$ . When  $[HfBr_6]^{2-}$  octahedra were assembled in the supramolecular approach, the dispersion of the bands decreased and 18C6 contributed to the valence band.

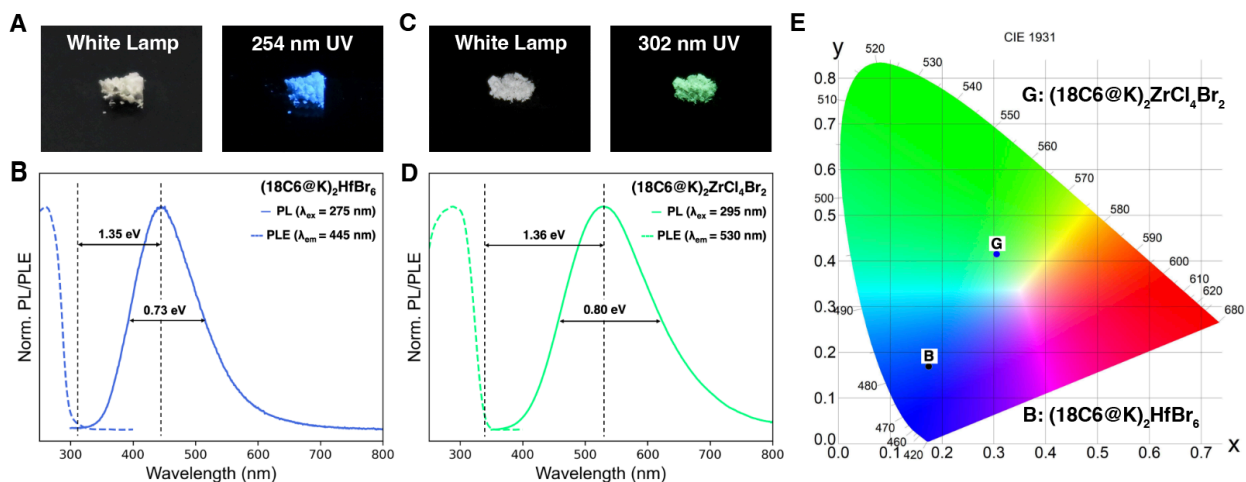

**Fig. 2. Blue emission with near-unity PLQY (96.2%) from  $(18C6@K)_2HfBr_6$  powders and green emission with a PLQY of 82.7% from  $(18C6@K)_2ZrCl_4Br_2$  powders.** (A)  $(18C6@K)_2HfBr_6$  powders under white light and 254-nm UV excitation. (B) PL and PLE spectra of  $(18C6@K)_2HfBr_6$  powders with 275-nm excitation. (C)  $(18C6@K)_2ZrCl_4Br_2$  powders under white lamp and 302-nm UV excitation. (D) PL and PLE spectra of  $(18C6@K)_2ZrCl_4Br_2$  powders with 295-nm excitation. (E) The CIE 1931 chromaticity diagram for the emission of  $(18C6@K)_2HfBr_6$  powders and  $(18C6@K)_2ZrCl_4Br_2$  powders. “B” stands for the blue emission of  $(18C6@K)_2HfBr_6$ , and “G” stands for the green emission of  $(18C6@K)_2ZrCl_4Br_2$ . The coordinates for the emission colors of  $(18C6@K)_2HfBr_6$  and  $(18C6@K)_2ZrCl_4Br_2$  were (0.17438, 0.16922) and (0.30597, 0.41533), respectively.

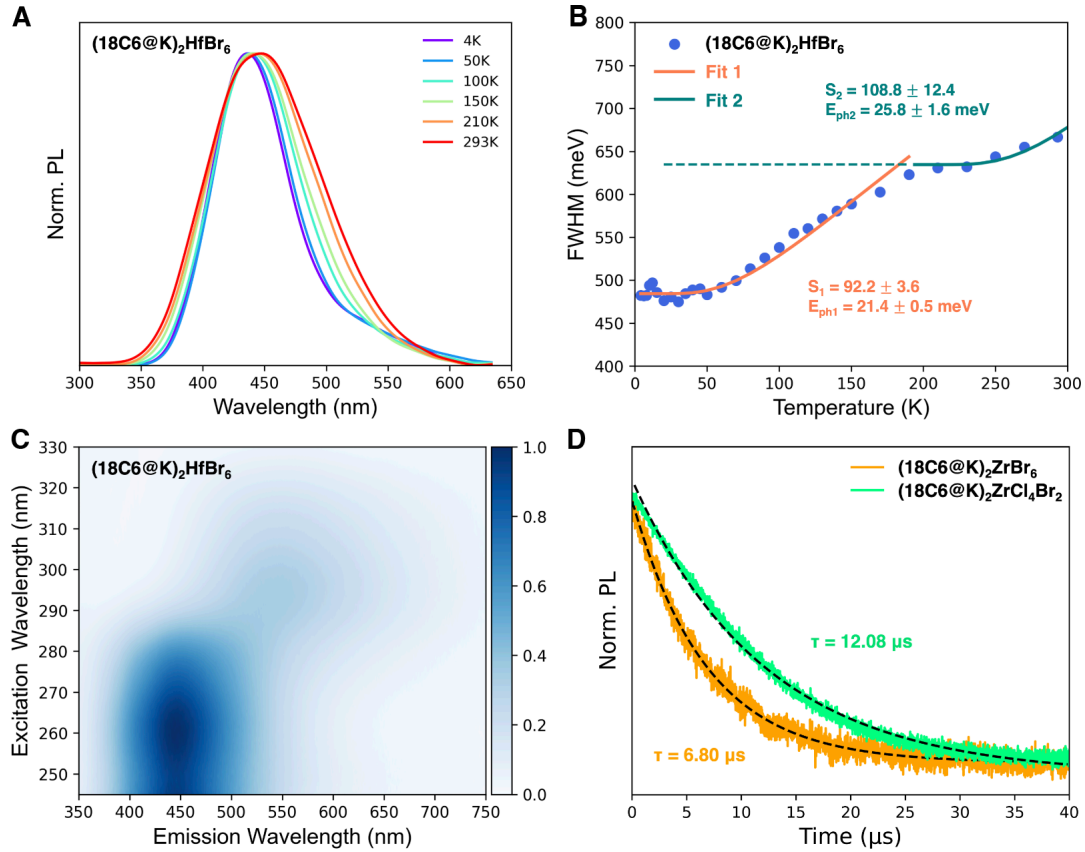


**Fig. 3. Photophysical analysis of  $(18C6@K)_2HfBr_6$  and  $(18C6@K)_2ZrCl_4Br_2$ .** (A) PL spectra of  $(18C6@K)_2HfBr_6$  powders at 4, 50, 100, 150, 210, and 293 K. (B) Full-width at half-maximum (FWHM) of the PL spectra of  $(18C6@K)_2HfBr_6$  powders at different temperatures, with the red and green solid lines denoting the least-square fit to Eq. 1 at low (4 to 190 K) and high (190 to 293 K) temperature ranges, respectively. (C) Photoluminescence excitation (PLE) spectroscopy of  $(18C6@K)_2HfBr_6$  powders. (D) Normalized PL decay curves of  $(18C6@K)_2ZrCl_4Br_2$  and  $(18C6@K)_2ZrBr_6$  single crystals.

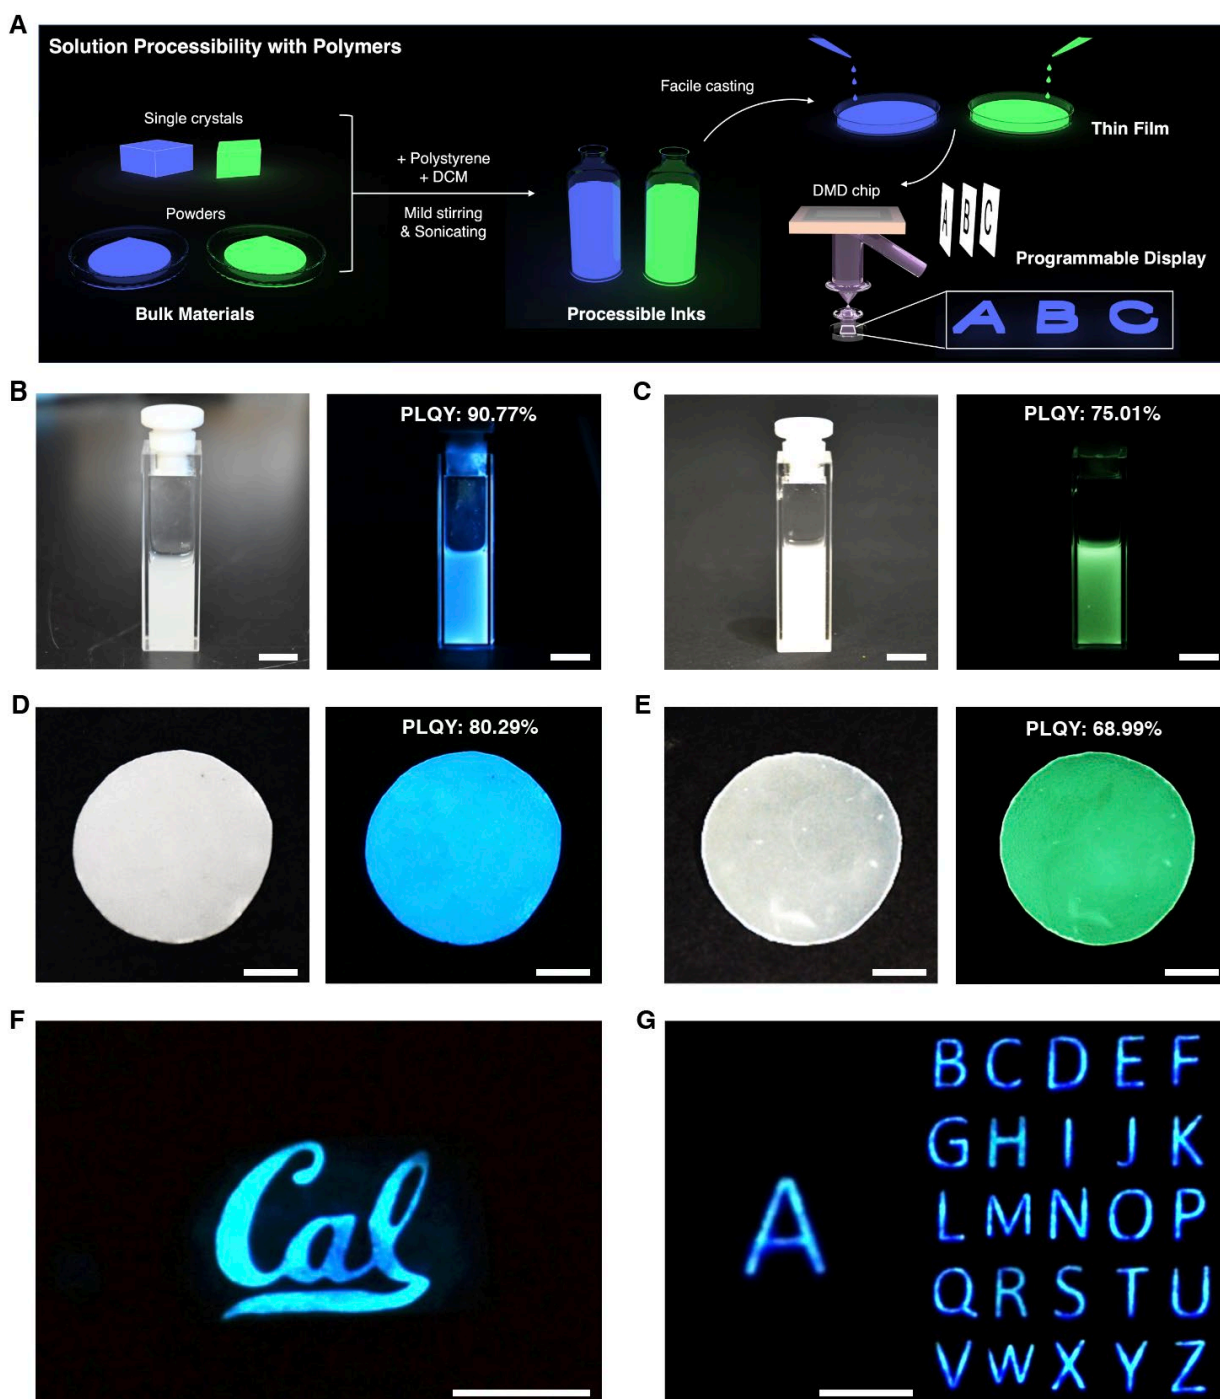

**Fig. 4. Solution processability and display application of highly emissive blue and green semiconductor inks.** (A) Schematic illustrating the thin film fabrication method and the display application. The inks were formed by mixing  $(18C6@K)_2HfBr_6$  or  $(18C6@K)_2ZrCl_4Br_2$  powders and polystyrene (PS) in dichloromethane (DCM). Thin films were obtained by drop casting, and they demonstrated programmable display capability. (B)  $(18C6@K)_2HfBr_6/PS$ -DCM ink under white lamp and 254-nm UV lamp excitation. (C)  $(18C6@K)_2ZrCl_4Br_2/PS$ -DCM ink under white light and 302-nm lamp excitation. (D)  $(18C6@K)_2HfBr_6/PS$  composite thin film under white light and 254-nm UV excitation. (E)  $(18C6@K)_2ZrCl_4Br_2/PS$  composite thin film under white light and 302-nm UV excitation. The scale bars for (B-E) are 1 cm. The PLQYs of all samples are shown in the photos. (F) Image of the ‘Cal Logo’ blue emission on

(18C6@K)<sub>2</sub>HfBr<sub>6</sub>/PS composite thin film. (G) Snapshots of a video showing alphabet A to Z with 0.1 s per letter on (18C6@K)<sub>2</sub>HfBr<sub>6</sub>/PS composite thin film. The scale bars for (F) and (G) are 3 mm and 4 mm, respectively.

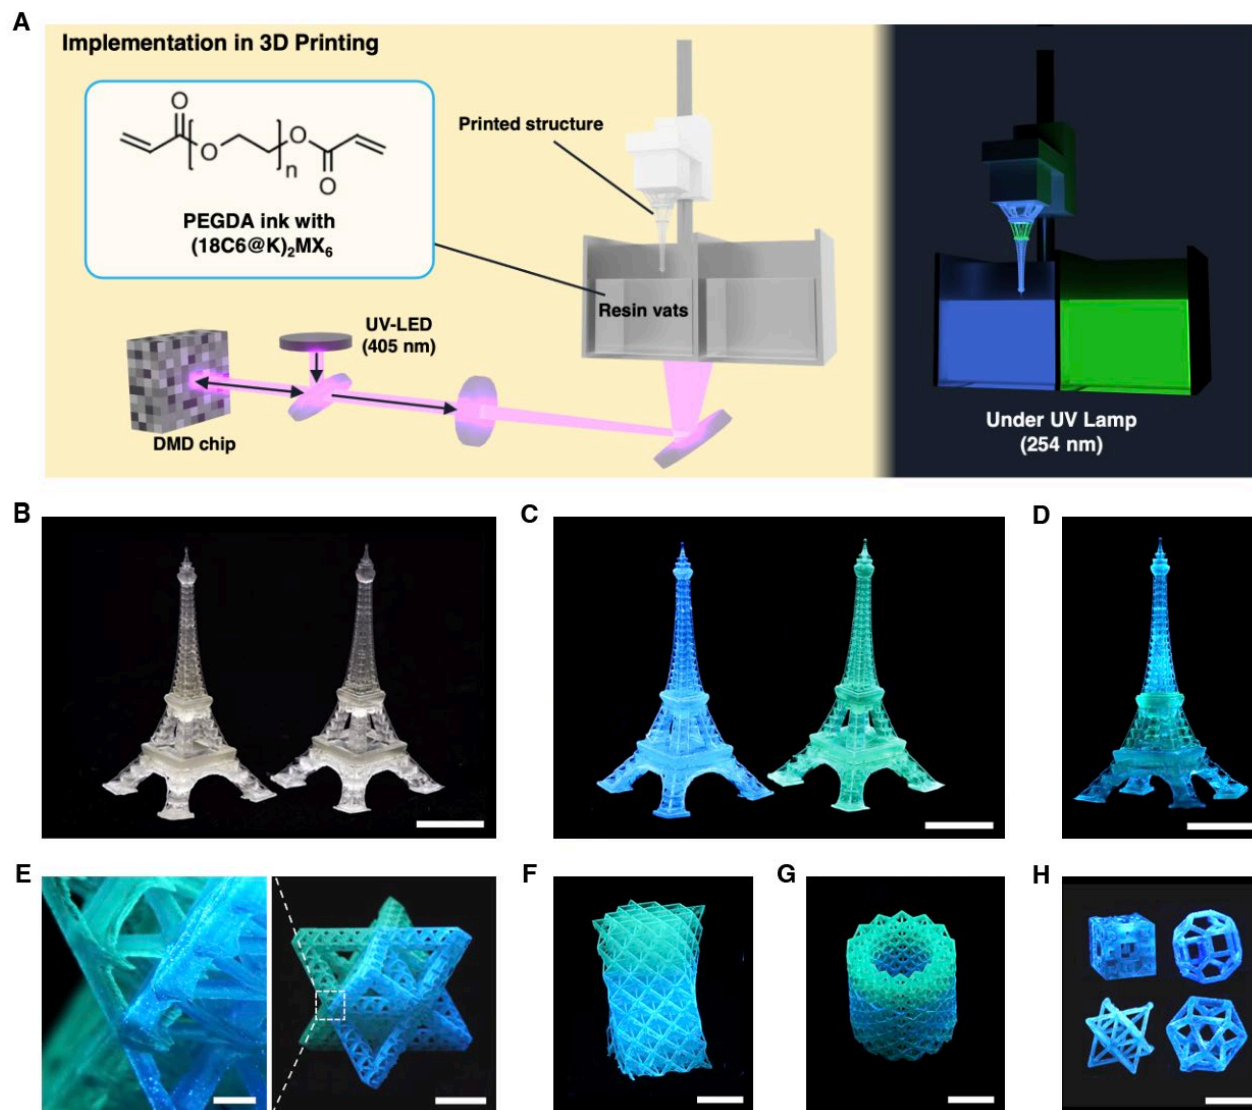

**Fig. 5. Implementation of the blue-green dual-color 3D printing.** (A) Schematic illustrating the multi-material 3D printing process. Two 3D-printed light-emitting Eiffel Towers under (B) white light and (C) 254-nm UV excitation. (D) A dual-emitting Eiffel Tower under 254-nm UV excitation. (E-H) Conformal and twisted octet trusses with varying hierarchical structures and geometric shapes, including cuboctahedron, tetrakaidecahedron, and Menger sponge structures with the blue and green emitters or their combinations, respectively. These printed architectures were photoexcited at 254 nm. The scale bars for (B) to (G) are 5 mm. The scale bar for the zoom-in image of (E) is 0.6 mm. The scale bar for (H) is 4 mm.

## Acknowledgements:

The authors sincerely thank Alexander M. Oddo (University of California, Berkeley) for valuable discussions on the design of the experiments. We sincerely thank Dr. Nick Settineri at University of California, Berkeley for his assistance in SCXRD collection. **Funding:** This work was supported by the U.S. Department of Energy, Office of Science, Office of Basic Energy Sciences, Materials Sciences and Engineering Division, under Contract No. DE-AC02-05-CH11231 within the Fundamentals of Semiconductor Nanowire Program (KCPY23). Single-crystal x-ray diffraction studies were performed at the UC Berkeley College of Chemistry X-ray Crystallography (CheXray). We thank the MGCF (Molecular Graphics and Computation Facility, NIH S10OD023532) and Kavli Energy NanoScience Institute (KENI) at UC Berkeley for support on Materials Studio 2020 and the CASTEP package. C.Z. and M.C.F. acknowledges support from the Kavli ENSI Philomathia Graduate Student Fellowship. J.J. acknowledges the fellowship support from Suzhou Industrial Park. H.K.D.L acknowledges support from the National Science Foundation's Graduate Research Fellowship Program (NSF GRFP) under grant DGE 1752814. X.Z. would like to thank funding support from National Science Foundation, 2048200, DARPA Young Faculty Award (D20AP00001-02) and Office of Naval Research (N00014-23-1-2797). The TRPL measurement was supported by the U.S. Department of Energy, Office of Science, Office of Basic Energy Sciences, Materials Sciences and Engineering Division under Contract No. DE- AC02-05-CH11231 (van der Waals heterostructure program KCFW16). **Author contributions:** All authors contributed substantially to the work presented in this manuscript. C.Z., J.J. and P.Y. conceived the study. C.Z. conducted the synthesis of the powders, single crystals, inks, and thin films. C.Z. conducted the powder XRD, Raman, UV-vis, PL, PLE, 2D PLE mapping, PLQY, CIE chromaticity diagram, SEM imaging, and photodegradation tests. J.J. and C.Z. conducted the single crystal XRD measurements. J.J. conducted the DFT calculations and designed the schematics. Z.W., C.Z. and J.J. took the digital camera images. Z.W. designed the photo-absorber-free resin for 3D printing. Z.W., Z.X., X.Z., and C.Z. conducted the 3D-printing experiments. Z.X., X.Z., and C.Z. conducted the display demonstrations. M.C.F. and C.Z. conducted the low-T PL measurements. C.B.U., F.W., and C.Z. conducted the TRPL measurements. Y.J. conducted the ICP measurements. H.K.D.L, Y.J., and C.Z. conducted the SEM-EDX measurements. C.Z., J.J., and P.Y. organized the manuscript. All authors participated in discussing the results and providing various sections and comments for the paper. **Competing interests:** Lawrence Berkeley National Laboratory has filed a patent application related to this work for which P.Y. and C.Z. are inventors (U.S. Patent Application Ser. No: 63/509,821). The remaining authors declare no competing interests. **Data and materials availability:** All data needed to evaluate the conclusions in the paper are present in the paper or the supplementary materials. The crystallographic information files (CIF) have also been deposited in the Inorganic Crystal Structure Database under reference numbers CSD 2225998-2225999 and 2292758. These data can be obtained free of charge via <https://www.ccdc.cam.ac.uk/structures/>, or by emailing [data\\_request@ccdc.cam.ac.uk](mailto:data_request@ccdc.cam.ac.uk).

**Supplementary Materials:**

Materials and Methods

Figs. S1 to S44

Tables S1 and S8

Movie S1

References (61-67)