

UC Berkeley

UC Berkeley Previously Published Works

Title

Electrocatalytic CO₂ Reduction to Fuels: Progress and Opportunities

Permalink

<https://escholarship.org/uc/item/4wg61540>

Journal

Trends in Chemistry, 2(9)

ISSN

2589-7209

Authors

Resasco, Joaquin

Bell, Alexis T

Publication Date

2020-09-01

DOI

10.1016/j.trechm.2020.06.007

Peer reviewed

Electrocatalytic CO₂ Reduction to Fuels – Progress and Opportunities

Authors: Joaquin Resasco^{1,2}, Alexis T. Bell^{3,4*}

Affiliations:

1. Department of Chemical Engineering, University of California, Santa Barbara, Santa Barbara, California 93106, United States

2. McKetta Department of Chemical Engineering, The University of Texas at Austin, Austin, Texas 78712, United States

3. Department of Chemical Engineering, University of California, Berkeley, California 94720, United States

4. Joint Center for Artificial Photosynthesis, Material Science Division, Lawrence Berkeley National Laboratory, Berkeley, California 94720, United States

*Corresponding author: alexbell@berkeley.edu

Submitted to
Trends in Chemistry
March 30, 2020

Abstract

The electrochemical reduction of CO₂ remains an appealing option for storing renewable energy in a chemical form. Here, we assess progress in designing catalysts that convert CO₂ to high energy density products. We explain how reaction data can be reported to reflect the intrinsic properties of the catalyst. This analysis shows that limited advances have been made in improving the performance of Cu. We suggest that opportunities remain using bimetallic catalysts that are resistant to dealloying. While aqueous systems are instrumental to developing our understanding of this chemistry, gas-fed systems that operate at high current densities must be developed. Although obstacles remain for practical application of CO₂ reduction, advances in fundamental understanding made over the years give reason for optimism.

Copper catalysts for Electrochemical CO₂ reduction Electrochemical CO₂ reduction (CO₂R) provides a way to store energy from renewable sources of electricity in the form of chemical bonds.[1] Practical implementation of CO₂R is currently limited in large part by a lack of active and selective electrocatalysts to facilitate the reaction. Since the discovery that Cu electrodes are uniquely capable of catalyzing CO₂R to fuels and chemicals, many studies have focused on enhancing the catalytic performance of Cu.[2-5] The aim of this perspective is to evaluate the success of these catalyst discovery efforts and assess what further prospects and challenges await CO₂R. We begin by describing a way in which CO₂R rate measurements can be collected and reported to reflect the intrinsic behavior of a catalytic material. We use this methodology to determine whether various catalyst design strategies have been effective at enhancing the intrinsic activity of Cu and suggest new promising avenues. While our discussion centers on Cu catalysts in aqueous electrolytes, we suggest that gas-fed systems hold promise for practical applications. We hope that this assessment will help identify the areas for future research that will bring the prospect of practical electrochemical CO₂R closer to reality.

Important considerations when comparing CO₂R electrocatalysts

Metrics for evaluating catalyst performance

We begin by defining what is meant by catalyst performance for CO₂R and how it should be described most appropriately.[6] This will allow us to accurately assess the effectiveness of catalyst design strategies. A commonly used metric is the Faradaic efficiency (FE), which measures the fraction of the total current used to produce a specific product. An increase in the FE to a given product should not be used to suggest an increase in catalytic activity for forming that product without demonstrating that the rate, described by the partial current density to that product, has also increased.[6]

Another important point is that current density or partial current density to a given product is typically reported with respect to the geometric area of the electrode; however, this metric is dependent on catalyst loading and the specific surface area of the catalyst. If twice the number of catalytic sites are loaded onto a given electrode area, the geometric rate of reaction will

correspondingly double. Therefore, to understand the performance of a catalyst it is important to know its electrochemically active surface area (ECSA). While different methods for evaluating surface area or number of sites exist, each with its own strengths and limitations, most forms of normalization yield a much more satisfactory evaluation of activity than activity reported without any sort of normalization.[7, 8] Normalization of catalytic activity based on number of catalyst active sites is standard practice in thermal catalysis, and has been widely adopted for other electrocatalytic reactions such as the water electrolysis and fuel cell reactions.[9-12] Adopting these standard practices would greatly facilitate objective evaluation of CO₂R catalysts and aid in identification of promising new materials.

Mass transport limitations

Because the solubility of CO₂ and its mass transport coefficient in aqueous electrolytes are low, the CO₂R reaction becomes mass-transport limited even at relatively low current densities. [13, 14] Transport limitations also affect the measured product distribution, complicating the assessment of the intrinsic catalyst properties. Under conditions of moderate polarization, hydroxide ions produced at the cathode surface increase the near-surface pH. This change affects the product selectivity, since rates of CH₄ and C₂H₄ formation exhibit different dependencies on the electrolyte pH.[15-18] As electrolyte pH increases, the partial current density for CH₄ decreases whereas the C₂H₄ partial current density remains constant when the rates are compared on an SHE scale. By contrast, the CH₄ partial current density remains constant while the C₂H₄ partial current density increases as the electrolyte pH increases when the pH-dependent RHE scale is used. These trends are explained by the nature of the kinetically relevant step involved in forming the two products. The C-C bond formation step for forming C₂H₄ does not involve a proton transfer, thus C₂H₄ rates are independent of proton concentration on an absolute potential scale (SHE).[19-23] On the other hand, the formation of CH₄ involves a coupled proton-electron transfer (or alternatively, the transfer of a hydrogen atom via reaction of an electron with water) in the kinetically relevant CO hydrogenation step, and therefore, CH₄ formation rates depend on proton activity.[24] Under sufficiently high polarization, the CO₂ concentration at the cathode surface is depleted and the product distribution shifts toward hydrogen and methane. This is likely due to a reduced surface coverage of CO relative to H.[13, 17, 25] Therefore, the

distribution of products observed under conditions of significant mass transport limitations are a convolution of the intrinsic catalyst kinetics and the dynamics of mass transport. These factors indicate that research focused on identifying catalysts with higher intrinsic activity should be carried out at low current densities where transport limitations are negligible. Tests for the effects of external mass transport limitations can be conducted by varying the extent of mixing in the cell, to assure that catalyst activity is measured under kinetic control.[6, 26] Without these demonstrations, the possibility of mass transport limitations should always be considered along with their effect on measured performance.

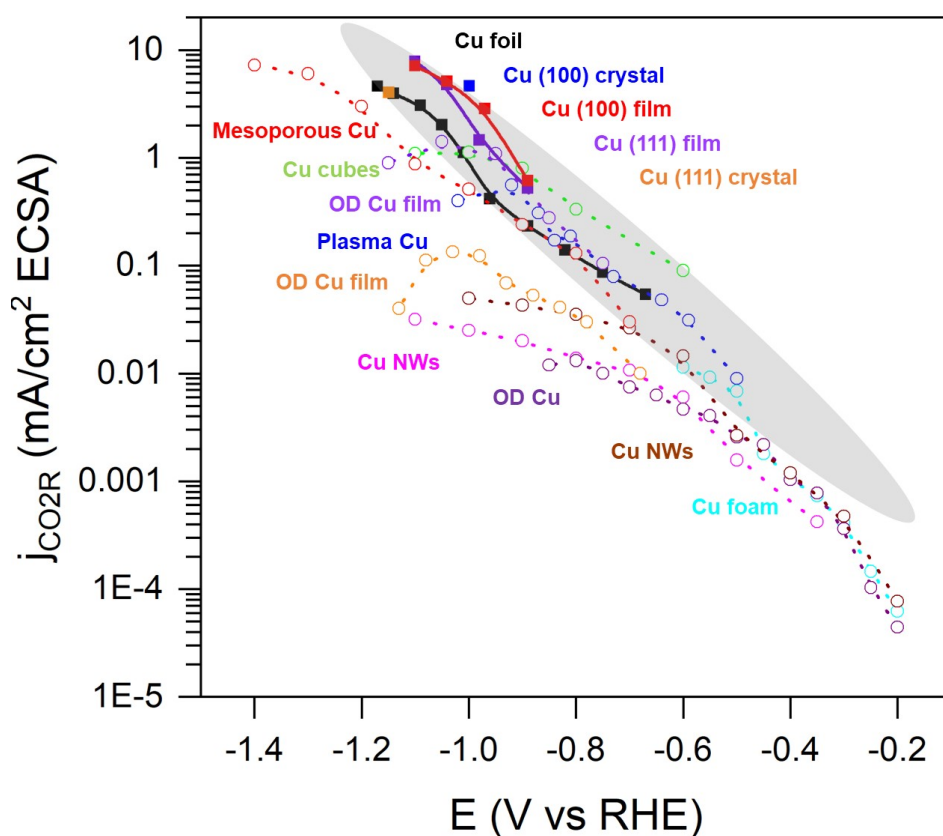


Figure 1: Effects of Cu facets and nanostructure on ECSA normalized activity for CO₂R.

Comparison of overall CO₂R activity normalized to surface area for various nanostructured Cu electrocatalysts with Cu standards. The data were obtained from the following studies: Cu foil Kuhl et al. [27]; Cu (111) and (100) crystals Hori et al.[28]; Cu (111) and (100) films Hahn et al.[29]; Cu cubes Kwon et al.[30]; Plasma Cu Mistry et al.[31]; Cu foam Min et al.[32]; Cu NWs Ma et al.[33]; OD Cu Li et al.[34]; Cu NWs Raciti et al.[35]; OD Cu film Handoko et al.[36]; OD Cu film Ren et al.[37]; Mesoporous Cu Yang et al.[38]. The gray region indicates the approximate Tafel behavior of Cu standards and illustrates that no nanostructured catalyst shows significantly higher reactivity than these standards. Adapted with permission from Nitopi et al.[3].

Evaluating progress in improving the performance of Cu catalysts for aqueous CO₂ reduction

The preceding sections provide guidelines for how the intrinsic behavior of electrocatalysts for CO₂R can be assessed. Catalytic activity should be measured under conditions that mass transport limitations do not significantly affect rates and reported as partial current densities normalized by catalyst surface area or number of catalytic sites. Having established a method for clearly comparing catalytic performance, we now examine the effectiveness of common catalyst design strategies for improving the performance of Cu.

Modifying Activity and Selectivity of Cu Catalysts through Nanostructuring

Many investigators have examined the effects of surface faceting and roughening (referred to collectively as nanostructuring) on the activity and selectivity of Cu for CO₂R.[3, 27-42] The first question is whether surface roughening affects the intrinsic CO₂R activity of Cu. As noted above, surface roughness results in a higher geometric activity (i.e., current density normalized to the geometric surface area of the electrode) due to an increase in the catalyst surface area relative to that of a planar electrode. Figure 1 illustrates the ECSA-corrected current densities for CO₂R for a large number of Cu catalysts prepared in different ways.[3, 6] For cathode voltages below c.a. - 0.6 V vs RHE the Tafel slope is similar for different preparations of Cu, suggesting that the CO₂R activity of these catalysts is essentially the same. The deviation from Tafel-like behavior observed for each sample at higher applied potential reflects the effects of mass transport limitations. In all these cases, the FE for the HER rises relative to that for CO₂R. The rougher the surface, the lower the applied potential at which the onset of this effect occurs because the onset of transport limitations depends on the total current density and not the ECSA-based current density.[6] No nanostructured catalysts show significantly higher activity than Cu standards (single crystals, metal foils, and oriented thin films). Therefore, the lack of evidence for higher intrinsic activity of nanostructured catalysts suggests that modifying the surface topography of Cu is not a useful tool for significantly enhancing the intrinsic CO₂R activity of Cu. We note that the same conclusion has been reached by other authors.[3, 43]

While roughening Cu surfaces produces insignificant changes in the total CO₂R ESCA-based current density, it can affect the distribution of products formed. Figure 2 shows that increasing roughness of Cu surfaces, produced by electrochemical reduction of electropolished Cu pretreated in an Ar, O₂, or N₂ plasma or nitrated at high-temperature to form Cu₃N, increases the ratio of C₂₊ products and the ratio of oxygenated to hydrocarbon products. These changes are independent of the roughening procedure. This high selectivity can result from restructuring of the surface to present (100) terminations, as this crystal facet has been shown to be selective to C₂ products.[16, 28, 30, 40] Consistent with this, the ECSA normalized partial current density to C₂H₄ of a range of high surface area Cu catalysts is very similar to that of Cu (100) oriented films.[6] Selectivity increases to C₂₊ products with roughening are instead often the result of decreased TOFs to H₂ and CH₄, rather than increases in TOF to C₂ species.[6] Finally, under conditions where mass transport limitations are significant, local pH changes at the electrode-electrolyte interface can further increase the C₂₊/C₁ selectivity.

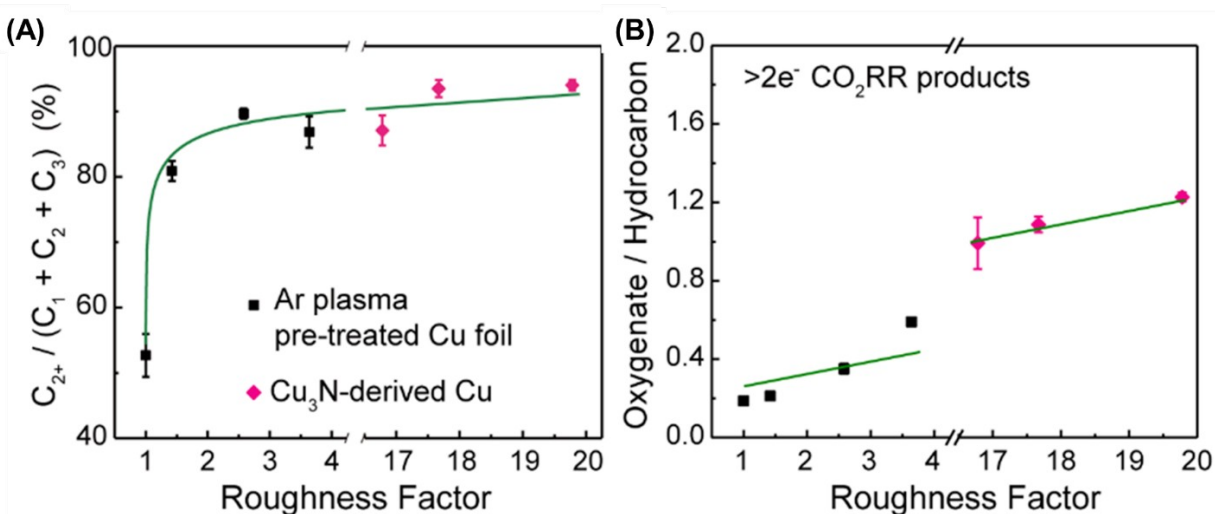


Figure 2: Effects of Cu roughening on CO₂R product distribution. (A) C₂₊ product selectivity and (B) Faradaic efficiency ratio of oxygenate versus hydrocarbon products for physically roughened Cu foils obtained by Ar-plasma pretreatment and Cu₃N-derived Cu electrodes prepared with different annealing times; all measurements were made at a cathode potential of -1 V vs RHE, in 0.1 M CO₂-saturated CsHCO₃. Adapted with permission from Ebaid et al. [40]

Modifying reactivity of Cu catalysts through change in composition

Bimetallic catalysts

Research has been done to determine whether the CO₂R activity and selectivity of Cu can be modified by forming a bimetallic alloy. Combining Cu with a second metal can influence reactivity through both electronic and geometric effects.[44] Electronic effects result from modification of the electronic structure of Cu through interaction with the second metal. This in turn influences the interaction of Cu with adsorbates.[45] Modifications that reduce the electron density of Cu d-states near the Fermi level weaken the interactions of adsorbates with Cu, whereas an increase in populated d-states near the Fermi level leads to stronger interactions.[45] Electronic effects can be caused by charge transfer between the two metals (ligand effect) or a modification in the lattice constant of Cu upon addition of a second metal (strain effect).[46] Changes in the lattice constant result in differences in orbital overlap between metal atoms and thus the broadness of the density of electronic states of the metal. To maintain orbital occupancy constant, a change in the broadness of the metal d-band results in a shift in its position relative to the Fermi level, thereby modifying metal-adsorbate interactions.[47] Geometric effects include changes in the atomic arrangement of active sites (ensemble effects) and the creation of bifunctional active sites where neighboring metals serve different catalytic roles. For instance, the addition of an oxophilic modifier to a Cu surface could potentially modify its activity by preferential stabilization of oxygenated intermediates through interaction of the oxygen functionality with this second metal.[48]

Similar to the case for nanostructured catalysts, previous studies have shown that the turnover frequency (catalytic rate per catalytic site per unit time) of Cu for both forming multicarbon products, and separately for forming 2e⁻ products (CO and HCOO⁻), is not enhanced significantly by addition of a second metal (see Ref. 3 and references therein). Unfortunately, the small number of studies reporting electrochemically active surface areas for bimetallic Cu catalysts limits systematic comparison of the intrinsic activity of such catalysts.[49, 50]

It is interesting to consider why extensive studies of bimetallic catalysts have not yielded larger improvements in activity. A plausible explanation is that this is due to the difficulty in controlling bimetallic surface composition through synthesis, handling, and reaction testing. Cu forms relatively weak alloys with many transition metals. This means that the energetic benefit

for mixing a second metal with Cu is low. In contrast, the energetic benefit from adsorption of gas phase species onto these metal surfaces can be much higher. For example, if Cu is mixed with a more reactive metal (such as Ni, Fe, Pt) the energy gained by adsorbing CO, the most abundant reaction intermediate formed during CO₂R over Cu, onto the more reactive metal is much larger than the free energy of formation of the alloy. This suggests that CO formation will drive surface segregation of the more reactive metal and result in a surface composition that is different from the bulk composition. This has been observed for alloys of Cu under CO₂ hydrogenation conditions.[51, 52] Consistent with this proposition, most alloys of Cu with reactive metals have yielded product distributions much more representative of the reactive metal (i.e., high selectivity to HER) than the product distribution associated with Cu.[53] For Cu mixed with oxophilic metals (such as Zn, Sn, In) the enthalpy of formation of a monometallic oxide of the oxophilic metal is much larger than the alloy formation energy of the metals. Consequently, the alloy catalyst is likely terminated with a monometallic oxide layer after exposure to air and potentially the electrolyte. When a reducing potential is applied this metal oxide reduces, but it is unclear to what extent re-alloying of the two metals occurs under conditions of CO₂R. Again, the product distributions for this class of bimetals have generally not been representative of Cu catalysts, with bimetals showing high selectivity to 2e⁻ reduction products, CO and HCOO⁻. [54-56] While probing these surface compositional changes under relevant conditions is difficult, as the presence of the electrolyte strongly attenuates the signal from most surface sensitive compositional probes, it appears from the reactivity of these catalysts that the surface compositions intended is not realized.

Non-metallic modifiers

In addition to modifying the composition of Cu through alloying with a second metal, many studies have explored the use of non-metal dopants (e.g. oxygen, sulfur, nitrogen).[34, 57-61] A number of authors have proposed that upon reduction of oxidized Cu, subsurface oxygen is retained, resulting in the creation of Cu sites that are particularly active for formation of C₂₊ products.[31, 61-66] However, both experimental and theoretical studies strongly suggest that subsurface oxygen is not retained under the aggressively reducing conditions used for CO₂R (e.g., cathode voltages of -1 V vs RHE).[67-69] Similar behavior has been shown for dopants

such as sulfur and nitrogen.[58, 59] Therefore, while dopants can be introduced into Cu, their impact on steady state catalytic performance is not significant.

Status of catalyst design efforts

We have shown that despite extensive efforts, catalyst design strategies aimed at improving the intrinsic catalytic activity of Cu for CO₂R have been largely ineffective. Given the wealth of studies on these materials we emphasize the importance of accurately assessing intrinsic catalytic behavior. New candidate catalysts should show enhanced activity (normalized to the number of catalytic sites) under conditions free of transport limitations before investigations of unique properties of the candidate catalyst are warranted. Given the challenges in enhancing the intrinsic activity of Cu, we now suggest remaining avenues to do so, and consider alternative methods for improving the overall performance of electrochemical CO₂R systems.

Opportunities for further improvements of the performance of Cu catalysts

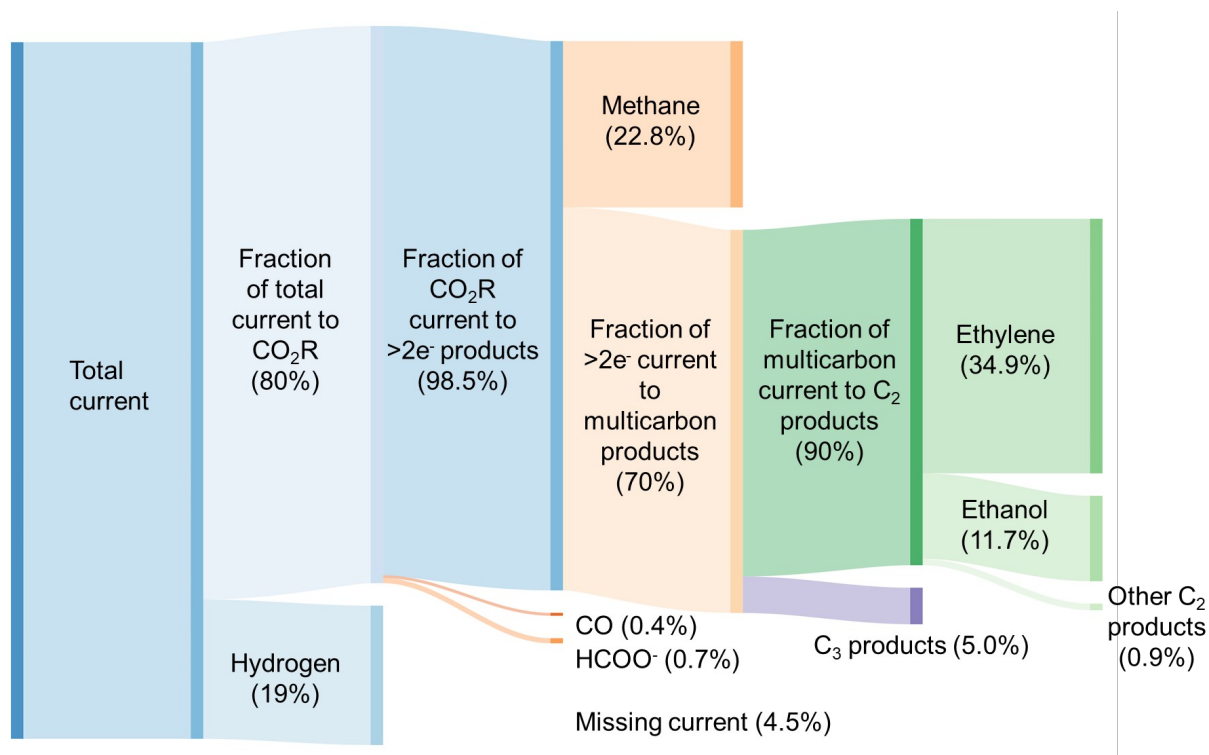


Figure 3: Understanding the product distribution of Cu for CO₂R. Sankey diagram showing the breakdown of current for Cu (100) at -1.04 V vs RHE. Note that fractions of current are distinct from

overall Faradaic efficiencies. Total current efficiency is 95.5%, and missing current is 4.5%. Adapted with permission from Hahn et al.[29]

The distribution of total current to different products formed over a Cu (100) surface at ~ -1 V vs RHE, is shown in Figure 3. This plot helps us identify what improvements might be made in the performance of Cu-based catalysts.[29] The first deduction is that a significant fraction of the total current is lost to hydrogen evolution; thus, catalysts that inhibit the propensity of Cu to produce hydrogen are desirable. Secondly, while nearly all the CO produced at this potential is further reduced, a certain fraction is lost to methane, an undesired product due to its low cost and volumetric energy density. A significant fraction of current goes to C_{2+} products, primarily ethylene, ethanol, and a smaller proportion of propanol. While ethanol and propanol are useful as fuels, their separation from water is energy intensive.[70] Therefore, for systems with an aqueous electrolyte it would be desirable to achieve high selectivity to ethylene, the most abundant C_2 product formed over Cu. It would also be desirable to find catalyst compositions and structures that could produce higher alcohols and alkenes. Propylene and butene are valuable molecules, but no catalysts currently produce these products in measurable yields. The selective formation of butanol would also be attractive since this alcohol would phase separate from water at concentrations above 9%. To target specific multicarbon products, it is important to understand which elementary steps in the reaction network control the growth of C-C bonds and which bifurcate between different products (hydrocarbons and oxygenates). Few studies have examined the reaction mechanism after the first C-C coupling step.[22, 71] In summary, future effort on catalyst development should focus on lowering the kinetic overpotential for CO_2 reduction to CO and C-C coupling and enhancing the selectivity for CO_2R relative to that for HER. Tuning of the product selectivity towards specific multicarbon products will likely be difficult as these steps occur after the kinetically difficult first C-C coupling step, but further investigation of the reaction elementary steps past this point are needed. With these goals in mind, we discuss some possibilities for influencing the performance of CO_2R systems.

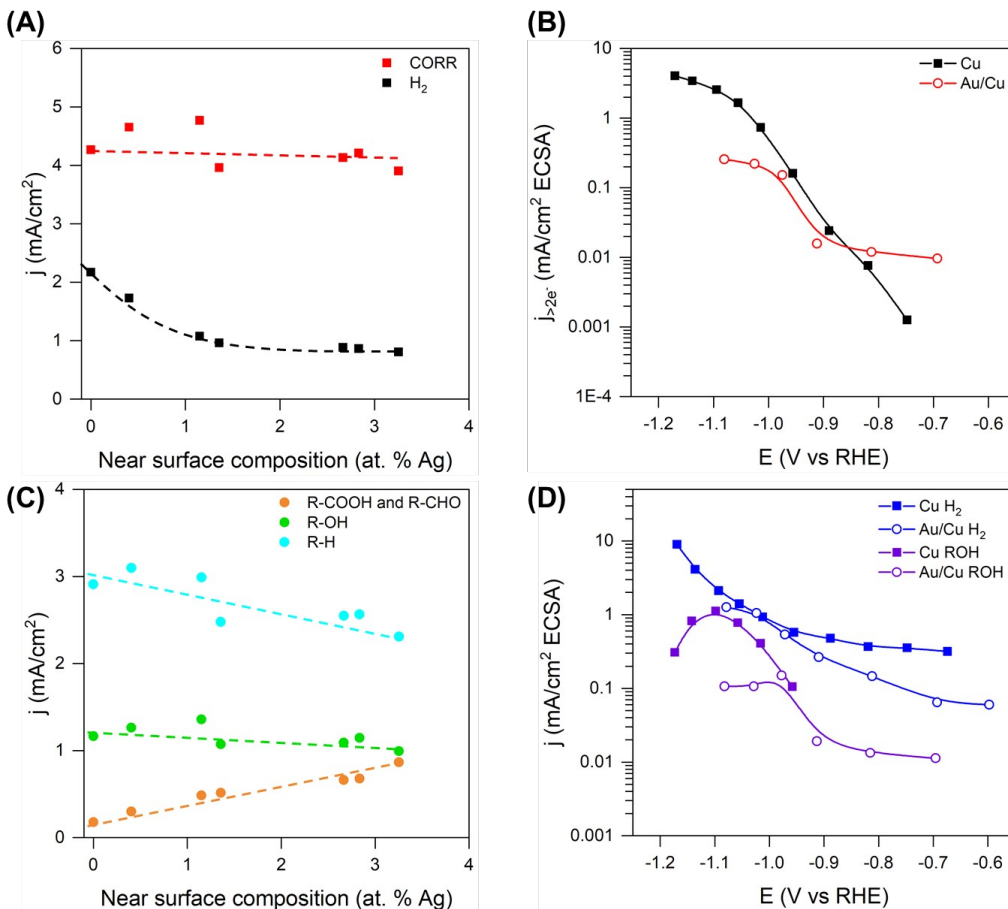


Figure 4: Effects of surface alloying on the product distribution of Cu catalysts. A) and C) show the effect of addition of Ag into the surface of a Cu(100) oriented thin film. While overall rates of $>2e^-$ -products (CO reduction products) are relatively unaffected, rates of hydrogen evolution and hydrocarbon formation are reduced with Ag incorporation, while the rates of carbonyl and carboxylic acid formation are enhanced. B) and D) show the effect of Au addition to the product distribution of Cu. While the total activity to forming $>2e^-$ -products is similar for all but the lowest potentials, the distribution of products is changed by Au addition, mainly due to lower rates of hydrogen evolution. Figures adapted with permission from Clark et al.[49] and Morales-Guio et al.[50].

Prospects for surface alloys

While demonstrable improvements in the overall activity of Cu catalysts through alloying are lacking, there are still opportunities for modifying the reactivity of Cu through the addition of a second metal. As mentioned above, bulk Cu alloys suffer from surface segregation, which result in a composition at the surface that is different from that in the bulk. One way to mitigate this issue is through the formation of a surface alloy, a catalyst in which the bulk is Cu and only the topmost layer of Cu contains a second metal. Since the second metal is not present in the bulk, adsorbates produced during reaction or pretreatment will not allow the formation of a shell of the

second metal. Few previous reports have studied the behavior of such materials for CO₂R. Notably, surface alloys of Cu and Ag have been shown to tune the product distribution over Cu without compromising overall activity.[49] The introduction of larger Ag atoms into the Cu lattice results in compressive strain. This strain leads to preferential destabilization of adsorbed hydrogen, resulting in a product distribution that favors oxygenates over more hydrocarbon products. Figure 4 illustrates similar shifts in product distribution towards alcohols and away from hydrocarbons for Au-promoted Cu.[50] In addition to this strain effect, these surface-modifying atoms can impact reactivity through electron transfer with Cu, ensemble effects, and by providing bifunctionality.[48] The fundamental properties of surface alloys of Cu have been studied in some detail in the context of so-called single atom alloys.[72-76] We suggest that this class of materials could yield interesting and enhanced performance for Cu catalysts.

Targeting other products of CO₂R

It is possible that the most efficient route for forming fuels and chemicals will not be via direct electrocatalytic reduction of CO₂. For example, selective production of CO from CO₂R and H₂ from water splitting can produce syngas that can be converted to a range of valuable products through well-established thermochemical routes. Figure 5 shows some possible pathways to produce fuels and chemicals from CO₂. It seems unlikely that direct production of syngas from CO₂R (i.e., unselective production of CO combined with HER) will be the most efficient approach, as the activity for HER under CO₂R conditions and catalysts is very low compared to the performance of conventional HER.[77] Preliminary assessments of the technoeconomic feasibility of obtaining different products from CO₂ have been reported by several authors.[78-80] While these analyses show that molecular building blocks which can be produced with high selectivity are most desirable, the conclusions are sensitive to both the model inputs and catalyst performance. Recent studies have also examined the possibility of coupling electrocatalytic CO₂R to biochemical processes to produce commodity chemicals and fuels that are currently inaccessible through direct CO₂R (e.g. isopropanol, butanol, 3-methyl-1-butanol).[81] Due to the uncertainty concerning which processes will be most impactful in practice, we suggest that the development of active, selective, and durable catalysts for producing different products of CO₂R (CO, HCOO⁻, multicarbon products) should continue.

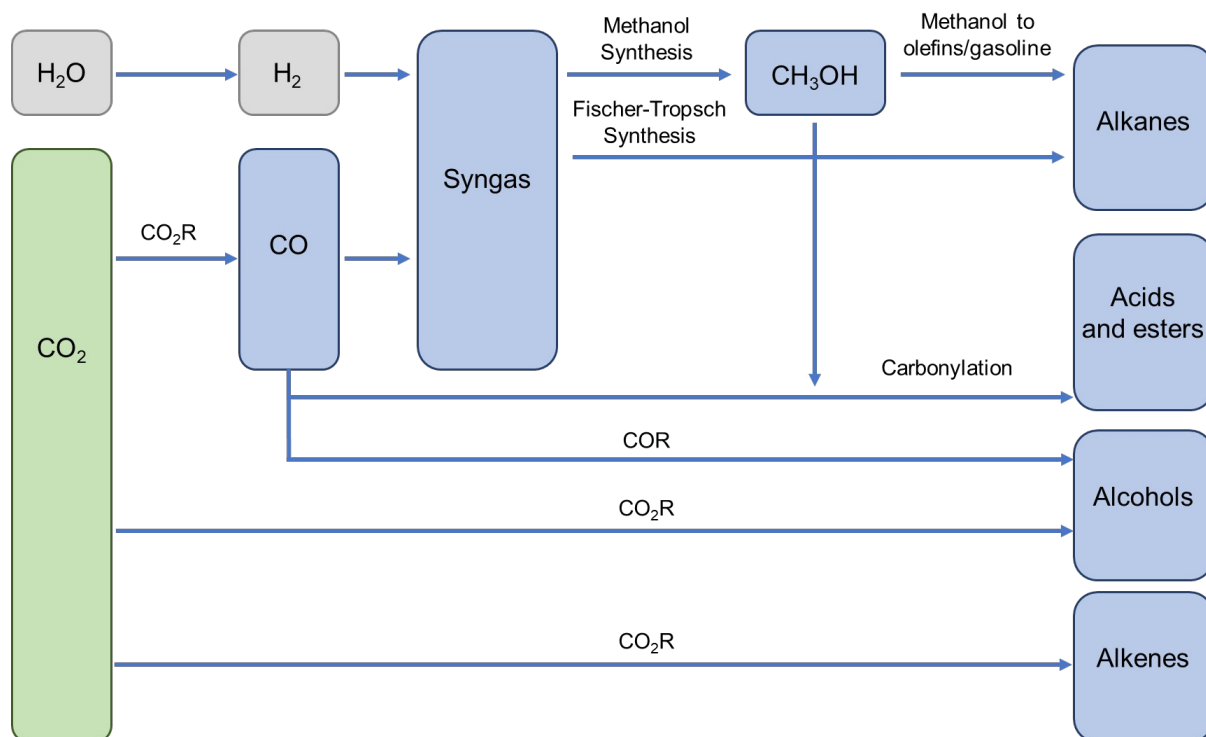


Figure 5: Possible routes to fuels and chemicals using CO₂R. Possible routes to renewable commodity chemicals driven by electrocatalysis from H₂O and CO₂ as feedstocks. Adapted with permission from De Luna et al.[78]

Enhancing the performance of CO₂ reduction beyond aqueous systems

Non-aqueous, liquid phase systems

The use of non-aqueous solvents to enhance the performance of CO₂R systems has been suggested.[82] The proposed benefits are often based on the higher solubility of CO₂ in solvents such as methanol or acetonitrile. While initially appealing, it is not clear that increased CO₂ solubility should fundamentally enhance CO₂R rates. The kinetic rate of CO₂R is dependent on the chemical potential of the reactant, dissolved CO₂, rather than its concentration.[83] As the solution is in phase equilibrium with the gas phase, the chemical potential of CO₂ in solution is equal to that of CO₂ in the gas phase. If the solvent is changed, the chemical potential of dissolved CO₂ remains fixed to the chemical potential of the gas it is in equilibrium with (i.e., 1 bar CO₂). Therefore, CO₂R kinetic rates should be independent of CO₂ solubility.

However, solvent composition can influence the kinetics of CO₂R.[84-86] The solvent may preferentially stabilize kinetically relevant transition states relative to their precursor state.[20,

87] If both reactant and transition states are similarly stabilized, the solvent will have no effect on activation barriers.[88] In cases where solvents influence measured rates, it is important to decouple the effects of solvent composition on intrinsic reaction kinetics from other effects. For example, water or a proton source is needed to yield hydrogenated products (i.e., products besides CO and oxalate) when aprotic solvents are used.[1] However, the addition of water makes it difficult to understand the electrode-electrolyte interface and what effects dominate observed reaction rates. More studies should be undertaken aimed at understanding the effects of solvent composition and how it can be used to tune activity and selectivity of Cu for CO₂R.

The promise of gas-fed reactor systems

While planar electrode assemblies (PEAs) are well suited for developing a deeper understanding of CO₂R and identifying promising electrocatalysts, they are not well suited for practical applications. The maximum current density attainable in a PEA is limited by mass transport through the electrolyte (< 10 mA/cm²).[13] For CO₂R to be commercially viable, it is necessary to operate at current densities > 100 mA/cm². [80] This is achievable using gas-diffusion electrodes (GDEs), which exhibit significantly lower mass-transfer resistances for CO₂ and ion transport.[89-103] For practical application of CO₂R, it is also desirable to eliminate aqueous electrolytes, since at high current densities, the ohmic losses associated with the electrolyte contribute significantly to a loss of energy efficiency. This can be done using a membrane electrode assembly (MEA).[104, 105] In an MEA the catalyst layer (CL) is deposited onto a polymeric electrolyte or onto a gas diffusion layer (GDL) to form a GDE, which is then bonded to the electrolyte membrane. To provide pathways for ions to transit from the membrane to the CL in an MEA system, the nanoparticles of catalyst in the CL are coated with a thin layer of ionomer. Typically, this material has the same composition as the membrane. However, little is known about how the ionomer-catalyst interface influences the progress of reactions occurring on the catalyst surface. Understanding how ionomers influence catalytic activity could provide a means for controlling CO₂R through targeted modification of ionomer functionalities. These modifications could leverage recently developed understanding of how the reaction environment influences catalysis in the liquid phase.[17, 106, 107] There are additionally open questions in understanding mass transport and water management in these systems.[95, 104, 105, 108] We

anticipate that investigation of these questions will benefit from knowledge gained in the development of more mature electrochemical technologies, such as fuel cells and electrolyzers. It is also worth noting that high temperature CO₂R in solid-oxide electrolysis cells represents an alternative and promising approach to low temperature systems.[109]

Concluding remarks

Producing high-value fuels and chemicals in a sustainable way via electrochemical CO₂R coupled with a renewable source of electricity remains an attractive goal. In this perspective, we have summarized the state of catalyst design efforts for Cu catalysts capable of producing valuable products and future opportunities for enhanced performance.

While limited advances have been made in improving the intrinsic activity of Cu catalysts, opportunities still exist for the development of CO₂R systems. To improve the activity of Cu catalysts, bimetallic catalysts that mitigate the problems introduced by surface segregation should be investigated more thoroughly. Stable surface alloys of Cu should enable the formation of multicarbon products while modifying the selectivity and activity compared to pure Cu. While direct production of hydrocarbons or alcohols is particularly appealing, it is also possible that the most efficient systems may make use of tandem processes where CO₂ is first converted to CO, followed by further transformation.[110]

In parallel to the development of new active and selective catalysts, work should continue on the development of gas-fed CO₂R reactor systems capable of operation at high current densities. These systems have already shown promising performance. We expect that increased fundamental understanding of the transport processes in these reactors, and the nature of the environment surrounding catalytic active sites will help in the design of reactor components (catalysts, membranes, supports, electrolytes) and the choice of operating conditions.

While many challenges remain in the development of CO₂R systems with sufficient activity, selectivity, stability, and scalability for practical application, there is reason to remain optimistic. Significant progress has been made in developing fundamental understanding of this process, and we expect that with continued research, the electrochemical reduction of CO₂ will enable sustainable production of chemicals and fuel.

Outstanding questions

- Extensive efforts aimed at increasing the intrinsic catalytic activity of Cu catalysts for producing multicarbon products from CO₂ have been largely unsuccessful. How do we design stable and active catalysts that are selective for desired multicarbon products?
- The environment surrounding catalytic active sites can significantly affect measured performance. How can we develop experimental and computational tools for understanding effects of the electrochemical environment on catalysis, both in aqueous and non-aqueous systems?
- How can we leverage knowledge from fuel cell and electrolyzer technologies to rapidly develop highly efficient gas-fed CO₂ reduction systems?

Highlights

- Standard practices are necessary for accurate assessment of catalytic performance for CO₂ reduction
- Catalyst design efforts aimed at improving the activity of Cu for CO₂ reduction have been largely unsuccessful
- Opportunities remain for modifying Cu through formation of surface alloys
- For practical application of CO₂ reduction, transition to gas-fed systems is necessary
- Increasing fundamental understanding of surface chemistry will continue to aid the development of efficient CO₂ reduction systems

Glossary

Faradaic efficiency (FE): The fraction of total charge used in a specific Faradaic process (to produce a certain product).

Mass transport limitations: For reaction to occur, reactants must be transported to and products transported from the catalyst surface. When surface reaction rates become sufficiently high, overall measured rates will be influenced by these transport processes, masking the intrinsic kinetic behavior of the catalyst surface. Under conditions of mass transport limitations, the conditions in the electrolyte (pH, concentration of CO₂) near the catalyst surface will differ significantly from the bulk solution.

Tafel slope: Defined by the Tafel equation that relates applied potential and current density:

$$\eta = a + b \log(j)$$

Where η is the overpotential or the difference between the electrode potential and the standard potential, a is the exchange current density, b is the Tafel slope, and j is the current density. The Tafel slope quantifies the sensitivity of the current density to the applied potential. In principle,

experimentally observed Tafel slopes can be compared with theoretically derived slopes based on a microkinetic model.

Turnover frequency (TOF): The number of molecules of a specified product made per catalytic site per unit time. TOFs generally depend on electrode potential, reactant concentration, temperature, etc.

Conflict of interest statement: The authors declare no conflicts of interest.

References

- [1] Y. Hori, Electrochemical CO₂ Reduction on Metal Electrodes, in: C.G. Vayenas, R.E. White, M.E. Gamboa-Aldeco (Eds.) *Modern Aspects of Electrochemistry*, Springer New York, New York, NY, 2008, pp. 89-189.
- [2] Y. Hori, A. Murata, R. Takahashi, Formation of hydrocarbons in the electrochemical reduction of carbon dioxide at a copper electrode in aqueous solution, *Journal of the Chemical Society, Faraday Transactions 1: Physical Chemistry in Condensed Phases*, 85 (1989) 2309-2326.
- [3] S. Nitopi, E. Bertheussen, S.B. Scott, X. Liu, A.K. Engstfeld, S. Horch, B. Seger, I.E.L. Stephens, K. Chan, C. Hahn, J.K. Nørskov, T.F. Jaramillo, I. Chorkendorff, Progress and Perspectives of Electrochemical CO₂ Reduction on Copper in Aqueous Electrolyte, *Chemical Reviews*, 119 (2019) 7610-7672.
- [4] M. Gattrell, N. Gupta, A. Co, A review of the aqueous electrochemical reduction of CO₂ to hydrocarbons at copper, *Journal of electroanalytical Chemistry*, 594 (2006) 1-19.
- [5] R. Kortlever, J. Shen, K.J.P. Schouten, F. Calle-Vallejo, M.T.M. Koper, Catalysts and Reaction Pathways for the Electrochemical Reduction of Carbon Dioxide, *The Journal of Physical Chemistry Letters*, 6 (2015) 4073-4082.
- [6] E.L. Clark, J. Resasco, A. Landers, J. Lin, L.-T. Chung, A. Walton, C. Hahn, T.F. Jaramillo, A.T. Bell, Standards and Protocols for Data Acquisition and Reporting for Studies of the Electrochemical Reduction of Carbon Dioxide, *ACS Catalysis*, 8 (2018) 6560-6570.
- [7] S. Trasatti, O. Petrii, Real surface area measurements in electrochemistry, *Pure and applied chemistry*, 63 (1991) 711-734.
- [8] M. Łukaszewski, M. Soszko, A. Czerwiński, Electrochemical methods of real surface area determination of noble metal electrodes—an overview, *International Journal of Electrochemical Science*, 11 (2016) 4442-4469.
- [9] M. Boudart, Turnover Rates in Heterogeneous Catalysis, *Chemical Reviews*, 95 (1995) 661-666.
- [10] C.C.L. McCrory, S. Jung, J.C. Peters, T.F. Jaramillo, Benchmarking Heterogeneous Electrocatalysts for the Oxygen Evolution Reaction, *Journal of the American Chemical Society*, 135 (2013) 16977-16987.
- [11] C.C.L. McCrory, S. Jung, I.M. Ferrer, S.M. Chatman, J.C. Peters, T.F. Jaramillo, Benchmarking Hydrogen Evolving Reaction and Oxygen Evolving Reaction Electrocatalysts for Solar Water Splitting Devices, *Journal of the American Chemical Society*, 137 (2015) 4347-4357.

- [12] H.A. Gasteiger, S.S. Kocha, B. Sompalli, F.T. Wagner, Activity benchmarks and requirements for Pt, Pt-alloy, and non-Pt oxygen reduction catalysts for PEMFCs, *Applied Catalysis B: Environmental*, 56 (2005) 9-35.
- [13] M.R. Singh, E.L. Clark, A.T. Bell, Effects of electrolyte, catalyst, and membrane composition and operating conditions on the performance of solar-driven electrochemical reduction of carbon dioxide, *Physical Chemistry Chemical Physics*, 17 (2015) 18924-18936.
- [14] K. Yang, R. Kas, W.A. Smith, Tenacious Mass Transfer Limitations Drive Catalytic Selectivity during Electrochemical Carbon Dioxide Reduction, *ChemRxiv* (2019) <https://doi.org/10.26434/chemrxiv.7770338.v1>.
- [15] Y. Hori, R. Takahashi, Y. Yoshinami, A. Murata, Electrochemical Reduction of CO at a Copper Electrode, *The Journal of Physical Chemistry B*, 101 (1997) 7075-7081.
- [16] F.S. Roberts, K.P. Kuhl, A. Nilsson, Electroreduction of Carbon Monoxide Over a Copper Nanocube Catalyst: Surface Structure and pH Dependence on Selectivity, *ChemCatChem*, 8 (2016) 1119-1124.
- [17] J. Resasco, Y. Lum, E. Clark, J.Z. Zeledon, A.T. Bell, Effects of Anion Identity and Concentration on Electrochemical Reduction of CO₂, *ChemElectroChem*, 5 (2018) 1064-1072.
- [18] L. Wang, S.A. Nitopi, E. Bertheussen, M. Orazov, C.G. Morales-Guio, X. Liu, D.C. Higgins, K. Chan, J.K. Nørskov, C. Hahn, Electrochemical carbon monoxide reduction on polycrystalline copper: Effects of potential, pressure, and pH on selectivity toward multicarbon and oxygenated products, *ACS Catalysis*, 8 (2018) 7445-7454.
- [19] J.H. Montoya, A.A. Peterson, J.K. Nørskov, Insights into C-C Coupling in CO₂ Electroreduction on Copper Electrodes, *ChemCatChem*, 5 (2013) 737-742.
- [20] J.H. Montoya, C. Shi, K. Chan, J.K. Nørskov, Theoretical Insights into a CO Dimerization Mechanism in CO₂ Electroreduction, *The Journal of Physical Chemistry Letters*, 6 (2015) 2032-2037.
- [21] R.B. Sandberg, J.H. Montoya, K. Chan, J.K. Nørskov, CO-CO coupling on Cu facets: Coverage, strain and field effects, *Surface Science*, 654 (2016) 56-62.
- [22] J.D. Goodpaster, A.T. Bell, M. Head-Gordon, Identification of Possible Pathways for C-C Bond Formation during Electrochemical Reduction of CO₂: New Theoretical Insights from an Improved Electrochemical Model, *The Journal of Physical Chemistry Letters*, 7 (2016) 1471-1477.
- [23] X. Liu, P. Schlexer, J. Xiao, Y. Ji, L. Wang, R.B. Sandberg, M. Tang, K.S. Brown, H. Peng, S. Ringe, C. Hahn, T.F. Jaramillo, J.K. Nørskov, K. Chan, pH effects on the electrochemical reduction of CO₂ towards C₂ products on stepped copper, *Nature Communications*, 10 (2019) 32.
- [24] X. Liu, J. Xiao, H. Peng, X. Hong, K. Chan, J.K. Nørskov, Understanding trends in electrochemical carbon dioxide reduction rates, *Nature communications*, 8 (2017) 15438.
- [25] E.L. Clark, A.T. Bell, Direct Observation of the Local Reaction Environment during the Electrochemical Reduction of CO₂, *Journal of the American Chemical Society*, 140 (2018) 7012-7020.
- [26] R.J. Madon, M. Boudart, Experimental criterion for the absence of artifacts in the measurement of rates of heterogeneous catalytic reactions, *Industrial & Engineering Chemistry Fundamentals*, 21 (1982) 438-447.
- [27] K.P. Kuhl, E.R. Cave, D.N. Abram, T.F. Jaramillo, New insights into the electrochemical reduction of carbon dioxide on metallic copper surfaces, *Energy & Environmental Science*, 5 (2012) 7050-7059.

- [28] Y. Hori, I. Takahashi, O. Koga, N. Hoshi, Selective Formation of C₂ Compounds from Electrochemical Reduction of CO₂ at a Series of Copper Single Crystal Electrodes, *The Journal of Physical Chemistry B*, 106 (2002) 15-17.
- [29] C. Hahn, T. Hatsukade, Y.-G. Kim, A. Vailionis, J.H. Baricuatro, D.C. Higgins, S.A. Nitopi, M.P. Soriaga, T.F. Jaramillo, Engineering Cu surfaces for the electrocatalytic conversion of CO₂: Controlling selectivity toward oxygenates and hydrocarbons, *Proceedings of the National Academy of Sciences*, 114 (2017) 5918-5923.
- [30] Y. Kwon, Y. Lum, E.L. Clark, J.W. Ager, A.T. Bell, CO₂ Electroreduction with Enhanced Ethylene and Ethanol Selectivity by Nanostructuring Polycrystalline Copper, *ChemElectroChem*, 3 (2016) 1012-1019.
- [31] H. Mistry, A.S. Varela, C.S. Bonifacio, I. Zegkinoglou, I. Sinev, Y.-W. Choi, K. Kisslinger, E.A. Stach, J.C. Yang, P. Strasser, B.R. Cuenya, Highly selective plasma-activated copper catalysts for carbon dioxide reduction to ethylene, *Nature Communications*, 7 (2016) 12123.
- [32] S. Min, X. Yang, A.-Y. Lu, C.-C. Tseng, M.N. Hedhili, L.-J. Li, K.-W. Huang, Low overpotential and high current CO₂ reduction with surface reconstructed Cu foam electrodes, *Nano Energy*, 27 (2016) 121-129.
- [33] M. Ma, K. Djanashvili, W.A. Smith, Selective electrochemical reduction of CO₂ to CO on CuO-derived Cu nanowires, *Physical Chemistry Chemical Physics*, 17 (2015) 20861-20867.
- [34] C.W. Li, M.W. Kanan, CO₂ Reduction at Low Overpotential on Cu Electrodes Resulting from the Reduction of Thick Cu₂O Films, *Journal of the American Chemical Society*, 134 (2012) 7231-7234.
- [35] D. Raciti, K.J. Livi, C. Wang, Highly Dense Cu Nanowires for Low-Overpotential CO₂ Reduction, *Nano Letters*, 15 (2015) 6829-6835.
- [36] A.D. Handoko, C.W. Ong, Y. Huang, Z.G. Lee, L. Lin, G.B. Panetti, B.S. Yeo, Mechanistic Insights into the Selective Electroreduction of Carbon Dioxide to Ethylene on Cu₂O-Derived Copper Catalysts, *The Journal of Physical Chemistry C*, 120 (2016) 20058-20067.
- [37] D. Ren, N.T. Wong, A.D. Handoko, Y. Huang, B.S. Yeo, Mechanistic Insights into the Enhanced Activity and Stability of Agglomerated Cu Nanocrystals for the Electrochemical Reduction of Carbon Dioxide to n-Propanol, *The Journal of Physical Chemistry Letters*, 7 (2016) 20-24.
- [38] K.D. Yang, W.R. Ko, J.H. Lee, S.J. Kim, H. Lee, M.H. Lee, K.T. Nam, Morphology-Directed Selective Production of Ethylene or Ethane from CO₂ on a Cu Mesopore Electrode, *Angewandte Chemie International Edition*, 56 (2017) 796-800.
- [39] K.H. Jiang, Yufeng; Zeng, Guosong; Toma, Francesca M.; Goddard, William A. III; Bell, Alexis T., Effects of Surface Roughness on the Electrochemical Reduction of CO₂ over Cu, *ACS Energy Letters*, 5 (2020), 1206-1214.
- [40] M.J. Ebaid, Kun; Zhang, Zemin; Drisdell, Walter S.; Bell, Alexis T.; Cooper, Jason K., Production of C₂/C₃ Oxygenates from Planar Copper Nitride-Derived Mesoporous Copper via Electrochemical Reduction of CO₂, *Chemistry of Materials*, 32 (2020) 3304-3311.
- [41] C. Choi, T. Cheng, M. Flores Espinosa, H. Fei, X. Duan, W.A. Goddard III, Y. Huang, A highly active star decahedron Cu nanocatalyst for hydrocarbon production at low overpotentials, *Advanced Materials*, 31 (2019) 1805405.
- [42] Y. Wang, Z. Wang, C.-T. Dinh, J. Li, A. Ozden, M.G. Kibria, A. Seifitokaldani, C.-S. Tan, C.M. Gabardo, M. Luo, Catalyst synthesis under CO₂ electroreduction favours faceting and promotes renewable fuels electrosynthesis, *Nature Catalysis*, 3 (2020) 98-106.

- [43] R. Kas, K. Yang, D. Bohra, R. Kortlever, T. Burdyny, W. Smith, Electrochemical CO₂ Reduction on Nanostructured Metal Electrodes: Fact or Defect?, *Chemical Science*, (2020).
- [44] P. Liu, J.K. Nørskov, Ligand and ensemble effects in adsorption on alloy surfaces, *Physical Chemistry Chemical Physics*, 3 (2001) 3814-3818.
- [45] B. Hammer, J.K. Nørskov, Theoretical surface science and catalysis—calculations and concepts, in: *Advances in catalysis*, Elsevier, 2000, pp. 71-129.
- [46] J.R. Kitchin, J.K. Nørskov, M.A. Barteau, J. Chen, Role of strain and ligand effects in the modification of the electronic and chemical properties of bimetallic surfaces, *Physical review letters*, 93 (2004) 156801.
- [47] M. Mavrikakis, B. Hammer, J.K. Nørskov, Effect of strain on the reactivity of metal surfaces, *Physical Review Letters*, 81 (1998) 2819.
- [48] H.A. Hansen, C. Shi, A.C. Lausche, A.A. Peterson, J.K. Nørskov, Bifunctional alloys for the electroreduction of CO₂ and CO, *Physical Chemistry Chemical Physics*, 18 (2016) 9194-9201.
- [49] E.L. Clark, C. Hahn, T.F. Jaramillo, A.T. Bell, Electrochemical CO₂ Reduction over Compressively Strained CuAg Surface Alloys with Enhanced Multi-Carbon Oxygenate Selectivity, *Journal of the American Chemical Society*, 139 (2017) 15848-15857.
- [50] C.G. Morales-Guio, E.R. Cave, S.A. Nitopi, J.T. Feaster, L. Wang, K.P. Kuhl, A. Jackson, N.C. Johnson, D.N. Abram, T. Hatsukade, C. Hahn, T.F. Jaramillo, Improved CO₂ reduction activity towards C₂₊ alcohols on a tandem gold on copper electrocatalyst, *Nature Catalysis*, 1 (2018) 764-771.
- [51] I. Zegkinoglou, L. Pielsticker, Z.-K. Han, N.J. Divins, D. Kordus, Y.-T. Chen, C. Escudero, V. Pérez-Dieste, B. Zhu, Y. Gao, B.R. Cuenya, Surface Segregation in CuNi Nanoparticle Catalysts During CO₂ Hydrogenation: The Role of CO in the Reactant Mixture, *The Journal of Physical Chemistry C*, 123 (2019) 8421-8428.
- [52] S. Liu, Z.-J. Zhao, C. Yang, S. Zha, K.M. Neyman, F. Studt, J. Gong, Adsorption Preference Determines Segregation Direction: A Shortcut to More Realistic Surface Models of Alloy Catalysts, *ACS Catalysis*, 9 (2019) 5011-5018.
- [53] A.S. Varela, C. Schlaup, Z.P. Jovanov, P. Malacrida, S. Horch, I.E.L. Stephens, I. Chorkendorff, CO₂ Electroreduction on Well-Defined Bimetallic Surfaces: Cu Overlayers on Pt(111) and Pt(211), *The Journal of Physical Chemistry C*, 117 (2013) 20500-20508.
- [54] S. Rasul, D.H. Anjum, A. Jedidi, Y. Minenkov, L. Cavallo, K. Takanabe, A highly selective copper–indium bimetallic electrocatalyst for the electrochemical reduction of aqueous CO₂ to CO, *Angewandte Chemie International Edition*, 54 (2015) 2146-2150.
- [55] S. Sarfraz, A.T. Garcia-Esparza, A. Jedidi, L. Cavallo, K. Takanabe, Cu–Sn bimetallic catalyst for selective aqueous electroreduction of CO₂ to CO, *ACS Catalysis*, 6 (2016) 2842-2851.
- [56] Y. Mun, S. Lee, A. Cho, S. Kim, J.W. Han, J. Lee, Cu-Pd alloy nanoparticles as highly selective catalysts for efficient electrochemical reduction of CO₂ to CO, *Applied Catalysis B: Environmental*, 246 (2019) 82-88.
- [57] T. Shinagawa, G.O. Larrazábal, A.J. Martín, F. Krumeich, J. Pérez-Ramírez, Sulfur-Modified Copper Catalysts for the Electrochemical Reduction of Carbon Dioxide to Formate, *ACS Catalysis*, 8 (2018) 837-844.
- [58] Y. Zhou, F. Che, M. Liu, C. Zou, Z. Liang, P. De Luna, H. Yuan, J. Li, Z. Wang, H. Xie, H. Li, P. Chen, E. Bladt, R. Quintero-Bermudez, T.-K. Sham, S. Bals, J. Hofkens, D. Sinton, G.

- Chen, E.H. Sargent, Dopant-induced electron localization drives CO₂ reduction to C₂ hydrocarbons, *Nature Chemistry*, 10 (2018) 974-980.
- [59] Z.-Q. Liang, T.-T. Zhuang, A. Seifitokaldani, J. Li, C.-W. Huang, C.-S. Tan, Y. Li, P. De Luna, C.T. Dinh, Y. Hu, Q. Xiao, P.-L. Hsieh, Y. Wang, F. Li, R. Quintero-Bermudez, Y. Zhou, P. Chen, Y. Pang, S.-C. Lo, L.-J. Chen, H. Tan, Z. Xu, S. Zhao, D. Sinton, E.H. Sargent, Copper-on-nitride enhances the stable electrocatalysis of multi-carbon products from CO₂, *Nature Communications*, 9 (2018) 3828.
- [60] T.-T. Zhuang, Z.-Q. Liang, A. Seifitokaldani, Y. Li, P. De Luna, T. Burdyny, F. Che, F. Meng, Y. Min, R. Quintero-Bermudez, Steering post-C-C coupling selectivity enables high efficiency electroreduction of carbon dioxide to multi-carbon alcohols, *Nature Catalysis*, 1 (2018) 421-428.
- [61] A. Verdager-Casadevall, C.W. Li, T.P. Johansson, S.B. Scott, J.T. McKeown, M. Kumar, I.E.L. Stephens, M.W. Kanan, I. Chorkendorff, Probing the Active Surface Sites for CO Reduction on Oxide-Derived Copper Electrocatalysts, *Journal of the American Chemical Society*, 137 (2015) 9808-9811.
- [62] D. Ren, Y. Deng, A.D. Handoko, C.S. Chen, S. Malkhandi, B.S. Yeo, Selective Electrochemical Reduction of Carbon Dioxide to Ethylene and Ethanol on Copper(I) Oxide Catalysts, *ACS Catalysis*, 5 (2015) 2814-2821.
- [63] Y. Lum, B. Yue, P. Lobaccaro, A.T. Bell, J.W. Ager, Optimizing C-C coupling on oxide-derived copper catalysts for electrochemical CO₂ reduction, *The Journal of Physical Chemistry C*, 121 (2017) 14191-14203.
- [64] A. Eilert, F. Cavalca, F.S. Roberts, J. Osterwalder, C. Liu, M. Favaro, E.J. Crumlin, H. Ogasawara, D. Friebel, L.G.M. Pettersson, A. Nilsson, Subsurface Oxygen in Oxide-Derived Copper Electrocatalysts for Carbon Dioxide Reduction, *The Journal of Physical Chemistry Letters*, 8 (2017) 285-290.
- [65] D. Gao, I.T. McCrum, S. Deo, Y.-W. Choi, F. Scholten, W. Wan, J.G. Chen, M.J. Janik, B. Roldan Cuenya, Activity and Selectivity Control in CO₂ Electroreduction to Multicarbon Products over CuO_x Catalysts via Electrolyte Design, *ACS Catalysis*, 8 (2018) 10012-10020.
- [66] D. Gao, I. Zegkinoglou, N.J. Divins, F. Scholten, I. Sinev, P. Grosse, B. Roldan Cuenya, Plasma-Activated Copper Nanocube Catalysts for Efficient Carbon Dioxide Electroreduction to Hydrocarbons and Alcohols, *ACS Nano*, 11 (2017) 4825-4831.
- [67] Y. Lum, J.W. Ager, Stability of Residual Oxides in Oxide-Derived Copper Catalysts for Electrochemical CO₂ Reduction Investigated with ¹⁸O Labeling, *Angewandte Chemie International Edition*, 57 (2018) 551-554.
- [68] S.B. Scott, T.V. Hogg, A.T. Landers, T. Maagaard, E. Bertheussen, J.C. Lin, R.C. Davis, J.W. Beeman, D. Higgins, W.S. Drisdell, C. Hahn, A. Mehta, B. Seger, T.F. Jaramillo, I. Chorkendorff, Absence of Oxidized Phases in Cu under CO Reduction Conditions, *ACS Energy Letters*, 4 (2019) 803-804.
- [69] A.J. Garza, A.T. Bell, M. Head-Gordon, Is Subsurface Oxygen Necessary for the Electrochemical Reduction of CO₂ on Copper?, *The Journal of Physical Chemistry Letters*, 9 (2018) 601-606.
- [70] M.R. Singh, A.T. Bell, Design of an artificial photosynthetic system for production of alcohols in high concentration from CO₂, *Energy & Environmental Science*, 9 (2016) 193-199.
- [71] A.J. Garza, A.T. Bell, M. Head-Gordon, Mechanism of CO₂ reduction at copper surfaces: Pathways to C₂ products, *ACS Catalysis*, 8 (2018) 1490-1499.

- [72] G. Kyriakou, M.B. Boucher, A.D. Jewell, E.A. Lewis, T.J. Lawton, A.E. Baber, H.L. Tierney, M. Flytzani-Stephanopoulos, E.C.H. Sykes, Isolated metal atom geometries as a strategy for selective heterogeneous hydrogenations, *Science*, 335 (2012) 1209-1212.
- [73] F.R. Lucci, J. Liu, M.D. Marcinkowski, M. Yang, L.F. Allard, M. Flytzani-Stephanopoulos, E.C.H. Sykes, Selective hydrogenation of 1,3-butadiene on platinum–copper alloys at the single-atom limit, *Nature Communications*, 6 (2015) 8550.
- [74] J. Liu, F.R. Lucci, M. Yang, S. Lee, M.D. Marcinkowski, A.J. Therrien, C.T. Williams, E.C.H. Sykes, M. Flytzani-Stephanopoulos, Tackling CO Poisoning with Single-Atom Alloy Catalysts, *Journal of the American Chemical Society*, 138 (2016) 6396-6399.
- [75] A.J. Therrien, A.J.R. Hensley, M.D. Marcinkowski, R. Zhang, F.R. Lucci, B. Coughlin, A.C. Schilling, J.-S. McEwen, E.C.H. Sykes, An atomic-scale view of single-site Pt catalysis for low-temperature CO oxidation, *Nature Catalysis*, 1 (2018) 192-198.
- [76] F. Besenbacher, I. Chorkendorff, B. Clausen, B. Hammer, A. Molenbroek, J.K. Nørskov, I. Stensgaard, Design of a surface alloy catalyst for steam reforming, *Science*, 279 (1998) 1913-1915.
- [77] E.R. Cave, C. Shi, K.P. Kuhl, T. Hatsukade, D.N. Abram, C. Hahn, K. Chan, T.F. Jaramillo, Trends in the Catalytic Activity of Hydrogen Evolution during CO₂ Electroreduction on Transition Metals, *ACS Catalysis*, 8 (2018) 3035-3040.
- [78] P. De Luna, C. Hahn, D. Higgins, S.A. Jaffer, T.F. Jaramillo, E.H. Sargent, What would it take for renewably powered electrosynthesis to displace petrochemical processes?, *Science*, 364 (2019) eaav3506.
- [79] O.S. Bushuyev, P. De Luna, C.T. Dinh, L. Tao, G. Saur, J. van de Lagemaat, S.O. Kelley, E.H. Sargent, What should we make with CO₂ and how can we make it?, *Joule*, 2 (2018) 825-832.
- [80] S. Verma, B. Kim, H.R.M. Jhong, S. Ma, P.J. Kenis, A gross-margin model for defining technoeconomic benchmarks in the electroreduction of CO₂, *ChemSusChem*, 9 (2016) 1972-1979.
- [81] N. Kornienko, J.Z. Zhang, K.K. Sakimoto, P. Yang, E. Reisner, Interfacing nature's catalytic machinery with synthetic materials for semi-artificial photosynthesis, *Nature Nanotechnology*, 13 (2018) 890-899.
- [82] J. Qiao, Y. Liu, F. Hong, J. Zhang, A review of catalysts for the electroreduction of carbon dioxide to produce low-carbon fuels, *Chemical Society Reviews*, 43 (2014) 631-675.
- [83] M. Boudart, *Kinetics of Chemical Processes: Butterworth-Heinemann Series in Chemical Engineering*, Elsevier, 2014.
- [84] Y. Tomita, S. Teruya, O. Koga, Y. Hori, Electrochemical reduction of carbon dioxide at a platinum electrode in acetonitrile-water mixtures, *Journal of The Electrochemical Society*, 147 (2000) 4164.
- [85] T. Saeki, K. Hashimoto, A. Fujishima, N. Kimura, K. Omata, Electrochemical reduction of CO₂ with high current density in a CO₂-methanol medium, *The Journal of Physical Chemistry*, 99 (1995) 8440-8446.
- [86] L. Sun, G.K. Ramesha, P.V. Kamat, J.F. Brennecke, Switching the Reaction Course of Electrochemical CO₂ Reduction with Ionic Liquids, *Langmuir*, 30 (2014) 6302-6308.
- [87] C. Shi, K. Chan, J.S. Yoo, J.K. Nørskov, Barriers of Electrochemical CO₂ Reduction on Transition Metals, *Organic Process Research & Development*, 20 (2016) 1424-1430.

- [88] G. Li, B. Wang, D.E. Resasco, Water-Mediated Heterogeneously Catalyzed Reactions, *ACS Catalysis*, 10 (2020) 1294-1309.
- [89] R.L. Cook, R.C. Macduff, A.F. Sammells, High-Rate Gas-Phase CO₂ Reduction to Ethylene and Methane Using Gas-Diffusion Electrodes, *J. Electrochem. Soc.*, 137 (1990) 607-608.
- [90] K. Hara, T. Sakata, Large current density CO₂ reduction under high pressure using GDEs, *Bull. Chem. Soc. Jpn.*, 70 (1997) 571-576.
- [91] S. Ma, R. Luo, S. Moniri, Y.C. Lan, P.J.A. Kenis, Efficient Electrochemical Flow System with Improved Anode for the Conversion of CO₂ to CO, *J. Electrochem. Soc.*, 161 (2014) F1124-F1131.
- [92] D.M. Weekes, D.A. Salvatore, A. Reyes, A. Huang, C.P. Berlinguette, Electrolytic CO₂ Reduction in a Flow Cell, *Accounts of Chemical Research*, 51 (2018) 910-918.
- [93] B. Endrodi, G. Bencsik, F. Darvas, R. Jones, K. Rajeshwar, C. Janaky, Continuous-flow electroreduction of carbon dioxide, *Progress in Energy and Combustion Science*, 62 (2017) 133-154.
- [94] S. Garg, M. Li, A.Z. Weber, L. Ge, L. Li, V. Rudolph, G. Wang, T.E. Rufford, Advances and challenges in electrochemical CO₂ reduction processes: an engineering and design perspective looking beyond new catalyst materials, *Journal of Materials Chemistry A*, 8 (2020) 1511-1544.
- [95] U.O. Nwabara, E.R. Cofell, S. Verma, E. Negro, P.J.A. Kenis, Durable Cathodes and Electrolyzers for the Efficient Aqueous Electrochemical Reduction of CO₂, *ChemSusChem*, 13 (2020) 855-875.
- [96] D. Salvatore, C.P. Berlinguette, Voltage Matters When Reducing CO₂ in an Electrochemical Flow Cell, *ACS Energy Letters*, 5 (2020) 215-220.
- [97] E.W. Lees, M. Goldman, A.G. Fink, D.J. Dvorak, D.A. Salvatore, Z. Zhang, N.W.X. Loo, C.P. Berlinguette, Electrodes Designed for Converting Bicarbonate into CO, *ACS Energy Letters*, (2020) 2165-2173.
- [98] T. Li, E.W. Lees, M. Goldman, D.A. Salvatore, D.M. Weekes, C.P. Berlinguette, Electrolytic conversion of bicarbonate into CO in a flow cell, *Joule*, 3 (2019) 1487-1497.
- [99] D.A. Salvatore, D.M. Weekes, J. He, K.E. Dettelbach, Y.C. Li, T.E. Mallouk, C.P. Berlinguette, Electrolysis of Gaseous CO₂ to CO in a Flow Cell with a Bipolar Membrane, *ACS Energy Letters*, 3 (2018) 149-154.
- [100] C.M. Gabardo, C.P. O'Brien, J.P. Edwards, C. McCallum, Y. Xu, C.-T. Dinh, J. Li, E.H. Sargent, D. Sinton, Continuous Carbon Dioxide Electroreduction to Concentrated Multi-carbon Products Using a Membrane Electrode Assembly, *Joule*, 3 (2019) 2777-2791.
- [101] Y.C. Li, G. Lee, T. Yuan, Y. Wang, D.-H. Nam, Z. Wang, F.P. García de Arquer, Y. Lum, C.-T. Dinh, O. Voznyy, E.H. Sargent, CO₂ Electroreduction from Carbonate Electrolyte, *ACS Energy Letters*, 4 (2019) 1427-1431.
- [102] C.-T. Dinh, F.P. García de Arquer, D. Sinton, E.H. Sargent, High Rate, Selective, and Stable Electroreduction of CO₂ to CO in Basic and Neutral Media, *ACS Energy Letters*, 3 (2018) 2835-2840.
- [103] Y. Chen, A. Vise, W.E. Klein, F.C. Cetinbas, D.J. Myers, W.A. Smith, T.G. Deutsch, K.C. Neyerlin, A Robust, Scalable Platform for the Electrochemical Conversion of CO₂ to Formate: Identifying Pathways to Higher Energy Efficiencies, *ACS Energy Letters*, 5 (2020) 1825-1833.
- [104] L.C. Weng, A.T. Bell, A.Z. Weber, Modeling gas-diffusion electrodes for CO₂ reduction, *Physical Chemistry Chemical Physics*, 20 (2018) 16973-16984.

- [105] L.-C. Weng, A.T. Bell, A.Z. Weber, Towards membrane-electrode assembly systems for CO₂ reduction: a modeling study, *Energy & Environmental Science*, 12 (2019) 1950-1968.
- [106] J. Resasco, L.D. Chen, E. Clark, C. Tsai, C. Hahn, T.F. Jaramillo, K. Chan, A.T. Bell, Promoter Effects of Alkali Metal Cations on the Electrochemical Reduction of Carbon Dioxide, *Journal of the American Chemical Society*, 139 (2017) 11277-11287.
- [107] S. Ringe, E.L. Clark, J. Resasco, A. Walton, B. Seger, A.T. Bell, K. Chan, Understanding cation effects in electrochemical CO₂ reduction, *Energy & Environmental Science*, (2019).
- [108] T. Burdyny, W.A. Smith, CO₂ reduction on gas-diffusion electrodes and why catalytic performance must be assessed at commercially-relevant conditions, *Energy & Environmental Science*, 12 (2019) 1442-1453.
- [109] R. Küngas, P. Blennow, T. Heiredal-Clausen, T. Holt, J. Rass-Hansen, S. Primdahl, J.B. Hansen, eCOs-a commercial CO₂ electrolysis system developed by haldor Topsoe, *ECS Transactions*, 78 (2017) 2879.
- [110] Gurudayal, D. Perone, S. Malani, Y. Lum, S. Haussener, J.W. Ager, Sequential Cascade Electrocatalytic Conversion of Carbon Dioxide to C–C Coupled Products, *ACS Applied Energy Materials*, 2 (2019) 4551-4559.