

UC Irvine

UC Irvine Previously Published Works

Title

Superconductivity with Europium

Permalink

<https://escholarship.org/uc/item/53m7h9w2>

Journal

Physics Letters A, 72(3)

ISSN

0375-9601

Authors

Matthias, BT

Fisk, Z

Smith, JL

Publication Date

1979-07-09

DOI

10.1016/0375-9601(79)90021-5

License

[CC BY 4.0](#)

Peer reviewed

SUPERCONDUCTIVITY WITH EUROPIUM

Bernd T. MATTHIAS and Zachary FISK

*Institute for Pure and Applied Physical Sciences*¹, *University of California, San Diego, La Jolla, CA 92093, USA*

and

James L. SMITH

*Los Alamos Scientific Laboratory of the University of California*², *Los Alamos, NM 87545, USA*

Received 9 May 1979

EuIr_2 becomes superconducting at 0.2 K. Arc melting this compound raises T_c to 2.6 K, in an apparently different and unidentified structure. These are the first superconductors containing Eu.

Americium becomes superconducting below 1 K [1]. This happens, even though the element is right in the middle of the magnetic 5f elements. Superconductivity is not inhibited because it has a nonmagnetic configuration of its six 5f electrons, which through spin-orbit coupling form a singlet ground state [2].

Europium is the 4f analog of americium among the rare earths (RE) as far as its position is concerned. However, in the elemental state, it has seven 4f electrons one of which was removed from the usual RE three outer s-d electrons. It is therefore strongly magnetic and will not become superconducting.

When americium was seen to be superconducting, it became evident that europium would do the same if only the half filled 4f shell could be broken up. This would require pressures near 300 kbar and temperatures perhaps as low as 0.1 K, clearly a very difficult experiment.

However, another way out is to simply subject europium to the pressure of an intermetallic crystal lattice. There are intermetallic europium compounds in which the Eu has only six 4f electrons. This fact can easily be seen from its atomic radius since the lattice constants will then be very close to the corres-

ponding samarium and gadolinium compounds.

Due to a long history [3,4], the compound which comes foremost to mind is EuIr_2 . Here Eu is strictly in its trivalent, nonmagnetic state. Almost all iridium compounds with the rare earths of the form $(\text{RE})\text{Ir}_2$ are of the cubic Laves phase and become either ferromagnetic or superconducting, depending on whether the RE element is either magnetic or superconducting by itself [5]. On the basis of these systematics, EuIr_2 had to become superconducting at low temperatures. In fact, it did just that at 0.2 K. This is a clear indication that pure europium once it is in its trivalent state will also become a superconductor at sufficiently low temperatures and at pressures > 250 kbar [6].

In fig. 1, the ferromagnetism and superconductivity of the known $(\text{RE})\text{Ir}_2$ compounds is (now) shown. Just as in the case of americium, EuIr_2 is the lone superconductor right in the middle of strongly magnetic compounds. The strictly nonmagnetic character of europium becomes evident from magnetic susceptibility data over the whole temperature range, since EuIr_2 shows only an essentially temperature independent van Vleck paramagnetism.

Similar to the other superconducting $(\text{RE})\text{Ir}_2$ compounds, the detailed superconducting behavior is quite complicated. Various values for critical temperatures are reported [7] and given in table 1. Whether this is due to a homogeneity range or a second phase

¹ Research sponsored by the National Science Foundation under contract #NSF/DMR77-08469.

² Work performed under the auspices of the Department of Energy.

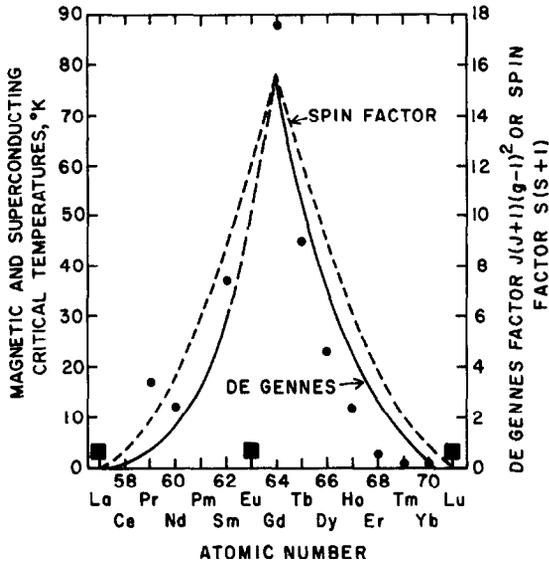


Fig. 1. Ferromagnetic (●) and superconducting (■) transition temperatures of (RE)Ir₂ compounds.

is at present not clear. Similarly, when the sintered EuIr₂ is arc melted, the superconducting transition is raised to 2.6 K. Additional lines also appear in the X-ray picture. Therefore we believe that T_c of 2.6 K is due to another, as yet unidentified phase, rather than an extended homogeneity range.

In principle, however, this is not important now

Table 1
Spectrum of superconducting transition temperatures for (RE)Ir_{2+x} compounds.

ScIr ₂	0.42,	1.03,	2.13,	2.46
Y Ir ₂	1.09,	2.18		
LaIr ₂	0.48,	2.32		
LuIr ₂	2.47			
EuIr₂	0.200;	2.64;	2.66.	

since we have been able to show that europium metal in its trivalent state will be a superconductor.

References

- [1] J.L. Smith and R.G. Haire, *Science* 200 (1978) 535.
- [2] J.H. van Vleck, *The theory of electric and magnetic susceptibilities* (Oxford U.P., 1932) pp. 246 and 251.
- [3] B.T. Matthias, R.M. Bozorth and J.H. van Vleck, *Phys. Rev. Lett.* 7 (1961) 160.
- [4] J.H. van Vleck, *J. Less Common Met.* 62 (1978) xv.
- [5] K.A. Gschneidner, *Rare earth alloys* (Van Nostrand, 1961) p. 183;
R.M. Bozorth, B.T. Matthias, H. Suhl, E. Corenzwit and D.D. Davis, *Phys. Rev.* 115 (1959) 1595.
- [6] B. Johansson and A. Rosengren, *Phys. Rev. B* 11 (1975) 2836.
- [7] B.W. Roberts, *Survey of superconductive materials and critical evaluation of selected properties*, reprint No. 84 from *J. Phys. Chem. Ref. Data* 1976, Vol. 5, No. 3, pp. 581-821.