

# Lawrence Berkeley National Laboratory

## Recent Work

### Title

THE TEMPERATURE DEPENDENCE OF THE ELASTIC CONSTANTS OF Cu, Ag, AND Au ABOVE ROOM TEMPERATURE

### Permalink

<https://escholarship.org/uc/item/5sp2v14g>

### Authors

Chang, Y.A.  
Himmel, L.

### Publication Date

1966

UCRL-16697

University of California  
Ernest O. Lawrence  
Radiation Laboratory

THE TEMPERATURE DEPENDENCE OF THE ELASTIC CONSTANTS  
OF Cu, Ag AND Au ABOVE ROOM TEMPERATURE

TWO-WEEK LOAN COPY

*This is a Library Circulating Copy  
which may be borrowed for two weeks.  
For a personal retention copy, call  
Tech. Info. Division, Ext. 5545*

Berkeley, California

## **DISCLAIMER**

This document was prepared as an account of work sponsored by the United States Government. While this document is believed to contain correct information, neither the United States Government nor any agency thereof, nor the Regents of the University of California, nor any of their employees, makes any warranty, express or implied, or assumes any legal responsibility for the accuracy, completeness, or usefulness of any information, apparatus, product, or process disclosed, or represents that its use would not infringe privately owned rights. Reference herein to any specific commercial product, process, or service by its trade name, trademark, manufacturer, or otherwise, does not necessarily constitute or imply its endorsement, recommendation, or favoring by the United States Government or any agency thereof, or the Regents of the University of California. The views and opinions of authors expressed herein do not necessarily state or reflect those of the United States Government or any agency thereof or the Regents of the University of California.

UNIVERSITY OF CALIFORNIA  
Lawrence Radiation Laboratory  
Berkeley, California  
AEC Contract No. W-7405-eng-48

THE TEMPERATURE DEPENDENCE OF THE ELASTIC CONSTANTS OF  
Cu, Ag AND Au ABOVE ROOM TEMPERATURE

Y. A. Chang and L. Himmel

January 1966

THE TEMPERATURE DEPENDENCE OF THE ELASTIC CONSTANTS  
OF Cu, Ag AND Au ABOVE ROOM TEMPERATURE

Y. A. Chang<sup>†</sup> and L. Himmel<sup>‡</sup>

Inorganic Materials Research Division, Lawrence Radiation Laboratory  
and Department of Mineral Technology, College of Engineering, University  
of California, Berkeley, California.

ABSTRACT

The adiabatic elastic constants  $C_{44}$ ,  $1/2 (C_{11} - C_{12})$  and  $1/2 (C_{11} + C_{12} + 2C_{44})$  have been measured for copper, silver and gold over the temperature range from 300° to about 800°K using the conventional ultrasonic pulse-echo technique. The room temperature values of the stiffness coefficients are shown to be in acceptable agreement with previously published data for the noble metals. Over the entire range from 300° to 800°K it is found that, to a remarkably good approximation, the elastic constants for all three metals decrease linearly with temperature. Additional evidence is presented to show that the linear temperature dependence of the elastic constants for silver extends to at least 1000°K, i. e. to within 0.8 of the absolute melting temperature. The isothermal compressibilities calculated from the elastic constant data are used to evaluate the dilational term in the specific heat,  $C_{dil} = C_p - C_v$ , and it is established that the approximate Nernst-Lindemann relation for estimating  $C_{dil}$  is valid for Cu, Ag, and Au at least up to 800°K.

---

+ Present address: Materials Research Laboratory, Aerojet-General Corporation, Sacramento, California.

‡ Present address: University of California, Lawrence Radiation Laboratory, Livermore, California

## INTRODUCTION:

Although generally lacking, knowledge of the elastic constants of solids at temperatures approaching their melting points is of interest in several connections. For example, the isothermal compressibilities, derived from such data, make it possible to obtain an accurate estimate of the dilational or thermal expansion contribution to the specific heat. This dilational term, which increases rapidly above the Debye temperature, must be subtracted, along with the electronic specific heat, from the calorimetrically determined values of the specific heat at constant pressure in order to separate out the contribution due solely to lattice vibrations. Moreover, the high temperature elastic properties also enter in an important way into the theory of diffusion in cubic metals as Zener<sup>(1)</sup> and LeClaire<sup>(2)</sup> have shown, the magnitude of the pre-exponential factor,  $D_0$ , in the usual Arrhenius equation for the self diffusion coefficient is explicitly related to the temperature dependence of the stiffness moduli.

Since the elastic constants of the monovalent noble metals, copper, silver, and gold, have previously been determined only over the temperature range from 4.2° to 300°K, we felt it would be desirable to extend the measurements to substantially higher temperatures. In the present investigation, the adiabatic stiffness coefficients for all three metals have been determined from 300° to about 800°K using the conventional ultrasonic pulse-echo technique. Unfortunately, it was not possible to carry out measurements above 800°K because of deterioration of the epoxy resin which was used to cement the quartz transducers to the single crystal specimens. Even if a better high temperature bonding agent were available, the measurements would still have been limited to about 846°K - the temperature of the  $\alpha$ - $\beta$  transformation in quartz - using the techniques currently employed.

The elastic constant data obtained for Cu, Ag and Au between 300° and 800°K have subsequently been employed to evaluate the dilational contribution to the specific heat, i. e.,  $C_p - C_v$ . The latter calculations, in turn, have permitted a fairly stringent test to be made of the semi-empirical Nernst-Lindemann relation<sup>(3)</sup>, by means of which the dilational term is frequently approximated in the absence of the required compressibility data<sup>(4)</sup>.

### EXPERIMENTAL DETAILS

Copper, silver and gold single crystals in the form of 2.5 cm diameter spheres were grown under vacuum ( $\sim 5 \times 10^{-6}$  Torr) in previously outgassed reactor grade graphite crucibles using a modified Bridgman technique. The nominal purities and sources of the starting materials were as follows: Cu, 99.999%, American Smelting and Refining Company; Ag, 99.9999%, oxygen-free grade, COMINCO Electronic Products, Inc.; Au, 99.99% Western Gold and Platinum Company. Specimens with faces normal to the  $\langle 110 \rangle$  direction were then cut from each crystal by spark erosion. The orientations of these surfaces were determined by the standard back reflection Laue method and were adjusted to within 0.25 degree of  $\langle 110 \rangle$ .

Inasmuch as the Laue reflections obtained directly from the spark eroded surfaces were found to be somewhat broad or diffuse, the crystals were first etched to remove the damaged surface layer resulting from the spark cutting operation; after etching (dilute  $HNO_3$  for Cu and Ag, aqua regia for Au) sharp Laue reflections were observed. Each crystal was then mounted inside a surface ground hardened steel ring of appropriate thickness and polished with  $3\mu$  diamond paste on a vibratory lap (Syntron) until the two  $\{110\}$  faces were flat and parallel to within  $\pm 0.0002$  cm. Lapping in this manner preserved the sharpness of the Laue reflections, thus indicating that the specimen surfaces

were comparatively free of distortion. Two copper specimens of different lengths were prepared as well as two of silver and one of gold. The lengths of the resulting crystals, measured at 24°C were: Cu, 1.2040 and 1.6939 cm; Ag, 1.2037 and 1.5786 cm; Au, 0.6175 cm.

For cubic crystals, three independent combinations of the elastic constants  $C_{11}$ ,  $C_{12}$  and  $C_{44}$  may be obtained by measuring the velocities of plane longitudinal waves and appropriately polarized transverse waves propagating the  $\langle 110 \rangle$  direction. The three directly measured quantities are, in the notation introduced by Zener<sup>(5)</sup>,  $C'_{11} = 1/2 (C_{11} + C_{12} + 2C_{44}) = \rho V_l^2$ ,  $C = C_{44} = \rho V_{t_1}^2$  and  $C'' = 1/2 (C_{11} - C_{12}) = \rho V_{t_2}^2$ , where  $\rho$  is the crystal density,  $V_l$  is the longitudinal wave velocity and  $V_{t_1}$  and  $V_{t_2}$  are the velocities of transverse shear waves polarized in the  $\langle 100 \rangle$  and  $\langle 110 \rangle$  directions, respectively.

We have measured these sound wave velocities with a Sperry Products ultrasonic attenuation comparator<sup>(6)</sup>. Longitudinal waves were generated by 1/2-in. dia. X-cut quartz crystal transducers and transverse waves by Y-cut crystals, both resonant at 10 Mc/sec. The quartz transducers were bonded to the specimen surfaces with a special high-temperature epoxy resin consisting of Epon 1031 (Shell Development Co.) and nadic methyl anhydride.\*

Experience showed that the most satisfactory results were obtained when the epoxy resin was applied without the use of a supplementary catalyst. After curing for about 2 hours at 150°C, the epoxy resin bond provided excellent acoustic coupling between the quartz transducer and all three metals at temperatures up to roughly 550°K. Above this temperature, the quality of the bond varied depending upon the particular metal and, to some extent, on the mode of propagation. The coupling, in general, was best for Cu and poorest

---

\*This material was kindly supplied by Dr. H. Chen, formerly of the Shell Development Company, Emeryville, Calif. The exact proportions of the two ingredients are unknown.



for Au, with silver being intermediate. A complete loss of coupling was frequently observed above about 550°K on initial warmup, as evidenced by a sudden drop in echo intensity. However, it was found that by raising the temperature to about 700°K and then slowly cooling back to 500° - 550°K, sufficient coupling could be restored to permit additional measurements to be made on reheating.

With Cu and Ag, the longitudinal and the two shear modes could all be propagated successfully up to 800°K. With gold, on the other hand, only the shear wave velocity,  $V_{t1}$ , corresponding to particle displacement in the  $\langle 100 \rangle$  direction could be measured to temperatures as high as 800°K; despite repeated efforts, measurements of the other two wave velocities could not extend above about 550°K because of the lack of sufficient acoustic coupling.

Measurements were made with the specimen mounted in a suitable holder inside a resistance heated furnace in which an atmosphere of dry argon was maintained. A flat copper plate, against which the crystal was held in good thermal and electrical contact, served as the specimen support. Furnace temperatures were controlled to  $\pm 2^\circ\text{C}$  and the temperature of the specimen was measured to within  $\pm 1^\circ\text{C}$  with a calibrated copper-constantan thermocouple inserted in a small hole in the copper plate. A more detailed description of the equipment and measuring techniques has been given elsewhere<sup>(7)</sup>.

To estimate the magnitude of any possible transit-time corrections due to the finite thickness of the acoustic bond, a series of experiments were carried out at room temperature using specimens of different length as well as different bonding agents (e.g., "Nonaq" stopcock grease vs. epoxy resin). In all cases, the measured wave velocities agreed to within 0.1%. This is well within the scatter of the elastic constant data as a function of temperature (See Figures 1 - 3).

The room temperature densities used in computing the elastic constants, viz.,  $\rho = 8.937 \text{ g/cm}^3$  for Cu,  $10.50 \text{ g/cm}^3$  for Ag and  $19.30 \text{ g/cm}^3$  for Au were derived from the x-ray lattice spacings given by Pearson<sup>(8)</sup>. These densities, together with the measured sound velocities, were corrected for thermal expansion using the data of Nix and McNair<sup>(9)</sup> and Balluffi and Simmons<sup>(10)</sup>.

## RESULTS

The directly measured elastic constants  $C = \rho V^2$  for Cu, Ag and Au are plotted as a function of temperature in Figures 1 - 3. The solid lines shown in these figures represent, in each case, the best least squares fit to the observed values. In Tables I-III we have listed the smoothed values of the adiabatic elastic constants  $C'_{11}$ ,  $C'$  and  $C$  taken from Figures 1 - 3 as well as the calculated stiffness coefficients  $C_{11}$  and  $C_{12}$ . Also included in these tables are the smoothed values of the adiabatic bulk moduli  $B_s = 1/3 (C_{11} + 2C_{12}) = C'_{11} - C - C'/3$  and the isothermal compressibilities,  $\chi_T$ , which have been calculated from  $B_s$  in the standard manner<sup>(3)</sup>.

The number of significant figures displayed in Tables I-III is greater than is warranted by the absolute accuracy of the measurements, but an extra figure has been retained both to indicate the smoothness of the data and to permit a valid determination of the temperature coefficients; this is justified, to some extent, because the relative variation of the elastic constants with temperature has been established with somewhat better accuracy than have the absolute values. From the statistical spread or scatter in the experimental data shown in Figures 1 - 3, the uncertainties in the directly measured constants  $C'_{11}$ ,  $C$  and  $C'$  are found to be  $\pm 0.5\%$ . Using the standard propagation-of-error treatment,<sup>(11)</sup> the corresponding uncertainties in the calculated quantities are as follows:  $C_{11}$ ,  $\pm 0.7\%$ ,  $C_{12}$ ,  $\pm 0.9\%$ ;  $B_s$ ,  $\pm 0.9\%$ .

### Comparison with Previous Room Temperature Measurements

A detailed comparison between the results obtained at 300°K and room temperature elastic constant data for the noble metals previously reported in the literature is given in Table IV. The most accurate measurements for Cu are those of Overton and Gaffney<sup>(12)</sup> who also employed the ultrasonic pulse-echo technique. Agreement is seen to be quite good — within 0.3% for the shear constants C and C', 0.5% for C<sub>11</sub>' and 0.7% for B<sub>s</sub>. The present experimental values for Ag are likewise in good agreement with earlier measurements by Bacon and Smith<sup>(13)</sup>, Neighbours and Alers<sup>(14)</sup> and Corll<sup>(15)</sup>, the maximum percentage difference between any of the values listed in Table IV being only about 0.6%. For gold, however, the agreement is somewhat less good, especially for C' which is about 2% higher than Neighbours and Alers' value. The isothermal compressibilities computed from the adiabatic bulk moduli also compare favorably with previously published data for these metals and are within 2% of Bridgman's static room temperature values. Chang and Hultgren<sup>(7)</sup> have recently measured the longitudinal and transverse sound velocities in polycrystalline Cu over the temperature range 77° to 800°K; they report virtually the same temperature dependence of the compressibility as that from the present single crystal measurements.

### Temperature Dependence of the Elastic Constants

The most noteworthy feature of the data recorded in Figs. 1 - 3 is that, within the uncertainty of the measurements, the elastic stiffness coefficients for all three metals decrease linearly with temperature over the entire range investigated. For further reference we have also plotted in Fig. 1 the elastic constants of Cu between 4.2° and 300°K taken from the work of Overton and Gaffney; similarly, the low temperature data of Neighbours and Alers for Ag

and Au are reproduced in Figs. 2 and 3, respectively. In general, by making only slight relative shifts along the vertical axes, the least-squares lines which describe the present high temperature measurements may be joined, without any appreciable discontinuity in slope, to the corresponding low temperature curves. This offers further support for the consistency of the data and also indicates that the linear variation of the elastic constants holds to good approximation down to about 50°K for Au and Ag and nearly 100°K for Cu. These temperatures roughly correspond to about one-third the Debye temperature in each case.

Accurate modulus data which confirm and extend the observed linear temperature dependence for silver have recently been obtained by Guinan<sup>(16)</sup>. Using the resonant bar technique, Guinan has measured the elastic moduli of  $\langle 100 \rangle$  - and  $\langle 111 \rangle$  - oriented silver single crystals of both 6 - 9's pure and oxygen saturated ( $\sim 40$  ppm) specimens over the range from 200° to 1000°K. His data, to which small corrections have been applied for lateral inertia effects are plotted as a function of temperature in Fig. 4. They demonstrate that Young's moduli for silver continue to decrease with temperature in strictly linear fashion at least up to 1000°K, and perhaps well beyond.

To provide a more succinct comparison with Guinan's measurements, we have calculated the Young's moduli,  $E_{100}$  and  $E_{111}$ , for silver from our data (Table II) as well as from the low temperature data of Neighbours and Aders. The following standard relations between the moduli and the elastic constants have been employed<sup>(17)</sup>:

$$\frac{1}{E_{100}} = \frac{1}{3} \left( \frac{1}{3B_s} + \frac{1}{C} \right) \quad (1)$$

and

$$\frac{1}{E_{111}} = \frac{1}{3} \left( \frac{1}{3B_s} + \frac{1}{C} \right)$$

The resulting values are plotted in Fig. 4. It is clear from this figure that the calculated values of  $E_{100}$  and  $E_{111}$  and the temperature dependence of  $E_{100}$  and  $E_{111}$  from our data as well as those of Neighbours and Alers agree reasonably well with the directly measured values of Ag by Guinan within the experimental error.

We should also mention here that because of experimental limitations, most of the constants for gold above 550°K could only be arrived at by linear extrapolation. However, in view of the behavior exhibited by Cu and Ag, and the observed linear temperature dependence of  $C_{44}$  for Au over the full temperature range, this extrapolation can be carried out with complete confidence. Although we feel that these extrapolated values are probably reliable to within ± 1%, they are enclosed in parentheses in Table III to distinguish them from the experimentally measured quantities.

The thermal variation of the elastic constants near room temperature is summarized in Table V. Following the procedure adopted in the review by Huntington<sup>(18)</sup>, we have listed in Table V the values of  $1/C_{ij} (dC_{ij}/dT)$  at 300°K computed from the data given in Figs. 1 - 3 and Tables I - III. These temperature coefficients are expressed in parts per/10<sup>6</sup>°K. The corresponding quantities deduced from the measurements of Overton and Gaffney and Neighbours and Alers are also presented in this table, as are the values of  $1/E_{100} (dE_{100}/dT)$  and  $1/E_{111} (dE_{111}/dT)$  for silver. The temperature coefficients

for the directly measured constants,  $C$ ,  $C'$  and  $C'_{11}$  for Cu and Au are seen to be in good accord with earlier results, but the thermal variation of  $C'_{11}$  and  $C'$  for Ag is 10 - 15% greater than that found by Neighbours and Alers. This accounts for the somewhat smaller temperature dependence of  $E_{100}$  calculated from Neighbours and Alers' data. The excellent correspondence previously noted between Guinan's measurements on silver and the temperature coefficients of  $E_{100}$  and  $E_{111}$  derived from the present experiments is also demonstrated in Table V.

Dilational Contribution to the Specific Heat

Knowing the isothermal compressibilities of Cu, Ag and Au between room temperature and 800°K, (see Tables I - III) the dilational term in the specific heat,  $C_{dil}$ , can be computed from the well-known thermodynamic relation<sup>(3)</sup>

$$C_{dil} = C_p - C_v = \frac{9\beta^2 TV}{\chi_T} \quad (3)$$

where  $C_p$  and  $C_v$  are the specific heats at constant pressure and volume, respectively,  $\beta$  is the linear coefficient of thermal expansion and  $V$  is the atomic volume. In making these calculations, the necessary values of  $\beta$  have been obtained from the thermal expansion data of Nix and McNair<sup>(9)</sup> and Balluffi and Simmons<sup>(10)</sup>, and the atomic volumes, corrected for thermal expansion, have been computed from the lattice constants given by Pearson<sup>(8)</sup>.

When compressibility data at high temperatures are lacking, as is generally the case,  $C_{dil}$  is frequently approximated using the Nernst-Lindemann relation

$$C_{dil} = AC_p^2 T \quad (4)$$

and taking the Nernst-Lindemann parameter

$$A = 9\beta^2 V / C_P^2 \chi_T \quad (5)$$

to be constant independent of temperature. The validity of this assumption may be tested with the aid of the data recorded in Tables I - III and the values of  $C_P(T)$  for Cu, Ag and Au given in the recent compilation by Hultgren, et. al.<sup>(19)</sup> We listed in Table VI, for example, the values of A for all three metals between 300° and 800°K calculated from Eq. (5) solely on the basis of experimentally determined quantities. The essential constancy of A for Cu and Au over this relatively wide temperature range is indeed apparent. For silver, the value of A decreases roughly 8% between room temperature and 800°K. However, in terms of specific heat, the error introduced using the value of A obtained at room temperature amounts to only 1% of the total specific heat at 800°K.

### DISCUSSION

The data presented above demonstrate that the linear temperature dependence of the elastic constants for Ag holds remarkably well to temperatures of at least 1000°K, or to within 0.8 of the absolute melting temperature. The thermal variation of the elastic constants of Cu and Au appears qualitatively similar in all aspects. Although the linear variation with temperature has been established experimentally for these two metals only up to about 800°K, the fact that they have higher melting points than Ag would seem to suggest that the existing data for Cu and Au could safely be extrapolated in a linear fashion to  $0.8 T_m \approx 1100^\circ\text{K}$ . The strictly linear decrease in the stiffness coefficients of Cu, Ag and Au with temperature indicates that the elastic stiffness coefficients decrease in essentially a linear manner with thermal energy. Moreover, it

suggests that relaxation processes could have exerted but little influence on the measured moduli. If this were not so, a departure from linearity would have been observed, especially at high temperatures, and associated with the lowering of the true modulus.

Turning now to a consideration of the dilational specific heats, Gschneidner<sup>(4)</sup> has recently indicated that the constancy of the parameter A in Eq. (4) has been demonstrated experimentally over a wide temperature range for many metals. The basis for this statement was not documented, but the calculations summarized in Table VI demonstrate that it applies quite well to the noble metals at temperatures up to 800°K. In fact, the assumption that A is a constant independent of temperature is well enough supported experimentally to justify the use of the approximate Nernst-Lindemann relationship in estimating  $C_{dil}$  at temperatures considerably beyond those covered in this investigation. For this purpose it appears that a slightly more reliable estimate of  $C_{dil}$  between say 800°K and the melting point might be obtained by using the values of A at 800°K listed in Table VI instead of the room temperature values.

Some additional calculations not recorded here have been carried out. Using the approximate Nernst-Lindemann relation, Eq. (4), and assuming that the electronic specific heat varies linearly with temperature, we have evaluated the lattice contribution to the specific heats from room temperature to the respective melting points for all three metals. As might be anticipated, the lattice specific heats so obtained are in excellent agreement with the values predicted by the simple Debye continuum model, and the Dulong and Petit value,  $C_v = 3R = 5.96$  cal/deg-g-atom is approached within 0.04 cal/deg-g-atom at the melting point of Cu and Ag. For gold, the agreement is less good, but it



appears that either the dilational or the electronic contribution may have been overestimated since the calculated values of  $C_v$  decrease with temperature above about 900°K and fall about 0.20 cal/deg.g-atom below the Dulong-Petit value at the melting point.

Table I. Adiabatic Elastic Constants in Units of  $10^{12}$  dyne/cm<sup>2</sup>  
and Isothermal Compressibility in Units of  $10^{-13}$  cm<sup>2</sup>/dyne  
for Copper

T°K	C	C'	C <sub>11</sub> '	C <sub>11</sub>	C <sub>12</sub>	B <sub>s</sub>	$\chi_T$
300	0.758	0.2355	2.220	1.700	1.225	1.385	7.44
350	0.745	0.2305	2.190	1.675	1.215	1.370	7.56
400	0.731	0.2250	2.165	1.655	1.205	1.355	7.69
450	0.718	0.2200	2.135	1.635	1.195	1.345	7.80
500	0.704	0.2145	2.105	1.615	1.185	1.330	7.93
550	0.691	0.2095	2.075	1.595	1.175	1.315	8.06
600	0.677	0.2045	2.045	1.575	1.165	1.300	8.19
650	0.663	0.1990	2.020	1.555	1.155	1.290	8.33
700	0.650	0.1940	1.990	1.535	1.145	1.275	8.47
750	0.636	0.1885	1.960	1.515	1.135	1.260	8.63
800	0.623	0.1835	1.930	1.495	1.125	1.250	8.77

Table II. Adiabatic Elastic Constants in Units of  $10^{12}$  dyne/cm<sup>2</sup> and Isothermal Compressibility in Units of  $10^{-13}$  cm<sup>2</sup>/dyne for Silver

T°K	C	C'	C' <sub>11</sub>	C <sub>11</sub>	C <sub>12</sub>	B <sub>S</sub>	$\chi_T$
300	0.465	0.1525	1.555	1.240	0.940	1.040	10.00
350	0.455	0.1480	1.530	1.225	0.930	1.025	10.20
400	0.446	0.1440	1.510	1.205	0.920	1.015	10.40
450	0.436	0.1400	1.485	1.190	0.910	1.005	10.60
500	0.426	0.1360	1.460	1.170	0.900	0.990	10.80
550	0.417	0.1315	1.440	1.155	0.890	0.980	11.05
600	0.407	0.1275	1.415	1.135	0.880	0.965	11.25
650	0.398	0.1235	1.395	1.120	0.870	0.955	11.50
700	0.388	0.1195	1.370	1.100	0.860	0.940	11.75
750	0.379	0.1155	1.345	1.085	0.855	0.930	12.00
800	0.369	0.1110	1.325	1.065	0.845	0.915	12.25

Table III. Adiabatic Elastic Constants in Units of  $10^{12}$  dyne/cm<sup>2</sup> and Isothermal Compressibility in Units of  $10^{-13}$  cm<sup>2</sup>/dyne for Gold

T°K	C	C'	C' <sub>11</sub>	C <sub>11</sub>	C <sub>12</sub>	B <sub>s</sub>	$\alpha_T$
300	0.424	0.1485	2.200	1.925	1.630	1.725	6.01
350	0.417	0.1460	2.180	1.910	1.615	1.705	6.10
400	0.410	0.1435	2.155	1.890	1.605	1.700	6.19
450	0.403	0.1410	2.135	1.875	1.590	1.685	6.28
500	0.397	0.1385	2.115	1.850	1.580	1.670	6.38
550	0.390	0.1360	2.090	1.840	1.565	1.655	6.48
600	0.383	0.1335	2.070	1.820	1.555	1.645	6.58
650	0.376	0.1310	2.050	1.805	1.540	1.630	6.69
700	0.369	0.1285	2.025	1.785	1.530	1.620	6.80
750	0.362	0.1260	2.005	1.770	1.520	1.600	6.90
800	0.355	0.1235	1.985	1.755	1.505	1.580	7.06

Table IV. Comparison of Present Results with Literature Data at 300°K

Metal	Investigators	$G \times 10^{-12}$	$G' \times 10^{-12}$	$B_s \times 10^{-12}$	$\%T \times 10^{13}$
Cu	This Study	0.756	0.235	1.38	7.49
	Schmunk & Smith <sup>(20)</sup>	0.7489	0.2338	1.395	
	Overton & Giffney <sup>(12)</sup>	0.7539	0.2348	1.371	
	Goens & Weerts <sup>(21)</sup>	0.753	0.263	1.38	
	Lazarus <sup>(22)</sup>	0.756	0.235	1.40	
	Bridgman <sup>(4)</sup>				7.64
	Chang & Hultgren <sup>(7)</sup>				7.42
Ag	This Study	0.464	0.152	1.04	9.98
	Bacon & Smith <sup>(13)</sup>	0.4613	0.1528	1.036	
	Neighbours & Alers <sup>(14)</sup>	0.4612	0.1516	1.038	
	Corll <sup>(15)</sup>	0.4632	0.1527	1.038	
	Bridgman <sup>(4)</sup>				9.93
Au	This Study	0.424	0.149	1.73	6.01
	Neighbours & Alers <sup>(14)</sup>	0.4195	0.1460	1.729	
	Bridgman <sup>(4)</sup>				5.78

Table V. Thermal Variation of Elastic Constants of Cu, Ag, and Au

Expressed by  $-\frac{1}{C_{ij}} \frac{dC_{ij}}{dT}$  in parts /  $10^6$  °C at 300°K.

Metal	Investigator	-TC	-TC'	-TC' <sub>11</sub>	-TE <sub>100</sub>	-TE <sub>111</sub>
Cu	This Study	360	440	260	-	-
	Overton & Gaffney	370	425	240	-	-
Ag	This Study	410	540	295	515	380
	Neighbours & Alers	400	470	260	455	375
	Guinan, oxygen free	-	-	-	540	390
	Guinan, oxygen sat'd	-	-	-	-	380
Au	This Study	325	340	195	-	-
	Neighbours & Alers	300	340	190	-	-

Table VI. Values of Lindemann Parameter

T, °K	$A \times 10^{-5}$ in g-atom/cal		
	Cu	Ag	Au
300	1.67	2.21	1.97
400	1.67	2.16	1.97
500	1.67	2.15	1.97
600	1.67	2.08	1.95
700	1.64	2.06	1.95
800	1.61	2.05	1.92

## FIGURE CAPTIONS

- Figure 1. Elastic Constants of Cu as a Function of Temperature
- Figure 2. Elastic Constants of Ag as a Function of Temperature
- Figure 3. Elastic Constants of Au as a Function of Temperature
- Figure 4. The Young's Moduli in the Directions  $\langle 111 \rangle$  and  $\langle 100 \rangle$  for Ag as a Function of Temperature.



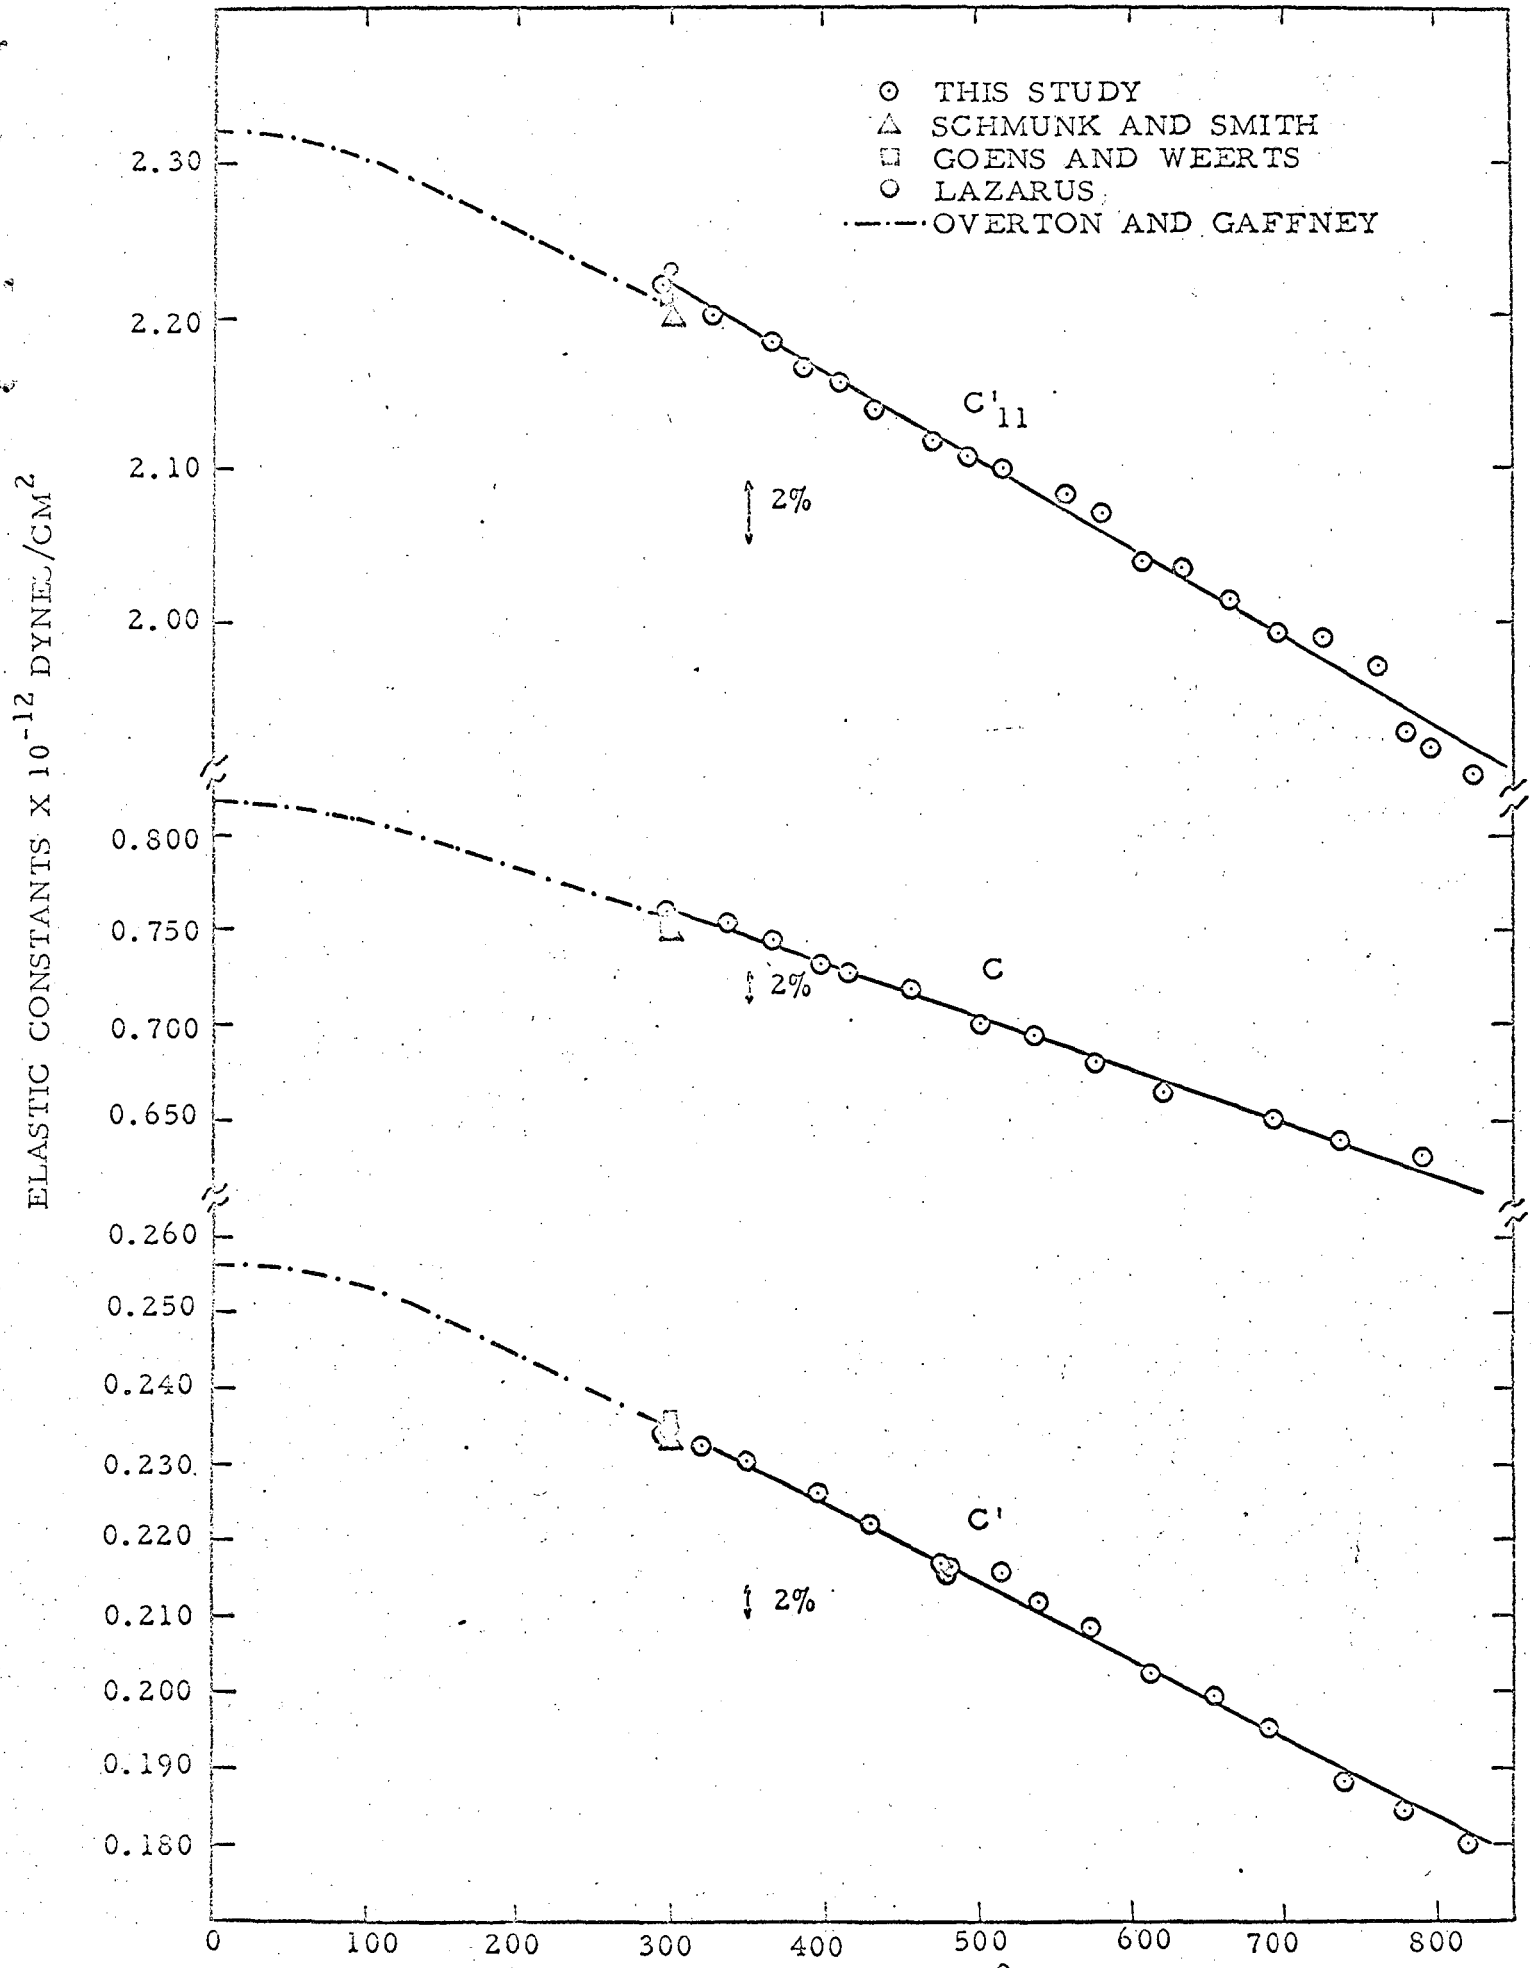


Fig 1

TEMPERATURE, °K



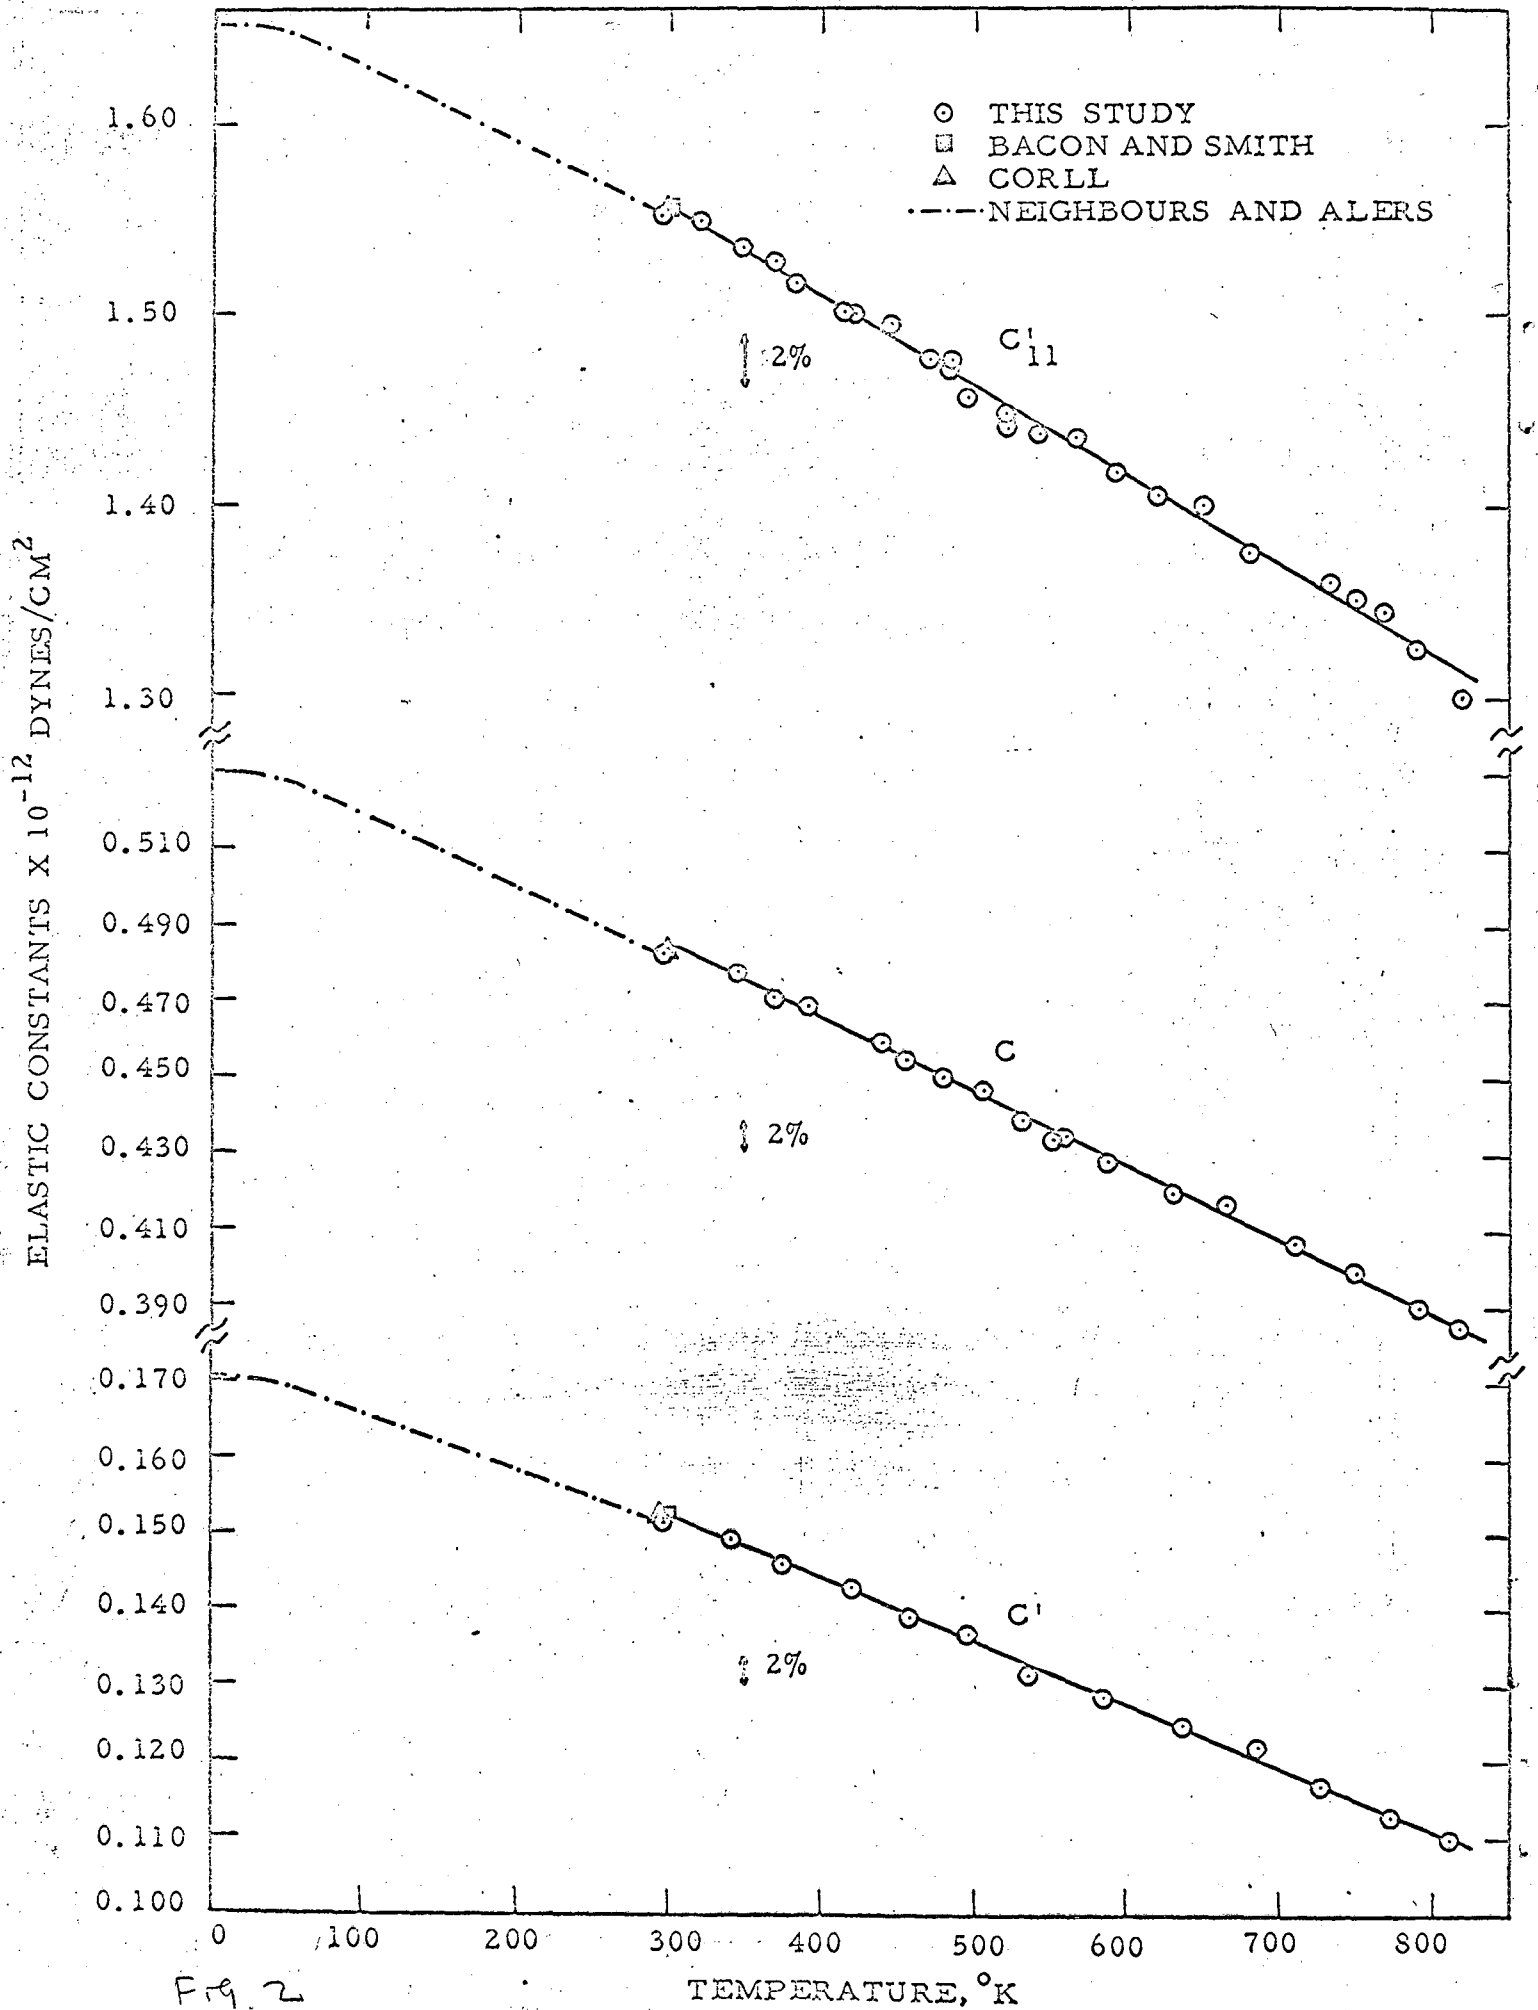


Fig 2

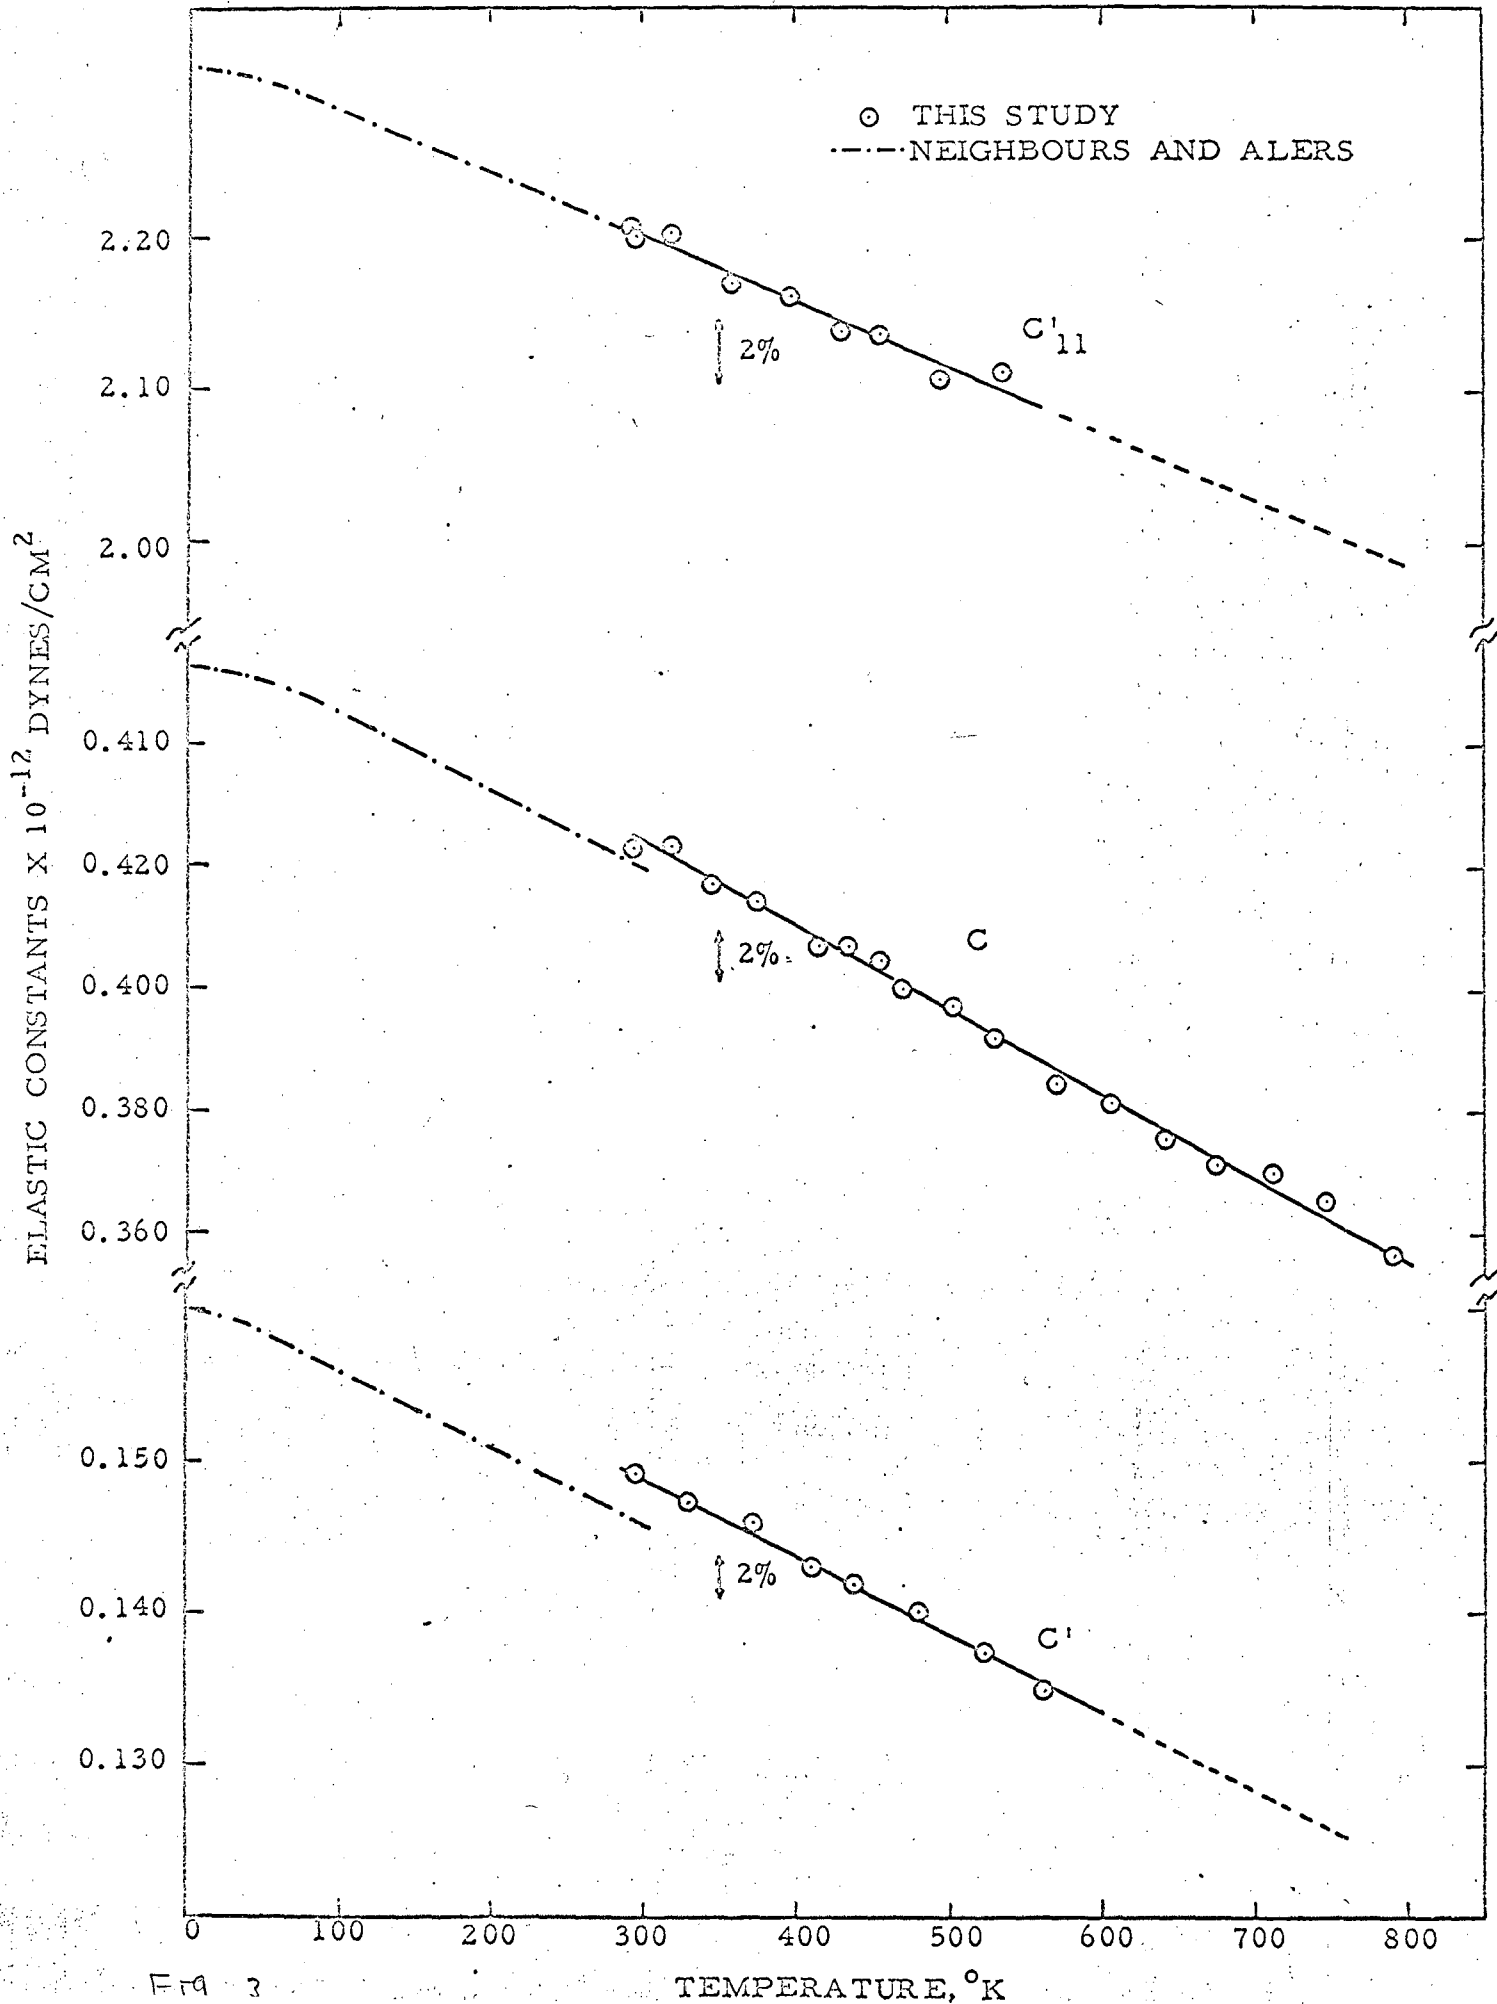

$E_{100}$  OR  $E_{111} \times 10^{-11}$  DYNE/CM<sup>2</sup>

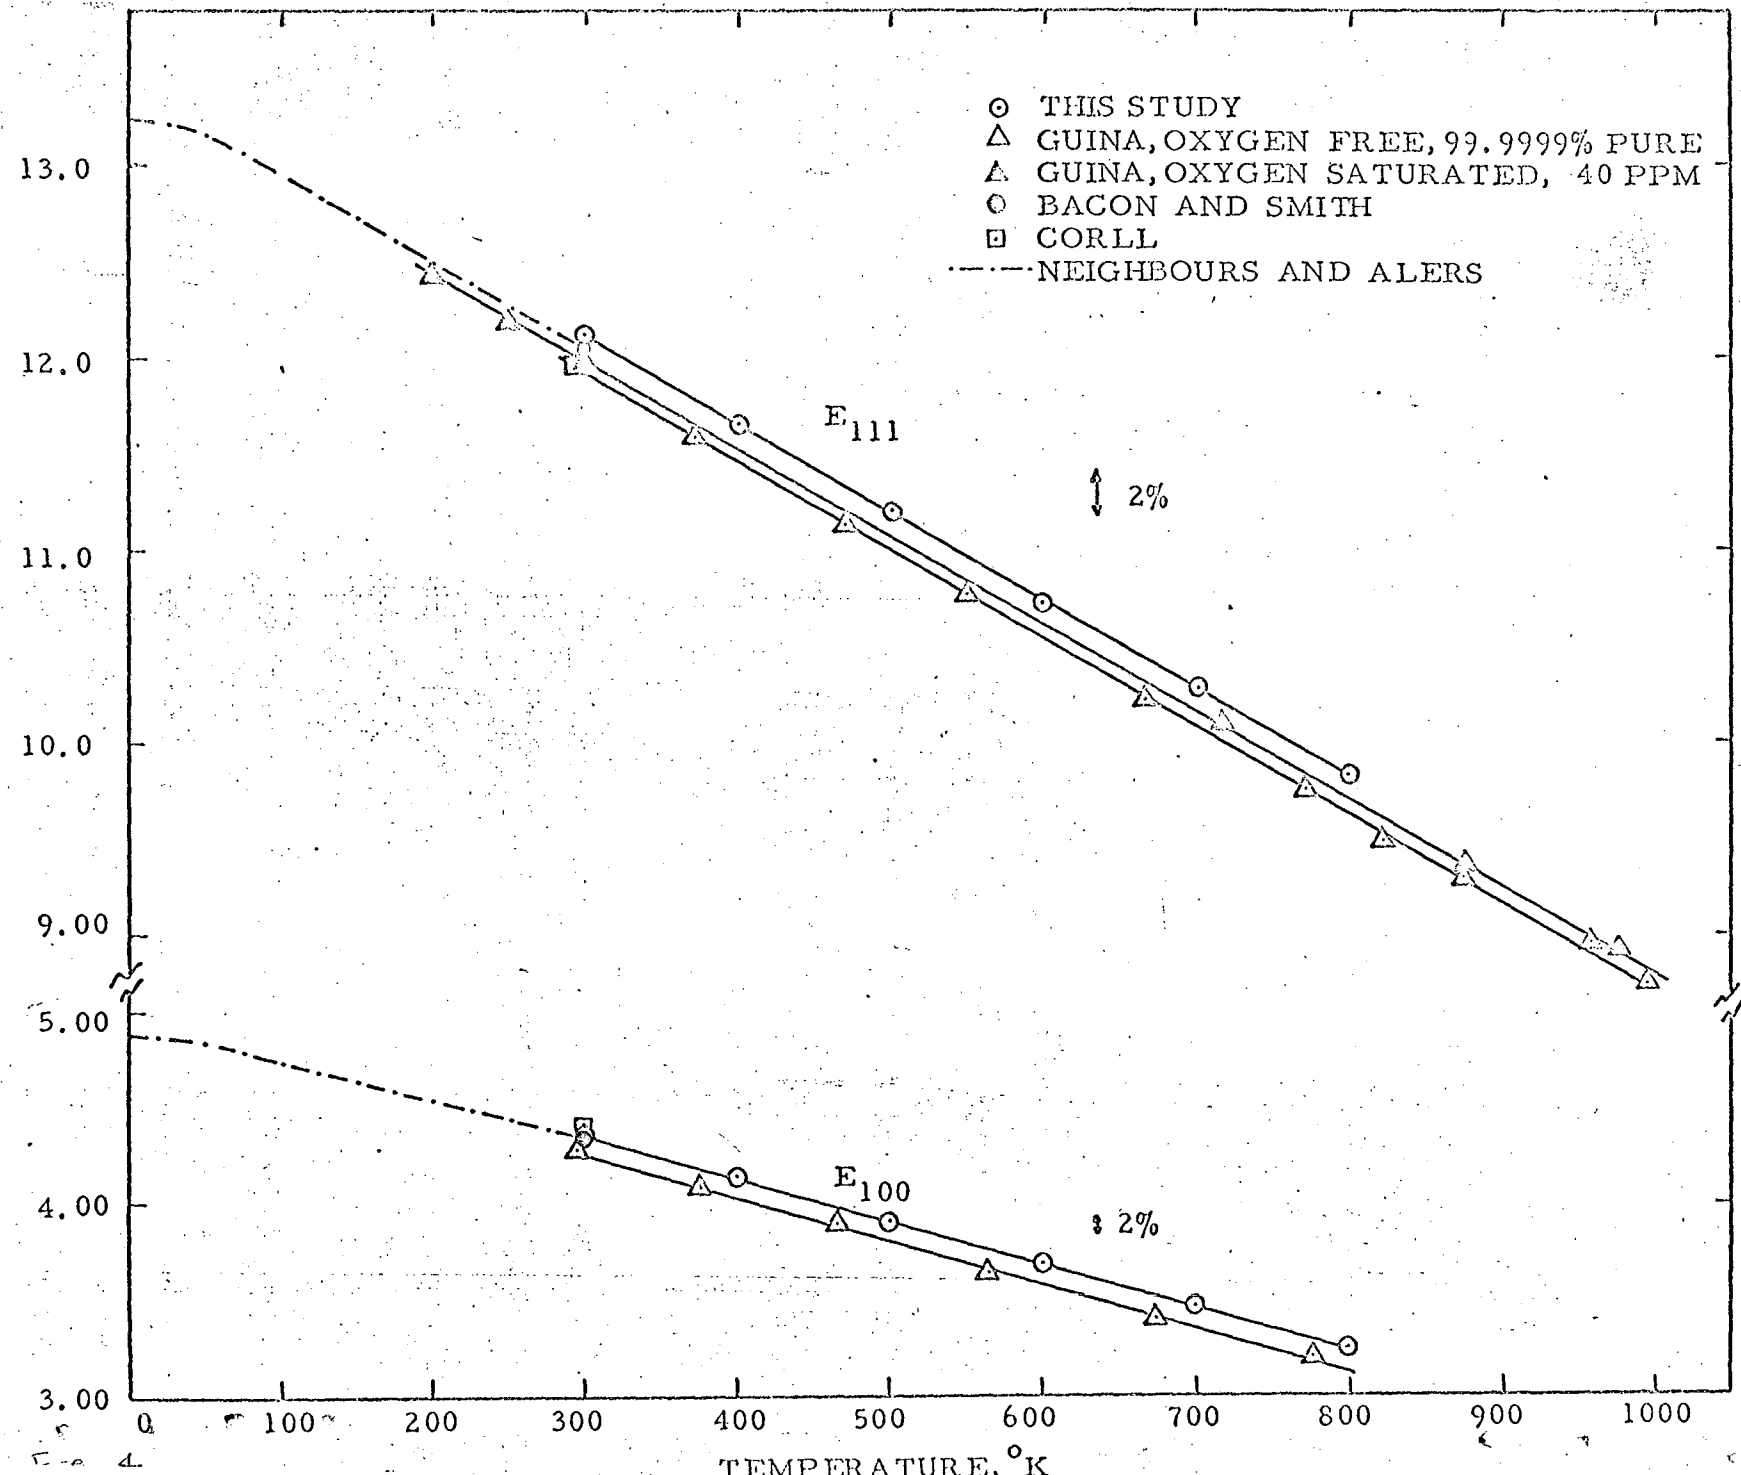

## REFERENCES

1. C. Zener, *J. Appl. Phys.*, 22, 372 (1951).
2. A.D. LeClaire, *Acta. Met.*, 1, 438 (1953).
3. M.W. Zemansky, Heat and Thermodynamics (McGraw-Hill Book Company, Inc., New York, 1957).
4. K.A. Gschneidner, Jr., *Solid State Physics*, 16, 275 (1964).
5. C. Zener, Elasticity and Anelasticity of Metals (the University of Chicago Press, Chicago, Illinois, 1948).
6. Sperry Attenuation Comparator Unit 56A001, Sperry Products Co., Danbury, Connecticut.
7. Y.A. Chang and R. Hultgren, to be published in the February issue, *J. Phys. Chem.*, (1966).
8. W.B. Pearson, A Handbook of Lattice Spacings and Structures of Metals and Alloys (Pergamon Press, 1958).
9. F. C. Nix and D. McNair, *Phys. Rev.*, 61, 74 (1942).
10. R. W. Balluffi and R. O. Simmons, *Phys. Rev.*, 119, 600 (1960).
11. W. Volk, Applied Statistics for Engineers (McGraw-Hill Book Company, Inc., New York, 1958).
12. W.C. Overton, Jr., and J. Gaffney, *Phys. Rev.*, 98, 969 (1955).
13. R. Bacon and C. S. Smith, *Acta. Met.*, 4, *Acta. Met.*, 4, 337 (1956).
14. J.R. Neighbours and G.A. Alers, *Phys. Rev.*, 111, 707 (1958).
15. J.A. Corll, Office of Naval Research, Technical Report No. 5., Contract Nonr-1141 (05), Project NR 017-309 (1961).
16. M. Guinan, Ph.D. Thesis, University of California (1966).
17. P. Mason, Physical Acoustics and the Properties of Solids, (D. VanNostrand Company, Inc., New York, 1958).
18. H.B. Huntington, *Solid State Physics*, 7, 213 (1958).
19. R. Hultgren, R.L. Orr, P.D. Anderson, and K.K. Kelley, Selected Values of Thermodynamic Properties of Metals and Alloys, (John Wiley & Sons., Inc., 1963).

## REFERENCES (cont'd)

20. R. E. Schmunk and C. S. Smith, *Acta. Met.*, 8, 396 (1960).
21. E. Goens and J. Weerts, *Physik. Z.*, 37, 321 (1936).
22. D. Lazarus, *Phys. Rev.*, 76, 545 (1949).

ACKNOWLEDGEMENT

5        This work was supported by the U. S. Atomic Energy Commission.  
The authors wish to thank Dr. M. Guinan for his valuable comments and  
review of the manuscript.

This report was prepared as an account of Government sponsored work. Neither the United States, nor the Commission, nor any person acting on behalf of the Commission:

- A. Makes any warranty or representation, expressed or implied, with respect to the accuracy, completeness, or usefulness of the information contained in this report, or that the use of any information, apparatus, method, or process disclosed in this report may not infringe privately owned rights; or
- B. Assumes any liabilities with respect to the use of, or for damages resulting from the use of any information, apparatus, method, or process disclosed in this report.

As used in the above, "person acting on behalf of the Commission" includes any employee or contractor of the Commission, or employee of such contractor, to the extent that such employee or contractor of the Commission, or employee of such contractor prepares, disseminates, or provides access to, any information pursuant to his employment or contract with the Commission, or his employment with such contractor.



