

Lawrence Berkeley National Laboratory

Recent Work

Title

ELECTRICAL LOSS MEASUREMENTS IN A NbTi MAGNET

Permalink

<https://escholarship.org/uc/item/5v70c84r>

Author

Voelker, Ferd

Publication Date

1968-07-25

UCRL-18374

C.2

RECEIVED
UNIVERSITY OF CALIFORNIA
RADIATION LABORATORY

SEP 3 1968

LIBRARY AND DOCUMENTS SECTION

University of California

Ernest O. Lawrence
Radiation Laboratory

ELECTRICAL LOSS MEASUREMENTS IN A NbTi MAGNET

Ferd Voelker

July 25, 1968

Berkeley, California

UCRL-18374
C.2

I

DISCLAIMER

This document was prepared as an account of work sponsored by the United States Government. While this document is believed to contain correct information, neither the United States Government nor any agency thereof, nor the Regents of the University of California, nor any of their employees, makes any warranty, express or implied, or assumes any legal responsibility for the accuracy, completeness, or usefulness of any information, apparatus, product, or process disclosed, or represents that its use would not infringe privately owned rights. Reference herein to any specific commercial product, process, or service by its trade name, trademark, manufacturer, or otherwise, does not necessarily constitute or imply its endorsement, recommendation, or favoring by the United States Government or any agency thereof, or the Regents of the University of California. The views and opinions of authors expressed herein do not necessarily state or reflect those of the United States Government or any agency thereof or the Regents of the University of California.

For BNL Superconducting Summer Study
Upton, L.I., N.Y., June 10 - July 16, 1968

UCRL-18374
Preprint

UNIVERSITY OF CALIFORNIA

Lawrence Radiation Laboratory
Berkeley, California

AEC Contract No. W-7405-eng-48

ELECTRICAL LOSS MEASUREMENTS IN A NbTi MAGNET

Ferd Voelker

July 25, 1968

ELECTRICAL LOSS MEASUREMENTS IN A NbTi MAGNET*

Ferd Voelker

Lawrence Radiation Laboratory
University of California
Berkeley, California

July 25, 1968

I. Introduction

Our work on ac losses has been mostly with NbTi wire magnets. These magnets were built for direct current use, but since they were available to us, it was convenient to use them while developing an electrical method of measuring losses.

First, I shall describe this electrical method and then describe some of our results. I shall talk mostly about results obtained since our earlier report⁽¹⁾.

Most of the results that will be described here were made on a solenoid wound with Supercon NbTi wire which had a 0.015 inch diameter superconducting core in a copper wire of 0.03 inch overall diameter. The wire was insulated turn-to-turn with a copper-oxide surface, and layer-to-layer with fiberglass cloth. The maximum field on axis was about 70 kG at 120 A. The winding had a 1.5 inch inner diameter, 4.5 inch outer diameter, and was 4.5 inches long.

*Work performed under the auspices of the U.S. Atomic Energy Commission.

1. Gilbert, Hintz, Voelker, UCRL-18176, April 1968.

II. Loss Measurements

This method of measuring losses depends on measuring the accumulated electrical energy entering the magnet over a period of several cycles. This is accomplished with the circuit shown in Fig. 1. The two key elements are a multiplying circuit to obtain instantaneous power flow between the magnet and power supply, and an integrator to keep track of electrical energy balance into the superconducting magnet.

The multiplier circuit works in the following way. It uses a semiconductor Hall device which develops an output voltage proportional to the product of input current to the Hall device, and magnetic field surrounding the device. A pair of potential leads inserted into the cryostat connects the test magnet to the Hall device through a resistor, so that current input to the Hall device is proportional to the magnet voltage. The Hall device is mounted in the gap of a small magnet which has been designed to give a magnetic field proportional to current in its windings. This magnet is put in series with the superconducting magnet so that the Hall device has a magnetic field input proportional to the current in the SC magnet. The inputs to the Hall device then, are proportional to voltage across the SC magnet, and to current through it, and hence the output of the Hall device is a voltage proportional to instantaneous power into the SC magnet. This output voltage changes polarity with the direction of power flow.

The integrator uses a solid-state chopper-input operational amplifier with a feed-back capacitor C, and a series resistor R, so that its output voltage is

$$e_{\text{out}} = \frac{1}{RC} \int_0^T e_{\text{in}}(t) dt.$$

Drift in the integrator circuit appears on the recorder as an equivalent power loss (except that it can have either sign), and so must be kept small. Typically, we had about 1 mV drift for a period of 1000 seconds with a dynamic range of 10 V. For one particular multiplier constant this corresponds to a sensitivity of 1 joule in a 1000 seconds (or 1 milliwatt) with a dynamic range of 10000 joules (stored in the magnet).

We obtained a 1 joule sensitivity on a cycle-to-cycle basis by using a digital voltmeter to read the voltage on successive minimums of the integrator output.

A section of the multiple recorder tracing illustrating how the loss information is presented, is shown in Fig. 2. Here the current had a triangular waveform with a peak amplitude of 10 A. The middle trace shows the accumulated energy over a number of cycles as the frequency was increased. The slope of the envelope is directly proportional to the ac losses. (The boil-off gas was almost constant over this run, and change in slope of the right-hand trace is due to changes in chart speed).

Another kind of data sheet is shown in Fig. 3. In this case, the current waveform is trapezoidal with a constant $\frac{di}{dt}$. Several cycles were run at each current. The constant current intervals were long enough to allow us to read the integrator output with a digital voltmeter. The trace labeled \dot{B} shows an increasing amount of flux jumping as the current was increased, and more will be said about this later.

III. Experimental Results

While making cycle to cycle loss measurements with a trapezoidal current waveform, we discovered that the first cycle at a new current level had considerably more energy loss than succeeding cycles. On a well stabilized coil we reached an asymptotic value within two or three cycles, while on another coil with less stabilization, it took four or five cycles. When there was a flux jump during a given cycle, the next cycle was extraordinarily lossy. Fig. 4 shows several types of information relating to the cycle to cycle losses. The loss in joules/cycle is given as a function of the maximum current. Note that there is an envelope of asymptotic values obtained by pulsing a number of times at the same current. The first-cycle envelope was obtained by reversing the direction of current in the magnet at the beginning of each new current value to destroy the "ordering" effect.

The energy loss on a cycle after a flux jump, or after increasing current without reversing direction always lay somewhere between the two envelopes. The maximum current of 116A corresponds to about 67 kG on axis in the solenoid.

In general, the measured losses were within about a factor of two of values calculated by the loss equation in Hancox⁽²⁾. We were also able to measure losses over a partial cycle. For example, the current was varied from 0-10A several times then from 10-20A several times, continuing on up to 100A. The losses for this data are given in Fig. 4 as a partial-cycle envelope. Data for several values of ΔI are shown. Since we could record the maximum energy in the coil, as well as the minimum, we were able to measure the stored energy. Fig. 5 shows the Q (stored energy/energy loss per cycle) as a function of maximum current during a cycle. The Q had a minimum at around 50A, which probably corresponds to the current at which the average of the winding has complete field penetration in the superconductor. We can also calculate the inductance using the relationship: stored energy = $1/2 LI^2$. The inductance is not constant, and is shown as a function of current in Fig. 5.

We are interested in ac losses at typical synchrotron repetition rates, and we have made several runs on our magnets at cycling rates as high as once a second, although these magnets were not designed to be pulsed, and even though the losses are very high. Fig. 6 shows typical results on the magnet previously described. The loss in joules/cycle are shown as a function of frequency. The maximum current was 10A, 14A, and 20A with triangular, sinusoidal, and trapezoidal waveforms. The 20A data had to be taken a few cycles at a time in order to keep the magnet from going normal, and so only trapezoidal waveforms were used. At 14A the magnet could only be pulsed for 8 - 10 cycles at the higher frequencies, and we suspect that the magnet was heating considerably. The different waveforms merely indicate that the losses are related to $\frac{dI}{dt}$, as well as maximum current.

All of these curves show a rise in losses at very low cycling rates. This is because of a constant 60 cycle ripple voltage. When the cycling times are very long, the loss due to ripple voltage

2. R. Hancox, Proc. IEEE 113, 1221 (1966).

accumulates over a longer period and makes data below about 0.05 Hz unreliable. Tests made last week with a transistor-regulated (very low ripple) power supply indicate that the losses are linear with frequency at the low end.

If we calculate eddy currents at 0.5 Hz with a 0 - 14A triangular waveform in the copper, we obtain a loss of about 0.53 watts. The magnet was wound on a thin stainless steel form and had end flanges of the same material. We calculate 0.272 watts loss in each flange and 0.002 watts loss for the tube. The total eddy current losses, then, should be

$$P_T = 0.53 + 2 \times .272 + .002 = 1.1 \text{ watt.}$$

From Fig. 6, we see that the losses for 0-14A at 0.5 Hz are about 9 J/cycle or 4.5 watts. Thus, the measured eddy current losses are about four times larger than we can account for⁽³⁾.

Data is shown in Fig. 7 for trapezoidal current waveforms in which the losses were measured after each cycle. (Fig. 3 is a typical data sheet for this kind of run.) The maximum current was increased while the $\frac{dI}{dt}$ was held fixed. If one neglects the repetitive data for very low $\frac{dI}{dt}$ because it contains appreciable losses due to ripple voltage, we see a definite increase in losses due to increasing $\frac{dI}{dt}$. There is a large scatter in data, however, because each pulse has a different loss, depending on the previous history of current, and whether a flux jump occurred in the previous cycle. At the higher currents this scatter is more pronounced as there were often several flux jumps in each cycle.

IV. Conclusions


We feel that this electrical method can be very useful for measuring ac losses in superconducting magnets, or in parts of such magnets. Since accumulated energy can be monitored at many currents during

3. Note added in proof: It has been suggested by several people subsequent to this talk, that the copper oxide is not insulating well and that the extra losses are $\frac{V^2}{R}$ losses due to parallel resistance paths from turn-to-turn. This kind of loss would have the right frequency dependence.

a cycle, it is possible to measure losses and stored energy during the parts of a cycle, which may help to separate some of the complicated phenomena taking place during the cycle.

We are building a magnet which will be a duplicate of the magnet that I have been describing, except that it will be wound with AIRCO multiple strand wire. The new wire has 130 strands of 1 mil NbTi wire in the same cross-section of copper. We hope to compare its performance with its solid-wire sister in time to be presented later in this conference. ⁽⁴⁾

4. Note added in proof: The magnet tests on the AIRCO magnet were completed and are given by W. S. Gilbert in a later session of this conference.

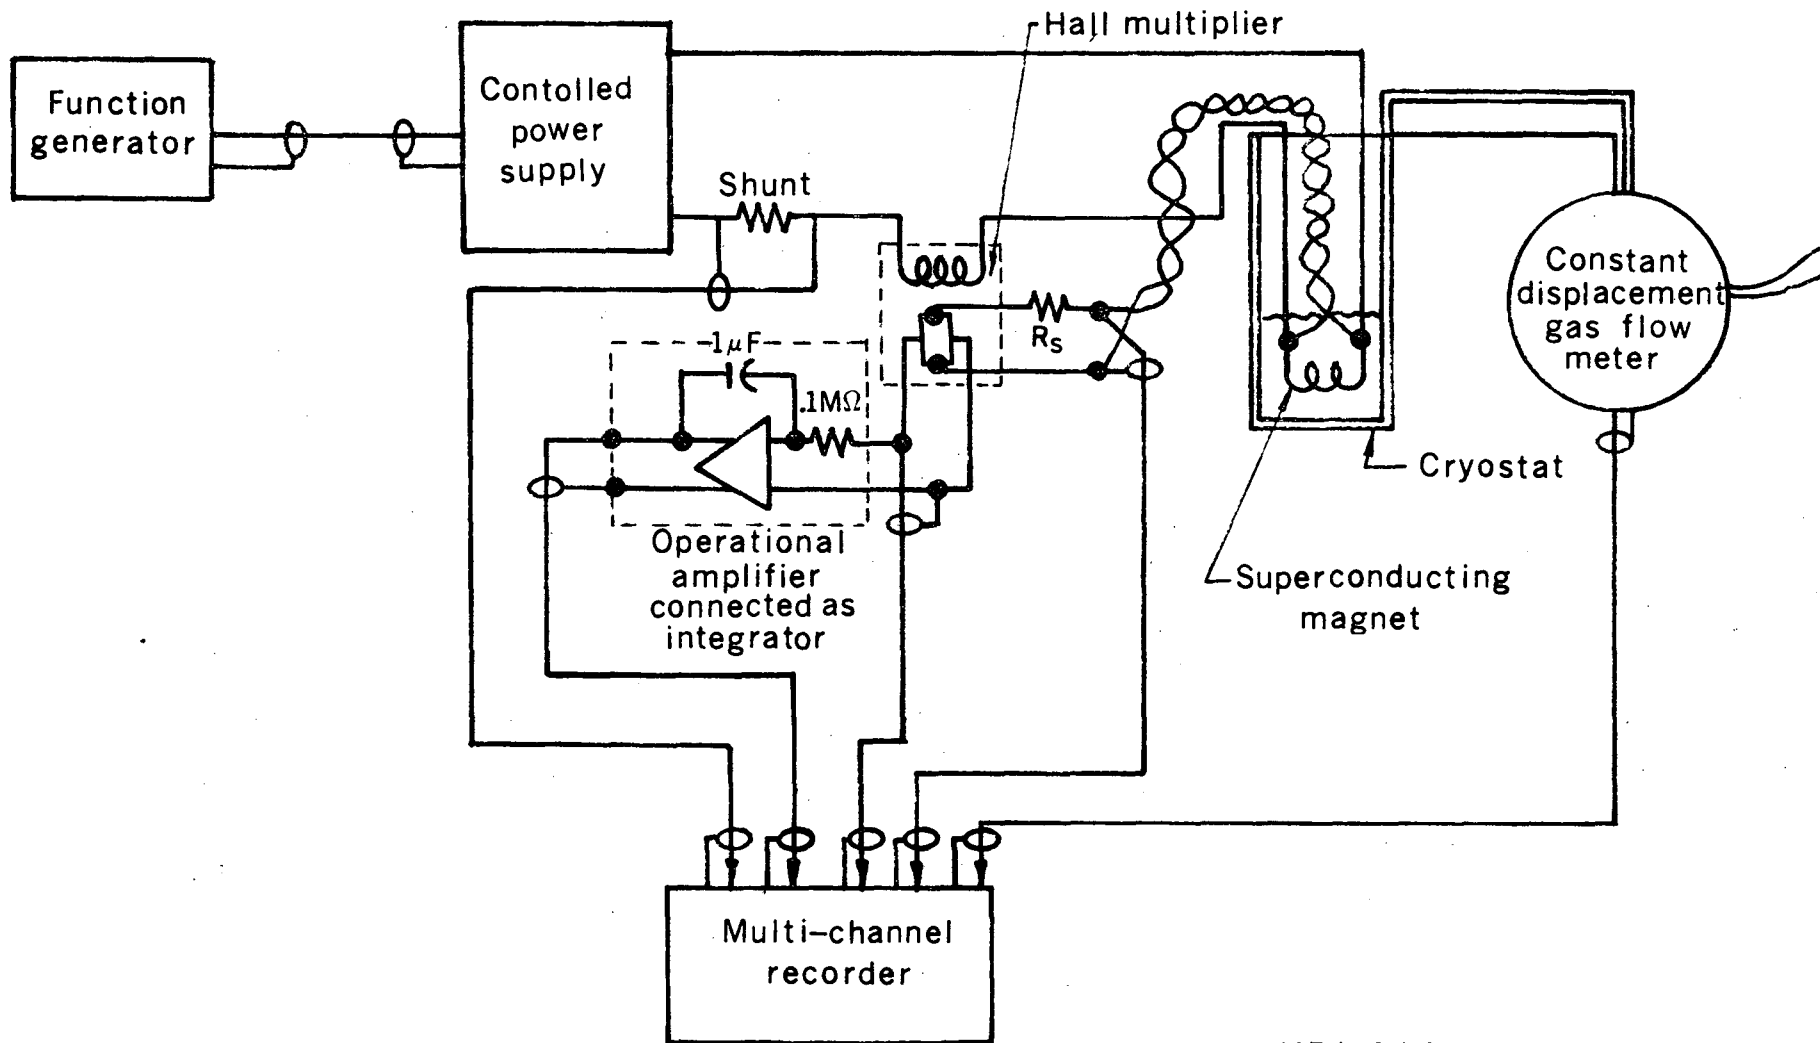

XBL 682 4489

Fig. 1 - Schematic representation of pulsed loss experiments.

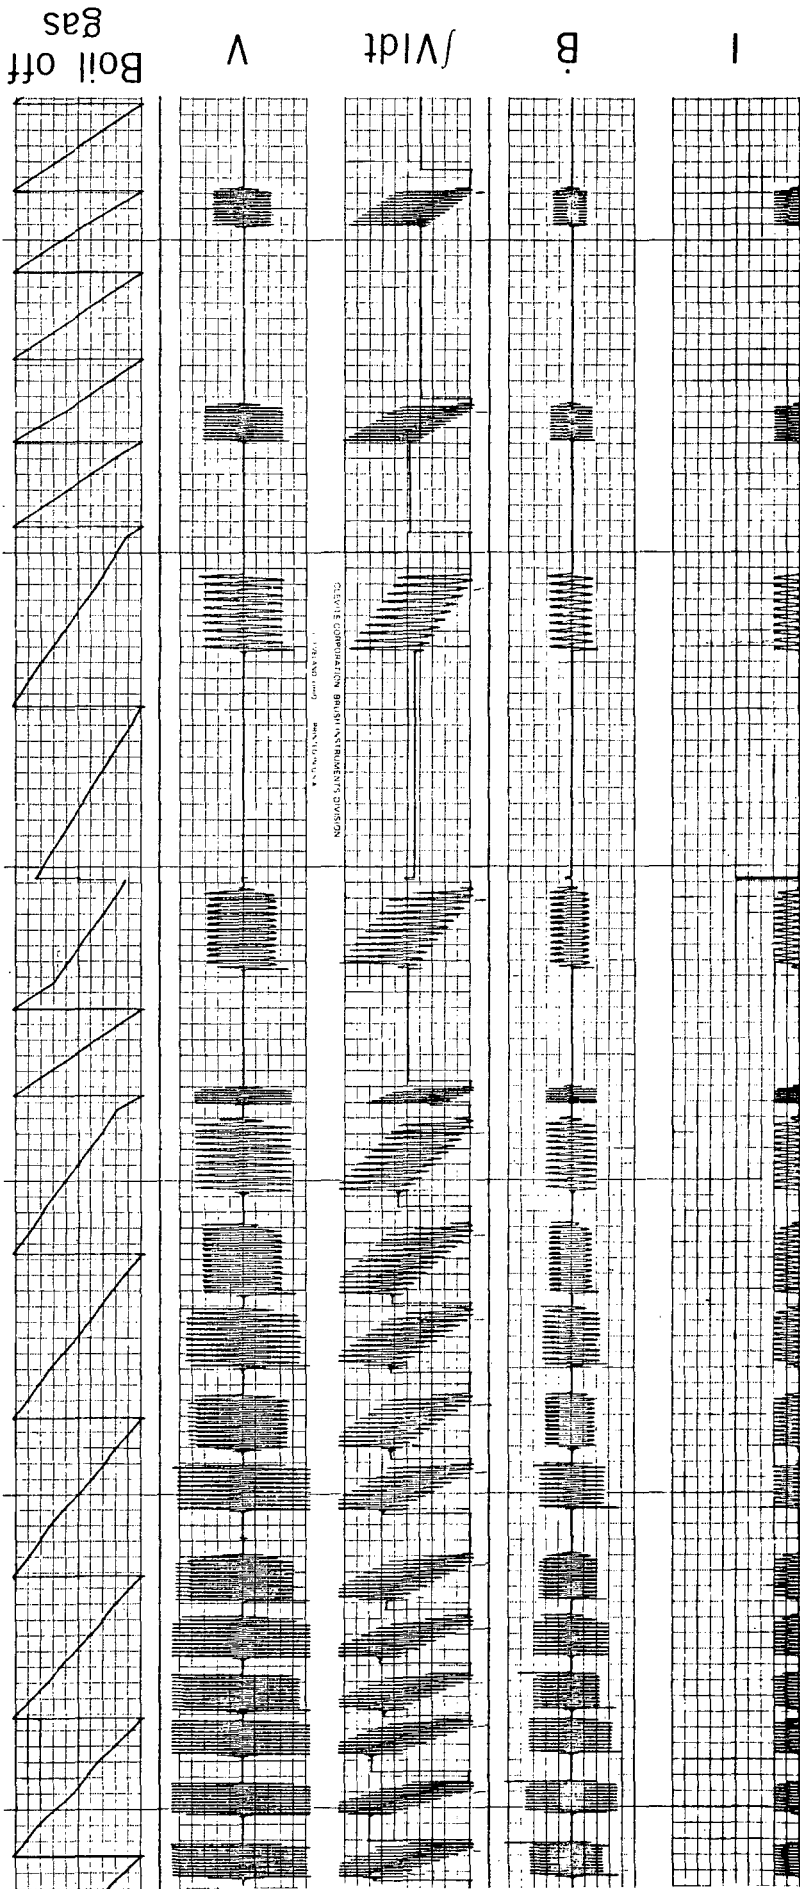


Fig. 2 - Data for frequency run

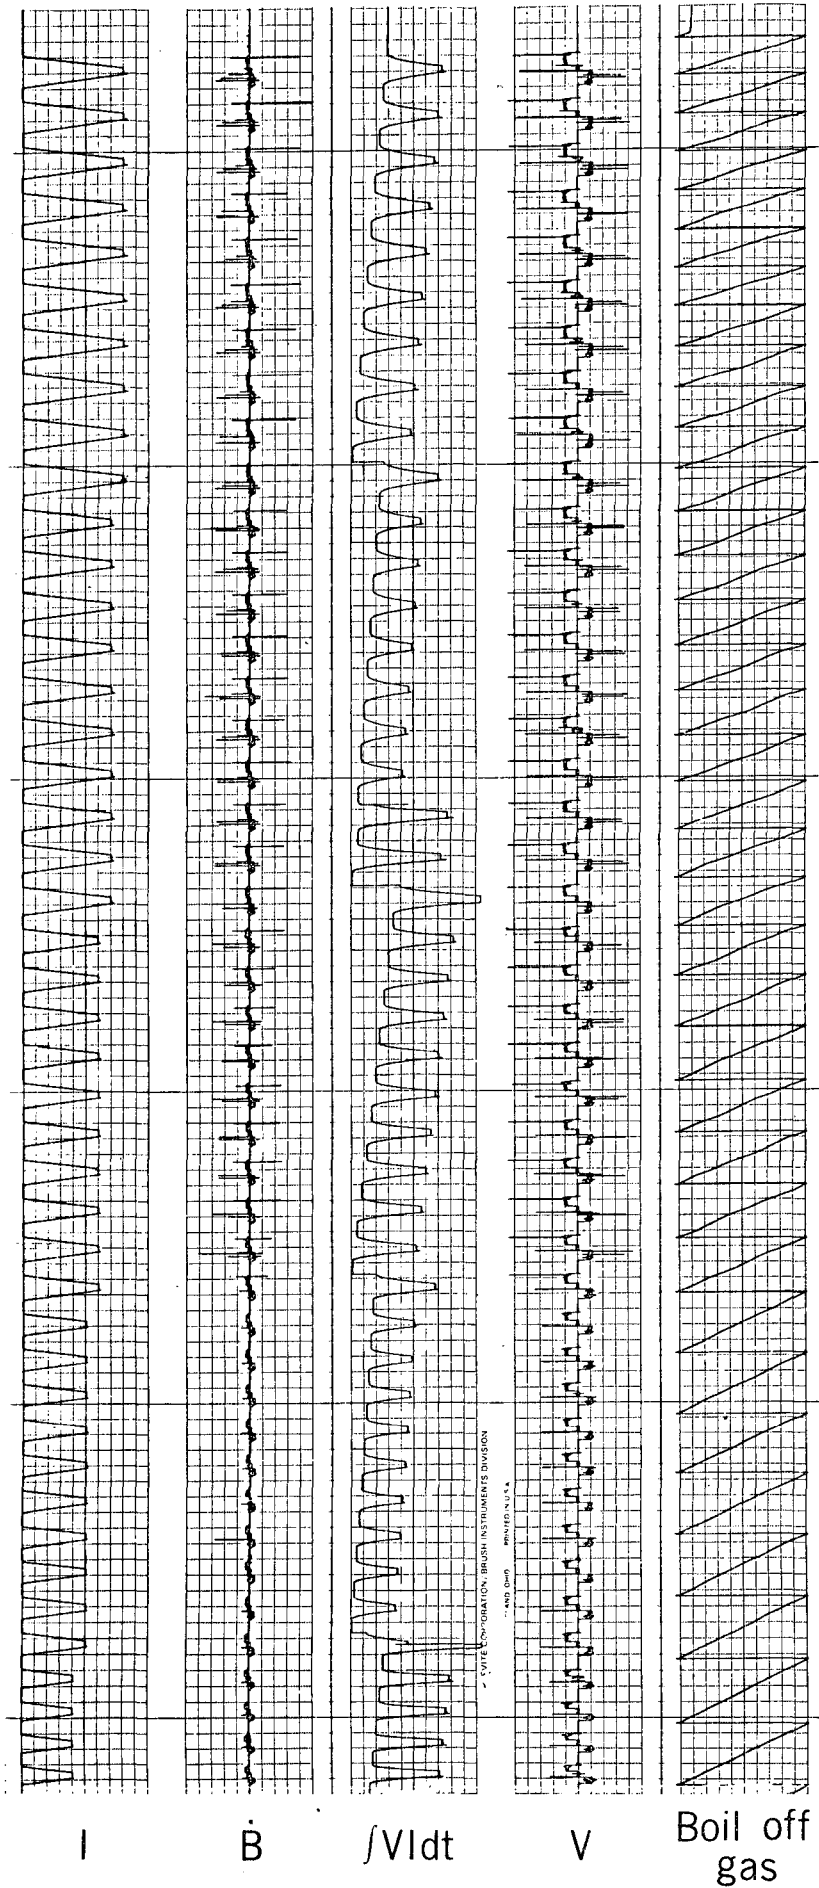


Fig. 3 - Data for constant $\frac{dI}{dt}$ run

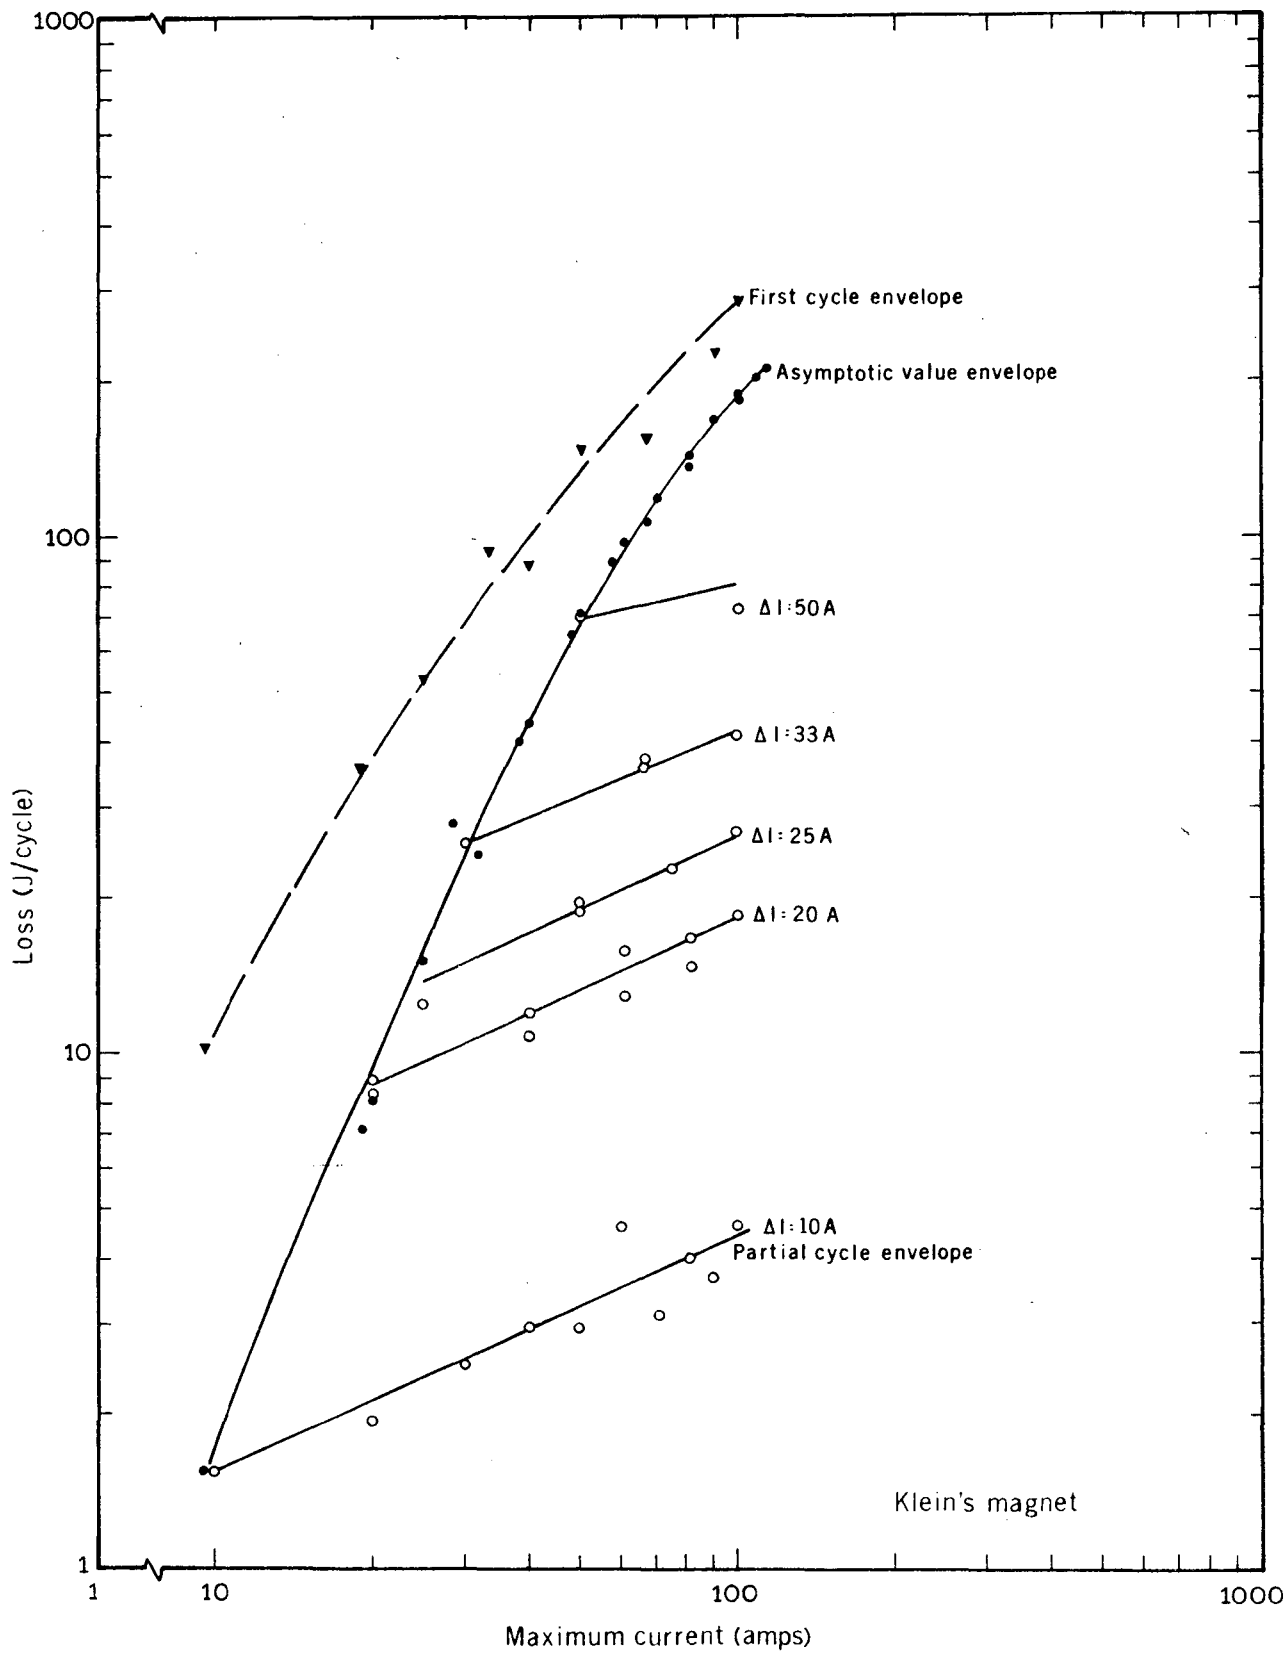


Fig. 4 - Hysteresis losses

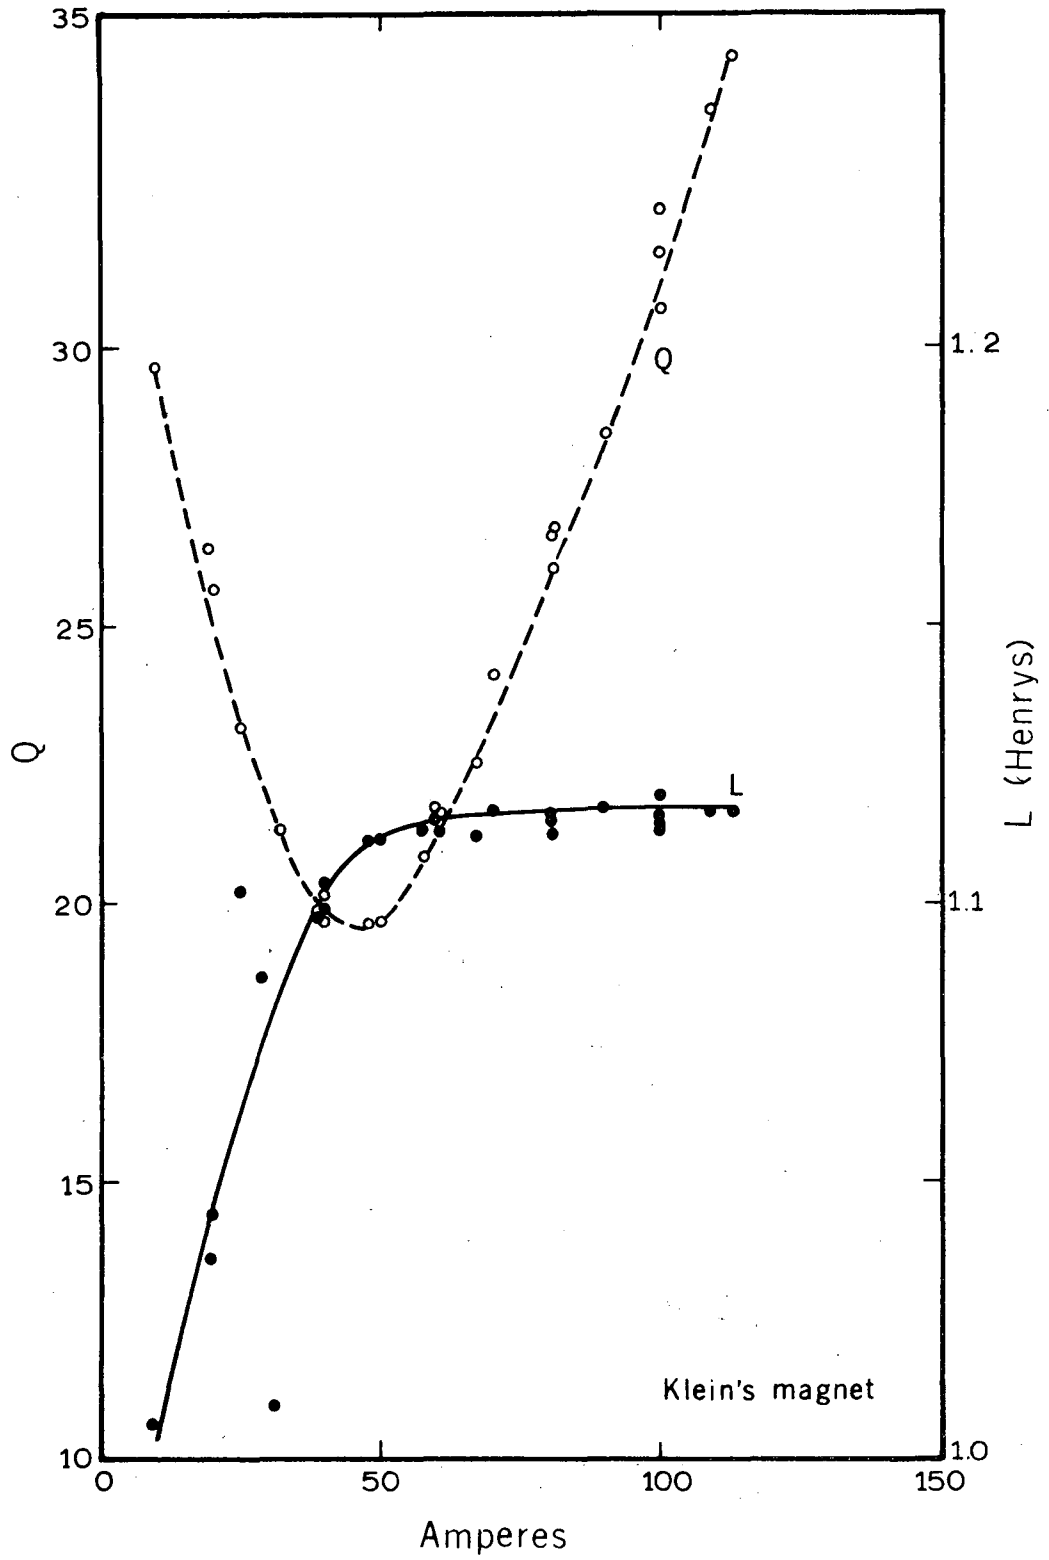


Fig. 5 - Q and L as a function of maximum current

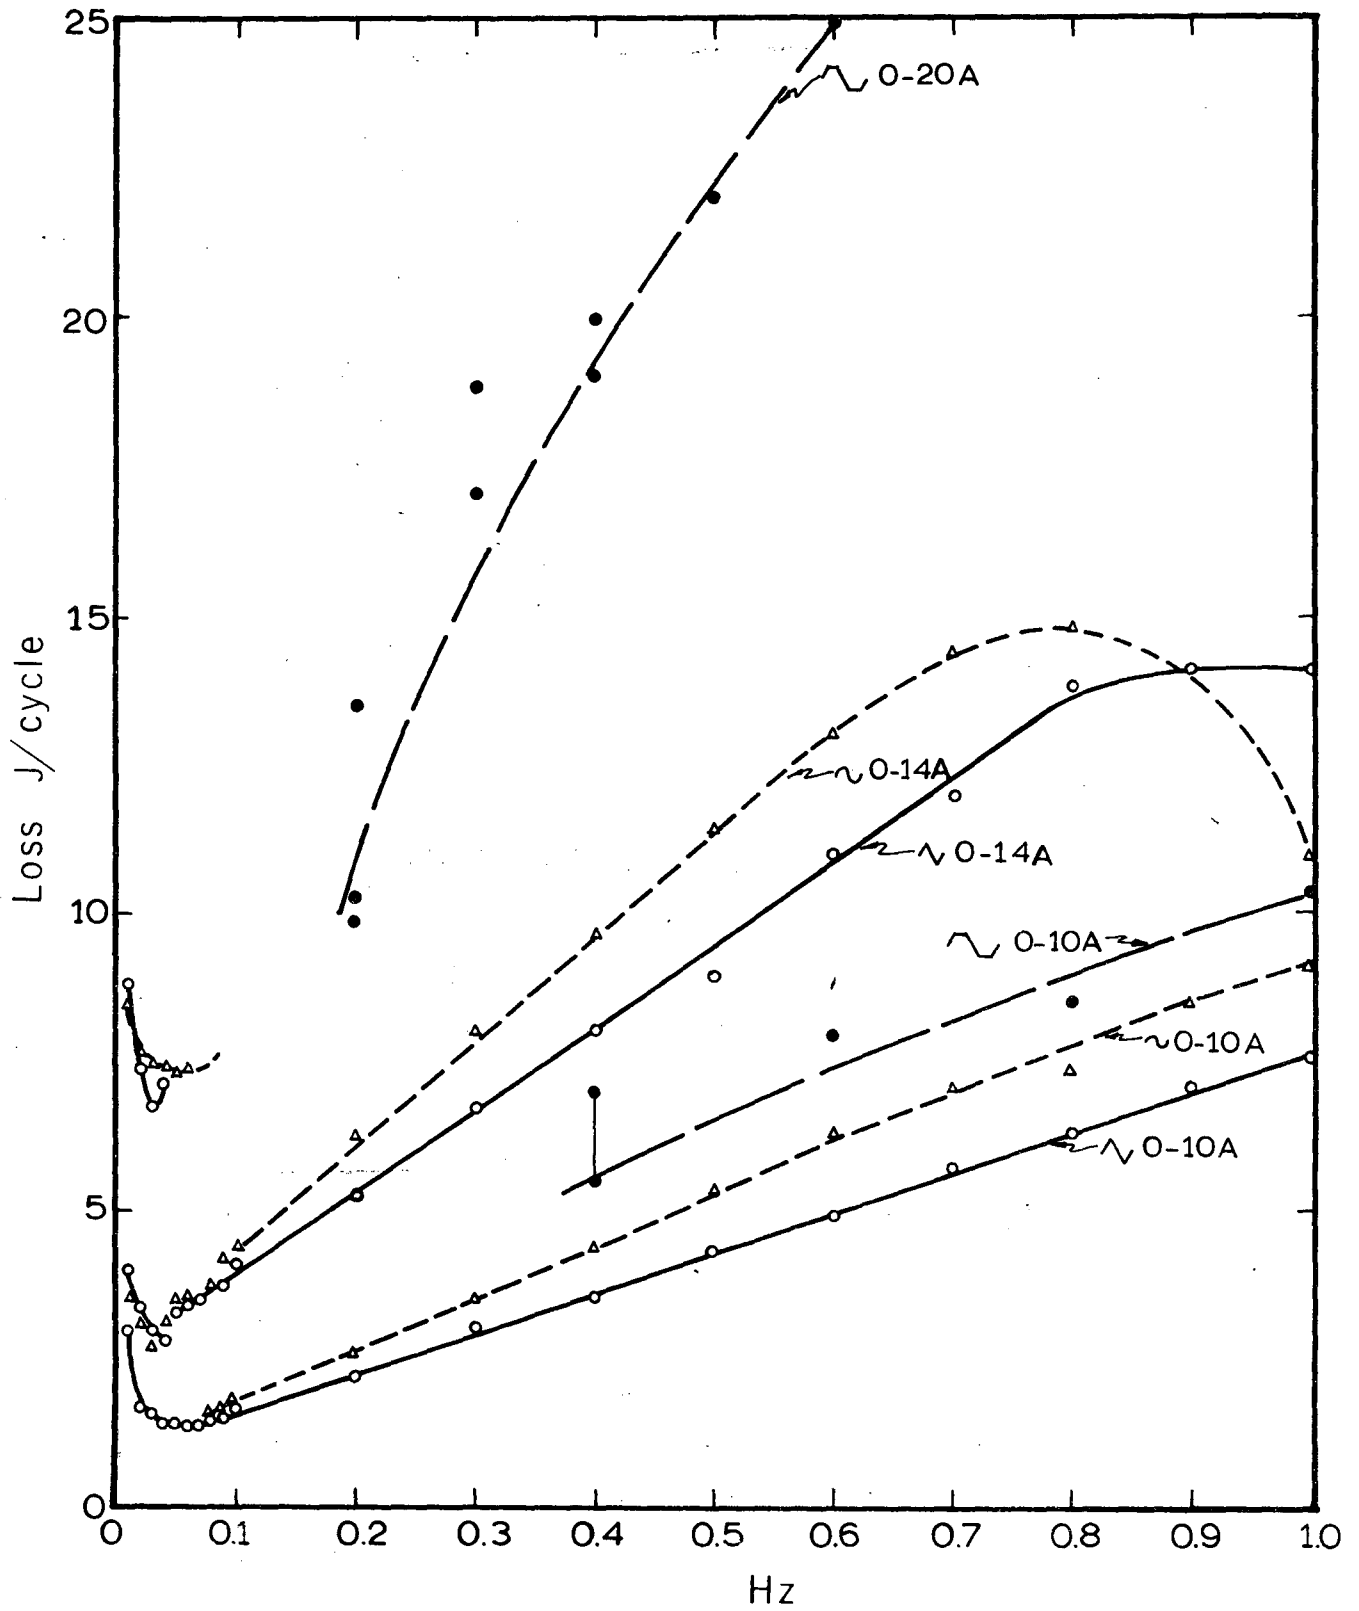


Fig. 6 - Eddy current losses

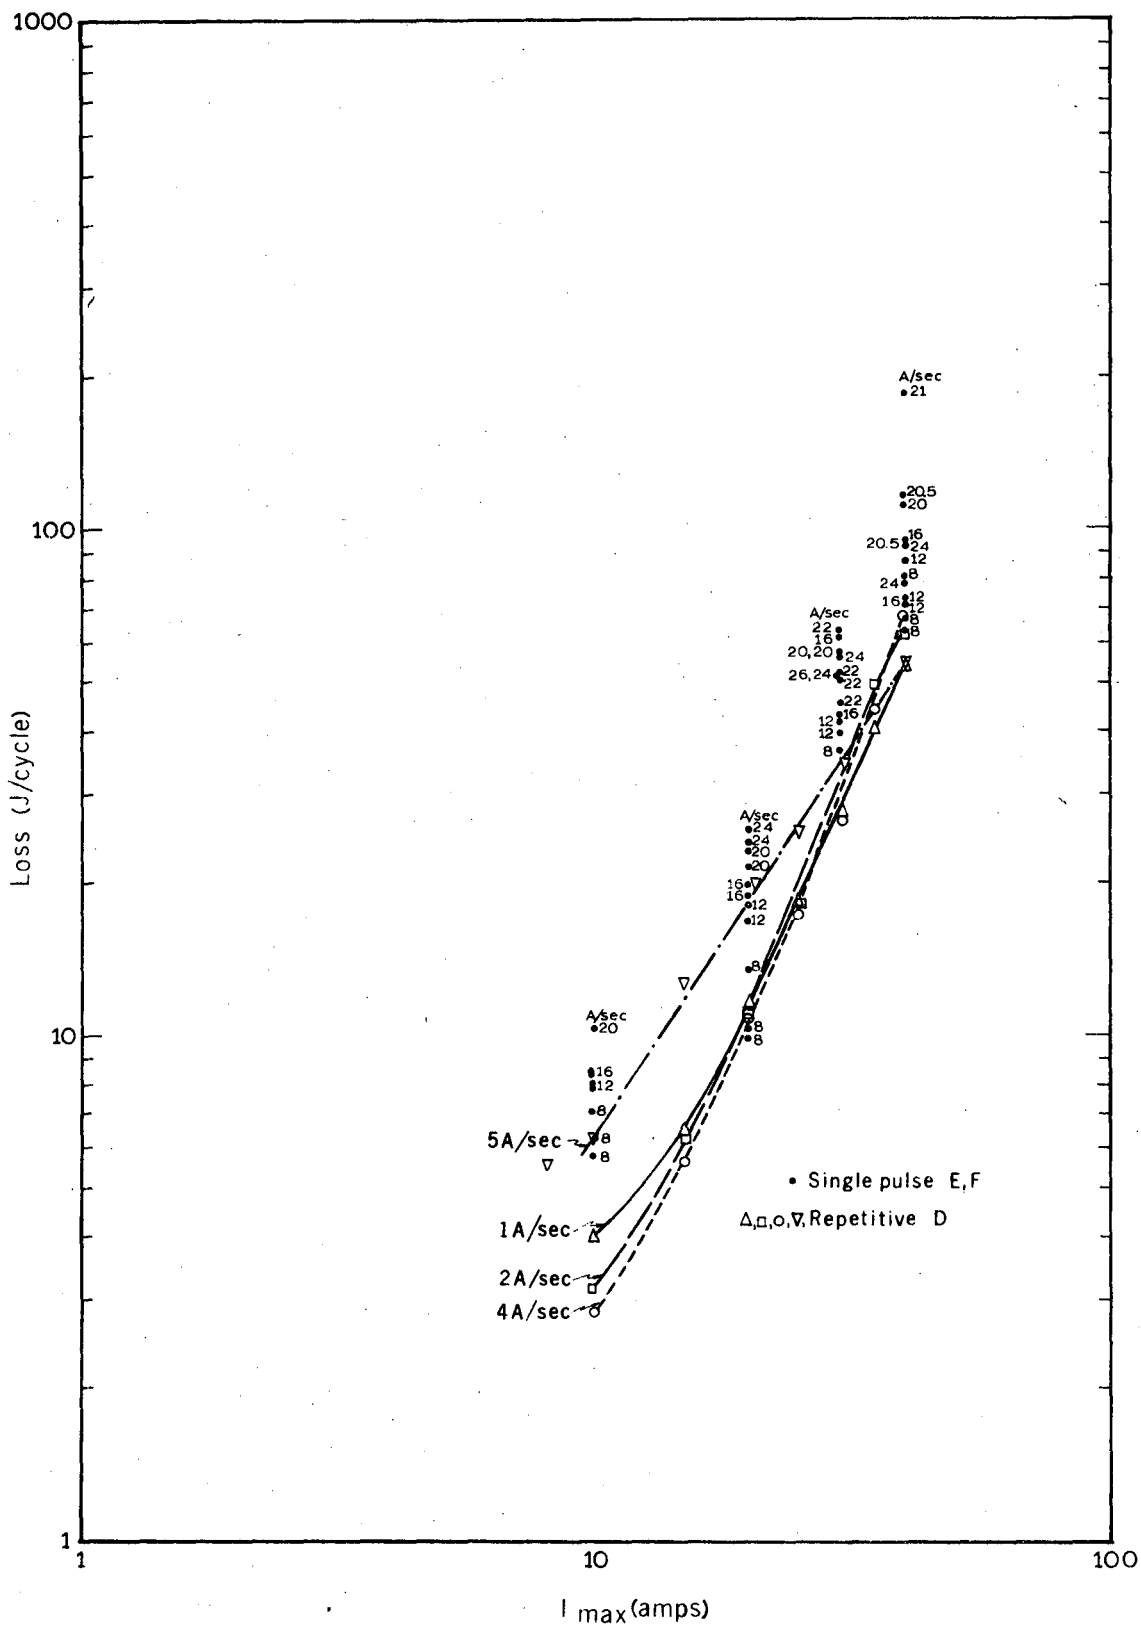


Fig. 7 - Losses as a function of $\frac{dI}{dt}$