

Lawrence Berkeley National Laboratory

LBL Publications

Title

Vapor-Liquid Equilibria for Binary Solutions of Polyisobutylene in C6 through C9 n-Alkanes

Permalink

<https://escholarship.org/uc/item/64p6h89g>

Authors

Lieu, John G

Prausnitz, John M

Publication Date

1999-02-01

Copyright Information

This work is made available under the terms of a Creative Commons Attribution License, available at <https://creativecommons.org/licenses/by/4.0/>



LBNL-42898
Preprint

ERNEST ORLANDO LAWRENCE BERKELEY NATIONAL LABORATORY

Vapor-Liquid Equilibria for Binary Solutions of Polyisobutylene in C_6 through C_9 n-Alkanes

John G. Lieu and John M. Prausnitz
Chemical Sciences Division

February 1999

Submitted to
Polymer



Lawrence Berkeley National Laboratory
Bldg. 50 Library - Ref.

REFERENCE COPY
Does Not
Circulate

Copy 1

LBNL-42898

DISCLAIMER

This document was prepared as an account of work sponsored by the United States Government. While this document is believed to contain correct information, neither the United States Government nor any agency thereof, nor the Regents of the University of California, nor any of their employees, makes any warranty, express or implied, or assumes any legal responsibility for the accuracy, completeness, or usefulness of any information, apparatus, product, or process disclosed, or represents that its use would not infringe privately owned rights. Reference herein to any specific commercial product, process, or service by its trade name, trademark, manufacturer, or otherwise, does not necessarily constitute or imply its endorsement, recommendation, or favoring by the United States Government or any agency thereof, or the Regents of the University of California. The views and opinions of authors expressed herein do not necessarily state or reflect those of the United States Government or any agency thereof or the Regents of the University of California.

Vapor-Liquid Equilibria for Binary Solutions of Polyisobutylene in C₆ through C₉ n-Alkanes

John G. Lieu and John M. Prausnitz *

Department of Chemical Engineering

University of California

and

Chemical Sciences Division

Lawrence Berkeley National Laboratory

University of California

Berkeley, CA 94720, U.S.A.

February 1999

* To whom correspondence should be addressed

This work was supported by the Director, Office of Energy Research, Office of Basic Energy Sciences, Chemical Sciences Division of the U.S. Department of Energy under Contract Number DE-AC03-76SF00098.

ABSTRACT

Vapor-liquid equilibria for binary solutions of polyisobutylene in C₆ through C₉ n-alkanes were obtained at 65°C. Using a classic gravimetric-sorption method, the amount of solvent absorbed by polyisobutylene was measured as a function of solvent vapor pressure. The data are interpreted with the Flory-Huggins theory and the Prigogine-Flory-Patterson theory.

INTRODUCTION

Vapor-liquid-equilibrium (VLE) data for polymer solutions are useful for a variety of applications including surface acoustic-wave sensors, polymer devolatilization, polymeric membrane-separation processes, pervaporation, and vapor-phase photografting¹⁻⁶. Efficient design of such processes requires characterizing VLE behavior of polymer solutions through experimental data or molecular-thermodynamic models.

Modeling polymer-solution properties is traditionally done by lattice theory or by equation-of-state theory; the Flory-Huggins lattice theory⁷ and the Prigogine-Flory-Patterson equation-of-state theory⁸⁻¹¹ provide classical examples. In general, an equation-of-state theory gives a more complete and accurate description of real polymer solutions than lattice theory. For example, the excess volume upon mixing is accessible through an equation-of-state model but not through an incompressible lattice model. On the other hand, whereas the Flory-Huggins lattice theory requires only one adjustable interaction

parameter, the Prigogine-Flory-Patterson theory requires an adjustable interaction parameter in addition to three pure-component parameters for the solvent and for the polymer.

This work reports vapor-liquid-equilibrium data for binary solutions of polyisobutylene (PIB) in C₆ through C₉ n-alkanes. Data are interpreted with the Flory-Huggins theory and with the Prigogine-Flory-Patterson theory.

EXPERIMENTAL

Materials

Solvents were degassed with a standard freeze-thaw procedure described by Panayiotou and Vera¹² and used without further purification.

The polyisobutylene sample was a white, rubbery solid with a glass-transition temperature at about 29°C. The viscosity-average molecular weight was in the range 4.2×10^6 to 5.2×10^6 . The average value 4.7×10^6 is assumed in our calculations.

Table 1 gives properties of solvents and polyisobutylene.

Apparatus

Vapor-liquid-equilibrium data were collected using a gravimetric-sorption method previously described by several authors (see, for example, Gupta and Prausnitz¹³). *Figure 1* shows a schematic diagram of the apparatus. The entire system is submerged in an isothermal water bath maintained at $\pm 0.1^\circ\text{C}$.

Each glass chamber contains one aluminum pan suspended from a quartz spring (Ruska Instruments Corp., Houston, TX). The calibrated springs have a sensitivity of

about 1 mg/mm and a maximum load of 250 mg. Within this range, the elongation of each spring is linear with respect to change in mass.

A cathetometer (Gaertner Scientific Corp., Chicago) is used to measure the extension of the springs and the mercury levels of the manometer.

Experimental Procedure

Polymer samples of known mass (20–25 mg) are placed into previously weighed aluminum pans. The system is then vacuum-dried for 12 to 24 hours to remove residual moisture and solvent. After obtaining the mass of dry polymer, solvent is introduced by opening and then closing the valve between the solvent flask and the evacuated glass chambers.

The system is allowed to equilibrate anywhere from 12 hours to a few days after each solvent injection. Equilibrium is assumed when measurements in spring length do not change more than ± 0.03 mm over a 12-hour period.

Because the polymer is nonvolatile, the total pressure is equal to the vapor pressure of solvent above the polymer solution. Because experimental pressures are low (less than 0.9 bar), the solvent vapor is considered to be an ideal gas. Solvent activity a_1 is given by the ratio of the measured pressure to the pure-solvent saturation pressure at system temperature.

The vernier scale on the cathetometer allows measurements to be made to the nearest 0.01 millimeter; therefore, pressure and mass readings have a precision of 0.02 torr and 0.02 mg, respectively. Uncertainty in solvent activity is less than 1% for the pressures used here. Solvent weight fraction w_1 uncertainty is less than 1% above

$w_1 = 0.1$ and 1–10% below $w_1 = 0.1$. Reliability of the apparatus and experimental procedure were established by reproducing published experimental vapor-liquid-equilibrium data for polystyrene in chloroform at 50°C¹⁴.

RESULTS AND DISCUSSION

Table 2 presents vapor-liquid-equilibrium data for polyisobutylene in C₆ through C₉ n-alkanes.

The data were fitted using the Flory-Huggins lattice theory⁷ and the Prigogine-Flory-Patterson equation-of-state theory⁸⁻¹¹.

Flory-Huggins Theory

The activity of the solvent is given by

$$\ln a_1 = \ln \Phi_1 + \left(1 - \frac{r_1}{r_2}\right) \Phi_2 + \chi_{FH} \Phi_2^2. \quad (1)$$

Solvent and polymer segment fractions, Φ_1 and Φ_2 , are defined by

$$\Phi_2 = 1 - \Phi_1 = \frac{r_2 N_2}{r_1 N_1 + r_2 N_2} \quad (2)$$

where N_1 and N_2 are the number of molecules and r_1 and r_2 are the number of segments per molecule of solvent and polymer, respectively. We set r_1 equal to unity and calculate r_2 by

$$r_2 = \frac{M_2 \rho_1}{M_1 \rho_2} = \frac{\text{molar volume of polymer}}{\text{molar volume of solvent}} \quad (3)$$

where M_1 and M_2 are molecular weights and ρ_1 and ρ_2 are mass densities of solvent

and polymer, respectively. The dimensionless Flory-Huggins parameter χ_{FH} characterizes the solvent-polymer interaction energy; the lower this parameter, the stronger the attraction between solvent and polymer. *Figure 2* shows that our vapor-liquid-equilibrium data are fit reasonably well by adjusting χ_{FH} . *Table 3* gives fitted χ_{FH} values and indicates that the solvent power of n-alkanes decreases (increasing χ_{FH}) with rising alkane carbon number.

Prigogine-Flory-Patterson Theory

The Prigogine-Flory-Patterson theory gives a reduced equation of state

$$\frac{\tilde{P}\tilde{v}}{\tilde{T}} = \frac{\tilde{v}^{1/3}}{\tilde{v}^{1/3} - 1} - \frac{1}{\tilde{v}\tilde{T}} \quad (4)$$

where temperature T , pressure P , and specific volume v , are reduced, respectively, by characteristic parameters T^* , P^* , and v^* such that

$$\tilde{T} = \frac{T}{T^*} \quad (5); \quad \tilde{v} = \frac{v}{v^*} \quad (6); \quad \tilde{P} = \frac{P}{P^*}. \quad (7)$$

A binary mixture requires six pure-component parameters: T_1^* , T_2^* , v_1^* , v_2^* , P_1^* , and P_2^* . For pure solvents and polymers, these parameters are found from volumetric data. *Table 4* shows pure-component parameters for PIB and n-alkanes; we define T^* in Kelvin, v^* in cm^3/g , and P^* in cal/cm^3 .

For the mixture, T^* and P^* depend on composition according to

$$T^* = \frac{P^*}{\left(\frac{P_1^*}{T_1^*}\right)\Phi_1^* + \left(\frac{P_2^*}{T_2^*}\right)\Phi_2^*} \quad (8)$$

and

$$P^* = P_1^* \Phi_1^* + P_2^* \Phi_2^* - \Phi_1^* \theta_2 X_{12} \quad (9)$$

where Φ_1^* , Φ_2^* , θ_1 , and θ_2 are, respectively, the segment fractions and surface fractions of the solvent and polymer and given by

$$\Phi_2^* = 1 - \Phi_1^* = \frac{m_2 v_2^*}{m_1 v_1^* + m_2 v_2^*} \quad (10)$$

and

$$\theta_2 = 1 - \theta_1 = \frac{(s_2/s_1)\Phi_2^*}{\Phi_1^* + (s_2/s_1)\Phi_2^*} \quad (11)$$

where m_1 and m_2 are the masses of solvent and polymer, respectively. Because solvent and polymer segments are chosen to have the same core volume, the segment-surface ratio s_2/s_1 is the ratio of surfaces per unit core volume and can be estimated from structural data, as tabulated, for example, by Bondi¹⁵. However, Flory and Höcker¹⁶ note that using group surface-area increments by Bondi overestimates the available surface area of polymers because it ignores shielding of constituent groups by intramolecular contacts between near-neighbors in the polymer chain. Thus, we follow Flory et al.¹⁷ and calculate s_2/s_1 from crystallographic data as follows. We consider n-alkanes to be right cylinders with length $L_1 = 1.19n + 1.32 \text{ \AA}$, mean radius $R_1 = 2.49 \text{ \AA}$, molecular surface area A_1 , and core molar volume V_1^* . Similarly, we consider polyisobutylene to be a right cylinder divided into repeat units with length $L_u = 2.325 \text{ \AA}$, radius $R_u = 3.48 \text{ \AA}$, molecular surface area A_u , and core molar volume V_u^* . The ratio s_2/s_1 is then calculated by

$$\frac{s_2}{s_1} = \frac{A_u}{A_1} \frac{V_1^*}{V_u^*}. \quad (12)$$

Molecular surface areas are defined by

$$A_1 = 2\pi R_1 L_1 + 2\pi R_1^2 \quad (13) \quad \text{and} \quad A_u = 2\pi R_u L_u \quad (14)$$

and core molar volumes are defined by

$$V_1^* = \pi R_1^2 L_1 N_{av} \quad (15) \quad \text{and} \quad V_u^* = \pi R_u^2 L_u N_{av} \quad (16)$$

where N_{av} is Avogadro's number.

For the mixture, the reduced volume \tilde{v} can be conveniently determined by following the procedure of Flory et al.¹⁸. First, we define an ideal reduced volume

$$\tilde{v}^0 = \Phi_1^* \tilde{v}_1 + \Phi_2^* \tilde{v}_2 \quad (17)$$

where

$$\tilde{v}_1 = \frac{v_1}{v_1^*} \quad (18) \quad \text{and} \quad \tilde{v}_2 = \frac{v_2}{v_2^*}. \quad (19)$$

The reduced volume of the real mixture is given by

$$\tilde{v} = \tilde{v}^0 + \tilde{v}^E. \quad (20)$$

The excess volume is calculated from

$$\tilde{v}^E = \left(\frac{\partial \tilde{v}}{\partial \tilde{T}} \right) (\tilde{T} - \tilde{T}^0) = \frac{3(\tilde{v}^0)^{7/3}}{4 - 3(\tilde{v}^0)^{1/3}} (\tilde{T} - \tilde{T}^0) \quad (21)$$

where the reduced temperature corresponding to \tilde{v}^0 is found by rearranging Equation (4)

for $P = 0$ such that

$$\tilde{T}^0 = \frac{(\tilde{v}^0)^{1/3} - 1}{(\tilde{v}^0)^{4/3}}. \quad (22)$$

Equation (21) provides an excellent approximation for polymer solutions at low or moderate pressures where pressure has a negligible effect on thermodynamic properties.

The solvent activity is then given by

$$\ln a_1 = \ln \Phi_1^* + \left(1 - \frac{r_1}{r_2}\right) \Phi_2^* + \frac{P_1^* M_1 v_1^*}{RT} \left[3\tilde{T}_1 \ln \frac{\tilde{v}_1^{1/3} - 1}{\tilde{v}^{1/3} - 1} + \left(\frac{1}{\tilde{v}_1} - \frac{1}{\tilde{v}}\right) \right] + \frac{M_1 v_1^*}{RT} \left(\frac{X_{12}}{\tilde{v}}\right) \theta_2^2 \quad (23)$$

where M_1 is the solvent molecular weight and R is the universal gas constant. The interchange-interaction parameter, X_{12} , measures the energy change upon formation of a solvent-polymer segment contact from a solvent-solvent and a polymer segment-polymer segment contact. The lower the value of X_{12} , the stronger the attraction between solvent and polymer.

Figure 3 shows solvent-activity data fitted with the Prigogine-Flory-Patterson theory. As shown in *Table 5*, X_{12} increases from C_6 to C_8 , but surprisingly decreases from C_8 to C_9 . Similar results for X_{12} , however, have been reported by Kasprzycka-Guttman et al.^{19,20} who measured heats of mixing for γ -picoline in C_6 through C_{10} n-alkanes and found that X_{12} is not monotonic with alkane carbon number.

A significant advantage of the Prigogine-Flory-Patterson theory is its ability to account for negative enthalpies of mixing without necessarily assigning negative interchange energies. Instead, observed negative enthalpies of mixing are accounted for with equation-of-state contributions, e.g. negative excess volumes upon mixing. Delmas et al.²¹ obtained enthalpy-of-mixing data for mixtures of PIB and n-alkanes and found them to be negative and to decrease in magnitude from C_6 to C_{10} n-alkanes. Using the

Prigogine-Flory-Patterson theory, Flory et al.¹⁷ calculated X_{12} from these enthalpy-of-mixing data and showed that X_{12} is positive and decreases with rising alkane carbon number, as shown in *Table 6*. For mixtures of nonpolar molecules, such as PIB and n-alkanes, the interchange energy should be small and positive. Further, it is expected that the interchange energy decreases with alkane carbon number; as carbon number $\rightarrow \infty$, the contact energy for mixing polymethylene segments and PIB should decline to a small value.

As Eichinger and Flory²² pointed out, however, X_{12} found from enthalpy-of-mixing data does not agree well with X_{12} found from solvent-activity data. Therefore, we follow the proposed extension of the Prigogine-Flory-Patterson theory by Orwoll and Flory²³ and express solvent activity by

$$\ln a_1 = \ln \Phi_1^* + \left(1 - \frac{r_1}{r_2}\right) \Phi_2^* + \frac{P_1^* M_1 v_1^*}{RT} \left[3\tilde{T}_1 \ln \frac{\tilde{v}_1^{1/3} - 1}{\tilde{v}^{1/3} - 1} + \left(\frac{1}{\tilde{v}_1} - \frac{1}{\tilde{v}}\right) \right] + \frac{M_1 v_1^*}{RT} \left(\frac{X_{12}}{\tilde{v}} - TQ_{12} \right) \theta_2^2 \quad (24)$$

where parameter Q_{12} accounts for the interaction entropy. *Figure 4* shows that upon introducing Q_{12} , vapor-liquid-equilibrium data measured here can be fitted using Flory's X_{12} values obtained from enthalpy-of-mixing data. *Table 6* lists fitted TQ_{12} .

A deficiency of the Prigogine-Flory-Patterson theory may follow from overestimating the magnitude of \tilde{v}^E , thereby underestimating X_{12} . A larger negative \tilde{v}^E causes X_{12} to become less positive. *Table 7* shows that the Prigogine-Flory-Patterson theory significantly overestimates the magnitude of \tilde{v}^E in mixtures of PIB and

n-alkanes investigated by Flory et al.¹⁷.

A comparison of results shown in *Figures 2-4* indicates that our data are not fit better with the Prigogine-Flory-Patterson theory than with the Flory-Huggins theory. Application of the Prigogine-Flory-Patterson theory may be less successful than hoped because pure-component parameters for polyisobutylene vary with molecular weight. We used pure-component parameters reported by Eichinger and Flory²⁴ based on a viscosity-average molecular weight of ca. 4×10^4 , whereas the molecular weight of the sample used here is ca. 4.7×10^6 , two orders of magnitude larger. Although theory predicts that VLE behavior should converge at high polymer molecular weights, experimental data do not always agree with this prediction. For example, Wang et al.²⁵ showed that diethyl-ether solubility significantly depended on polymer molecular weight in high-molecular-weight poly(butyl methacrylate).

CONCLUSIONS

New vapor-liquid-equilibrium data for polyisobutylene in n-alkanes indicate that alkane solubility decreases as alkane carbon number rises. Data were reduced using the Flory-Huggins theory and the Prigogine-Flory-Patterson theory. Both theories give a fair representation of the data. An extended Prigogine-Flory-Patterson theory correlates the vapor-liquid-equilibrium data using Flory's X_{12} parameters calculated from enthalpy-of-mixing data.

ACKNOWLEDGMENTS

This work was supported by the Director, Office of Energy Research, Office of Basic Energy Sciences, Chemical Sciences Division of the U.S. Department of Energy under contract No. DE-AC03-76SF0098, and by the Donors of the Petroleum Research Fund administered by the American Chemical Society. The authors are grateful to John O. Tanbonliong and Cristina Mio for construction of experimental apparatus and helpful comments.

REFERENCES

1. Ballantine, D. S., Jr. and Wohltjen, H., *Anal. Chem.*, 1989, **61**, 704A.
2. High, M. S. and Danner, R. P., *Fluid Phase Equilib.*, 1990, **55**, 1.
3. Baker, R. W., Yoshioka, N., Mohr, J. M. and Khan, A. J., *J. Membr. Sci.*, 1987, **31**, 259.
4. Matsumoto, K., Ishii, K., Kuroda, T., Inoue, K. and Iwama, A., *Polym. J.*, 1991, **23**, 491.
5. Maeda, Y., Tsuyumoto, M., Karakane, H., and Tsugaya, H., *Polym. J.*, 1991, **23**, 501.
6. Kubota, H., Yoshino, N. and Ogiwara, Y., *J. Appl. Polym. Sci.*, 1990, **39**, 1231.
7. Flory, P. J., *Principles of Polymer Chemistry*. Cornell University Press, New York, 1953.
8. Flory, P. J., *Disc. Faraday Soc.*, 1970, **49**, 7.
9. Patterson, D., *Macromolecules*, 1969, **2**, 672.
10. Patterson, D. and Delmas, G., *Disc. Faraday Soc.*, 1970, **49**, 98.
11. Prigogine, I., *The Molecular Theory of Solutions*. North-Holland Publishing Company, Amsterdam, 1957.
12. Panayiotou, C. and Vera, J. H., *Polym. J.*, 1984, **16**, 89.
13. Gupta, R. B. and Prausnitz, J. M., *J. Chem. Eng. Data.*, 1995, **40**, 784.
14. Bawn, C. E. H. and Wajid, M. A., *Trans. Faraday Soc.*, 1956, **52**, 1658.
15. Bondi, A., *Physical Properties of Molecular Crystals, Liquids and Glasses*. John Wiley & Sons, Inc., New York, 1968.

16. Flory, P. J. and Höcker, H., *Trans. Faraday Soc.*, 1971, **67**, 2258.
17. Flory, P. J., Ellenson, J. L. and Eichinger, B. E., *Macromolecules*, 1968, **1**, 279.
18. Flory, P. J., Orwoll, R. A. and Vrij, A., *J. Am. Chem. Soc.*, 1964, **86**, 3515.
19. Kasprzycka-Guttman, T. and Wilczura, H., *Thermochim. Acta*, 1991, **184**, 321.
20. Kasprzycka-Guttman, T. and Kurcińska, H., *Thermochim. Acta*, 1990, **173**, 63.
21. Delmas, G., Patterson, D. and Somcynsky, T., *J. Polym. Sci.*, 1962, **57**, 79.
22. Eichinger, B. E. and Flory, P. J., *Trans. Faraday Soc.*, 1968, **64**, 2035.
23. Orwoll, R. A. and Flory, P. J., *J. Am. Chem. Soc.*, 1967, **89**, 6822.
24. Eichinger, B. E. and Flory, P. J., *Macromolecules*, 1968, **1**, 285.
25. Wang, K., Hu, Y and Wu, D. T., *J. Chem. Eng. Data*, 1994, **39**, 916.
26. Daubert, T. E. and Danner, R. P., *Physical and Thermodynamic Properties of Pure Chemicals: Data Compilation*. Hemisphere Pub. Corp, New York, 1989.
27. Orwoll, R. A. and Flory, P. J., *J. Am. Chem. Soc.*, 1967, **89**, 6814.
28. Flory, P. J., Orwoll, R. A. and Vrij, A., *J. Am. Chem. Soc.*, 1964, **86**, 3507.

Table 1 Solvent and polymer properties

Substance	Supplier	Lot Number	Purity
n-hexane	Aldrich Chemical Co., Inc.	13004CR	99+%
n-heptane	Sigma-Aldrich	06438LQ	99+%
n-octane	Aldrich Chemical Co., Inc.	JR01557HR	99+%
n-nonane	Aldrich Chemical Co., Inc.	ER10504PQ	99%
polyisobutylene	Aldrich Chemical Co., Inc.	AF03243TZ	

Table 2 Vapor-liquid-equilibrium data for polyisobutylene in n-alkanes at 65°C

w_1 = solvent weight fraction in the liquid phase

Φ_1 = solvent segment fraction in the liquid phase

$a_1 = P / P_1^{\text{sat}}$ = solvent activity

P = vapor pressure in Torr

P_1^{sat} = pure-solvent saturation pressure (calculated from equations suggested by Daubert and Danner²⁶) in Torr

Solvent: n-Hexane; $P_1^{\text{sat}} = 671$ Torr			Solvent: n-Heptane; $P_1^{\text{sat}} = 255$ Torr		
w_1	Φ_1	a_1	w_1	Φ_1	a_1
0.011	0.016	0.117	0.017	0.023	0.122
0.030	0.043	0.232	0.040	0.055	0.243
0.060	0.085	0.343	0.067	0.091	0.367
0.087	0.122	0.464	0.097	0.130	0.487
0.121	0.167	0.580	0.135	0.178	0.604
0.162	0.219	0.694	0.179	0.232	0.720
0.217	0.287	0.792	0.237	0.301	0.829
0.292	0.374	0.890	0.292	0.364	0.904
0.401	0.493	0.967	0.350	0.428	0.972
			0.451	0.533	1.000
Solvent: n-Octane; $P_1^{\text{sat}} = 96$ Torr			Solvent: n-Nonane; $P_1^{\text{sat}} = 37$ Torr		
w_1	Φ_1	a_1	w_1	Φ_1	a_1
0.021	0.028	0.171	0.021	0.027	0.137
0.040	0.053	0.276	0.053	0.068	0.320
0.065	0.085	0.427	0.073	0.094	0.453
0.091	0.119	0.550	0.104	0.132	0.591
0.122	0.157	0.670	0.134	0.169	0.720
0.156	0.199	0.777	0.167	0.208	0.863
0.199	0.250	0.879			

Table 3 Flory-Huggins interaction parameter for polyisobutylene in n-alkanes at 65°C

n-Alkane	χ_{FH}
C ₆	0.612
C ₇	0.637
C ₈	0.860
C ₉	0.877

Table 4 Pure-component parameters for the Prigogine-Flory-Patterson theoryParameters for polyisobutylene estimated from Eichinger and Flory²⁴ v_1 and P_1^* for n-alkanes estimated from Orwoll and Flory²⁷ T_1^* and v_1^* for n-alkanes estimated from Flory et al.²⁸ s_2/s_1 calculated from structural data following Flory et al.¹⁷

Substance	v_i (cm ³ /g)	v_i^* (cm ³ /g)	T_i^* (K)	P_i^* (cal/cm ³)	s_2/s_1
n-hexane	1.620	1.162	4510	97	0.549
n-heptane	1.551	1.144	4757	99	0.565
n-octane	1.503	1.126	4946	100	0.577
n-nonane	1.465	1.115	5096	102	0.587
polyisobutylene	1.114	0.952	7820	105	

Table 5 Interchange-interaction parameter X_{12} fitted to solvent-activity data

n-Alkane	X_{12} (cal/cm ³)
C ₆	2.00
C ₇	2.21
C ₈	3.69
C ₉	3.36

Table 6 Flory's X_{12} from enthalpy-of-mixing data and fitted TQ_{12} using an extended Prigogine-Flory-Patterson theory; T = 338.15 K

n-alkane	X_{12} (cal/cm ³)	TQ_{12} (cal/cm ³)
C ₆	1.75	-0.205
C ₇	1.28	-0.770
C ₈	1.05	-2.191
C ₉	0.91*	-2.045

* estimated

Table 7 Calculated and observed \tilde{v}^E for binary solutions of polyisobutylene in n-alkanes investigated by Flory et al.¹⁷

n-Alkane	$\tilde{v}_{\text{observed}}^E \times 100$	$\tilde{v}_{\text{calculated}}^E \times 100$	% Overestimation*
C ₅	-1.583	-1.920	21.3
C ₆	-1.043	-1.214	16.4
	-1.053	-1.191	13.2
	-0.995	-1.066	7.1
C ₇	-0.749	-0.902	20.3
C ₈	-0.578	-0.661	14.4
	-0.582	-0.653	12.3
	-0.564	-0.624	10.6
C ₁₀	-0.342	-0.399	16.6
	-0.349	-0.396	13.4
	-0.330	-0.428	30.0
C ₁₆	-0.092	-0.131	42.9
	-0.095	-0.131	37.5
	-0.092	-0.118	28.2

*
$$\frac{(\tilde{v}_{\text{observed}}^E - \tilde{v}_{\text{calculated}}^E)}{\tilde{v}_{\text{observed}}^E} \times 100\%$$

Figure Captions

Figure 1 Experimental apparatus for vapor-liquid equilibrium measurements.

Figure 2 Calculated solvent activities (solid lines) for binary solutions of polyisobutylene in n-alkanes at 65°C; data fitted with the Flory-Huggins equation; points are experimental

Figure 3 Calculated solvent activities (solid lines) for binary solutions of polyisobutylene in n-alkanes at 65°C; data fitted with the Prigogine-Flory-Patterson equation of state; points are experimental

Figure 4 Calculated solvent activities (solid lines) for binary solutions of polyisobutylene in n-alkanes at 65°C; data fitted with an extended Prigogine-Flory-Patterson equation of state; points are experimental

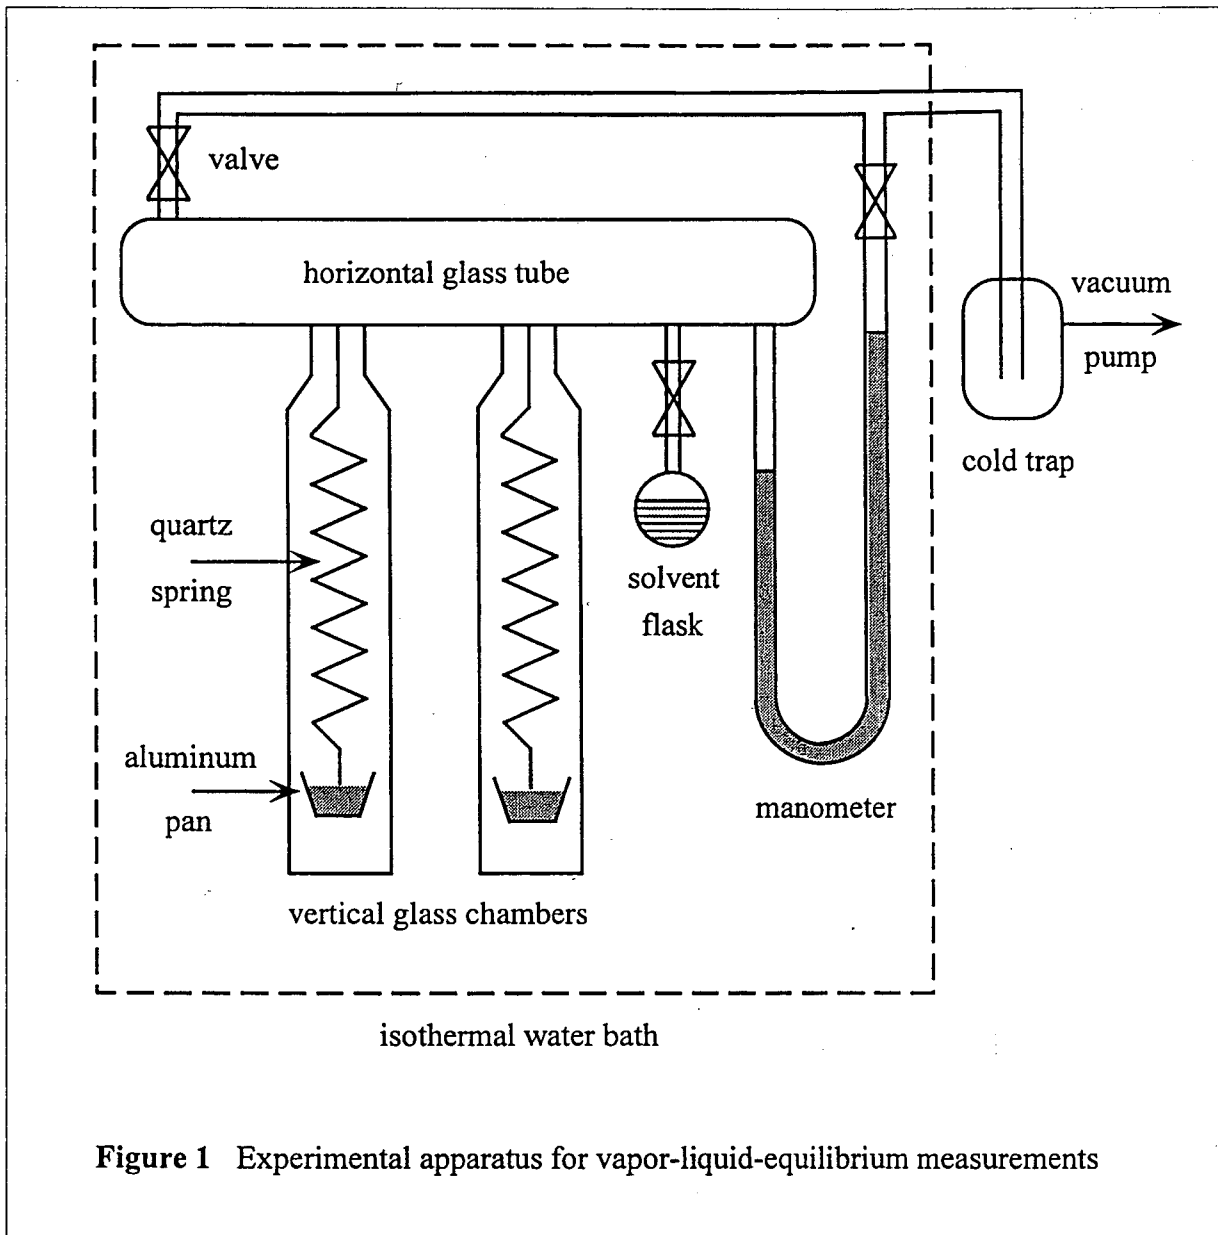


Figure 1 Experimental apparatus for vapor-liquid-equilibrium measurements

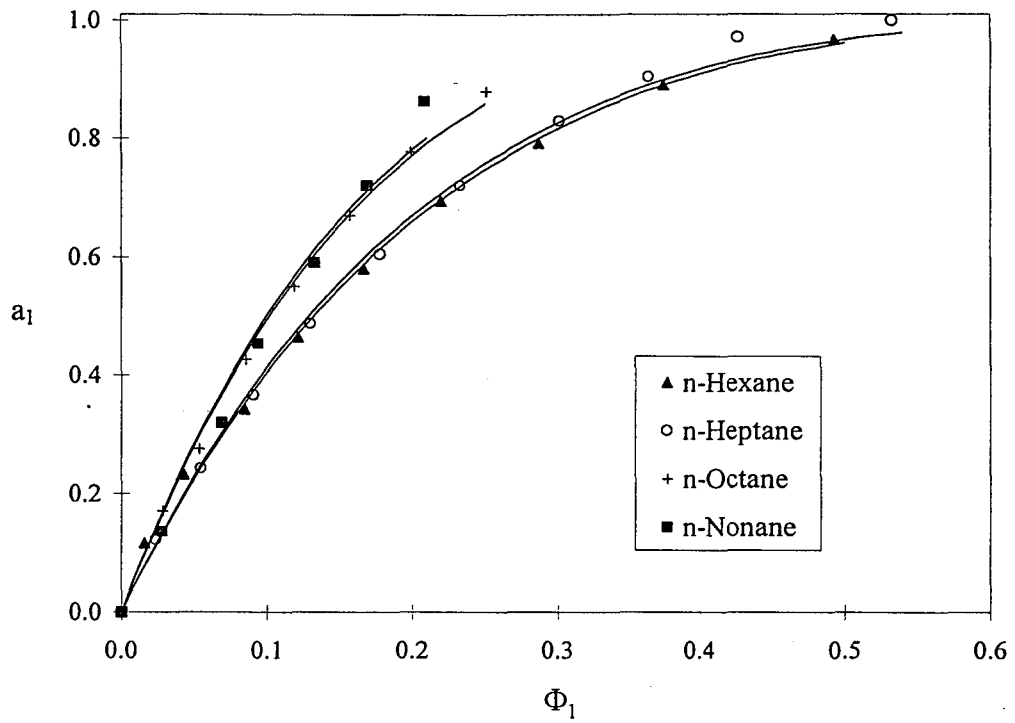


Figure 2

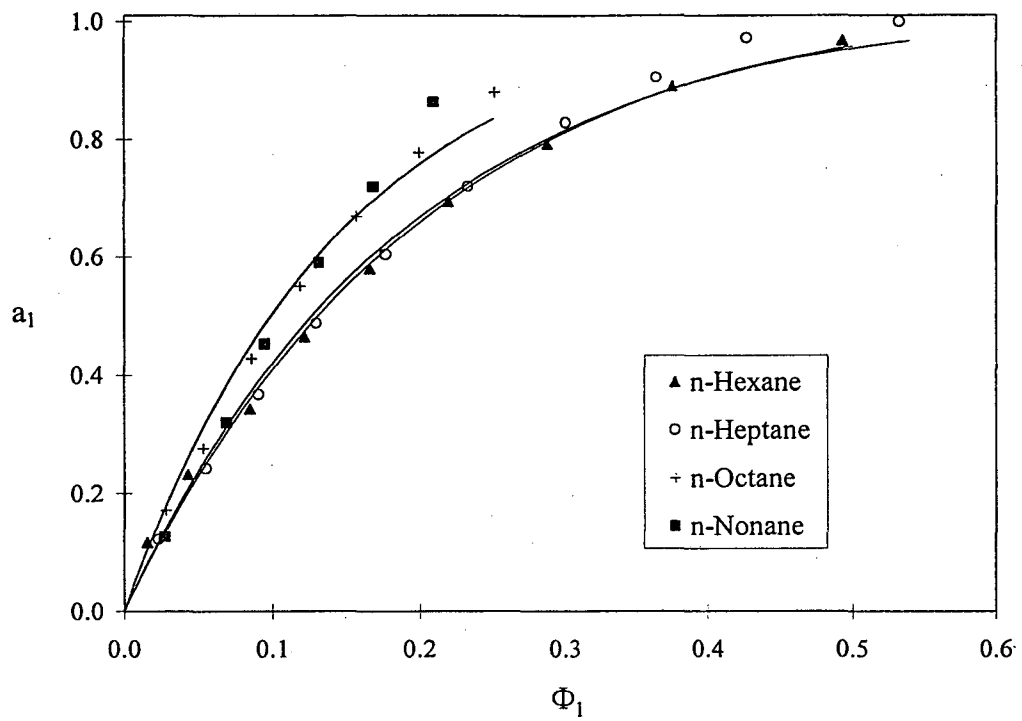


Figure 3

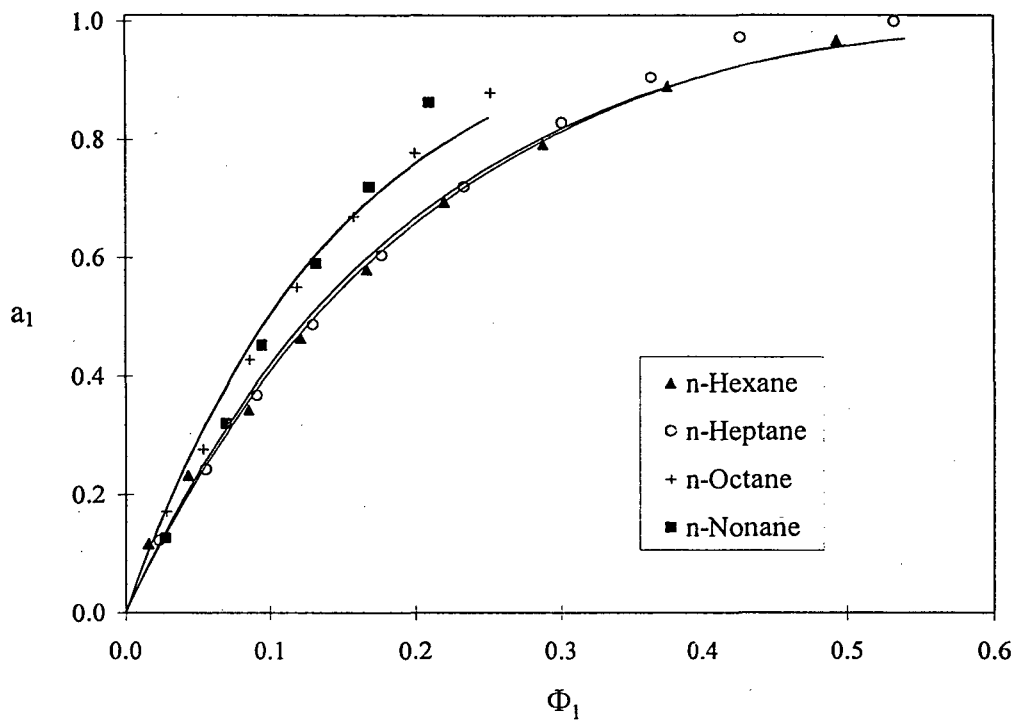


Figure 4

**ERNEST ORLANDO LAWRENCE BERKELEY NATIONAL LABORATORY
ONE CYCLOTRON ROAD | BERKELEY, CALIFORNIA 94720**