

# UC Berkeley

## UC Berkeley Previously Published Works

### Title

Heavy boron doping in superconducting carbon materials

### Permalink

<https://escholarship.org/uc/item/6bw569x9>

### Journal

Physical Review Materials, 4(5)

### ISSN

2476-0455

### Authors

Sakai, Yuki  
Chelikowsky, James R  
Cohen, Marvin L

### Publication Date

2020-05-01

### DOI

10.1103/physrevmaterials.4.054801

Peer reviewed

# Heavy boron doping in superconducting carbon materials

Yuki Sakai,<sup>1</sup> James R. Chelikowsky,<sup>1,2,3</sup> and Marvin L. Cohen<sup>4,5</sup>

<sup>1</sup>*Center for Computational Materials,*

*Oden Institute for Computational Engineering and Sciences,*

*The University of Texas at Austin, Austin, Texas 78712, USA*

<sup>2</sup>*Department of Chemical Engineering,*

*The University of Texas at Austin, Austin, Texas 78712, USA*

<sup>3</sup>*Department of Physics, The University of Texas at Austin, Austin, Texas 78712, USA*

<sup>4</sup>*Department of Physics, University of California*

*at Berkeley, Berkeley, California 94720, USA*

<sup>5</sup>*Materials Sciences Division, Lawrence Berkeley*

*National Laboratory, Berkeley, California 94720, USA*

(Dated: February 10, 2020)

## Abstract

We examine physical properties of heavily boron-doped  $sp^3$  hybridized carbon allotropes: cubic diamond, hexagonal diamond, and body centered tetragonal  $C_4$ . The structural similarity between cubic diamond and hexagonal diamond leads to similar responses to substitutional boron doping. On the other hand, body centered tetragonal  $C_4$  exhibits distinct structural and electronic properties because of its characteristic structure. Our study also shows that the superconducting transition temperatures up to 60 K are possible in heavily-doped carbon materials despite their various atomistic structures.

## I. INTRODUCTION

Carbon has various allotropes with different crystal structures. Graphite is composed of layers of  $sp^2$  hybridized carbon atoms arranged into a honeycomb lattice. The single layer of graphite, two-dimensional graphene, has special properties which normal three-dimensional materials do not possess [1]. The carbon nanotube is a one-dimensional cylinder of graphene, which shows interesting electronic properties depending on its chirality [2, 3]. The fullene ( $C_{60}$ ) molecule is another  $sp^2$  allotrope of carbon, which forms a crystalline solid [4].

There are  $sp^3$  hybridized carbon allotropes where atoms are four-fold coordinated. The most abundant  $sp^3$  carbon allotrope is cubic diamond. Lonsdaleite, hexagonal diamond, is another  $sp^3$  allotrope with a 2H or wurtzite type structure if we view cubic diamond as a 3C (zinc-blende type) structure. In addition to these existing materials, there are numerous computationally-designed allotropes of carbon. For example, the carbon kagome lattice has a direct band gap owing to its characteristic orbital frustration and is promising for optical applications [5, 6]. M-Carbon, W-carbon, and body centered tetragonal  $C_4$  (bct  $C_4$ ) have been proposed to explain the carbon phase that appears when graphite is compressed at low temperature [7–10]. These existing and proposed carbon materials exhibit various interesting properties depending on their detailed atomistic structures.

Carbon materials become superconductors typically when carriers are doped. For instance, doping alkali atoms to internal space of fullene crystals and graphite yields superconductivity through electron doping [11, 12]. The highest superconducting transition temperature ( $T_c$ ) is 11.5 and 33 K for graphite ( $CaC_6$ ) and fullene ( $Cs_xRb_yC_{60}$ ) cases, respectively. Boron (hole) doping in carbon nanotube causes superconductivity with the highest  $T_c$  of 19 K under pressure [13, 14]. Boron-doped  $sp^3$  cubic diamond exhibits superconductivity due to shallow acceptor states with a  $T_c$  up to 11 K [15–17]. Even when no carriers are doped, twisted bilayer graphene at "magic twist angles" exhibits superconductivity [18].

The recent finding of the high  $T_c$  of 55 K in heavily boron-doped amorphous "Q-carbon" motivates further investigations of high  $T_c$  in boron-doped carbon materials [19–22]. In particular,  $sp^3$ -hybridized carbon materials should be of interest as Q-carbon is considered to be an  $sp^3$ -rich material [23, 24]. A potentially higher  $T_c$  associated with the high electronic density of states at the Fermi energy in heavily boron-doped cubic diamond was theoret-

ically proposed by Moussa and Cohen [25]. However, the effect of heavy boron-doping in other carbon allotropes is not well studied. Understanding the superconductivity in boron-doped carbon materials with different crystal structures should also help understanding the interesting properties of Q-carbon since the detailed mechanism of the high temperature superconductivity and the atomistic structure remains an open question.

Here we study the superconductivity in several different boron-doped  $sp^3$  carbon allotropes. We select cubic diamond and hexagonal diamond because they are found in nature. We also consider bct  $C_4$  since this material has characteristic four-membered rings in its structure, which are sometimes observed in amorphous carbon. We consider different concentrations of substitutionally-doped boron atoms (12.5%, 25%, and 50%) to see their effect on physical properties. Hexagonal diamond exhibits similar properties to those of cubic diamond owing to their structural similarity even when doped with boron atoms. On the other hand, the characteristic structure of bct  $C_4$  causes structural and electronic responses to boron doping different from cubic and hexagonal diamond. In spite of such distinct properties even bct  $C_4$  exhibits similar superconducting properties to other carbon materials.

## II. COMPUTATIONAL METHOD

We employ a total-energy pseudopotential method constructed within density functional theory (DFT) [26–29]. A plane-wave basis is used to represent wavefunctions with a cut-off energy of 65 Ry, respectively [30]. Troullier-Martins norm-conserving pseudopotentials are constructed by using local density approximation for the exchange-correlation energy functional [31–33].

Cubic and orthorhombic  $2 \times 2 \times 2$  supercells containing 64 atoms are used for simulations of cubic diamond and bct  $C_4$ , respectively as shown in Figs 1(a) and 1(c). For hexagonal diamond, we use a  $3 \times 3 \times 2$  supercell with 72 carbon atoms [see Fig. 1(b)]. A  $k$ -grid of  $2 \times 2 \times 2$  is used for total energy calculations and structural relaxations of cubic diamond. For hexagonal diamond and bct  $C_4$ , we use a  $2 \times 2 \times 4$   $k$ -grid. We take a denser  $8 \times 8 \times 8$   $k$ -grid for the calculation of electronic densities of states (DOS) with the tetrahedron method.

Density functional perturbation theory is used to simulate vibrational and superconducting properties [34]. Phonon calculations are performed with a  $2 \times 2 \times 2$   $k$ -grid using  $\Gamma$ -only

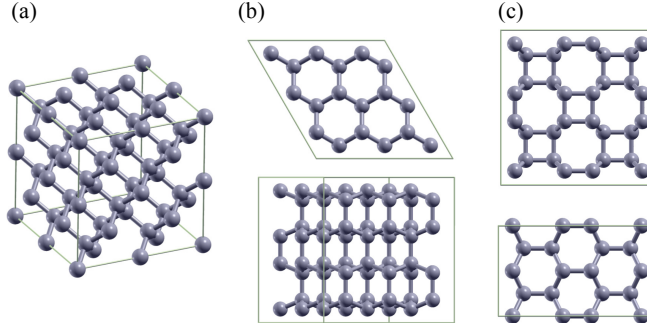


FIG. 1. (Color online) Crystal structures of (a) cubic diamond, (b) hexagonal diamond, and (c) body centered tetragonal (bct)  $C_4$ . Top and bottom panels of (b) and (c) represent top and side views of the structures, respectively. Carbon atoms are illustrated with gray spheres. The size of the cell is equivalent to the initial undoped supercell used in this work. The number of atoms is 64 in (a) and (c) while (b) contains 72 atoms.

sampling in the phonon  $q$  space. Electron-phonon linewidth for each phonon mode is calculated from the electron-phonon matrix elements [35]. Here we use a finer  $6 \times 6 \times 6$   $k$ -grid to obtain accurate results. A Gaussian broadening of 0.015-0.025 Ry is used to approximate delta function appears in Brillouin zone summations. We further compute the Eliashberg spectral function and electron-phonon coupling strength  $\lambda$  by using the linewidth obtained above. Superconducting transition temperature is estimated from the electron-phonon coupling strength  $\lambda$  by using Allen-Dynes equation [36] with an effective Coulomb repulsion parameter  $\mu^*$  of 0.12.

We focus on substitutional boron doping in this work as the contribution from boron interstitial doping to superconductivity is not significant [37]. We study 128 completely randomly-substituted boron-doped structures for the boron concentration of 12.5%, 25%, and 50%. In addition to these random sets, we independently generate 48 structures without pairing (neighboring) of boron atoms for 25% boron doping cases to consider the effect of boron pairing. We perform a variable-cell structural relaxation [38] for each structure after boron atoms are incorporated.

TABLE I. Total energies (in eV/cell) of boron-doped cubic diamond, hexagonal diamond, and bct  $C_4$  with 25% boron concentration. The highest, lowest, and average total energies of randomly generated structures are listed. Left and right sub-columns for each material indicate structures with and without boron pairing (BP), respectively. The zero of the total energy is that of the lowest-energy structure for each allotrope.

	Cubic diamond		Hexagonal diamond		bct $C_4$	
	BP	no BP	BP	no BP	BP	no BP
Average	2.2	2.3	1.7	1.4	2.3	1.6
Highest	4.0	3.9	3.4	3.2	4.2	3.3
Lowest	0.8	0	0.05	0	0.4	0

### III. RESULTS AND DISCUSSION

We consider the effect of boron pairing on the energetic stability of boron-doped carbon materials. Table I lists the total-energy statistics of 25% boron-doped three allotropes. The effect of boron pairing on the average energy is relatively small in cubic diamond and hexagonal diamond (the energy differences are 0.1 and 0.3 eV/cell, respectively). The lowest energy structure does not have the pairing in either case. These data show the stability in terms of the total energy should not be strongly affected by the existence of boron pairing in these materials. On the other hand, the boron-pairing costs energy in bct  $C_4$  by 0.7 eV/cell, on average. The highest energy of bct  $C_4$  with boron pairing is 0.9 eV/cell higher than that without pairing. This indicates that boron pairing is not favored in the bct  $C_4$  when compared with other allotropes.

Heavy boron doping causes structural distortions even in relatively-rigid cubic and hexagonal diamond. Figures 2(a) and 2(b) illustrate the structures of 25% boron-doped hexagonal diamond with and without boron pairing, respectively. The boron-boron bond tends to be longer than the carbon-carbon and carbon-boron bonds as shown in Fig. 2(a). This tendency causes a strong structural distortion around clustered boron atoms. In fact, the structure without boron pairing [Fig.2(b)] is almost the same as that of the undoped case shown in Fig. 1(b). The distortion is more significant in the bct  $C_4$  as illustrated in Figs. 2(c) and 2(d). The bct  $C_4$  is less stable than diamond as indicated by the uneven bond angles (90,

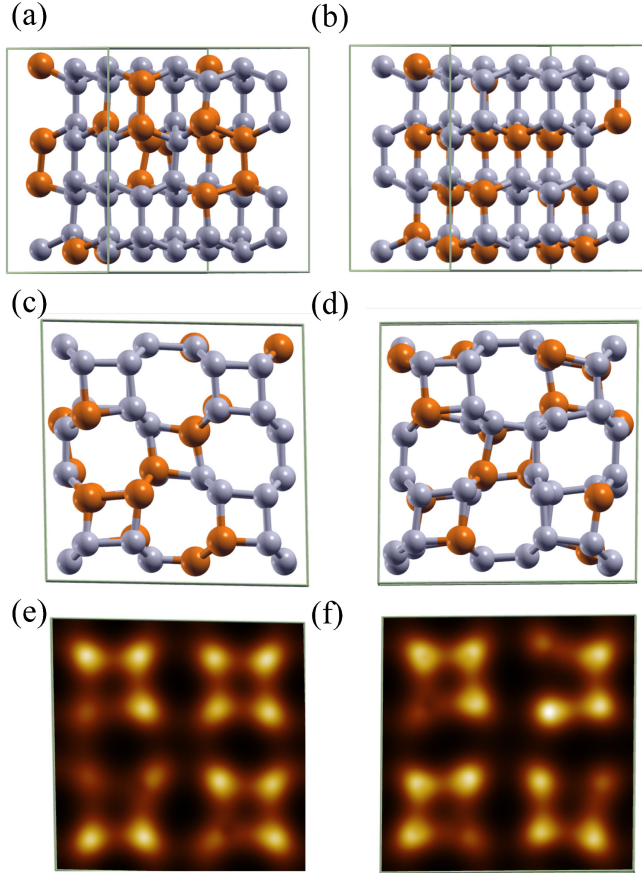


FIG. 2. (Color online) Distorted crystal structures of 25% boron-doped carbon allotropes. Hexagonal diamond, (a) with and (b) without boron pairing. The structures of bct C<sub>4</sub> (c) with and (d) without boron pairing. (a) and (c) are the highest-energy structure among each set while (b) and (d) are the lowest-energy structures. Gray and orange spheres represent carbon and boron atoms, respectively. (e) Charge density color plot taken at a plane right above the topmost atoms of (c). (f) Similar plot but for (d). Here a black-brown-white color scale is used.

111, or 114 degrees) deviated from the ideal  $sp^3$  bond angle (109.5 degrees). For example, boron dopants strongly distort the square shape in Fig. 2(d).

The square-shaped four-membered rings formed by the 90 degrees bonds are more strongly distorted in bct C<sub>4</sub> when no boron pairing exists as shown in Fig. 2(d). This is completely opposite from hexagonal diamond where the boron pairing promotes stronger distortion. The boron-carbon bond length is 2.24 Å in the upper-right broken square. This indicates that these atoms are almost three-fold coordinated (i.e.,  $sp^2$  hybridized). The charge density described in Fig. 2(f) confirms that no bonding is formed between the two atoms. Such a

change in the coordination number cannot be observed in the case with boron pairing as the charge density map in Fig. 2(e) shows. The boron-doped site favors three-fold coordination because of the electron deficiency. However, the longer boron-boron bond length prevents the boron atoms from lowering the coordination number when the boron pairing exists. The lower coordination number in boron-doped bct  $C_4$  explains the relatively large energy difference (0.7 eV/cell) between those with and without boron pairing.

Boron pairing significantly affects the electronic properties as well. Figure 3 shows the partial electronic density of states (PDOS) of 25% boron-doped carbon allotropes. Here the left and right columns correspond to the structures with and without boron pairing, respectively. The electronic properties shows considerable difference particularly around the Fermi energy. The PDOS for carbon and boron atoms is almost equivalent when there is no boron pairing because the dopant distribution can be regarded as uniform [see 3(b), 3(d), and 3(f)]. On the other hand, the boron PDOS is larger than that of carbon when boron pairing exists because of localized acceptor states created by the pairing or clustering of boron atoms. Figures 3(a), 3(c), and 3(e) clearly indicates that boron contributions shows high and localized PDOS particularly around 2 eV above the Fermi energy.

Table III lists the average, lowest, and highest electronic DOS at the Fermi energy [ $N(E_F)$ ] of three carbon materials with different amount of boron doping. The increase in boron concentration from 12.5% to 25% contributes to the higher average  $N(E_F)$  by 44, 30, and 11% for cubic diamond, hexagonal diamond, and bct  $C_4$ , respectively when boron pairing exists. The  $N(E_F)$  is more than double in cubic diamond when boron pairing is avoided. This confirms that the localization of acceptor states caused by boron pairing prevents an increase in  $N(E_F)$ . In fact, even 50% boron doping does not increase both average and highest  $N(E_F)$  (0.12 and 0.17 states/eV/atom respectively) in cubic diamond because of inevitable boron paring in heavy boron doping. Also,  $N(E_F)$  does not increase in hexagonal diamond and bct  $C_4$  in a similar fashion even with 50% doping.

The average and the highest  $N(E_F)$  of bct  $C_4$  is almost the same as those of cubic diamond and hexagonal diamond when the boron concentration is 12.5%. However, the average  $N(E_F)$  without boron pairing is smaller by 32 and 24% when compared with cubic and hexagonal diamond, respectively. This indicates that the increase in the  $N(E_F)$  with respect to boron concentration is slower than in the other allotropes. In addition, cubic and hexagonal diamond does not exhibit clear localization of electronic states above the Fermi



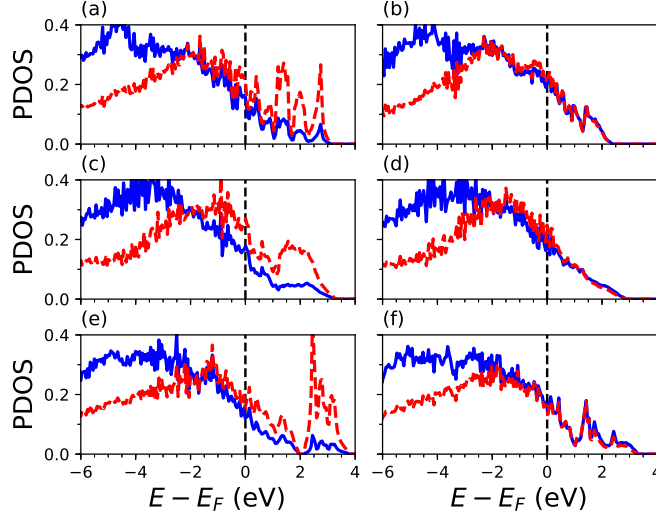


FIG. 3. (Color online) Partial electronic DOS (PDOS) in states/eV/atom of (a)-(b) cubic diamond, (c)-(d) hexagonal diamond, and (e)-(f) bct  $C_4$ . (a), (c), and (e) represent the PDOS for the structures with boron pairing while (b), (d), and (f) are those without boron pairing. The boron concentration is 25% and the PDOS is the average over all atoms from each atomic species. Blue solid and red dashed lines represent the partial DOS of carbon and boron atoms, respectively. The vertical dashed line shows the position of the Fermi energy.

energy while the localized states are prominent in the PDOS of bct  $C_4$  [see Figs. 3(b), 3(d), and 3(f)]. Boron doping causes a large structural distortion in bct  $C_4$ . We see some atoms are three-fold coordinated as illustrated in Fig. 2(d). Such  $sp^2$ -like atoms have remaining  $p_z$  orbitals, which are not used for bonding. These remaining orbitals appear within the band gap and form localized states in a similar fashion to dense amorphous carbon [20, 24]. The structural distortion due to boron doping causes the distinct electronic properties of bct  $C_4$ .

Figure 4 displays the superconducting temperature ( $T_c$ ), the logarithmic average of phonon frequency ( $\omega_{\log}$ ), and the electron-phonon coupling constant ( $\lambda$ ) as a function of  $N(E_F)$  for boron-doped carbon allotropes. Here we select samples from a set of randomly doped structures as follows: three structures with high  $N(E_F)$ , three with low  $N(E_F)$ , and three with  $N(E_F)$  close to the average  $N(E_F)$  for each boron doping concentration and material. For those without boron pairing, we take three structures with high  $N(E_F)$  and compute superconducting properties. We obtain the highest  $T_c$  of 57, 47, and 55 K for cubic diamond, hexagonal diamond, and bct  $C_4$ , respectively.

The almost linear correlation between  $N(E_F)$  and  $\lambda$  is observed in all three carbon al-

TABLE II. Electronic density of states at the Fermi energy [ $N(E_F)$  in state/eV/atom] of boron-doped cubic diamond, hexagonal diamond, and bct  $C_4$  with 12.5%, 25%, and 50% boron-doping. Here the highest (MAX), lowest (MIN), and average (AVG) of  $N(E_F)$  are listed. Left and right sub-columns for each material with 25% doping indicate structures with and without boron pairing (BP), respectively. We do not distinguish the existence of boron pairing in the 12.5% and 50% doped cases.

		Cub. diamond		Hex. diamond		bct $C_4$	
		BP	no BP	BP	no BP	BP	no BP
12.5%	AVG		0.09		0.10		0.09
	MAX		0.14		0.14		0.14
	MIN		0.05		0.06		0.04
25%	AVG	0.13	0.19	0.13	0.17	0.11	0.13
	MAX	0.18	0.26	0.18	0.21	0.16	0.18
	MIN	0.07	0.15	0.08	0.14	0.04	0.09
50%	AVG		0.12		0.12		0.13
	MAX		0.17		0.16		0.17
	MIN		0.04		0.07		0.05

lotropes in Fig. 4. On the other hand, the  $\omega_{\log}$  is weakly but negatively correlated with  $N(E_F)$ . The reduction of  $\omega_{\log}$  occurs because of the weakened chemical bonds owing to the increase of the number of boron atoms. The respective clustering of blue squares (12.5% doped cases) and green circles (25% doped cases) shows this relation between the doping concentration and  $\omega_{\log}$ .  $T_c$  exhibits a similar trend to  $\lambda$  although the linear correlation is relatively weak because of  $\omega_{\log}$  dependence. Boron pairing generally eliminates effective carriers at the Fermi energy, and results in a relatively low  $N(E_F)$  and  $T_c$ . Therefore, a uniform boron doping is desirable for achieving high  $T_c$ .

In Fig. 4, the slope of the linear relation between  $N(E_F)$  and  $\lambda$  is steeper in cubic diamond than in hexagonal diamond. Hexagonal diamond has an anisotropic structure between the plane spanned by  $a$  vectors and  $c$  directions. The electronic properties also exhibit anisotropy due to this structural anisotropy. The valence band top at the  $\Gamma$  point is doubly degenerated and the wave functions are distributed in the  $a$  plane. However, a

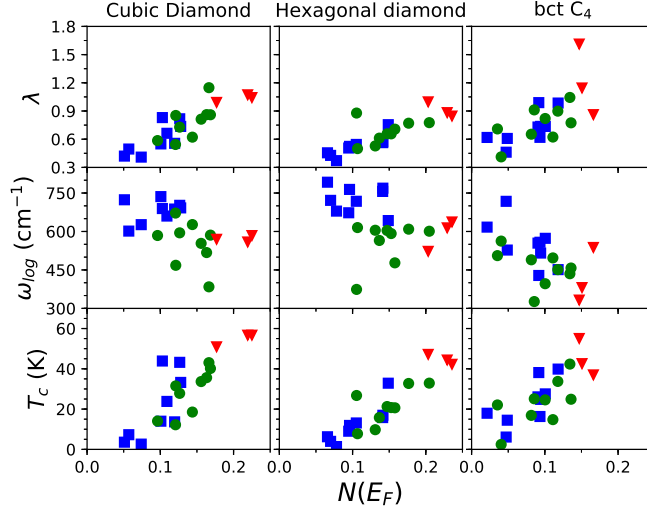


FIG. 4. (Color online) Superconducting transition temperature ( $T_c$  in K, bottom panels), logarithmic average of phonon frequency ( $\omega_{\log}$  in  $\text{cm}^{-1}$ , center panels), and electron-phonon coupling constant ( $\lambda$ , top panels) for boron-doped three carbon materials as a function of electronic DOS at the Fermi energy [ $N(E_F)$  in states/eV/atom]. Left, center, and right columns show the results for cubic diamond, hexagonal diamond, and bct  $C_4$ , respectively. Blue squares and green circles represent the data for 12.5% and 25% boron-doped cases with boron paring, respectively. Red triangles represent the results for 25% doping without boron paring.

similar wave function along  $z$  direction is about 0.5 eV below the valence top states. Such anisotropy in electronic states does not promote electron-phonon coupling when compared with cubic diamond. The maximum of  $N(E_F)$  is relatively low for the bct  $C_4$  case because of the localized states created by the emergence of  $sp^2$  hybridized atoms. Nevertheless, the superconducting parameters are comparable to the other materials.

The Eliashberg spectral function and phonon density of states (phonon DOS) of boron-doped systems shown in Fig. 5 describe the characteristic phonon and superconducting properties of each material. Cubic diamond (blue dash-dotted line) exhibit the smallest phonon frequency range (from  $300 \text{ cm}^{-1}$  to  $1200 \text{ cm}^{-1}$ ). This reflects the robustness of cubic diamond as a host material for boron substitutional doping. Hexagonal diamond exhibits low-frequency modes below  $300 \text{ cm}^{-1}$ . These low-frequency modes arise from relatively long boron-carbon bonds and further softened low-frequency scissor modes. The integrated Eliashberg spectral function up to  $500 \text{ cm}^{-1}$  is almost the same in cubic diamond and hexagonal diamond. However, the resulting  $\lambda$  is larger in cubic diamond by 0.07 because of

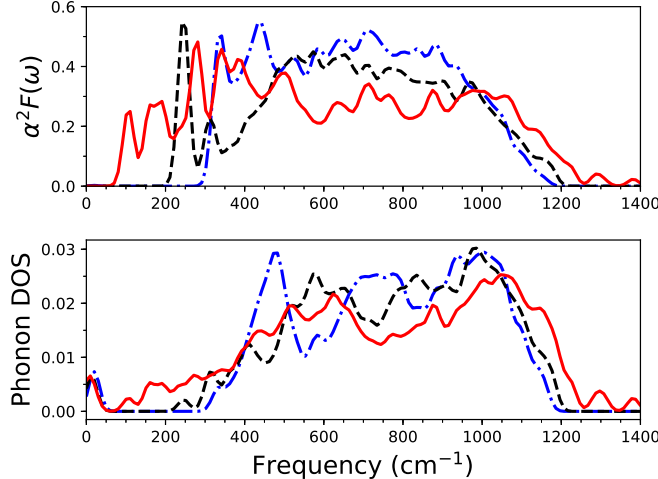


FIG. 5. (Color online) Eliashberg spectral function (top panel) and phonon density of states (bottom panel) of 25% boron-doped cubic diamond (blue dash-dotted lines), hexagonal diamond (black dashed lines), bct C<sub>4</sub> (red solid lines). Here we select the structure with the highest  $T_c$  for each material. The finite phonon DOS around the zero frequency is artifact because of the unconverged acoustic phonon modes at the  $\Gamma$  point.

the larger contributions from middle-frequency phonon modes (between 600 and 1000  $\text{cm}^{-1}$ ).

Further low-frequency phonon modes below 200  $\text{cm}^{-1}$  appears in bct C<sub>4</sub> (red solid lines in Fig. 5). The low frequency modes significantly contribute to the Eliashberg spectral function when compared with the other materials. These modes involve collective twisting motion of four-membered ring. In addition, higher frequency phonon modes above 1200  $\text{cm}^{-1}$  are also observed and contribute to the spectral function and phonon DOS in bct C<sub>4</sub>. The low frequency contribution arises from collective twisting motion of four membered ring. The high frequency modes are associated with the  $sp^2$ -hybridized atoms caused by the boron doping [see Fig. 2(d)]. Interestingly the contribution from low and high frequency modes in bct C<sub>4</sub> is similar to that of amorphous carbon where large empty space also exists in its structure [20, 21]. The high  $T_c$  of 55 K in this structure suggests that perfect symmetry of crystal structure or perfect tetrahedra are not necessarily required to obtain such a high  $T_c$ .

The structure with the highest  $T_c$  for each material is further studied with a combination of  $6 \times 6 \times 6$   $k$ -grid and  $2 \times 2 \times 2$   $q$ -grid to confirm the  $q$  dependence. The difference in  $T_c$  is approximately 10% in all three cases. We also consider a few different structures other than

TABLE III. Superconducting parameters of 25% boron-doped cubic diamond, hexagonal diamond, and bct C<sub>4</sub> with the highest  $T_c$  for each material. Two subcolumns show the results with the  $\Gamma$ -only sampling and  $2 \times 2 \times 2$   $q$ -grid for electron-phonon calculations.

	Cub. diamond		Hex. diamond		bct C <sub>4</sub>	
	$\Gamma$	$2 \times 2 \times 2$	$\Gamma$	$2 \times 2 \times 2$	$\Gamma$	$2 \times 2 \times 2$
$\lambda$	1.07	1.25	1.00	1.00	1.61	1.42
$\omega_{\log}$	804	707	752	694	478	495
$T_c$	56.7	61.9	47.2	43.8	55.0	50.2

those listed here but the errors are even smaller and always less than 10%. These results confirms that increasing the  $q$ -grid to  $2 \times 2 \times 2$  does not significantly affect the calculated superconducting properties when we use these sizes of supercells.

#### IV. SUMMARY

In summary, we study structural, electronic, and superconducting properties of substitutional boron-doped cubic diamond, hexagonal diamond, and bct C<sub>4</sub>. The key structural character for high  $T_c$  is the absence of boron pairing inside carbon materials. Cubic and hexagonal diamond exhibits similar trends because of their structural similarity. The characteristic structure in bct C<sub>4</sub> is the origin of the distinct responses to boron doping. It is interesting that even boron-doped bct C<sub>4</sub> could exhibit superconductivity around 50 K despite its considerable structural distortion. If heavy boron doping in bct C<sub>4</sub> is achieved, the boron pairing should be avoided as the boron paring costs high energy. The upper bound of  $T_c$  is around 60 K in cubic diamond. A higher boron concentration than 25% does not significantly contribute to the  $N(E_F)$ . A further high  $T_c$  in boron-doped amorphous carbon suggested in the literature [39] requires a different mechanism for superconductivity as the  $N(E_F)$  does not increase with excess amount of boron doping.

## ACKNOWLEDGMENTS

Y.S. and J.R.C. acknowledge support from the U.S. Department of Energy (DOE) for work on nanostructures from Grant No. DE-FG02-06ER46286, and on algorithms by a subaward from the Center for Computational Study of Excited-State Phenomena in Energy Materials at the Lawrence Berkeley National Laboratory, which is funded by the U.S. Department of Energy, Office of Science, Basic Energy Sciences, Materials Sciences and Engineering Division under Contract No. DEAC02-05CH11231, as part of the Computational Materials Sciences Program. Computational resources are provided in part by the National Energy Research Scientific Computing Center (NERSC). M.L.C. acknowledges the National Science Foundation Grant No. DMR-1926004 support for research associated with conceptualizing and developing the theory and from the Theory of Materials Program at the Lawrence Berkeley National Laboratory funded by the Director, Office of Science and Office of Basic Energy Sciences, Materials Sciences and Engineering Division, U.S. Department of Energy under Contract No. DE-AC02-05CH11231 for supporting research related to the computational aspects involved in this project.

- 
- [1] K. S. Novoselov, A. K. Geim, S. V. Morozov, D. Jiang, Y. Zhang, S. V. Dubonos, I. V. Grigorieva, and A. A. Firsov, *Science* **306**, 666 (2004).
  - [2] S. Iijima, *Nature (London)* **354**, 56 (1991).
  - [3] N. Hamada, S. Sawada, and A. Oshiyama, *Phys. Rev. Lett.* **68**, 1579 (1992).
  - [4] H. W. Kroto, J. R. Heath, S. C. O'Brien, and R. E. Smalley, *Nature (London)* **318**, 162 (1985).
  - [5] Y. Chen, Y. Y. Sun, H. Wang, D. West, Y. Xie, J. Zhong, V. Meunier, M. L. Cohen, and S. B. Zhang, *Phys. Rev. Lett.* **113**, 085501 (2014).
  - [6] Y. Sakai, S. Saito, and M. L. Cohen, *Phys. Rev. B* **91**, 165434 (2015).
  - [7] P. A. Schultz, K. Leung, and E. B. Stechel, *Phys. Rev. B* **59**, 733 (1999).
  - [8] Q. Li, Y. Ma, A. R. Oganov, H. Wang, H. Wang, Y. Xu, T. Cui, H.-K. Mao, and G. Zou, *Phys. Rev. Lett.* **102**, 175506 (2009).

- [9] K. Umemoto, R. M. Wentzcovitch, S. Saito, and T. Miyake, *Phys. Rev. Lett.* **104**, 125504 (2010).
- [10] J.-T. Wang, C. Chen, and Y. Kawazoe, *Phys. Rev. Lett.* **106**, 075501 (2011).
- [11] K. Tanigaki, T. W. Ebbesen, S. Saito, J. Mizuki, J. S. Tsai, Y. Kubo, and S. Kuroshima, *Nature (London)* **352**, 222 (1991).
- [12] T. E. Weller, M. Ellerby, S. S. Saxena, R. P. Smith, and N. T. Skipper, *Nature Phys.* **1**, 39 (2005).
- [13] N. Murata, J. Haruyama, J. Reppert, A. M. Rao, T. Koretsune, S. Saito, and Y. Matsudaira, M. abd Yagi, *Phys. Rev. Lett.* **101**, 027022 (2008).
- [14] J. Haruyama, M. Matsudaira, J. Reppert, A. Rao, T. Koretsune, S. Saito, H. Sano, and Y. Iye, *J. Supercond. Nov. Magn.* **24**, 111 (2011).
- [15] E. A. Ekimov, V. A. Sidorov, E. D. Bauer, N. N. Mel'nik, N. J. Curro, J. D. Thompson, and S. M. Stishov, *Nature (London)* **428**, 542 (2004).
- [16] Y. Takano, T. Takenouchi, S. Ishii, S. Ueda, T. Okutsu, I. Sakaguchi, H. Umezawa, H. Kawarada, and M. Tachiki, *Diamond and related materials* **16**, 911 (2007).
- [17] H. Okazaki, T. Wakita, T. Muro, T. Nakamura, Y. Muraoka, T. Yokoya, S. Kurihara, H. Kawarada, and T. Oguchi, *Appl. Phys. Lett.* **106**, 052601 (2015).
- [18] Y. Cao, V. Fatemi, S. Fang, K. Watanabe, T. Taniguchi, E. Kaxiras, and P. Jarillo-Herrero, *Nature* **556**, 43 (2018).
- [19] A. Bhaumik, R. Sachan, and J. Narayan, *ACS Nano* **5351**, 11 (2017).
- [20] Y. Sakai, J. R. Chelikowsky, and M. L. Cohen, *Phys. Rev. B* **97**, 054501 (2018).
- [21] Y. Sakai, J. R. Chelikowsky, and M. L. Cohen, *Phys. Rev. Mater.* **3**, 084802 (2019).
- [22] A. Bhaumik and J. Narayan, *Nanoscale* **11**, 9141 (2019).
- [23] J. Narayan and A. Bhaumik, *J. Appl. Phys.* **118**, 215303 (2015).
- [24] Y. Sakai, J. R. Chelikowsky, and M. L. Cohen, *Phys. Rev. Mater.* **2**, 074403 (2018).
- [25] J. E. Moussa and M. L. Cohen, *Phys. Rev. B* **77**, 064518 (2008).
- [26] J. Ihm, A. Zunger, and M. L. Cohen, *J. Phys. C* **12**, 4409 (1979).
- [27] M. L. Cohen, *Phys. Scr.* **T1**, 5 (1982).
- [28] P. Hohenberg and W. Kohn, *Phys. Rev.* **136**, 864 (1964).
- [29] W. Kohn and L. J. Sham, *Phys. Rev.* **140**, 1133 (1965).

- [30] P. Giannozzi, S. Baroni, N. Bonini, M. Calandra, R. Car, C. Cavazzoni, D. Ceresoli, G. L. Chiarotti, M. Cococcioni, I. Dabo, A. Dal Corso, S. de Gironcoli, S. Fabris, G. Fratesi, R. Gebauer, U. Gerstmann, C. Gougoussis, A. Kokalj, M. Lazzeri, L. Martin-Samos, N. Marzari, F. Mauri, R. Mazzarello, S. Paolini, A. Pasquarello, L. Paulatto, C. Sbraccia, S. Scandolo, G. Sclauzero, A. P. Seitsonen, A. Smogunov, P. Umari, and R. M. Wentzcovitch, *J. Phys. Condens. Matter* **21**, 5502 (2009).
- [31] N. Troullier and J. L. Martins, *Phys. Rev. B* **43**, 1993 (1991).
- [32] D. M. Ceperley and B. J. Alder, *Phys. Rev. Lett.* **45**, 566 (1980).
- [33] J. P. Perdew and A. Zunger, *Phys. Rev. B* **23**, 5048 (1981).
- [34] S. Baroni, S. de Gironcoli, A. dal Corso, and P. Giannozzi, *Rev. Mod. Phys.* **73**, 515 (2001).
- [35] F. Giustino, *Rev. Mod. Phys.* **89**, 015003 (2017).
- [36] P. B. Allen and R. C. Dynes, *Phys. Rev. B* **12**, 905 (1975).
- [37] J. P. Goss and P. R. Briddon, *Phys. Rev. B* **73**, 085204 (2006).
- [38] M. Parrinello and A. Rahman, *Phys. Rev. Lett.* **45**, 1196 (1980).
- [39] J. Nayaran, R. Sachan, and A. Bhaumik, *Mater. Res. Lett.* **7**, 164 (2019).