

# UC Berkeley

## UC Berkeley Previously Published Works

### Title

Evaporated tellurium thin films for p-type field-effect transistors and circuits

### Permalink

<https://escholarship.org/uc/item/6st89138>

### Journal

Nature Nanotechnology, 15(1)

### ISSN

1748-3387

### Authors

Zhao, Chunsong  
Tan, Chaoliang  
Lien, Der-Hsien  
[et al.](#)

### Publication Date

2020

### DOI

10.1038/s41565-019-0585-9

Peer reviewed

# Evaporated tellurium thin films for *p*-type field-effect transistors and circuits

*Chunsong Zhao*<sup>1,2,3,#</sup>, *Chaoliang Tan*<sup>1,2,#</sup>, *Der-Hsien Lien*<sup>1,2</sup>, *Xiaohui Song*<sup>3,4</sup>,  
*Matin Amani*<sup>1,2</sup>, *Mark Hettick*<sup>1,2</sup>, *Hnin Yin Yin Nyein*<sup>1,2,3</sup>, *Zhen Yuan*<sup>1,2</sup>, *Lu Li*<sup>1,2</sup>,  
*Mary C. Scott*<sup>3,4</sup> and *Ali Javey*<sup>1,2,\*</sup>

<sup>1</sup>Electrical Engineering and Computer Sciences, University of California at Berkeley, Berkeley, CA 94720, United States

<sup>2</sup>Materials Sciences Division, Lawrence Berkeley National Laboratory, Berkeley, CA 94720, United States

<sup>3</sup>Department of Materials Science and Engineering, University of California at Berkeley, Berkeley, CA 94720, United States

<sup>4</sup>The Molecular Foundry, Lawrence Berkeley National Laboratory, Berkeley, CA, 94720

#These authors contributed equally to this work.

\*Address correspondence to [ajavey@eecs.berkeley.edu](mailto:ajavey@eecs.berkeley.edu)

**There is an emerging need for semiconductors that can be processed at near ambient temperature with high mobility and device performance. Although multiple *n*-type options have been identified, the development of their *p*-type counterparts remains limited. Here, we report the realization of tellurium (Te) thin films through thermal evaporation at cryogenic temperatures for fabrication of high-performance wafer-scale *p*-type field-effect transistors (FETs). We achieve an effective hole mobility of  $\sim 35 \text{ cm}^2 \text{ V}^{-1}\text{s}^{-1}$ , on/off current ratio of  $\sim 10^4$  and subthreshold swing of  $108 \text{ mVdec}^{-1}$  on an 8 nm thick film. High-performance Te *p*-FETs are fabricated on a wide range of substrates including glass and plastic, further demonstrating the broad applicability of this material. Significantly, 3D circuits are demonstrated by integrating multi-layered transistors on a single chip using sequential lithography, deposition and lift-off processes. Finally, various functional logic gates and circuits are demonstrated.**

Exploring low-temperature (400 °C or lower) grown semiconductor thin films with high mobility and device performance is of great importance for a number of applications including transparent/flexible electronics, and monolithic three-dimensional (3D) complementary metal-oxide-semiconductor (CMOS) architectures<sup>1-3</sup>. Specifically, the processing temperature for constructing monolithic 3D CMOS, where multiple active circuit layers are stacked on top of each other, needs to be maintained below 300-400 °C to prevent degradation of the underlying devices and interconnects, and it needs to be even lower (below 200 °C or even less) for flexible electronics due to low glass transition temperatures of polymer substrates (for example, the maximum stable temperature of polyethylene terephthalate (PET) is around 150 °C)<sup>4-6</sup>. Multiple *n*-type material systems with respectable electron mobility on the order of  $10 \text{ cm}^2\text{V}^{-1}\text{s}^{-1}$ , such as *a*-IGZO, *a*-ZnO,  $\text{InO}_x$ , CdS and CdSe<sup>1,7-10</sup>, have been identified, but the development in their *p*-type counterparts has been still limited despite many years of efforts. Widely explored low-temperature processing *p*-type thin films are amorphous Si, metal oxides (e.g.  $\text{CuO}_x$ ,  $\text{NiO}_x$  and  $\text{SnO}_x$ ), organic compounds/polymers

and polycrystalline germanium (Ge)<sup>2,3,11,12</sup>. Among them, amorphous Si, metal oxides and organic compounds/polymers normally exhibit low hole mobilities on the order of  $1 \text{ cm}^2\text{V}^{-1}\text{s}^{-1}$  or even less<sup>2,5,11,13,14</sup>. Vapor phase-deposited polycrystalline Ge films give high hole mobility up to  $110 \text{ cm}^2\text{V}^{-1}\text{s}^{-1}$ . However, its application is limited by the need of sequential annealing and/or metal catalysts to induce the crystallization<sup>12</sup>. Alternatively, carbon nanotubes (CNTs) have been explored as a promising *p*-type nanomaterial and solution-processed CNT-based networks exhibit hole mobility of up to tens of  $\text{cm}^2\text{V}^{-1}\text{s}^{-1}$ . However, their nanoscale processing remains a concern<sup>6,15-18</sup>. In addition, layer transfer of high-temperature grown materials such as chemical vapor deposition (CVD)-grown CNT arrays and III-V has also been explored, but their large-scale processing is still a challenge<sup>4,19,20</sup>.

Recently, single-crystalline tellurium (Te) nanostructures with a bandgap  $E_g = 0.31 \text{ eV}$  have been shown to exhibit high hole mobilities up to  $707 \text{ cm}^2\text{V}^{-1}\text{s}^{-1}$ , but their large-scale processing is challenging, hence limiting their applications<sup>21,22</sup>. On the other hand, large-scale polycrystalline Te thin films with tens of nanometer thickness prepared by thermal evaporation were

studied in 1960-70s<sup>23-25</sup>. Material quality (*i.e.*, grain size) and transport properties (*i.e.*, carrier mobility) of the evaporated Te films were shown to be tuned by substrate temperature<sup>24</sup>, nucleation layer<sup>26,27</sup> and deposition rate<sup>26,27</sup>. Specifically, the grain size strongly depends on the deposition temperature with the maximum size obtained at cryogenic temperatures<sup>24</sup>. Optimized evaporated Te films have shown high Hall mobility (up to a few hundred  $\text{cm}^2\text{V}^{-1}\text{s}^{-1}$ )<sup>23,24</sup>. However, high-performance FETs with good switching characteristics still have not been achieved<sup>23,25</sup>. Here we report ultrathin Te thin films, which are deposited by thermal evaporation at low temperature ( $-80\text{ }^\circ\text{C}$ ), for fabrication of high-performance wafer-scale *p*-FETs, logic gates and computational circuits. The low processing temperature of Te *p*-FETs makes it compatible with a wide range of substrates, including Si integrated circuits, glass and plastics.

### **Te thin film synthesis and characterization**

Te is composed of covalently-bonded atoms sequenced in a helical chain along a single axis, with chains packed in a hexagonal array *via* van der Waals force (Fig. 1a). Domains with different contrast were observed under polarized light microscopy.

The domains correspond to the arrays of aligned Te molecular chains, acting like wire grid polarizers, with absorption dependent on the angle between the light polarization and the array (polarized transmission measurements of different domains are shown in Supplementary Fig. 1). From XRD analysis, the absence of the (003) peak indicates that Te molecular chains are aligned in plane of the substrate (Supplementary Fig. 2a). To further confirm the crystal structure of different domains, TEM was performed (Fig. 1c). The selected-area electron diffraction (SAED) patterns of two regions with different contrast show single-crystalline diffraction spots with different orientations, suggesting that both regions are single-crystal-like domains (Fig. 1d). The high-resolution transmission electron microscopy (HRTEM) image clearly shows the grain boundary of the two domains (Fig. 1e). Note that defects can be observed from the HRTEM image (Supplementary Fig. 2b), suggesting that domains are not perfect single crystals.

We first investigate the thickness effect on the domain size of Te films evaporated with a substrate temperature of  $-80\text{ }^{\circ}\text{C}$ . Te films with thickness varying from 8 to 30 nm were analyzed using

the polarized light microscope. We observed minimal thickness dependence for the domain size for the studied thickness of 8 to 30 nm (Supplementary Fig. 3). The extracted optical bandgap from the absorption measurements shows a thickness-dependent behavior, from 0.3 eV for bulk to 0.6 eV for 4.5 nm-thick evaporated Te films (Fig. 1e and Supplementary Fig. 4) due to quantum confinement effect. Our results are consistent with the previously reported calculations<sup>28</sup> and experimental results on single-crystalline Te layers<sup>29</sup>.

We also found that the substrate temperature for evaporation has significant impact on the Te film quality. When the substrate temperature decreases from -10 °C to -60 °C, the average area of domains monotonically increases from  $\sim 3 \mu\text{m}^2$  to  $\sim 25 \mu\text{m}^2$  (Supplementary Fig. 5). Below -60 °C, the domain size does not change with further decrease of temperature (Supplementary Fig. 5f). At room temperature (the substrate temperature of 25 °C), the film is not continuous and instead consists of small nanoparticles (Supplementary Fig. 5e).

### **Electrical characterization of Te field-effect transistors**

The evaporation temperature effect on the device



performance of Te FETs is explored given its significant impact on the domain size. We fabricate FETs based on Te films (8 nm) evaporated at different temperatures from 25 °C to -80 °C. The device structure consists of a Ti/Au local bottom gate, a 5-nm ZrO<sub>2</sub> ( $\epsilon \approx 16$ ) gate dielectric (Fig. 2a), and Ni as source/drain metal contacts. The energy band diagram of the device is shown in Supplementary Fig. 6a. As shown in Supplementary Fig. 6b, the effective mobility decreases from 35 to 10 cm<sup>2</sup>V<sup>-1</sup>s<sup>-1</sup> with the increase of the substrate temperature. The higher mobility for FETs based on Te thin film evaporated at -80 °C can be mainly attributed to larger domain size as compared to those deposited at higher temperatures<sup>24</sup>. To this end, we use Te films evaporated with a substrate temperature of -80 °C for subsequent device and circuit fabrication.

Uniform Te FETs can be easily fabricated at wafer scale given the simplicity of the Te deposition (Fig. 2b inset). Te FET shows a typical *p*-type characteristic as shown in Fig. 2b, c. A hysteresis in the voltage sweep measurement is observed which is a common behavior for a thin film device without encapsulation (Supplementary Fig. 6c, d). The transistor exhibits an effective

hole mobility of  $\sim 35 \text{ cm}^2\text{V}^{-1}\text{s}^{-1}$ , on/off current ratio of  $\sim 10^4$  and subthreshold swing (SS) of  $108 \text{ mVdec}^{-1}$  at room temperature (Fig. 2d, e). To study the uniformity of Te FETs, we randomly measured 60 devices on a wafer. The devices exhibit a narrow distribution in performance with standard deviation of  $32 \pm 7 \text{ cm}^2\text{V}^{-1}\text{s}^{-1}$  in mobility,  $9491 \pm 4765$  in on/off current ratio, and  $114 \pm 9 \text{ mVdec}^{-1}$  in SS (Fig. 2f, g, h). Importantly, the performance of Te FET did not show obvious degradation after leaving the device in ambient air without any encapsulation for 30 days (Fig. 2i). Temperature-dependent  $I_d$ - $V_g$  transfer curves are measured to investigate the carrier scattering mechanisms (Supplementary Fig. 6e, f). The effective mobility is nearly independent of temperature from 77 K to 300 K (Supplementary Fig. 6g), suggesting that the mobility is limited by the grain boundary and surface roughness scattering<sup>22,30</sup>. In the future, it is possible to further improve the mobility by increasing the domain size and reducing the surface roughness by optimizing the evaporation process.

We then investigated the thickness-dependent effective mobility and on/off current ratio, the key metrics for transistors (Fig. 2j). Here, we vary the channel thickness from 4 to 16 nm. Te

FETs become open circuits at sub-4 nm thickness and the evaporated films were found to be not continuous. The on/off current ratio decreases from  $\sim 10^5$  (4 nm Te) to  $\sim 10$  (16 nm Te), which is likely due to the bandgap of Te channel decreases and electrostatic control is reduced as thickness increases. In contrast, the effective mobility increases with thickness monotonically from  $10 \text{ cm}^2\text{V}^{-1}\text{s}^{-1}$  to  $140 \text{ cm}^2\text{V}^{-1}\text{s}^{-1}$ . The monotonically increased mobility along with the film thickness could be attributed to the reduced effect of surface roughness scattering for thicker films, which is often observed in various material systems<sup>19,31</sup>.

As a benefit of the low temperature evaporation process, Te can be readily deposited on various substrates such as glass and plastic over large areas (Fig. 3a,b). We fabricated 8-nm-thick Te FETs on 4-inch quartz wafer and polyethylene terephthalate (PET) substrates with the same device structure shown in Fig. 2a. Te FETs on different substrates show similar hole mobilities (in the range of  $25\text{-}35 \text{ cm}^2\text{V}^{-1}\text{s}^{-1}$ ) and on-currents (Fig. 3c,d, and Supplementary Fig. 7), suggesting that Te FETs can be used in broad applications, such as flexible and transparent electronics

and displays<sup>32</sup>. We characterized the mechanical flexibility and operational stability of Te FETs on Kapton substrate. Fig. 3e shows a photograph of Te FETs on Kapton substrate when bent to a radius of 6 mm. The device mobility and on/off current ratio do not significantly change during bending up to a radius of 4 mm, corresponding to a tensile strain of 0.63% (Fig. 3f). A change in device performance is observed when strain is higher than 0.63%. The device becomes open circuit when strain reaches 1.5%, which is nonrecoverable (Supplementary Fig. 8). Furthermore, the electrical properties of the device do not significantly change after multiple cycles (500) of bending at a radius of 6 mm, which corresponds to a strain of 0.42% (Fig. 3g, and h).

### **Logic gates and circuits based on Te devices**

The high uniformity of Te FETs allows for fabrication of logic gates and computational circuits. Considering the trade-off between on/off current ratio and mobility, 8-nm-thick Te FETs are selected as the building blocks. First, a *p*-MOS inverter, the simplest logic gate, is constructed using two Te devices, acting as the driver and active load, respectively (Fig. 4a inset, Supplementary Fig.9a). Fig. 4a shows typical voltage transfer

curves with a gain of 22 and 38 at an operating voltage  $V_{dd}=1$  V and  $V_{dd}=2$  V, respectively. We also fabricated a NAND gate with a logically valid output (Fig. 4b, Supplementary Fig.9b). The basic logic gates facilitate the design of more complex circuits. A full-adder is a key component of arithmetic logic units, with myriad applications such as encoders, decoders and binary calculation<sup>17</sup>. Functionally, a full-adder is aimed to add two one-bit numbers (A and B) and one carry number ( $C_0$ ), producing a two-bit sum (S) and new carry ( $C_1$ ) as outputs. The Te FET based full-adder, which includes 9 NANDs and 4 inverters that are constructed from a total number of 35 transistors, is fabricated and shown in Fig. 4c. The full-adder functions properly with a maximum output voltage loss of 6% (Fig. 4c, d, Supplementary Fig.9c, d). Therefore, we also fabricated a multiplier circuit to realize multiplication functions using 39 transistors. Functionally, 4 input terminals accept two 2-bit factors ( $A_1A_0$  and  $B_1B_0$ ) and the output is a 4-bit product ( $F_3F_2F_1F_0$ ). The multiplication operation is achieved with a maximum output voltage loss of 3% (Fig. 4c, d, Supplementary Fig.9e, f).

### **Demonstration of three-dimensional monolithic circuits**

The performance of Te  $p$ -FETs is sufficient to enable the realization of complementary 3D monolithic ICs and back-end-of-line (BEOL) electronics when combined with the existing  $n$ -FETs such as  $a$ -IGZO<sup>1,4</sup>. Therefore, as a proof-of-concept, we fabricated multilayer transistors and logic gates based on Te  $p$ -FETs. Figure 5a, b show the two-layer transistors fabricated using an evaporated SiO<sub>x</sub> isolation layer. The devices on the 1<sup>st</sup> and 2<sup>nd</sup> layers show similar  $I_d$ - $V_g$  transfer curves (Fig. 5c). Importantly, the electrical property of the 1<sup>st</sup> layer does not significantly change after the construction of the top layer given the low processing temperature used for all the fabrication steps (Supplementary Fig. 10). Note that a small threshold voltage ( $V_t$ ) shift is observed. This shift is likely caused by fixed charge in the intermediate oxide or at the semiconductor-oxide interface, which can be improved by moving to a more suitable insulation layer or a more optimized deposition technique. A 3D circuit, specifically, a two-layer inverter, is also demonstrated. The upper-layer transistor, acting as an active load, is vertically connected to the bottom-layer transistor acting as the driver (Fig. 5d, f). The 3D inverter accomplishes the desired NOT function with a gain of

approximately 12 at a  $V_{dd}=2$  V (Fig. 5f). These results demonstrate the practicality of Te  $p$ -FETs for monolithic 3D circuits.

## Conclusions

We have demonstrated that evaporated Te thin films are an attractive material for  $p$ -FETs processed at low temperatures with important practical implications in monolithic 3D circuits, as well as flexible and transparent, and/or large-area electronics. We believe that further improvements in the thin film quality (e.g. purity, crystallinity and surface smoothness) will enhance the device performance of Te FETs. Future integration of Te  $p$ -FETs with low temperature  $n$ -type FETs, such as  $a$ -IGZO, can enable the construction of 3D CMOS circuits. Te  $p$ -FETs can also be implemented into BEOL electronics with existing Si CMOS circuits to further extend/enhance the system performance.

## References

- 1 Nomura, K. *et al.* Room-temperature fabrication of transparent flexible thin-film transistors using amorphous oxide semiconductors. *Nature* **432**, 488 (2004).
- 2 Wang, Z., Nayak, P. K., Caraveo-Frescas, J. A. & Alshareef, H. N. Recent developments in  $p$ -Type oxide semiconductor materials and devices. *Adv. Mater.* **28**, 3831-3892 (2016).
- 3 Kim, M.-G., Kanatzidis, M. G., Facchetti, A. & Marks, T. J. Low-temperature fabrication of high-performance metal oxide thin-film electronics via combustion processing. *Nat.*

- Mater.* **10**, 382 (2011).
- 4 Shulaker, M. M. *et al.* Three-dimensional integration of nanotechnologies for computing and data storage on a single chip. *Nature* **547**, 74 (2017).
- 5 Kwon, J. *et al.* Three-dimensional monolithic integration in flexible printed organic transistors. *Nat. Commun.* **10**, 54 (2019).
- 6 Chen, H., Cao, Y., Zhang, J. & Zhou, C. Large-scale complementary macroelectronics using hybrid integration of carbon nanotubes and IGZO thin-film transistors. *Nat. Commun.* **5**, 4097 (2014).
- 7 Rembert, T., Battaglia, C., Anders, A. & Javey, A. Room temperature oxide deposition approach to fully transparent, all-oxide thin-film transistors. *Adv. Mater.* **27**, 6090-6095 (2015).
- 8 Yeom, H.-I., Ko, J. B., Mun, G. & Park, S.-H. K. High mobility polycrystalline indium oxide thin-film transistors by means of plasma-enhanced atomic layer deposition. *J. Mater. Chem. C* **4**, 6873-6880 (2016).
- 9 Martinez-Landeros, V. H. *et al.* Low-temperature thin film transistors based on pulsed laser deposited CdS active layers. *Semicond. Sci. Tech.* (2018).
- 10 Stinner, F. S. *et al.* Flexible, high-speed CdSe nanocrystal integrated circuits. *Nano Lett.* **15**, 7155-7160 (2015).
- 11 Sirringhaus, H. 25th Anniversary Article: Organic field-effect transistors: the path beyond amorphous silicon. *Adv. Mater.* **26**, 1319-1335 (2014).
- 12 Shahrjerdi, D., Hekmatshoar, B., Mohajerzadeh, S., Khakifirooz, A. & Robertson, M. High mobility poly-Ge thin-film transistors fabricated on flexible plastic substrates at temperatures below 130 °C. *J. Electron. Mater.* **33**, 353-357 (2004).
- 13 Fortunato, E., Barquinha, P. & Martins, R. Oxide semiconductor thin-film transistors: a review of recent advances. *Adv. Mater.* **24**, 2945-2986 (2012).
- 14 Powell, M. J. The physics of amorphous-silicon thin-film transistors. *IEEE T. Electron Dev.* **36**, 2753-2763 (1989).
- 15 Geier, M. L. *et al.* Solution-processed carbon nanotube thin-film complementary static random access memory. *Nat. Nanotechnol.* **10**, 944 (2015).
- 16 Park, H. *et al.* High-density integration of carbon nanotubes via chemical self-assembly. *Nat. Nanotechnol.* **7**, 787 (2012).
- 17 Chen, B. *et al.* Highly uniform carbon nanotube field-effect transistors and medium scale integrated circuits. *Nano Lett.* **16**, 5120-5128 (2016).
- 18 Cao, Q. *et al.* Arrays of single-walled carbon nanotubes with full surface coverage for high-performance electronics. *Nat. Nanotechnol.* **8**, 180 (2013).
- 19 Ko, H. *et al.* Ultrathin compound semiconductor on insulator layers for high-performance nanoscale transistors. *Nature* **468**, 286 (2010).
- 20 Ahn, J.-H. *et al.* Heterogeneous three-dimensional electronics by use of printed semiconductor nanomaterials. *Science* **314**, 1754-1757 (2006).
- 21 Wang, Y. *et al.* Field-effect transistors made from solution-grown two-dimensional tellurene. *Nat. Electron.* **1**, 228 (2018).



- 22 Zhou, G. *et al.* High-mobility helical tellurium field-effect transistors enabled by  
transfer-free, low-temperature direct growth. *Adv. Mater.* **30**, 1803109 (2018).
- 23 Dutton, R. W. & Muller, R. S. Electrical properties of tellurium thin films. *Proc. IEEE* **59**,  
1511-1517 (1971).
- 24 Okuyama, K. & Kumagai, Y. Grain growth of evaporated Te films on a heated and  
cooled substrate. *J. Appl. Phys.* **46**, 1473-1477 (1975).
- 25 Weimer, P. A p-type tellurium thin-film transistor. *Proc. IEEE* **52**, 608-609 (1964).
- 26 Okuyama, K., Yamamoto, H. & Kumagai, Y. Effect of Au nucleation centers and  
deposition rate on crystallinity and electronic properties of evaporated Te films. *J.*  
*Appl. Phys.* **46**, 105-111 (1975).
- 27 Dutton, R. & Muller, R. Large grain tellurium thin films. *Thin Solid Films* **11**, 229-236  
(1972).
- 28 Wu, W., Qiu, G., Wang, Y., Wang, R. & Ye, P. Tellurene: its physical properties, scalable  
nanomanufacturing, and device applications. *Chem. Soc. Rev.* **47**, 7203-7212 (2018).
- 29 Chen, J. *et al.* Ultrathin  $\beta$ -tellurium layers grown on highly oriented pyrolytic graphite  
by molecular-beam epitaxy. *Nanoscale* **9**, 15945-15948 (2017).
- 30 Ellmer, K. & Mientus, R. Carrier transport in polycrystalline ITO and ZnO: Al II: the  
influence of grain barriers and boundaries. *Thin Solid Films* **516**, 5829-5835 (2008).
- 31 Dimitriadis, C. A., Coxon, P. A., Dozsa, L., Papadimitriou, L. & Economou, N.  
Performance of thin-film transistors on polysilicon films grown by low-pressure  
chemical vapor deposition at various pressures. *IEEE T. Electron Dev.* **39**, 598-606  
(1992).
- 32 Franklin, A. D. Nanomaterials in transistors: From high-performance to thin-film  
applications. *Science* **349**, aab2750 (2015).

## Acknowledgements

Synthesis work was supported by the U.S. Department of Energy,

Office of Science, Office of Basic Energy Sciences, Materials

Sciences and Engineering Division under contract no.DE-AC02-

05CH11231 within the Electronic Materials Program (KC1201).

Work at the Molecular Foundry was supported by the Office of Science, Office of Basic Energy Sciences, of the U.S. Department of Energy under Contract No. DE-AC02-05CH11231. We thank N. Tamura for help with XRD measurements.

### **Author contributions**

C.Z., C.T. and A.J. conceived the idea for the project. C.Z. and A.J. designed the experiments. C.Z., M.A. and Y.Z. fabricated the devices. C.Z. performed the device measurements. C.Z., C.T., X.S., D.H.L., M.H., H.N., L.L. and M.S. performed material characterizations. C.Z. and A.J. analyzed the data. C.Z., C.T., D.H.L.

and A.J. wrote the manuscript. All authors discussed the results and commented on the manuscript.

### **Competing interests**

The authors declare no competing financial interests.


### **Additional information**

Supplementary information is available for this paper at

<https://doi.org/xxx>.


**Reprints and permissions information** is available at

[www.nature.com/reprints](http://www.nature.com/reprints)

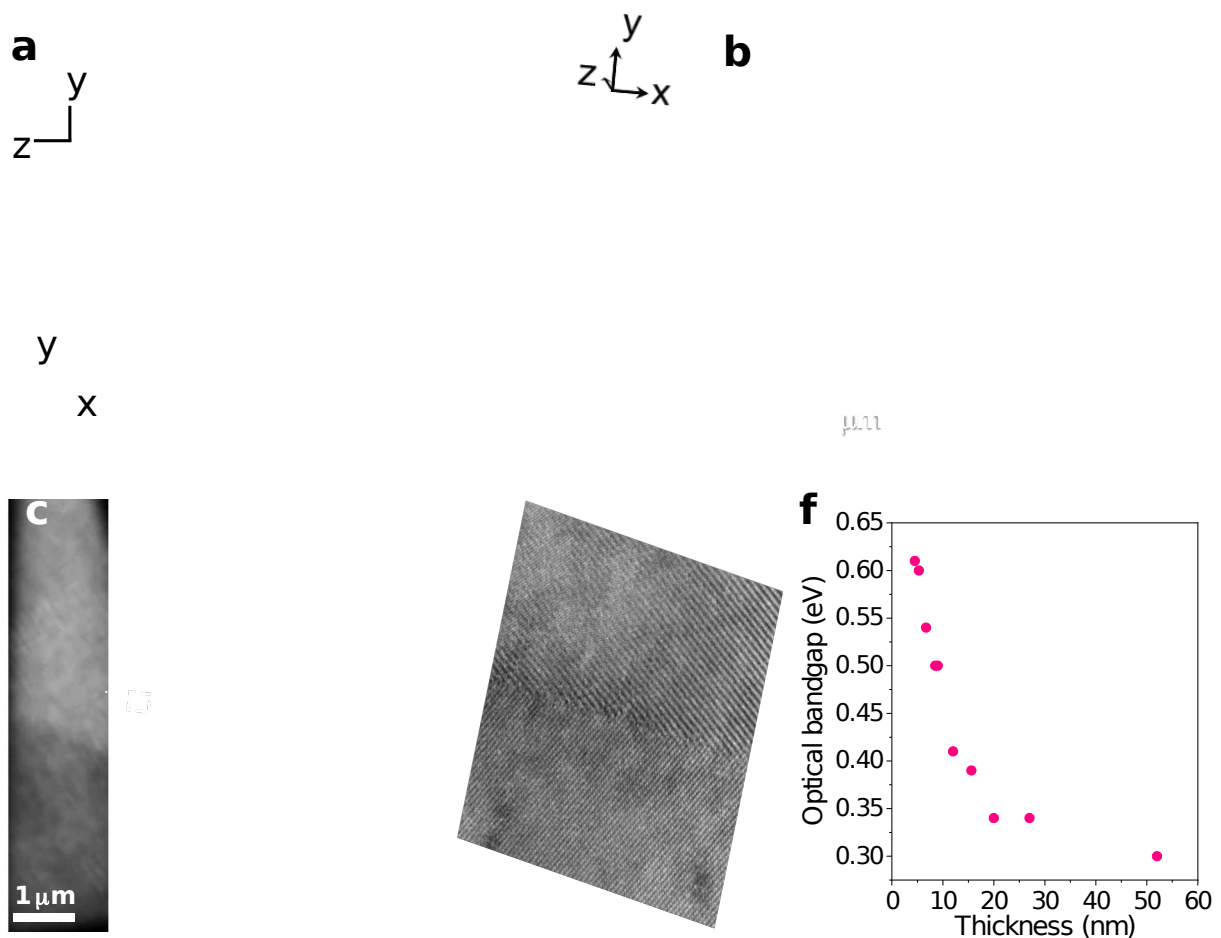


**Fig. 1 | Characterization of Te thin films evaporated with a substrate temperature of -80 °C. a,** Crystal structure of Te. **b,** Polarized light microscopy image of a Te film (9 nm). **c,** Zoom-in optical image of a Te film (9 nm) on SiO<sub>2</sub> TEM grid, depicting a grain boundary. **d,** The low magnification TEM image of the Te film (9 nm) in **c**. The dash line indicates the grain boundary. Insets are the corresponding SAED patterns of selected areas. **e,** HRTEM image of the same film at the boundary area. **f,** Thickness-

dependent optical bandgap of Te thin films.

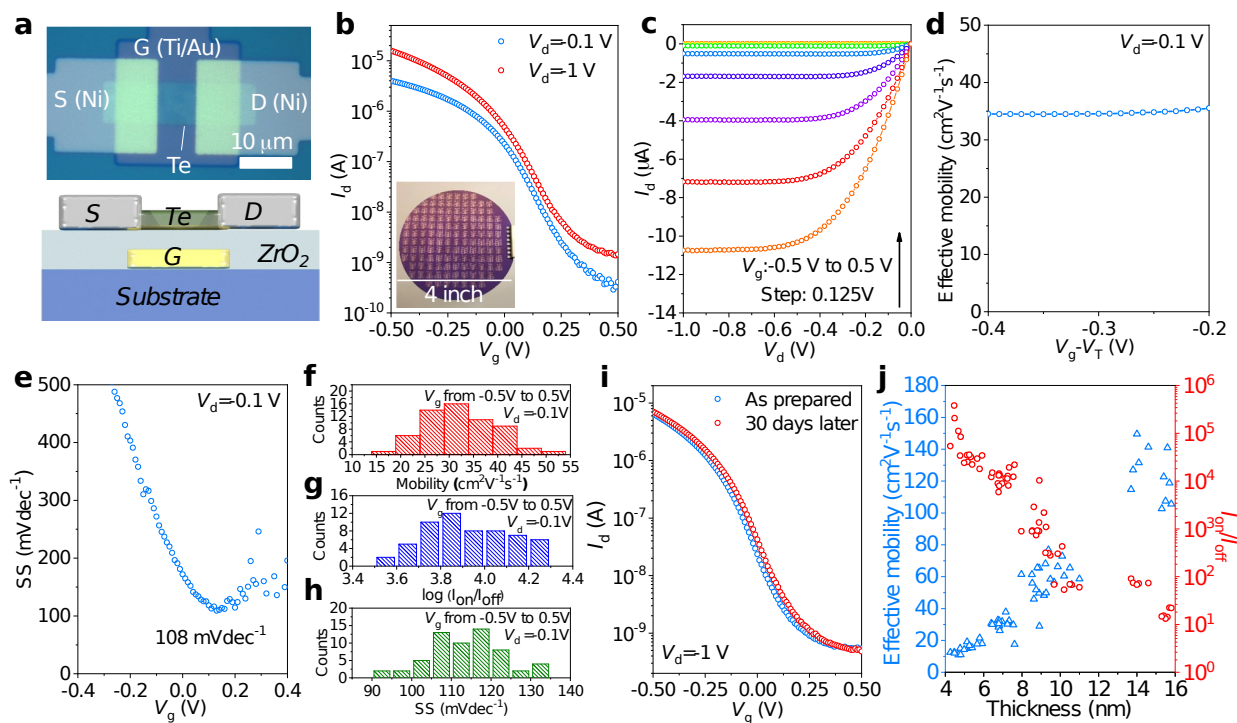


**Fig. 2 | Field-effect transistors based on Te evaporated with a substrate temperature of -80 °C.** **a**, Optical image of a typical Te FET and schematic diagram of the device structure. **b**,  $I_d$ - $V_g$  transfer curves of the Te transistor (8 nm) in **a**. Inset, photograph of wafer-scale (4 inch) Te FETs. **c**,  $I_d$ - $V_d$  output characteristics of the same device as shown in **b**. **d-e**, effective mobility (**d**) and SS (**e**) derived from the  $I_d$ - $V_g$  shown in **b**. **f-h**, The statistical distribution of effective mobility (**f**),  $\log(I_{on}/I_{off})$  (**g**), SS (**h**) for 60 individual transistors from different points on the wafer. **i**,  $I_d$ - $V_g$  characteristic of a Te FET measured immediately and thirty

days after fabrication. **j**, Thickness-dependent effective mobility (blue) and on/off current ratio (red) for Te FETs. Note that the thicknesses of Te film were measured by AFM.

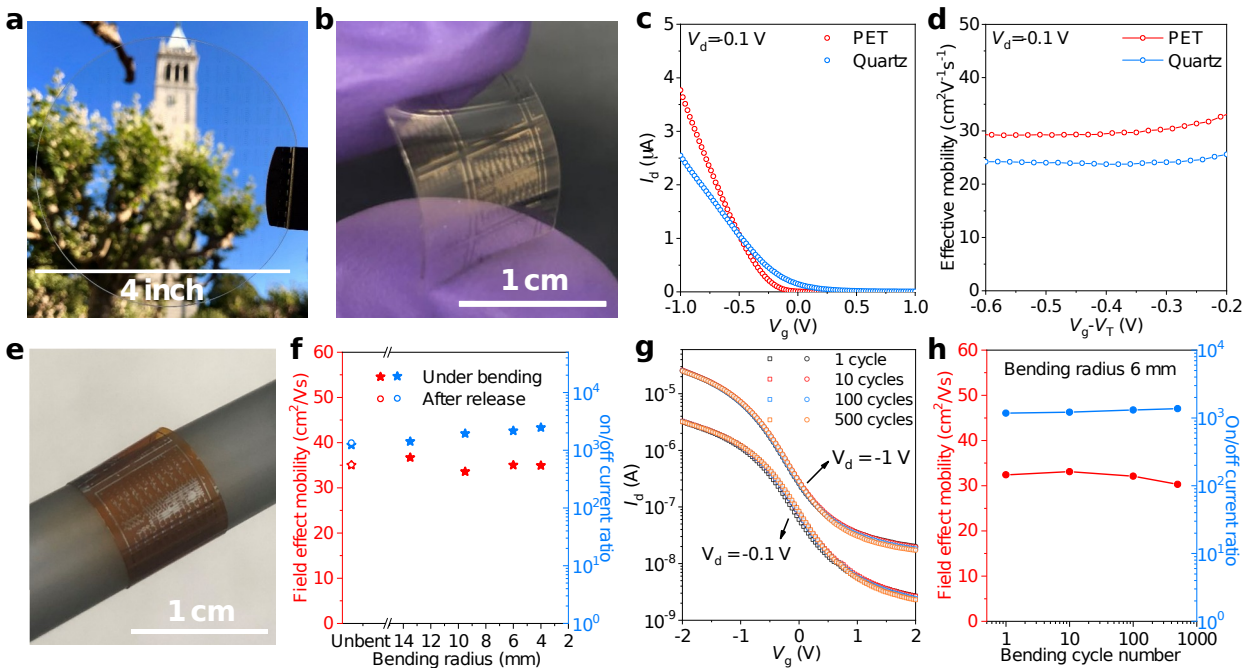

**Fig. 3 | Flexible and transparent field-effect transistors based on Te evaporated with a substrate temperature of 80 °C. a-b,** Photograph of Te FETs fabricated on 4-inch quartz wafer (a) and PET substrate (b). **c,**  $I_d$ - $V_g$  transfer curves for evaporated Te FETs on quartz and PET substrates. **d,** Effective mobility of 8-nm-thick Te FETs on quartz and PET substrates. **e,** Photograph of Te FETs on Kapton substrate while bent (thickness of the Kapton substrate is 50  $\mu\text{m}$ ). **f,** Effective mobility and on/off current ratio of Te FET (8 nm) on Kapton substrate under different bending radius. **g,**  $I_d$ - $V_g$  transfer curves of the Te transistor (8 nm) on PET substrate after different bending cycles. **h,** Effective mobility and on/off current ratio of Te FET (8 nm) on Kapton


substrate after different bending cycles.

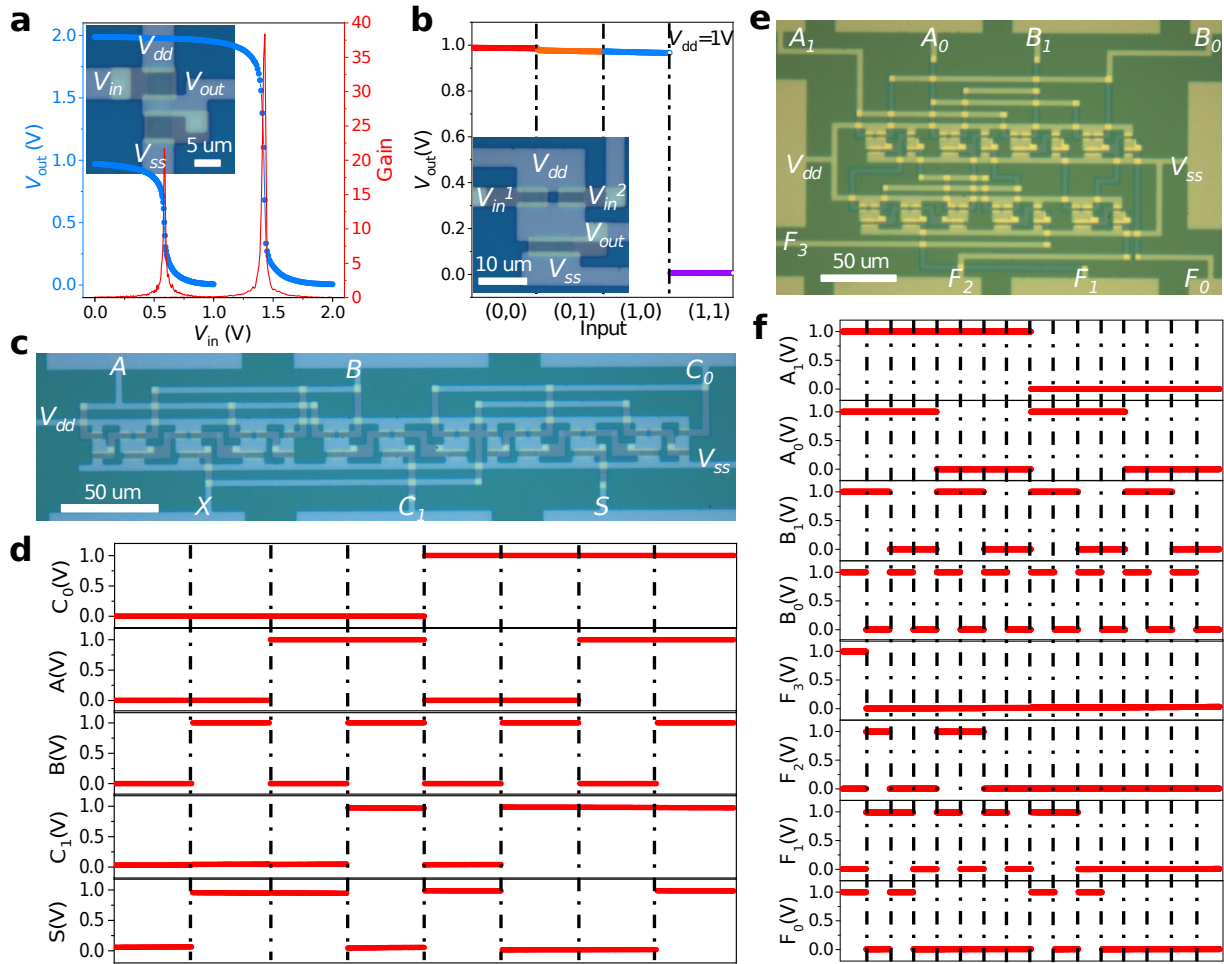

**Fig. 4 | Integrated circuits based on Te field-effect transistors. a-b,** Inverter (a) and NAND (b) logic gate performance, inset shows an optical image of the device. **c-d,** Optical image (c) and output voltage (d) of a full adder. **e-f,** Optical image (e) and output voltage (f) of a 2-bit multiplier. The



supply voltage,  $V_{dd}$  was 1 V for the NAND gate, full adder, and 2-bit multiplier. Different input and the corresponding output states were separated by black dashed lines in **d** and **f**. Circuit designs and experimental truth table are shown in Supplementary Fig. 9.

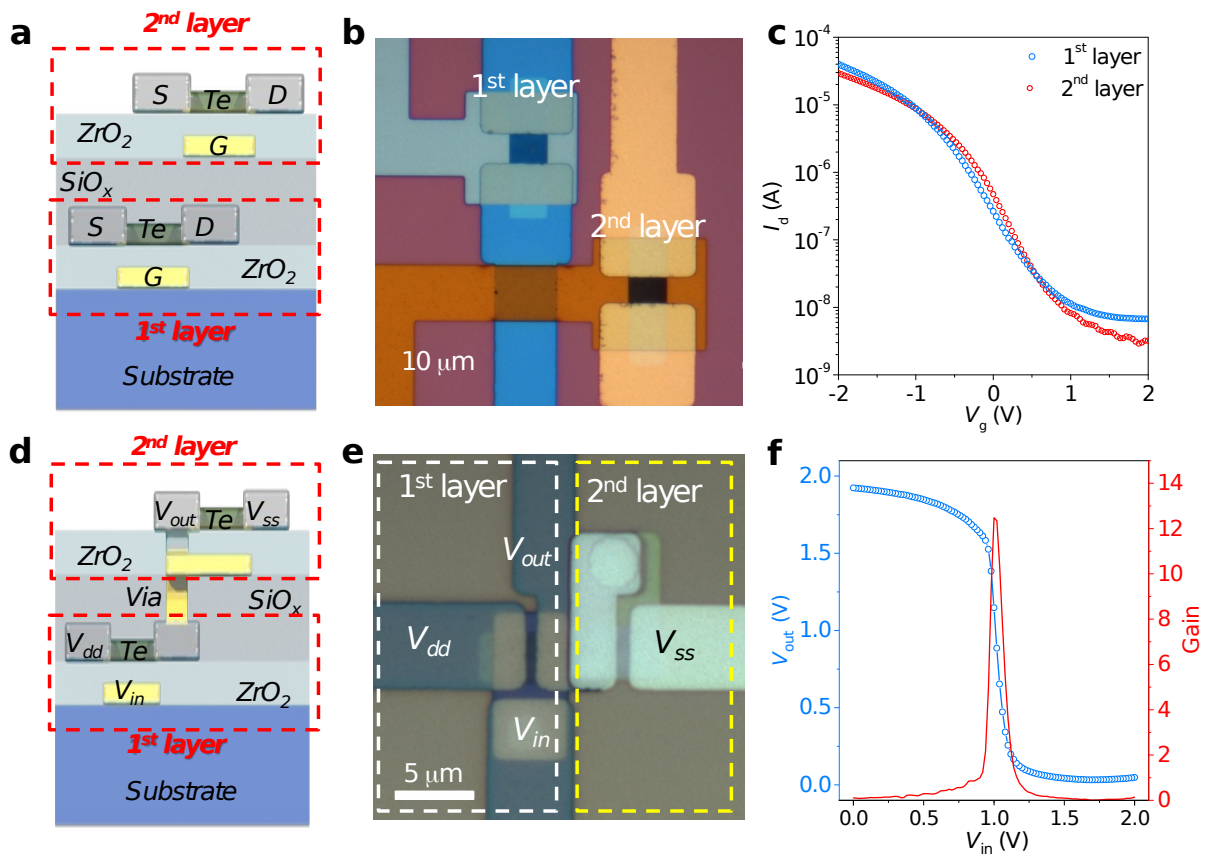

**Fig. 5 | Multilayered Te field-effect transistors and 3D inverters.** **a-c**, A schematic diagram (**a**), optical image (**b**) and  $I_d$ - $V_g$  transfer curves ( $V_d = -1$  V) (**c**) of the 2-layered transistor. The

thickness of Te channels for both layers is 8 nm. **d-f**, A schematic diagram (**d**), optical image (**e**) and voltage transfer characteristic (**f**) of the 3D inverter based on Te FETs (Te channels 8 nm).

## **Methods**

**Thermal evaporation of tellurium thin films.** Te thin films were deposited in an Edwards Coating System (E306A thermal evaporator system) with a base pressure about  $1.5 \times 10^{-6}$  mbar. Te pellets (99.999%, Sigma-Aldrich) were used as the thermal evaporation source. When the pressure reached  $2 \times 10^{-6}$  mbar, the substrate temperature was reduced to  $-80$  °C by cooled nitrogen gas flow prior to the evaporation. The evaporation rate was controlled to be around  $10 \text{ \AA s}^{-1}$  for all the evaporations. The thickness of Te thin film was monitored by during deposition. After evaporation, the samples were taken out after the substrate temperature recovered to room temperature. All the Te thin films studied were prepared under these conditions except Te thin films evaporated at different substrate temperatures.

### **Device Fabrication.**

**Single transistors.** Field-effect transistors were fabricated on various substrates by the following photolithography, deposition and lift-off processes. Firstly, gate regions were patterned on the  $\text{SiO}_2/\text{Si}$ , PET, Kapton or quartz substrates and Ti/Au (2 nm/18 nm) gate electrodes were deposited by e-beam evaporation. The  $\text{ZrO}_2$

dielectric layer was then deposited by ALD. For single transistors on SiO<sub>2</sub>/Si substrates, ZrO<sub>2</sub> was deposited at 200 °C with a thickness of 5nm. For transistors on PET, and quartz, ZrO<sub>2</sub> was deposited at 110 °C with a thickness of 10 nm. For transistors on Kapton, ZrO<sub>2</sub> was deposited at 110 °C with a thickness of 20 nm. Following the gate fabrication, Te channel regions were patterned over the gate area and Te was deposited. After the lift-off process, source and drain regions were patterned. Ni (30 nm) was deposited by e-beam evaporation as metal contact. For Te FETs on quartz, sputtered ITO was used as gate (20 nm) and contact material (25 nm) to enable device transparency.

**Logic gates and circuits.** For the logic circuits a 10 nm ZrO<sub>2</sub> was deposited at 200 °C by ALD as the dielectric layer. Via regions were etched by buffered HF solution (BHF). Additionally, Ni/Au (20 nm/10 nm) contacts were used to avoid Ni etching by BHF.

**Two layered transistors and 3D inverters.** The bottom layers were fabricated using the process described above. After the fabrication of the bottom layer, 30 nm SiO<sub>x</sub> was deposited on the top as an intermediate insulation layer by e-beam evaporation and then the next layer was built on the top using the same

procedure used for the first layer. ZrO<sub>2</sub> (10 nm) was deposited at 110 °C by ALD.

**Characterizations.** Te thin films with varying thickness were deposited on quartz substrates for the optical measurement. The thicknesses of Te thin films for optical bandgap measurements and thickness-dependent device performance were measured by AFM (Dimension ICON AFM microscope (Bruker), operating in tapping mode). All other thickness measurements were based on the crystal quartz monitor. TEM characterization was performed on 9-nm thick Te deposited on SiO<sub>2</sub> support TEM membrane (TED PELLA, INC). The Te film in Figure 1c was patterned and transferred on SiO<sub>2</sub> support TEM membrane. TEM characterization was carried on a FEI Titan 60-300 microscope with an acceleration voltage 200 kV at the National Center for Electron Microscopy at Lawrence Berkeley National Laboratory. The sample for XRD measurement was deposited on glass with a thickness of 50 nm (based on the quartz crystal monitor). XRD measurement was performed on an AXS D8 Discover GADDS, Bruker with a Co K $\alpha$  X-ray source ( $\lambda = 1.7903 \text{ \AA}$ ). A Shimadzu SolidSpec-3700 spectrometer was used to measure the transmission and diffuse

reflection of the samples. The polarized-light optical microscopy images of Te thin films were taken by a polarized LV100N optical microscopy (Nikon Inc.). Room-temperature electrical measurements were performed in probe station using 4155C Semiconductor Parameter Analyzer (Agilent Technologies). Temperature-dependent electrical measurements were performed in a cryogenic probe station (LakeShore) with a B1500a Semiconductor Device Analyzer (Keysight). Effective mobility is calculated using:  $\mu_{eff} = \frac{dI_d}{dV_d} \frac{L}{WC_{ox}(V_g - V_t)}$  (1), where  $C_{ox}$  is the gate

oxide capacitance,  $L$  is the channel length,  $W$  is the device width and  $V_t$  is the threshold voltage.  $I_d$  was measured at low bias ( $V_d = -0.1$  V). Subthreshold swing (SS) is derived from equation:

$$SS = \left( \frac{d(\log I_d)}{dV_g} \right)^{-1} \quad (2), \text{ at the low bias } (V_d = -0.1 \text{ V}).$$