

UCLA

UCLA Previously Published Works

Title

Ensembles of Metastable States Govern Heterogeneous Catalysis on Dynamic Interfaces

Permalink

<https://escholarship.org/uc/item/7nx413ss>

Journal

Accounts of Chemical Research, 53(2)

ISSN

0001-4842

Authors

Zhang, Zisheng

Zandkarimi, Borna

Alexandrova, Anastassia N

Publication Date

2020-02-18

DOI

10.1021/acs.accounts.9b00531

Peer reviewed

Ensembles of metastable states govern heterogeneous catalysis on dynamic interfaces

ZISHENG ZHANG,¹ BORNA ZANDKARIMI,¹

ANASTASSIA N. ALEXANDROVA^{1,2,*}

¹Department of Chemistry and Biochemistry, University of California, Los Angeles, 607 Charles E. Young Drive East, Los Angeles, CA 90095

²California NanoSystems Institute, 570 Westwood Plaza, Los Angeles, CA 90095


*ana@chem.ucla.edu

RECEIVED ON ...

CONSPECTUS

Heterogeneous catalysis is at the heart of chemical industry. Being able to tune and design efficient catalysts for processes of interest is of an utmost importance, and for this, the molecular-level understanding of heterogeneous catalysts is the first step, and indeed a prime focus of the modern catalysis research. For a long time, a single most thermodynamically stable structure of the catalytic interface attained in reaction conditions had been envisioned as the reactive phase. However, some catalytic interfaces continue to undergo structural dynamics in the steady state, triggered by high temperatures, pressures, and binding and changing reagents. Among particularly dynamic interfaces are such widely-used catalysts as crystalline and amorphous surfaced supporting (sub-)nano metallic clusters. Recently, it became clear that this dynamic fluxionality causes the supported clusters to populate many distinct structural and stoichiometric states in catalytic conditions. Hence, the catalytic interface should be viewed as an evolving statistical ensemble of many (not one) structures. Every member in the ensemble contributes to the properties of the catalyst differently, and in proportion to its probability to be populated. This new notion flips the established paradigm and calls for new theory, modeling approaches, *operando* measurements, and updated design strategies.

The statistical ensemble nature of surface-supported sub-nano cluster catalysts can be exemplified by oxide-supported and adsorbate-covered Pt, Pd, Cu, CuPd clusters, catalytic toward oxidative and non-oxidative dehydrogenation. They have access to a variety of 3D and quasi-2D shapes. The compositions of their thermal ensembles are dependent on the cluster size, leading to size-specific catalytic activities and the famous “every atom counts” phenomenon. The support and adsorbates affect catalyst structures, and state of the reacting species causes the ensemble to change in every reaction intermediate. The most stable member of the ensemble dominates the thermodynamic properties of the corresponding intermediate, whereas the kinetics can be determined by more active but less populated metastable catalyst states, and that suggests that many earlier studies might have overlooked the actual active sites. Both effects depend on the relative time-scales of catalyst restructuring and reaction dynamics. The catalyst may routinely operate off-equilibrium. Ensemble phenomena lead to surprising exceptions from established rules of catalysis, such as scaling relations, and Arrhenius behavior. Catalyst deactivation is also an ensemble property, and its extent of mitigation can be predicted through the new paradigm. These findings were enabled by advances in theory, such as global optimization and subsequent utilization of multiple local minima, and pathways sampling, as well as *operando* catalyst characterization. The fact that the per-site and per-species resolution is needed for the description and predicting of catalyst properties gives theory the central role in catalysis research, as most experiments provide ensemble-average information and cannot detect the crucial minority species that may be responsible for the catalytic activity.

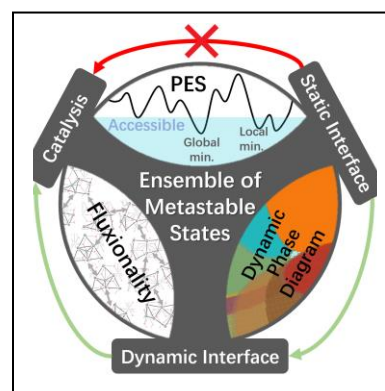

Heterogeneous catalysis is the pivot of modern chemical industry, enabling the efficient production of over 90% of all commercial chemicals.^{1,2} Central to catalysis research has been the molecular-level insight into the catalytic processes, the state of the catalyst in reaction conditions, and the nature of the active site. This insight has been enabled by the development of experimental and theoretical characterization techniques. Surface science methods such as XPS, XAFS, XANES, STM, neutron diffraction, operating at low pressures, are used to characterize model catalysts, and inform about the elementary events possible at the interface. A subset of these techniques advanced to the *operando* regime, probing the state of the system in reaction conditions. On the theory side, electronic structure, kinetic modeling, and computational spectroscopy give highly specific mechanistic details. The challenge for theory has been to have a realistic enough model, and accurate enough electronic structure methods, for the results to be reliable. Despite the known limitations, theory provided useful and complementary insights, trends, and suggestions to experiment in catalyst discovery.^{3,4} Still, in some cases, the discrepancy between theory and experiment have been inconsolable, and not always easily blamed on the error of Density Functional Theory (DFT) prevalently used in catalysis research. Clearly our models are often insufficient.

The molecular view of the catalytic interface has been largely inspired by what surface science could probe and theory could affordably model: a largely stationary surface, nano particle, or the global minimum (GM) of a supported cluster. This well-defined and stable structure of the interface has been presumed to be the active phase whose geometry would be largely maintained during the catalytic process. However, the real catalytic interface is subject to heat, illumination, electrochemical potential, pressure of reactants, products and solvent.⁵⁻⁸ Such conditions can bring a dynamic interfaces into motion, as was seen by *operando* measurements. Nanoparticles and nanostructured surfaces have been observed to undergo restructuring.⁹⁻¹¹ The interfaces supporting sub-nano clusters, or amorphous and understoichiometric surfaces are even more dynamic, because they have more unsaturated bonds.^{6,12-14} Even perfect surfaces have certain dynamicity due to different adsorbate configurations that go through constant interconversion.¹⁵ Clearly, this motion should thermally populate new local minima on the free energy surface of the catalyst, which could play a non-trivial role in catalysis. However, in most theoretical studies, the PES is not thoroughly sampled, and only the GM, or a few putative minima structure, was desired and used in mechanistic calculation. Our contribution consists of

the extension of the paradigm in catalysis modeling toward including those metastable catalyst states present in reaction conditions and describing the interface as a statistical ensemble of many states, not just one. On this basis, we arrived at a number of surprising findings that now change our thinking about catalysis when the interface is highly dynamic. We largely focus on surface-supported clusters, though venture in extended amorphous surface, and describe how the paradigm applies also to more stationary interfaces.

DYNAMIC CATALYSTS ARE ENSEMBLES OF MANY DISTINCT STATES

Metallic clusters are held together by delocalized, non-directional chemical bonds, causing structural flexibility, and relatively flat and anharmonic potential energy surfaces (PESs). Geometries of clusters are easily influenced by atomic substitution, change of charge or the support, adsorption of molecules, etc. Most obviously, the structure can just relax upon adsorbate binding. This phenomenon was originally named “fluxionality” by Landman.¹⁶ We shows that clusters may also thermally cross small barriers separating the local minima, and the available minima and the barriers may change as a function of the bound adsorbates.^{17,18} Dozens if not hundreds of minima can be populated at catalytic temperatures (e.g. 300-700 K), and the resulting ensembles of states may dynamically evolve during the reaction.²¹ In our works, the term “fluxionality” began to be used in this broader sense.

Evidence for this kind of fluxionality exists in experiment and simulations. The *in situ* time-resolved structural characterization by energy-dispersive X-ray absorption fine structure (DXAFS) was used to demonstrate the CO-induced disintegration of Rh clusters on Al₂O₃ under 26.7 kPa of CO at 298 K, occurring on the time-scales of 0.8–3 s.¹⁹ For Au clusters deposited on CeO₂, the PES is apparently flatter and rearrangement time-scales are shorter,¹³ so *ab initio* Molecular Dynamics (MD) was able to show significant restructuring involving CO adsorption-induced dissociation of Au-CO entities to the support (Figure 1a).¹⁴ Isomerization without disintegration was also filmed: Pd₄ clusters on graphene isomerize on the time-scales of seconds, leading to all accessible geometries to co-exist at finite temperature.²⁰ The fluxional behavior of supported Pt and PtSn nanoclusters was demonstrated,^{17,21} using a combination of DFT MD and XAS (Figure 1b). Note that the relatively long time-scales involved in the fluxionality with barrier crossing generally limit the insight that MD can provide. The exhaustive sampling of the PES is necessary, and it gives a very rich picture of the states accessible to the catalytic interface.

For example, Pt clusters on α -Al₂O₃ access to ~30 distinct minima in under 1 ns (Figure 1c).¹⁷ If this same Pt₇/ α -Al₂O₃ cluster is covered with adsorbates, e.g. ethylene,²² or hydrogen and alkyls,^{15,22} as in reactions of dehydrogenation, cluster shapes again change beyond recognition.

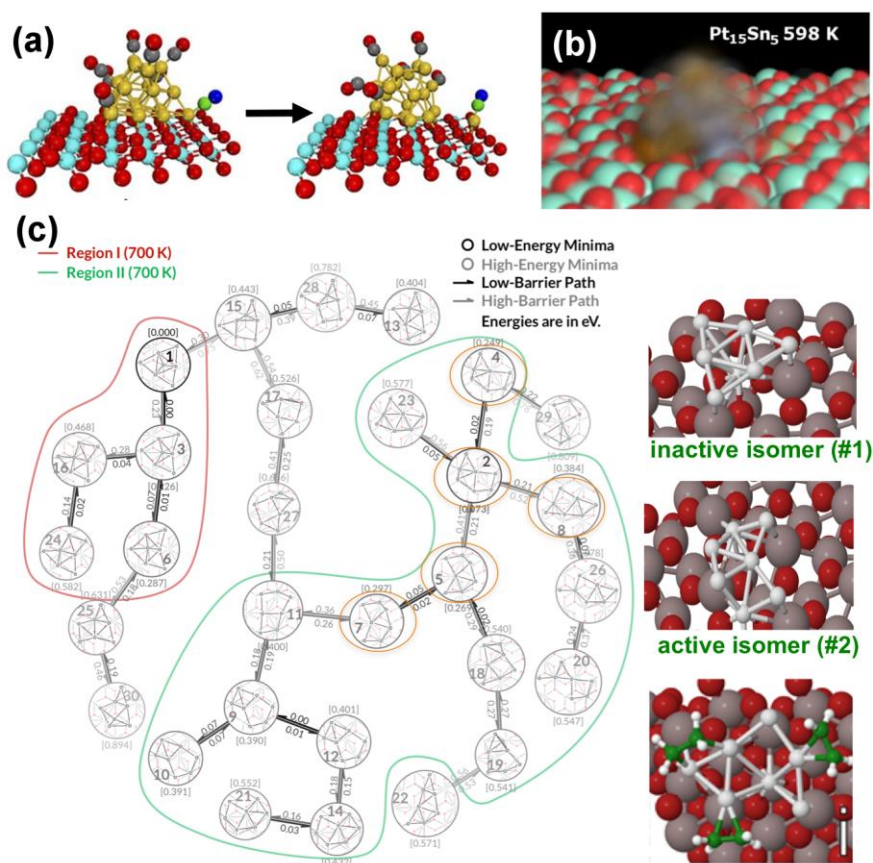


Figure 1. (a) Initial and final configuration from the MD trajectory of Au₂₀/CeO₂(111) showing edge Au dissociating with the CO adsorbate. (b) Time-elapsed rendering of DFT-MD trajectory of Pt₁₅Sn₅/ γ -Al₂O₃ at 598 K showing the dynamic behavior of the cluster. (c) 30 isomers of Pt₇ on α -Al₂O₃ accessible at 700 K, with minimal energy paths forming the isomerization graph. The two lowest-energy isomers are shown in the inset, with the ethylene adsorption further favoring isomer #2. Reprinted with permissions from Refs. 14, 17, 22. Copyright 2015 Nature Publishing Group. Copyright 2018 American Chemical Society. Copyright 2003 Wiley Online Library.

Although this Account extensively discusses catalytic clusters, structural fluxionality is characteristic of many amorphous interfaces, and some typical amorphous supports.²³ In addition, perfect crystalline surfaces can transform into amorphous through heat or electrochemical treatment,^{24,25} suggesting the key role of surface dynamics in reaction conditions. For example, hexagonal boron nitride (h-BN) came as a surprise as an earth-abundant catalyst for oxidative

dehydrogenation of propane (ODHP).²⁶ h-BN itself is inert, but in conditions of ODHP, its surface layer becomes partially oxidized amorphous BO_x .²⁷ Global optimization found many low-lying local minima of varying stoichiometries of BO_x on h-BN. Based on Boltzmann statistics, we constructed a “hot” phase diagram with respect to chemical potential of O and B, where every phase is an ensemble of many states populated at ODH temperature (Figure 2a,b).²⁸ With the temperature and partial pressures of reactants changing, the distribution of states changes accordingly, and the phase diagram become dynamic. We further found that some specific electronic states of B (involved in B-B bonds and having atomic charge between those in boron oxide and elemental boron) appear on the interface only at high T.²⁸ We now have preliminary indications that those rare sites are catalytic.

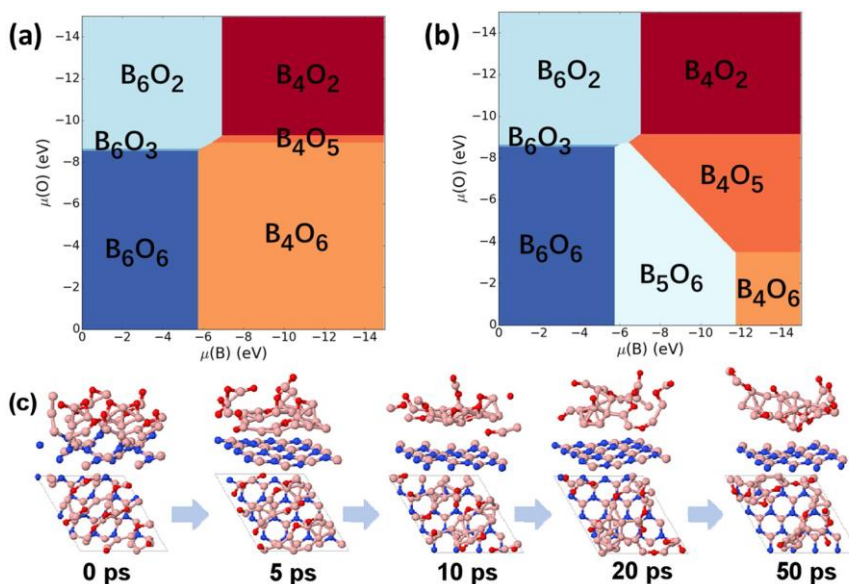


Figure 2. Phase diagram of the BO layer on h-BN at temperatures of ODHP as a function of $\mu(\text{B})$ and $\mu(\text{O})$, based on (a) GMs, (b) thermal ensembles of states of each stoichiometry. (c) Snapshot from a supporting MD simulation showing high fluxionality of the BO layer. Reprinted with permission from Ref. 28. Copyright 2019 American Chemical Society.

Another ample evidence for ensemble effects and the catalytic action of the less abundant but particularly active sites comes from the works of Scott and Peters.²⁹ Organometallic complexes grafted on amorphous surfaces exist in diverse coordination microenvironments, each of slightly different activity. The team developed elaborate approaches to identify the most active sites in this context, and also realized that catalysis is likely governed by minority species in the ensemble.³⁰

ENSEMBLES OF METASTABLE CATALYST STATES REDEFINE PROPERTIES OF THE INTERFACE

It is essential to capture the full vastness of the configurational space of fluxional interfaces, because each populated local minimum can contribute uniquely to the activity and selectivity, and the effect of some metastable members of the ensemble may override the effect of the GM. These minima also affect other properties such as the binding configurations and IR spectra of the bound reactants, intermediates, or poisons.^{12,22,31} Hence, it is essential that reactivity is studied also on the ensemble level. The contributions of coexisting structures to properties can be assessed statistically, and every property can then be described as ensemble-averages. At elevated temperatures, the contribution of GM becomes less significant, while the local minima gain influence. The denser the manifold of accessible states, the more the properties of ensembles are temperature-dependent. If we assume no kinetic hindrance to minima population and that the system can sufficiently equilibrate, we can apply simple Boltzmann statistics to calculate the probability of a minimum to be populated, P_i , as:

$$P_i = \frac{Z_{elec,i}Z_{trans,i}Z_{vib,i}Z_{rot,i}}{\sum_i Z_i} \approx \frac{g_i e^{-\beta E_i}}{\sum_i g_i e^{-\beta E_i}}$$

, where $Z_{elec,i}$, $Z_{trans,i}$, $Z_{vib,i}$, and $Z_{rot,i}$ are electronic, translational, vibrational, and rotational partition functions, respectively. Then, every minimum contributes to every property in proportionality to P_i . Hence, any observable property of a dynamic cluster-decorated interface would form a broadened distribution, and the maximum would shift as a function of T.

A very simple example is the vertical electron detachment energy (VDE) calculated for the ensembles of Pt clusters in the gas phase.¹² The global and local minima for these clusters were found using a Basin Hopping (BH) algorithm operating on a neural network (NN) trained to represent the DFT PES. Every obtained minimum was refined with DFT and duplicates were removed. The Boltzmann population probabilities were assigned to the minima. Entropy in the calculations was based on harmonic vibrational analysis and symmetry/degeneracy of the cluster forms, and the electronic entropy was ignored as the electronic excitations were beyond the thermal reach. The ensemble-average VDEs as a function of T are shown in Figure 3a, for Pt₉ and Pt₁₃. It is apparent that the average signal shifts strongly with T, and the trend is different for the two cluster sizes. Clearly, the VDE measured by *operando* photoelectron spectroscopy at

higher T should not correspond to the VDE of the GM, and the computed spectrum would not reproduce the experiment unless based on the appropriate ensemble of states.

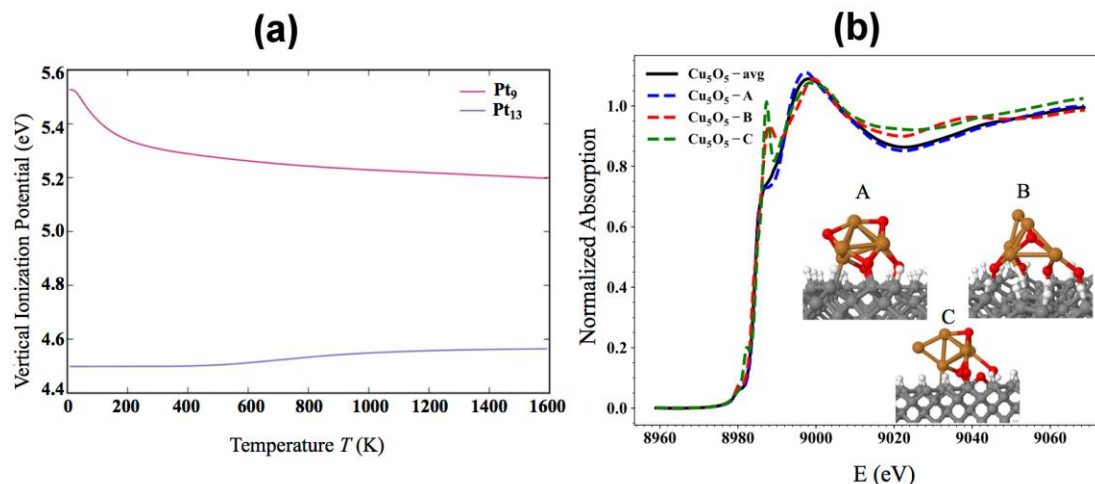


Figure 3. (a) Ensemble-average VDE for gas-phase Pt_9 and Pt_{13} as a function of temperature. (b) XANES of all thermally-accessible Cu_5O_5 /UNCD isomers (A, B, and C) obtained from global optimization. The ensemble-average spectrum was calculated at 535 K. Reprinted with permission from Ref. 12. Copyright 2016 American Chemical Society.

Ensemble effects can be electronic in origin. For example, recently, it has been shown that the conventional representation of static charge of a supported metal atom can be misleading.³² Instead, several well-defined charge states of Pt can coexist and dynamically interconvert in CO oxidation on $Pt/CeO_2(100)$.³²

XANES is often employed to characterize cluster catalysts, and we used our approach to elucidate how thermally-accessible non-GM isomers may contribute to the *operando* XANES spectra. Figure 3b shows calculated XANES spectra for UNCD-supported CuO clusters.³³ The shown isomers are populated at 535 K. When a specific selectivity in cyclohexane dehydrogenation was observed. We found that the XANES spectrum is distinct for every isomer, due to differences in the geometry and binding with the support. The average XANES is then an ensemble property (Figure 3b), but it closely resembles the spectrum of the GM isomer A. We see that the *operando* signal can be heavily dominated by the most abundant species, which may not be the most catalytically relevant, as we show next.

EVOLVING ENSEMBLES AFFECT MECHANISMS OF CATALYZED REACTIONS

When a multitude of catalyst isomers coexist in catalytic conditions, any one or few of them can be most effective in catalyzing the reaction, despite the potentially lower population in the ensemble. For example, we showed this in a joint theory-experiment study on ethylene dehydrogenation on size-selected Pt clusters on α -Al₂O₃ (Figure 4a). Pt₇ and Pt₈ exhibited markedly different activities, despite similar size, as well as the shapes and electronic structures of the GMs, as was measured by TPD/R. The size-dependent activity could only be explained when thermally-accessible ensembles of states were considered. Pt₇/Al₂O₃ easily accesses isomers that are flatter on the support and draw more electrons from it. At 700 K, we predict the isomers of that flatter type to constitute more than 30% of the population. These more negatively charged isomers more efficiently activate ethylene toward dehydrogenation, and are responsible for the avalanche of dehydrogenation events at higher temperature and ethylene coverage. At the same time, for Pt₈, GM is much more prevalent at all temperatures, while its higher energy isomers are less negatively charged, and thus, less efficient in ethylene activation. Hence, as a function of temperature, the behaviors of the Pt₇ and Pt₈ ensembles diverge, and Pt₇ becomes more active due to the recruitment of more active isomers into the population. Note that while the “every atom counts” phenomenon in cluster catalysis has been known for a while,³⁴ theory did not provide an explanation for it. We showed that (at least for dehydrogenation on Pt clusters) the number and nature of the metastable states in the catalyst ensemble recruited in reaction conditions can explain it. As another example, for reaction of dehydrogenation of methane on gas phase Pt₁₃, it was theoretically shown that the second lowest-energy isomer has a significantly smaller barrier than the global minimum.³⁵ Villa also showed that, depending on the isomer of supported PtSn, the barrier to O₂ binding is markedly different (Figure 4b).³⁶

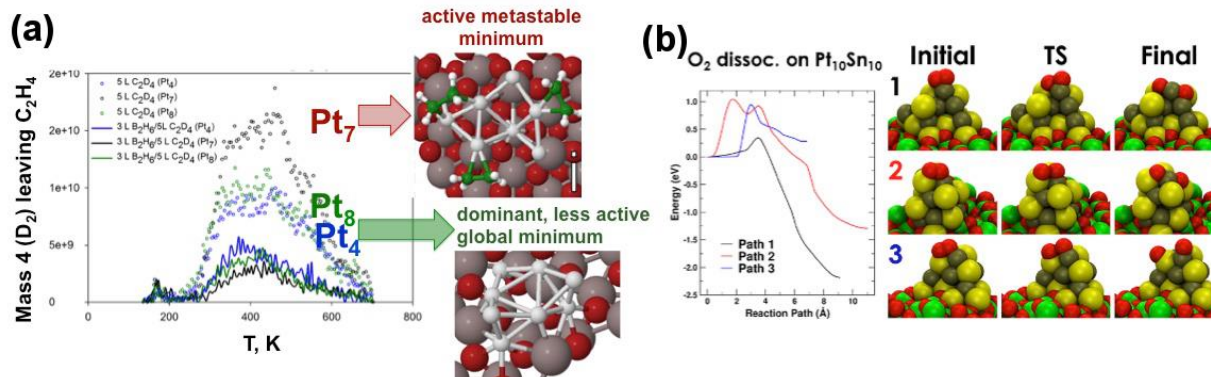


Figure 4. The effect of evolving ensembles of catalyst states on the catalytic mechanism: (a) Ethylene dehydrogenation on size-selected Pt_{4,7,8}/Al₂O₃ monitored via D₂-TPD shows Pt₇ having the highest activity; the effect was linked to the access of Pt₇ to higher-energy active isomers, in contrast to Pt₈. (b) Reaction paths for the dissociation of O₂ on Pt₁₀Sn₁₀ as a function of nanoparticle disorder show different behaviors, from exothermic to endothermic. Reprinted with permission from Refs. 22, 36. Copyright 2017 American Chemical Society. Copyright 2014 American Institute of Physics.

The message is quite disheartening for surface science characterization, which measures an ensemble-average signal and thus mostly reports on the most abundant sites and may miss the weak signal from the important minority sites. New *operando* techniques with below-angstrom resolution to observe the atomic structures and improved time resolution to capture the dynamics are required to investigate the true nature of the active site. At the same time, theory begins to play an ever more significant role in catalyst characterization, since it has access to the per-site and per-state information about the system.

Clusters may change not just shape but also number and types of adsorbates and effective chemical compositions in catalytic conditions. For example, partially oxidized clusters of Cu and Pd deposited on various supports appear to undergo partial reduction at elevated temperatures, as judged by *in situ* XANES.^{37,38} In collaboration with experiment, we showed that supported PdO clusters produce mainly benzene in ODH of cyclohexane, whereas CuO clusters produce cyclohexene with unprecedented rates.³⁹ For the selectivity on CuO/UNCD clusters to emerge in calculations, it is essential to capture their significant restructuring upon adsorbate binding, and partial reduction at reaction temperatures. Cu₅O₃/UNCD ensemble appears to be more prone to yielding cyclohexene than the fully oxidized Cu₅O₅.³⁷

Even when the catalyst itself is more stationary, and not prone to extreme dynamism, arrangements of adsorbed reactants, intermediates, and products can create diverse local

environments. Lateral interaction among different adsorbates can change the system state and lattice configuration. The same chemical reaction becomes subject to a wide range of microscopic events, leading to significant differences in activity, selectivity, and even reaction pathways, which makes surface catalysis a complex multi-adsorbate and multi-timescale reaction network. To address this, Xu and coworkers proposed a method combining explicit diffusion-only kinetic Monte Carlo (KMC) with implicit KMC in the phenomenological kinetics (PK) form to account for lateral interactions among adsorbates in catalysis.⁴⁰ For the model system of ammonia decomposition, lateral interaction between adsorbed N are found to significantly affect the shape of the volcano plot and its maximum position, suggesting the need to include lateral interactions into catalyst description and design. The number of adsorbates is another factor contributing to the state-diversity. The cluster expansion (CE) is a theoretical framework to treat multi-adsorbate systems, and Schneider and coworkers approximate ternary CE as a linear combination of three binary CEs by fitting to DFT database.⁴¹ The three-binary-to-single-ternary (TBST) approach shows good consistence with results by full ternary CE with the number of needed DFT data points greatly reduced.

Because the ensemble of the catalyst states changes as a function of the adsorbate(s), in the limit of full thermodynamic equilibration, the free energy of every point along the reaction profile of a catalyzed reaction can be governed by a different catalyst state (state being a dynamic collection of many structures). The free energy and all ensemble-average properties of every intermediate would be defined mainly by the most stable and hence dominant species in the current equilibrium ensemble. On the other hand, every TS would be dominated by the most active and possibly less populated catalyst states, whose contribution to the rate would be pro-rated by the probability of the species to exist.

One straightforward consequence of the different stationary points on the reaction profile being controlled by different catalyst states is the breaking down of scaling relations. The scaling relationships are linear correlation between thermodynamic properties of chemically-related species (including TSs) across different extended surfaces used in catalysis.⁴² These relations result in volcano plots, wherein the most active catalyst binds the adsorbate neither too strongly to not react, nor too weakly to not bind, and then it shows up at the top of the volcano. These powerful relations allow describing catalytic systems by simple descriptors such as coordination number, the position of d-band center, and partial charge.^{42,43} However, they also impose

fundamental limitations on the catalyst maximal performance. Therefore, there has been some efforts to find a way to overcome these constraints.^{44,45} We showed that metal clusters, because of fluxionality^{6,16,46} and shape sensitivity to even chemically-related adsorbates or their different numbers, do not follow the scaling relationships, almost as a rule.⁴⁷ In our considered example of oxygen reduction reaction (ORR) catalyzed by gaseous and graphene-supported Pt clusters, which is illustrated in Figure 5, the binding energies of molecular fragments, O, OH, and OOH, break the scaling relations because of the ever-changing cluster shapes.⁴⁷ Similar breakdown of scaling relations through different mechanisms has been reported in other catalytic reactions.^{45,48}

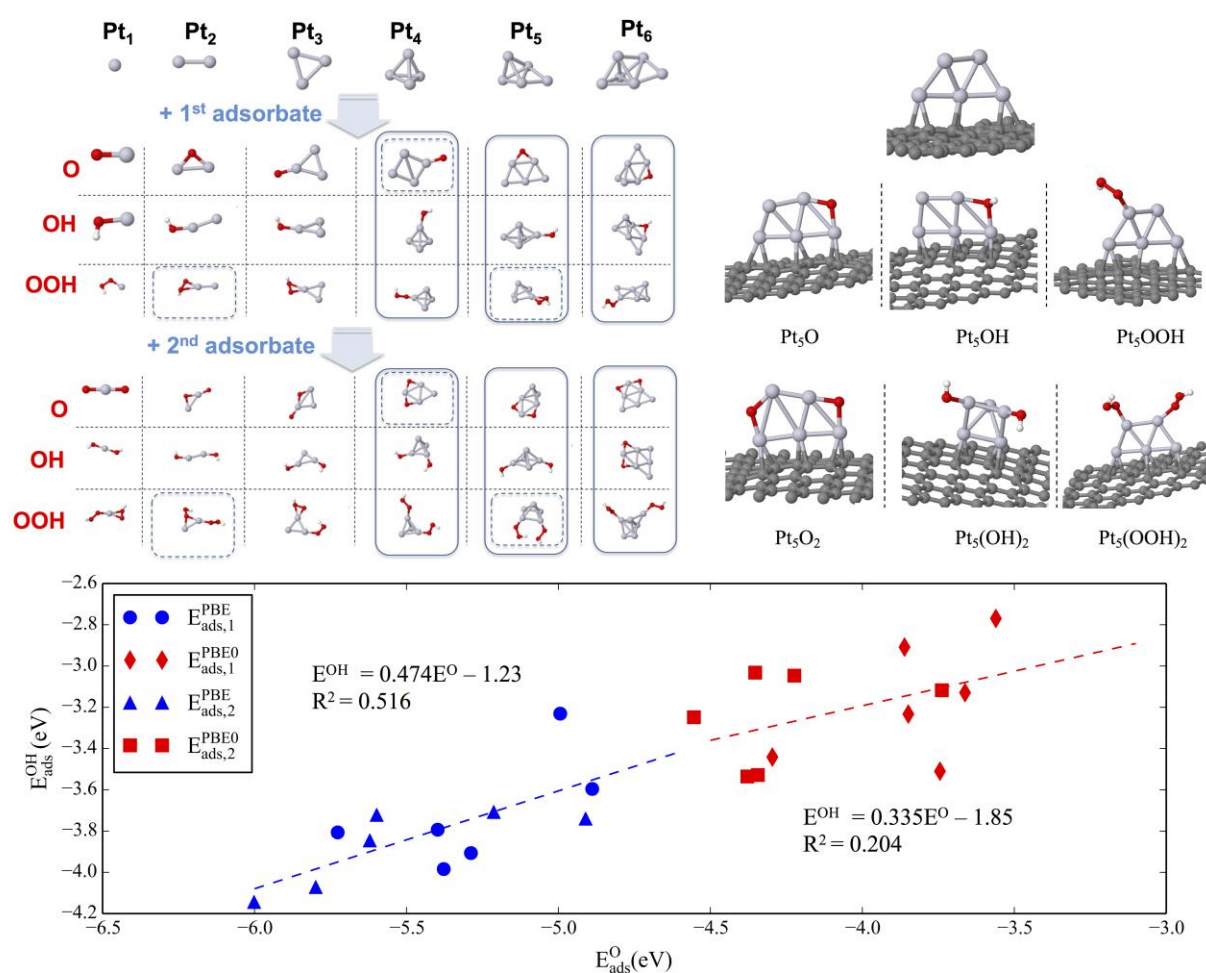


Figure 5. GM structures of gas-phase and graphene-supported Pt clusters with and without O, OH, and OOH adsorbates (TOP), and the poor correlation between OH and O adsorption energies using PBE and PBE0 functionals, illustrating the breakdown of scaling relations for fluxional clusters. Adapted with permission from Ref. 47. Copyright 2019 American Chemical Society.

Another consequence of the ensemble representation has to do with the whole notion of the reaction mechanism. The mechanism may involve catalyst isomerization as part of the reaction coordinate. There could be several states of the catalyst of competing level of activity, which would produce a swarm of different reaction mechanisms that collectively yield experimental observables, such as rates and product distributions. Hence, a single reaction profile on a dynamic interface is likely to be completely misleading, as we began demonstrating.³⁹

The ensemble representation leads to a different view on reaction kinetics. Firstly, conventional Arrhenius picture needs to be reconsidered. As T increases, chemically-distinct states of the catalyst get recruited, and so the Arrhenius plot should be non-linear. A proposed simple modification to the Arrhenius equation using ensemble-average representation is to write the apparent activation free energy in terms of activation energies of every state weighted by Boltzmann populations:

$$\Delta G_{ens}^{\ddagger} = \sum_{i=1}^n P_i \Delta G_i^{\ddagger}$$

Hence, the modified formula for the rate corresponding to the ensemble, r_{ens} , can be written as

$$r_{ens} \propto e^{-\Delta G_{ens}^{\ddagger}/RT} = e^{-\sum_{i=1}^n P_i \Delta G_i^{\ddagger}/RT}$$

, which can be further simplified as

$$r_{ens} \propto \prod_{i=1}^n (e^{-P_i \Delta G_i^{\ddagger}/RT}) = \prod_{i=1}^n (e^{-\Delta G_i^{\ddagger}/RT})^{P_i} = \prod_{i=1}^n r_i^{P_i}$$

The latter equation shows that the final rate of the reaction catalyzed by an ensemble of clusters is proportional to the product of rates of each individual cluster corrected by a Boltzmann factor.

ENSEMBLES OF CATALYST STATES AND DEACTIVATION

Catalysts deactivation in realistic catalysis conditions also needs a full ensemble-based description. Surface-supported nanoclusters deactivate mainly via sintering (merging to form larger particles with lower surface energies), and poisoning (e.g. coking). Sintering can happen via particle migration and coalescence, or Ostwald ripening that involves single atoms dissociating from a cluster, migrating on the support, and associating with other clusters while statistically favoring the larger ones. Ostwald ripening is the more prevalent mechanism for the

clusters that we studied. In simulations of Ostwald ripening, we considered Boltzmann ensembles of all cluster-isomers of every accessible composition and size up to 4-5 atoms.⁴⁹⁻⁵¹ Beyond that size, cluster energies were extrapolated based on the number and kind of atoms in the cluster. The cluster dissociation energies, and the PESs for the monomers on the support (as a grid) were pre-computed using DFT. The simulations then followed a Monte Carlo scheme, and involved cluster dissociation, association, atom migration, and atom evaporation and redeposition. One illustrating example is supported PtPd clusters. It was seen in the experiment that these clusters at the 50/50 Pt/Pd ratio sinter less than pure Pt or Pd clusters (Figure 5a).⁵²⁻⁵⁴ We simulated Ostwald ripening on rutile at different temperatures and starting Pt/Pd ratios (Figure 5b). We found that indeed, mixed PtPd clusters sinter less quickly.⁵⁰ The analysis showed no particular structural or electronic differences between clusters of different Pt/Pd ratios (Figure 5c). We eventually correlated the sintering inhibition with the configurational entropy, accessible to these clusters, which is the highest at the 50/50 ratio. In other words, within every accessible geometry, these clusters have more ways to arrange the Pt and Pd atoms, thereby lowering the free energy, and that is yet again an ensemble property that cannot be captured at the level of a single structure.

We found a striking impact of the metastable states on the poisoning of cluster catalysts. We predicted that alloying supported Pt clusters with B should help mitigating both coking (by stopping alkane dehydrogenation at the olefin), and sintering.⁵⁵ This was experimentally confirmed: size-selected Pt clusters on α -Al₂O₃ were borated post-deposition by adding diborane and heating.³¹ These model catalysts showed significantly tempered ethylene dehydrogenation activity, and no deactivation after several catalytic cycles, in stark contrast to pure Pt counterparts (Figure 6d,e).³¹ Boron does this by forming strong B-O bonds between the cluster and the surface, cutting down the net charge transfer from support to clusters from 1.2~1.4 e to 0.3~1.0 e, thus reducing the binding energies of ethylene and products of deeper dehydrogenation including carbon itself (Figure 6f). Furthermore, theory showed that the higher-energy cluster isomers in the PtB ensemble are increasingly worse at activating ethylene and binding carbon. So as T increases, PtB/ α -Al₂O₃ coke less, whereas pure Pt/ α -Al₂O₃ clusters coke more. In fact, at low T (in the limit of GM being the only populated species), Pt₇B/alumina should coke more than Pt₇/alumina, in disagreement with the experiment (Figure 5f). We clearly needed an ensemble in order to capture the experimentally observed phenomenon.

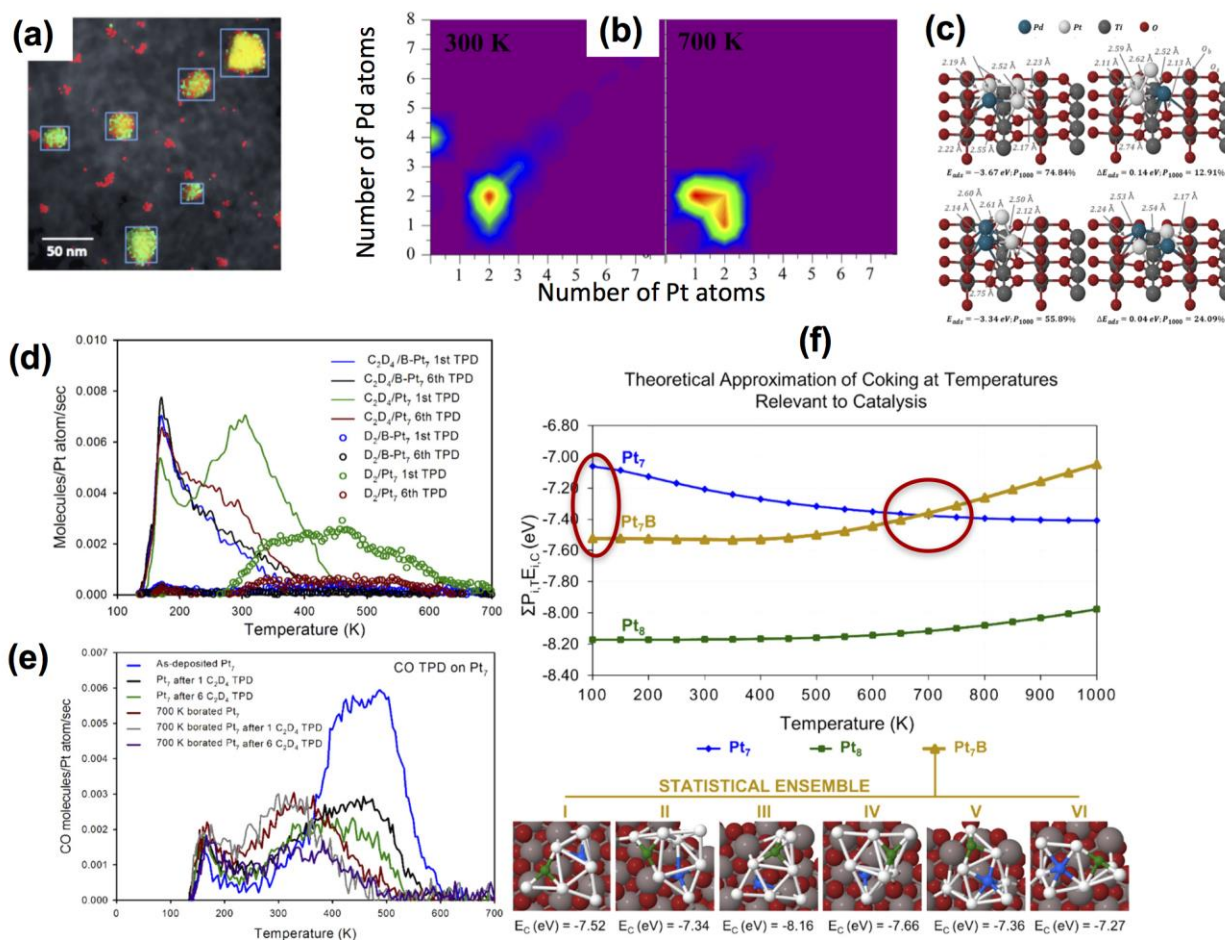


Figure 6. (a) Experimental STEM shows mixed PtPd particles to resist sintering more than pure Pt or Pd particles. (b) Monte Carlo simulations of Ostwald ripening based on ensembles of cluster isomers for every size and stoichiometry show the highest survival of mixed PtPd clusters at 300K and 700K, in agreement with experiment. (c) The two lowest-energy isomers for tetraatomic PtPd clusters, showing no apparent differences. The stability against sintering was explained by increased configurational entropy. (d) Experimental C_2H_4 TPD on $Pt_7/\alpha-Al_2O_3$ and $Pt_7B/\alpha-Al_2O_3$: after the 1st-5th ethylene dehydrogenation, ethylene binding sites go away on pure Pt_7 , but stay intact on Pt_7B , as seen from the 6th TPD. Lowering of the ethylene binding energy upon cluster boration is also seen from the position of the TPD peak. (e) CO TPD on Pt_7/Al_2O_3 and $Pt_7B/\alpha-Al_2O_3$ after the same 1st-6th ethylene TPD, showing the disappearance of the Pt sites (due to coking and sintering) for pure Pt_7 , and preservation of the Pt sites for Pt_7B . (f) Theoretical assessment of coking on Pt_7/Al_2O_3 and $Pt_7B/\alpha-Al_2O_3$: the low-T ensembles suggest higher coking propensity for Pt_7 , but at rising T the ensembles show opposing trends, with Pt_7 coking more and Pt_7B coking less, in agreement with the experiment, due to the enrichment of the ensemble with the isomers having lower affinity to C. Adapted or reprinted with permission from Refs. 50, 54, 31. Copyright 2013 Wiley Online Library. Copyright 2014 and 2017 American Chemical Society.

All our subsequent works that involved alloying Pt for selectivity control have involved ensemble representation. One well-known dopant for Pt in the bulk and in nanoparticle is Sn, known to reduce coking. We showed in a joint theory-experiment study that the effect of Sn is robust also in small clusters, and furthermore, the anti-coking mechanism is different from that induced by boration.^{56,57} In contrast to PtB, PtSn clusters supported on amorphous silica and α -alumina have the unchanged or even increased affinity for ethylene from that of pure Pt clusters. The selectivity arises from the Sn and Pt mixing within the cluster, and forming strong covalent bonds, quenching all unpaired spins, and eliminating the adjacent Pt sites, both of which are required for ethylene activation. Hence, ethylene desorbs. The effect is persistent across all thermally accessible isomers in the catalyst ensemble. We also identified Si and Ge as two highly promising dopants, which should surpass the effects of both B and Sn on the selectivity and coking resistance of Pt clusters.^{58,59} The mechanism for Si and Ge is electronic spin-based, similar to that of Sn. Again, the entire ensemble of states was simulated and analyzed to confirm that no accessible isomer could break the desired trend.

COMPUTATIONAL AND EXPERIMENTAL METHODS OF CHARACTERIZATION OF DYNAMIC CATALYSTS – CURRENT STATUS AND REQUIRED UPDATES

Accessing the ensembles of states on dynamic catalytic interfaces requires computational methods to address the problem at several different levels. To locate the GM and local minima on the PES, global optimization techniques are needed. The most popular ones include Genetic Algorithm,^{60–63} Particle Swarm Optimization,^{64,65} Basin Hopping.^{66–68} Many of these techniques have been developed in our laboratory,^{12,69} including the very first Genetic Algorithm for clusters.⁶³ One possible advance needed here is to increase the efficiency of these algorithms in finding the local minima, since by definition they target the GM discovery, and do not necessarily the characterization of the full PES. Sampling in trained potentials is also welcome, since the computational cost associated with global optimization is very high.

Another complication is finding the lowest-energy pathways for catalyst isomerization, especially in presence of adsorbates and/or during a reaction step. We need to identify catalyst structures that are likely to be connected by a direct isomerization pathway. Geometric similarity may be used as a criterion.⁶ Next, matching the atoms from one structure to another can be

highly non-trivial. It is not unique, and the associated computed barriers will be different.⁶ The multitude of adsorbate configurations drastically increases the number of possible pathways. Certainly, such studies are possible but extremely costly. One way forward could be fitting a simplified potential for the entire system (surface, cluster, adsorbates), including the regions of TSs, to enable quick qualitative estimates of the barriers, and the kinetic accessibility of all isomers in the network. We are working on this development.

The global optimization can be performed on DFT, *ab initio*, empirical, and semiempirical PES. Force field and NN fitting of an approximate PES can be incorporated to further reduce the computational cost.^{12,69} The accuracy of these methods goes against the efficiency of the sampling, and so, more efficient electronic structure methods are highly desired. Currently DFT offers a balance between accuracy and computational cost and has been applied to many systems. However, due to its lack of cancellation of Coulomb self-interaction and single-reference nature, DFT cannot yield meaningful results when treating strongly correlated systems such as late transition metal and rare earth oxides.⁷⁰⁻⁷² DFT+U provides a way to treat such systems with DFT-level cost through addition of Hubbard U term to a set of atomic-like orbitals.⁷³ However, the U is often fitted to a chosen property, via linear response approach, or to a solution obtained with another imperfect Hamiltonian, and may depend on the chemical composition or the pseudopotentials employed. High-level electronic structure methods including Green's function,⁷⁴ and screened Coulomb potential⁷⁵ have been developed to treat strongly correlated systems. However, for catalytic interfaces involving large supercell and coverage, those are unaffordable. Hybrid-DFT with stochastic exchange may offer a practical way to handle large systems with improved accuracy and efficiency compared to DFT, but they are still single reference.⁷⁶ Dispersion interactions can significantly contribute to nearly all covalent and noncovalent interactions, including H-bonds, metal coordination, adsorbate configuration, and reaction energetics.⁷⁷ Efforts have been made to provide affordable method for the accurate evaluation of dispersion. Domain-based local pair-natural orbital approximation greatly accelerates coupled cluster calculations, reducing 7-order scaling with system size to near-linear.⁷⁸ Dispersion correction methods developed by Grimme focus on improving the thermodynamic results at little additional computational cost.⁷⁹

On the experimental side, the *operando* spectroscopy is very promising for catalyst characterization.^{80,81} Measurements of activity and selectivity *in situ* becomes possible. In

agreement with the recent theoretical investigations, it has been shown by *operando* studies that the dynamic structural transformations of catalyst in reaction conditions can strongly affect the catalyst performance.^{38,82,83} In order to develop catalysts with enhanced performance the correct determination of reaction kinetics of the system is of great importance.^{82,84-86} To address critical mechanistic questions, XAS has become an important tool. XAS has the capability to resolve the electronic structural features of operating catalysts. Furthermore, the combination of small-angle X-ray scattering (SAXS) and XANES spectroscopy *in situ* studies probe different length-scales, and can be combined with simulations and machine learning.⁸⁷⁻⁸⁹ In samples where the signal of the cluster may be overwhelmed by bulk contribution, more surface-sensitive techniques such as *in situ* IR and surface enhanced Raman spectroscopy (SERS) are needed. These *operando* techniques would benefit the field of catalysis if they would gain the ability to detect important minority species at the catalytic interface, rather than giving an ensemble-average information. Until this is accessible, the role of theory remains really singular.

CONCLUSIONS AND OUTLOOK

To summarize, in the limit of full thermodynamic equilibration of a highly-dynamic interface along the entire reaction profile, the properties and energies of every intermediate and every TS are dominated by a different state or states of the catalyst. Intermediates would be mainly defined by the most thermodynamically stable and hence dominating species in the ensemble. TSs would be defined by less prevalent but more active states of the catalyst. The ensemble would generally change as a function of the bound intermediate (including changes in structure, and adsorbates nature and number). From this perspective, basing all intermediate geometries on the starting geometry of the interface could make the constructed reaction profile problematic, and it is critical to perform the separate sampling in all intermediates of a reaction. Each well on the reaction profile should be characterized with an ensemble of metastable state that is independent from the ensemble of the previous well. Catalyst isomerization steps thus should be part of the catalytic process. For the less stable but more active species to be the active sites, the catalyst needs to be able to reach those species through isomerization. In addition, the reaction profile might be not one, but many, all with slightly different mechanisms and rates, and operating as a swarm. This picture is much more complicated than what can be found in majority

of the catalysis literature, where the catalyst is not undergoing any major changes beyond relaxation, and there is only one reaction profile.

We showed that all major properties of supported cluster catalysts, including activity, selectivity, stability against sintering and poisoning, and *operando* spectra are affected by the presence, or even dominance of the metastable states. Some intriguing results of this include routine breaking of scaling relations, and a non-Arrhenius behavior.

One open question is that of the relative time-scales. Do the catalytic systems really have the time to undergo this constant reorganization that would allow them to operate on the minimum free energy reaction path, as an equilibrium ensemble? For example, in enzymatic catalysis, the full equilibration all along the free energy surface is standardly assumed and treated through extensive sampling combined with free energy perturbation (FEP).^{90,91} Or does the reaction instead proceed along a series of metastable states, keeping some memory of the initial state of the catalyst that it was when the reagent bound to it? This picture would be closer to the modeling approaches that dominates the catalysis literature now, but in our studies, we've seen that such modeling leads to selectivities and cluster size- and composition-dependencies of activity that do not agree with the experiment. The partial equilibration of the catalyst along the reaction profile, where the current ensembles are neither fully equilibrated, nor correspond to the GM of the initial state, would be truly difficult for theory.

It is also interesting to know the degree to which the importance of ensembles changes as we consider larger catalytic particles. While we do not have the full answer for this question, it can be reasonably hypothesized that larger particles would retain the structure in the bulk but undergo dynamic surface reconstruction and exhibit varying coverages around different active site, forming ensembles in these ways.

Another key question is that of the possible dynamic coupling between the catalyzed reaction and catalyst reorganization. Are there reaction steps that involve not just the movement of light reacting atoms but also catalyst isomerization? While we do not yet have a complete and general answer, we have made several initial observations. For adsorbate-free supported Pt clusters, the isomerization is quite fast, but not faster than the catalyzed reactions of dehydrogenation. The reaction dynamics is then decoupled from the cluster dynamics: facile cluster isomerization can be induced by a reaction step, but it is delayed and occurs as an independent step. The picture might change, when the reacting atoms and cluster atoms are

closer in masses. Similarly, can the binding of a reagent, which can have a large kinetic energy and be vibrationally excited at high T, trigger catalyst isomerization? This coupling could in fact facilitate the catalyst equilibration toward the most stable ensemble with the bound reagents. We began investigating this aspect of cluster catalysis through dynamics simulations, paying particular attention to kinetic energy exchange between the catalyst and the reagent. So far, the results are again system dependent. Also, reagent scattering, non-reactive adsorption, and reactive adsorption all affect the catalyst dynamics differently.

We hope to construct a unified theory of dynamics in catalysis and have made out first strides in this direction. We see that some catalysis rules are routinely broken on such dynamic interfaces. We develop tools that we need to access the nature and mechanisms of such interfaces. However, we still have a long way to go to a truly generalized theory, as the emerging picture is breathtakingly complex.

Acknowledgements

The work that gave the basis for this Account was supported over the years by the NSF CAREER Award CHE-1351968, ACS Petroleum Research Fund (51052-DNI6), Air Force Office of Scientific Research, AFOSR (BRI FA9550-12-1-0481, FA9550-16-1-0141, FA9550-19-1-0261), and most recently DOE-BES (DE-SC0019152). CPU resources at the DOD (Department of Defense) High Performance Computing Modernization Program [the U.S. Air Force Research Laboratory DoD Supercomputing Resource Center (AFRL DSRC), the U.S. Army Engineer Research and Development Center (ERDC), and the Navy Supercomputing Resource Center (Navy DSRC)], National Energy Research Scientific Computing Center (NERSC), a U.S. Department of Energy Office of Science User Facility operated under Contract No. DE-AC02-05CH11231, and Extreme Science and Engineering Discovery Environment's (XSEDE). We also thank experimental collaborators: Scott Anderson, Stefan Vajda, and Ive Hermans.

Biographical Information

Biographical Information must be submitted for each author and include date and place of birth, universities attended and degrees obtained, principal professional

posts held, present title, a line or two about other major research interests, and anything else professionally relevant that is of special interest.

Anastassia N. Alexandrova

Anastassia Alexandrova was born in USSR in 1978. She obtained a B.S./M.S. Diploma with highest honors, from Saratov University, Russia, her Ph.D. in theoretical physical chemistry from Utah State University, and she was then a Postdoctoral Associate and an American Cancer Society Postdoctoral Fellow at Yale University. Anastassia joined the faculty of UCLA in 2010, where she is now a Professor and the Vice Chair for Undergraduate Education. The focus of her laboratory is computational and theoretical design and multi-scale description of functional materials: catalytic interfaces, ultra-hard alloys, quantum materials, photo-active quantum dots, artificial metalloenzymes, and molecular qubits. She is a recipient of numerous awards, including NSF CAREER Award, Alfred Sloan Fellowship 2013, DARPA Young Faculty Award 2011, ACS WCC Rising Star Award 2016, as well as UCLA's Distinguished Teaching Award 2019.

Zisheng Zhang

Zisheng Zhang was born in Wuhan (PRC) in 1997. He received his B.Sc. in Chemistry from South University of Science and Technology of China in 2019, supervised by Prof. Jun Li. He was a UCLA-CSST fellow in 2018 summer and is currently a Ph.D. student at UCLA under the supervision of Prof. Anastassia Alexandrova. His current research interest includes modeling supported clusters and amorphous surfaces under catalytic conditions.

Borna Zandkarimi

Borna Zandkarimi was born in Tehran in 1992. He received a B.Sc. in Chemistry and a B.Sc. in Chemical Engineering in 2015 from Sharif University of Technology in Tehran. After that, he obtained his M.Sc. in Chemistry under the supervision of Prof. Jason Goodpaster from University of Minnesota, Twin Cities. He is currently a Ph.D. candidate at UCLA doing research in Prof. Anastassia Alexandrova's group. His current research interest includes modeling catalytic systems using modern electronic structure methods.

References

- (1) Dingerdissen, U.; Martin, A.; Herein, D.; Wernicke, H. J. In Handbook of Heterogeneous Catalysis; Ertl G., Knözinger H., Schüth F.; Weitkamp J., Eds.; Wiley - VCH Verlag GmbH & Co. KGaA: Weinheim, Germany, 2008; pp 37-56.
- (2) Wang, Y.; Védrine, J. C. The Past, Present and Future of Heterogeneous Catalysis. *Catal. Today* **2012**, *189*, 2–27.
- (3) Friend, C. M.; Xu, B. Heterogeneous Catalysis: A Central Science for a Sustainable Future. *Acc. Chem. Res.* **2017**, *50*, 517–521.
- (4) Holena, M.; Baerns, M. In Handbook of Heterogeneous Catalysis; Ertl G., Knözinger H., Schüth F.; Weitkamp J., Eds.; Wiley - VCH Verlag GmbH & Co. KGaA: Weinheim, Germany 2008; pp 66-81.
- (5) Jimenez-Izal, E.; Alexandrova, A. N. Computational Design of Clusters for Catalysis. *Annu. Rev. Phys. Chem.* **2018**, *69*, 377–400.
- (6) Zhai, H.; Alexandrova, A. N. Fluxionality of Catalytic Clusters: When It Matters and How to Address It. *ACS Catal.* **2017**, *7*, 1905–1911.
- (7) Hook, A.; Massa, J. D.; Celik, F. E. Effect of Tin Coverage on Selectivity for Ethane Dehydrogenation over Platinum–Tin Alloys. *J. Phys. Chem. C* **2016**, *120*, 27307–27318.
- (8) Ghosh, P.; Farnesi Camellone, M.; Fabris, S. Fluxionality of Au Clusters at Ceria Surfaces during CO Oxidation: Relationships among Reactivity, Size, Cohesion, and Surface Defects from DFT Simulations. *J. Phys. Chem. Lett.* **2013**, *4*, 2256–2263.

- (9) Song, S.; Zhou, J.; Su, X.; Wang, Y.; Li, J.; Zhang, L.; Xiao, G.; Guan, C.; Liu, R.; Chen, S. Operando X-Ray Spectroscopic Tracking of Self-Reconstruction for Anchored Nanoparticles as High-Performance Electrocatalysts towards Oxygen Evolution. *Energy Environ. Sci.* **2018**, *11*, 2945–2953.
- (10) Duan, M.; Yu, J.; Meng, J.; Zhu, B.; Wang, Y.; Gao, Y. Reconstruction of Supported Metal Nanoparticles in Reaction Conditions. *Angew. Chemie* **2018**, *130*, 6574–6579.
- (11) Tao, F.; Grass, M. E.; Zhang, Y.; Butcher, D. R.; Renzas, J. R.; Liu, Z.; Chung, J. Y.; Mun, B. S.; Salmeron, M.; Somorjai, G. A. Reaction-Driven Restructuring of Rh-Pd and Pt-Pd Core-Shell Nanoparticles. *Science (80-.)*. **2008**, *322*, 932–934.
- (12) Zhai, H.; Alexandrova, A. N. Ensemble-Average Representation of Pt Clusters in Conditions of Catalysis Accessed through GPU Accelerated Deep Neural Network Fitting Global Optimization. *J. Chem. Theory Comput.* **2016**, *12*, 6213–6226.
- (13) Wang, Y.-G.; Yoon, Y.; Glezakou, V.-A.; Li, J.; Rousseau, R. The Role of Reducible Oxide–Metal Cluster Charge Transfer in Catalytic Processes: New Insights on the Catalytic Mechanism of CO Oxidation on Au/TiO₂ from Ab Initio Molecular Dynamics. *J. Am. Chem. Soc.* **2013**, *135*, 10673–10683.
- (14) Wang, Y.-G.; Mei, D.; Glezakou, V.-A.; Li, J.; Rousseau, R. Dynamic Formation of Single-Atom Catalytic Active Sites on Ceria-Supported Gold Nanoparticles. *Nat. Commun.* **2015**, *6*, 6511.
- (15) Blomberg, S.; Hoffmann, M. J.; Gustafson, J.; Martin, N. M.; Fernandes, V. R.; Borg, A.; Liu, Z.; Chang, R.; Matera, S.; Reuter, K.; Lundgren, E. In Situ X-Ray Photoelectron Spectroscopy of Model Catalysts: At the Edge of the Gap. *Phys. Rev. Lett.* **2013**, *110*, 117601.
- (16) Häkkinen, H.; Abbet, S.; Sanchez, A.; Heiz, U.; Landman, U. Structural, Electronic, and Impurity-Doping Effects in Nanoscale Chemistry: Supported Gold Nanoclusters. *Angew. Chemie - Int. Ed.* **2003**, *42*, 1297–1300.
- (17) Zhai, H.; Alexandrova, A. N. Local Fluxionality of Surface-Deposited Cluster Catalysts: The Case of Pt₇ on Al₂O₃. *J. Phys. Chem. Lett.* **2018**, *9*, 1696–1702.
- (18) Xing, X.; Yoon, B.; Landman, U.; Parks, J. H. Structural Evolution of Au Nanoclusters: From Planar to Cage to Tubular Motifs. *Phys. Rev. B* **2006**, *74*, 165423.

- (19) Suzuki, A.; Inada, Y.; Yamaguchi, A.; Chihara, T.; Yuasa, M.; Nomura, M.; Iwasawa, Y. Time Scale and Elementary Steps of CO-Induced Disintegration of Surface Rhodium Clusters. *Angew. Chemie Int. Ed.* **2003**, *42*, 4795–4799.
- (20) Imaoka, T.; Toyonaga, T.; Morita, M.; Haruta, N.; Yamamoto, K. Isomerizations of a Pt₄ Cluster Revealed by Spatiotemporal Microscopic Analysis. *Chem. Commun.* **2019**, *55*, 4753–4756.
- (21) Vila, F. D.; Rehr, J. J.; Kelly, S. D.; Bare, S. R. Operando Effects on the Structure and Dynamics of Pt_nSn_m/γ-Al₂O₃ from Ab Initio Molecular Dynamics and X-Ray Absorption Spectra. *J. Phys. Chem. C* **2013**, *117*, 12446–12457.
- (22) Baxter, E. T.; Ha, M.-A.; Cass, A. C.; Alexandrova, A. N.; Anderson, S. L. Ethylene Dehydrogenation on Pt_{4,7,8} Clusters on Al₂O₃: Strong Cluster Size Dependence Linked to Preferred Catalyst Morphologies. *ACS Catal.* **2017**, *7*, 3322–3335.
- (23) Ertl G. In *Advances in Catalysis: Impact of Surface Science on Catalysis*; Gates, B. C.; Knoezinger, H., Eds.; Academic Press: San Diego, CA, 2000; Vol. 45, pp 1–69.
- (24) Hutchings, G. J.; Desmartin-Chomel, A.; Olier, R.; Volta, J.-C. Role of the Product in the Transformation of a Catalyst to Its Active State. *Nature* **1994**, *368*, 41.
- (25) Bergmann, A.; Martinez-Moreno, E.; Teschner, D.; Chernev, P.; Gliach, M.; De Araújo, J. F.; Reier, T.; Dau, H.; Strasser, P. Reversible Amorphization and the Catalytically Active State of Crystalline Co₃O₄ during Oxygen Evolution. *Nat. Commun.* **2015**, *6*, 8625.
- (26) Grant, J. T.; Carrero, C. A.; Goeltl, F.; Venegas, J.; Mueller, P.; Burt, S. P.; Specht, S. E.; McDermott, W. P.; Chiericato, A.; Hermans, I. Selective Oxidative Dehydrogenation of Propane to Propene Using Boron Nitride Catalysts. *Science (80-.)*. **2016**, *354*, 1570–1573.
- (27) Love, A. M.; Thomas, B.; Specht, S. E.; Hanrahan, M. P.; Venegas, J. M.; Burt, S. P.; Grant, J. T.; Cendejas, M. C.; McDermott, W. P.; Rossini, A. J. Probing the Transformation of Boron Nitride Catalysts under Oxidative Dehydrogenation Conditions. *J. Am. Chem. Soc.* **2018**, *141*, 182–190.
- (28) Zhang, Z.; Jimenez-Izal, E.; Hermans, I.; Alexandrova, A. N. Dynamic Phase Diagram of Catalytic Surface of Hexagonal Boron Nitride under Conditions of Oxidative Dehydrogenation of Propane. *J. Phys. Chem. Lett.* **2019**, *10*, 20–25.
- (29) Peters, B.; Scott, S. L. Single Atom Catalysts on Amorphous Supports: A Quenched Disorder Perspective. *J. Chem. Phys.* **2015**, *142*, 104708.

- (30) Goldsmith, B. R.; Peters, B.; Johnson, J. K.; Gates, B. C.; Scott, S. L. Beyond Ordered Materials: Understanding Catalytic Sites on Amorphous Solids. *ACS Catal.* **2017**, *7*, 7543–7557.
- (31) Ha, M. A.; Baxter, E. T.; Cass, A. C.; Anderson, S. L.; Alexandrova, A. N. Boron Switch for Selectivity of Catalytic Dehydrogenation on Size-Selected Pt Clusters on Al₂O₃. *J. Am. Chem. Soc.* **2017**, *139*, 11568–11575.
- (32) Daelman, N.; Capdevila-Cortada, M.; López, N. Dynamic Charge and Oxidation State of Pt/CeO₂ Single-Atom Catalysts. *Nat. Mat* **2019**.
- (33) Zandkarimi, B.; Sun, G.; Halder, A.; Vajda, S.; Sautet, P.; Alexandrova, A. N. Interpreting Operando XANES of Surface-Supported Subnanometer Clusters: When Fluxionality, Oxidation State, and Size Effect Fight. *J. Phys. Chem.* **2019**, *submitted*.
- (34) Heiz, U.; Sanchez, A.; Abbet, S.; Schneider, W.-D. Catalytic Oxidation of Carbon Monoxide on Monodispersed Platinum Clusters: Each Atom Counts. *J. Am. Chem. Soc.* **1999**, *121*, 3214–3217.
- (35) Sun, G.; Sautet, P. Metastable Structures in Cluster Catalysis from First-Principles: Structural Ensemble in Reaction Conditions and Metastability Triggered Reactivity. *J. Am. Chem. Soc.* **2018**, *140*, 2812–2820.
- (36) Rehr, J. J.; Vila, F. D. Dynamic Structural Disorder in Supported Nanoscale Catalysts. *J. Chem. Phys.* **2014**, *140*, 134701.
- (37) Halder, A.; Ha, M.-A.; Zhai, H.; Yang, B.; Pellin, M. J.; Seifert, S.; Alexandrova, A. N.; Vajda, S. Oxidative Dehydrogenation of Cyclohexane by Cu vs Pd Clusters: Selectivity Control by Specific Cluster Dynamics. *ChemCatChem* **2019**, *n/a*.
- (38) Jung, U.; Elsen, A.; Li, Y.; Smith, J. G.; Small, M. W.; Stach, E. A.; Frenkel, A. I.; Nuzzo, R. G. Comparative in Operando Studies in Heterogeneous Catalysis: Atomic and Electronic Structural Features in the Hydrogenation of Ethylene over Supported Pd and Pt Catalysts. *ACS Catal.* **2015**, *5*, 1539–1551.
- (39) Halder, A.; Ha, M.-A.; Zhai, H.; Alexandrova, A. N.; Vajda, S. Dynamics Defines Selectivity of Subnanometer Cluster Catalysts: Oxidative Dehydrogenation of Cyclohexane on Pd versus Cu Clusters. *ChemCatChem* **2019**, *in press*.

- (40) Chen, Z.; Wang, H.; Su, N. Q.; Duan, S.; Shen, T.; Xu, X. Beyond Mean-Field Microkinetics: Toward Accurate and Efficient Theoretical Modeling in Heterogeneous Catalysis. *ACS Catal.* **2018**, *8*, 5816–5826.
- (41) Bajpai, A.; Frey, K.; Schneider, W. F. Binary Approach to Ternary Cluster Expansions: NO–O–Vacancy System on Pt (111). *J. Phys. Chem. C* **2017**, *121*, 7344–7354.
- (42) Greeley, J. Theoretical Heterogeneous Catalysis: Scaling Relationships and Computational Catalyst Design. *Annu. Rev. Chem. Biomol. Eng.* **2016**, *7*, 605–635.
- (43) Calle-Vallejo, F.; Loffreda, D.; Koper, M. T. M.; Sautet, P. Introducing Structural Sensitivity into Adsorption-Energy Scaling Relations by Means of Coordination Numbers. *Nat. Chem.* **2015**, *7*, 403–410.
- (44) Khorshidi, A.; Violet, J.; Hashemi, J.; Peterson, A. A. How Strain Can Break the Scaling Relations of Catalysis. *Nat. Catal.* **2018**, *1*, 263–268.
- (45) Calle-Vallejo, F.; Krabbe, A.; García-Lastra, J. M. How Covalence Breaks Adsorption-Energy Scaling Relations and Solvation Restores Them. *Chem. Sci.* **2016**, *8*, 124–130.
- (46) Gao, M.; Lyalin, A.; Takagi, M.; Maeda, S.; Taketsugu, T. Reactivity of Gold Clusters in the Regime of Structural Fluxionality. *J. Phys. Chem. C* **2015**, *119*, 11120–11130.
- (47) Zandkarimi, B.; Alexandrova, A. N. Dynamics of Subnanometer Pt Clusters Can Break the Scaling Relationships in Catalysis. *J. Phys. Chem. Lett.* **2019**, *10*, 460–467.
- (48) Kauppinen, M. M.; Korpelin, V.; Verma, A. M.; Melander, M. M.; Honkala, K. Escaping Scaling Relationships for Water Dissociation at Interfacial Sites of Zirconia-Supported Rh and Pt Clusters. *J. Chem. Phys.* **2019**, *151*, 164302.
- (49) Zhang, J.; Alexandrova, A. N. Structure, Stability, and Mobility of Small Pd Clusters on the Stoichiometric and Defective TiO₂ (110) Surfaces. *J. Chem. Phys.* **2011**, *135*, 174702.
- (50) Ha, M. A.; Dadras, J.; Alexandrova, A. Rutile-Deposited Pt-Pd Clusters: A Hypothesis Regarding the Stability at 50/50 Ratio. *ACS Catal.* **2014**, *4*, 3570–3580.
- (51) Dadras, J.; Shen, L.; Alexandrova, A. Pt-Zn Clusters on Stoichiometric MgO(100) and TiO₂(110): Dramatically Different Sintering Behavior. *J. Phys. Chem. C* **2015**, *119*, 6047–6055.
- (52) Ward, M. R.; Hyde, T.; Boyes, E. D.; Gai, P. L. Nanostructural Studies of Fresh and Road-Aged Practical Pt/SiO₂ and Pt-Pd/Al₂O₃ Diesel Oxidation Catalysts by Using

- Aberration-Corrected (Scanning) Transmission Electron Microscopy. *ChemCatChem* **2012**, *4*, 1622–1631.
- (53) Graham, G. W.; Jen, H.-W.; Ezekoye, O.; Kudla, R. J.; Chun, W.; Pan, X. Q.; McCabe, R. W. Effect of Alloy Composition on Dispersion Stability and Catalytic Activity for NO Oxidation over Alumina-Supported Pt–Pd Catalysts. *Catal. Letters* **2007**, *116*, 1–8.
- (54) Johns, T. R.; Gaudet, J. R.; Peterson, E. J.; Miller, J. T.; Stach, E. A.; Kim, C. H.; Balogh, M. P.; Datye, A. K. Microstructure of Bimetallic Pt–Pd Catalysts under Oxidizing Conditions. *ChemCatChem* **2013**, *5*, 2636–2645.
- (55) Dadras, J.; Jimenez-Izal, E.; Alexandrova, A. N. Alloying Pt Sub-Nano-Clusters with Boron: Sintering Preventative and Coke Antagonist? *ACS Catal.* **2015**, *5*, 5719–5727.
- (56) Gorey, T. J.; Zandkarimi, B.; Li, G.; Baxter, E. T.; Alexandrova, A. N.; Anderson, S. L. Preparation of Size- and Composition-Controlled Pt_nSn_x/SiO₂ (n = 4, 7, 24) Bimetallic Model Catalysts with Atomic Layer Deposition. *J. Phys. Chem. C* **2019**, *123*, 16194–16209.
- (57) Li, G.; Zandkarimi, B.; Cass, A. C.; Gorey, T. J.; Allen, B. J.; Alexandrova, A. N.; Anderson, S. L. Sn-Modification of Pt₇/Alumina Model Catalysts: Suppression of Carbon Deposition and Enhanced Thermal Stability. *J. Chem. Phys.* **2019**, *submitted*.
- (58) Jimenez-Izal, E.; Liu, J.-Y.; Alexandrova, A. N. Germanium as Key Dopant to Boost the Catalytic Performance of Small Platinum Clusters for Alkane Dehydrogenation. *J. Catal.* **2019**, *374*, 93–100.
- (59) Jimenez-Izal, E.; Zhai, H.; Liu, J.-Y.; Alexandrova, A. N. Nanoalloying MgO-Deposited Pt Clusters with Si To Control the Selectivity of Alkane Dehydrogenation. *ACS Catal.* **2018**, *8*, 8346–8356.
- (60) Davis, J. B. A.; Shayeghi, A.; Horswell, S. L.; Johnston, R. L. The Birmingham Parallel Genetic Algorithm and Its Application to the Direct DFT Global Optimisation of Ir_N (N = 10–20) Clusters. *Nanoscale* **2015**, *7*, 14032–14038.
- (61) Kanters, R. P. F.; Donald, K. J. CLUSTER: Searching for Unique Low Energy Minima of Structures Using a Novel Implementation of a Genetic Algorithm. *J. Chem. Theory Comput.* **2014**, *10*, 5729–5737.

- (62) Alexandrova, A. N. H·(H₂O)_n Clusters: Microsolvation of the Hydrogen Atom via Molecular Ab Initio Gradient Embedded Genetic Algorithm (GEGA). *J. Phys. Chem. A* **2010**, *114*, 12591–12599.
- (63) Alexandrova, A. N.; Boldyrev, A. I. Search for the Li_n^{0/+1/-1} (N= 5– 7) Lowest-Energy Structures Using the Ab Initio Gradient Embedded Genetic Algorithm (GEGA). Elucidation of the Chemical Bonding in the Lithium Clusters. *J. Chem. Theory Comput.* **2005**, *1*, 566–580.
- (64) Avendaño-Franco, G.; Romero, A. H. Firefly Algorithm for Structural Search. *J. Chem. Theory Comput.* **2016**, *12*, 3416–3428.
- (65) Wang, Y.; Lv, J.; Zhu, L.; Ma, Y. CALYPSO: A Method for Crystal Structure Prediction. *Comput. Phys. Commun.* **2012**, *183*, 2063–2070.
- (66) Wales D. J. In *Modern Methods of Crystal Structure Prediction*; Oganov, A. R., Ed.; Wiley-VCH Verlag GmbH & Co. KGaA: Weinheim, Germany, 2010; pp 29–54.
- (67) Chen, X.; Zhao, Y.; Zhang, Y.; Li, J. TGMin: An Efficient Global Minimum Searching Program for Free and Surface-supported Clusters. *J. Comput. Chem.* **2019**, *40*, 1105–1112.
- (68) Zhao, Y.; Chen, X.; Li, J. TGMin: A Global-Minimum Structure Search Program Based on a Constrained Basin-Hopping Algorithm. *Nano Res.* **2017**, *10*, 3407–3420.
- (69) Zhai, H.; Ha, M.-A.; Alexandrova, A. N. AFFCK: Adaptive Force-Field-Assisted Ab Initio Coalescence Kick Method for Global Minimum Search. *J. Chem. Theory Comput.* **2015**, *11*, 2385–2393.
- (70) Weigend, F.; Ahlrichs, R. Quantum Chemical Treatments of Metal Clusters. *Philos. Trans. R. Soc. A Math. Phys. Eng. Sci.* **2010**, *368*, 1245–1263.
- (71) Krcha, M. D.; Janik, M. J. Challenges in the Use of Density Functional Theory to Examine Catalysis by M-doped Ceria Surfaces. *Int. J. Quantum Chem.* **2014**, *114*, 8–13.
- (72) Pacchioni, G. Modeling Doped and Defective Oxides in Catalysis with Density Functional Theory Methods: Room for Improvements. *J. Chem. Phys.* **2008**, *128*, 182505.
- (73) Anisimov, V. I.; Gunnarsson, O. Density-Functional Calculation of Effective Coulomb Interactions in Metals. *Phys. Rev. B* **1991**, *43*, 7570.
- (74) Rusakov, A. A.; Zgid, D. Self-Consistent Second-Order Green's Function Perturbation Theory for Periodic Systems. *J. Chem. Phys.* **2016**, *144*, 54106.

- (75) Heyd, J.; Scuseria, G. E. Efficient Hybrid Density Functional Calculations in Solids: Assessment of the Heyd–Scuseria–Ernzerhof Screened Coulomb Hybrid Functional. *J. Chem. Phys.* **2004**, *121*, 1187–1192.
- (76) Neuhauser, D.; Baer, R.; Zgid, D. Stochastic Self-Consistent Second-Order Green’s Function Method for Correlation Energies of Large Electronic Systems. *J. Chem. Theory Comput.* **2017**, *13*, 5396–5403.
- (77) Lu, Q.; Neese, F.; Bistoni, G. Formation of Agostic Structures Driven by London Dispersion. *Angew. Chemie Int. Ed.* **2018**, *57*, 4760–4764.
- (78) Guo, Y.; Riplinger, C.; Becker, U.; Liakos, D. G.; Minenkov, Y.; Cavallo, L.; Neese, F. Communication: An Improved Linear Scaling Perturbative Triples Correction for the Domain Based Local Pair-Natural Orbital Based Singles and Doubles Coupled Cluster Method [DLPNO-CCSD (T)]. *J. Chem. Phys.* **2018**, *148*, 11101.
- (79) Grimme, S. Density Functional Theory with London Dispersion Corrections. *Wiley Interdiscip. Rev. Comput. Mol. Sci.* **2011**, *1*, 211–228.
- (80) Carter, C. B.; Williams, D. B. In *Transmission Electron Microscopy*; Carter, B., Williams, D. B., Eds.; Springer International Publishing: Boston, MA, 2016; pp 17–26.
- (81) Bañares, M. A.; Guerrero-Pérez, M. O.; Fierro, J. L. G.; Cortez, G. G. Raman Spectroscopy during Catalytic Operations with On-Line Activity Measurement (Operando Spectroscopy): A Method for Understanding the Active Centres of Cations Supported on Porous Materials. *J. Mater. Chem.* **2002**, *12*, 3337–3342.
- (82) Chakrabarti, A.; Ford, M. E.; Gregory, D.; Hu, R.; Keturakis, C. J.; Lwin, S.; Tang, Y.; Yang, Z.; Zhu, M.; Bañares, M. A.; Wachs, I. E. A Decade+ of Operando Spectroscopy Studies. *Catal. Today* **2017**, *283*, 27–53.
- (83) Li, Y.; Zakharov, D.; Zhao, S.; Tappero, R.; Jung, U.; Elsen, A.; Baumann, P.; Nuzzo, R. G.; Stach, E. A.; Frenkel, A. I.; Understanding. Complex Structural Dynamics of Nanocatalysts Revealed in Operando Conditions by Correlated Imaging and Spectroscopy Probes. *Nat. Commun.* **2015**, *6*, 7583–7588.
- (84) Weckhuysen, B. M. Operando Spectroscopy: Fundamental and Technical Aspects of Spectroscopy of Catalysts under Working Conditions. *Phys. Chem. Chem. Phys.* **2003**, *5*, 1.

- (85) Guerrero-Pérez, M. O.; Bañares, M. A. From Conventional in Situ to Operando Studies in Raman Spectroscopy. *Catal. Today* **2006**, *113*, 48–57.
- (86) Dou, J.; Sun, Z.; Opalade, A. A.; Wang, N.; Fu, W.; Tao, F. (Feng). Operando Chemistry of Catalyst Surfaces during Catalysis. *Chem. Soc. Rev.* **2017**, *46*, 2001–2027.
- (87) Pagliaro, M. Taking “Nothing” into Consideration: Supported Metal Catalysts by SAXS. *Adv. Synth. Catal.* **2005**, *347*, 1961–1964.
- (88) Povia, M.; Herranz, J.; Binniger, T.; Nachtegaal, M.; Diaz, A.; Kohlbrecher, J.; Abbott, D. F.; Kim, B.-J.; Schmidt, T. J. Combining SAXS and XAS To Study the Operando Degradation of Carbon-Supported Pt-Nanoparticle Fuel Cell Catalysts. *ACS Catal.* **2018**, *8*, 7000–7015.
- (89) Newton, M. A. Time Resolved Operando X-Ray Techniques in Catalysis, a Case Study: CO Oxidation by O₂ over Pt Surfaces and Alumina Supported Pt Catalysts. *Catalysts* **2017**, *7*, 58–106.
- (90) Heimdal, J.; Ryde, U. Convergence of QM/MM Free-Energy Perturbations Based on Molecular-Mechanics or Semiempirical Simulations. *Phys. Chem. Chem. Phys.* **2012**, *14*, 12592–12604.
- (91) Polyak, I.; Benighaus, T.; Boulanger, E.; Thiel, W. Quantum Mechanics/Molecular Mechanics Dual Hamiltonian Free Energy Perturbation. *J. Chem. Phys.* **2013**, *139*, 64105.