

LIBRARY AND
DOCUMENTS SECTION

DIRECT EVIDENCE OF PRESENCE OF BOTH INTERSTITIAL
AND VACANCY DISLOCATION LOOPS
IN PLASTICALLY DEFORMED AND SUBSEQUENTLY
ANNEALED MAGNESIUM OXIDE

J. Narayan and J. Washburn

January 1972

AEC Contract No. W-7405-eng-48

TWO-WEEK LOAN COPY

*This is a Library Circulating Copy
which may be borrowed for two weeks.
For a personal retention copy, call
Tech. Info. Division, Ext. 5545*



25

e.i.

DISCLAIMER

This document was prepared as an account of work sponsored by the United States Government. While this document is believed to contain correct information, neither the United States Government nor any agency thereof, nor the Regents of the University of California, nor any of their employees, makes any warranty, express or implied, or assumes any legal responsibility for the accuracy, completeness, or usefulness of any information, apparatus, product, or process disclosed, or represents that its use would not infringe privately owned rights. Reference herein to any specific commercial product, process, or service by its trade name, trademark, manufacturer, or otherwise, does not necessarily constitute or imply its endorsement, recommendation, or favoring by the United States Government or any agency thereof, or the Regents of the University of California. The views and opinions of authors expressed herein do not necessarily state or reflect those of the United States Government or any agency thereof or the Regents of the University of California.

DIRECT EVIDENCE OF PRESENCE OF BOTH INTERSTITIAL AND VACANCY DISLOCATION LOOPS IN
PLASTICALLY DEFORMED AND SUBSEQUENTLY ANNEALED MAGNESIUM OXIDE

J. Narayan and J. Washburn
Department of Materials Science and Engineering
University of California, Berkeley

When magnesium oxide is deformed plastically most of the damage is introduced in the form of dislocation dipoles. On annealing these dislocation dipoles break up into rows of prismatic edge dislocation loops. As it is annealed further there is loop coarsening by self climb, prismatic slip (1) and bulk diffusion (1,2). Groves and Kelly (3) on the basis of electron diffraction contrast experiments concluded that most or all of the loops in plastically deformed and subsequently annealed foils are vacancy type. Cass (4) found that both interstitial and vacancy dipoles were present in as deformed magnesium oxide. By developing a contamination free technique of annealing thin foils outside the electron microscope above $\sim 1000^{\circ}\text{C}$ and photographing the same area under identical diffraction conditions, the present authors were able to analyze precisely the mechanisms of annealing out the damage introduced by plastic deformation (1). The observations show in a direct way, not depending on diffraction contrast analysis, that both vacancy and interstitial loops are present after annealing of a deformed MgO foil.

Figure 1 is a set of pictures of the same area after the following annealing treatments: 1A \rightarrow 1B, 27 min. at 1050°C ; 1B \rightarrow 1C, 34 min. at 1050°C . The set of pictures clearly shows the coalescence of a large elongated loop with a smaller loop of opposite Burgers vector by prismatic slip of the latter along its glide cylinder. After coalescence the part of the big loop (denoted by the arrow) breaks up pipe diffusion. A small loop is pinched off for the same reason that all dipoles tend to break up into circular loops particularly at their ends (5).

Figure 2 shows another set of pictures with the following annealing treatments: 2A \rightarrow 2B, 76 min. at 1195°C , 2B \rightarrow 2C, 38 min. at 1195°C ; 2C \rightarrow 2D, 30 min. At 6 there is an example where two dislocation loops are gliding due to their mutual interactions along glide cylinders that are at 90° to each other. Stereomicroscopy was done at each step of the picture making to locate the dislocation loops in the foil. Since both loops have "outside contrast" (image outside the extra half plane), they must have been of opposite type; one of them interstitial and the other vacancy. As can be seen in the last photograph when they finally came together




they annihilated each other by rapid pipe diffusion even though the Burgers vectors were at 90° to one another. Pairs of loops at 1 2 3 4 and 5 (Fig. 2) are all similar pairs, either both vacancy or both interstitial type. Observations of interaction between opposite pairs were relatively rare. Contrast experiments similar to those reported by Groves and Kelly showed, in agreement with these authors, (3) that in thin foils annealed at high temperature (1300°C) for a long time almost all of the loops were vacancy type. Therefore, it was concluded that during plastic deformation of MgO , both kinds of dipoles are produced but vacancy type dipoles predominate. On long annealing all the interstitial loops are annihilated by prismatic slip and climb. Only the excess vacancy type defects are left.

Acknowledgement

We acknowledge the continued support of the U.S. Atomic Energy Commission through the Inorganic Materials Research Division of the Lawrence Berkeley Laboratory of the University of California at Berkeley.


References

1. J. Narayan, Ph. D. Thesis, University of California, Berkeley, LBL 406, (1971).
2. G. W. Groves and A. Kelly, J. Appl. Phys. 34 (1963) 3104.
3. G. W. Groves and A. Kelly, Phil. Mag. 6 (1961) 1527;
7 (1962) 892.
4. T. R. Cass, Ph. D. Thesis, University of California, Berkeley UCRL 11996 (1966).
5. J. Narayan, M.S. Thesis, UCRL 20305, University of California, Berkeley (1970).

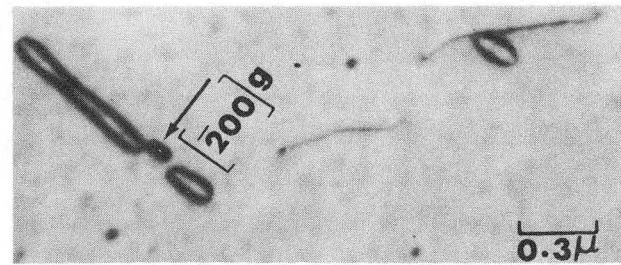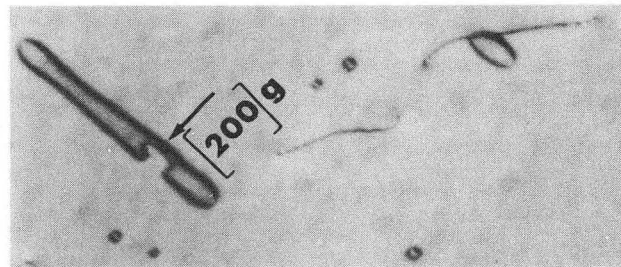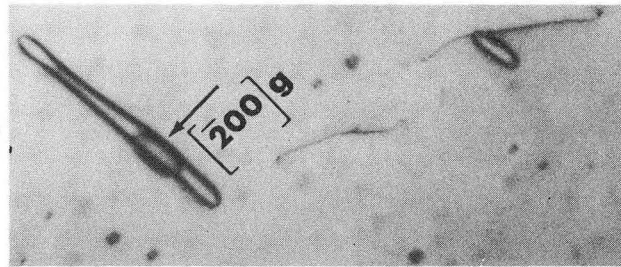

XBB 721-1

Fig. 1.

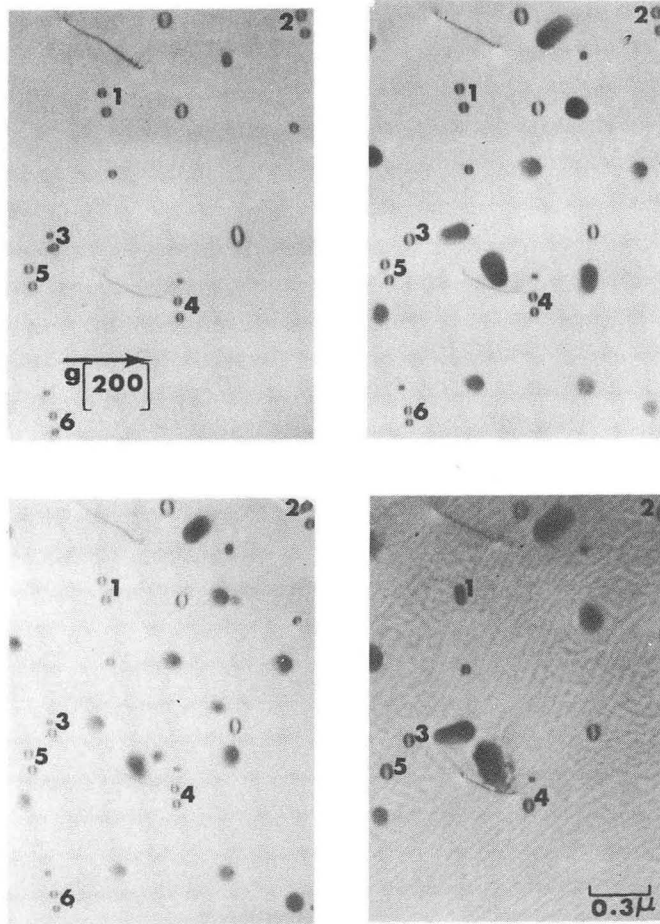

XBB 721-2

Fig. 2.

LEGAL NOTICE

This report was prepared as an account of work sponsored by the United States Government. Neither the United States nor the United States Atomic Energy Commission, nor any of their employees, nor any of their contractors, subcontractors, or their employees, makes any warranty, express or implied, or assumes any legal liability or responsibility for the accuracy, completeness or usefulness of any information, apparatus, product or process disclosed, or represents that its use would not infringe privately owned rights.

TECHNICAL INFORMATION DIVISION
LAWRENCE BERKELEY LABORATORY
UNIVERSITY OF CALIFORNIA
BERKELEY, CALIFORNIA 94720