

Lawrence Berkeley National Laboratory

LBL Publications

Title

AN ELECTRON MICROSCOPY STUDY OF THE LOW TEMPERATURE CATALYZED STEAM GASIFICATION OF GRAPHITE

Permalink

<https://escholarship.org/uc/item/7zb8n39x>

Author

Coates, D.J.

Publication Date

1982-05-01



Lawrence Berkeley Laboratory

UNIVERSITY OF CALIFORNIA

Materials & Molecular Research Division

RECEIVED
LAWRENCE
BERKELEY LABORATORY
JUN 18 1982
LIBRARY AND
DOCUMENTS SECTION


Submitted to the Journal of Catalysis

AN ELECTRON MICROSCOPY STUDY OF THE LOW TEMPERATURE
CATALYZED STEAM GASIFICATION OF GRAPHITE

D.J. Coates, J.W. Evans, A.L. Cabrera,
G.A. Somorjai and H. Heinemann

May 1982

TWO-WEEK LOAN COPY
*This is a Library Circulating Copy
which may be borrowed for two weeks.
For a personal retention copy, call
Tech. Info. Division, Ext. 6782.*

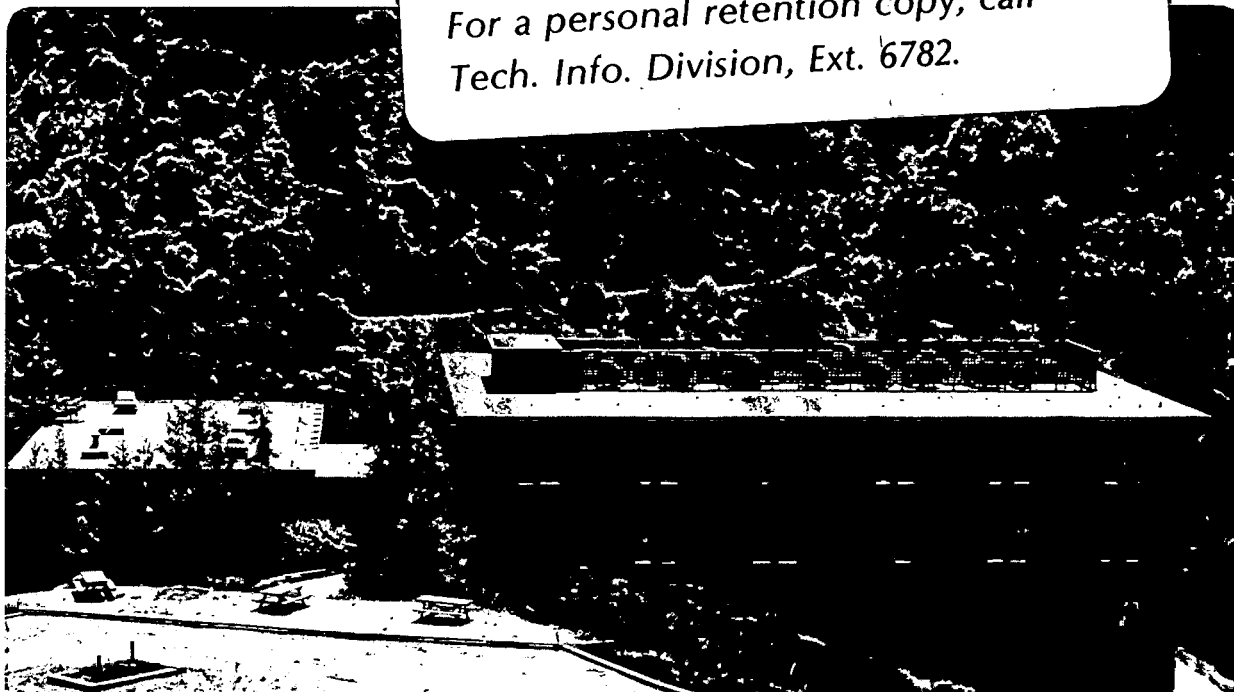

LBL-14463
2

DISCLAIMER

This document was prepared as an account of work sponsored by the United States Government. While this document is believed to contain correct information, neither the United States Government nor any agency thereof, nor the Regents of the University of California, nor any of their employees, makes any warranty, express or implied, or assumes any legal responsibility for the accuracy, completeness, or usefulness of any information, apparatus, product, or process disclosed, or represents that its use would not infringe privately owned rights. Reference herein to any specific commercial product, process, or service by its trade name, trademark, manufacturer, or otherwise, does not necessarily constitute or imply its endorsement, recommendation, or favoring by the United States Government or any agency thereof, or the Regents of the University of California. The views and opinions of authors expressed herein do not necessarily state or reflect those of the United States Government or any agency thereof or the Regents of the University of California.

AN ELECTRON MICROSCOPY STUDY OF THE
LOW TEMPERATURE CATALYZED STEAM GASIFICATION OF GRAPHITE

D.J. Coates, J.W. Evans, A.L. Cabrera, G.A. Somorjai & H. Heinemann

Materials and Molecular Research Division
Lawrence Berkeley Laboratory
University of California
Berkeley, California 94720

This work was supported by the Director, Office of Energy Research, Office of Basic Energy Sciences, Chemical Sciences Division and the Assistant Secretary for Fossil Energy, Office of Coal Research, Liquefaction Division of the U.S. Department of Energy under Contract DE-AC03-76SF00098 through the Pittsburgh Energy Technology Center, Pittsburgh, PA.

The use of an environmental cell in a transmission electron microscope in which a gas-solid reaction may be carried out while observing the solid specimen (controlled atmosphere electron microscopy or CAEM) has been employed in the study of a number of carbon gasification reactions (see, for example 1-11). Catalysis of the gasification of graphite crystals may occur by facilitating penetration of perfect regions of the basal plane, or by altering the rate of reaction at edges or steps in the crystal. Catalysts operating in the former mode are termed pitting catalysts and those operating by the latter mode are referred to as edge-specific or channeling catalysts. Catalytic gasification by the channeling mode is a reaction that is ideally suited to study by CAEM and observed for a number of metal catalysts. In these studies channels were observed to propagate in the graphite crystals, each channel having a catalyst particle at its head and in all cases the channels were observed to emanate from some step or edge in the crystal. Significant differences in the qualitative characteristics of various metal and metal oxide catalysts for the oxidation reaction of graphite have been found. Thus, lead (2) and silver (4) were found to be extremely active at relatively low temperatures ($\sim 350^{\circ}\text{C}$) whereas temperatures of 725°C were required for zinc (1). Metals such as molybdenum (3), platinum and palladium (7) catalyzed the oxidation of graphite by a pitting mode at lower temperatures and then switched over to channeling attack at higher temperatures. A limited number of CAEM studies focussed on the catalytic gasification of graphite with steam have been reported. Baker and Chludzinski (10) have examined the catalytic gasification of graphite in oxygen, steam and hydrogen using copper and chromium as catalysts. They found no evidence of catalytic gasification of the graphite when using steam and concluded that neither metal was an effective agent for dissociation of water molecules, a necessary step in the catalytic process. Baker and Sherwood (12) investigated

the catalytic gasification of graphite by nickel in steam, hydrogen and oxygen. Channeling of the graphite by nickel in steam was reported but did not occur until a temperature of 935°C was reached.

Recently we reported (12,13) that methane may be produced from the catalyzed reaction of high density graphite and water vapor at low temperatures (200-300°C) to produce methane and carbon dioxide. The reaction is catalyzed by potassium hydroxide and potassium carbonate as well as by other alkali hydroxides. When this reaction was catalyzed by potassium compounds, an activation energy of 11.9 ± 0.5 kcal/mole (for the CH₄ production) was measured in the temperature range 200-300°C.

In the present study, CAEM has been used to examine the morphology of the high density graphite during the course of the gasification reaction. Thin specimens of highly oriented pyrolytic graphite were obtained by cleavage from similar specimens to those used in the kinetic studies. Potassium hydroxide was introduced onto the surface of the graphite by dipping the specimens, supported on copper or nickel grids, into a 0.38 M solution of the hydroxide and then drying them. Transmission electron microscopy was carried out in a Hitachi 650 keV microscope equipped with a Gatan environmental cell and single-tilt heating stage. Argon, at ~ 1 atm. pressure, was bubbled through water at room temperature, giving an Ar/H₂O ratio of about 40/1, and then introduced into the environmental cell to give a pressure of 50 Torr. The specimens were heated in the flowing gas mixture and periodically observed. At 500°C the potassium hydroxide was dispersed as particles 0.1-0.5 μm in diameter on the surface of the graphite. With increasing exposure time, gasification was evident as the particles at the edges of the graphite crystals began moving toward the crystal centers leaving channels in their wake.

Figure 1 shows two micrographs recorded 11 minutes apart taken from a

sequence showing the channel growth at 500°C. Channels are evident in two adjacent graphite crystals emanating from the edges of the crystals, each channel with a particle at its head. The interface between the particles in the channels and the graphite shows a hexagonal, faceted morphology. As the reaction continues the particles move and the length of the channels increase, as can be seen by the particles that are indicated by the arrows. The channels remain roughly parallel sided indicating that there is little effect of uncatalyzed reaction at the channel edges, or of wetting of the channel sides by catalytic material. Initially, particles lying on the surface of the graphite crystals do not contribute to the catalytic gasification of the carbon. At a later stage, however, faceted pits in the graphite are evident at the former positions of these particles. The catalyst particles are present within, and at one edge of, the pits. In some cases channeling by these particles away from the original pits is evident.

Similar observations have been noted at 600°C. At this temperature, however, no "incubation" period was noted for the catalytic reaction involving the particles dispersed on the surfaces of the graphite crystals and widespread channeling due to gasification was observed from the outset. Figure 2 shows two micrographs taken from the same area undergoing catalytic gasification at 600°C under the same gas conditions as before. The micrographs were taken 10 minutes apart and the first was taken after only 2 minutes exposure. Some of the catalytic particles are large and form wide channels up to ~ 1 μm wide, extending from the edge of the crystal. Channeling is also evident originating at pits, away from the edges of the crystal, again with particles at the heads of the channels. The channels are not straight-sided and there is a general enlarging of the pits. This suggests a wider dispersion of the catalytic phase, possibly as a liquid, forming a thin film along the crystal edges and

around the edges of the pits.

Because a pronounced catalytic activity of the KOH in the graphite was observed during these CAEM studies at 500°C and at higher temperatures, it was desirable to extend our kinetic investigations that were carried out in the 200-300°C range, up to 600°C. The purpose was to check whether the same mechanism was responsible for CH₄ production at 300°C as well as at 600°C by measuring the rates and activation energies over a wider temperature range. Therefore, a sample of high density graphite similar to those used in previous studies (12,13) was impregnated with a 0.38 M solution of KOH. Then, it was exposed to a mixture of 20 torr of water vapor and 1 atm. of purified helium and heated to the desired temperature. The surface composition was monitored by Auger electron spectroscopy (AES) before and after reaction and the reaction products were measured by means of an HP-gas chromatograph with a thermal conductivity detector. The apparatus used in these experiments has been described elsewhere (12,13). Since high temperatures (~ 600°C) were needed in these experiments we switched from our previous method of direct heating of the graphite (resistively heating the graphite by a high current AC power supply) to indirect heating (resistively heating a gold foil that was in contact with one face of the graphite crystal). The steady state rates for CH₄ production were measured at different temperatures between 300°C and 600°C. In order to obtain a turnover frequency, the rates were divided by the total number of carbon surface atoms exposed (assuming 1×10^{15} atoms per 1 cm²). The logarithms of the turnover frequency as a function of the inverse absolute temperature were plotted and are displayed in Figure 3. From this figure an activation energy of 11 ± 1 kcal/mole is obtained in good agreement with our previous experiments at much lower temperatures.

Pronounced increase in the amount of CH₄ produced was observed from one

graphite sample to another, when only the thickness of the samples was increased. This indicates that most of the active sites for this reaction are located on the edges of the graphite crystals. It is not surprising then, that scattering in the turnover frequencies is found, since it is very difficult to accurately reproduce the morphology of these edges when the samples are cut from a larger piece of graphite.

At high temperatures (over 500°C) a significant amount of the KOH was desorbed from the graphite basal plane, as revealed by AES and thermal desorption experiments (13). This partial loss of the catalyst might be responsible for a lower rate of CH₄ production than the rate expected at 600°C.

It is evident that a similar mechanism of catalytic gasification of graphite in water vapor by potassium hydroxide occurs at 500 and 600°C, causing channeling of the graphite in contact with the catalyst particles. The identical activation energy that was observed for the reaction at low (300°C) and at high (600°C) temperatures suggests that the mechanism of the reaction is unchanged throughout the 200-600°C temperature range.

This work shows that gasification of graphite with water vapor occurs catalytically and by a channeling mode from the edges inward. The temperatures at which this is observed are much lower than has previously been found using metal catalysts and may have significant implications in the low temperature gasification of coal and other carbonaceous materials. The results of CAEM investigations at lower temperatures which are currently being undertaken will be reported subsequently.

ACKNOWLEDGMENTS

This work was jointly supported by the Director, Office of Energy Research, Office of Basic Energy Sciences, Chemical Sciences Division, and the Assistant Secretary for Fossil Energy, Office of Coal Research, Liquefaction Division of the U.S. Department of Energy under Contract DE-AC03-76SF00098, through the Pittsburgh Energy Technology Center, Pittsburgh, Pennsylvania.

REFERENCES

1. Baker, R.T.K. and Harris, B.G., Carbon 11, 25 (1973).
2. Harris, P.S., Feates, F.S. and Reuben, B.G., Carbon 11, 565 (1973).
3. Baker, R.T.K., Harris, P.S., Kemper, D.J. and Waite, R.J., Carbon 12, 179 (1974).
4. Harris, P.S., Feates, F.S. and Reuben, B.G., Carbon 12, 189 (1974).
5. Baker, R.T.K., Thomas, R.B. and Wells, M., Carbon 13, 141 (1975).
6. Baker, R.T.K., France, J.A., Rouse, L. and Waite, R.J., J. Catal. 41, 22 (1976).
7. Keep, C.W., Terry, S. and Wells, M., J. Catal. 66, 451 (1980).
8. Baker, R.T.K. and Sherwood, R.D., J. Catal. 61, 378 (1980).
9. Baker, R.T.K., Sherwood, R.D. and Dumesic, J.A., J. Catal. 66, 56 (1980).
10. Baker, R.T.K. and Chludzinski, Jr., J.J., Carbon 19, 75 (1981).
11. Baker, R.T.K. and Sherwood, R.D., J. Catal. 70, 198 (1981).
12. Cabrera, A.L., Heinemann, H. and Somorjai, G.A., Chemical Physics Letters, 81, No. 3, 402 (1981).
13. Cabrera, A.L., Heinemann, H. and Somorjai, G.A., J. Catalysis 74 (1982).

FIGURE CAPTIONS

Figure 1: Catalytic channeling by KOH at 500°C in H₂O + Ar, (a) 22 minutes exposure, (b) 33 minutes exposure.

Figure 2: Catalytic gasification of carbon by KOH at 600°C in H₂O + Ar, (a) 2 minutes exposure, (b) 12 minutes exposure.

Figure 3: Logarithm of the CH₄ production rate as a function of the inverse absolute temperature for the KOH-catalyzed reaction of graphite and water vapor.

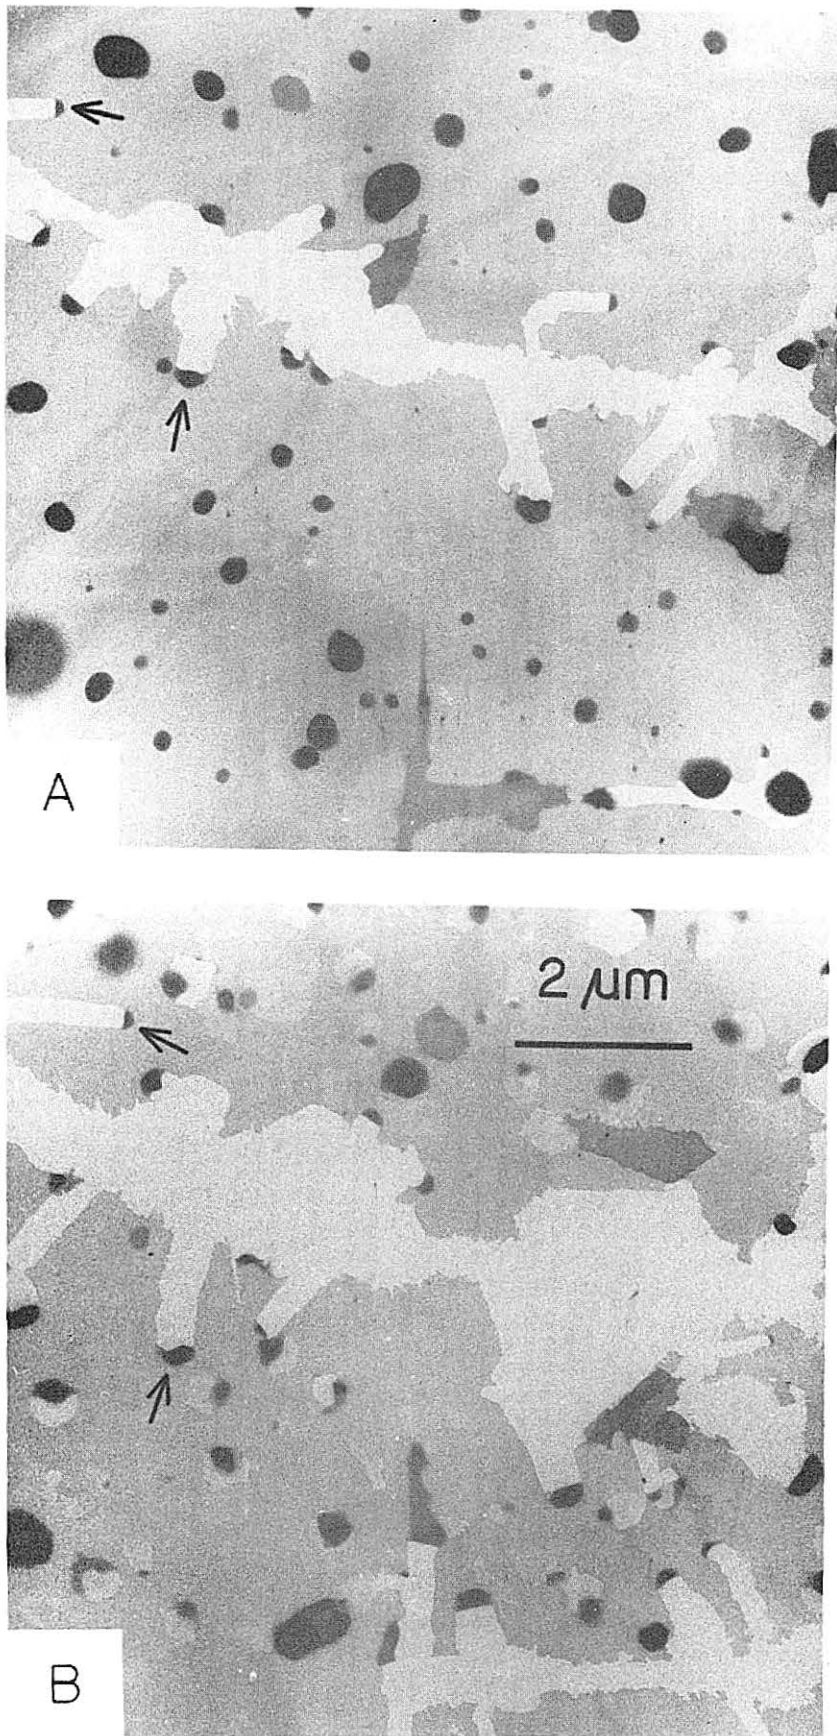


Figure 1

XBB824-3397

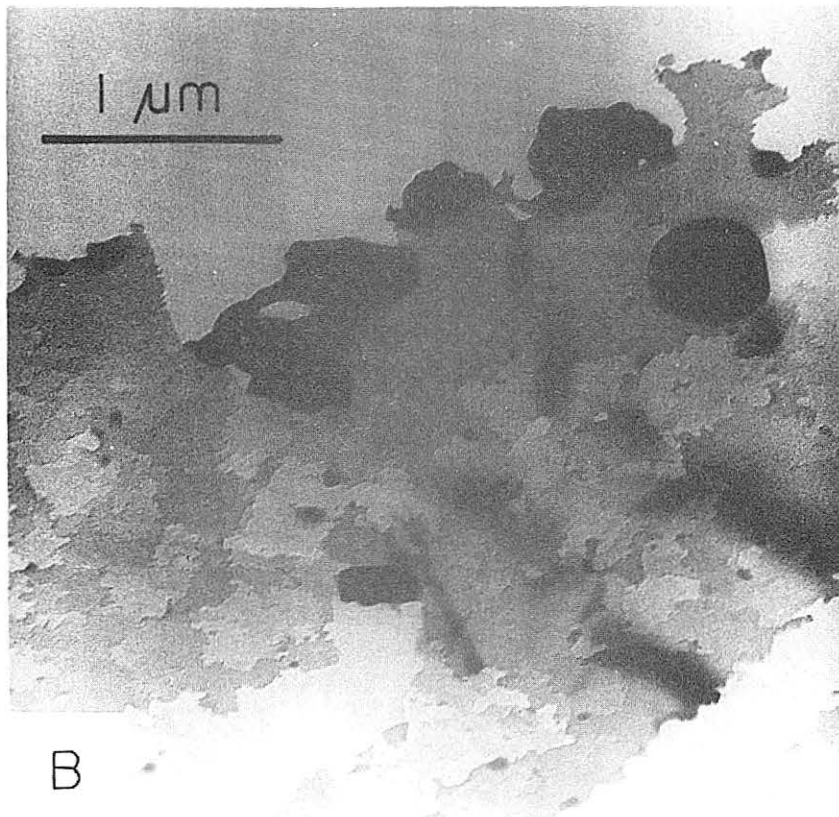
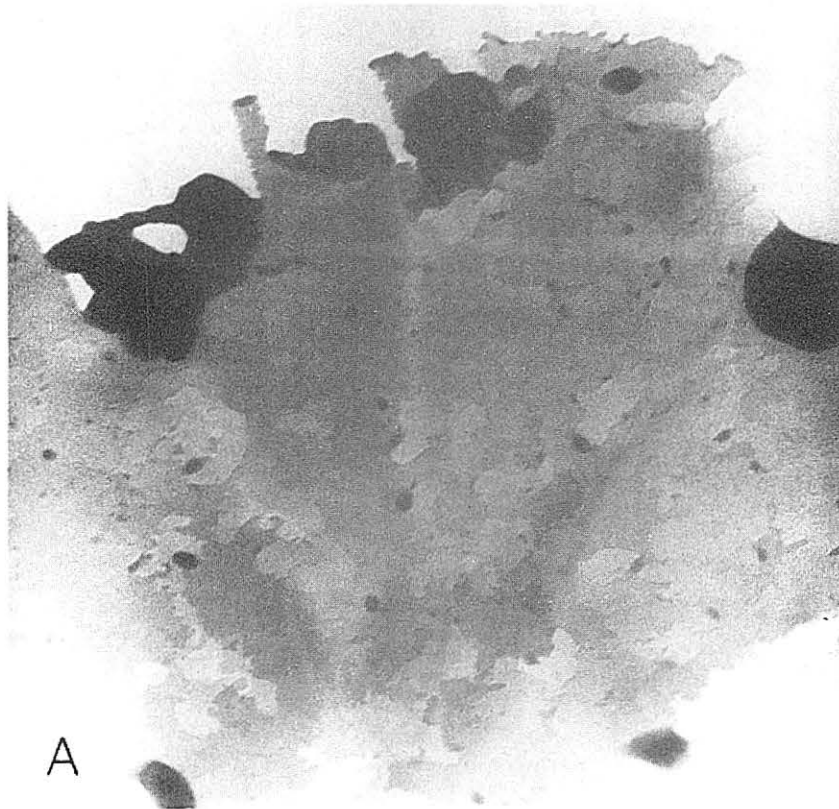


Figure 2

XBB824-3396

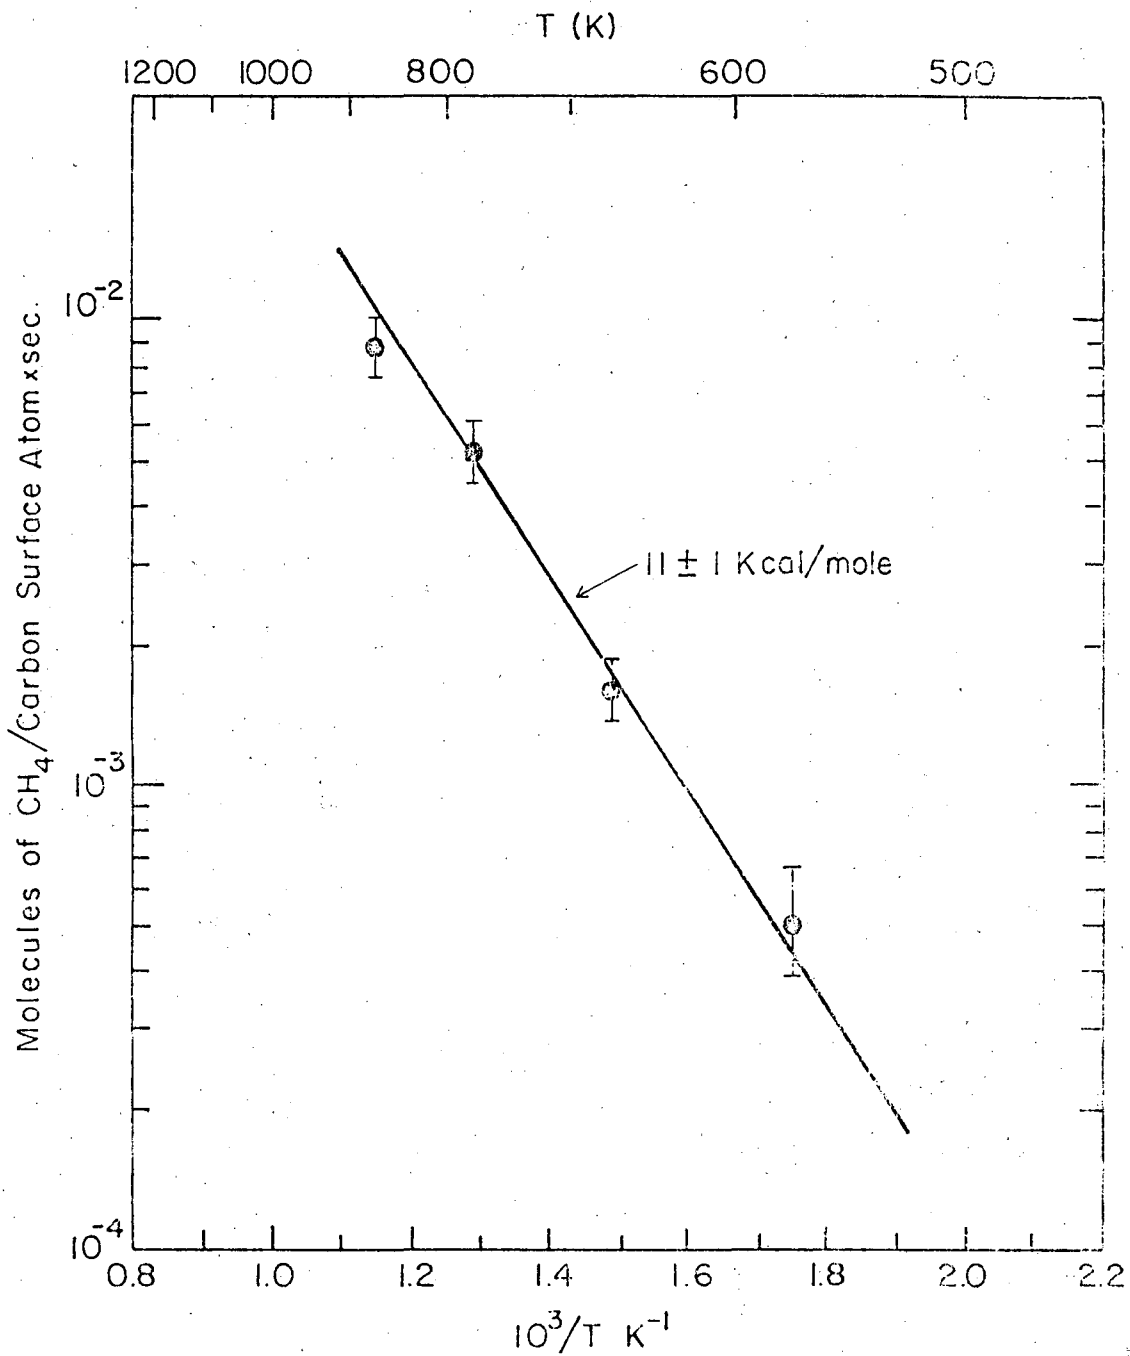


Figure 3

XBL 624-5535

This report was done with support from the Department of Energy. Any conclusions or opinions expressed in this report represent solely those of the author(s) and not necessarily those of The Regents of the University of California, the Lawrence Berkeley Laboratory or the Department of Energy.

Reference to a company or product name does not imply approval or recommendation of the product by the University of California or the U.S. Department of Energy to the exclusion of others that may be suitable.

TECHNICAL INFORMATION DEPARTMENT
LAWRENCE BERKELEY LABORATORY
UNIVERSITY OF CALIFORNIA
BERKELEY, CALIFORNIA 94720