

## Hydrogen-Bonding Interactions in Hybrid Aqueous/Non-Aqueous Electrolyte Enables Low-Cost and Long-Lifespan Sodium-Ion Storage

Rodney Chua, Yi Cai, Pei Qi Lim, Sonal Kumar, Rohit Satish, William Jr Manalastas, Hao Ren, Vivek Verma, Shize Meng, Samuel Morris, Pinit Kidkhunthod, Jianming Bai, and Madhavi Srinivasan

*ACS Appl. Mater. Interfaces*, **Just Accepted Manuscript** • DOI: 10.1021/acsami.0c03423 • Publication Date (Web): 28 Apr 2020

Downloaded from pubs.acs.org on May 1, 2020

### Just Accepted

“Just Accepted” manuscripts have been peer-reviewed and accepted for publication. They are posted online prior to technical editing, formatting for publication and author proofing. The American Chemical Society provides “Just Accepted” as a service to the research community to expedite the dissemination of scientific material as soon as possible after acceptance. “Just Accepted” manuscripts appear in full in PDF format accompanied by an HTML abstract. “Just Accepted” manuscripts have been fully peer reviewed, but should not be considered the official version of record. They are citable by the Digital Object Identifier (DOI®). “Just Accepted” is an optional service offered to authors. Therefore, the “Just Accepted” Web site may not include all articles that will be published in the journal. After a manuscript is technically edited and formatted, it will be removed from the “Just Accepted” Web site and published as an ASAP article. Note that technical editing may introduce minor changes to the manuscript text and/or graphics which could affect content, and all legal disclaimers and ethical guidelines that apply to the journal pertain. ACS cannot be held responsible for errors or consequences arising from the use of information contained in these “Just Accepted” manuscripts.

1  
2  
3 **Hydrogen-Bonding Interactions in Hybrid Aqueous/Non-Aqueous Electrolyte Enables**  
4  
5 **Low-Cost and Long-Lifespan Sodium-Ion Storage**  
6  
7  
8  
9

10 *Rodney Chua, <sup>a</sup> Yi Cai, <sup>a</sup> Pei Qi Lim, <sup>a</sup> Sonal Kumar, <sup>a</sup> Rohit Satish, <sup>b</sup> William Manalastas Jr.,*  
11 *<sup>a</sup> Hao Ren, <sup>a</sup> Vivek Verma, <sup>a</sup> Shize Meng, <sup>a</sup> Samuel A. Morris, <sup>a</sup> Pinit Kidkhunthod, <sup>c</sup> Jianming*  
12 *Bai, <sup>d</sup> and Madhavi Srinivasan <sup>a, \*</sup>*  
13  
14  
15  
16  
17  
18

19 <sup>a</sup> School of Materials Science and Engineering, Nanyang Technological University, 11 Faculty  
20 Ave, Singapore 639977, Singapore  
21  
22

23 E-mail: madhavi@ntu.edu.sg  
24  
25

26 <sup>b</sup> Energy Storage and Distributed Resources Division, Lawrence Berkeley National Laboratory,  
27 1 Cyclotron Road, Berkeley, 94720, USA  
28  
29

30 <sup>c</sup> Synchrotron Light Research Institute (Public Organization), Muang, Nakhon Ratchasima,  
31 30000, Thailand  
32  
33  
34

35 <sup>d</sup> Synchrotron Light Source II, Brookhaven National Laboratory, Upton, NY 11973, USA  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60

**Abstract**

Although “water-in-salt” electrolytes have opened a new pathway to expand the electrochemical stability window of aqueous electrolytes, the electrode instability and irreversible proton co-insertion caused by aqueous media still hinder the practical application, even when using exotic fluorinated salts. In this study, an accessible hybrid electrolyte class based on common sodium salts is proposed, and crucially an ethanol-rich media is introduced to achieve highly stable Na-ion electrochemistry. Here, ethanol exerts a strong hydrogen-bonding effect on water, simultaneously expanding the electrochemical stability window of the hybridized electrolyte to 2.5 V, restricting degradation activities, reducing transition metal dissolution from the cathode material and improving electrolyte-electrode wettability. The binary ethanol-water solvent enables the impressive cycling of sodium-ion batteries based on perchlorate, chloride, and acetate electrolyte salts. Notably, a  $\text{Na}_{0.44}\text{MnO}_2$  electrode exhibits both high capacity ( $81 \text{ mAh g}^{-1}$ ) and remarkable long cycle life  $>1000$  cycles at  $100 \text{ mA g}^{-1}$  (a capacity decay rate per cycle of 0.024%) in a 1 M sodium acetate system. The  $\text{Na}_{0.44}\text{MnO}_2/\text{Zn}$  full cells also show excellent cycling stability and rate capability in a wide temperature range. The gained understanding of the hydrogen-bonding interactions in the hybridized electrolyte can provide new battery chemistry guidelines in designing promising candidates for developing low cost and long lifespan batteries based on other ( $\text{Li}^+$ ,  $\text{K}^+$ ,  $\text{Zn}^{2+}$ ,  $\text{Mg}^{2+}$ , and  $\text{Al}^{3+}$ ) systems.

**Keywords:** hybrid, hydrogen-bonding, rechargeable sodium-ion batteries,  $\text{Na}_{0.44}\text{MnO}_2$ , electrolyte

## Introduction

Towards a green and sustainable large-scale stationary energy storage systems (ESSs), aqueous rechargeable sodium-ion batteries (ARSIBs) is considered as one of the promising candidates due to safer battery electrolytes and the abundance of low-cost sodium resources.<sup>1-</sup><sup>4</sup> However, ARSIBs are prone to suffer from inferior cycling stability, owing to the parasitic side reactions associated with the aqueous electrolyte system, such as limited operating voltage window ( $\sim 1.23\text{V}$ ) induced by the  $\text{H}_2/\text{O}_2$  evolution reactions, dissolution of electrode materials and water protons co-insertion into the host electrode, all of which have hampered their practical applications.<sup>1-2, 4</sup>

Recently, a new class of electrolytes, namely “water-in-salt” electrolytes, constituted from high-concentration salts, have been explored.<sup>5-8</sup> For instance, an electrolyte such as  $\text{NaCF}_3\text{SO}_3$  ( $9.26\text{ mol kg}^{-1}$ ,  $9.26\text{ m}$ ), can expand the operational voltage window from  $1.23$  to  $2.50\text{ V}$  and suppress hydrogen evolution through the formation of solid-electrolyte interphase (SEI) on the anode, thereby granting access to high-energy Na-ion batteries. An aqueous Na-ion full battery by using  $\text{Na}_{0.66}[\text{Mn}_{0.66}\text{Ti}_{0.34}]\text{O}_2$  as the cathode,  $\text{NaTi}_2(\text{PO}_4)_3$  as the anode and  $9.26\text{ m NaCF}_3\text{SO}_3$  as the electrolyte, can achieve a superior long-term cycle life of  $>1200$  cycles at  $1\text{C}$ .<sup>5</sup> However, the cell still suffered an obvious capacity fading in the initial few cycles with a low capacity of  $\sim 20\text{ mAh g}^{-1}$  after 100 cycles. Even in  $9.2\text{ m}$  saturated  $\text{NaCF}_3\text{SO}_3$  electrolyte, the molar ratio of water to sodium-ions ( $6.5$ ) remains high, because of the relatively low solubility of sodium salts with fluorinated anions. Hence, there is still a relatively large amount of free water in the electrolyte, which may lead to electrode instability. In addition, the high cost of these “water-in-salt” electrolytes (Table S1) has inevitably hindered their practical applications.

It is well known that each water molecule consists of one heavier oxygen atom and two lighter hydrogen atoms. In liquid water, the hydrogen atoms in a molecule are attracted to the oxygen atoms from neighboring water molecules and form hydrogen bonds. The hydrogen

1  
2  
3 bonds between water molecules are constantly breaking and reforming on picosecond time  
4  
5 scales.<sup>9</sup> Since hydrogen-bonding plays an essential role in the physical, chemical, and structural  
6  
7 properties of liquid water, selectively and significantly strengthen the hydrogen-bonding  
8  
9 strength of water by introducing a polar protic solvent could be an alternative low-cost  
10  
11 approach to suppress water activity. Ethanol (dielectric constant  $\epsilon = 25.10$ , dipole moment  
12  
13  $1.70$ ) as a polar protic solvent, is fully miscible with water (dielectric constant  $\epsilon = 80.10$ , dipole  
14  
15 moment  $1.84$ ).<sup>10-11</sup> By hybridizing ethanol with water solvents, there will be a structure  
16  
17 rearrangement through the breaking of the water hydrogen-bonding network and forming a  
18  
19 new type of hydrogen bond organization.<sup>12-14</sup> This would decrease the interfacial tension of  
20  
21 ethanol-water cosolvent, which is favorable for better electrode/electrolyte contact. In addition,  
22  
23 the low freezing point ( $-114\text{ }^{\circ}\text{C}$ ) of ethanol could potentially expand the hybrid electrolyte  
24  
25 working temperature range.<sup>15</sup>

26  
27  
28  
29  
30 Herein, we report a new type of hybrid electrolyte prepared by using binary ethanol-water  
31  
32 solvents. Such solvents are readily available, cost-effective, and can accommodate various low-  
33  
34 concentration sodium salts, such as chlorides, perchlorates, and acetates, enabling Na-ion  
35  
36 chemistries with high performance especially excellent cycling stability. In the ethanol-water  
37  
38 system, ethanol plays an active role in rearranging the network structures of water molecules  
39  
40 *via* hydrogen-bonding, thereby enabling intimate electrode-electrolyte contact and suppressing  
41  
42 the protons co-insertion into the electrode upon cycling and reducing the dissolution of Mn  
43  
44 from the cathode. An electrolyte consisting of 1 M sodium acetate in 5:1 *v/v* ethanol-water  
45  
46 (denoted as 1 M NaAc-Et/Di) system exhibits strong hydrogen-bonding interactions and  
47  
48 excellent wettability, which allows a  $\text{Na}_{0.44}\text{MnO}_2$  electrode to deliver a high discharge capacity  
49  
50 of  $81\text{ mAh g}^{-1}$  at  $100\text{ mA g}^{-1}$  with remarkable reversibility. Superior long-term cycle life of  
51  
52  $>1000$  cycles (a capacity decay rate per cycle of  $0.024\%$ ) was also achieved. Furthermore, *ex-*  
53  
54 *situ* XRD, SEM, and TEM-EDX studies of the  $\text{Na}_{0.44}\text{MnO}_2$  electrodes demonstrate that a  
55  
56  
57  
58  
59  
60

1  
2  
3 considerable number of protons can co-insert into the lattice of  $\text{Na}_{0.44}\text{MnO}_2$  in 1 M NaAc-Di  
4  
5 system, finally leading to irreversible phase collapse ( $\text{MnOOH}$ ). In comparison, the crystal  
6  
7 structure of  $\text{Na}_{0.44}\text{MnO}_2$  is maintained in the Et/Di system, indicating that hydrogen-bonding  
8  
9 with the water molecules would be an effective way to improve the cycling stability. This  
10  
11 approach guides a new direction for the development of sodium-ion battery with excellent cycle  
12  
13 life for green and sustainable large-scale practical applications.  
14  
15  
16  
17  
18  
19

## 20 **Results and discussion**

21  
22 Cosolvents of ethanol-water are prepared by mixing the two components in different volume  
23  
24 ratios. For convenience, the various ethanol-water volume ratios used will be denoted as x: y  
25  
26 Et-Di. To investigate the influence of solvent composition on the surface wettability, contact  
27  
28 angles of various ethanol-water solvents were measured and presented in Figure 1a. It can be  
29  
30 found that the presence of ethanol in the solvent system results in a ubiquitous reduction in the  
31  
32 contact angle when compared to that of Di water ( $85.9^\circ$ ). The decrease in contact angle  
33  
34 becomes increasingly pronounced with larger ethanol content. Due to four-coordinations  
35  
36 involving two donor and two acceptor hydrogen bonds, water exhibits a three-dimensional  
37  
38 tetrahedral hydrogen-bonding network. Because of the relatively high attraction among water  
39  
40 molecules through the hydrogen-bonding network, water has high surface tension.<sup>16</sup> By the  
41  
42 introduction of ethanol, new ethanol-water interactions (cross association) occur. The addition  
43  
44 of ethanol in water breaks the water hydrogen-bonding network, resulting in a decrease of the  
45  
46 water-water hydrogen bonds. As a result, the interfacial tension of ethanol-water cosolvent is  
47  
48 decreased, which is consistent with the previous report.<sup>17</sup> Overall, the ethanol-water system  
49  
50 shows a significant improvement in terms of wettability as compared to the Di water system.  
51  
52 From the results, the 5:1 Et-Di system displays the lowest contact angle ( $19.2^\circ$ ) among all  
53  
54 samples. It is predicted that using the 5:1 Et-Di system as electrolyte would allow a better  
55  
56  
57  
58  
59  
60

1  
2  
3 electrode penetration, critical to enhanced electrochemical performances.<sup>18</sup> This will be  
4  
5 verified in later experiments in this paper.  
6  
7

8 In ethanol-water solvents, ethanol readily forms hydrogen bonds with water molecules.<sup>19</sup> To  
9  
10 verify the existence and evaluate the strength of hydrogen bonds in ethanol-water solvents, a  
11  
12 combination of spectroscopy techniques such as confocal Raman, Fourier-transformed  
13  
14 infrared-attenuated total reflectance (FTIR-ATR) and <sup>1</sup>H nuclear magnetic resonance (NMR)  
15  
16 were employed. Figure 1b shows the Raman scattering spectra of Di water and the various  
17  
18 ethanol-water solvents at different volume ratios from 2700 cm<sup>-1</sup> to 4000 cm<sup>-1</sup>, which is the  
19  
20 wavenumber range focusing on the vibrational modes of interest (CH<sub>2</sub>, CH<sub>3</sub> and O-H bonds),  
21  
22 whereas the supplementary lower wavenumber regions are presented in Figure S1. A full  
23  
24 assignment for each peak is detailed in Table S2. As shown in Figure 1b, Di water exhibits  
25  
26 symmetric O-H stretching (~3254 cm<sup>-1</sup>) and asymmetric O-H stretching vibration (~3411 cm<sup>-1</sup>)  
27  
28 modes that form a broad Raman band owing to the abundant hydrogen-bonding  
29  
30 environments among the water molecules.<sup>13, 19-21</sup> Additionally, a weak shoulder peak located  
31  
32 around ~3613 cm<sup>-1</sup> corresponds to the free O-H of water molecules.<sup>19</sup> Upon introduction of  
33  
34 ethanol to the Di water, the peaks attributed to the symmetric (~2878cm<sup>-1</sup>) and asymmetric  
35  
36 (~2971 cm<sup>-1</sup>) stretching modes of CH<sub>3</sub> as well as the CH<sub>2</sub> stretching mode (~2926cm<sup>-1</sup>) of  
37  
38 ethanol start to appear in the ethanol-water spectra.<sup>13</sup> As the volume ratio of ethanol to water  
39  
40 increases, the O-H stretching bands display a distinct reduction in amplitudes, and the shoulder  
41  
42 peak (~3613 cm<sup>-1</sup>; free O-H) weakens until its complete disappearance. These results indicate  
43  
44 that the hydrogen-bonding interactions among water molecules have been significantly  
45  
46 weakened by increasing ethanol content. Meanwhile, the free O-H species activity has been  
47  
48 largely suppressed. Moreover, the stretching modes of CH<sub>2</sub> and CH<sub>3</sub> exhibit redshift towards  
49  
50 the lower wavenumber (Figure S2), indicating the new formation of hydrogen bonds between  
51  
52 ethanol and water associates.<sup>13, 19, 22-23</sup>  
53  
54  
55  
56  
57  
58  
59  
60

1  
2  
3 The effect of hydrogen bonds between ethanol and water molecules was further explored  
4 using FTIR spectroscopy, as displayed in Figures 1c and S3. Since the O-H stretching bands in  
5 IR spectra for Di water overlap with that of ethanol (Figure S3), the water (H-O-H) bending  
6 vibrational band was used instead for evaluating the strength of hydrogen bonds in the various  
7 ethanol-water systems (Figure 1c).<sup>12, 24</sup> As the ethanol concentration increases, the H-O-H  
8 bending vibrational bands exhibit blueshift behavior towards the higher wavenumber region,  
9 indicating that the hydrogen bonds of water hydrogens become stronger.<sup>12</sup> This is possibly due  
10 to the strengthened hydrogen-bonding interactions between water hydrogens and ethanol  
11 oxygens with increasing ethanol content.  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22

23  
24 To further understand the interplay of hydrogen bonds between ethanol and water and  
25 confirm the ratios of the different types of protons associated with the CH<sub>2</sub>, CH<sub>3</sub>, and O-H  
26 groups in the binary co-solvents, we performed <sup>1</sup>H nuclear magnetic resonance (NMR)  
27 measurements. Figures 1d and S4 present the <sup>1</sup>H chemical shifts for the Di water, ethanol, and  
28 binary ethanol-water samples. As shown in Figure 1d, the protons associated with the O-H  
29 group for Di water and ethanol exhibit chemical shift values of 4.77 and 5.86 ppm, respectively.  
30 The O-H peaks for the ethanol-water mixtures show intermediate values of chemical shift,  
31 exhibiting a gradual downfield shift behavior towards higher ppm with increasing ethanol  
32 content. This indicates that the hydrogen atoms on the hydroxyl groups are increasingly  
33 deshielded as the ethanol concentration is increased, which suggests a corresponding increase  
34 in strength of the hydrogen bonds formed in ethanol-water solvents. Among all the binary  
35 solvents investigated, it should be highlighted that the 5:1 Et-Di system depicts the highest  
36 downfield shift (5.28 ppm). It also exhibits the lowest proton ratio number associated with the  
37 O-H group (calculated and presented in Figure 1e and Table S3 using the proton ratios of  
38 hydroxyl with water, CH<sub>2</sub>, and CH<sub>3</sub>).<sup>25</sup> This demonstrates the strong hydrogen-bonding  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60



1  
2  
3 interaction between the ethanol and water molecules in the 5:1 Et-Di system. As such, the 5:1  
4  
5 Et-Di system would be subject to further studies in this paper.  
6  
7

8 Based on the above results, as discussed, the simplified structure models representing the  
9  
10 water-water molecular interactions and ethanol-water (5:1 Et-Di) molecular association are  
11  
12 illustrated in Figure 1f and g, respectively. In the Di water system (Figure 1f), the water  
13  
14 molecules are weakly hydrogen bonded with the presence of free water molecules. On the other  
15  
16 hand, in the binary ethanol-water system (Figure 1g), due to the existence of ethanol, the water-  
17  
18 water bonds are broken, resulting in a reorganized network structure of water molecules  
19  
20 through hydrogen-bonding with the hydroxyl group of ethanol. Meanwhile, the protons of free  
21  
22 water molecules are also hydrogen bonded with ethanol oxygens. Therefore, it is highly  
23  
24 anticipated that the 5:1 Et-Di system could suppress water protons activity and represent an  
25  
26 ideal solvent for electrolytes to be used in ARSIBs, potentially enabling electrode stability and  
27  
28 long-lasting cell cycle life.  
29  
30  
31  
32

33 Manganese-based oxides have been widely employed as active materials for energy storage  
34  
35 due to its high capacity and rate performance.<sup>26-36</sup> In particular,  $\text{Na}_{0.44}\text{MnO}_2$  (NMO) with a  
36  
37 stable tunnel structure is attractive due to its unique large tunnels suitable for sodium  
38  
39 insertion/extraction.<sup>33, 37-40</sup> Therefore, NMO has been chosen as the model cathode material to  
40  
41 evaluate the efficacy of the Et/Di system in enhancing the cell cycling stability for this  
42  
43 study. The NMO was prepared *via* an optimized polyvinylpyrrolidone (PVP)-assisted sol-gel  
44  
45 synthesis method.<sup>35</sup> The crystal structure of the as-synthesized NMO was characterized by X-  
46  
47 ray powder diffraction (XRD). As shown in Figure 2a, the diffraction peaks of the NMO sample  
48  
49 can be well-indexed to the orthorhombic  $\text{Na}_{0.44}\text{MnO}_2$  phase (PDF: 04-018-3147) with *Pbam*  
50  
51 space group, which is in good agreement with a previous report.<sup>34</sup> Based on the Rietveld  
52  
53 structure refinement, the lattice parameters of NMO are found to be  $a = 9.0897(6) \text{ \AA}$ ,  $b =$   
54  
55  $26.427(2) \text{ \AA}$ ,  $c = 2.8250(2) \text{ \AA}$ , with a lattice volume of  $678.60(8) \text{ \AA}^3$ . The structure parameter  
56  
57  
58  
59  
60

1  
2  
3 is summarized in Table S4. The crystal structure of  $\text{Na}_{0.44}\text{MnO}_2$  is shown in the inset of Figure  
4  
5  
6 2a. Three sodium sites can be found within the NMO tunnel-shaped framework formed by the  
7  
8 corner-sharing ( $\text{MnO}_5$ ) and edge-sharing ( $\text{MnO}_6$ ) polyhedrons. One sodium site (Na 1) is  
9  
10 located in the O-shaped tunnels, whereas two sodium sites (Na 2 and Na 3) are situated in the  
11  
12 larger S-shaped tunnels.<sup>26, 29, 33, 38, 41-43</sup> Scanning electron microscopy (SEM) imaging (Figure  
13  
14 2b) further shows the uniformly yielded NMO plates with lengths of 3.0–5.0  $\mu\text{m}$  and widths of  
15  
16 1.5–4.0  $\mu\text{m}$ . In addition, the high-resolution transmission electron microscopy (HRTEM)  
17  
18 image of NMO plates (Figure 2c) exhibits lattice fringe spacings of 0.45 nm, corresponding to  
19  
20 the (200) plane of  $\text{Na}_{0.44}\text{MnO}_2$ , consistent with the XRD analyses.  
21  
22

23  
24 To verify the hypothesis of modifying hydrogen-bonding interactions in ethanol-water  
25  
26 enabling the suppression of water protons activity, 5:1 Et-Di, and De-ionized water systems  
27  
28 were used as electrolytes to test three-electrodes cells with NMO, platinum foil and saturated  
29  
30 silver/silver chloride (Ag/AgCl) as positive, counter and reference electrodes, respectively. 1  
31  
32 M sodium acetate (NaAc) was fully dissolved in varied ethanol-water mixtures to yield  
33  
34 homogeneous electrolytes. Cycling voltammetry (CV) measurement was applied to evaluate  
35  
36 the electrochemical window of 1 M NaAc-Di and -Et/Di electrolytes by using Ti mesh and Pt  
37  
38 counter electrodes in three electrodes configuration. As shown in Figure 3a, the 1 M NaAc-  
39  
40 Et/Di provides a wider electrochemical window than that of 1 M NaAc-Di electrolyte. The  
41  
42 overall electrochemical stability window of 1 M NaAc-Et/Di electrolyte is  $\sim 2.5$  V, which is  
43  
44 larger than that of 1 M NaAc-Di electrolyte ( $\sim 1.8$  V). Ionic conductivity of 1 M NaAc-Et/Di  
45  
46 electrolyte was further measured. The 1 M NaAc-Et/Di electrolyte shows an ionic conductivity  
47  
48 of  $6.01 \text{ mS cm}^{-1}$ . It is 2-11 times higher than those of previously reported ionic liquid-based  
49  
50 electrolytes for Na batteries, such as 1 M  $\text{NaClO}_4$  in butylmethylpyrrolidinium-  
51  
52 bis(trifluoromethanesulfonyl)imide (BMP-TFSI) ionic liquid electrolyte ( $1.00 \text{ mS cm}^{-1}$ ), and  
53  
54 comparable to those of previously reported conventional organic electrolytes for Na batteries  
55  
56  
57  
58  
59  
60

1  
2  
3 (e.g., 1 M NaClO<sub>4</sub> in ethylene carbonate/dimethyl carbonate (EC: DMC, 30:70 wt%) has an  
4 ionic conductivity of ~5.00 mS cm<sup>-1</sup>).<sup>44-48</sup> Then, based on the salt solubility, two more sodium-  
5 based salts sodium chloride (0.1 M NaCl), sodium perchlorate (1 M NaClO<sub>4</sub>) were also fully  
6 dissolved to yield a series of electrolytes. The electrochemical performances of NMOs cycled  
7 in the various electrolytes were evaluated by galvanostatic charge-discharge (GCD)  
8 measurements (Figure S5), and their capacity retentions were recorded in Table S5. As  
9 expected, NMOs have shown superior cycling stability in Et/Di system as compared to that of  
10 the Di water system, regardless of the identity of the dissolved salt component. Specifically,  
11 the NMO cycled in 1 M NaAc-Et/Di electrolyte exhibited the best cycling performance with  
12 high capacity retention up to 99.0 % after 100 cycles.

13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26 Inspired by this observation, a series of electrochemical measurements were further  
27 conducted on NMO cycled in 1 M NaAc-Di and -Et/Di electrolytes to gain insight into the  
28 electrode kinetics. Cyclic voltammetry (CV) measurement was first performed at a scan rate of  
29 0.1 mV s<sup>-1</sup> between -0.4 V to 0.7 V vs. Ag/AgCl. Figures S6 and 3b depict the CV curves of  
30 NMO cycled in 1 M NaAc-Di and -Et/Di electrolytes, respectively. Seven pairs of redox peaks  
31 were found in both systems, corresponding to the de/insertion processes of sodium-ions at the  
32 various sites (Na 1, Na 2, and Na 3), as summarized in Table S6.<sup>38, 42</sup> Notably, in the first  
33 cathodic scan, the redox peaks of NMO cycled in 1 M NaAc-Di are weaker and broader (Figure  
34 S6), as compared to that of NMO cycled in 1 M NaAc-Et/Di (Figure 3b). This is mainly due to  
35 the partial sodium-ions (Na<sup>+</sup>) leakage through the substitution of protons (H<sup>+</sup>) in the Di water  
36 system.<sup>49</sup> From the second cycle onward, the CV profiles of NMO cycled in 1 M NaAc-Di  
37 show a significant reduction of current intensity, especially for redox peak III and peaks (V-  
38 VII) that correspond to the Na 3 and Na 2 sites, respectively.<sup>38, 42</sup> In general, sodium-ions  
39 located at Na 2 and Na 3 sites sharing the S-shaped tunnel would experience higher electrostatic  
40 repulsion than that of the sodium-ions located at Na 1 site in the O-shaped tunnel.<sup>42</sup> Therefore,  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60

1  
2  
3 due to the proton-rich environment, it is postulated that the Di system could have favored the  
4  
5 co-intercalation of protons into the NMO structure, inducing a higher electrostatic repulsion in  
6  
7 S-shaped tunnel, hindering further sodium-ions insertion process, resulting in the poor cycling  
8  
9 stability. In stark contrast, the NMO cycled in 1 M NaAc-Et/Di exhibits overlapping CV curves,  
10  
11 indicating its highly reversible sodium de/insertion process (Figure 3b). This can be attributed  
12  
13 to the suppressed water protons co-insertion. Due to the hydrogen-bond interaction of ethanol  
14  
15 and water, the water activity has been successfully suppressed.  
16  
17

18  
19 Figures 3c and d compare the galvanostatic discharge-charge profiles of NMOs tested in  
20  
21 both 1 M NaAc-Di and 1 M NaAc-Et/Di, respectively. As shown in Figure 3c, the NMO cycled  
22  
23 in 1 M NaAc-Di can deliver an initial discharge capacity of 71.6 mAh g<sup>-1</sup> at 100 mA g<sup>-1</sup>.  
24  
25 Subsequently, it can only maintain a capacity of 55.4 mAh g<sup>-1</sup> after five cycles, with an  
26  
27 irreversible capacity loss of 22.6 %. In contrast, the discharge capacity of NMO cycled in 1 M  
28  
29 NaAc-Et/Di is higher than of those cycled in 1 M NaAc-Di (Figure 3d). More strikingly, the  
30  
31 NMO cycled in 1 M NaAc-Et/Di can maintain a capacity of 76.8 mAh g<sup>-1</sup> after five cycles  
32  
33 without any capacity loss, which is in good agreement with the excellent reversibility indicated  
34  
35 from the overlapping curves as shown in previous CV results. Moreover, similar phenomena  
36  
37 can be found for NMOs tested in 0.1 M NaCl and 1 M NaClO<sub>4</sub> in both electrolyte systems  
38  
39 (Figures S7 and S8), demonstrating the excellent sodium diffusion kinetics of NMO cycled in  
40  
41 Et/Di system. This may be ascribed to the intrinsic hydrogen-bonding interaction between the  
42  
43 water protons and ethanol oxygen in the Et/Di system, which can effectively suppress the water  
44  
45 protons activity.  
46  
47  
48  
49

50  
51 To understand the variation of manganese oxidation state, we performed synchrotron X-ray  
52  
53 absorption near edge structures (XANES) measurement. Figure 3e shows the normalized Mn  
54  
55 K-edge profiles of the first fully discharged NMO electrodes as well as the pristine NMO  
56  
57 electrode and commercial reference powders. The Mn K-edge of the NMO pristine electrode  
58  
59  
60


1  
2  
3 resembles the characteristic absorption edge close to the  $\text{MnO}_2$  ( $\text{Mn}^{4+}$ ) reference powder, which  
4 indicates an average manganese valence state close to +4. On discharge, the Mn K-edge of the  
5 NMOs shift towards the lower energy as core-level binding energy changes with respect to the  
6 atomic valence states, indicating a reduction in the manganese valence state.<sup>50</sup> Interestingly,  
7 NMOs cycled in the two different electrolytes exhibit an apparent difference in the Mn  
8 oxidation state. The Mn K-edge of the fully discharged NMO in 1 M NaAc-Et/Di almost  
9 resembles the characteristic Mn K-edge of the  $\text{Mn}_2\text{O}_3$  ( $\text{Mn}^{3+}$ ) reference powder, indicating an  
10 average manganese valence state close to +3. On the other hand, the Mn K-edge of the fully  
11 discharged NMO in 1 M NaAc-Di exhibits an absorption edge between the characteristic Mn  
12 K-edges of  $\text{MnO}$  ( $\text{Mn}^{2+}$ ) and  $\text{Mn}_2\text{O}_3$  ( $\text{Mn}^{3+}$ ) reference powders, indicating the mixed of +2 and  
13 +3 valence states. The presence of the  $\text{Mn}^{2+}$  species is indicative of the disproportionation  
14 reaction of the trivalent Mn species ( $\text{Mn}^{3+}_s \rightarrow \text{Mn}^{4+}_s + \text{Mn}^{2+}_{\text{aq}}$ ),<sup>30-31, 51</sup> which could lead to Mn  
15 dissolution, resulting in the loss of active material.<sup>42</sup> Therefore, this could be the possible  
16 reason for the drastic capacity fading observed in the NMO when cycled in 1 M NaAc-Di  
17 electrolyte as opposed to a high capacity retention of NMO cycled in 1 M NaAc-Et/Di.  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36

37 The rate capabilities of NMOs cycled in 1 M NaAc-Di and -Et/Di were further studied at  
38 various current densities, as shown in Figure 3f. Notably, NMO cycled in 1 M NaAc-Et/Di  
39 exhibits much better rate capability: 90.8 mAh  $\text{g}^{-1}$  (50 mA  $\text{g}^{-1}$ ), 81.0 mAh  $\text{g}^{-1}$  (100 mA  $\text{g}^{-1}$ ), 67.6  
40 mAh  $\text{g}^{-1}$  (200 mA  $\text{g}^{-1}$ ) and 42.2 mAh  $\text{g}^{-1}$  (500 mA  $\text{g}^{-1}$ ). Moreover, when the current density  
41 returns to 50 mA  $\text{g}^{-1}$ , the capacity recovers well to a high value of 91.6 mAh  $\text{g}^{-1}$ , which is much  
42 higher than those cycled in 1 M NaAc-Di (41.6 mAh  $\text{g}^{-1}$ ), indicating its excellent reversibility.  
43 The long-term cycling stability of NMO plates cycled in different electrolytes are further  
44 examined. As shown in Figure 3g, the NMO electrode cycled in 1 M NaAc-Et/Di displays a  
45 high initial capacity of 76 mAh  $\text{g}^{-1}$  at 100 mA  $\text{g}^{-1}$ . After 100 cycles, the NMO electrode retains  
46 a high reversible capacity of 75 mAh  $\text{g}^{-1}$  with a capacity retention of 99 %, which is > 2 times  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60



1  
2  
3 higher than that in 1 M NaAc-Di (48%). Unexpectedly, the cycling stability is also superior to  
4 that of the “water-in-salt” 9.26 m NaCF<sub>3</sub>SO<sub>3</sub> and 17 m NaClO<sub>4</sub> electrolytes (capacity retention  
5 of 27.4% and 25.6%, respectively). Moreover, even after 1000 cycles, the NMO cycled in 1 M  
6 NaAc-Et/Di exhibit excellent cycling stability with a capacity decay rate per cycle of 0.024%  
7 at 100 mA g<sup>-1</sup>, which is much lower than that of NMO electrode cycled in 1 M NaAc-Di  
8 (0.087%). This can be ascribed to the reduced water protons activity induced by the intrinsic  
9 hydrogen-bonding between the ethanol oxygen and water protons in Et/Di system. Moreover,  
10 the 1 M NaAc in Et/Di electrolyte provides superior wetting characteristics. As displayed in  
11 Figure S9, due to the presence of ethanol, the contact angle of 1 M NaAc in Et/Di electrolyte  
12 on stainless steel is only 22.4°, much lower than that of 1 M NaAc in Di electrolyte (83.3°) and  
13 also lower than that of “water-in-salt” 9.26 m NaCF<sub>3</sub>SO<sub>3</sub> (79.4°) and 17 m NaClO<sub>4</sub> electrolytes  
14 (101.1°), demonstrating the hydrophilic property of 1 M NaAc in Et/Di electrolyte, which can  
15 effectively facilitate the electrolyte penetration into the electrode and thus improve the  
16 electrochemical performance. Therefore, good wettability, excellent rate capability, and long-  
17 term cycling performance make the Et/Di system a promising electrolyte candidate for  
18 applicable ARSIBs.  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39

40 To shed light on the charge storage mechanism of NMOs cycled in the Et/Di and Di systems,  
41 XRD, SEM, and TEM-EDS mapping measurements were conducted after different cycles. In  
42 comparison to the pristine morphology, NMO plates exhibit partial fragmentation with a rough  
43 surface after five cycles when cycled in the Di system, as shown in Figure 4a. As discussed  
44 above in the XANES section, the disproportionation of Mn<sup>3+</sup> leads to the formation of soluble  
45 Mn<sup>2+</sup> species. Thus, NMO suffers a significant capacity loss in the initial cycles due to the  
46 dissolution of electrochemical active NMO in Di system. By contrast, the NMO plate structure  
47 remains a smooth surface after cycled in the Et/Di system (Figure 4b), indicating that the  
48 introduction of ethanol in the electrolyte plays a critical role in stabilizing the NMO electrode  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60

1  
2  
3 structure. *Ex-situ* XRD characterizations were further performed to explore the storage  
4 mechanism of NMO cycled in both Et/Di and Di systems (Figures 4e and S10). As shown in  
5 Figure S10, the NMO still maintains the Na<sub>0.44</sub>MnO<sub>2</sub> (PDF 04-018-3147) phase with *Pbam*  
6 space group when cycled in Di system after 100 cycles, Notably, compared with the pristine  
7 electrode, a broad new diffraction peak located at around 26° appears after 200 cycles, which  
8 can be indexed to MnOOH (PDF 04-010-4788), demonstrating an irreversible de/insertion of  
9 sodium-ions in NMO upon cycling. When cycled after 500 cycles, the product remains a mixed  
10 phase. Eventually, the NMO totally transformed to MnOOH after 1000 cycles, as demonstrated  
11 by the XRD pattern in Figures S10 and 4e. In contrast, all the diffraction peaks of NMO cycled  
12 in Et/Di system after 1000 cycles are still consistent with that of the pristine electrode  
13 Na<sub>0.44</sub>MnO<sub>2</sub> (PDF 04-018-3147), indicating the excellent structure stability of NMO in Et/Di  
14 system. Based on the results, it is proposed that the NMO cycled in the Et/Di system undergoes  
15 reversible desodiation/sodiation processes as described below:



16  
17 In the Di system, sodium-ions and water protons are co-intercalated into the NMO structure  
18 during the discharge process. However, the existence of protons could induce electrostatic  
19 repulsion with sodium-ions in the NMO lattice,<sup>42</sup> which hinders sodium-ions insertion. The  
20 details of the reactions can be formulated as follows:



21  
22 *Ex-situ* TEM, selected area electron diffraction (SAED), and TEM-EDS analysis provide  
23 further proof for the storage mechanism of NMO cycled in both Et/Di and Di system after 1000  
24 cycles. SEM and enlarged TEM images (Figures S11 and 4c) reveal that the product of NMO  
25 cycled in Di system after 1000 cycles is composed of distributed nanorods with widths of 100  
26 nm and lengths of ~1 μm. The diffraction spots in the SAED pattern (Figure S12a) can be  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60

1  
2  
3 indexed to the (-111) and (002) planes of MnOOH. High-resolution TEM (HRTEM) image  
4 taken on the nanorod shows well-resolved lattice fringes with an interplanar distance of 0.34  
5 nm (inset in Figure 4c), corresponding to the (-111) crystal plane of manganese oxhydroxide  
6 (MnOOH), which is consistent with the XRD result. The corresponding TEM-EDS mapping  
7 (Figure S13) reveals the existence of Mn and O elements in the newly formed nanorods,  
8 whereas traces of Na have almost disappeared, further confirming the formation of manganese  
9 oxhydroxide after long-term cycling. As discussed above, the fragmentation is caused by the  
10 dissolution of Mn<sup>2+</sup> species formed during the disproportionation reaction of Mn<sup>3+</sup> when water  
11 protons and sodium-ions co-insert into the structure. As a result, the irreversible protons  
12 insertion causes a steady accumulation of manganese oxhydroxide, leading to poor  
13 electrochemical performance. By contrast, as shown in Figure 4d, the TEM image of NMO  
14 cycled in the Et/Di system reveals that the plate morphology is still well-maintained. SAED  
15 pattern in Figure S12b reveals that the plates are single-crystalline structure with the orientation  
16 along the [001] direction. HR-TEM image (inset of Figure 4d) displays a lattice spacing of 0.45  
17 nm, corresponding to the (200) plane of Na<sub>0.44</sub>MnO<sub>2</sub>. The TEM-EDS elemental mapping  
18 images of NMO cycled in the Et/Di system further demonstrate the uniform distribution of Mn,  
19 O, and especially Na elements in the cycled NMO (Figure 4f).

20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42 In addition, the Et/Di hybrid electrolyte can be applied in a wide temperature range. As  
43 demonstrated, the Na<sub>0.44</sub>MnO<sub>2</sub>/Zn full cells in 1 M NaAc-Et/Di electrolyte were assembled and  
44 cycled between 0.65 and 1.75 V at 25 °C and 0 °C, as shown in Figure 5. It delivers a high  
45 discharge capacity of 93 mAh g<sup>-1</sup> on the 2<sup>nd</sup> cycle at 25 °C, corresponding to a high energy  
46 density of 102 Wh kg<sup>-1</sup> (Figure 5a). It also exhibits excellent cycling stability with a high  
47 capacity retention of 99.8% after 50 cycles at 100 mA g<sup>-1</sup> (Figure 5b). Moreover, the full cell  
48 displays good rate capability (Figure 5c). As the current density increases to 500 mA g<sup>-1</sup>, the  
49 discharge capacity of the NMO remains at 42.7 mAh g<sup>-1</sup>. When the current density returns to  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60



1  
2  
3 100 mA g<sup>-1</sup>, the discharge capacity recovers to 90.2 mAh g<sup>-1</sup>, demonstrating its good rate  
4  
5 capability. When further tested at 0 °C, the full cell retains a discharge capacity of 44.5 mAh  
6  
7 g<sup>-1</sup> after 50 cycles with a capacity retention of 94% at 50 mA g<sup>-1</sup> (Figure 5d). Compared with  
8  
9 the recently reported sodium-ion batteries (Figure 5e), the full cell exhibits impressive energy  
10  
11 density (102 Wh kg<sup>-1</sup>).<sup>5, 52-58</sup>

12  
13  
14  
15 Herein, we discuss the reason accounting for the much higher cycling stability and rate  
16  
17 capability of NMO cycled in the Et/Di system. The ions storage and structural evolution of  
18  
19 NMO cycled in Et/Di and Di systems are displayed schematically in Scheme 1. Owing to the  
20  
21 hydrogen-bonding interactions in Et/Di system, most of the proton atoms in water molecules  
22  
23 are strongly bonded with the hydroxyl oxygens in ethanol (Scheme 1a). In contrast, abundant  
24  
25 water molecules exist in Di system, providing a proton-rich environment (Scheme 1b). During  
26  
27 the sodiation process, not only the Na ions, protons can co-insert into the tunnels of the NMO  
28  
29 electrode. Then, NMO suffers the dissolution of Mn<sup>2+</sup> induced by disproportionation reaction  
30  
31 and irreversible phase transformation to MnOOH (Scheme 1b). This explains the rapid capacity  
32  
33 fading and poor cycling stability of NMO in Di water system. In contrast, in Et/Di system,  
34  
35 water protons activity has been effectively suppressed by the existing hydrogen bonds with  
36  
37 ethanol oxygens (Scheme 1a). Therefore, Na ions can reversibly de/insert into the NMO  
38  
39 structure, resulting in much higher cycling stability and rate capability.  
40  
41  
42  
43  
44  
45  
46  
47

## 48 **Conclusions**

49  
50 In summary, we reported a novel type of ethanol-water system for hybrid electrolyte  
51  
52 formulations. Coupled with different low concentrated sodium-based salts, such green and low-  
53  
54 cost electrolytes enable Na-ion chemistry with superior electrochemical performances,  
55  
56 especially in terms of cycling stability. Benefiting from the formation of hydrogen-bonding  
57  
58 interactions, the introduction of ethanol improves surface wettability, suppresses water protons  
59  
60

1  
2  
3 activities, and reduces transition metal dissolution from the cathode, facilitating highly  
4 reversible sodium-ion de/intercalation processes in a wide temperature range. This hybrid  
5 electrolyte enables  $\text{Na}_{0.44}\text{MnO}_2$  electrodes to achieve a high capacity of  $81 \text{ mAh g}^{-1}$  and  
6 excellent cycling stability with a capacity decay rate per cycle of  $0.024\%$  at  $100 \text{ mA g}^{-1}$  for  
7 1000 cycles, four times better than that in the water-based electrolyte. Additionally, compared  
8 with the irreversible phase transformation from  $\text{Na}_{0.44}\text{MnO}_2$  to  $\text{MnOOH}$  when cycled in the  
9 water-based electrolyte, the  $\text{Na}_{0.44}\text{MnO}_2$  still maintains its original phase when cycled in the  
10 ethanol-water system, further confirming its structural stability. Overall, we have demonstrated  
11 the strategy of hydrogen bonded hybridization creates novel electrolyte systems that enable  
12 vastly improved electrochemical performances and may open doors for greener electrolytes in  
13 aqueous rechargeable sodium-ion batteries and others.  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60

## Acknowledgments

The authors wish to acknowledge financial support from by National Research Foundation of Singapore (NRF) Investigatorship award number NRFI2017-08/NRF2016NRF-NRFI001-22.

This research used the Beamline 28-ID-2 X-ray powder diffraction (XPD) of the National Synchrotron Light Source II, a U.S. Department of Energy (DOE) Office of Science User Facility operated for the DOE Office of Science by Brookhaven National Laboratory under Contract No. DE-SC0012704. The authors thank Synchrotron Light Research Institute (Public Organization), Muang, Nakhon Ratchasima, 30000, Thailand, for XANES measurements in Beamline 5.2. Rodney Chua and Yi Cai contributed equally to this work.

## Supporting Information

Experimental section; Cost comparison of various electrolytes based on different salts; Raman scattering spectra of pure water and ethanol-water co-solvents and the corresponding mode of vibrations; FTIR-ATR absorption spectra and NMR chemical shifts of water-ethanol co-solvents; Calculated integrated proton ratios in the pure ethanol and ethanol-water co-solvents; Occupancy of each atomic site refined by the Rietveld method of the as-synthesized NMO; Electrochemical performances of the NMO; Contact angles of different electrolytes; *Ex-situ* XRD, SEM images, SAED patterns, TEM-EDS elemental mappings of cycled NMO products

## References

- (1) Demir-Cakan, R.; Palacin, M. R.; Croguennec, L. Rechargeable Aqueous Electrolyte Batteries: From Univalent to Multivalent Cation Chemistry. *J. Mater. Chem. A* **2019**, *7* (36), 20519-20539.
- (2) Huang, J.; Guo, Z.; Ma, Y.; Bin, D.; Wang, Y.; Xia, Y. Recent Progress of Rechargeable Batteries Using Mild Aqueous Electrolytes. *Small Methods* **2019**, *3* (1), 1800272.

- 1  
2  
3 (3) Yamada, Y.; Wang, J.; Ko, S.; Watanabe, E.; Yamada, A. Advances and Issues in  
4 Developing Salt-Concentrated Battery Electrolytes. *Nat. Energy* **2019**, *4* (4), 269-280.  
5  
6  
7 (4) Kim, H.; Hong, J.; Park, K.-Y.; Kim, H.; Kim, S.-W.; Kang, K. Aqueous Rechargeable Li  
8 and Na Ion Batteries. *Chem. Rev.* **2014**, *114* (23), 11788-11827.  
9  
10  
11 (5) Suo, L.; Borodin, O.; Wang, Y.; Rong, X.; Sun, W.; Fan, X.; Xu, S.; Schroeder, M. A.;  
12 Cresce, A. V.; Wang, F. "Water-in-Salt" Electrolyte Makes Aqueous Sodium-Ion Battery Safe,  
13 Green, and Long-Lasting. *Adv. Energy Mater.* **2017**, *7* (21), 1701189.  
14  
15  
16 (6) Kühnel, R.-S.; Reber, D.; Battaglia, C. A High-Voltage Aqueous Electrolyte for Sodium-  
17 Ion Batteries. *ACS Energy Letters* **2017**, *2* (9), 2005-2006.  
18  
19  
20 (7) Nakamoto, K.; Sakamoto, R.; Sawada, Y.; Ito, M.; Okada, S. Over 2 V Aqueous Sodium-  
21 Ion Battery with Prussian Blue-Type Electrodes. *Small Methods* **2019**, *3* (4), 1800220.  
22  
23  
24 (8) Zheng, Q.; Miura, S.; Miyazaki, K.; Ko, S.; Watanabe, E.; Okoshi, M.; Chou, C. P.;  
25 Nishimura, Y.; Nakai, H.; Kamiya, T. Sodium - and Potassium -Hydrate Melts Containing  
26 Asymmetric Imide Anions for High-Voltage Aqueous Batteries. *Angew. Chem. Int. Ed.* **2019**,  
27 14202-14207.  
28  
29  
30 (9) Fecko, C. J.; Loparo, J. J.; Roberts, S. T.; Tokmakoff, A. Local Hydrogen Bonding  
31 Dynamics and Collective Reorganization in Water: Ultrafast Infrared Spectroscopy of  
32 HOD/D<sub>2</sub>O. *J. Chem. Phys.* **2005**, *122* (5), 054506.  
33  
34  
35 (10) Mohsen-Nia, M.; Amiri, H.; Jazi, B. Dielectric Constants of Water, Methanol, Ethanol,  
36 Butanol and Acetone: Measurement and Computational Study. *J. Solution Chem.* **2010**, *39* (5),  
37 701-708.  
38  
39  
40 (11) Lide, D. R. *Crc Handbook of Chemistry and Physics*, CRC press: Washington, DC, **2004**;  
41 Vol. 85, pp 15-16.  
42  
43  
44 (12) Mizuno, K.; Miyashita, Y.; Shindo, Y.; Ogawa, H. NMR and FT-IR Studies of Hydrogen  
45 Bonds in Ethanol-Water Mixtures. *J. Phys. Chem.* **1995**, *99* (10), 3225-3228.  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60

- 1  
2  
3 (13) Burikov, S.; Dolenko, T.; Patsaeva, S.; Starokurov, Y.; Yuzhakov, V. Raman and IR  
4 Spectroscopy Research on Hydrogen Bonding in Water–Ethanol Systems. *Mol. Phys.* **2010**,  
5 *108* (18), 2427-2436.  
6  
7  
8  
9  
10 (14) Nose, A.; Hojo, M.; Ueda, T. Effects of Salts, Acids, and Phenols on the Hydrogen-  
11 Bonding Structure of Water– Ethanol Mixtures. *J. Phys. Chem. B* **2004**, *108* (2), 798-804.  
12  
13 (15) Meng, L. Ethanol in Automotive Applications. *Ethanol*; Elsevier: Tempe, Arizona, **2019**;  
14 pp 289-303.  
15  
16  
17  
18 (16) Wu, N.; Li, X.; Liu, S.; Zhang, M.; Ouyang, S. Effect of Hydrogen Bonding on the Surface  
19 Tension Properties of Binary Mixture (Acetone-Water) by Raman Spectroscopy. *Appl. Sci.*  
20 **2019**, *9* (6), 1235.  
21  
22  
23 (17) Ghoufi, A.; Artzner, F.; Malfreyt, P. Physical Properties and Hydrogen-Bonding Network  
24 of Water–Ethanol Mixtures from Molecular Dynamics Simulations. *J. Phys. Chem. B* **2016**,  
25 *120* (4), 793-802.  
26  
27  
28 (18) Dou, Q.; Lu, Y.; Su, L.; Zhang, X.; Lei, S.; Bu, X.; Liu, L.; Xiao, D.; Chen, J.; Shi, S. A  
29 Sodium Perchlorate-Based Hybrid Electrolyte with High Salt-to-Water Molar Ratio for Safe  
30 2.5 V Carbon-Based Supercapacitor. *Energy Storage Mater.* **2019**, *23*, 603-609.  
31  
32  
33 (19) Li, F.; Men, Z.; Li, S.; Wang, S.; Li, Z.; Sun, C. Study of Hydrogen Bonding in Ethanol-  
34 Water Binary Solutions by Raman Spectroscopy. *Spectrochim. Acta A* **2018**, *189*, 621-624.  
35  
36  
37 (20) Scherer, J. R.; Go, M. K.; Kint, S. Raman Spectra and Structure of Water from -10 to 90.  
38 Deg. *J. Phys. Chem.* **1974**, *78* (13), 1304-1313.  
39  
40  
41 (21) Giguère, P. A. Bifurcated Hydrogen Bonds in Water. *J. Raman Spectrosc.* **1984**, *15* (5),  
42 354-359.  
43  
44  
45 (22) Du, Q.; Freysz, E.; Shen, Y. R. Vibrational Spectra of Water Molecules at Quartz/Water  
46 Interfaces. *Phys. Rev. Lett.* **1994**, *72* (2), 238.  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60

- 1  
2  
3 (23) Nose, A.; Hojo, M. Hydrogen Bonding of Water–Ethanol in Alcoholic Beverages. *J.*  
4 *Biosci. and Bioeng.* **2006**, *102* (4), 269-280.  
5  
6  
7 (24) Falk, M. The Frequency of the H-O-H Bending Fundamental in Solids and Liquids.  
8 *Spectrochim. Acta A* **1984**, *40* (1), 43-48.  
9  
10 (25) Demir, A., Nmr-the Basic Principles and Its Use in Studies of Water/Ethanol/Mixture.  
11 Bachelor Degree Thesis, Umeå University, April **2012**.  
12  
13 (26) Wang, Y.; Liu, J.; Lee, B.; Qiao, R.; Yang, Z.; Xu, S.; Yu, X.; Gu, L.; Hu, Y.-S.; Yang,  
14 W. Ti-Substituted Tunnel-Type Na<sub>0.44</sub>MnO<sub>2</sub> Oxide as a Negative Electrode for Aqueous  
15 Sodium-Ion Batteries. *Nat. Commun.* **2015**, *6* (1), 1-10.  
16  
17 (27) Jiang, C.; Tang, Z.; Wang, S.; Zhang, Z. A Truncated Octahedral Spinel LiMn<sub>2</sub>O<sub>4</sub> as High-  
18 Performance Cathode Material for Ultrafast and Long-Life Lithium-Ion Batteries. *J. Power*  
19 *Sources* **2017**, *357*, 144-148.  
20  
21 (28) Jiang, L.; Wu, Z.; Wang, Y.; Tian, W.; Yi, Z.; Cai, C.; Jiang, Y.; Hu, L. Ultrafast Zinc-  
22 Ion Diffusion Ability Observed in 6.0-Nanometer Spinel Nanodots. *ACS nano* **2019**, *13* (9),  
23 10376-10385.  
24  
25 (29) Kim, D. J.; Ponraj, R.; Kannan, A. G.; Lee, H.-W.; Fathi, R.; Ruffo, R.; Mari, C. M.; Kim,  
26 D. K. Diffusion Behavior of Sodium Ions in Na<sub>0.44</sub>MnO<sub>2</sub> in Aqueous and Non-Aqueous  
27 Electrolytes. *J. Power Sources* **2013**, *244*, 758-763.  
28  
29 (30) Doeff, M. M.; Anapolsky, A.; Edman, L.; Richardson, T. J.; De Jonghe, L. A High-Rate  
30 Manganese Oxide for Rechargeable Lithium Battery Applications. *J. Electrochem. Soc.* **2001**,  
31 *148* (3), A230-A236.  
32  
33 (31) Cao, Y.; Xiao, L.; Wang, W.; Choi, D.; Nie, Z.; Yu, J.; Saraf, L. V.; Yang, Z.; Liu, J.  
34 Reversible Sodium Ion Insertion in Single Crystalline Manganese Oxide Nanowires with Long  
35 Cycle Life. *Adv. Mater.* **2011**, *23* (28), 3155-3160.  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60

1  
2  
3 (32) Ma, G.; Zhao, Y.; Huang, K.; Ju, Z.; Liu, C.; Hou, Y.; Xing, Z. Effects of the Starting  
4 Materials of Na<sub>0.44</sub>MnO<sub>2</sub> Cathode Materials on Their Electrochemical Properties for Na-Ion  
5 Batteries. *Electrochim. Acta* **2016**, *222*, 36-43.  
6  
7

8  
9  
10 (33) Sauvage, F.; Laffont, L.; Tarascon, J.-M.; Baudrin, E. Study of the Insertion/Deinsertion  
11 Mechanism of Sodium into Na<sub>0.44</sub>MnO<sub>2</sub>. *Inorg. Chem.* **2007**, *46* (8), 3289-3294.  
12  
13

14 (34) Akimoto, J.; Hayakawa, H.; Kijima, N.; Awaka, J.; Funabiki, F. Single-Crystal Synthesis  
15 and Structure Refinement of Na<sub>0.44</sub>MnO<sub>2</sub>, *Solid State Phenom*, **2011**, *170*, 198-202.  
16  
17

18 (35) Chua, R.; Cai, Y.; Kou, Z. K.; Satish, R.; Ren, H.; Chan, J. J.; Zhang, L.; Morris, S. A.;  
19 Bai, J.; Srinivasan, M. 1.3 V Superwide Potential Window Sponsored by Na-Mn-O Plates as  
20 Cathodes Towards Aqueous Rechargeable Sodium-Ion Batteries. *Chem. Eng. J.* **2019**, *370*,  
21 742-748.  
22  
23  
24  
25  
26  
27

28 (36) Jiang, C.; Wang, S.; Li, Y.; Zhang, Z.; Tang, Z. A Layered-Spinel Lithium Manganite  
29 Hydrate for High-Capacity and Ultrafast Lithium Storage. *J. Power Sources* **2019**, *413*, 441-  
30 448.  
31  
32  
33  
34

35 (37) Whitacre, J.; Tevar, A.; Sharma, S. Na<sub>4</sub>Mn<sub>9</sub>O<sub>18</sub> as a Positive Electrode Material for an  
36 Aqueous Electrolyte Sodium-Ion Energy Storage Device. *Electrochem. Commun.* **2010**, *12* (3),  
37 463-466.  
38  
39  
40  
41

42 (38) Ma, G.; Zhao, Y.; Huang, K.; Ju, Z.; Liu, C.; Hou, Y.; Xing, Z. Effects of the Starting  
43 Materials of Na<sub>0.44</sub>MnO<sub>2</sub> Cathode Materials on Their Electrochemical Properties for Na-Ion  
44 Batteries. *Electrochim. Acta* **2016**, *222*, 36-43.  
45  
46  
47

48 (39) Wang, Y.; Wu, Z.; Jiang, L.; Tian, W.; Zhang, C.; Cai, C.; Hu, L. A Long-Lifespan,  
49 Flexible Zinc-Ion Secondary Battery Using a Paper-Like Cathode from Single-Atomic Layer  
50 MnO<sub>2</sub> Nanosheets. *Nanoscale Advances* **2019**, *1* (11), 4365-4372.  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60


- 1  
2  
3 (40) Zhao, Y.; Hu, L.; Zhao, S.; Wu, L. Preparation of  $\text{MnCo}_2\text{O}_4@\text{Ni}(\text{OH})_2$  Core–Shell  
4 Flowers for Asymmetric Supercapacitor Materials with Ultrahigh Specific Capacitance. *Adv.*  
5 *Funct. Mater.* **2016**, *26* (23), 4085-4093.  
6  
7  
8  
9  
10 (41) Chu, Q.; Wang, X.; Li, Q.; Liu, X. The Tunnel Manganese Oxide  $\text{Na}_{4.32}\text{Mn}_9\text{O}_{18}$ : A New  
11  $\text{Na}^+$  Site Discovered by Single-Crystal X-Ray Diffraction. *Acta Crystallogr. Sect. C: Cryst.*  
12 *Struct. Commun.* **2011**, *67* (2), i10-i12.  
13  
14  
15  
16 (42) Kim, H.; Kim, D. J.; Seo, D.-H.; Yeom, M. S.; Kang, K.; Kim, D. K.; Jung, Y. Ab Initio  
17 Study of the Sodium Intercalation and Intermediate Phases in  $\text{Na}_{0.44}\text{MnO}_2$  for Sodium-Ion  
18 Battery. *Chem. Mater.* **2012**, *24* (6), 1205-1211.  
19  
20  
21  
22  
23 (43) Momma, K.; Izumi, F. Vesta 3 for Three-Dimensional Visualization of Crystal,  
24 Volumetric and Morphology Data. *J. Appl. Crystallogr.* **2011**, *44* (6), 1272-1276  
25  
26  
27  
28 (44) Wongittharom, N.; Wang, C.-H.; Wang, Y.-C.; Yang, C.-H.; Chang, J.-K. Ionic Liquid  
29 Electrolytes with Various Sodium Solutes for Rechargeable  $\text{Na}/\text{NaFePO}_4$  Batteries Operated  
30 at Elevated Temperatures. *ACS Appl. Mater.* **2014**, *6* (20), 17564-17570.  
31  
32  
33  
34 (45) Wang, C.-H.; Yeh, Y.-W.; Wongittharom, N.; Wang, Y.-C.; Tseng, C.-J.; Lee, S.-W.;  
35 Chang, W.-S.; Chang, J.-K. Rechargeable  $\text{Na}/\text{Na}_{0.44}\text{MnO}_2$  Cells with Ionic Liquid Electrolytes  
36 Containing Various Sodium Solutes. *J. Power Sources* **2015**, *274*, 1016-1023.  
37  
38  
39  
40 (46) Hasa, I.; Passerini, S.; Hassoun, J. Characteristics of an Ionic Liquid Electrolyte for  
41 Sodium-Ion Batteries. *J. Power Sources* **2016**, *303*, 203-207.  
42  
43  
44  
45 (47) Ding, C.; Nohira, T.; Kuroda, K.; Hagiwara, R.; Fukunaga, A.; Sakai, S.; Nitta, K.;  
46 Inazawa, S.  $\text{NaFSA}-\text{C1C3pyrFSA}$  Ionic Liquids for Sodium Secondary Battery Operating over  
47 a Wide Temperature Range. *J. Power Sources* **2013**, *238*, 296-300.  
48  
49  
50  
51 (48) Bhide, A.; Hofmann, J.; Dürr, A. K.; Janek, J.; Adelhelm, P. Electrochemical Stability of  
52 Non-Aqueous Electrolytes for Sodium-Ion Batteries and Their Compatibility with  $\text{Na}_{0.7}\text{CoO}_2$ .  
53 *Phys. Chem. Chem. Phys.* **2014**, *16* (5), 1987-1998.  
54  
55  
56  
57  
58  
59  
60




- 1  
2  
3 (49) Dall'Asta, V.; Buchholz, D.; Chagas, L. G.; Dou, X.; Ferrara, C.; Quartarone, E.; Tealdi,  
4 C.; Passerini, S. Aqueous Processing of  $\text{Na}_{0.44}\text{MnO}_2$  Cathode Material for the Development of  
5 Greener Na-Ion Batteries. *ACS Appl. Mater.* **2017**, *9* (40), 34891-34899.  
6  
7  
8  
9  
10 (50) Chalmin, E.; Farges, F.; Brown, G. E. A Pre-Edge Analysis of Mn K-Edge Xanes Spectra  
11 to Help Determine the Speciation of Manganese in Minerals and Glasses. *Contrib. Mineral.*  
12 *Petrol.* **2009**, *157* (1), 111-126.  
13  
14  
15  
16 (51) Huang, J.; Guo, Z.; Dong, X.; Bin, D.; Wang, Y.; Xia, Y. Low-Cost and High Safe  
17 Manganese-Based Aqueous Battery for Grid Energy Storage and Conversion. *Sci. Bull.* **2019**,  
18 *64* (23), 1780-1787.  
19  
20  
21  
22  
23 (52) Kumar, P. R.; Jung, Y. H.; Wang, J. E.; Kim, D. K.  $\text{Na}_3\text{V}_2\text{O}_2(\text{PO}_4)_2\text{F}$ -MWCNT  
24 Nanocomposites as a Stable and High Rate Cathode for Aqueous and Non-Aqueous Sodium-  
25 Ion Batteries. *J. Power Sources* **2016**, *324*, 421-427.  
26  
27  
28  
29  
30 (53) Wu, X.; Cao, Y.; Ai, X.; Qian, J.; Yang, H. A Low-Cost and Environmentally Benign  
31 Aqueous Rechargeable Sodium-Ion Battery Based on  $\text{NaTi}_2(\text{PO}_4)_3$ - $\text{Na}_2\text{NiFe}(\text{CN})_6$   
32 Intercalation Chemistry. *Electrochem. Commun.* **2013**, *31*, 145-148.  
33  
34  
35  
36  
37 (54) Wang, L.-P.; Wang, P.-F.; Wang, T.-S.; Yin, Y.-X.; Guo, Y.-G.; Wang, C.-R. Prussian  
38 Blue Nanocubes as Cathode Materials for Aqueous Na-Zn Hybrid Batteries. *J. Power Sources*  
39 **2017**, *355*, 18-22.  
40  
41  
42  
43  
44 (55) Li, Z.; Ravnsbæk, D. B.; Xiang, K.; Chiang, Y.-M.  $\text{Na}_3\text{Ti}_2(\text{PO}_4)_3$  as a Sodium-Bearing  
45 Anode for Rechargeable Aqueous Sodium-Ion Batteries. *Electrochem. Commun.* **2014**, *44*, 12-  
46 15.  
47  
48  
49  
50  
51 (56) Nakamoto, K.; Kano, Y.; Kitajou, A.; Okada, S. Electrolyte Dependence of the  
52 Performance of a  $\text{Na}_2\text{FeP}_2\text{O}_7//\text{NaTi}_2(\text{PO}_4)_3$  Rechargeable Aqueous Sodium-Ion Battery. *J.*  
53 *Power Sources* **2016**, *327*, 327-332.  
54  
55  
56  
57  
58  
59  
60

1  
2  
3 (57) Liu, Y.; Zhang, B.; Xiao, S.; Liu, L.; Wen, Z.; Wu, Y. A Nanocomposite of MoO<sub>3</sub> Coated  
4 with PPy as an Anode Material for Aqueous Sodium Rechargeable Batteries with Excellent  
5 Electrochemical Performance. *Electrochim. Acta* **2014**, *116*, 512-517.  
6  
7


8  
9  
10 (58) Pasta, M.; Wessells, C. D.; Liu, N.; Nelson, J.; McDowell, M. T.; Huggins, R. A.; Toney,  
11 M. F.; Cui, Y. Full Open-Framework Batteries for Stationary Energy Storage. *Nat. Commun.*  
12 **2014**, *5* (1), 1-9.  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60

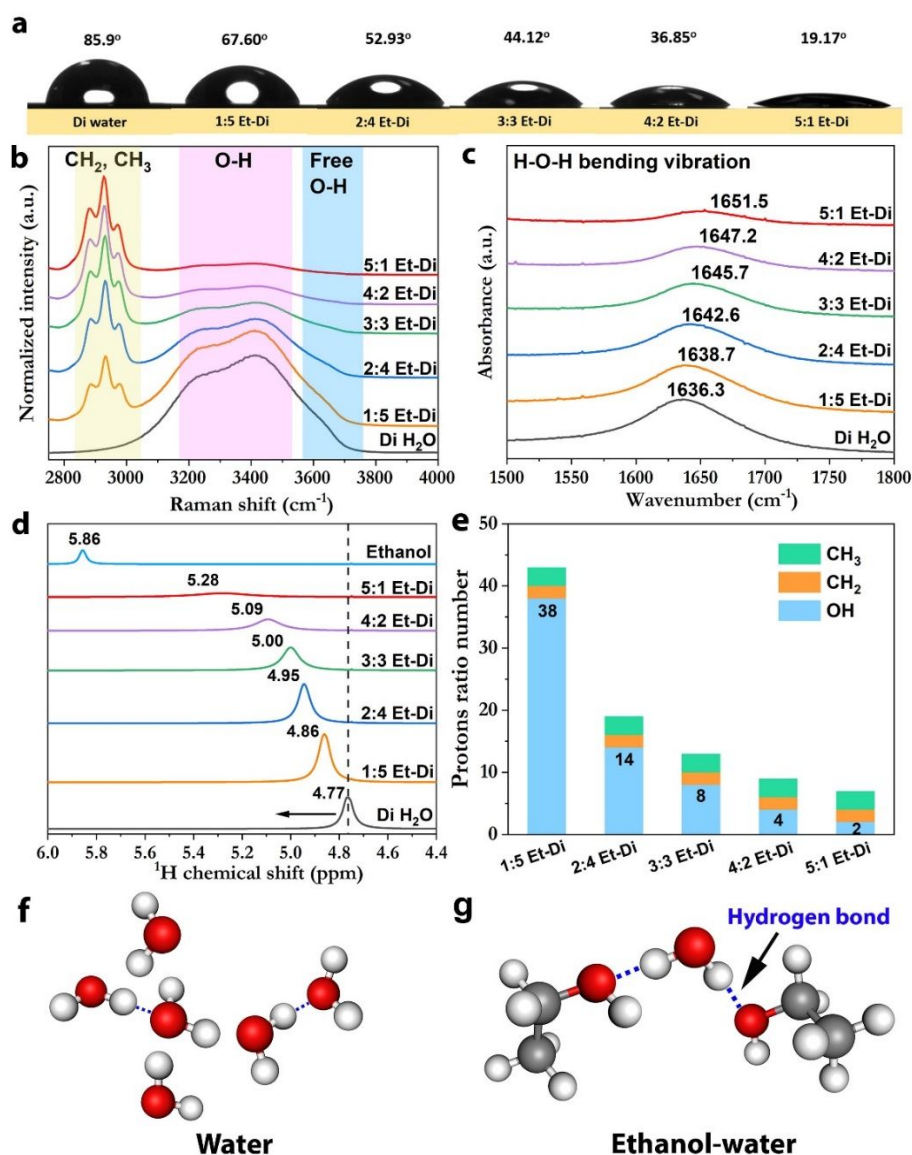


**Figure 1.** The bulk properties of the ethanol-water system with different concentrations. (a) Contact angles comparison, (b) confocal Raman and (c) Fourier transform infrared red-attenuated total reflectance (FTIR-ATR) spectra of water and ethanol-water solvents, (d) chemical shifts for <sup>1</sup>H nuclei in Di water, ethanol and ethanol-water solvents, (e) integrated proton ratio number of protons in the different hydrogen atoms environment (CH<sub>2</sub>, CH<sub>3</sub>, OH) of ethanol-water solvents and schematics of (f) water and (g) ethanol-water intermolecular interactions.

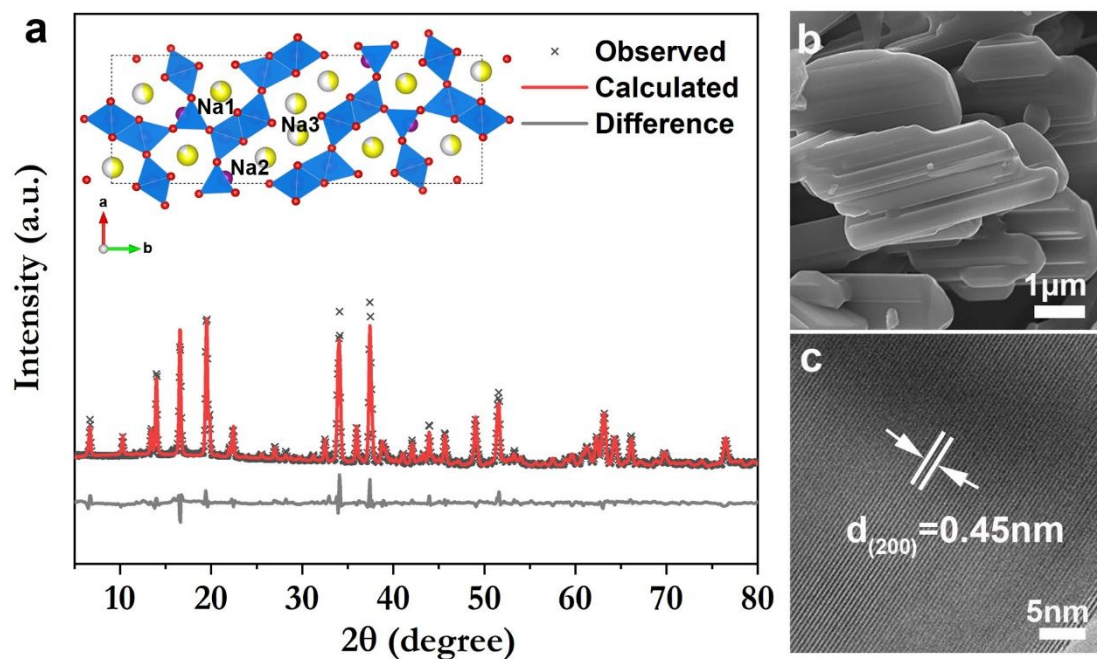


**Figure 2.** Structural characterizations of  $\text{Na}_{0.44}\text{MnO}_2$ . (a) High-resolution synchrotron-based XRD powder diffraction of  $\text{Na}_{0.44}\text{MnO}_2$  plates with its corresponding unit cell (inset of a), (b) SEM image, and (c) high-resolution TEM (HRTEM) image of NMO plates.

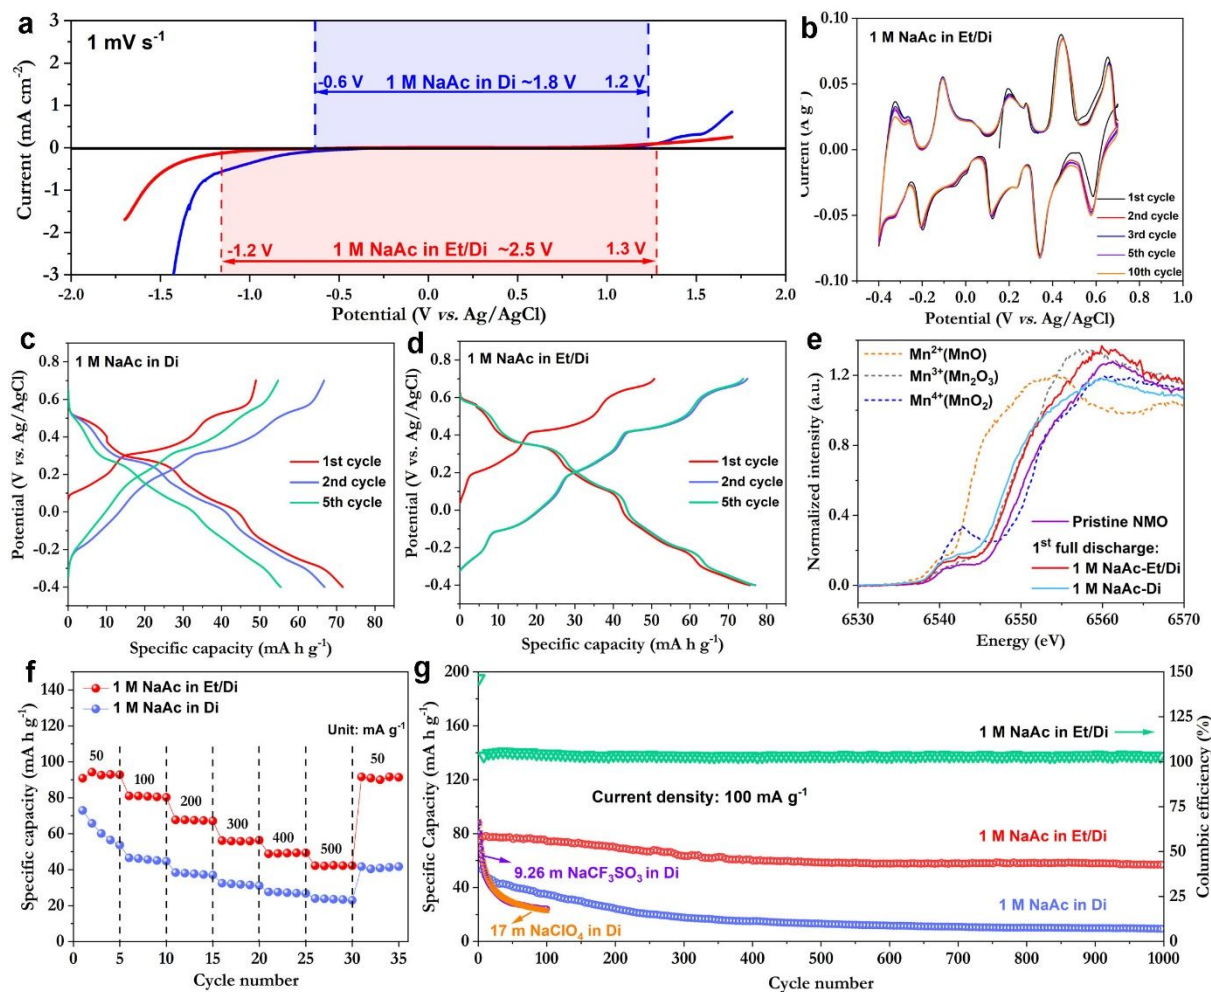


**Figure 3.** Electrochemical performances of the  $\text{Na}_{0.44}\text{MnO}_2$  plates in different electrolytes. (a) Electrochemical stability of 1 M NaAc in Et/Di and 1 M NaAc in Di electrolytes. Cyclic voltammetry profiles of NMO cycled in (b) 1 M NaAc-Et/Di, typical galvanostatic charge-discharge profiles (1<sup>st</sup>, 2<sup>nd</sup> and 5<sup>th</sup> cycles) of NMO cycled in (c) 1 M NaAc-Di and (d) 1 M NaAc-Et/Di, (e) XANES curves of NMOs in pristine and full discharge states, (f) rate capability comparison and (g) long term cycling performances of NMOs at  $100 \text{ mA g}^{-1}$ .

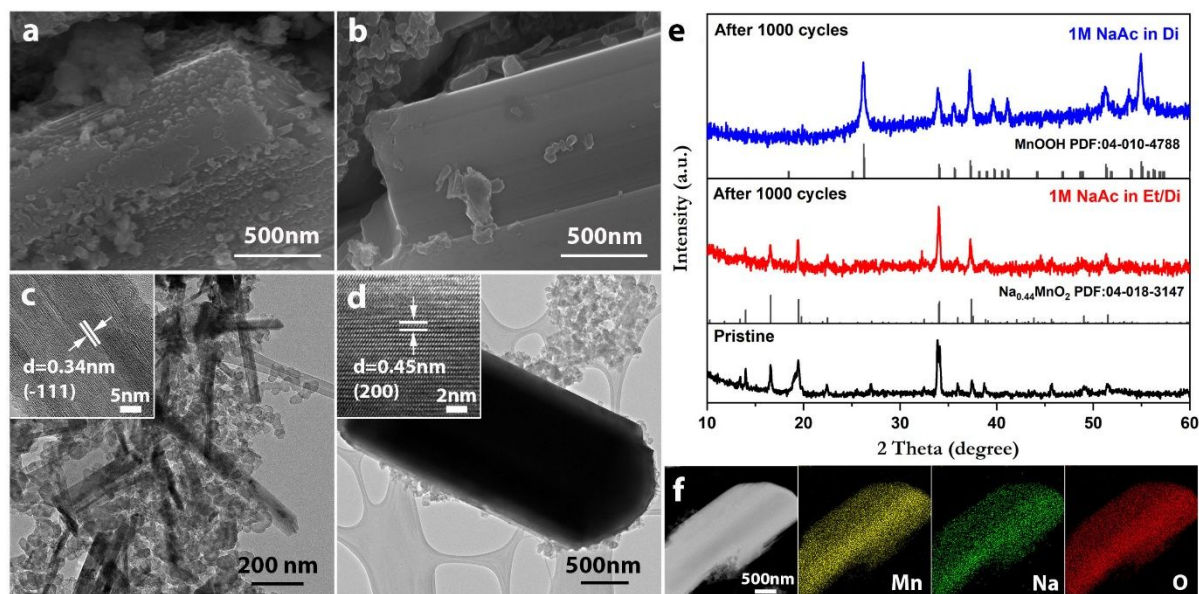

**Figure 4.** Postmortem characterizations of cycled  $\text{Na}_{0.44}\text{MnO}_2$  electrodes. (a, b) SEM images of NMO electrodes cycled in 1 M NaAc in Di, and 1 M NaAc in Et/Di after 5 cycles, respectively, (c, d) TEM and HRTEM (inset) images of NMO cycled in 1 M NaAc in Di, and 1 M NaAc in Et/Di after 1000 cycles, respectively, (e) XRD patterns of pristine and cycled electrodes, and (f) TEM-EDS elemental mappings of NMO cycled in 1 M NaAc in Et/Di after 1000 cycles.

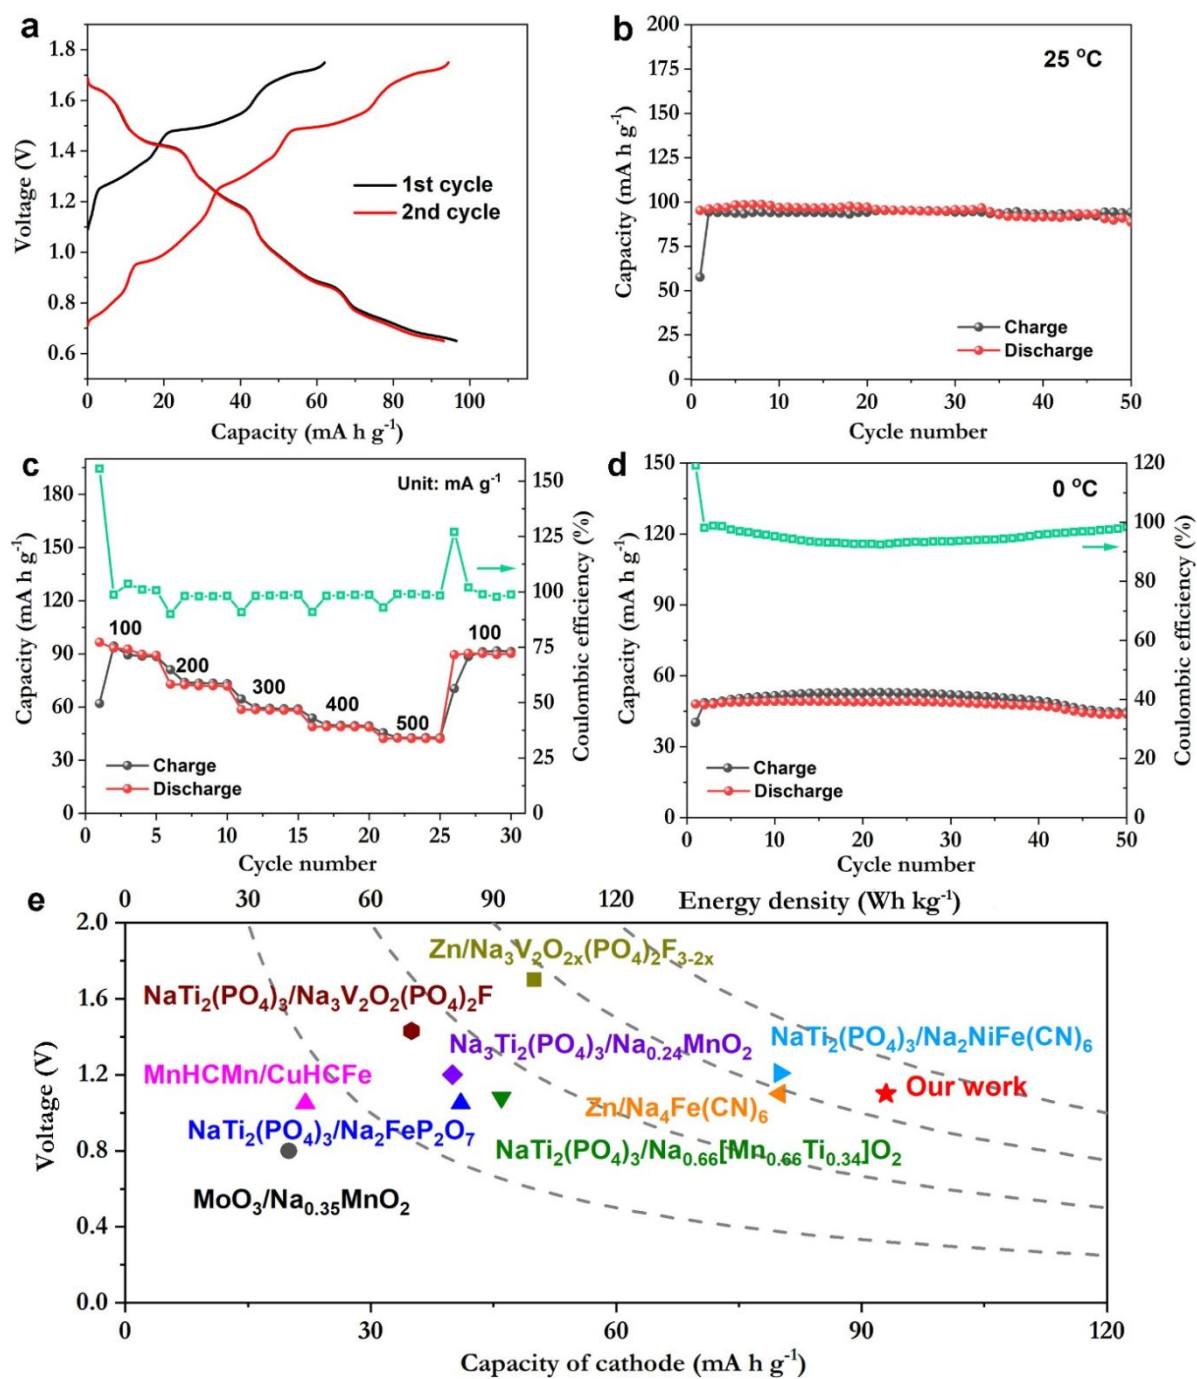

**Figure 5.** Electrochemical performances of Na<sub>0.44</sub>MnO<sub>2</sub>/Zn full cells in 1 M NaAc in Et/Di electrolyte. a) Charge-discharge profiles at 100 mA g<sup>-1</sup>, b) cycling stability of full cell at 100 mA g<sup>-1</sup> at 25 °C, c) rate capability, and d) cycling stability of full cell at 0 °C. The cells were cycled within the voltage range of 0.65 to 1.75 V. e) Comparison of capacity and energy density reported for aqueous sodium-ion batteries. (Energy densities are calculated based on the cathode from the reported papers)<sup>5, 52-58</sup>

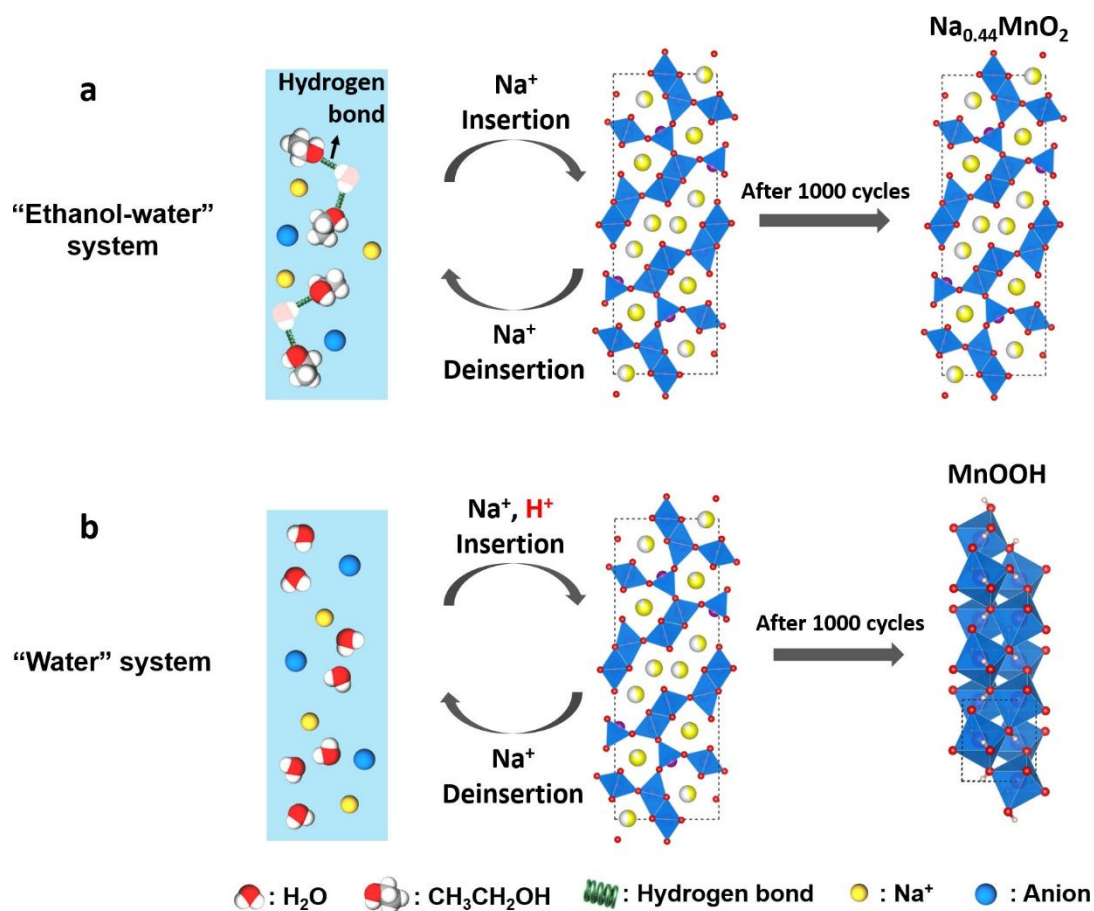

**Scheme 1.** Schematics illustration of ions storage in (a) ethanol-water and (b) water systems.

The lighter coloring of  $\text{H}_2\text{O}$  molecules in the ethanol-water system (scheme 1a) represents the suppressed water protons activity as compared to that in the water system (scheme 1b).



## For Table of Contents Only

