

UCLA

UCLA Electronic Theses and Dissertations

Title

Cooperation, the Craft Economy, and Metal Technology during the Bronze and Iron Ages in Central Anatolia

Permalink

<https://escholarship.org/uc/item/87p254n2>

Author

Lehner, Joseph William

Publication Date

2015

Peer reviewed|Thesis/dissertation

UNIVERSITY OF CALIFORNIA

Los Angeles

Cooperation, the Craft Economy, and Metal Technology
during the Bronze and Iron Ages in Central Anatolia

A dissertation submitted in partial satisfaction of the
requirements for the degree of Doctor of Philosophy
in Archaeology

by

Joseph William Lehner

2015

© Copyright by

Joseph William Lehner

2015

ABSTRACT OF THE DISSERTATION

Cooperation, the Craft Economy, and Metal Technology
in Bronze Age and Iron Age Central Anatolia

by

Joseph William Lehner

Doctor of Philosophy in Archaeology

University of California, Los Angeles, 2015

Professor Elizabeth F. Carter, Chair

Abstract

One of the most important transitions in human evolutionary history is the emergence and development of large-scale complex societies. The role of copper and bronze in the context of the emergence of Bronze and Iron Age states in the Near East is poorly understood due to a relative lack of comprehensive analysis of diachronic archaeometallurgical data. Excavations from Boğazköy and Kerkenes Dağ in central Anatolia have recovered one of the largest, diverse, and stratified corpora of copper objects and metal production debris, spanning the period from the Early Bronze Age, ca. 2300 BC, until the Late Iron Age, mid-5th century BC. Analysis of over 1100 objects employing energy dispersive X-ray fluorescence (EDXRF), in field portable X-ray fluorescence (pXRF), and select lead isotope analyses using multiple collector inductively coupled plasma mass spectrometry (MC-ICPMS) demonstrate that the rise of political

complexity is closely tied to increases in trade and the management of commodity chains.

Textual evidence illustrates how the Hittite state in particular managed the mobilization of metal commodities and finished goods as taxes, gifts, and payments for labor. Metal trade is further linked to state finance systems to explain how production and trade are tied to strategies of economic integration and interregional networking in Anatolia and beyond in the Near East and Mediterranean regions.

The dissertation of Joseph William Lehner is approved.

Charles S. Stanish

H. Craig Melchert

David A. Scott

Elizabeth F. Carter, Committee Chair

University of California, Los Angeles

2015

In memory of WJL

TABLE OF CONTENTS

| | |
|---|-----|
| CHAPTER 1: COOPERATION, CRAFT ECONOMY, AND METAL TECHNOLOGY | 1 |
| 1.1 Introduction and background | 1 |
| 1.2 Cooperation and the Craft Economy..... | 8 |
| 1.3 Theoretical perspective on cooperation and commodity chains | 15 |
| 1.4 Organization of the dissertation | 18 |
| CHAPTER 2: THE SOCIAL EVOLUTION OF METAL TECHNOLOGY IN ANATOLIA.... | 19 |
| 2.1 Introduction..... | 19 |
| 2.2 Metallurgy and the Craft Economy..... | 20 |
| 2.2.1 Raw Materials and Technologies..... | 21 |
| 2.2.2 Raw material acquisition..... | 22 |
| 2.2.3 Primary production | 23 |
| 2.2.4 Secondary Production | 26 |
| 2.3 Highland geography in Anatolia and the distribution of raw materials..... | 27 |
| 2.4 The earliest emergence of metallurgy in Anatolia..... | 33 |
| 2.4.1 Anatolia as a Region of Innovation | 34 |
| 2.5 Metal production and consumption during the Anatolian Neolithic | 37 |
| 2.6 Site-centered production: centralization, nucleation and balkanization | 38 |
| 2.7 The Development of Tin Bronze and Specialized Mining Communities..... | 46 |
| 2.8 Conclusion | 56 |
| CHAPTER 3: METAL PRODUCTION AND TRADE DURING THE BRONZE AND IRON AGES IN CENTRAL ANATOLIA..... | 58 |
| 3.1 Introduction..... | 58 |
| 3.2 Metal and markets: the evolution of the regional center in central Anatolia during the EBIII and MBA..... | 61 |
| 3.2.1 Archaeological context of metal production at Kültepe | 70 |
| 3.2.2 Compositional and isotopic analyses of copper from Kültepe | 73 |
| 3.3 Strategies of tribute, levies and tax, and domestic trade of metal during the rise of the Hittite Empire..... | 77 |
| 3.3.1 Hittite legal texts and the domestic economy | 80 |
| 3.3.2 Inventory and tax lists..... | 84 |
| 3.3.3 Archaeological evidence from Boğazköy..... | 89 |
| 3.4 Copper and bronze industries during the rise of Iron Age polities in central Anatolia | 97 |
| 3.4.1 Archaeological and archaeometallurgical evidence for copper trade and production during the Iron Age..... | 99 |
| 3.5 Conclusion: the organization of copper metallurgy and trade tracks onto the development of polities..... | 103 |

| | |
|---|-----|
| CHAPTER 4: ARCHAEOLOGICAL CONTEXT AND CHRONOLOGY OF THE SAMPLES | 105 |
| 4.1 Introduction..... | 105 |
| 4.2 Boğazköy | 105 |
| 4.2.1 Büyükkaya | 112 |
| 4.2.2 Büyükkale | 113 |
| 4.2.3 Lower City and Northwestern Slope..... | 114 |
| 4.2.4 Upper City..... | 117 |
| 4.2.5 Upper City West | 120 |
| 4.3 Kerkenes Dağ..... | 121 |
| 4.3.1 Palace Complex | 124 |
| 4.3.2 Cappadocian Gate | 128 |
| 4.3.3 Urban Quarters and Streets | 129 |
| 4.4 Conclusion | 130 |
| CHAPTER 5: COMPOSITIONAL ANALYSIS OF COPPER ALLOYS..... | 132 |
| 5.1 Introduction..... | 132 |
| 5.2 Analytical methods | 133 |
| 5.2.1 Analytical parameters and instrumentation | 134 |
| 5.2.2 Comparing methods and reproducibility | 139 |
| 5.3 Distribution of major and minor elements | 143 |
| 5.3.1 Arsenic | 144 |
| 5.3.2 Tin..... | 150 |
| 5.3.3 Lead..... | 153 |
| 5.3.4 Iron..... | 155 |
| 5.3.5 Nickel and Cobalt | 159 |
| 5.3.6 Antimony, Silver, and Zinc..... | 168 |
| 5.4 Discussion and Conclusion..... | 173 |
| CHAPTER 6: THE EMERGENCE OF METAL CRAFT ECONOMY IN THE BRONZE AGE AND IRON AGE CENTRAL ANATOLIA..... | 177 |
| 6.1 Introduction..... | 177 |
| 6.2 State fiscal systems and metallurgy: staple finance vs. wealth finance..... | 178 |
| 6.3 Surplus finance and wealth finance during the Bronze and Iron Ages in central Anatolia..... | 181 |
| 6.4 Conclusion | 192 |
| APPENDIX A: OBJECT CONTEXTUAL DATA | 196 |
| APPENDIX B: EDXRF RESULTS..... | 244 |
| APPENDIX C: PXRF RESULTS..... | 259 |
| REFERENCES | 295 |

LIST OF FIGURES

| | |
|---|----|
| Figure 1.1 Location of prominent archaeological sites in north central Anatolia mentioned in this dissertation. | 14 |
| Figure 2.1: Top: structural geology of the Anatolian peninsula highlighting major faults and geological zones or blocks (adapted from Okay 2008: 21, Fig. 3). Bottom: the tectonic and lithological development of the Anatolian peninsula have determinative effects on the distribution of known metal bearing regions, which can be characterized by their placement in major blocks..... | 31 |
| Figure 2.2: Değirmentepe with metallurgical remains which demonstrate both primary and secondary production technologies existing together (Lehner and Yener 2014: Fig. 20.5, Müller-Karpe 1994: Fig. 4)..... | 43 |
| Figure 2.3: The distribution of known tin sources/occurrences and the earliest sites where past communities consumed tin metal across the Near East and Central Asia demonstrates a major geographic disparity. The earliest tin bronzes occur along the piedmont of northern Syro-Mesopotamia and western Iran (above). The largest tin-bearing regions (in gradients) occur in Europe and Central Asia, while smaller occurrences (points) are irregularly distributed throughout the region and tend to be more proximate to larger tin sources (below) (Lehner 2014c). | 48 |
| Figure 3.1: Exchange equivalencies of iron, tin, gold, and copper relative to silver in Anatolia, irrespective of quality descriptors. Comparison is possible by creating an exchange ratio index which is the ratio of silver to the commodity multiplied by 1000 and then transformed to a log-scale. Boxes and whiskers represent quartiles of equivalency data from Old Assyrian texts dating to the 20 th -19 th centuries BC (equivalencies from Dercksen 1996 and 2005). | 65 |
| Figure 3.2: Exchange equivalencies of "fine" copper to silver recorded at different localities according to the Kültepe texts ca. 1950-1750 BC; abscissae indicate known ranges in prices (Lehner 2014: 143, fig. 2; data from Dercksen 1996). | 65 |
| Figure 3.3: Middle Bronze Age urban geography relative to known major metal deposits. Locations marked with a point are known or probably designations, while other locations are based on geographic inferences from texts. Location data of cities adapted from Veenhof 2008..... | 67 |
| Figure 3.4: Map of Kültepe-Kaneš showing the mound with select MBA architecture and the lower city excavations with known metal workshops (Lehner 2014: 144, fig. 3; adapted from Müller-Karpe 1994: figs. 28, 36) | 68 |
| Figure 3.5: Lead isotope binary plot comparing $^{207}\text{Pb}/^{206}\text{Pb}$ by $^{208}\text{Pb}/^{206}\text{Pb}$ of known ore bodies and artifacts dating to the MBA (adapted from Lehner 2014: 149, fig. 12; object data from Sayre et al. 2001; ore data from Wagner et al. 2003 and references therein). 1. AAN 282 | |

| | |
|--|-----|
| Acemhöyük Cu-ingot, 2. AAN 271 Acemhöyük Pb ore nodule, 3. AAN 925 Alisar Pb ring, 4. AAN 008 Acemhöyük Pb pendant, 5. AAN 843 Acemhöyük Cu pin, 6. AAN 199 Kültepe Pb frag, 7. AAN 842 Acemhöyük Cu pin, 8. AAN 17 096 Acemhöyük Cu crucible slag, 9. AAN 924 Alisar Pb ring, 10. AAN184 Acemhöyük Ag frag., 11. AAN185 Acemhöyük Ag frag., 12. AAN 17 095 Acemhöyük Cu ore nodule, 13. AAN288 Acemhöyük As ore nodule, 14. AAN 2032 Karahöyük-Konya Cu slag, 15. AAN 926 Alisar Pb ring, 16. AAN 286 Acemhöyük Cu ingot, 17. AAN 840 Acemhöyük Pb frag. | 76 |
| Figure 3.6: (Top) Relative frequency of metal commodity types for all different objects compared against tax and palace/temple inventory lists; (Middle) primary metal commodity types; and (Bottom) metal commodity types for finished goods (data from Siegelová 1986 and Müller-Karpe 1994: 75-76). | 88 |
| Figure 3.7: Map of the urban layout of Hattusa indicating major workshop (white circles) areas during the Late Bronze Age and Early Iron Age (Büyükkaya) (adapted from Lehner and Schachner in press: fig. 5; Müller-Karpe 1994: 83, fig. 57; Seeher 1995, 2006c). | 90 |
| Figure 3.8: Crucible types from Hattuša. 1. ETD 99/110, 2. ETD 96/218. Adapted from Lehner and Schachner in press (Fig. 9). | 91 |
| Figure 3.9: X-ray fluorescence analysis of crucible residues demonstrates melting and/or recycling practices. (a) Bo 2005: 293/305.263, (b) ETD 99/110, (c) ETD 96/218. Adapted from Lehner and Schachner (in press: fig. 10) | 91 |
| Figure 3.10: Ingot types from Bogazköy-Hattuša. (1) Bo 11/590, copper planoconvex MBA; (2) Boehmer 1972: Nr. 190, copper planoconvex LBA; (3) Bo 79/206, copper oxhide LBA; (4) Bo 83/819, copper planoconvex LBA; (5) Bo 87/69, silver planoconvex LBA. | 95 |
| Figure 3.11: Top: one of two tin bronze sheet metal ibex recovered from excavations at the monumental entrance to the Palace complex at Kerkenes Dağ (02TR01U02met02). Bottom left: optical micrograph of a polished and etched (in alcoholic ferric chloride, Scott 1991: 72) section of a sample showing diagnostic eta and epsilon intermetallic phases of copper-tin indicative of surface tinning. Bottom right: backscatter electron micrograph detailing a similar region of the same sample highlighting the phases (see Meeks 1986). | 102 |
| Figure 4.1: Map of Boğazköy with emphasis on the Late Bronze Age. Note most recent excavations at the Lower City are not shown here (courtesy of the Boğazköy Expedition). | 109 |
| Figure 4.2: Chronological development, stratigraphic periods, and key features from locations at Boğazköy-Hattuša from the Chalcolithic until the end of the Late Bronze Age. Bars represent periods of positively identified metal production (adapted from Schachner 2011: 14-15). | 110 |
| Figure 4.3: Chronological development, stratigraphic periods, and key features from locations at Boğazköy-Hattuša during the Iron Age. Bars represent periods of positively identified metal production (adapted from Schachner 2011: 16-17). | 111 |
| Figure 4.4: Iron Age city plan of Kerkenes Dag noting areas sampled by excavation up to 2014. Data from the project archive and Branting (2004). | 124 |

| | |
|---|-----|
| Figure 4.5: Schematic of developmental phases of the Palace Complex and its plan according to clearance and excavations from 1999 to 2005 (adapted from Summers and Summers 2008: figs. 22, 27). | 126 |
| Figure 4.6: Cappadocia Gate Plan (Kerkenes Dağ Project archives). | 127 |
| Figure 5.1: Comparison of EDXRF and pXRF methods across elements arsenic (As), tin (Sn), lead (Pb), and nickel (Ni)..... | 141 |
| Figure 5.2: Comparison of EDXRF and pXRF methods across elements cobalt (Co), iron (Fe), antimony (Sb), and zinc (Zn). | 142 |
| Figure 5.3: Comparison of EDXRF and pXRF methods across elements bismuth (Bi) and silver (Ag). | 143 |
| Figure 5.4: Diachronic frequency histograms of tin (Sn) and arsenic (As) from Boğazköy and Kerkenes Dağ. Note that distribution of tin is not differentiated between copper and tin bronze..... | 147 |
| Figure 5.5: Cast pendant (ETD 98/21) from Boğazköy. This broken pendant is produced with an exceptionally high arsenic content (26.9% As) and low traces of other elements. This alloy is distinctly silvery in color..... | 148 |
| Figure 5.6: Boxplot of arsenic (As) content through time for all objects from the EBA to the LIA at Boğazköy and Kerkenes Dağ. Bars and whiskers show quartile ranges, circles and asterisks symbolize outliers. | 148 |
| Figure 5.7: Diachronic frequency histograms of lead (Pb) and iron (Fe) from from Boğazköy and Kerkenes Dağ..... | 156 |
| Figure 5.8: Diachronic frequency histograms of nickel (Ni) and cobalt (Co) from from Boğazköy and Kerkenes Dağ. | 160 |
| Figure 5.9: Stamp seal (Bo 05/13) composed of three separate copper alloys, including an attached band of low nickel cupronickel. | 164 |
| Figure 5.10: In depth analysis of rolled head pin (Bo 09/972) from the Sarıkale Valley of Boğazköy. Point analyses across light and dark phases in the backscatter electron image (center) indicates a very strong coherence among related elements nickel, cobalt, and iron, reflecting the original casting segregation. | 165 |
| Figure 5.11: Concentrations of nickel (Ni) and cobalt (Co) compared across time periods and sites in this study. | 166 |
| Figure 5.12: Select examples of finished objects produced of high nickel cupronickel (>10.0 wt.% Ni) from Boğazköy dating to the Late Bronze Age..... | 167 |
| Figure 5.13: Diachronic frequency histograms of antimony (Sb) and zinc (Zn) from Boğazköy and Kerkenes Dağ. | 170 |
| Figure 5.14: Diachronic frequency histograms of silver (Ag) from Boğazköy and Kerkenes Dağ. | 171 |
| Figure 5.15: Copper alloy consumption profile at Boğazköy and Kerkenes Dağ from the Early Bronze Age to the Middle/Late Iron Age. The y-axis scale is enhanced to show the | |

| | |
|---|-----|
| distribution of alloy types below 0.10 of the assemblage group. Those above the scale are noted with arrows and their respective ratios. | 175 |
| Figure 5.16: Comparison of copper alloy types versus sample size. A significant logarithmic distribution demonstrates that sample size probably affects the distribution and diversity of observed alloy types per time period. | 176 |
| Figure 6.1: Preliminary lead isotope biplots comparing known ores to select artifacts recovered from Late Bronze Age and Iron Age contexts at Boğazköy. | 185 |
| Figure 6.2: Preliminary lead isotope biplots comparing known ores to select artifacts recovered from Iron Age contexts at Kerkenes Dağ. | 186 |
| Figure 6.3: Diachronic change in abundance ratios of copper alloy types among finished goods across observed contexts (top) and type diversity measures (Chao-1 and Shannon-H) during each respective time period (bottom). | 187 |
| Figure 6.4: Diversity indices of geochemical groups of pottery from Gordion, Boğazköy, and Kerkenes Dağ through time (data from Grave, et al. 2009; Kealhofer, et al. 2009; Kealhofer, et al. 2010); (top) absolute geochemical type frequency, (bottom) Shannon-H diversity, correcting for sample size and evenness among the sample groups. | 193 |

LIST OF TABLES

| | |
|--|-----|
| Table 1.1: Periodization of cultural developments in central Anatolia. Adapted from (Düring (2011); Sagona and Zimansky (2009); Summers (2008)). 1). Periods of focus in this dissertation in bold..... | 8 |
| Table 3.1: Old Assyrian descriptive metal lexicon for copper (Dercksen 1996)..... | 66 |
| Table 3.2: Administrative and spatial scope of known Hittite regional centers (adapted from Glatz 2009: 132, table 1)..... | 79 |
| Table 3.3: Metal commodity types and supplier locations according to 13 th century BC tax lists (data from Siegelová 1986, 1993, 2005; Siegelová and Tsumoto 2011)..... | 86 |
| Table 3.4: Context and composition (in wt.%) of planoconvex and oxhide copper and silver ingots from Hattusa. Quantitative results from EDXRF (Boehmer 1972: Nr.190, Bo 83/819, and Bo 87/69) and EDXRF (Bo 11/590 and Bo 797/206) (data from Lehner and Schachner in press: table 1)..... | 96 |
| Table 4.1: Total number of copper alloy samples from Boğazköy and Kerkenes Dağ that were analyzed for chemical composition in this study..... | 108 |
| Table 5.1: Analytical parameters of instrumentation to measure elemental composition used in this study..... | 136 |
| Table 5.2: Summary of mean values, standard deviation, relative standard deviation (%RSD), and minimum detection limit (MDL) for 13 elements and calculated from one standard reference material CTIF B12 (tin bronze) using pXRF. Results derive from 10 measurements taken intermittently throughout the duration of this study..... | 137 |
| Table 5.3: Compositional analysis of known copper alloy nominal standards which occupy a broad compositional range. In general, analytical accuracy noticeably decreases at concentrations less than 0.10 wt. % which is within the error range necessary to determine the major and many minor constituents. Industrial and in-house standards were analyzed at the Curt-Engelhorn-Zentrum Archäometrie | 138 |
| Table 5.4: Summary of mean values, standard deviation, relative standard deviation (%RSD), and minimum detection limit (MDL) for 15 elements and calculated from two standard reference materials BAM376 (pure copper) and BAM211 (copper tin bronze) using EDXRF. Calculated from 30 measurements taken during each measurement cycle throughout the duration of this study..... | 139 |
| Table 5.5: Arsenic (As) content of copper alloys at Boğazköy and Kerkenes Dağ..... | 146 |
| Table 5.6: Tin (Sn) content of copper alloys at Boğazköy and Kerkenes Dağ..... | 150 |
| Table 5.7: Lead (Pb) content of copper alloys at Boğazköy and Kerkenes Dağ..... | 155 |
| Table 5.8: Iron (Fe) content of copper alloys at Boğazköy and Kerkenes Dağ..... | 159 |
| Table 5.9: Nickel (Ni) content of copper alloys at Boğazköy and Kerkenes Dağ..... | 168 |
| Table 5.10: Cobalt (Co) content of copper alloys at Boğazköy and Kerkenes Dağ..... | 168 |

| | |
|--|-----|
| Table 5.11: Antimony (Sb) content of copper alloys at Boğazköy and Kerkenes Dağ. | 172 |
| Table 5.12: Zinc (Zn) content of copper alloys at Boğazköy and Kerkenes Dağ. | 172 |
| Table 5.13: Silver (Ag) content of copper alloys at Boğazköy and Kerkenes Dağ. | 172 |
| Table 6.1: Expectations following from theoretical archaic state fiscal systems (adapted from D'Altroy and Earle 1985; Stein 1994, 1999)..... | 181 |

LIST OF EQUATIONS

| | |
|--|-----|
| Equation 1: Minimum detection limit (MDL) using the Student t's method. | 137 |
|--|-----|

ACKNOWLEDGMENTS

This dissertation would not have been possible without the dedication and help of many people to whom I owe a great deal of personal and professional gratitude. First and foremost, my committee members have been incredibly supportive and responsive in all stages of this dissertation. Elizabeth Carter has been incredibly understanding and a constant guide in my progress as a scholar. She invested a great deal of time and effort in facilitating intellectual development throughout all of the various phases of my graduate career at UCLA. David Scott was ever available to discuss many aspects archaeometallurgy and archaeological science, more generally. His company and conversation, especially during the writing phase of this dissertation, was always reassuring. Since my first years at UCLA, Charles Stanish not only motivated me to develop as an anthropological archaeologist, but he urged me to look beyond archaeology as a discipline and to seek cross-cultural patterns in human evolution. Craig Melchert's knowledge as a Hittitologist equally influenced my work, demonstrating to me the intricacies of Hittite culture and language.

This dissertation research received the generous support of many institutions and laboratories. The bulk of this research was supported by the Alexander von Humboldt Foundation German Chancellor Fellowship. This fellowship afforded me the opportunity to work at the University of Tübingen, Germany and to conduct most of my laboratory work at the Curt-Engelhorn-Zentrum Archäometrie (CEZA) in Mannheim with Ernst Pernicka. The support of CEZA granted me scientific resources that allowed me to pursue a range of problems that would not have otherwise been possible. My development as a scholar in archaeological science was profoundly influenced by my time here and I will be forever grateful to everyone I was fortunate to work with during my stay. Funding and logistical support from the Cotsen Institute of

Archaeology at UCLA, the Steinmetz Travel Fund, UCLA Graduate Division, ASOR, and the UCLA Institute for Social Research has been greatly appreciated. Some aspects of this research were initially conducted at the Molecular and Nano Archaeology Laboratory at UCLA, for which I must thank directors Sergey Prikhodkho, Ioanna Kakoulli, and Christian Fischer for their assistance and cooperation.

I would also like to express my gratitude to the Turkish Ministry of Culture and Tourism, the Çorum Museum, the Yozgat Museum, and the Boğazkale Museum for providing me the official permission to conduct my research. In particular, I would like to thank Andreas Schachner, the current director of the Boğazköy-Hattuša Project, who has always provided incredible institutional support and hospitality at the site and in Istanbul. Jürgen Seeher and Ayşe Baykal-Seeher also deserve thanks for granting me access to their excavation materials at Boğazköy. Scott Branting, the current project director at Kerkenes Dağ, together with Geoff and Françoise Summers, delivered incredible support in the field and when writing. I owe also the Germany Archaeological Institute and the Oriental Institute at the University of Chicago for granting me access to archival data.

I must also extend the utmost appreciation to numerous friends and colleagues in the field. Suzanne Herbordt and Néhémie Strupler at Boğazköy were always happy to share ideas and discuss ideas before publication. At Kerkenes Dağ, Yasemin Özarıslan, Sevil Batalı-Tırpan, Bike Yazıcıođlu, and Susan Penacho have all shared their wisdom. I must thank all the members of the teams at Boğazköy and Kerkenes Dağ, too many to name individually, but all who made my time in the field enjoyable. In particular, I would also like to thank my elder colleagues Ulf-Dietrich Schoop, Aslihan Yener, and Fikri Kulakođlu for numerous discussions on culture

history and metallurgy in central Anatolia. My cohort and fellow graduate students at UCLA have always fostered a supportive and friendly network.

To my friends and family, I could not possibly emphasize enough how thankful and ever grateful I am for their support. My partner ACD supported me constantly and unquestionably.

VITA / BIOGRAPHICAL SKETCH

- 2005 Benjamin A. Gilman International Scholarship, Institute of International Education
- 2005 Simpson Scholarship in Egyptology
- 2005 American University in Cairo, Egypt
- 2006 B.S. with honors and distinction in Anthropology, University of Wisconsin, Madison
- 2007-2008 Chancellor's Prize, University of California, Los Angeles
- 2009 M.A. in Archaeology, University of California, Los Angeles
- 2009 Summer Research Fellowship, ULCA Institute for Social Research (ISR)
- 2010 Microscopy Society of American Presidential Award
- 2011 C.Phil in Archaeology, University of California, Los Angeles
- 2012-2013 Germany Chancellor Fellow, Alexander von Humboldt Foundation, University of Tübingen, Germany
- 2014-2015 Dissertation Year Fellow, University of California, Los Angeles

PUBLICATIONS

- In press Lehner, J.W., Evren Yazgan, Ernst Pernicka, and Fikri Kulakoğlu. Continuity of Tin Bronze Consumption and Production during the Late Third Millennium BC at Kültepe. In *Proceedings of the 1st Kültepe International Meeting*. F. Kulakoğlu and C. Michel, eds. Leuven: Subartu, Brepols.
- In press Yener, K. Aslıhan, Fikri Kulakoğlu, Evren Yazgan, Ryoichi Kontani, Yuichi S. Hayakawa, Joseph W. Lehner, Gonca Dardeniz, Güzel Öztürk, Michael Johnson, Ergün Kaptan, and Abdullah Hacı. The Discovery of New Tin Mines and Production Sites near Kültepe, Ancient Kanesh in Turkey: a Third Millennium BC Highland Production Model. *Antiquity*.
- 2014 Lehner, J.W. A Report on the Archaeometallurgical Research at Boğazköy, In Die Ausgrabungen in Boğazköy-Hattuša 2013. Schachner, A. ed. *Archäologischer Anzeiger* 2014(1):129-137.
- 2014 Lehner, J.W. and K.A. Yener. Organization and Specialization of Early Mining and Metal Technologies in Anatolia. In, Thornton, C. and B. Roberts, eds. *Global Perspectives in Early Metallurgy*, Pp. 529-557. New York: Springer Verlag.
- 2014 Lehner, J.W. Metal Technology, Organization, and the Evolution of Long-Distance Trade at Kültepe. In, Atici, L., F. Kulakoğlu, G. Barjamovic and A. Fairbairn, eds. *Current Research at Kültepe / Kanesh*, Pp. 135-155. Boston: American Schools of Oriental Research.
- 2012 Summers, G., S. A. Branting, S. Baltalı-Tırpan, N. Baturayoğlu Yonay, and J. W. Lehner. Kerkenes 2010. *Kazı Sonuçları Toplantısı* 33(4): 535-558.

- 2012 Lehner, J.W. Boğazköy-Hattuša Metal Objelerin Metalografik ve Kompozisyon Analizi. *Arkeometri Sonuçları Toplantısı* 27:261-276.
- 2011 Lehner, J.W. A Preliminary Report on the Microstructure and Microanalysis of Metal from Boğazköy., In, Schacher, A. (ed) Die Ausgrabungen in Boğazköy-Hattuša 2010. *Archäologischer Anzeiger* 2011(1):57-64.
- 2009 Lehner, J.W., K.A. Yener and J. Burton. Lead Isotope Analysis and Chemical Characterization of Metallic Residues of an Early Bronze Age Crucible from Göltepe Using ICP-MS. *Turkish Academy of Sciences Journal of Archaeology (TÜBA-AR)* 12:165-174.

CHAPTER 1: COOPERATION, CRAFT ECONOMY, AND METAL TECHNOLOGY

1.1 Introduction and background

One of the most important transitions in human evolutionary history is the emergence and development of large-scale complex societies. Several cross-cultural examples in many areas of the world demonstrate how the transition from small, dispersed, and autonomous villages to highly integrated larger towns and cities is further marked by substantial changes in how individuals and groups within these polities interacted and organized (Blanton and Fargher 2008; Flannery and Marcus 2012; Johnson and Earle 1987; Stein 2001). These changes include social, economic, political, and ideological transformations which may permit or support novel organizational types or strategies. More specifically, among the most important markers of this transformation is the reorganization of labor and long-distance trade (Algaze 2008; Arnold 1996), intensification of agricultural production to create a surplus (Marston 2012), higher degrees of interdependence and orders of interaction (Spencer 2010), and scaled manifestations of ideological power (DeMarrais, et al. 1996). Distinctly complex and multilineal, this transitional process is further characterized by the periodic and dynamic “rise and fall” of sociopolitical entities as groups competed for resources and status (Marcus 1998). In many known cases, this dynamic process of political and economic cycling within a region led to the formation of states through the related strategies of war and trade (Levine, et al. 2013; Redmond and Spencer 2012; Spencer 2003, 2010; Stanish and Levine 2011).

The region of central Anatolia presents an excellent example of this process. The increasing complexity and diversity of socioeconomic and political networks in this region

during the Bronze and Iron Ages are key characteristics in the development of state societies and empires (Alcock, et al. 2001; Goldstone and Haldon 2009). Archaic states have a marked economic patterning that is largely shaped by the structure and intensity of the trade relationships that were constructed and maintained to enable the dynamic operations among urban cores and resource areas (Algaze 1993, 2005, 2008; Stein 1999). People in these societies often used materials, technologies and artistic styles as forms of communication to develop and maintain social relations and long-term political alliances across great distances (Feldman 2006). This research will primarily examine how social groups within the Hittite Empire (ca. 1650-1200 BC) and the later political regime at Kerkenes Dağ (ca. 650-550 BC) structured copper metal technology and trade to form cooperative relations. Metal production and trade are particularly sensitive to changes in state fiscal and political strategies, and as such their analysis provides an important proxy into global economic processes. I argue that the expansion and decline of states in the region during this time period is particularly marked by the adoption and structuring of metal trade as part of wider state fiscal strategies in staple and wealth finance. Further, economic activities involved in metal production and trade show significant topological shifts, shedding light onto the network parameters associated with the evolution of cooperation in Anatolia.

Beginning during at least the Early Bronze Age II period (ca. 2600-2300 BC), parallel developments in long-distance trade and conflict appear in an unprecedented scale (Selover 2015). Together with the innovations in technologies of conflict, including elaborate alloyed copper weapons and fortification systems, evidence for increased levels of cooperation include the diversifications of settlements systems, corporate architecture, highly developed divisions of labor, and structured trade in exotic materials (Düring 2011: 270).

The diversity, scale, and intensity of all these developments increase during later periods of the Bronze Age, which culminated with the development of the Hittite Empire ca. 1650 BC. The Hittite Empire was arguably the first expansionist state to develop in central Anatolia. Archaeological and textual evidence demonstrates that its capital Hattuša developed into regional center around 2000 BC and, following the “Middle Chronology,” the state began its rapid expansion under the reign of Hattušili I ca. 1650 – 1620 BC (Bryce 2005; Klengel 1998; Schachner 2009a). According to the *Proclamation of Telipinu*, a Hittite historical text, an organized military force under the reign of Mursili I ca. 1620 – 1590 successfully sacked Aleppo, capital of the north Syrian kingdom of Yamhad, and Babylon in southern Mesopotamia ca. 1595 BC, entering the Hittites into large scale interregional interaction (Bryce 2005: 70-72). The greatest extent of the Hittite state arguably occurred from ca. 1400 BC to 1200 BC.

The transition from large territorial states of the Late Bronze Age to the subsequent rise of regional Iron Age kingdoms in the Near East and Anatolia is marked by one of the most empirically visible changes in the archaeological record (Bachhuber and Roberts 2009; Harrison 2008; Yener 2013). Late Bronze Age sites from across the Near East, Anatolia, and Aegean reflect large-scale destructions and abandonment, material culture appears to become rapidly regionalized, and environmental proxies demonstrate periods of climatic shift and anthropogenic degradation. These data have been variously interpreted together to help explain the processes and causes of rapid social and cultural change across the region. While scientific consensus generally appreciates the complexity of the sociopolitical cycling and cultural responses we observe more globally (eg. Butzer 2012), the difficulty to model complex past dynamics has led many scholars to reduce causation to only a few explanatory variables, including but not limited to prolonged climatic stress (Drake 2012; Kaniewski, et al. 2013), environmental degradation

(Chew 2001), warfare (Drews 1993), and pronounced shifts in established economic networks and core regions (Frank 1993).

In central Anatolia, the distinct millennium-long political and economic tradition of the Bronze Age began to decline during the end of the 13th century BC with the gradual deterioration of the administrative, economic, and religious infrastructure that was fundamental to the operation of the Hittite state (Seeher 2010: 220-221). By the end of the 13th and beginning of the 12th century BC, the capital Hattuša was probably composed mostly of waning temple and palace infrastructure (Seeher 2001), especially after the relocation of the residence of the ruling family and sanctuaries to the southeastern polities. The decline of the Hittite state also happened within the context of growing competition among neighboring states (Hawkins 2002: 151). While the historical events and processes that caused the decline of state institutions and the subsequent reorganization of communities in central Anatolia are unknown, empirical evidence is consistent with continuous occupation of the region even though it seems that communities dispersed and population densities appear to have decreased (Seeher 2010: 221).

The rapid cultural change from Hittite Anatolia to the Early Iron Age (ca. 1200-900 BC) is often attributed to migration and diffusion of social groups into north central Anatolia who introduced novel forms of social, economic, and political organization in the region (Seeher 2010: 222; Voigt and Henrickson 2000a: 46; Voigt and Henrickson 2000b). This interpretation is based on the appearance of new kinds of material culture and architecture in the region, yet there is little theoretical consensus concerning precisely the processes by which these changes happened, resulting most likely from the high fragmentary nature of the present data (Genz 2003, 2011). Evidence from Boğazköy, Gordion, and Çadır Höyük all attest to these significant discontinuities in cultural practices; however it is yet quite unclear how these changes reflect

cultural transmission due to cultural or demic diffusion (exogenous change) versus other aspects of cultural development inherent to localized internal processes (endogenous change).

The situation is somewhat clearer in regions to the south and southeast of the Bronze Age Hittite core, where the selective adoption of Hittite elite institutions demonstrates some continuity (Mora and d'Alfonso 2012). The current picture suggests that the development of these new political formations on the southern and southeastern periphery of the old Hittite core were established from Bronze Age dynastic lineages (Hawkins 1995). Conversely in north central Anatolia, the subsequent reemergence of polities appears to operate with greater continuity of earlier Iron Age cultures which are quite distinct from the so-called Neo-Hittite states to the southeast (Summers 2009). The Mid to Late Iron Age in central Anatolia can be characterized as a myriad network of small competing kingdoms and states, and there is little evidence to suggest powerful control over the entire region by any one polity over any extended period of time (Genz 2011: 360). Evidence from Gordion demonstrates that the development of a prominent state and its associated polities occurred only slightly later during the late 10th and early 9th centuries BC (Sams and Voigt 2011: 159). Gordion developed into a large urban center with monumental architecture, an expansive lower city, and a tradition of monumental tumulus burials, which attest to the existence of a ruling class of kings. A related regional center at Boğazköy during the 9th-7th centuries BC further east confirm the reemergence of polity within the bend of the Kızılırmak, where a complex settlement of fortified structures and monumental buildings demonstrate how this former Hittite capital redevelops as a central place. More regionally, the emergence of these larger political entities developed within the framework of secondary state formation across the Mediterranean and Near East, including the emergence of an enmeshed network and diversity of powerful states such as Assyria, Urartu, Tabal, and Syro-

Phoenicia (Joffe 2002; Sherratt and Sherratt 1993). Towards the late 7th and 6th centuries BC, the west Anatolian Lydian Empire briefly expanded into Central Anatolia from their capital of Sardis near to the Aegean coast, exacting tribute from the Phrygian capital at Gordion.

Perhaps related to the Lydian expansion east, the late 7th/early 6th century foundation of a large new urban center on the low mountain of Kerkenes Dağ southeast of Boğazköy marks the emergence of a new political regime with cultural, linguistic, and political affinities with Phrygian Anatolia (Summers 2006b, 2009). Kerkenes Dağ remains the largest Iron Age city in Anatolia and is comprised of a dense organization of urban blocks, monumental architecture, an expansive city wall, and numerous large tumuli that are likely the burials of the leaders of the polity. The city on Kerkenes Dağ seems to have flourished not only during the Lydian expansion eastward into the Phrygian core, but also during the Median expansion westward into Urartu and likely as far as the eastern limits of the Kızılırmak and the Neo-Babylonians northwards into the previously occupied Late Assyrian territories (Wittke 2004). These developments occurred just after the dissolution of the kingdoms of Tabal south of the Kızılırmak in modern Cappadocia (Hawkins 2000: 425-433). Only after several decades since its urban foundation, the city was abandoned and destroyed during the mid-6th century BC as a result of what is interpreted to be scaled warfare between the expanding powers of Lydia and Achaemenid Persia (Summers 1997). Shortly after the destruction of the city on Kerkenes Dağ, the Achaemenid Empire occupied much of Anatolia and the Near East, uniting all of Central Anatolia into a single satrapy called Kapatka, whose central city was Mazaca or modern day Kayseri .

I theorize that the political economy in Central Anatolia during the Bronze Age and Iron Age is marked by cyclical periods of economic expansion and contraction. These cyclical periods had a profound impact on the ways resources were acquired by states. Economic

expansion is marked by increases in the geographic scope of cooperation networks resulting in the further integration of producer and consumer communities. Spencer (2010: 7120) notes that expansion processes necessarily involve the adoption of novel bureaucracies or social institutions for their maintenance, and therefore parallel administrative institutions are expected to develop alongside large-scale expansions in trade. Economic contraction is marked by the disintegration of specific cooperation networks and institutions that once linked elite groups to foci of production and resources and are subsequently selected out of the repertoire of interactions. In a contracting economic environment where metal is a vitally important technology, social groups will sponsor select resource areas and production foci. A resulting pattern of intensive production may also increase the likelihood for cooperation networks to vertically integrate. In other words, the commodity chains associated with the production of value-added metal goods will likely centralize where values are particularly high, such as with the production of gold, silver, and tin bronze.

Table 1.1: Periodization of cultural developments in central Anatolia. Adapted from (Düring (2011); Sagona and Zimansky (2009); Summers (2008)). 1). Periods of focus in this dissertation in bold.

| Time Period | Date (BC) | Characteristics |
|--------------------------|----------------------|--|
| Chalcolithic | 6000 - 3000 | Dispersed autonomous village societies; ranked societies |
| Early Bronze Age | 3000 - 2000 | Complex chiefdoms, kingdoms, earliest state level societies |
| Middle Bronze Age | 2000 - 1750 | Competing states, Old Assyrian Trade |
| Late Bronze Age | 1750 - 1200 | Early Hittite State, Hittite Empire |
| Early Iron Age | 1200 - 900 | Political decline; dispersed villages, ranked societies |
| Middle Iron Age | 900 - 700 | Second urbanism, Phrygian state |
| Late Iron Age | 700 - ca. 547 | Kerkenes Dağ, Lydian expansion |
| Persian | ca. 547 - 330 | Achaemenid (Persian) Period |
| Hellenistic | 330 – 100 | Decline of major urban centers |

1.2 Cooperation and the Craft Economy

Early metal production is understood here to be part of a broader craft economy. The craft economy can be defined as the acquisition, manufacture, distribution, and consumption of crafted materials and finished goods. One of the principal characteristics of a craft economy in complex societies is the tendency for producers to specialize their activities. Craft specialization can be defined as the “differential participation in specific economic activities” in which producers rely on extra-local economic relationships and consumers rely on producers for products (Costin 1991: 20). The sustained efforts made to diversify and focus time and energy on production has particular advantages when most members of society participate, where diversification and an efficient labor organization can lead to increased returns and wealth

(Stanish 2003: 23). One reasonable explanation for these relationships to evolve on a large scale is the opportunity for cooperating partners or polities to produce greater returns and wealth that would not be possible without specialization and interdependence (Brumfiel and Earle 1987; Clark and Parry 1990; Costin 1991, 2001). Inherent economic advantages associated with these economies of scale conferred mutual economic gains among varying social groups in cooperative relations. The economic and social environment that develops under these conditions can allow for the evolution of cooperation among varying levels of society from individuals to groups (Carballo, et al. 2012). High degrees of cooperation, which is associated with the development of social complexity, also often leave a distinct signature in the archaeological record (see papers in Carballo 2013; Vidale and Miller 2000). For example, DeMarrais et al. (1996: 17) note that the production of prestige goods – usually objects that are highly valued due to being produced from scarce materials and labor intensive technologies – is often closely related to the emergence of elites. However, the scaled production and standardization of utilitarian goods is also a marker of high degrees of cooperation and specialization (Rice 1981: 220).

The increasing returns to scale associated with agglomeration economies in early complex societies in Anatolia and the Near East suggest that population density, cooperation, and location were key elements (Algaze 2008: 28-39) – a process similar to emerging industries more generally (Boschma and Frenken 2011; Krugman 1991a, 1991b; Potter and Watts 2011). Fujita, Krugman, and Venables formally theorized that the centripetal forces of market size are opposed by the centrifugal forces of dispersed natural resources (1999: 9), thereby creating basins of substantially integrated economic activity in space. This logic is mirrored by Costin (2001: 313), who argues that production and consumption processes themselves can serve to integrate social groups through the benefits of cooperation, while also reinforcing difference

through differential participation. Furthermore, the costs associated with transportation, production, and competition are often substantial in highland environments, and these factors likely influenced how production activities were both geographically situated and integrated. Highland environments often promote highly adapted and specialized sociocultural solutions to this problem (Aldenderfer 1998; Ehlers and Kreutzmann 2000; Körner 2004; Wilkinson 2003b; Zimansky 1985). Indeed, highland environments contain roughly half of the currently defined biodiversity hotspots on land even though they define up to a quarter of the land area (Kohler and Maselli 2009). This fundamental dynamic likely influenced much of the organization of production in Anatolia. The basic principle behind this pattern in Anatolia is that the topographically diverse highland ecologies profoundly affected the political and economic strategies of Anatolian populations.

YenerYener (2000) first described this process in the rise of complex metal industries in Anatolia in what she calls the highland production model. This model differs considerably from previous models that explain the rise of metallurgy based on data from the southern Levant or Europe (Strahm and Hauptmann 2009; Thornton 2009). Contrary to the development of cultural knowledge and technological innovations in the lowlands, Yener argues that metallurgical traditions develop out of a “balkanized technological horizon” during the Chalcolithic (ca. 4500 – 3500 BC), when Anatolian societies evolved a spectrum of highly regionalized political and economic systems (Düring 2011: 200-256; Schoop 2005), some of which, particularly in the upper Euphrates region, appear to have aspects of early urbanism. These regionalized polities across Anatolia functioned as multiple foci of production, where patterns of shared sealing traditions, ceramics, architecture, and other forms of materials culture are not observed in the distinctive metallurgical traditions (Yener 2000: 30-66).

Intrinsic to early metallurgy in Anatolia are the primary production strategies which differed from production models well known to the southern Levant. Primary production in metallurgy, which consists of the suite of technologies involved in the reduction of ores into metal through smelting (see Craddock 1995), has its likely origins in the Near East (cf. Radivojević and Rehren 2015; Radivojević, et al. 2010; Roberts 2011; Roberts, et al. 2009). The production of so-called “natural” or unintentional alloys as the result of prolific experimentation in smelting during the Chalcolithic (Strahm 1988; Strahm and Hauptmann 2009) may equally likely be associated with a well-adapted and fully intentional technology. Rather than smelting relatively homogenous iron- or manganese-rich copper ores, which are common to the Feinan and Timna sources of the southern Levant (Genz and Hauptmann 2002; Hauptmann, et al. 1992), Anatolian producers appear to have utilized a wide range of naturally available polymetallic ore types. The smelting of polymetallic ores or mixed smelting of select ores can result in the production of a wide variety of locally available copper alloys (Özbal, et al. 2002a; Özbal, et al. 2008; Radivojević and Rehren 2015; Radivojević, et al. 2013). Diverse alloy types can be found in much of the literature on Anatolian metallurgy. For example, metals like Cu-As, Ag-Cu, and Cu-As-Ni Late Chalcolithic / Early Bronze Age Arslantepe (Hauptmann, et al. 2002b; Palmieri and Di Nocera 2000) and Cu-Ni alloys from Late Bronze Age Boğazköy-Hattuša (Lehner 2011, 2014b) and Kaman Kalehöyük (Hirao and Enomoto 1997) demonstrate the prolonged practice of smelting mixed ore types in Anatolia.

A third important aspect of Yener’s highland model is the development of what she calls a “multi-tiered” or hierarchical organization of production. Contemporaneous with the first urbanization in Anatolia during the Early Bronze Age ca 3000-2000 BC, specialized mining and smelting communities developed in highland regions near to ore resources (e.g. Göltepe). This

pattern is noted also in the southern Levant and in Europe for varying reasons, but generally seem to be associated with parallel developments in social complexity. At the site of Göltepe in the central Taurus ca. 2880–2175 BC, people were engaged in the labor intensive benefaction of low grade tin ores rich in iron (Adriaens, et al. 1999a; Yener, et al. 2003) for the smelting of tin (Adriaens, et al. 1996; Earl and Özbal 1996; Yener and Vandiver 1993). Unfortunately intensive investigations of highland primary production sites like Göltepe are few in Anatolia. Recent research at the Early Bronze Age copper mining site of Derekutuğun in modern Çorum province proves to be an important exception (Yalçın and İpek 2011; Yalçın and Maass 2013).

Additionally, we have little data about primary production sites in Anatolia after the Early Bronze Age, yet we can infer from the Kültepe texts (Dercksen 1996), Hittite texts (Siegelová 2005, 2008; Siegelová and Tsumoto 2011), and from secondary production workshops at sites across Anatolia that they must exist (see Müller-Karpe 1994). Further intensive archaeological research in resource rich highland regions is obviously needed to help answer this problem (ex. Kaptan 1986; Kaptan 1990).

This observation implies that mining sites and many other specialized activities involved in raw material procurement and preparation developed out of increasing interaction and integration with lowland societies. However, the degree of actual autonomy that highland producers had is yet unknown. The degree of integration highland producers they themselves sponsored during changes in the political and economic organization of lowland societies likely served as an important determining factor. Simplistically, integration could function by means of market processes known to the Kültepe texts (Adams 1974; Larsen 1976; Lumsden 2008; Veenhof 1997), for example, or through redistributive processes and control on the other (Earle 2010, 2011; Oka and Kusimba 2008; Smith 2004). Specifically to central Anatolia, the shift from

the emergence of centralized estates in the late Early and Middle Bronze Age to the territorially integrated Hittite state of the Late Bronze Age likely had a notable effect not only on the exchange and redistribution of metals but also therefore their production (Cherry 1986; Liverani 1987, 2014 [1988]).

This challenge also makes it difficult to assess precisely how early highland metallurgists were integrated into the broader craft economy during the Bronze Age. It is further difficult to examine empirically because very little archaeological data for the Middle and Late Bronze Age exists for the primary production of metal in Anatolia during this crucial formative time period. Evidence for secondary production activities is much more prevalent because they often occur in urban contexts which have been the focus of archaeological research for the last several decades. Research at the ancient Bronze Age urban center of Kültepe-Kaneš, for example, demonstrates that urban producers were almost entirely limited to secondary metallurgy and were variably organized by authoritative leadership (Lehner and Yener 2014). This is particularly evident because metal workshops seem to be limited to households in the lower town rather than concentrated in closed contexts more indicative of attachment to state institutions like palaces or temples (Müller-Karpe 1994: 49-66). Ingots of copper and silver were recovered in workshops (Özgüç 1986a), which links the lowland urban and highland producers, however we know from texts that this linkage could be based on an extensive exchange system involving several interest groups rather than simplistic relationships between highland and lowland metallurgists alone (Dercksen 1996).

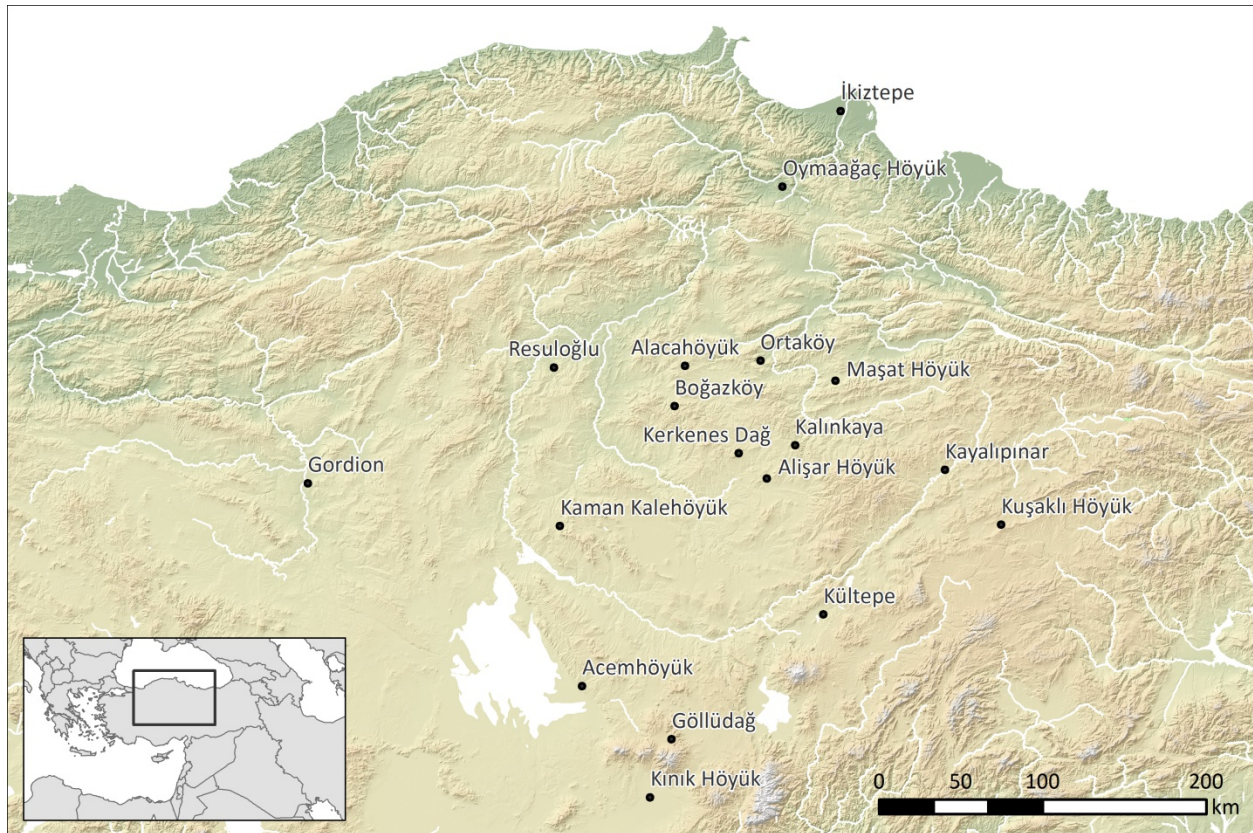


Figure 1.1 Location of prominent archaeological sites in north central Anatolia mentioned in this dissertation.

These three aspects of the highland production model, namely localized traditions of production, the early use of a diverse resource base including a wide variety of ore types, and the development of specialized primary metallurgy sites like Göltepe and Derekutuğun, encapsulate a generalized pattern that is theorized to characterize early metallurgy in highland regions like Anatolia (Lehner and Yener 2014), the Caucasus (Courcier 2014; Schachner 2002), and Iran (Thornton 2009). Yener’s work in particular focused on the early formative periods of development from the Neolithic to the Early Bronze Age, however little is known how these patterns developed in the later periods when highly networked state-level political strategies dominate as a primary means of political integration. The organization and control of the craft economy is certainly linked to these developments in later periods. During both the Middle and

Late Bronze Age in central Anatolia, the long-distance exchange of commodities, prestige objects, and knowledge is evident across the Near East, Aegean, and eastern Mediterranean. By the Late Bronze Age in particular, the craft economy functioned not only as a means to produce a wealth surplus more locally, but also as a means of alliance formation, cooperation, and diplomacy between competing regions (Feldman 2006; Liverani 2001).

1.3 Theoretical perspective on cooperation and commodity chains

This dissertation combines economic geography and theory in the evolution of cooperation as a way to understand changes in human behavioral strategies in state level societies. In so doing, I assume individuals and corporate groups interact within a framework of contingency and bounded logic (Bowles and Gintis 2011; Boyd and Richerson 2009; Gintis, et al. 2005; Henrich, et al. 2004; Henrich, et al. 2001), rather than rational in the classic economic sense of the word. Cooperation is defined here as an act of reciprocity, direct or indirect, whose stability is contingent upon a history of interaction and anticipated future outcomes in what is essentially an evolutionary process (Axelrod 1984; Axelrod and Hamilton 1981). Cooperation can occur between two or more individuals and between corporate social groups of any size (McElreath and Boyd 2007: 123-166). Under the right ecological conditions, social complexity (structured social diversity, hierarchies, etc.) can evolve through the self-interested interactions of individuals and groups (Nowak 2012).

Large-scale societies may differ drastically in the way cooperative networks are structured and maintained. One of the largest limiting factors to large-scale cooperation, especially among polities cyclically expanding through resource acquisition feedback mechanisms described by Spencer (2010), is geographic distance. Distance related costs,

including those incurred through transportation and communication, fundamentally structure the way individuals and corporate groups organize their long-distance activities. Communication networks evolve in changing environments where efficiencies, however measured, mitigate costs relative to the benefits provided by cooperative relations. As such, the geography of archaic states is more accurately characterized as highly structured social networks across space rather than necessarily cohesive aerial units or territories (Adams 1981; Branting, et al. 2013; Smith 2005, 2007; Ur 2010; Wilkinson 2003a).

One of the ways that metal technology tracked onto geographies of large-scale cooperation, was through the social construction of intertwined commodity chains (Earle 2010: 210). More commonly examined explicitly by economists and economic historians (Bair 2009), commodity chains are composed of the sequence of actions and processes inherent to the resource extraction, manufacture, distribution, and consumption. This directly parallels the previously described understanding of a craft economy; however it further focuses on these processes in space and time. How these chains are organized, and where different chains overlap, provide clues to how different communities may have sponsored or controlled them.

From the height of the Bronze Age urbanism in Anatolia to its eventual contraction and rise again during the Iron Age, global economic patterns are known to have shifted significantly in their extent and structure. The actual dynamics of this shift are unknown in Anatolia. I propose that these dynamics can be understood as economic expansions and contractions (Bair 2009). Expanding economies show increases in cooperation network size and complexity, while contracting economies demonstrate the selective abandonment of network ties and institutions. The global structure of cyclical economies, in the sense of expanding and contracting economies, consists of two variables. First, the geographical scope of a global economy, defined here as

distance and diversity involved in cooperation networks, should positively correlate with economic cycles. Increasingly expansionist strategies of polities necessarily take in more territories to acquire necessary agricultural surpluses and access to value-added goods like metal. During the Anatolian Bronze Age, the Hittites used combinations of staple and wealth surpluses to finance a coercive military force to integrate strategic regions into their state. These regions were often along important trade corridors, such as the Cilician gates into ancient Kizzuwatna or along the valleys to the metal rich regions of the eastern Pontides. An obvious effect of increased geographic scope in an expanding economy is the use and exploitation of more resource areas, the materials produced from them, and increases in the number of cooperating individuals or groups. This should be reflected in both the diversity of metal technologies and the provenance of their raw materials.

Second, the organization of commodity chains that adapt to an increasing geographic scope should show changes in integration. This can take the form of both vertical and horizontal integration of commodity chains. Social groups involved in the production of materials like metals may aggregate similar production activities horizontally to produce scale up production efficiencies in a region. Spatial clustering of industries is an example of such integration, and this is first observed with the development of regional centers in Anatolia. At sites like Boğazköy and Kültepe, which were central places of large states, similar production activities are located in proximity to one another. Similarly, some social groups may muster the necessary surplus and capital to vertically integrate commodity chains, integrating several production processes and commodities within a single organizational unit. Evidence of vertical integration is discernable when an attempt is made to centralize many or all aspects of production along a commodity chain. As I will argue in this dissertation, evidence points towards the tendency for Anatolian

states to horizontally integrate aspects of secondary metal production in regional centers as a way to manage the production of high value finished goods.

1.4 Organization of the dissertation

Following this introduction, Chapter 2 outlines the general theory and interpretive methods associated with metal technology. This includes a necessary description in a highly simplified commodity chain organized through the three major production sequences, raw material acquisition, primary production, and secondary production. All three of these processes leave determinative archaeological markers and their presence or absence at any particular site aids in the description and interpretation of the commodity chain involved. The second part of this chapter discusses the environmental parameters of Anatolia specifically pertaining to the geology of Asia Minor and the distribution of scientifically described metal resources. This then leads into an assessment of the cultural history of metal production leading up to the Early Bronze Age. Chapter 3 describes the state of the art concerning Bronze and Iron Age metal production and trade. This chapter focuses on the published archaeological and textual remains of Kültepe and Boğazköy to empirically generate a model capable of describing the organization of metal production and trade at these sites. Because the Iron Age in central Anatolia is data poor, this chapter describes and postulates why there is a lack of knowledge and how to explain this pattern. While Chapter 4 describes the chronological and contextual information of all samples analyzed in this study, Chapter 5 presents the results of the methods and analyses. Chapter 6 concludes the study with a discussion of state fiscal systems, dichotomized here as wealth and staple finance systems, as they relate to the production and trade of metal in Anatolia.

CHAPTER 2: THE SOCIAL EVOLUTION OF METAL TECHNOLOGY IN ANATOLIA

2.1 Introduction

Regional traditions of metal production and consumption seem to emerge in areas where mineral and native metal resources were relatively abundant (Golden 2009: 34-47; Hauptmann 2007: 255; Roberts, et al. 2009: 1013-1014; Yener 2000: 18-25). However, it is well known that geographic proximity to resources and technological proficiency alone cannot generate interest in producing and developing costly materials. There must also be social and economic incentives. Social differentiation and inequality often necessitated the use of scarce resources and complex technologies to display and communicate social heterogeneity or homogeneity (Vidale and Miller 2000). Metal production, a unique pyrotechnological development involving both rare materials and complex technologies, provides a way for some groups to manage access to wealth used to differentiate social groups (Brumfiel and Earle 1987; Helms 1993). Once metal became locked into a cultural system as an indicator of wealth, disparities in access to these resources necessitated varying degrees of cooperation among producer and consumer groups. These relations often linked distant groups together into cooperative agreements based on economies of scale. Therefore, metal technologies are embedded in complex networks and institutions of production, exchange, and consumption that effectively unite disparate highland resource areas and lowland regions.

In this chapter, I consider metallurgy and its related technologies as integral to the craft economy present in the archaic societies of Anatolia. Here I develop the necessary framework to help understand the principles of the craft and how various stages of production can be

reorganized to adapt to overarching social and cultural changes. Then I discuss the geology and distribution of raw materials used in the production of metal in Anatolia before considering how they were acquired and used over time up until the end of the Early Bronze Age. These data form a necessary background to aid in the interpretation of compositional data found in Chapter 5.

2.2 Metallurgy and the Craft Economy

Metal technology is an important proxy of highly cooperative behavior in a craft economy because as a technology it often requires a high amount of labor, knowledge of a variety of related technologies, and access to highly dispersed resources. In many ways, an efficient metal technology requires cooperation. However, the evolution of this technology over time in highlands of Anatolia and Iran has resulted in several different regional configurations, suggesting that there is no single optimal strategy in metal production (Thornton 2009: 320; Yener 2000: 4-10). Rather, empirical evidence suggests that people produced a wide variety of metals by intentionally utilizing a diverse resource and knowledge base that evolved in the context of distinct natural and cultural ecologies.

This observation is somewhat contrary, although not entirely, to how archaeometallurgists understand the organization of metal production in the Near East, which is dominated by research in the southern Levant (Thornton 2009). In the Levantine models, Thornton describes an important shift from site-centered smelting and melting during the Chalcolithic and EB I (ca. 4200–3000 BC) to a more diversified, large-scale, and centralized production that took place outside of habitation areas during the EB II–III (ca. 3000–2300 BC) (Genz and Hauptmann 2002; Levy 1995), where ingots of metal were imported rather than locally produced (Golden, et al. 2001: 961). In this lowland model of production, similar also to how Mesopotamian

metallurgy is understood (Stech 1999), peripheral highland resource areas supplied lowlands with valuable metal products (Algaze 2008; Kohl 1987; Stein 2005; Stein 1999).

Following Yener (2000), Thornton switches focus to the metallurgy of more highland regions in Anatolia and Iran, where a more explicit highland model of production better fits the data. In this model, highland production areas rich in metal resources were not simply unified suppliers of raw materials and semi-finished products, but rather highly adapted culturally specific regions with varying metal technologies. Multiple centers of metal production in these regions made up what Yener described as the “balkanized technological horizon” (p. 26) in the Anatolian Chalcolithic (ca. 4500–3500 BC). However similar to the development in the southern Levant, there is a corresponding shift in the organization of production during the later part of the third millennium BC in Anatolia, where production activities diversified, and many of the primary production centers moved into the highlands. Göltepe, a specialized mining community in the central Taurus and dated to the EBA (3000–2000 BC), is one such example (Yener and Vandiver 1993). Additionally, data indicates that metal production in Bronze Age Anatolia is not limited to specialized sites nor is production necessarily centralized, but production activities also occur in a wide range of urban contexts.

2.2.1 Raw Materials and Technologies

This developed highland-lowland relationship, or rather simply the relationship between regional centers and dispersed resource areas, is a pronounced feature of the metal based craft economy evident in urban cultures of Bronze Age and Iron Age Anatolia. An understanding of the sequences of metal production allows for a better understanding of these relationships. Identifying these production sequences in the archaeological record, therefore, allows us to build

powerful inferences concerning how people chose to operate within economic systems. In the following, I categorize metal production into three categories: raw material acquisition, primary production, and secondary production. While these categories do have cross-cultural relevance (eg. Killick and Fenn 2012; Tylecote 1976: xi-xii), they should be considered as heuristic categories and not actual salient cultural categories that communities in Anatolia would have used themselves.

2.2.2 Raw material acquisition

Metal technologies can use a surprising amount of different raw materials, including different choices of waxes and resins, ceramic materials, stone, fuel, and of course different ores and fluxes. By the late Chalcolithic and Early Bronze Age in Anatolia (ca. 4000-3000 BC), ores were collected first by hammering out exposed and weathered veins of metal rich ores, including mostly carbonates and oxides. In many places where ore deposits are particularly large, such as in northeastern Anatolia or Ergani in the Upper Tigris region, weathered ores formed caps on deeper non-weathered sulphide deposits. The collection of sulphide deposits, and other deep deposits, required mining, which in turn required a larger labor investment and more organization. The earliest mining activities conservatively date to the late 4th and early 3th millennium BC, evident at Derekutuğun in Çorum (Yalçın and Maass 2013), Kozlu in Tokat (Giles and Kuijpers 1974), and Kestel in the Taurus (Yener, et al. 1989). However, numerous types of polymetallic, oxidic, and sulphidic ores have been identified at a number of 5th and 4th millennium settlements such as Değirmentepe (Esin 1985; Özbal 1985) and Arslantepe (Hauptmann, et al. 2002b; Palmieri, et al. 1993) along the Upper Euphrates, and Çamlıbel Tarlası

in modern Çorum province (Schoop 2010, 2011), suggesting that a spectrum of diverse and intensive acquisition and provisioning strategies likely date earlier.

Very little archaeological evidence of mining activities is documented for the Middle and Late Bronze Ages (ca. 2000 – 1200 BC). Despite the apparent increase in production of metals during this time period, we know very little about how raw materials were extracted and/or how that labor was organized. This is likely due to both a lack of research in highland regions and later mining activities that would remove previous workings.

2.2.3 Primary production

The primary production of metal from ores is a complex process that depends on both the careful selection of raw materials and the control of redox conditions of the atmosphere in the reaction vessel with high temperatures. By the 2nd millennium BC in central Anatolia, we can be fairly certain that most metals were produced by the reduction of ores into relatively pure metal using both crucibles and furnaces, often together with induction enhancing tools like tuyères and pot bellows. The techniques for reducing different metals will differ based on the chemical and thermodynamic properties of the raw materials and desired outcome. Ore composition plays a large role in this. For example, copper sulphide ores must first be roasted at temperatures between 600° and 800°C to partially transform chemically the sulphides into oxides. These oxide ores can then be smelted in a reducing environment where oxygen bonds with silicates in the ores and flux leaving slag as a waste product and relatively pure copper metal. Lead metal is easily extracted using similar techniques.

Early silver metal was produced through a two-step process, where lead carbonates or lead sulphides were smelted under reducing conditions to produce argentiferous lead. Then

through a process called cupellation, silver would be separated from this solid solution through the selective oxidation of lead. Silver produced by this method always leaves a minor amount of lead, and practically all of the analyzed 3rd and 2nd millennium silver in the Near East contain around 0.1 wt% lead or suggesting cupellation was widely used to produce silver (Moorey 1994: 323-240)

. The earliest examples of silver extraction through cupellation date to the late 4th millennium BC from Fatmalı-Kalecik (Hess, et al. 1998) and Habuba Kabira (Pernicka, et al. 1998). During the Bronze Age in Anatolia, gold or electrum would have most likely been collected by panning in stream beds or mining veins. It is unlikely that silver was removed from native gold in the Bronze Age, which is achieved through the cementation process, the earliest evidence of which dates to the 6th century BC at Sardis located in western Anatolia (Bachmann 1999; Ramage and Craddock 2000).

Iron production also deserves some mention for the Anatolian Bronze Age. Re-dating of the Alaca Höyük irons, including the iron dagger with gold handle, places them firmly with the later part of the 3rd millennium BC (Yalçın 2010). In addition, numerous iron objects from Kaman-Kalehöyük Stratum III dating to the early second millennium BC attest to some degree of control of iron and possibly steel production (Akanuma 2006). Several texts demonstrate the importance of this metal as costly, rare, and controlled (Dercksen 2005: 27-29; Maxwell-Hyslop 1972). Additionally, amorphous iron lumps discovered in a large house from the lower city at Kültepe (Müller-Karpe 1994: 55; Özgüç 1959: 56) give material evidence to its use in the city. Iron of this nature is almost certainly produced from the reduction of iron rich ores into metal by smelting. It is yet unclear whether iron production was intentional or a byproduct result of copper smelting (Akanuma 2006). However some opinion persists to explain the origin of these metals

not through smelting but through the hot and cold working of meteoritic iron or even terrestrial iron (telluric iron) (for further discussion, see Pernicka 1990: 60-63; Waldbaum 1999). The presence of nickel in iron metal may help distinguish it from terrestrial iron in origin however nickel can also accompany many iron ores and remain in the metal after a smelt. Both forms of naturally occurring iron metal have distinct crystalline microstructure that is identifiable under a microscope even if the object was heavily worked.

Extracted metals either went directly into the production of finished objects or were formed into ingots for transportation. Two of the most common shapes in the Middle Bronze Age, evident both at Kültepe and Acemhöyük, are bun-shaped and bar-shaped ingots (Özgül 1995). Presumably bun-shaped ingots were produced in the smelting installation, where the segregated molten metal sinks and takes the shape of the furnace floor. However, little empirical archaeological evidence exists in support of this. Alternatively, bun-shaped ingots can also be produced from copper pooling, recycling, or raffination. Bun-shaped and bar-shaped ingots can also be recast into molds, and there are numerous examples of these located in the metal workshops in the lower city of Kültepe. Depending on the efficiency and technique of the smelt, these ingots could vary considerably in composition which may reflect quality and purity. For example, bun-shaped copper ingots from the Uluburun shipwreck are relatively pure in copper (Hauptmann, et al. 2002a), while contemporary ingots from the Caucasus are noted to be high in constituents like arsenic (Gambaschidze, et al. 2001) and lead (Hauptmann 2000) and ingots from Oman having significant concentrations of arsenic and nickel (Prange 2001). Producers may also choose to re-melt ingots with additional fluxes to refine the metal and remove unwanted slaggy inclusions in the metal.

What we may perceive as impurities in raw metal may very well have been intentional. Particularly controversial is the isolation of arsenic for use in alloys with copper. To date, there is no evidence that pure arsenic metal was traded like copper or tin, ingots of which were used to produce tin bronzes or other intentional alloys. Current evidence suggests that the addition of arsenic was achieved through other means early in the primary production chain. It is not clear whether copper-arsenic alloys were produced via a mixed or co-smelting process involving copper and arsenic rich ores (Lechtman 1991, 1996; Lechtman and Klein 1999) or through the addition of an arsenic-rich secondary product like speiss (a material often found in copper slags rich in iron and arsenic) to molten copper in a crucible (Rehren, et al. 2012; Thornton, et al. 2009). Arsenic is highly volatile at high temperatures, so it is difficult to mutually control arsenic and copper in a single environment. Producers likely developed specific ways to carefully time the addition of arsenic without losing significant amounts of the metal. This has particular relevance for the Kültepe metals because arsenic persists as a common constituent in copper and copper alloys in Anatolia until the end of the Late Bronze Age ca. 1200 BC (Kuruçayırılı 2011; Kuruçayırılı and Özbal 2005; Lehner 2011, 2014b).

2.2.4 Secondary Production

The transformation and working of raw metal from ingots or scrap into desired shapes is secondary production. Empirical evidence demonstrates that this stage of production was technologically related to primary production; however the limiting constraints in secondary production evolved around the requirements of finished objects rather than the reduction of ores into raw metal. This stage includes the re-melting of metals, ranging from raw primary produced metal to worked scrap, alloying, casting, and working. Typically, Bronze Age workshops in

Anatolia associated with melting have less expedient, reusable installations and associated tools as a result, including a large type range of furnaces, crucibles, and molds (see Müller-Karpe 1994). As a result, secondary production technologies in Bronze Age Anatolia are frequently associated with permanent architecture, ranging from independent households to attached workshop quarters in elite residences and palaces (Lehner 2014a).

Innovations and experimentation in the secondary production stage led to a high variation in shapes and forms of finished metal objects as well as metal alloy types. By the Late Bronze Age, we observe many different alloy types, and it is clear that past metallurgists were certainly aware of the effects that varying concentrations of metals in alloys had on the desired outcome. For example, the addition of tin and arsenic to copper in low percentages create broadly similar alloys in terms of hardness and tensile strength (Lechtman 1996), yet they can produce different colors (tin bronzes tend to be more golden yellow and arsenical copper alloys tend to be more reddish to silvery) and aural pitches when struck (Hosler 1995).

2.3 Highland geography in Anatolia and the distribution of raw materials

The landscape of Anatolia, modern-day Turkey, is extraordinarily complex. Anatolia is a large peninsular landmass that is surrounded by three seas: the Black Sea to the north, the Aegean to the west, and the Mediterranean to the southwest. The landmass is primarily composed of a series of high mountain ranges and steppes as a result of relict continental agglomeration, tectonic activity and volcanism that took place during most of the Phanerozoic (Okay 2008). Turkey is composed geologically of three main tectonic units including the Pontide, the Anatolide-Tauride Block and the Arabian Platform. Resting in between the Pontide and Anatolide-Tauride Block, the Central Anatolian crystalline complex stretches from modern

Kırıkkale to Sivas and is composed of mostly metamorphic and plutonic rocks dating to the Cretaceous. Anatolia is also highly varied in terms of climate, with arid regions to the south and southeast along the Syro-Mesopotamian plains and sub-tropical rainforests in the northeast along the Black Sea. Many of the mountainous regions are heavily wooded, including most of the Pontide belt and western Anatolia. Relict forests that have survived several different periods of deforestation can be found in different areas of the Central Anatolian Plateau (Miller 1999; Willcox 1974, 2002).

The highlands of Anatolia, a varied mountainous and steppe landscape, are endowed with pockets rich in metal-bearing mineral concentrations (Figure 4.1). As part of a larger metallogenic belt within the Alpine-Himalayan orogenic system (Okay 2008), Anatolia has extensive polymetallic deposits of copper, iron, lead, silver (often in the form of argentiferous lead), and zinc in addition to rarer deposits of antimony, arsenic, nickel, gold and tin (Bayburtoğlu and Yıldırım 2008; Çağatay, et al. 1979, 1989; Çağatay and Pehlivan 1988; de Jesus 1980; Maden Tetkik ve Arama Enstitüsü 1970, 1971, 1972; Öztürk and Hanilçi 2009; Yalçın and Özbal 2009; Yener, et al. 2015). Prior to any larger archaeometallurgy research programs, the characterization of these ore bodies was accomplished by the Turkish General Directorate of Mineral Research and Exploration (MTA). While most of this original exploratory work was aimed at defining the economic potential and modern industrial interpretation of the ores, the extensive placement of major ore bodies and smaller metal occurrences throughout the Anatolian peninsula provided the necessary environment for the development of early metallurgy. De Jesus (de Jesus 1980) compiled much of this early work and analyses of archaeological metal, mostly conducted by Ufuk Esin (Esin 1969), in the first major synthesis of Anatolian archaeometallurgy and resource use based on scientific data.

In addition to the fundamental exploratory work of the MTA, a series of later surveys in the 80s and 90s geared towards understanding how these resources related to ancient societies further generated a large archaeometallurgical dataset. These data characterized the elemental and isotopic composition of hundreds of ore sources and occurrences across Anatolia. This work includes the Heidelberg-Mainz surveys across Anatolia in the 1980s (see Wagner, et al. 2003: , and references therein), later surveys lead by A. Yener in the Bolkardağ mining district of the central Taurus (Yener 1986; Yener and Özbal 1986), and analyses of ore samples from the Taurus and across central Anatolia by the Japanese expedition to Kaman Kalehöyük (Hirao, et al. 1995). Much of this work was accomplished in the context of extensive analyses of ore sources across the Mediterranean, as scholars sought to define and explain the origins of metallurgy in the Old World, the nature of metals trade, and the provenance of copper, tin, silver, and lead metal more generally (for Anatolia and the Near East more specifically, see Pernicka 1990; Yener 2000).

The three largest massive copper sulphide ore bodies in Anatolia include the metallogenic zones of Ergani in the eastern Taurus and Küre and Murgul/Göktaş along the central and eastern Pontide belt (Wagner and Öztunalı 2000). The geological age of these mineralizations also varies in relation to ongoing tectonic and geothermal activity throughout peninsular Turkey – a determining factor in the success of extensive lead isotope research conducted in the greater Anatolian region (Begemann and Schmitt-Strecker 2008). The geographic distribution of ore bodies roughly follows the contours of the Pontide and Tauride orogenic belts in northern and southern Turkey. Polymetallic copper and lead-zinc-silver ores are particularly abundant in the eastern sectors of these regions (Seeliger, et al. 1985; Wagner, et al. 1989). Arsenic and antimony-rich ore of the fahlerz type are evident in both Pontide and Tauride sources (Özbal, et

al. 1999; Özbal, et al. 2001; Özbal, et al. 2008) and from fourth millennium BC archaeological deposits at Norşuntepe (Seeliger, et al. 1985; Zwicker 1980) and Arslantepe (Palmieri, et al. 1993) along the Upper Euphrates. A major copper-nickel sulphide deposit near modern Bitlis in eastern Turkey has also been reported (Çağatay 1987), while further smaller sources of copper-nickel sulphides have been reported from within the major iron-bearing ore zones of Divriği-Sivas (Harada, et al. 1971). The Bolkardağ mining district of the central Taurus and immediately north of Cilicia includes mostly iron, argentiferous lead, copper-lead-zinc ores and also oxides and sulfides of tin including stannite and cassiterite (Pehlivan and Alpan 1986; Yener and Özbal 1987; Yener, et al. 1989). More recently, a tin occurrence at Hisarcık in Kayseri province, located north of the Bolkardağ, was found associated with scores of mines (Yener, et al. 2015). In the northwest, the Troad sources reveal a diverse array of complex ore deposits, including copper, lead, silver, and gold (Pernicka, et al. 2003; Pernicka, et al. 1984; Wagner, et al. 1985). Arsenic-bearing ore bodies are unknown in this metallogenic zone. The Central Anatolian highland, an arid steppe environment bounded to the north and south by high mountains, is less abundant in copper resources. Exceptions include the polymetallic copper-lead-silver ores located near Akdağmadeni, small oxidic and native copper deposits near Sungurlu, and secondary copper ore deposits near Karaali south of Ankara.

A key pattern in the distribution of raw materials and environments in highland regions like Anatolia, Transcaucasia, and Iran are their heterogeneous and uneven distribution (Wilkinson 2003b). Despite a relative abundance of ore sources, their spotty distribution and diverse characteristics influenced how they were extracted, refined, smelted and transported (Craddock 1995). The geographic and social parameters of mining regions had significant influence on technological organization, socioeconomic processes, and interregional relations

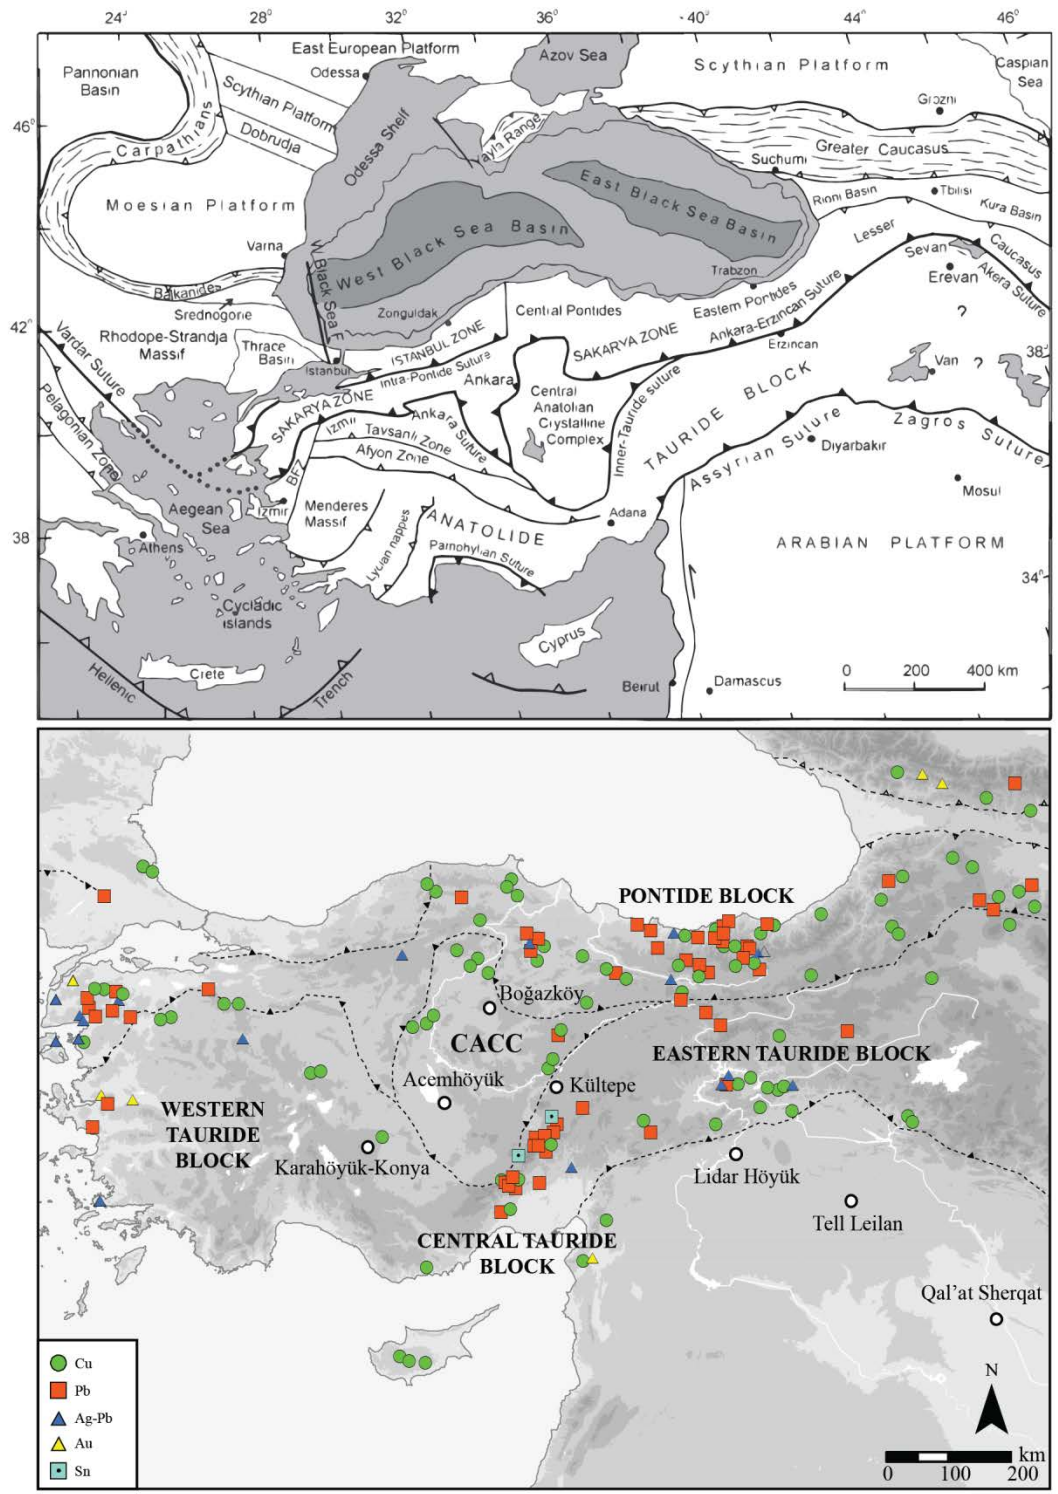


Figure 2.1: Top: structural geology of the Anatolian peninsula highlighting major faults and geological zones or blocks (adapted from Okay 2008: 21, Fig. 3). Bottom: the tectonic and lithological development of the Anatolian peninsula have determinative effects on the distribution of known metal bearing regions, which can be characterized by their placement in major blocks.

(Knapp 1998). Distance from the raw materials to fuel and food supplies, as well as seasonal weather conditions, would have been key factors in how they were accessed. Production and transportation to and from the highland resource areas was almost certainly restricted by seasonal conditions due to harsh prohibitive winters. Furthermore, economic transportation routes were most often limited to navigable rivers and intermontane valleys. Patterns associated with climatic and social events, such as poor weather, trade embargos, and regional warfare, further constrained access. As the Kültepe demonstrate, movement of goods across central Anatolia was often abruptly postponed due to poor weather and war, and this likely had significant effects on trade relations and the exchange values of metal types (Barjamovic 2011: 28-29; Dercksen 1996). Furthermore, the dynamic and costly ventures of mining and smelting activities often had considerable impact on the environment, leading to deforestation and alterations of drainage routes (Monna, et al. 2004).

The clustered distribution and diverse mineralogical characteristics of these metal resources no doubt influenced their availability over time. Disparities in proximate access to these resources and regional competition for material use created incentives for long distance cooperation among some individuals and communities while providing leveraging power to others. As will be argued later, economic specialization and diversification in mining, and extraction technologies, were not only the result of an increased demand for metals and finished forms but also the result of innovations in labor organization. Increased sophistication in technological organization ensured a predictable supply of important materials necessary for the regular maintenance of social relations while at the same time generating potential for significant social inequality. Suffice to say for now, diverse alloys and technologies are well represented in many fourth and third millennium BC burial contexts in Anatolia. For example, the well-known

collections of decorated copper alloy swords and spearheads from the Early Bronze Age “Royal Tomb” at Arslantepe (Hauptmann, et al. 2002b; Palmieri and Di Nocera 2000), and the elaborate Alacahöyük, Kalinkaya, and Horoztepe cast tin-bronze standards and figurines (Arik 1937; Koşay 1938; Özgüç 1964; Yıldırım and Zimmermann 2006; Zimmermann and Yıldırım 2007; Zimmermann, et al. 2009), indicate metal resources and technologies were associated with disparities among social groups.

2.4 The earliest emergence of metallurgy in Anatolia

The model of highland Anatolia and lowland Syro-Mesopotamia as a core-periphery relationship in which lowland predominantly urban cultures extract highland raw materials is of course simplistic. While archaeologists continue to refer to Anatolia as a highland region, it should be stressed that the dichotomy between highland and lowland regions is somewhat problematic because, as Yener (2000) and Thornton (2009:305) point out, the Near Eastern highland regions are internally variable. They constitute a series of interlocked highland intermontane and lowland valleys and plateaus. However within the greater Near East, Anatolian physical geography is distinctive, providing not only important resources in the formation of complementary links with the Syro-Mesopotamian plains but also naturally defensible environments. Nevertheless, Anatolia is a distinct region that warrants discussion of both broad diachronic changes in the organization of metal technologies and localized traditions of metallurgical practice.

The framework for this discussion is divided into two parts. First, I discuss how perceptions of the role of ancient Anatolia in the Near East are changing with respect to complex technologies. As a corollary to this and in agreement with Thornton (2009), I then offer an

alternative view which suggests that Anatolia and other resource-rich regions in the Near East were regions of indigenous technological and social innovation. This is apparent because organized mining and metal production exists before apparent large scale Mesopotamian involvement in Anatolia. Second, I discuss how metal production is coordinated over long distances in order to mitigate disparities in access to rare materials and technologies. Changes in the organization of metal technology coordinate with socioeconomic shifts in the way metal resources are acquired and distributed, which results in the emergence of a multi-tier hierarchy of mining and metal production. This organizational trajectory sets the stage for metal production and consumption that we observe during the Late Bronze Age (ca. 1550 – 1200 BC) and Middle/Late Iron Age (ca. 800-500 BC), which are political optima in terms of polity size and the foci periods of this dissertation.

2.4.1 Anatolia as a Region of Innovation

An increasingly sophisticated understanding of cultural and historical process in Anatolia is changing our conceptualization of this region as a focus of analysis (Düring 2011; Mathews 2011; Sagona and Zimansky 2009). Past researchers tended to view archaeological problems in terms of the regions that surround Anatolia, including the Aegean and Mesopotamia. It was usually assumed that novel social, political, and technological forms originated elsewhere, outside the frontier highlands of the Anatolian. It was V. Gordon Childe who suggested that metallurgy was central to cultural diffusion in the region, where ‘itinerant metalsmiths’ contributed to the rise of social elites and complex societies across the Near East (Childe 1930, 1944). It logically followed that traditions of metallurgy diffused from the Near East, specifically Mesopotamia and the Levant, into other regions including Anatolia and the Aegean. Criticism of

this simple model came first from Europe, where scholars used radiocarbon dates to challenge the claim, suggesting an independent development of metallurgy in southeastern Europe (Renfrew 1969, 1973). Empirical evidence to date further demonstrates complex social processes of technological innovation associated with the origins of metallurgy occurred not within the lowland resource poor regions of the Near East, but within the resource diverse regions in Anatolia and Iran (Roberts, et al. 2009). Rather, we can now expect innovations in metallurgy to occur as a distinctive relationship between resource availability and cultural transmission. It is most likely that Mesopotamia did not need to develop novel primary production technologies, but instead social groups found new ways to organize labor and technologies associated with secondary production and distribution strategies. Anatolia, on the other hand, had proximate resources and different social systems, and therefore we can expect innovations to occur both in primary and secondary production strategies.

In a review of the intellectual history and rhetorical devices used to describe the Anatolian peninsula, particularly as a region of analysis, Yazıcıoğlu (2007) examines the origins and pitfalls of the conception of Anatolia as a “land bridge,” most notably as a conduit of knowledge rather than a landscape of innovation unto itself. Yazıcıoğlu argues against the conceptualization of Anatolia as a land bridge because this metaphorical simplification “hampers a thorough understanding of the material culture of Anatolia and skews our perspective, especially in analyzing trade and exchange relations or processes of diffusion and/or migration” (Yazıcıoğlu 2007:219). In effect, she argues that this perspective generates an emphasis on the movement of people, things and ideas through the region while downplaying the significance of several millennia of regional traditions and cultural practices. As Yener (1995: 119) has pointed out, “Anatolia is often presented as a cultural frontier in which it is seen as passive receiver of

innovations that emanated from more sophisticated centers.” The common metaphor is of Anatolia embodying a land bridge from Mesopotamia to Europe—from the East to the West *ex oriente lux*.

The suggestion that highland regions promote diversity is not a novel concept. Aldenderfer (1998), Ehlers and Kreutzmann (2000) and Körner (2003, 2004) all argue that various challenges inherent in highland environments promote behavioral specialization. Human communities adapted to these local environments to facilitate predictable access to their unique resources, including pastureland, food sources, and raw materials used in the manufacture of tools and ornaments. Highland regions, rather than impeding transportation, guided trade and exchange routes by way of valleys and mountain passes. Central to the question of Anatolia as a region of innovation are the resources of its diverse natural environments and the close proximity of its ecotones that were the necessary preconditions for the emergence of metallurgy and its rapid success in the region.

Regional environments and resource distributions in the Anatolian highlands influenced diverse institutions of production and specialization that otherwise would not be feasible in the lowland plains of Mesopotamia. Highland mining communities are one subset of these specialized institutions. These communities seemed to emerge with the greater demand for resources used in the creation of utilitarian and wealth objects during the mid-fourth millennium BC.

2.5 Metal production and consumption during the Anatolian Neolithic

The use of native metals and metalliferous minerals (e.g., malachite $\text{Cu}_2\text{CO}_3(\text{OH})_2$, hematite Fe_2O_3 and galena PbS) during the Anatolian Neolithic demonstrates a high degree of technological sophistication and familiarity before the development of formal smelting techniques (Schoop 1995, 1999). In addition, access to raw materials during formative periods of emergent complexity help generate temporally-resilient acquisition networks important to many later complex technologies. As early as the 11th millennium BC, metalliferous minerals were used as raw materials for pigments and ornaments, such as a perforated pendant possibly made of malachite from Shanidar in Iraq and green stone beads from Rosh Horesha in Israel (Bar-Yosef Mayer and Porat 2008; Solecki, et al. 2004; Solecki 1969). Evidence for the regional occurrence of cold-worked native copper begins during the 9th – 7th millennia BC in the form of ornaments (Schoop 1995).

Substantial evidence for the working of native copper comes from the Neolithic site of Çayönü in southeastern Turkey (Özdoğan and Özdoğan 1999). Dating from the 9th to the 7th millennia BC, successive occupational strata at Çayönü provide key evidence for the emergence of complex societies that partake in agricultural economies and specialized technologies in the Near East (Özdoğan 1999). Located in a highland setting near to the Tigris river valley and approximately 20 km from Ergani Maden, one of the largest copper sources in Turkey, materials from all occupation layers demonstrate the use of native copper metal and minerals. Parallel traditions in working lithic and metal minerals include the production of perforated stone beads and cold-hammered and annealed metal beads rolled into small tubes (Maddin, et al. 1999). Similar use of metal minerals and annealed and hammered native copper beads has been noted in

Central Anatolia at the sites of Aşıklı Höyük (Esin 1995, 1999; Yalçın and Pernicka 1999) and Çatalhöyük (Mellaart 1964). Two native silver tube beads from Domuztepe in modern Kahramanmaraş date to the mid-sixth millennium BC and show evidence of annealing and hammering (Carter, et al. 2003).

The production and consumption patterns related to these materials indicate that they were used to demarcate social boundaries and were also likely indicators of social status. These scarce materials were naturally circumscribed by rugged highland terrain and their technological alteration into ornaments required sufficient specialized knowledge. Later metallurgical traditions correspond to two important patterns that emerge during the Neolithic. First, the establishment of metal materials and technologies as a source of wealth developed alongside the emergence of increasingly complex social institutions. This is best evinced by the presence of scarce materials associated with early monumental architecture at many important Neolithic sites along the Taurus such as Çayönü, Nevalı Çori, and Hallan Çemi (Lichter 2007). Second, the emergence of long-distance trade patterns promoted path-dependent economies that influenced the way materials were exchanged and distributed. Economic interaction patterns between highland source areas and adjacent lowland agricultural villages established a successful way of accessing and distributing these materials that would have dramatic network effects.

2.6 Site-centered production: centralization, nucleation and balkanization

Significant socioeconomic reorganization during the Early and Middle Chalcolithic (ca. 6000 – 4000 BC) created a mosaic of complex cultural regions across Anatolia (Düring 2011; Schoop 2005). Regionalized political affiliations and exchange networks focused largely on local materials, although certain materials (e.g., obsidian) are known to have been transported over

very long distances (Carter, et al. 2008; Healey 2007). Important developments in extractive metallurgy occur during this crucial time period in lowland regions that are proximate to highland resource areas such as in the Altınova, in Cilicia and in the Amuq Valley. As Yener et al. note (1996), these regions are set apart from other sites in northern Mesopotamia by virtue of their direct access to scarce materials, while at the same time sharing similar highly-productive agricultural conditions. Interregional patterns of competition and cooperation, and the management of access to lowland centers, is identified by the possible innovation of city walls or enclosures at sites like Hacilar, Kuruçay, Mersin and Değirmentepe. In addition, the repertoire of metal objects drastically increases during this time period. Ornaments and jewelry were produced with tools and weapons by the Late Chalcolithic period, which provides sound evidence for the diversification of the technology as it was variably adopted in different parts of Anatolia.

Dating to the beginning of the fifth millennium BC, a series of metal axes, chisels and other tools from Mersin (XVI – XIV) in Cilicia (Garstang 1953) demonstrate the development of casting technologies and the possible smelting of ores into metal (Caneva 2000; Esin 1969; Yalçın 2000). Unlike objects made from native copper, which is relatively pure, the metal objects from Mersin show significant amounts of antimony (0.032-0.748 wt%), arsenic (<0.006-0.604 wt%), and tin (<0.005-0.01 wt%) (Yalçın 2000: 114). The presence of these elements indicates that the metals were derived from the smelting of polymetallic ores, several sources of which have been documented to the north in the Central Taurus Mountains (Yener, et al. 1991). Problematically, no production debris (e.g., slags, crucibles, furnace installations) has been discovered at Mersin dating to this early period, so the actual characteristics of extractive metallurgy can only be inferred from these finished products.

Some of the first evidence for the organization of extractive metallurgy comes from the site of Değirmentepe and dates to the end of the 5th and beginning of the 4th millennia BC (Esin and Harmankaya 1988; Yener 2000: 33-44). Değirmentepe is a multi-period village along the Upper Euphrates with a significant Middle and Late Chalcolithic occupation sharing cultural affinities with Ubaid Mesopotamia. Several houses were excavated to reveal that many of the households were involved with many metallurgical activities from ore processing, smelting and possibly melting and casting. Importantly, many of the households also had evidence of administrative activities including seals, sealings, tokens, and bullae of local and foreign styles (Esin 1990) and their production (Arsebük 1986).

Several different polymetallic ore sources are known in the region and their use has a long history that starts during this period. Metallurgical debris from the site indicates that the organization of production relied heavily on nearby ore sources. However, it is not clear whether or not mining sites that date to this period took part in smelting activities. The presence of several furnaces and some raw ore materials indicate that primary production was a village activity and that ores could have been transported directly from the source areas and consumed at the village. Parallels for these activities are noted at the nearby sites of Norşuntepe (Hauptmann 1982) and Tepecik (Esin 1982). The analysis of slag debris and slaggy encrustations on crucibles, however, suggest that much of the production may have been the further refinement of copper-rich slags and copper metal in a secondary or final production stage to produce arsenical copper alloys (Kunç and Çukur 1988; Özbek 1985). It is entirely possible that ores and slags were smelted elsewhere and then brought into the village for further working and refinement. Metallurgical production debris is evenly distributed across the site, which suggests that the

organization of production may be characterized as an independent household or nucleated workshop level production.

The Late Chalcolithic site of Arslantepe, near to modern Malatya along the Upper Euphrates, provides an excellent contrast to the organization of metal production at Değirmentepe. Arslantepe was the center of a large network of Late Chalcolithic villages during the so-called Uruk period of Mesopotamia. This period is particularly known for the intrusive activities of Mesopotamian communities into regions outside their political and cultural core in southern Iraq. Algaze (2005), Stein (1999), Rothman (2001) and Frangipane (2001a) have argued for different forms of interaction among communities in Anatolia and Mesopotamia during this period. It is clear that Mesopotamian communities at this time sourced metal materials and finished products from the Taurus and Zagros, although the nature of those interactions, as based on symmetrical or asymmetrical relations, is hotly debated. Excavations at Arslantepe indicate a certain degree of interaction with Uruk Mesopotamia, but there was also a local elite presence independent of Uruk control. A large monumental structure dating to the Late Chalcolithic (period VIA) contained several rooms for storage, which suggest that the building was the center of a local power and possibly a redistributive center (Frangipane 1997).

Frangipane (2001b) notes two opposing forms of power at Arslantepe in this period – a local kingdom and a later intrusive power related to Transcaucasian migrations into southeastern Anatolia and Syro-Palestine – both of which correspond to developments in Mesopotamia. Metallurgical traditions and the economic networks inferred from the analyses of the raw materials, production debris, and finished goods differ significantly between these two periods. Palmieri (1999) defines a significant relationship among successive periods (VII ca. 3700 – 3400 BC, VIA ca. 3400 – 3000 BC, and VIB 3000-2900 BC) and the types of alloys and ores. During

the Late Chalcolithic (period VIA), communities used polymetallic ores with varying quantities of arsenic, antimony, silver, bismuth, and nickel. Ore selection changes to the predominant use of copper-iron sulphides during the Early Bronze Age (period VIB), which indicates possible shifts in trade networks and metallurgical traditions. Finished artifacts also reflect these variations with a predominance of copper-arsenic alloys but also alloys of copper-silver and copper-arsenic-nickel (Hauptmann, et al. 2002b).

A hoard of 21 metal alloy weapons dating to the VIA period contain almost predominantly copper-arsenic alloys ranging from 2.57-6.08 wt% arsenic. Intriguingly, lead isotope analysis (LIA) of the objects suggests they originate from several likely sources in the northeastern Pontides near to the Black Sea (Hauptmann, et al. 2002b: 61-62). In contrast, metals from a large tomb dating to the VIB period, contemporary with large-scale changes in material culture related to the Kura-Araxes culture of Transcaucasia, demonstrate a change in alloy preference and provenance. In addition to copper-arsenic alloys, several non-utilitarian objects made of a silver-copper alloy and objects made of a copper-arsenic-nickel alloy reflect gross changes in ore consumption and alloy preferences. LIA of the copper-arsenic alloys from Period VIB suggest a similar provenience to those from the earlier period VIA, but the copper-arsenic-nickel alloys may reflect a more local source or one potentially to the north-east in Transcaucasia or the Central Taurus. The copper-silver alloys have a unique isotopic signature that does not allow their identification with any known ore source, but does match with other artifacts from Central Anatolia (Hauptmann, et al. 2002b; Sayre, et al. 2001).

Slag analyses from the site suggest a wide-ranging technological variety of extractive metallurgy. Perhaps most significantly, a class of slags containing prills of an arsenic-nickel-iron speiss (Palmieri, et al. 1999: 145) indicate that alloying strategies may have involved the

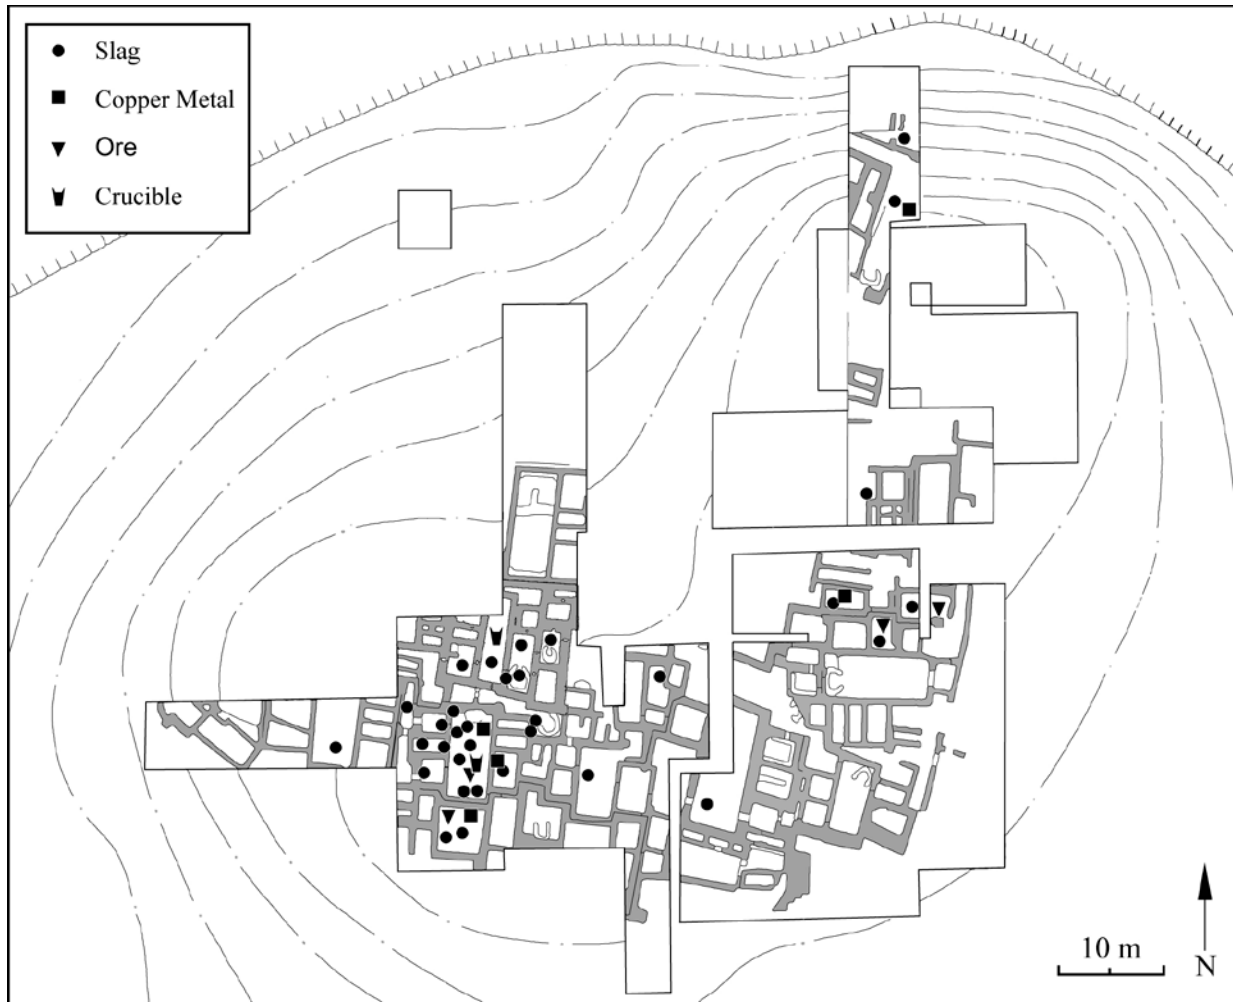


Figure 2.2: Değirmentepe with metallurgical remains which demonstrate both primary and secondary production technologies existing together (Lehner and Yener 2014: Fig. 20.5, Müller-Karpe 1994: Fig. 4).

production and trade of this special cosmelting product used to produce early copper-arsenic alloys (Rehren, et al. 2012; Thornton, et al. 2009). It may also have been a by-product of smelting copper-nickel-arsenic ores. However, the use of speiss as a necessary ingredient in the production of arsenic alloys may help explain the emergence of high-arsenic copper alloys. Further complex advances in primary smelting is also evinced in the earliest production of silver from the reduction of argentiferous lead ores. At the sites of Habuba Kabira and Fatmalı-Kalecik, both dating to the Late Chalcolithic, the presence of lead-rich litharge provides the earliest

evidence in the Near East to date for the reduction of argentiferous lead ores into silver metal using cupellation (Hess, et al. 1998; Pernicka, et al. 1998).

Recent excavations at Çamlıbel Tarlası have explored in detail the activities of a small Chalcolithic village in Central Anatolia that thrived ca. 3590 – 3470 cal. BC (Schoop 2008, 2009, 2010, 2011). Four occupational phases (CBT I – IV) of rectangular architecture with stone foundations and rammed earth revealed a range of activities including different stages of stone tool and metal production. All phases show the presence of metallurgical slags, ores, pounding stones, crucible fragments, a diagnostic ring-idol mold, and finished metal objects. Analyses of the slags by Rehren and Radivojević (2010) demonstrated that the primary reduction of sulphide and oxide ores into pure copper metal was an activity on site. This explains the presence of pounding stones, which were used in the benefaction of ore materials for their preparation in a smelt. Fieldwork within the vicinity of the site discovered a large outcropping of sulphide and oxide ore minerals (Marsh 2010) that seem to correlate with the slag analyses. Near to Çamlıbel Tarlası, the Late Chalcolithic site of Yarıkaya demonstrates a similar household-level production of metal (Hauptmann 1969; Schoop 2005). Production debris, including several crucibles with a thin layer of encrusted metalliferous residues, indicates that producer communities in North-Central Anatolia lived in small household aggregates composed of part-time specialists.

Published analyses of a few finished artifacts from Çamlıbel Tarlası demonstrate that the metals used are arsenical copper (Rehren and Radivojević 2010: 215). As the current analyses of slags from the site do not show any presence of arsenic in the copper nor iron-arsenic-nickel speiss, it is not clear whence the arsenic derived. Recent surveys by Özbal and his colleagues (Özbal, et al. 2008) discovered a range of arsenical minerals to the north of Çamlıbel along the

Pontide belt. These resources may have been used in the production of the arsenical copper found at Çamlıbel, although direct evidence for this has yet to be demonstrated.

The emergence of complex metallurgy, as highlighted above, is clearly a reflection of the availability of necessary resources, appropriate technologies, and the ability to free up labor for specialized production. The regionalism and localization of political entities that occur with urbanism, as highlighted with the administrative technologies and monumental architecture of Arslantepe, allowed for constrained networks of production. It is not clear how groups acquired the necessary raw materials for the various technologies examined above. During these periods along the Upper Euphrates, many stages of metal production occurred perhaps simultaneously and in the same location. The sites in this region can be characterized as having in-site production with nucleated production areas. Similar patterns are recognized for other regions in regards to finished materials with the caveat that local alloying traditions likely remained a conservative tradition often unique to the area in which it was produced (Yakar 1984, 1985; Yener 2000). Ores were purposely chosen for their properties and alloys were produced from a range of complex and divergent traditions that likely reflected the local socioeconomic and political networks of production. The presence of arsenical copper alloys across Anatolia, for example at Ilıpınar in north-western Anatolia (Begemann, et al. 1994) and İkiztepe near to the Black Sea (Bilgi 1984, 1990; Özbal, et al. 2002a; Özbal, et al. 2008), means that while divergent patterns of metal production were localized, some metallurgical techniques, perhaps utilizing speiss, were shared across very long distances.

2.7 The Development of Tin Bronze and Specialized Mining Communities

During the Early Bronze Age (ca. 3000 – 2000 BC), several regional polities across Central Anatolia and regions south of the Taurus began to participate in long-distance trade for materials like lapis lazuli and tin that possibly extended as far east as modern Afghanistan (Delmas and Casanova 1990; Muhly 1973a, 1973b; Muhly and Wertime 1973). Two major innovations in copper metallurgy during this time period altered the way metal technology was organized. First is the advent of an intentional copper-tin alloy (i.e., tin-bronze). The alloying of tin and copper hardens the metal, alters casting properties, and changes its color to yellowy-gold if the correct amount of tin is incorporated (Scott 2011: 109-173). Second, the organization of production shifted from site-centered metallurgy to a multi-tiered hierarchy of production (Yener 2000: 67-70) allowing for the development of large scale industrial systems to evolve for the first time in Anatolia.

The earliest bronze alloys occur in the Near East during the late 4th and early 3rd millennia BC (generally the Late Chalcolithic and EB I), whereas the wide spread consumption of bronze can be dated to the mid-3rd millennium BC and extends from the Persian Gulf to the Aegean (Pare 2000; Pernicka 1998; Weeks 2004). Many of the earliest bronzes come from early excavations whose exact contexts and dates cannot be directly confirmed using independent absolute dating techniques¹. Furthermore, analytical sensitivity has improved considerably for both lower and upper limits of detection of important elements relating to metal technology. Given these uncertainties we are still presented with plausible evidence for a range of early tin bronzes whose adoption in the Near East can be confidently dated to at least the early 3rd millennium BC. Examples of copper tin alloys across Mesopotamia include several objects

¹ See Buchholz (1967), de Jesus (1980), Esin (1969), and Muhly (1973a) for a comprehensive discussion of these older analyses and the references therein.

dating to the early 3rd millennium BC from Tepe Gawra (Hauptmann and Pernicka 2004: no. 267, 289) the Y cemetery at Kish (Hauptmann and Pernicka 2004: no. 8, 10, 18; Müller-Karpe 1989; Stech 1999), Tell Razuk (Hauptmann and Pernicka 2004: no. 723), and Tell Agrab (Hauptmann and Pernicka 2004: no. 45). Several more examples from a burial dating to the EB I in northern Syria at Tell Qara Quzaq along the Middle Euphrates show appreciable evidence for the use of copper tin alloys (Montero Fenollós 1995, 1997, 2000, 2004).

Among the earliest examples of copper tin alloys in the Near East include a group of ornaments from Kalleh Nisar (northwestern Iran) with tin contents ranging from 3.5% to 14.8% and are considered to be purposefully alloyed. These ornaments come from a burial excavated by Louis Vanden Berghe in the 1960s and date to the EB I in Luristan, which is roughly contemporary with the Jamdet Nasr to Early Dynastic I (ED I) periods in Mesopotamia (Fleming, et al. 2005; Vanden Berghe 1970). Although not scientifically tested, it is likely that the tin for these early tin bronzes in the Iranian highlands was derived from the small occurrences of tin located in the Astaneh-Sarband region (Nezafati, et al. 2008, 2009, 2011). Further examples of early tin bronzes and possible tin occurrences are noted in the Caucasus in Dagestan (Kohl 2002), Armenia (Meliksetian, et al. 2003), and Georgia (Erb-Satullo, et al. in press).

Along the northwestern bend of the eastern Mediterranean at sites in Cilicia and within the Amuq Valley, early copper tin alloys are first observed in early 3rd millennium BC contexts. For example, six figurines from a cache at Tell Judeidah and probably dating to the Amuq G period were produced from a cast copper tin alloy (Braidwood, et al. 1951). Although the date

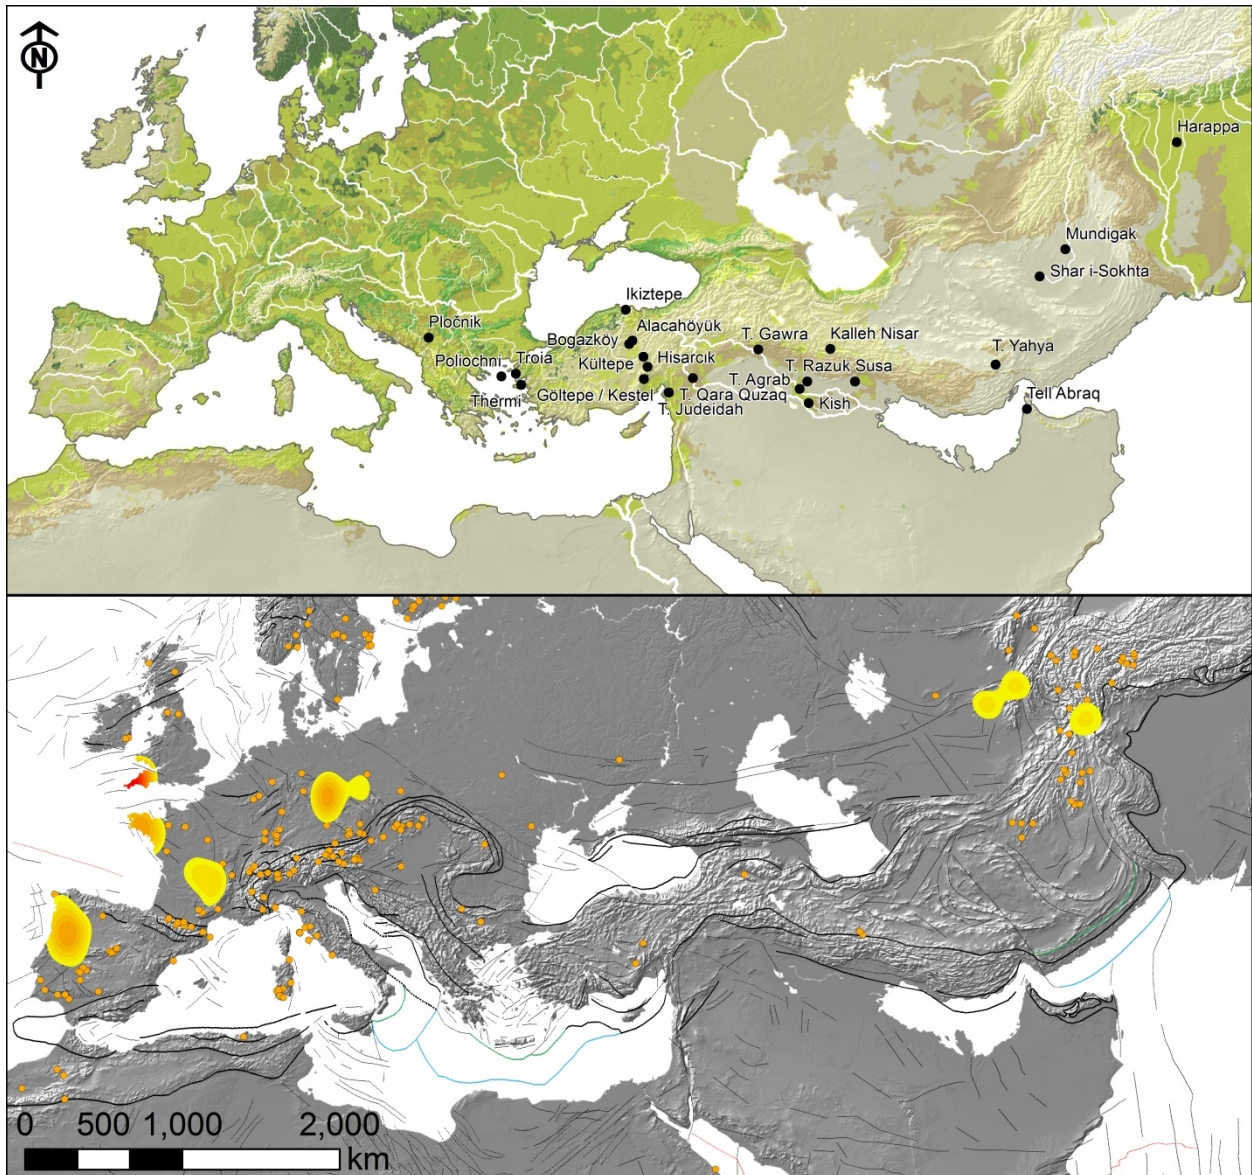


Figure 2.3: The distribution of known tin sources/occurrences and the earliest sites where past communities consumed tin metal across the Near East and Central Asia demonstrates a major geographic disparity. The earliest tin bronzes occur along the piedmont of northern Syro-Mesopotamia and western Iran (above). The largest tin-bearing regions (in gradients) occur in Europe and Central Asia, while smaller occurrences (points) are irregularly distributed throughout the region and tend to be more proximate to larger tin sources (below) (Lehner 2014c).

and context of the figurines has been seriously questioned (Hall and Steadman 1991: 227; Seeden 1980: 8; Yakar 1984: 70), renewed investigations of Amuq G copper alloys and production debris from Tell Judeidah (Adriaens, et al. 2002) and radiocarbon dates from a sounding in 1995 confirming the Amuq G chronology (Yener, et al. 2000: 197) reinforce the evidence for early tin consumption at the site. Early 3rd millennium deposits at Tarsus (EB II) in Cilicia also provide several examples of early copper tin alloys (Esin 1969; Kuruçayırılı and Özbal 2005). Near to modern Gaziantep at the site of Gedikli, analyses confirmed the presence of copper tin alloys from Level III (Bengliyan 1985), which are dated to the EB II with radiocarbon dates bracketing the assemblage between 3060-2500 BC (1 σ) (Duru 2006: 206).

Empirical evidence for copper tin alloys in central and eastern Anatolia appears to date somewhat later. It is presently unknown if the adoption of tin use in these regions was a result of a slower technological diffusion rate, because relatively fewer analyses of Late Chalcolithic / EB I metal assemblages have been conducted to date. This is partly due to the relative paucity of contexts in these periods in central Anatolia. An important exception includes the Late Chalcolithic and EB I contexts from İkiştepe and Bekaroğlu in north central Anatolia. Several hundred analyses of weapons, tools, and ornaments demonstrate the prolific consumption of arsenical copper and a near conspicuous absence of copper tin alloys² (Bilgi 1984; Özbal, et al. 2008; Özbal, et al. 2002b; Zimmermann and Ipek 2010), which parallels patterns observed in most EBA contexts in Transcaucasia (Edens 1995). Analysis of Late Chalcolithic and EB I fine weapons and ornaments at the site of Arslantepe shows a somewhat different pattern of copper alloy production and consumption without the use of tin. Here we find the production of copper silver alloys and arsenical copper with significant lead, nickel, and antimony contents

² Two exceptions from İkiştepe include a spearhead (İ/93-120) and a dagger (İ/93-043) that date to a later EBIII occupational context and contain 1.05% and 1.25% tin respectively (Özbal, et al. 2008: 68).

(Hauptmann, et al. 2002b). A similar compositional profile from several objects at the roughly contemporary sites Tepecik and Tülintepe have been described, however also including the presence of a single rolled head pin with 5.27% tin (Yalçın and Yalçın 2009: 137). Unfortunately the date of these objects, which were discovered by chance in a hoard found in 1966, cannot be independently verified beyond stylistic comparisons and are therefore unreliable. Nearby at Norşuntepe, select analyses of a long sequence of copper alloys demonstrate that tin bronzes do not appear until levels 8-6 which date to the EB III (Pernicka, et al. 2002: 117).

The well-known metal assemblages associated with the Early Bronze Age burials at Alacahöyük provide some of the earliest examples of a well-developed tin bronze tradition in central Anatolia. Several so-called standards and other copper-based objects were first analyzed by Esin (1969), which demonstrated that cast tin bronzes were consumed alongside with arsenical copper. Recent surface analyses of several objects confirm the presence of tin bronzes, however also demonstrating a remarkable diversity in metal compositions, including alloys of copper silver gold, copper silver, leaded tin bronze, and one example of an antimonial tin bronze figurine (Yalçın 2010, 2012). Stylistically and contextually similar objects from the nearby sites of Horoztepe and Mahmatlar (Esin 1969), Kalınkaya (Yıldırım and Zimmermann 2006; Zimmermann and Geniş 2012), and Resuloğlu (Zimmermann 2012; Zimmermann and Yıldırım 2007; Zimmermann, et al. 2009) all attest to a similar profile of metal consumption.

There is not yet an absolute chronology which defines the central Anatolian Early Bronze Age which is capable of linking these sites and the metallurgical tradition that they collectively represent. It is not out purposes to enter into a discussion of Early Bronze Age chronology in this region, which is very much in dispute, but suffice to say it is now clear that the Alişar sequence, which was developed in the 1930s-1960s, needs to be critically reexamined in light of

chronological inconsistencies across the region (Ivanova 2013: 233-237; Schoop 2005: 66). The important ongoing research at nearby Çadır Höyük promises to resolve some of the problems (Steadman, et al. 2013; Steadman, et al. 2008). New work by Spagni at Alişar Höyük and nearby Çadır Höyük, for example, demonstrates that tin bronze consumption develops during the mid-3rd millennium (personal communication 2014). Nevertheless, relative interregional chronologies based on stylistic comparison variously place the Alacahöyük burials in the mid to late 3rd millennium BC (Bachhuber 2008; Gerber 2006; Gürsan-Salzman 1992). The work at Kalınkaya and Resuloğlu, which has important parallels with EBA Alacahöyük, dates the burials and settlement to the late 3rd millennium BC (Yıldırım 2006; Zimmermann 2007). Recent analyses by Yalçın, however, are beginning to provide an absolute chronology based on three radiocarbon dates derived from charcoal trapped in the corrosion of some of the copper-based objects (2010: 61-62). These dates would conservatively place the burial deposits into the early to mid-third millennium BC, roughly contemporary with Troy I and Amuq H. Further analysis is required before this important data can be interpreted with any probabilistic confidence, answering whether this tradition of bronze production and consumption extended through many centuries in the 3rd millennium, or if this tradition represents a short period of use shortly before the emergence of numerous of regional urban centers across Anatolia.

Evidence for the adoption of tin bronze is comparably better understood in northwest Anatolia, where analyses of materials from the Troad and across the Aegean demonstrate the consumption of tin bronze by the mid-3rd millennium BC. Data from the Troad, primarily from the sites of Troy and Beşiktepe, show that bronze consumption is confirmed in the Troy I period during the first half of the 3rd millennium BC (Begemann, et al. 2003; Pernicka, et al. 1984), and with a rapid adoption in use by the Troy II period (Pernicka, et al. 2003). A similar pattern can be

observed in the Aegean at sites like Poliochni on Lemnos (Pernicka, et al. 1990), Thermi on Lesbos (Begemann, et al. 1995), and Kastri on Syros (Stos-Gale, et al. 1984).

Lead isotope analysis of many mid-3rd millennium BC copper tin alloys roughly contemporary with Troy I and II from northwestern Anatolia and the Aegean demonstrate that the copper in the bronze is distinct from many of the copper ores from these regions (Begemann, et al. 2003; Pernicka, et al. 1984). This highly radiogenic lead is probably derived from ores of at least Precambrian age, the rocks of which are almost entirely unknown to the Aegean, Anatolia and the Middle East more generally. Additionally, because placer deposits of cassiterite have little to no trace lead, the lead from the bronzes is most likely derived from the copper. Lead isotope measures from these studies also suggest that the copper used to produce arsenical copper, a much older metallurgical technology, is likely sourced locally. This influx of imported copper is observed elsewhere in the Aegean (e.g. Kastri) and from sites as far as in Oman and the United Arab Emirates (Weeks 1999, 2004), which coincides with the rise of tin bronzes in the region. This combined evidence suggests that the earliest bronzes of northwestern Anatolia and the Aegean regions were imported and not locally produced.

The second major innovation in the Early Bronze Age is the reorganization of and use of labor to scale up production at second-tier processing sites in mining regions (Yener 2000: 67-68). Increased urbanization and a diversified means of acquiring important subsistence resources through pastoralism and improved agricultural practices helped create a social environment in which economically-specialized settlements emerged to mediate access to metal resources. The development of second-tier processing sites occurred as economic alliances grew larger and more complex, effectively networking multiple regions together to hedge against the uncertainty

of access. This uncertainty was derived from several variables, including seasonality, finite availability, and sudden shifts in political and economic networks.

Yener and her colleagues began a survey of the Bolkardağ mining district in the early 1980s to examine the economic and technological components of one of the earliest known mining regions (Yener 1986; Yener and Özbal 1986; Yener, et al. 1989). Several small sites along the valley suggested that much of the activity in this region was the seasonal extraction of ores. Excavations at the Early Bronze Age mining village of Göltepe and the Kestel mining complex demonstrated that these communities were actively involved in the intensive and sophisticated extraction of polymetallic ores and the reduction of these ores into raw metal.

The site of Göltepe was a mining village situated on top of a large natural hill facing the Kestel mine complex. The hill measures close to 60 hectares and is fortified at the summit with a circuit wall. Excavations from 1990 – 1993 uncovered a total of 1500 m² of the settlement dating to the Late Chalcolithic through to the EB III phase (from ca. 4375 – 3750 BC to 2880 – 2175 BC). Habitation structures in period 3 (EBII) are semi-subterranean to fully subterranean and would have had superstructures of wattle and daub (Figure 2.3). One house in particular had a full range of metallurgical production paraphernalia including crushers, mortars, a crucible, and kilos of ground ore and ore nodules. The house contained large EBA burnished orange-ware jars full of ground and refined ore and processed waste materials containing 0.28 – 3.65 wt% tin, 6.90 – 41.00 wt% iron, plus minor amounts of arsenic (Adriaens, et al. 1999a; Vandiver, et al. 1992). The relatively high concentration of tin in the prepared ore is evidence that one of the primary activities of the metal-smiths at Göltepe was the preparation of tin metal. The single most significant find at Göltepe relating to the processing of tin has been discovery of over one ton of vitrified earthenware bowl furnaces or crucibles with a glassy slag accretion rich in tin.

Constructed with a coarse straw- and grit-tempered ware, they range in rim size from 6 to 50 cm in diameter and have vitrified surfaces containing between 30-90 wt% tin content (Adriaens, et al. 1999a; Adriaens, et al. 1996, 1999b; Adriaens, et al. 1997). Activities involved the intentional production of tin metal by reduction firing of tin oxide in crucibles in a labor-intensive, multi-step process carried out between 800° and 950°C (Özbal 2009; Yener and Vandiver 1993). Metal artifacts from the site, including copper-tin, copper-tin-arsenic, and copper-tin-silver alloys, range from 4.75 – 12.3 wt% tin and some have traces of gold (1.23 – 52.1 ppm), which are comparable with the Kestel ore analyses (Yener, et al. 2003).

The recent discovery of central Anatolian tin deposits in the vicinity of Kültepe has ushered in a reinvigorated research program regarding the tin problem. This new deposit of tin, located near the town of Hisarcık along the hilly flanks of the near-4,000-m stratovolcano Erciyes Dağ, is also associated with scores of ancient mining operations (Yener, et al. 2015). The tin deposits were first discovered by the MTA (General Directorate of Mineral Research and Exploration), specifically by geologist Evren Yazgan (Yener, et al. 2015). Initial analyses of select samples from an outcropping demonstrated that cassiterite was associated with iron oxides and a rare iron-arsenic oxide mineral called yazganite. These deposits formed in a subsurface volcanic environment and were deposited on the soft andesitic walls of near-surface fumaroles as hot gases that cooled when they escaped into air. As such, they differ substantially from tin ores more common to Europe and central Asia, which primarily derive from hard granitic lithologies.

The concurrence of tin and iron would have presented significant challenges to ancient smelters hoping to reduce tin metal from these ores. Tin and iron oxides have a similar reducibility, and in order to control for the amount of iron as an impurity in the tin metal, ancient smelters would have faced a trade-off (Smith 1996). Under low reducing conditions, nonmetallic

tin would be trapped in slags, effectively reducing the efficiency of the smelt, even if metallic prills of tin could be retrieved. Conversely, tin metal extraction could be increased through high reducing conditions, a process which would also admit significant quantities of undesirable iron. This results in a product called hardhead, an iron-tin alloy. Additionally, these natural deposits could have been used in a co-smelting or mixed-smelting technique, whereby smelters reduced the tin ores together with copper ores or directly in molten copper through a cementation process. Preliminary archaeological surveys in the region, led by Fikri Kulakoğlu, Ryoichi Kontani, Yuichi Hayakawa, and Aslıhan Yener, also identified industrial sites and ancient mining operations in the region of the tin deposits. One such site, called Teknekayası Höyük, has been dated to the third millennium BC by associated pottery, suggesting that many of the ancient mining operations in the area may be related.

If the current interpretation of the region holds, then along with the Bolkardağ occurrences this would be the second known tin occurrence associated with Bronze Age industries in Anatolia. These results suggest that early metallurgy, especially given the highly dispersed nature of resources intrinsic to the craft, developed from the utilization of a diversity of deposit types, including smaller occurrences of metal deposits, many of which could have been totally exhausted. These results also have direct impact on the hypotheses of bronze adoption in the region. We must now consider the role of small deposits of local tin in the earliest innovation and adoption of bronzes in the Near East; however, it is also important to remember that these results do not necessarily falsify the standard model, which is based on second millennium BC textual and archaeological data. Local small-scale production of tin during the third millennium BC could have conceivably operated alongside the importation of exotic tin produced from distant operations elsewhere in the Old World. Rather than explaining the early presence of

copper-tin alloys as a product of long-distance exchange, these new alloys were being produced locally by innovations in technological organization that focused on the primary extraction of tin ores (Yener 2009) but also through regional trade networks that linked these regions to other areas of production.

2.8 Conclusion

In this chapter, I first described briefly the geological background and distribution of ore resources in Anatolia. The distribution of these resources ultimately influenced the extent to which distant lowland agrarian communities conducted trade relations with highland resources areas. One of the most distinctive characteristics of Anatolia, and even highland Iran, is the incredible diversity of metal resources, including the increasing likelihood of tangible, though small tin occurrences. Unlike the southern Levant, Anatolian deposits are characterized by their polymetallic nature, though punctuated by just a few massive sulphide deposits like Ergani and Küre. I first argued first that Anatolian metal industries and their organization must be seen in light of local developments and patterns. Past views of the organization of production, such as those imported from the southern Levant or Mesopotamia (Thornton 2009), do not fit the data in Anatolia. Rather, we see the development of what has been called the “balkanized technological horizon” during the mid-late Chalcolithic (Yener 2000). These developments occurred *before* formal interaction began with Mesopotamian communities south of the Taurus. The effect of these regionalized traditions is the production of many different types of metal products by many, likely yet unidentified, means of production. Not until the Early Bronze Age do we witness the effects of larger-scale interaction networks on technological traditions.

Second, I argued for the development of specialized labor evinced by settlement hierarchies based on a cooperative model that sees production specialization as a way to mitigate uncertainty of access to crucial raw materials and finished goods. The beginnings of this can be seen at the site of Göltepe in the Central Taurus, although indications of long-distance exchange have been demonstrated to exist earlier despite a more constrained, site-centered mode of production. These sites demonstrate how the intensive production of locally-available materials creates incentives for long-distance exchange of other scarce materials necessary for the production of socially-desirable materials, such as copper-arsenic or copper-tin alloys.

As will become apparent, evidence for metal production and consumption is poorly studied for later periods, despite the fact that some types of data are available. The history of metallurgy is generally left with the adoption of tin bronze, however we know very little about how and precisely where this technology was adopted. Furthermore, tin bronze does not appear to replace arsenical copper rapidly, but rather these two different technologies, which required very different sets of working knowledge and economic bases, are used in parallel for more than a millennium. Yener's work on Early Bronze Age metal production is only assumed to continue during these later periods, however this has never been tested (however, see Lehner 2014a, 2014b; Lehner and Schachner in press). In the following chapters, I provide new evidence for a sequence of production strategies that further highlight the role of localized traditions, despite periods of political and economic expansion.

CHAPTER 3: METAL PRODUCTION AND TRADE DURING THE BRONZE AND IRON AGES IN CENTRAL ANATOLIA

3.1 Introduction

In order to understand the organization of metal production and trade during the rise of Boğazköy and Kerkenes Dağ as regional centers, it is first necessary to examine the development of regional polities in central Anatolia more generally. In the previous chapter, I argued that by the Early Bronze Age (EBA) in Anatolia (ca. 3000 – 2000 BC), metal technologies evolved in a landscape of increasingly complex societies. During the EBA, empirical evidence demonstrates that individuals and coalitions opted to select strategies of diversification and specialization to not only overcome the organizational problems of large-scale cooperation but also to benefit from it. These interrelated strategies included the development of regionalized ways of primary and secondary production, an increased reliance on long-distance trade for raw materials, and finally the development of a “multi-tiered” organization of production (Yener 2000).

In this chapter, I examine how these strategies were further developed during the 2nd and first half of the 1st millennia BC. During the Middle Bronze Age (ca. 2000-1750 BC), small competing states eventually gave way to the rise of the Hittite Empire, which strategically sought to integrate much of central Anatolia and parts of western Anatolia and northern Syria. The integration of central Anatolia into the Hittite Empire was financed in part by the control of high value commodities through a system of tribute, levies and sponsorship of markets. I argue that the diversification and specialization of metal technologies during the EBA led to the elaborate and highly organized system of production and trade that we observe during these successive

periods of increased political and economic integration. I use empirical evidence from both archaeological excavations and the analyses of Old Assyrian and Hittite texts to understand the complex though fundamental relationship that producers, traders, and state institutions all had with metal materials and technologies. The increasing efforts of political entities to integrate developed polities had profound effects on the nature in which metal commodities flowed into regional centers. After several centuries of competition among smaller polities in central Anatolia, at least one sector of metal trade and production was loosely integrated into state institutions visible archaeologically and textually at the capital Hattuša.

The geographic dispersion of raw materials effectively limited how state officials, traders, and producers alike managed their access and transport to regional centers. Conversely, segments of production activities that added increasing value to copper, from refining processes to the skilled production of finished goods, appear to be often integrated into regional centers. One trajectory of this development is explained by ecological processes associated with industrial production, such as economies of scale, transport costs, and social network effects (Fujita, et al. 1999). Yet another compatible explanation for this development is the role of elite individuals and institutions that directly sponsored or controlled metal industries and trade. We now know that the specialized production activities involved in secondary metallurgy, especially in urban contexts, promoted the clustering of metal industries in regional centers like Kültepe (Lehner 2014a). These metal workshops were primarily devoted to the specialized production of various finished goods and the workshops cut across social contexts in cities of central Anatolia. By the height of the Hittite Empire during the later half of the 2nd millennium BC, texts demonstrate that temple and palace officials would commission the production of a range of objects in gold, silver, and bronze that would be distributed to local elites as a form of wealth

finance (Siegelová 1986: 110-121); however, there is no evidence to suggest that most workshops were exclusively or directly attached to the palaces or temples themselves. Rather, both textual and archaeological data are more consistent with the hypothesis that state institutions periodically sponsored specialists and workshops involved in copper production, but the working and provisioning of precious metals like gold and possibly iron likely happened directly under the control of the state.

During the Iron Age in central Anatolia, much less is known because few production contexts have ever been excavated and there is a lack of textual evidence. After the disintegration of the Hittite Empire and the abandonment of its state institutions in central Anatolia, the subsequent emergence of Iron Age polities in the region appears to have involved novel political and economic strategies (Genz 2011; Grave, et al. 2009; Grave, et al. 2012; Kealhofer, et al. 2009; Kealhofer, et al. 2010; Voigt and Henrickson 2000a). There is a resounding lack of data and theoretical discussion on precisely how these new polities organized the domestic and long-distance trade of metal and its production. Virtually all data is derived primarily from roughly contemporary cultural contexts outside of central Anatolia.

The conclusion of this chapter reiterates the original research questions to be tested in the following chapters. The archaeological and textual evidence of the 2nd and 1st millennia provide valuable insight into the relatively rapid rise and fall of complex polities. Metal commodities effectively track these processes.

3.2 Metal and markets: the evolution of the regional center in central Anatolia during the EBIII and MBA

The EBII – EBIII (mid to end of the 3rd millennium BC) in central Anatolia is characterized by incipient state formation (Düring 2011: 257-299). Multiple lines of evidence indicate this, including 1) the development of dispersed urban centers and settlement hierarchies in regions associated with the largest sites (Kontani, et al. 2014a; Kontani, et al. 2014b; Kulakoğlu 2011); 2) pronounced status differentiation (Zimmermann 2009); 3) monumental residential, religious, and defensive architecture (Ezer 2014); 4) administrative technology (Kulakoğlu and Öztürk 2015); 5) craft specialization (Lehner and Yener 2014) and 6) long-distance trade (Aruz 2006; Kulakoğlu and Öztürk 2015; Lehner, et al. 2015; Özgüç 1986b; Zimmermann 2006). These developments in central Anatolia had far reaching effects on the organization of metal production and trade, as was demonstrated in Chapter 2 specifically concerning the development of pronounced divisions of labor across primary and secondary metallurgy operations.

Beginning sometime around 1975 BC until 1725 BC, textual evidence deriving from the archives of Mesopotamian entrepreneurs and their companies at Kültepe points to the immediate presence of a variety of small states interlocked into an extensive and complex political economy (Larsen 1976). Merchants from northern Mesopotamia (most from the city-state of Aššur) developed cooperative enterprises partially based on kinship, long-distance exchange, and regional market integration to trade tin and textile commodities for gold and silver originating in Anatolia at high profit margins (Larsen 1976; Veenhof 2008). Once in Anatolia, merchants participated in a highly developed and indigenous copper exchange system to build a further surplus of silver and gold to transport back to Aššur (Dercksen 1996). The texts and

archaeological evidence demonstrate that by the early second millennium BC, just as the first enterprises were developed in Anatolia, highly competitive polities in central Anatolia, the largest of which was *Kaniš*, had already established a complex political economy based on rain-fed agriculture, pastoralism, and the long-distance trade of high value materials and objects often produced of metal. The well-documented existence of complex economic institutions and long-distance trade in Anatolia during the early second millennium suggests that an extensive exchange network was already in place during the Early Bronze Age (Şahoğlu 2005). Following the work of Sherratt and Sherratt (1991) and Helms (1993), Bachhuber (2011) theorizes that the development of long-distance exchange in central Anatolia happened because of the increased interest among competing resident elite social groups to acquire exotic materials, including most importantly metal and textiles. This pattern is recognized cross-culturally in periods of early formative chiefdoms and states in many parts of the world (Marcus 2008).

Archaeological excavations at Kültepe provided numerous details on the organization of metal production at the site. In addition to the rich archaeological record, the textual documents found at the site reveal aspects of the nature and organization of metal production. The published translations and interpretations of the Kültepe texts reveal in some detail the Anatolian-Mesopotamian networks in addition to the inter-Anatolian trade networks associated with metal industries (Barjamovic 2011; Dercksen 1996; Larsen 1967, 1976; Veenhof 2008). The production and exchange of copper, tin, gold, and silver according to the texts, which has been scrutinized in some detail by Dercksen (1996, 2005) and Veenhof (2014), indicates the presence of at least two main systems of exchange. One concerns the long-distance exchange of tin and wool for silver between Assur and Anatolia, and another consists of an intra-Anatolian copper exchange system in which Assyrians also participated. Donkey caravans with carts loaded with

hundreds of kilos of copper of varying qualities would be transported by Assyrian caravans, and presumably other social groups, over hundreds of kilometers to regional centers like *Kaneš* and *Purušhaddum* in exchange for silver to be reinvested in the copper trade or sent back to Assur to purchase more tin and textiles.

One of the distinguishing characteristics of this commodities trade represented by the Kültepe texts was the ubiquity of silver weights used as an equitable standard of exchange. The use of silver as a standard of exchange has a deep history in greater Mesopotamia, and it is likely that this practice influenced economic strategies of domestic and long-distance trade since at least the early 3rd millennium BC (Helwing 2014; Peyronel 2010; van de Mieroop 2014). The far reaching buying power of silver, in addition to the availability of markets of high value textiles and tin in Mesopotamia, allowed the Assyrian merchants to enter into an extensive trade network in place before their arrival. Favorable prices for commodities in central Anatolia created a lucrative market for entrepreneurial Assyrians, who could return with 100% return on their investments for tin and over 200% for textiles. For metals specifically, textual evidence provides the relative prices of iron, gold, tin and copper relative to silver (Figure 3.1). These data demonstrate how iron, gold, and tin were all highly valued commodities relative to copper. The exchange value of copper presumably did not offset the costs of its transport south of the Taurus to *Aššur*, which is one of the reasons the Assyrian merchants chose not to return to Assur with it.

The Old Assyrian metal and metallurgical lexicon from the tablets excavated at Kültepe indicate a precise but varied categorization of raw metal qualities, morphologies and sources. Dercksen (1996: 33-39) details the suggested meanings and contexts of several Assyrian words that describe a spectrum from high quality to low quality copper. Table 3.1 lists some of the Old Assyrian words and their respective translations according to Dercksen. Technologically, the

meanings embedded in the categories of qualities used by the Assyrian merchants demonstrates that there not only existed a great variety of metal qualities based on relative purity, but also that there was variety in metallurgical sophistication and technology.

The quality of copper also fluctuates based on where it was produced (1996: 43-45, 154-157), which is consistent with a hierarchical model of production. Much like the varying qualities of copper, there are also a significant number of other qualifiers to copper that refer to its specific source or origin. Toponyms associated with copper, such as *ša Purušhaddim* (from *Purušaddum*) or *Tišmurnāyūm* (from *Tišmurna*), indicate that copper can be signified with a particular place. Sites of known high quality metals are also attested to have a *kārum* and a palatial establishment where a local ruler resided, including the textually known cities of *Wahšušana*, *Durhumit*, *Purušhaddum* and, of course, *Kaniš*. There is also an observable relationship between sites known textually for poor quality copper and a close proximity to copper sources (Figure 3.2).

While the textual evidence does not indicate the entire production operation from primary processing sites to urban centers – from ore to pure metal – there is at least an indication of a particular hierarchy of production centers. Poor quality smelt products, probably in the shape of bun ingots, were taken from primary processing sites to secondary processing sites where they were further refined. The refining process increased the purity of the metal adding intrinsic value. Apparent refining centers, such as *Durhumit*, were significant links in the production chain of metals (Barjamovic 2011: 242-267; Dercksen 1996: 154-155; Michel 1991). Satellite sites, perhaps *Kunanamit* and *Tišmurna*, supplied poor quality and relatively impure copper smelt products to *Durhumit* so that the smelt products are further refined and exchanged for various other products, including tin, wool, textiles, and rarely, silver (Dercksen 1996: 155).

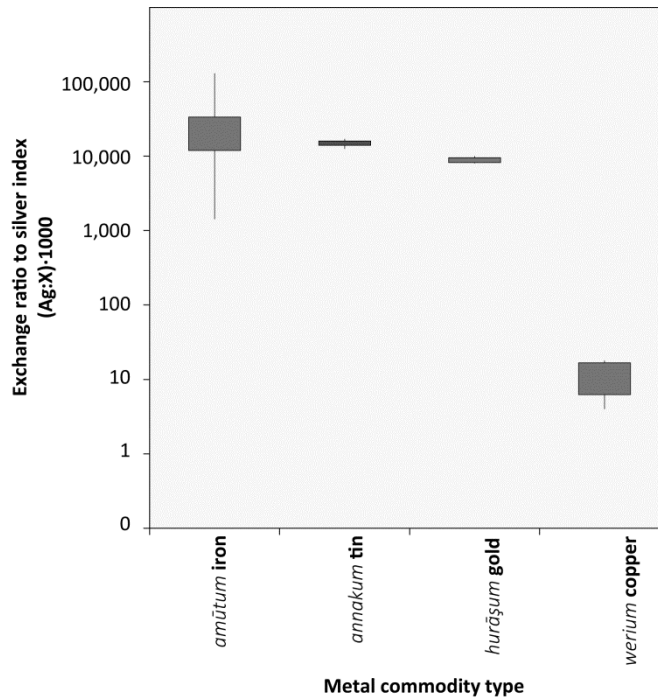


Figure 3.1: Exchange equivalencies of iron, tin, gold, and copper relative to silver in Anatolia, irrespective of quality descriptors. Comparison is possible by creating an exchange ratio index which is the ratio of silver to the commodity multiplied by 1000 and then transformed to a log-scale. Boxes and whiskers represent quartiles of equivalency data from Old Assyrian texts dating to the 20th-19th centuries BC (equivalencies from Dercksen 1996 and 2005).

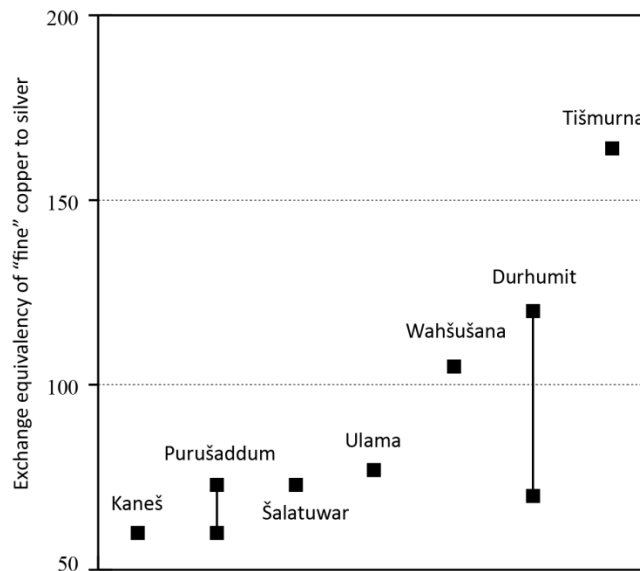


Figure 3.2: Exchange equivalencies of "fine" copper to silver recorded at different localities according to the Kültepe texts ca. 1950-1750 BC; abscissae indicate known ranges in prices (Lehner 2014: 143, fig. 2; data from Dercksen 1996).

Table 3.1: Old Assyrian descriptive metal lexicon for copper (Dercksen 1996).

| | Qualification of Copper | Notes |
|--------------|-------------------------|---|
| High Quality | <i>werium</i> | copper |
| | <i>masium</i> | “washed” or refined |
| | <i>dammuqum</i> | fine, traded in form of finished ingots (<i>šabburum</i>) |
| | <i>watrum</i> | excellent |
| | <i>zaku’um</i> | clean |
| Low Quality | <i>lammunum</i> | poor, raw |
| | <i>massuhum</i> | dirty, occurs also with silver and tin |
| | <i>sallāmum</i> | black |
| | <i>ša masā’im</i> | copper that requires refining |

The production and exchange of metals according to the proximity of urban centers to active ore sources is thus an important aspect to consider. As indicated above, there does appear to be a hierarchy of production and refinement according to the texts; however, what effect does this have on exchange equivalencies? In Figure 3.1, one can observe from ranked exchange equivalencies between high quality copper and silver that a rough 100% profit is gained when a direct exchange from the source areas to the urban centers of either *Kaniš* or *Purušhaddum* occurred. These profits would dramatically increase through the process of indirect exchanges from city to city, which is a known economic strategy (Larsen 1967). Significantly, this pattern indicates not only that a clear cost-distance relationship exists, but also that it demonstrates a significant degree of economic integration into at least two regional centers at both *Kaniš* and *Purušhaddum*, at least during the Karum II period ca. 1950 – 1836 BC (Veenhof 2003: 57).

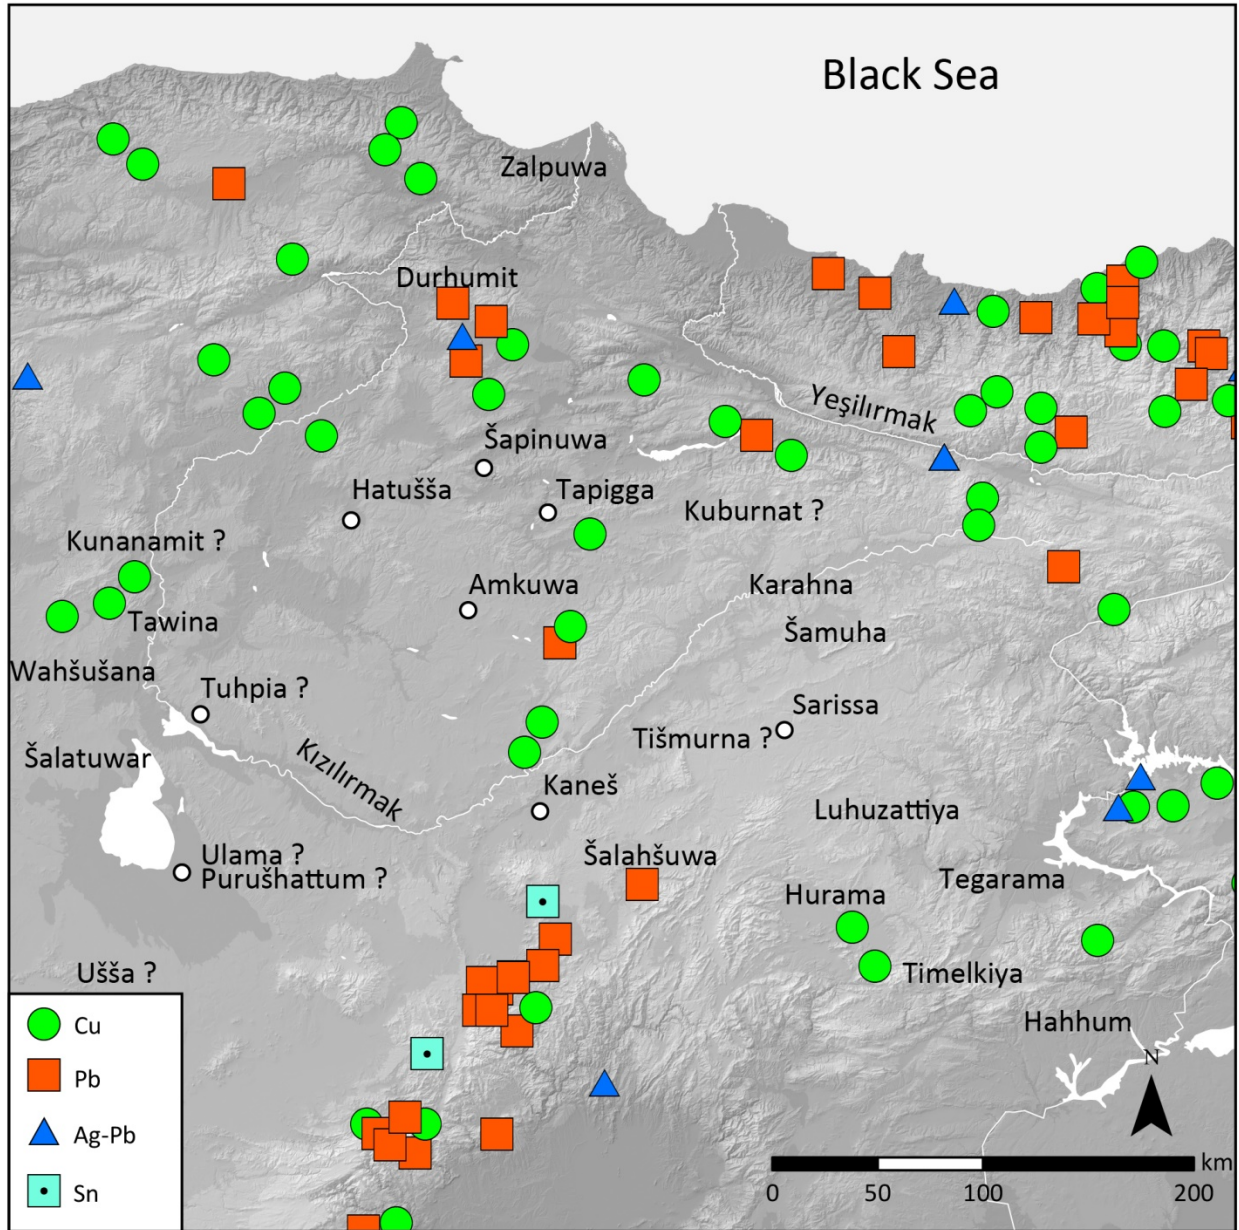


Figure 3.3: Middle Bronze Age urban geography relative to known major metal deposits. Locations marked with a point are known or probably designations, while other locations are based on geographic inferences from texts. Location data of cities adapted from Veenhof 2008.

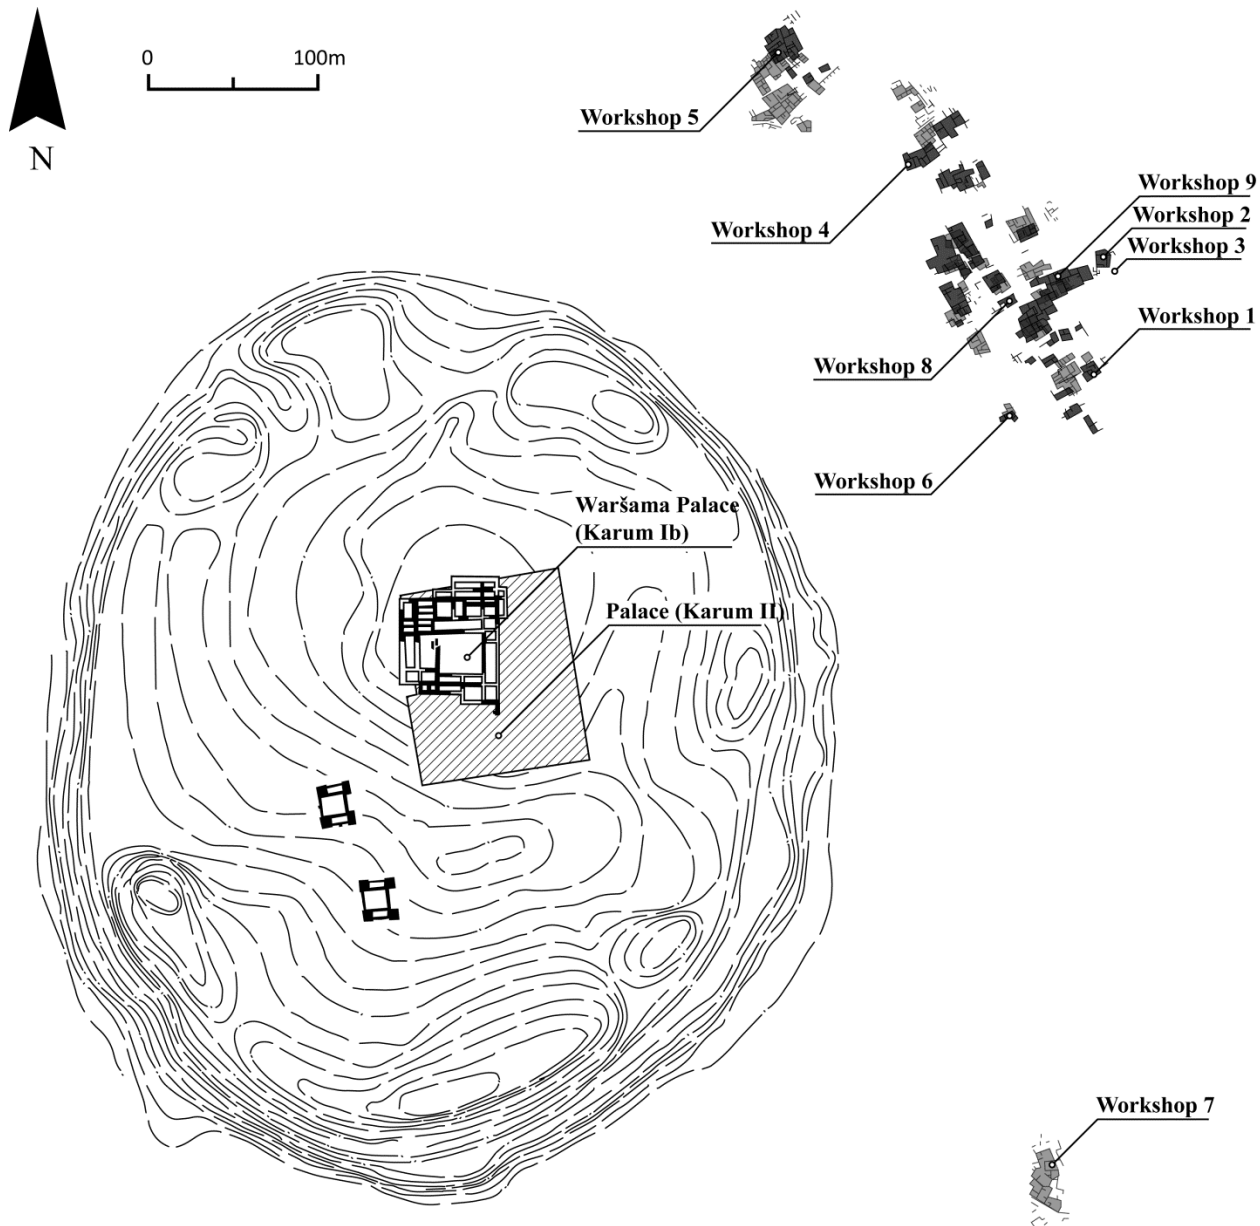


Figure 3.4: Map of Kültepe-Kaneš showing the mound with select MBA architecture and the lower city excavations with known metal workshops (Lehner 2014: 144, fig. 3; adapted from Müller-Karpe 1994: figs. 28, 36)

In addition to describing indirectly the interregional economic environment associated with metal materials, the Kültepe texts also provide evidence for craft organization at the level of the individual and workshop. In the Kültepe excavation reports, Özgüç (1955, 1986a) notes that excavated workshops in the lower city were most likely local artisans rather than their Assyrian counterparts. Closer analysis of the textual record by (Dercksen 1996: 71) indicates, conversely, that metal smiths had both Anatolian and Assyrian names. While it does not appear that the metal smiths kept records as merchants did, merchants regularly interacted with metal smiths and kept records of these interactions. According to the texts, the metal smiths would take orders in addition to selling prefabricated finished objects, such as metal vessels and tools. While the metal smiths, *nappāhum* in Old Assyrian, of *Kārum-Kaniš* appear to be organized on the household scale, their productive efforts may have been controlled to a yet unknown degree by the palace. This is indicated by the presence of a “lord of metal smiths” functionary – *rabī nappāhī* in Old Assyrian. The exact role of this functionary is not entirely understood, but it is known that this title belonged to a palace official who often dealt with the exchange of metals with merchants in addition to collaborating with or nominally managing metal workshops within the city (Dercksen 1996: 71-76).

The merchant records do provide a degree of information about the organization of metal production. A hierarchy of production can be gleaned from the texts, suggesting that multiple centers were variably involved in the whole process of transforming an ore mineral into a finished metal. Poor quality and relatively unrefined smelt products were transported and exchanged at central refining centers, such as *Durhumit*, where an active *kārum* and local palace dictated the terms of the trade to other urban centers further away. Merchants could gain increasing returns because of this hierarchy of production. In addition, the practices of the metal

smith and their functionary palace officials also signify that an existent specialization of metal production at urban centers such as *Kārum-Kaniš* was codified in the Kültepe tablets.

3.2.1 Archaeological context of metal production at Kültepe

The interface between the textual and archaeological evidence of metal production provides the opportunity to assess the validity of either body of evidence. The exchange system inferred from the Assyrian tablets places the workshops at *Kārum-Kaniš* near to the end of the metal production cycle and commodity chain. Archaeological evidence from the lower city at Kültepe does in fact indicate that secondary production was the most important metallurgical technology at the site (Figure 3.4).

At least three workshops were excavated from the Karum II period, all suggesting the manufacture of finished goods rather than the smelting of metal from ores. A workshop in the southern lower city (workshop seven) was based in a small three-roomed building that appears to have also been a residence. Finds from two of the rooms include tuyères, stone tools, standardized hematite weights, a lead ingot, several open molds of varying types, small slag deposits and an in situ furnace. What is particularly interesting about this workshop are the several different types of molds, indicating that the smith was capable of producing several different forms for a diverse community. Two other workshops in the central part of the *kārum* (workshops 8 and 9) were not as well preserved; however, they are nominally similar compared to workshop seven. A furnace with associated blowpipes and bellows was found in two different rooms of a larger structure from workshop eight (Müller-Karpe 1994: 53; Özgüç 1950).

In addition to the three workshops of the Karum II period, excavations in the residence of the local dignitary Peruwa demonstrate that this wealthy individual was also involved in the

production and exchange of metals. In a central room (room 7) of the 14-roomed building several slaggy deposits in addition to possible crucibles were discovered (Özgüç 1959: 36). In addition, the excavator noted that two large iron ingots remained in this central room, however no scientific analyses of these objects have been published. The significance of the presence of iron cannot be overstated. Assyrian words *amūtu* and *ašī'u* have been translated as iron or iron ore (Maxwell-Hyslop 1972) and was as much as eight times the value of silver (Yener 2007: 373). Textual evidence demonstrates that iron was a politically-charged material during the Middle Bronze Age, and regional palaces attempted to control it. Larsen demonstrated how one individual, Pusu-Ken, was taken and punished for having smuggled iron (Larsen 1976). The degree of control over the exchange and presumably the production of iron stems from the fact that this early technology and material was extremely sophisticated. There is also the possibility that nickel-rich meteoritic iron was the *amūtu*-metal in the Assyrian texts, but this hypothesis, tested by Akanuma (2006), demonstrates that early second millennium iron from Kaman Kalehöyük was likely produced through smelting. The presence of two iron ingots in the residence of *Peruwa* is evidence that this individual had access to a highly regulated material (Balkan 1955: 21; Özgüç 1959: 36).

The preservation of at least six excavated workshops from Karum Ib is considerably poorer than those excavated from the previous level Karum II. From what information that can be gleaned from the excavation reports, it appears that despite the destruction and hiatus, there is a significant continuity in technology and organization. The presence of crucibles, blowpipes, bellows and furnaces demonstrates again the melting and possible refining of metals taking place at the workshops. In addition, the Karum Ib workshops also appear to be attached to residential

households. This is significant because this shows that the production and exchange of metals in the lower city had the same organization as in the previous level.

One workshop in the northern Karum, however, had a substantial diversity of finds (workshop four). This workshop had a minimum of five rooms, some of which were probably storage rooms (Özgülç 1986a). In a corner next to a furnace were the remains of several molds, crucibles, bellows, blowpipes, and tuyères. The density and diversity of these finds indicates the virtuosity of the particular metalsmith and the sophistication of the workshop.

The wide distribution of metal workshops and production areas as well as other metallurgical devices, such as the wide distribution of lead figurine molds (Emre 1971), attests to the central role metallurgy had in everyday economic life at the city. However, contrary to large-scale industrial societies, there is yet no evidence that metal workshops were highly nucleated into identifiable urban areas or neighborhoods. Results of excavations indicate that metal workshops could be accommodated by a wide range of architecture, including relatively small two roomed houses or in agglomerated constructions. Residential buildings and merchant houses alternated with workshops. In addition, it appears that the workshops adjoined residential spaces indicating that the smiths may have lived and worked in the same place. There is not a steady building type for workshops. In addition, inventories of the buildings in which craft activities were demonstrated show that these houses are not exclusively workshops as much as areas for the preparation of food (Müller-Karpe 1994: 60). All workshops have clear indications that melting and casting was a primary activity instead of smelting. This is demonstrated by the presence of multiple kinds of molds, tuyeres, crucibles fashioned with pouring nozzles, ceramic bellows, and permanent furnaces. Ingots of copper, lead, and possibly also iron have been

identified with these workshops which confirm their connection to primary producers, who likely resided closer to the source areas.

3.2.2 Compositional and isotopic analyses of copper from Kültepe

Compositional analyses of 86 samples from Kültepe by Esin (1967) and 25 by Lehner et al. (2015) confirm our understanding of tin and bronze consumption in addition to the prolific consumption of arsenical copper. These samples were taken from discernible finished objects from secure contexts in the lower city. Arsenic ranges in all samples from 0.02 wt% to 4.05 wt%, however the mean composition hovers around 1.15 wt%, suggesting that many of the arsenical coppers may not be intentionally alloyed with arsenic. Tin ranges from measurements below the detection limit to around 10.0 wt% tin bronze. Lead appears in minor or trace amounts in many of the analyzed objects, ranging from a few ppm up to 3.0 wt%. Because the amount of lead is relatively low, it is difficult to be certain whether or not lead was intentionally added. Lead, like arsenic, is also present in many of the copper ores of Anatolia and it is also a useful additive to smelts to regulate melting temperatures. Therefore, it is likely, however difficult to demonstrate at present, that copper and copper alloys with minor amounts of lead represents a technological preference for ores rich in lead or the intentional addition of lead ores to the smelt.

The compositional data demonstrate the presence of at least three major alloy groups, including copper-arsenic, tin bronze, and a ternary alloy of copper with tin and arsenic. This observation is verified by cluster analysis and principle components analysis by Lehner (2014), which is a method that quantitatively groups samples together based on their compositional similarity. The relatively similar amount of arsenic across the three different groups (ranging

from 0.90 – 1.25 wt%) suggest that minor concentrations of arsenic derived in part from the smelting process in primary production and/or extensive recycling.

Alloys of copper and tin were not rare; however, as one might expect from the importance of tin in the texts, tin bronzes do not dominate the assemblage. In fact, arsenical copper seems to be more common. This observation was further verified by a recent study of EBIII and karum period copper alloys from Kültepe (Lehner, et al. 2015). This is significant for two reasons. First there is little to no mention of arsenic in the Kültepe texts. This is a problem that Adams (1978) first mentioned when reviewing M. T. Larsen's synthesis of the Old Assyrian Trading Colony Period based on the Kültepe texts (1976). Adams' cites the work of Eaton and McKerrell (1976) who were able to demonstrate a more gradual adoption of tin bronzes later into the second half of the 2nd millennium BC. This observation is consistent with over 300 analyses of copper alloys from Boğazköy-Hattuša (Lehner 2012) and further analyses of copper alloys at İkiztepe (Özbal, Pehlivan, et al. 2002). Tin is almost certainly to be identified with the *annuku*-metal of the Kültepe texts, but this leaves arsenic as a curiously unmentioned alloy constituent.

Second, this lack of arsenic in the texts may in fact relate to how arsenical copper is produced. As mentioned earlier, most arsenical bronzes in excess of 1.0 wt% arsenic were not produced from the melting of pure copper and arsenic together, but rather from a much more complex process of mixed or co-smelting of different copper and arsenic minerals, which often involved the direct selection of appropriate ores together in a smelting process (Lechtman 1991; Lechtman and Klein 1999). Copper metal could have also been melted together with the secondary product called *speiss*, an iron-arsenide, which was demonstrated to be intentionally produced at the 3rd millennium BC site of Arisman in North-West Iran (Rehren, et al. 2012). Arsenic contents below 1.0 wt% could very well have been introduced as part of a fluxing agent

such as an iron oxide or in the copper ores themselves. Additionally, the high volatility of arsenic at high temperatures in oxidizing atmospheres would also decrease the concentration of arsenic as copper alloys were further refined or recycled with tin bronzes. Many of the copper-tin alloys at Kültepe do have arsenic in excess of 1.0 wt%, which suggests that either ternary copper-tin alloys with arsenic were an intentional alloy type, or that copper-tin alloys were produced from the alloying of copper containing arsenic.

Lead isotope analysis by Sayre et al. (2001) of samples from large Middle Bronze Age centers Acemhöyük, Karahöyük-Konya, and Kültepe is consistent with an extensive metal production network (Figure 3.5). All samples are consistent with regional sources Tauride, Pontide and Central Anatolian sources, including one lead metal sample from Kültepe is consistent with both central Tauride and Central Anatolian sources (see Chapter 2 for a brief description of these geological regions). Two silver objects sampled from Acemhöyük are not consistent with any Anatolian sources; however, this likely reflects an inadequate understanding of all the silver-lead ore sources available during the Bronze Age. None of the analyzed samples are consistent with southeastern Tauride sources, such as Ergani or the Keban series, although a southern source would be most consistent with the textual data (Dercksen 1996: 16). These data are mutually consistent with the texts, attesting to the presence of a large copper trade originating in part by the use of Pontide copper. Unknown to the texts, however, is the simultaneous use of central Tauride sources to the south. The use of the copper and silver producing regions in the Taurus points to a long continuous pattern of exploitation through all periods of political development.

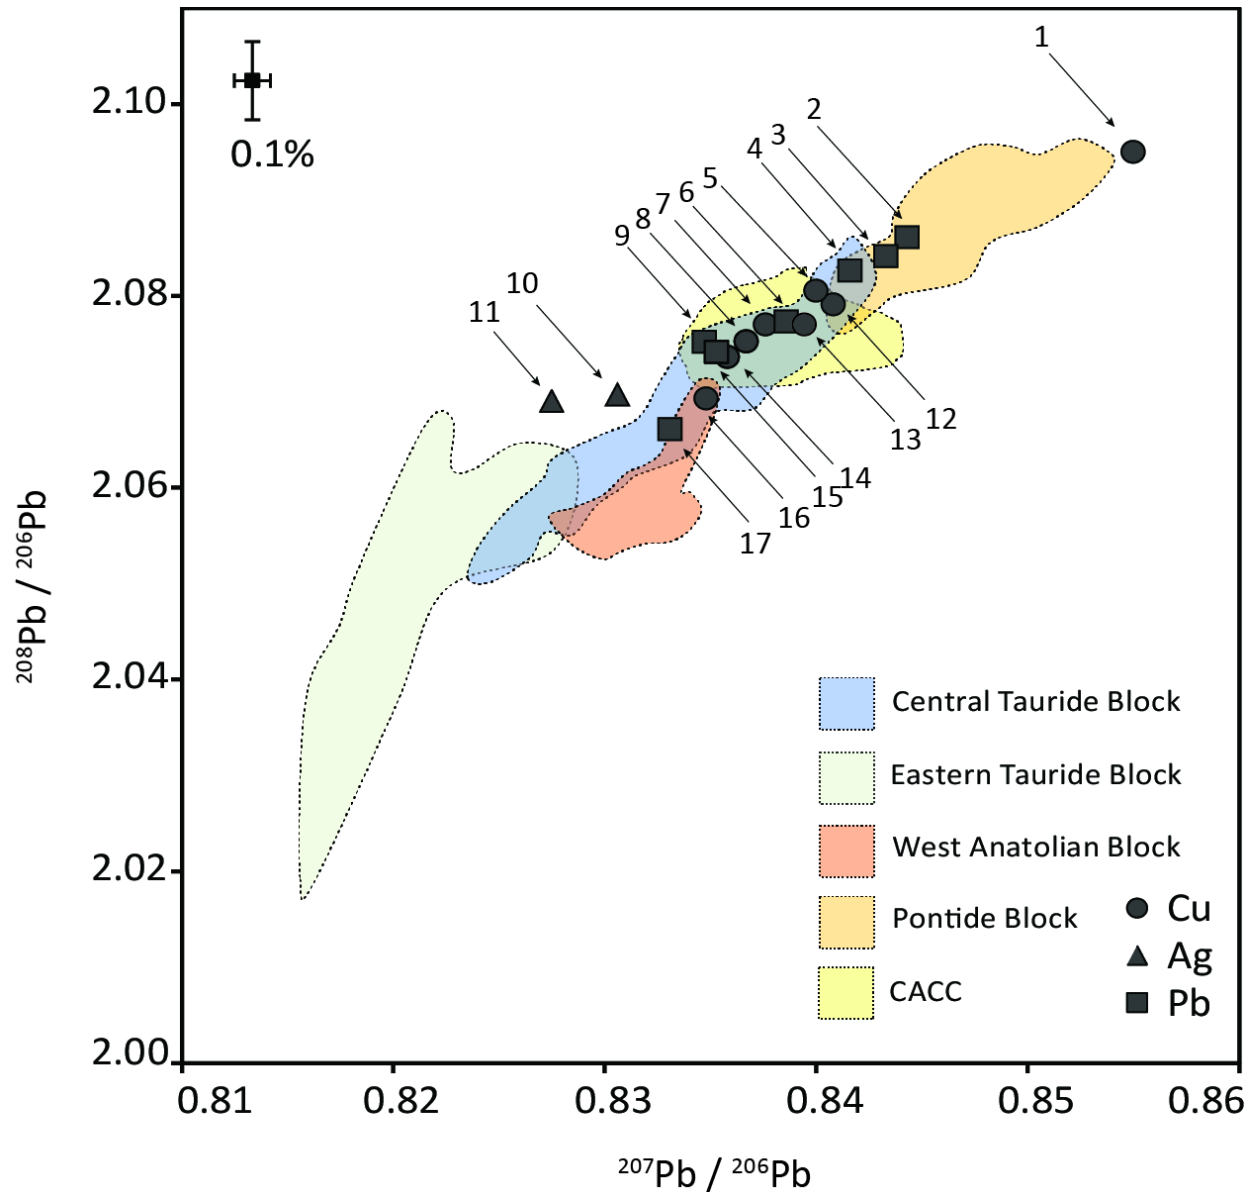


Figure 3.5: Lead isotope binary plot comparing $^{207}\text{Pb}/^{206}\text{Pb}$ by $^{208}\text{Pb}/^{206}\text{Pb}$ of known ore bodies and artifacts dating to the MBA (adapted from Lehner 2014: 149, fig. 12; object data from Sayre et al. 2001; ore data from Wagner et al. 2003 and references therein). 1. AAN 282 Acemhöyük Cu-ingot, 2. AAN 271 Acemhöyük Pb ore nodule, 3. AAN 925 Alisar Pb ring, 4. AAN 008 Acemhöyük Pb pendant, 5. AAN 843 Acemhöyük Cu pin, 6. AAN 199 Kültepe Pb frag, 7. AAN 842 Acemhöyük Cu pin, 8. AAN 17 096 Acemhöyük Cu crucible slag, 9. AAN 924 Alisar Pb ring, 10. AAN184 Acemhöyük Ag frag., 11. AAN185 Acemhöyük Ag frag., 12. AAN 17 095 Acemhöyük Cu ore nodule, 13. AAN288 Acemhöyük As ore nodule, 14. AAN 2032 Karahöyük-Konya Cu slag, 15. AAN 926 Alisar Pb ring, 16. AAN 286 Acemhöyük Cu ingot, 17. AAN 840 Acemhöyük Pb frag.

3.3 Strategies of tribute, levies and tax, and domestic trade of metal during the rise of the Hittite Empire

For historical reasons that are yet quite unclear, the Middle Bronze Age state polities declined during the 17th century BC (Kulakoğlu 2014). The largest polities in central Anatolia, including the sites of Kültepe, Acemhöyük and Karahöyük (Konya), all exhibit significant conflagration without immediate phases of rebuilding and were abandoned. The likely scenario points towards a periodic episode of intense competition leading to the formation of a novel form of state organization and scale of political integration evinced by the subsequent emergence of the territorial Hittite state centered at Hattuša. The following several generations, approximately 1725 – 1650 BC, have been seldom studied due to a lack of data and preservation of archaeological remains; however analysis based on later historical texts have permitted important interpretations of the historical events, military strategy, and processes of political integration that likely occurred (Forlanini 2008). These Hittite historical texts, namely the so-called Anitta Text (Neu 1974), the Annals and Testament of Hattušili I (de Martino 2003; Melchert 1978; Sommer and Falkenstein 1938), and the Proclamation of Telipinu (Hoffmann 1984), refer to these critical moments and military exploits leading to the formation of the Hittite state. By ca. 1650 BC, well organized elites strategically transformed central Anatolia from a mosaic of small states present during the MBA into the beginning of a large territorial empire, whose capital was founded at Boğazköy-Hattuša.

Judging from available archaeological data, Glatz (2009) theorizes that the Hittite state emerged through a selective and regionalized process of political domination represented by four important imperial strategies. These are evinced by the development of at least four suites of ceramic assemblages which predominate in the political core and decay in frequency with

distance. This pattern has been variously interpreted as the extension of imperial control or influence on the domestic craft economy (Glatz 2012; Gunter 2006; Postgate 2007). Second, settlement trends show a four-tiered hierarchy within central Anatolia with Boğazköy-Hattuša being the largest (ca. 180 ha). Furthermore, regional analysis of the settlement history reveals a depopulation of peripheral regions in western-central Anatolia and the Pontic region and the resettlement of those regions that were previously dominated by the large MBA regional centers (Table 3.2, adapted from Glatz 2009: 133, Table 1). Third, the use of distinctly stylized glyptic, including titles and professions of officials in Luwian hieroglyphs, in palace/temple contexts within regions peripheral to the core of the Hittite state demonstrates a networked elite interaction based on the administration of these regions by the Hittite state. Fourth, a category of monuments in carved stone, which normally show a Hittite king with an associated Luwian inscription, are distributed throughout Anatolia with particular concentrations on the periphery of the imperial territories. These relief carvings are thought to demonstrate attempts of state hegemony in the borderlands or in those regions of intense political interaction (Glatz and Plourde 2011), including far western Anatolia (ex. Karabel, Akpınar, and Surat kaya). Additional rock carvings more central to the Hittite core, including those near to Boğazköy at Yazılıkaya and others at Fraktin, further connect Luwian iconography with Luwian inscriptions.

Schachner (2009a) further describes the important role of distinct innovations of the cities of the core of the Hittite state. The emergence of LBA cities in north central Anatolia, including again the capital Boğazköy-Hattuša and regional centers Kuşaklı-Sarissa, Alacahöyük, Oymağaç-Nerik, Ortaköy-Şapinuwa, and Kaman-Kalehöyük, variously include the monumental architecture associated with state administration and storage of a scale that was previously unobserved in earlier periods. According to Schachner, these structures include grain storage

Table 3.2: Administrative and spatial scope of known Hittite regional centers (adapted from Glatz 2009: 132, table 1).

| Admin. scope | Official role | Hittite name | Modern name | Size (ha) |
|---------------------|---|----------------|-------------|-----------|
| State/empire | Imperial capital | <i>Hattuša</i> | Boğazköy | 180 |
| Region | Capital 'Upper Land' | <i>Samuha</i> | Kayalıpınar | 20 |
| Subregion | Cult center | <i>Sarissa</i> | Kuşaklı | 18.2 |
| ~District | Seat of provincial officials (AGRIG and BEL MADGALTI) | <i>Tapikka</i> | Maşat Höyük | ~8 |

silos and sunken water reservoirs that were designed to provision the city and possibly also neighboring settlements with less risk. Schachner argues on the basis of radiocarbon dating that these structures date to the early 16th century BC, precisely within a couple generations of the formation of the Hittite state itself. Like Glatz, Schachner recognizes the role of the state in the production of these important structures, especially since they are located in key settlements within the core of the state itself.

As mentioned above, patterns of pottery consumption, settlement patterns, administrative technologies, landscape monuments, and distinct urban architecture all show important overlapping imperial strategies involved in the transformation of Hittite Anatolia into a territorial state. By the middle of the 16th century BC, elites centered at Boğazköy-Hattuša integrated much of central Anatolia into a novel form of sociopolitical organization (Schachner 2009a, 2011b, 2012), which also extended networks of imperial power into populous neighboring regions to extract tribute and facilitate trade. While certain elements of tribute and levies were adopted during the preceding period (Dercksen 2007), the geographic scope and centralization of the tribute and levy system increases in scale and operation during Hittite rule (Beckman 1995; Imparati 2002; Klengel 1975, 2005; van den Hout 2006).

Metals as ingots or finished goods, and their producers, functioned intimately within this system, and they provide an appropriate proxy and a second line of evidence for the functioning of the imperial system. In the following, I examine briefly three groups of Hittite texts to examine how metal fit into the economy, both in terms of regional domestic and long-distance trade. The domestic economy of central Anatolia during the Hittite Empire may be contrasted with the economic activity associated with long-distance trade, which was typically linked to the transport of exotic materials and high value-added finished products (e.g., tribute and gifts between elites). Contrary to our understanding of economy from the Kültepe texts, which is strictly biased from the point of view of the archives of Mesopotamian merchants who operated in part within the geographic bounds of central Anatolia, data from Hittite texts do not provide direct evidence of mercantile activity among individuals and institutions. Among the thousands of texts known to Hittite Anatolia, none of them are economic texts from the private archives of merchants (Klengel 1979). The texts are composed of state archives located primarily in the capital Boğazköy-Hattuša, Maşat Höyük (Alp 1980), Ortaköy-Şapinuwa (Süel 1992), and Kuşaklı-Sarissa (Wilhelm 1997). Despite the lack of private economic records among merchants, texts concerning the administration of the state, namely palace/temple inventory lists, tax lists, and legal texts, all provide data concerning the organization of metal production and trade.

3.3.1 Hittite legal texts and the domestic economy

The Hittite Laws are a collection of texts that codified norms of punishment and fairness, often into an equitable system of exchange or compensation (Hoffner 1997; Imparati 1964). Like all legal texts, the Hittite laws contain provisions suggesting reforms of earlier practice; however,

the reality of such reforms is debated. For example, later versions of most laws are notably compensatory in nature, many of which had exacted corporal punishment in previous times (Hoffner 1997: 7). In Hoffner's critical edition, he lists at least 25 different categories of laws based on common subjects, including but not limited to homicide, theft, marriage, land tenure, breach of contracts, wages, sexual offences, and commodity prices (1997: 13-14, table 6).

The legal texts demonstrate two fundamental characteristics of the domestic economy. First, according to the tariff lists in the legal texts (§§178-186), silver was the main standard of compensation, and it was exchanged on the basis of the weight of shekels (approximately 11.75g in Hatti, 9.4g in Ugarit, 7.83g in Mesopotamia), minas (40 shekels in Hatti, 60 in Mesopotamia), and talents (60 minas). Second, standard weights of cereals like barley were also used as compensation, most often when equivalencies in silver were too small or the recipient had more use for cereal grains (Floreano 2001: 232). The fungibility and market liquidity of silver and grains fostered a remarkable flexibility in exchange across a wide geography, range, and scale of goods and services (for discussion on fungibility and measure in a cross-cultural context, see Renfrew 2012).

Floreano (2001: 210-221) makes the intriguing argument that regulated barter is evident in the tariff lists, even though these lists report exclusive equivalency in silver. Among the lists, the minimum reported value is 1/8 shekel (a copper axe), the maximum is 40 shekels (a mule or 3600m² of vineyard), but the mode compensation value is simply 1 shekel for a surprising amount and diversity of goods and services. The apparently extensive purchasing power of a single shekel suggests that the amount was a heuristic value allowing wide equivalency across several commodity types. Since 1 shekel of silver was equivalent to 1 sheep, 3 *PARISU* (150 liters) of wheat, and 4 minas (160 shekels) of copper, most commonly used commodities in daily

life could be used both as a means of exchange and a way of payment. If indeed the fungibility of commodities operated in such a fashion, then the price lists in the legal texts functioned as a sort of price control on common goods and a basis of fair exchange in the wider market present at the time. Furthermore, considering that 1 shekel of silver could purchase a single sheep, 2 shekels of silver is the price of a calf, and 3 shekels for 3600m² of irrigated land, the circulation of silver for most daily encounters and needs would have proved unsuitable for most purchases of reduced quantities (Floreano 2001: 212).

Metals and metallurgy are thus placed in an important position within the laws. On the one hand, the ubiquitous use of silver in the texts demonstrates the traditional use of this scarce metal as a means of exchange. The use of silver in this context was a well-adapted economic strategy that was adopted in many states through the Bronze and Iron Ages in the Near East (van de Mieroop 2014). On empirical grounds, its capacity for domestic circulation appears to have pervaded most urban contexts and networks, enabling an equitable system of exchange that could facilitate large-scale cooperation. Weights of silver were accepted in exchange for goods and services well beyond central Anatolia, and therefore some sectors of its local production, refining, and bulk exchange was possibly regulated by state officials (Floreano 2001: 232). Copper and bronze are also mentioned, although less frequently, and only in reference to finished goods. From the standpoint of the Hittite laws, the domestic production and trade of copper operated within a less centralized system than did silver. Gold, tin, and iron are not mentioned at all in the legal texts, which suggests that these commodities were traded and stored outside of the domestic context that the laws governed (Hoffner 1997: 11; Siegelová 2005: 36).

Hoffner (2002: 181) notes that there is no evidence among the Hittite texts for a separate merchant or entrepreneurial class that operated outside of the purview of the palace and temple.

As he also observes, the current Hittite textual corpus almost exclusively documents how privileged and protected individuals conducted official long-distance trade missions sponsored by the king of Hattuša. Regional trade and exchange within central Anatolia therefore most likely operated in a similar fashion to exchange mechanisms in earlier periods. There was less need for state bureaucrats to administer trade in Anatolia through textual records than in Mesopotamian communities. This suggestion is also consistent with the idea that writing was limited to a minority of the population, including a specialized scribal class who were nominally attached to elite institutions and were often themselves trained in Syro-Mesopotamia (Beckman 1995: 25; Bryce 2002: 69-70).

Another possibility, expressed recently by Alparslan (Alparslan 2005: 381), speculates that traders would have rather kept records on perishable materials which would not have preserved over time. Supporting this idea are the two well-preserved wooden writing boards (diptych) from the 13th c. BC shipwreck at Uluburun located off the southwestern Anatolian coast (Bass, et al. 1989: 10, fig. 19; Payton 1991: 101-110). Unfortunately, the wax infilling of these boards did not preserve so there is no way of determining without doubt of speculation which language or script was employed.

The commodities represented on the shipwreck, including hundreds of kilos of Cypriote oxhide copper ingots, tin, and cobalt blue glass ingots from Egypt, in addition to finished objects produced from several exotic materials, are also consistent with trade between elites from Egypt to the Aegean, and with materials deriving from locations bracketed by central Asia to the east and possibly the Iberian peninsula to the west (Bachhuber 2006; Matthäus 2005; Pulak 2005). We cannot assume the trade network and economic strategies evinced by the Uluburun data operated the same way in central Anatolia, which was mostly limited to over-land transportation.

Rather it appears that select and seasonal segments of the Mediterranean trade network entered into central Anatolia, presumably via the port cities and hinterlands of Cilicia (Bronze Age *Kizzuwatna*, Iron Age *Hiyawa/Que*) and the northern Levant, carrying tribute and exotic commodities such as gold, silver, tin, glass, and ivory in addition to bulk quantities of copper. More recently, compositional analyses of Red Lustrous Ware from Temple contexts at Boğazköy, and across the Eastern Mediterranean, appear to have been produced in Cyprus (Grave et al. 2014). Imperial Hittite impact on the southern coast has been well documented at the site of Kinet Höyük, where the ceramic production and potmarks are consistent with state sponsorship (Gates 2001). State sanctioned transportation of staple goods is also known but seems to be limited to the transport of surplus from Egypt to supply redistributive institutions in the Hittite heartland to avert severe food shortages in a period of famine (Bryce 2005: 331-332).

3.3.2 Inventory and tax lists

The palace and temple institutions of Hattuša also kept meticulous administrative accounts recording both the palace and temple inventories and the incoming taxes levied as tribute of staple and wealth goods, including vast quantities of metal. Editions of these texts have been published by Košak (1982) and Siegelova (1986), in which the authors describe the relation of the textual information with the administration of the state. Where there is information concerning provenance, most texts discovered at Boğazköy were found among the palace archives at Büyükkale, rooms within the *Haus am Hang*, and from within the precincts of Temple 1. The data within these texts underscore the efforts that state institutions required to not only administer effectively their territories, but also to finance the state rituals and expansion. Siegelová (1986) characterizes the tax lists into two functional though related types. The first are so-called *arka(m)man(n)-*, MADATTU/MANDATU (Akk.) lists (levies or taxes) and IGI.DU₈.A

(required gifts, tribute), both of which typically identify the act of paying tribute and/or tax from a location to a central palace or temple institution. Apart from the tax lists are the so-called inventory lists, which date primarily to the Empire Period (Hazenbos 2003). These lists took account of the holdings of the palace or temples and included for the most part high value added goods and exotic materials. The tax lists and inventory texts therefore effectively account the incoming flow of goods and their storage, although contextually biased from the point of view of state institutions.

Discussed in further detail by Müller-Karpe (Müller-Karpe 1994: 76-79), these lists demonstrate an important differential use of metal. Treating all objects equal, whether ingots or finished goods, there is a clear tendency for most incoming tribute and tax to be collected in copper or bronze (ca. 60% of all metal mentioned) and much less so of tin, silver, iron, and gold. Table 3.4 lists supplier locations of tributaries from which these metal commodities were sent. Although these locations do not necessarily indicate the provenance of the raw materials, the place names are nevertheless informative concerning the formality of tribute, and the places are associated with the objects by the Hittite state bureaucracy. Only a few of the locations have been positively identified, including *Kizzuwatna* (Cilicia), *Alašiya* (Cyprus), *Ugarit*, all three of which were important actors on the periphery of the Hittite Empire and were periodically under Hittite control. The fact that copper and tin were known imports from these locations within the Eastern Mediterranean region gives more strength to the data from the Uluburun and Cape Gelidonya shipwrecks.

Table 3.3: Metal commodity types and supplier locations according to 13th century BC tax lists (data from Siegelová 1986, 1993, 2005; Siegelová and Tsumoto 2011).

| Metal Commodity | Supplier Location | Source |
|--|--|--|
| Copper URUDU <i>kuwanan-/kunnan-</i> | Hen[-, -]hira | KUB 42.29 II 4', 12', 15'-16' V 18' |
| | Arpuzziia | |
| | Šawatta | |
| | Kurkuriša | KUB 42.28 + III 4', 8', IV 6', 7', 14', 19' |
| | Kuenma/zuliia | |
| | Mizamizana | |
| | Huwar[- | |
| | Šar[- | |
| | Tuššimna | |
| | Šapla | KUB 26.67, right col. 3', 13' |
| | Tetum[- | |
| | Kapittat[- | KBo 18.162 I 6', 13' |
| | Munna[- | |
| | Šahhu[- | KBo 7.24 II 14', IV 1' |
| | Ar[x]huz[i- | |
| Luli[- | KBo 18.161 rev. 8, 13, 16 | |
| Ank[uwa (?) | | |
| Anzilatašši | | |
| Parnašši | | |
| Zarar[a- | KUB 42.28 + IV 17', KUB 26.67, right col. 6' | |
| Kizzuwatna | | |
| <i>Ugarit</i> | | |
| <i>Alašiya</i> | | |
| Tin NAGGA <i>arzili- (?)</i> | Awan[a- | KBo 18.164, right col. 5' |
| | Tetum[- | KUB 26.67 KUB 26.67, right col. 3', 13' |
| | Kapittat[- | |
| | Munna[- | KBo 18.162 I 6', 13' |
| | Šahhu[- | |
| | Ar[x]huz[i- | KBo 7.24 II 4', IV 1' |
| | Luli[- | |
| <i>Kizzuwatna</i> | KUB 26.67 right col. 6' | |
| <i>Alašiya</i> | KUB 36.98 b rev. 14' | |
| Gold GUŠKIN | <i>Alašiya</i> | KBo 12.38 I 5'; KBo 12.38 I 13', 15'; KUB 36.98 b rev. 14' |
| | <i>Amurru</i> | KBo 10.12 I 9' |
| | <i>Ugarit</i> | RS 17.227, 20-21; RS 17.340, 23 |
| Silver KU ₃ .BABBAR <i>harkanza- (?)</i> | DU [- | KBo 18.155 |
| | Ḫadduna | |
| | Ḫilammattiia | |
| | [K]ašuliya | |
| | <i>Alašiya</i> | KUB 36.98 b rev. 14' |
| <i>Ugarit</i> | RS 17.227, 20-21 | |

To examine the divisions in how tribute and institutional storage treated metal as a commodity as opposed to as a value added finished product, isolating mentions of primary metal ingots (PAD) by metal type is first necessary. Figure 3.6 displays the relative frequency of these primary metal commodity types. Among the taxed items, again the majority are composed of copper and bronze, and then silver, followed by tin with only a couple examples of gold. This demonstrates that, at least according to the official texts, raw copper functioned as one of the most frequent metal forms of tax. That we should also discern ingots of tin and silver is consistent with past analyses, especially given that tin was traded almost exclusively in its pure form and that unalloyed silver was used as a money standard. Among the inventories, silver ingots dominate with around 90% of the mentions, the remainder consisting of ingots of gold and one of iron. This pattern corresponds with what we understand about the domestic trade of silver from the legal texts.

The relationship is somewhat reversed for the relative frequency of finished goods in the tax lists and inventory texts (Figure 3.6). Copper and bronze objects account for nearly all the items described in the tax lists, demonstrating that copper metal and its alloys functioned as an appropriate method of tribute. The tribute lists include different types of tools, weapons, pins, vessels, belts and other unknown objects. Many of these objects could be used functionally or more simply understood in terms of weight, which seems to have been the case for items like axes which have standard weights (Siegelová and Tsumoto 2011: 281). Among the inventories, finished goods comprised mostly of gold objects, such as small commissioned jewelries, palace equipment, votives, and vessels are common. Objects of silver, copper, bronze and iron occur less frequently.

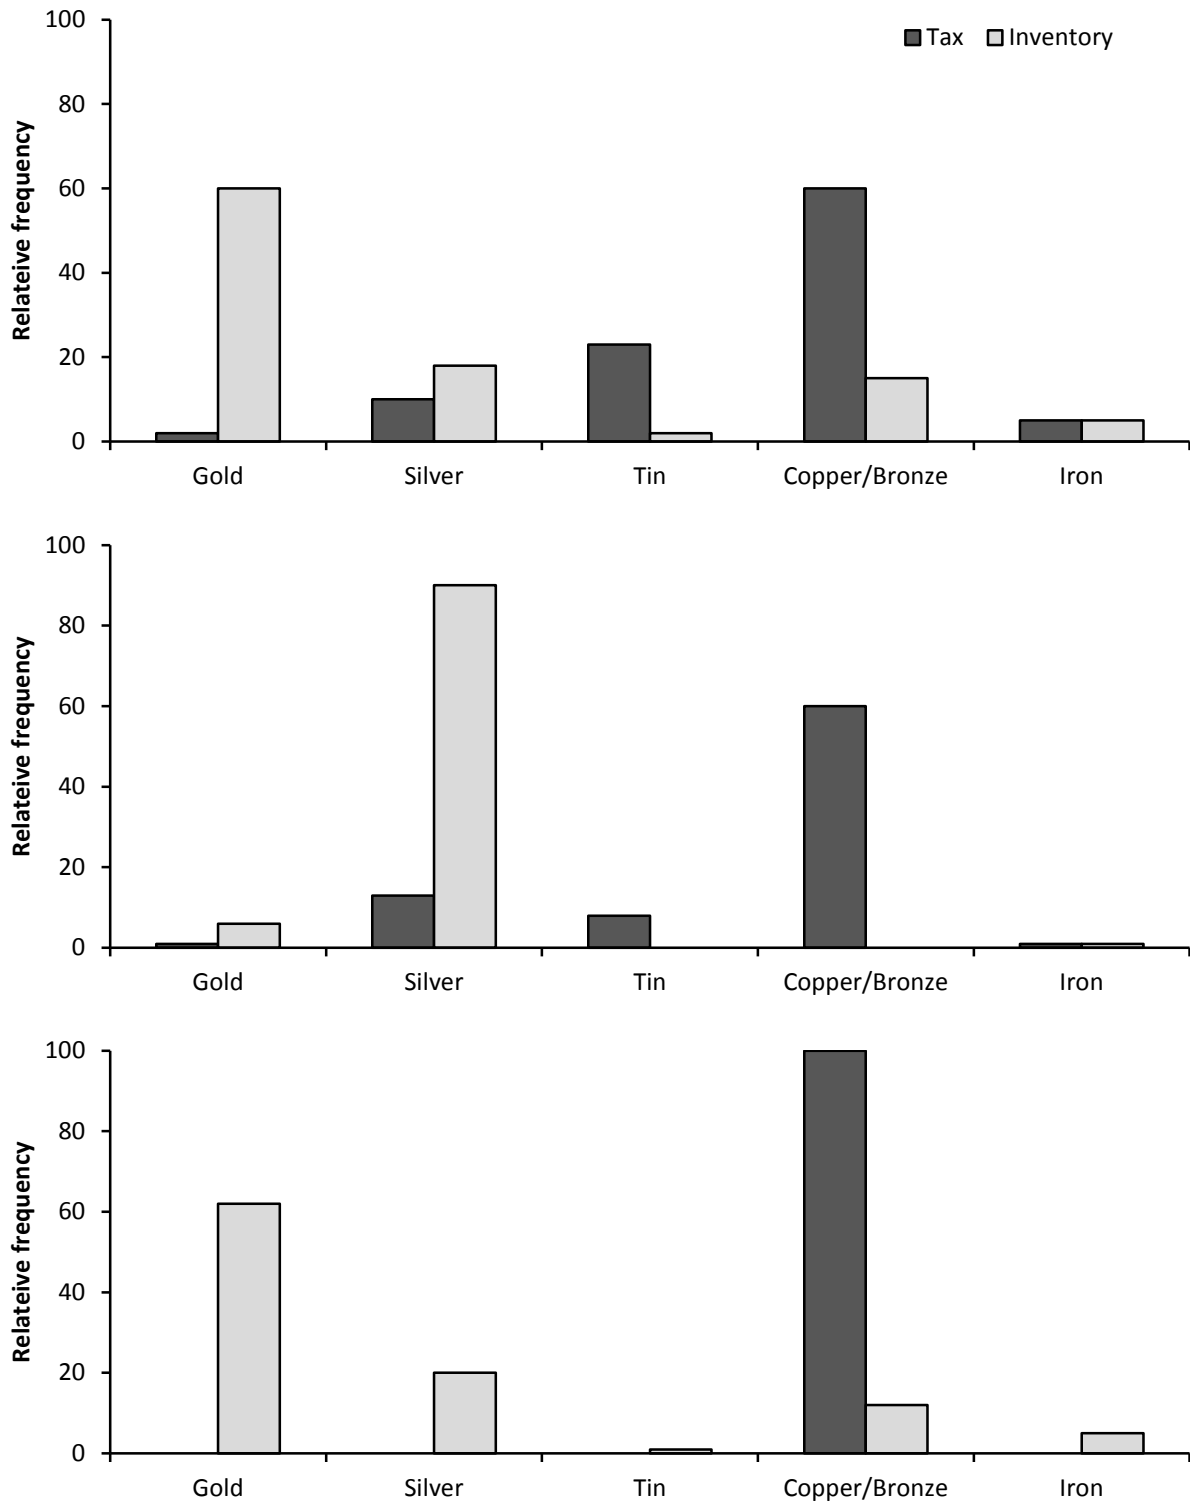


Figure 3.6: (Top) Relative frequency of metal commodity types for all different objects compared against tax and palace/temple inventory lists; (Middle) primary metal commodity types; and (Bottom) metal commodity types for finished goods (data from Siegelová 1986 and Müller-Karpe 1994: 75-76).

3.3.3 Archaeological evidence from Boğazköy

One of the most prominent features of metallurgical production at Boğazköy-Hattuša is that secondary metallurgy is sponsored indirectly by state institutions during the Late Bronze Age (see Figure 3.7). This degree of sponsorship allowed for workshops to be relatively autonomous in production, however textual evidence does suggest that the metal supply was controlled through redistribution and taxation (Siegelová 1986). Specialized craft producers, including textile weavers, ceramicists/potters, seal carvers, stoneworkers, and metal smiths, all appear to have been loosely attached to some degree to state institutions at the site. This can be inferred from material evidence associated with residential architecture in both the lower and upper cities of Hattuša (Müller-Karpe 1994: 66-86). Assemblages of secondary metallurgy are common in these contexts. These include ceramic bellow bowls and tuyères that would have fitted over the top of a range of portable crucibles. The directed heat and exhaust from these configurations would have allowed producers to attain the appropriate temperatures to melt metals and alloys for later casting and working. Metal working tools, including awls, chisels, and piercers, often accompany pyrotechnological workshops suggesting that object finishing occurred alongside melting technologies. Importantly, working tools like these are highly mobile and would have been essential for a number of crafts, suggesting that metal smiths cooperated closely with wood and stone workers, among others.

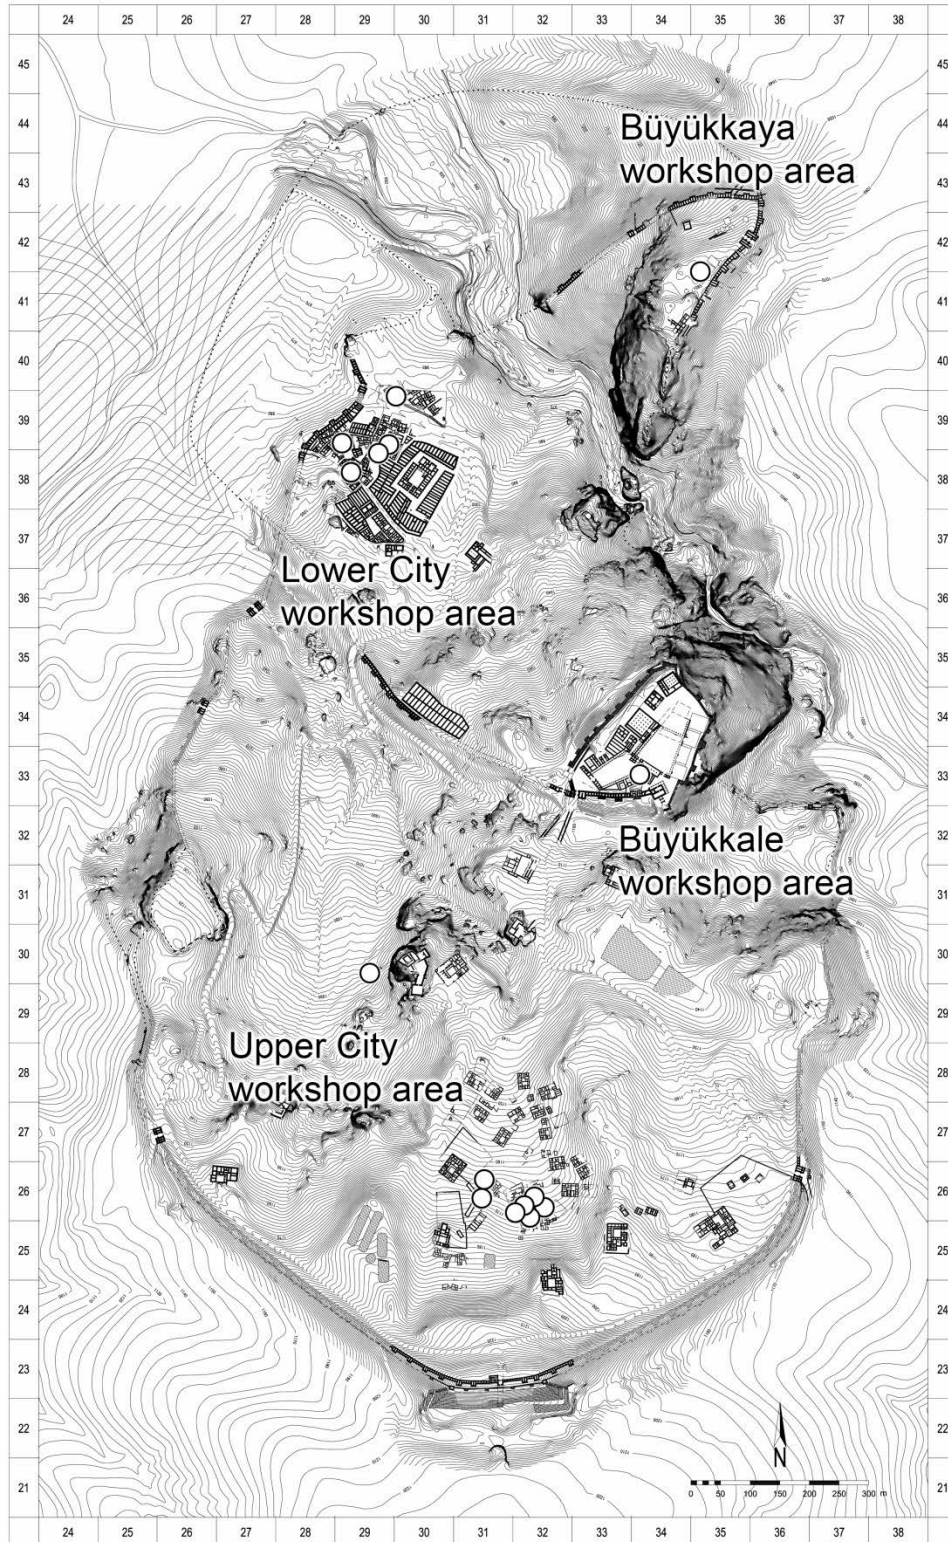


Figure 3.7: Map of the urban layout of Hattusa indicating major workshop (white circles) areas during the Late Bronze Age and Early Iron Age (Büyükkaya) (adapted from Lehner and Schachner in press: fig. 5; Müller-Karpe 1994: 83, fig. 57; Seeher 1995, 2006c).



Figure 3.8: Crucible types from Hattuša. 1. ETD 99/110, 2. ETD 96/218. Adapted from Lehner and Schachner in press (Fig. 9).

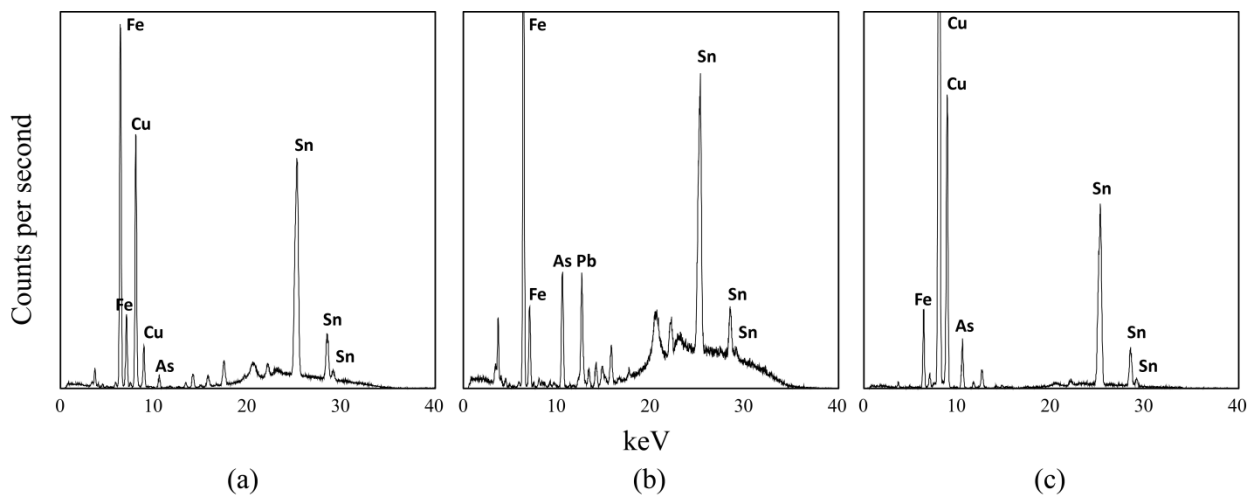


Figure 3.9: X-ray fluorescence analysis of crucible residues demonstrates melting and/or recycling practices. (a) Bo 2005: 293/305.263, (b) ETD 99/110, (c) ETD 96/218. Adapted from Lehner and Schachner (in press: fig. 10)

Three such examples of crucibles were available for analysis in 2013 by in-field portable XRF (see Figures 3.10 and 3.11) in order to examine qualitatively their adhering residues. The analysis of metal melting residues is fraught with a number of complex issues (Kearns, et al. 2010), however when used to identify individual elements, it is possible to characterize what materials were being melted but it is impossible with these methods to determine the original production methods and metal ratios. Additionally, these crucibles could have been used more than once; therefore mixed signatures could also result. Spectra for Bo 2005: 293/305.263 and ETD 96/218 show similar patterns with notable peaks in iron, copper, and tin. Traces of arsenic also attest to either multiple use for different alloys, ternary alloy processing, or arsenical impurities reacting preferentially with the ceramic body. Bo 2005: 293/305.263 (no photo) is a highly fragmented bottom portion of the crucible bowl, and was found near to a possible furnace installation in the Sarıkale valley dating to the 15th century (Seeher 2006c: 175). ETD 96/218 probably dates to the Early Iron Age ca. 11-10th century BC and was found alongside other metal production debris at Büyükkaya (Seeher 1997: 327-331). ETD 99/110, which was found in a fill deposit of the east ponds in the Upper City (Baykal-Seeher 2006), shows a lack of copper but enrichments in lead, in addition to major peaks in tin and arsenic. The lack of copper could result from the fact that only the rim of the crucible was analyzable which may allow for this heterogeneous signature. It is unlikely that this crucible was used for the alloying of tin, lead, and arsenic alone as there is no precedent for this.

The crucible data are mutually consistent with both recycling and melting ingots of copper and tin for later casting. Obviously more data is needed from more crucibles to more accurately generalize on production technologies, however from the data so far we can be certain that tin bronze production was a central activity of metal producers at Hattuša. This further

suggests that these producers focused on a metal type that held a more interregional quality, which is somewhat contradictory to the known compositional data from finished objects at Hattuša. Tin bronze production at Hattuša therefore lends credence to the value and prestige of this metal type.

Excavations at Boğazköy-Hattuša have further uncovered a total of at least four planoconvex ingots and one oxhide ingot dating to the Middle and Late Bronze Ages (see Figure 3.12). These primary ingots are simply produced from pouring molten metal into a rough form and retain a bubbly ‘blistered’ pattern on the surface where it contacts air upon cooling. The compositions of these reflect relatively unrefined and unalloyed blister copper (see Table 3.3). The compositional ranges of arsenic between 0.01 and 0.32 wt% differ from the range of arsenical copper in analyzed objects which in general have higher arsenic. This is consistent with the later addition of arsenic to produce alloyed metal in finished objects. While theoretically the ingots could have derived from recycling, the lack of common alloying components like arsenic or tin suggests that the copper metal reflects a composition that is close to the original primary smelt. A large planoconvex ingot discovered in 1958 in debris behind the Phrygian East Gate of Büyükkale phase Ia (Boehmer 1972: 74, Nr. 190) is particularly unique in that it has a relatively high composition of the impurity nickel (ca. 1.3 wt.%). This most certainly derived from the original ore source. Bo 11/590, which dates to the early second millennium BC and was uncovered in the karum-period Lower City in 2011 (Schachner 2013: 89-91, fig. 11). The quarter fragment of an oxhide ingot was found in the Upper City (Bo 79/206) and was previously analyzed in Oxford showing compatibility with the Apliki source in Cyprus (Stos-Gale, et al. 1997: 117). These data confirm our existing understanding of second millennium BC metal

trade, and they further confirm the well-known southward interests that the Hittite state had according to the tax documents discussed above.

Evidence for silver recycling is evident from a small planoconvex from the Temple Precinct of the Upper City (Bo 87/69). The bulk composition of the ingot demonstrates significant impurities of gold (ca. 7.5 wt.%) and copper (ca. 5.4 wt.%). Values for tin and zinc are likely over estimated in the XRF quantifications due to the x-ray peak overlaps. This ingot was discovered in an insecure context in the temple quarter of the Upper City (Herbordt in prep), however its silver composition is consistent with Bronze Age silver technologies. Impurities of lead and bismuth are consistent with the cupellation of silver from argentiferous lead. This production technology was known in Anatolia and the Near East since at least the fourth millennium BC (Helwing 2014; Hess, et al. 1998; Pernicka, et al. 1998). The presence of gold and copper, which do not naturally occur at such high concentrations in argentiferous lead, suggests that the gold and copper was unintentionally added to the silver as a recycling impurity. It is possible that silver objects with gold plating, or silver alloyed with copper, were later melted down into ingots for transportation and reworking.



Figure 3.10: Ingot types from Bogazköy-Hattuša. (1) Bo 11/590, copper planoconvex MBA; (2) Boehmer 1972: Nr. 190, copper planoconvex LBA; (3) Bo 79/206, copper oxide LBA; (4) Bo 83/819, copper planoconvex LBA; (5) Bo 87/69, silver planoconvex LBA.

Table 3.4: Context and composition (in wt.%) of planoconvex and oxhide copper and silver ingots from Hattusa. Quantitative results from EDXRF (Boehmer 1972: Nr.190, Bo 83/819, and Bo 87/69) and EDXRF (Bo 11/590 and Bo 79/206) (data from Lehner and Schachner in press: table 1).

| Catalogue Number | Ingot type | Context | Cu | Sn | As | Pb | Zn | Sb | Ni | Co | Se | Fe | Te | Bi | Ag ppm | Au ppm |
|----------------------|----------------------|--|------|-------|------------|-------|------------|-------|-------|------------|------------|------------|------------|------------|--------|--------|
| Bo 11/590 | Planoconvex (5 kg) | MBA; Lower City residential building | 100 | 0.006 | 0.036 | 0.016 | 0.008 | 0.018 | 0.082 | 0.001 | 0.007 | 0.040 | 0.001 | 0.001 | 290 | - |
| Boehmer 1972: Nr.190 | Planoconvex (4.4 kg) | Ind.; Büyükkale la in the fill behind the Phrygian East Gate | 99 | 0.011 | 0.086 | 0.030 | <i>bdl</i> | 0.007 | 0.522 | 0.004 | <i>bdl</i> | 0.021 | <i>bdl</i> | 0.001 | 230 | - |
| Bo 79/206 | ¼ Oxhide (~7 kg) | LBA; Upper City House 4 near to Temple VII | 98 | 0.085 | 0.327 | 0.024 | 0.051 | 0.165 | 0.037 | 0.061 | 0.029 | 0.717 | 0.001 | 0.006 | 35 | 6.2 |
| Bo 83/819 | Planoconvex (1087 g) | LBA; Upper City Temple VII | 96 | 0.014 | 0.046 | 0.018 | <i>bdl</i> | 0.031 | 0.111 | 0.058 | 0.066 | 3.22 | 0.011 | <i>bdl</i> | 20 | - |
| Bo 87/49 | Planoconvex (387 g) | Ind.; Upper City | 5.41 | 0.40 | <i>bdl</i> | 0.45 | 0.36 | 0.05 | 0.10 | <i>bdl</i> | - | <i>bdl</i> | - | 0.06 | 86% | 7.55% |

1) Schachner 2013: 89-91; 2) Boehmer 1972: cat. inv. Nr. 190; 3) Müller-Karpe 2005, values for Ag and Au from Stos-Gale et al. 1997; 4-5) Herbordt (in press)
- = not determined, *bdl* = below detection limit.

3.4 Copper and bronze industries during the rise of Iron Age polities in central Anatolia

The political and economic processes that led to the rise of the Hittite territorial state in central Anatolia are evident in the production and exchange of metal commodities and finished goods. During the Bronze Age, archaeological and textual evidence demonstrates that communities developed elaborate hierarchies of production, exchange, and consumption based primarily on mechanisms of commercialism and state control leading to increases in centralization during the height of the Hittite Empire. From these data, it is therefore possible to interpret how strategic metal production sequences and commodity chains effectively integrated urban and hinterland social environments through both the organization of labor and the elaborate exchange of unfinished and finished goods. Unfortunately, little to no data of metal production exists dated directly to the end of the Hittite Empire during the 13th century BC, so it is not possible currently to determine empirically how the craft economy responded during periods of regional political and economic reorganization.

During the Mid to Late Iron Age (ca. 900-330 BC), there is an unprecedented virtuosity of metal craftsmanship associated with the rise of large scale polities, especially in tin bronze metallurgy, as is evident through the remains of remarkably well-crafted finished goods (Muscarella 1988). These include intricately finished and stylized bronze sheet metal, which often decorated architecture and clothing and also was used in the production of fine vessels. Cast objects further demonstrate the masterful familiarity with the various properties of bronze, including ornate fibulae and carefully cast socketed arrowheads. It is further clear that these finished goods were consumed within a cultural framework of status display and recognition. While bronze objects are noted across domestic contexts at Gordion, Kaman Kalehöyük, and Kerkenes Dağ, objects which required greatest skill are found in increasing frequency in elite

contexts, including citadel and monumental burial tumuli at Gordion and the palace complex at Kerkenes Dağ.

Despite this development of bronze metallurgy in the Iron Age, there is almost no published data with direct evidence of Iron Age copper production (including extraction mining, primary or secondary production sequences) in central Anatolia, especially those related to the production of high value metal objects. No well stratified remains indicative of metal production are known from the plateau, aside from the Early Iron Age workshop at Boğazköy (Seeher 1997), Tell Tayinat (Roames 2011), Büyükkardıç in Erzincan Province (Şenyurt 2006; Şenyurt, et al. 2006), and a single bronze crucible fragment from early-mid 4th c. BC Gordion (Toteva 2007: 43) used in the secondary production of leaded tin bronze (Rademakers 2014). Yet according to art historical analyses, typologically distinct categories of finished goods typify “Phrygian” style and are thus interpreted to have been produced locally, at least in terms of the secondary production of finished goods (Muscarella 1988: 183-186, and references therein).

Given the current state of evidence, there are three main possibilities that explain the absence of production sites. First, production sequences are located within urban bounds and are similar to Bronze Age strategies, but current excavations and data have not yet uncovered material evidence. Second, all primary and secondary production sequences involved in metal industries must have been located outside of the cities but yet within the bounds of the polity. There is reason to believe that this would be the case, especially since pyrotechnological activities associated with metal production can be hazardous and unhealthy in dense urban environments. The further possibility that workshops were operating in both iron and copper/bronze metallurgy would strengthen this hypothesis, because iron workshops are typically more labor intensive than bronze workshops alone. Lastly, the various primary and

secondary production sequences may have occurred outside of central Anatolia, thereby requiring polities in central Anatolia to import primary ingots of metal and finished goods. This hypothesis requires long-distance exchange and connections with manufacturing centers elsewhere in the Mediterranean and Near East. This model would be consistent with Sherratt and Sherratt (1993: 375), who argue that economic growth first centered in the capital and labor intensive manufacturing zone of the eastern Mediterranean prior to the emergence of secondary states elsewhere in the region. This hypothesis also problematizes any art historical analysis that supposes local styles among many of the objects known to central Anatolia.

3.4.1 Archaeological and archaeometallurgical evidence for copper trade and production during the Iron Age

While there is a general lack of data from central Anatolia, sparse data from directly adjacent regions do suggest that secondary production activities, at least, were supported by the dispersed urban infrastructure during the 9th-5th c. BC. Some evidence suggests that within the florescence of the Neo-Hittite states during the first half of the 1st millennium BC, the circulation of precious metal commodities were similar to those adopted by state institutions of the Late Bronze Age. Silver ingots, including three with Aramaic inscriptions, and Hacksilber pieces were found associated with the lower palace and *Hilāni* temple structures of the prominent regional center of Zincirli-*Sam'al* in southeastern Anatolia (Müller-Karpe 1994: 99-100; von Luschan and Andrae 1943: 119-121). Furthermore, a tuyère and several casting molds, one of which for jewelry, associated with the palace further demonstrate elite sponsorship of metal technologies. A single bronze bun shaped ingot, composed roughly of a 10% tin bronze, was also discovered here but it was from an uncertain context (von Luschan and Andrae 1943: 121).

Data concerning trade and production is no more clear during the Iron Age in east Anatolia and the Caucasus (Belli 1991; Seeliger, et al. 1985; Seidl 1988), where the establishment of Urartian fortress settlements during the 9th-7th centuries BC united into a state in competition with and defense against powerful Assyrian interest based in northern Mesopotamia (Smith 2003; Zimansky 1985). Examples of secondary production are evinced by primary ingots of copper and apparent bronze working tools from sites including Van-Toprakkale, Kayalidere, and Çavuştepe (Müller-Karpe 1994: 101-102). Further examples of secondary production of copper and iron in domestic contexts, and possibly primary production, is noted from the site of Armavir (Argištixinili), where extensive excavations of Urartian households were associated with copper and iron working slags (Martirosyan 1974). This region, extending from the Upper Tigris to the Caucasus is rich in metal resources, and it is likely to produce more important data concerning the rise of metal industries and their social organization during the Iron Age (for earlier periods, see Courcier 2014).

From the few analytical studies of finished objects from across Iron Age central and eastern Anatolia, data clearly point towards two important developments in copper metallurgy. First, there is the clear dominance of leaded and unleaded tin bronze relative to pure copper and other copper alloys for the production of most Iron Age copper based objects. This observation is supported empirically by the adoption of tin bronze across many object type categories (Atasoy and Buluç 1982; Faraldi, et al. 2013; Hirao and Enomoto 1993; Hirao, et al. 1992; Hughes, et al. 1981; Ingo, et al. 2010; Twilley 1996). Trade in pure tin as a commodity, which is normally only identified by pure tin ingots, is also indirectly evinced by the production of pure tinned surfaces on bronze sheet metal, indicative from the 7th c. BC shields from Ayanis in eastern Turkey (Ingo, et al. 2010) and more recently identified on decorative bronze sheet metal from Kerkenes Dağ

dating to slightly later during the 7th-6th c. BC (this dissertation, objects 02TR01U02met01, 02TR01U02met02 and 11TR24U11met01, see Figure 3.11). The interregional adoption of tin bronze is particularly interesting given the reliance of long-distance trade necessary to produce it. It is increasingly likely that local occurrences of tin were probably not sufficient to supply bronze workshops of this size; therefore we must expect tin to be imported inter-regionally in large sums (for weight amounts of tin from 6th c. BC texts from Uruk, see Oppenheim 1967: 240-242). While it is not possible at this time to determine empirically whence the tin came, it seems increasingly likely that Iberian tin is a candidate, which would have been circulated by Phoenician traders across the Mediterranean, in addition to central Asian sources transported over traditional routes. What is less clear is if the production of tin bronze using non-local tin experienced disruptions in tin supply during regional shifts in polities, specifically during the 12th-10th centuries of the Early Iron Age. Data from Chapter 5 will examine this in some detail, thanks to the clearly stratified and continuous deposits at Boğazköy dating from Late Bronze Age through the Late Iron Age.

Second, and perhaps related to the dominance of tin bronze, is a precipitous decline in the production and consumption arsenical copper beginning sometime around the 10th century BC. Copper alloy objects with greater than 1.0% arsenic are increasingly rare for the Iron Age, evinced from selective analyses from this study, Kaman Kalehöyük, Phrygian tumuli in Ankara, and the analysis Urartian bronzes, all referenced above. This observation also holds for most of the Neo-Assyrian bronzes from Nimrud analyzed by Curtis (2013). This is likely the cause of several possible factors or a combination thereof, including but not limited to a decline in the use of iron arsenide speiss, decreases in the use of common polymetallic arsenical minerals like

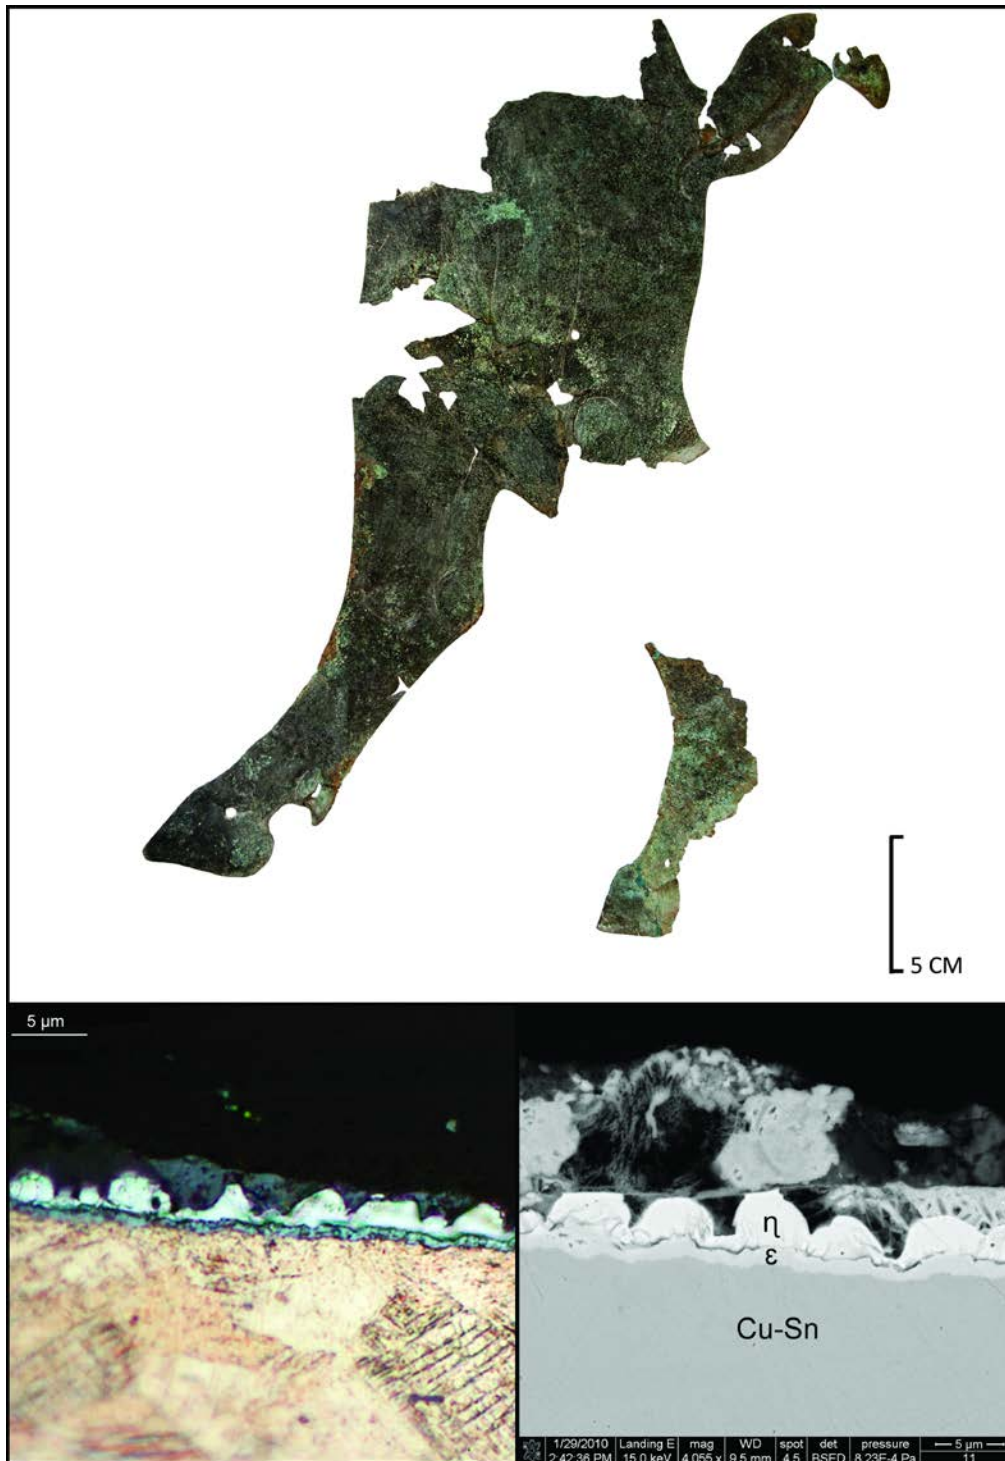


Figure 3.11: Top: one of two tin bronze sheet metal ibex recovered from excavations at the monumental entrance to the Palace complex at Kerkenes Dağ (02TR01U02met02). Bottom left: optical micrograph of a polished and etched (in alcoholic ferric chloride, Scott 1991: 72) section of a sample showing diagnostic eta and epsilon intermetallic phases of copper-tin indicative of surface tinning. Bottom right: backscatter electron micrograph detailing a similar region of the same sample highlighting the phases (see Meeks 1986).

arsenopyrite or enargite, more efficient refining technologies, increased frequency of remelting episodes, and the adoption of primary production technologies that allowed the selective vaporization of arsenic into air, perhaps through roasting ores in open space.

3.5 Conclusion: the organization of copper metallurgy and how trade tracks onto the development of polities

In this chapter I used data primarily from Bronze Age and Iron Age regional centers to examine the organization of metal production and trade. Data from the Bronze Age is richer, allowing the following interpretations. First, Early Bronze Age strategies of metal production and organization were adopted and enhanced during subsequent periods of increasing social complexity. Following Yener (2000), these strategies include adaptive and fairly regionalized primary and secondary production; the prolific use of polymetallic ores common to Anatolia but uncommon to other regions in the Near East; and finally the development of geographically segmented divisions of labor into what Yener called “multi-tiered organization of production.” Towards the end of the 3rd millennium BC and by the beginning of the 2nd millennium BC, evidence points towards the development of incipient industrialism and markets. The regional landscape of copper production and trade appears to be highly structured according to an industrial ecology, where dispersed natural resources extend networks of trade into regional centers, and where the pull of cooperation and economies of scale enforce the emergence of highly clustered economic activities.

Second, this evidence for increased modes of secondary production is apparent in urban contexts during the MBA, where workshop clusters appear across domestic and palace/temple elite contexts. Texts from Kültepe further inform the nature of metal trade, demonstrating a

particular foci of production along the northern periphery of central Anatolia, including those proximate to the polity of *Durhumit*. Archaeometallurgical evidence from Kültepe add further nuance to the texts, showing that there is a clear gap in the textual data, where copper is also derived from ore sources to the south in the central Taurides. Evidence points towards a somewhat decentralized copper and bronze production economy, and a centralized production of high-value objects made of silver, iron, and gold.

Third, the imperialistic efforts of the Hittites transformed the nature of metal commodity and finished goods flow by requiring an expanded system of tribute and tax into the core. This effectively brought metals, both raw materials and objects, into the inventories of the palace and temples, first and foremost at the empire capital of Hattuša. Textual data demonstrate important differences between the flow of materials and objects coming in as tribute and taxes (mostly copper and tin) and those being stored in palaces and redistributed (mostly silver and gold). Archaeological data reveal how during the later phases of the LBA, metal workshops across Boğazköy-Hattuša were variously associated with both elite domestic and palace/temple contexts, demonstrating differential sponsorship in production activities.

Lastly, the reemergence of polities during Iron Age shows a paucity of data relating to metal production and trade. It was suggested above that this is most likely due to the fact that production activities have either not yet been discovered in urban contexts or they are simply not there, reflecting a novel organization of regional production not yet observed in central Anatolia. Trade in pure metal, however, must have occurred given the near complete adoption of tin bronze and decline in arsenical copper, as evidenced from peripheral regions. I will evaluate this problem as it relates specifically to Bronze Age production and trade strategies in the following chapters.

CHAPTER 4: ARCHAEOLOGICAL CONTEXT AND CHRONOLOGY OF THE SAMPLES

4.1 Introduction

This chapter presents the background information pertaining to the stratigraphic, chronological, and contextual information of the samples analyzed in this dissertation. A total of 1147 copper base samples were used in this study, 1074 from the multi-period site of Boğazköy and 73 samples from the single period Iron Age city of Kerkenes Dağ. A total of 381 samples dating primarily to the Late Bronze Age and Middle to Late Iron Age assemblages were analyzed by EDXRF and the remainder samples were prepared and analyzed by pXRF in the field (see Chapter 5). Most of the samples come from non-funerary contexts, with the exception of several fibulae discovered during excavations of Iron Age 7th-8th century BC pithos and urn burials in the Lower City (Büyükkale phase IIa). The chronological and contextual information is summed up in Table 4.1, and these will be more fully discussed below. Unless noted, inventory numbers, descriptions, and contextual details concerning the find spots of the objects where available are presented briefly in Appendix A.

4.2 Boğazköy

The impressive remains of the archaeological site of Boğazköy (directly adjacent to the modern village of Boğazkale in Çorum Province) are situated at the narrows of the southwestern end of the Budaközü Valley (Figure 4.1). This location consists of several large outcroppings of

rock, a deep perennially watered canyon, and several flat laying plateaus watered by natural springs. By the mid 1800s, European travelers visited the location and variously published reports on the remains of the Great Temple (Temple 1) and the extramural sanctuary of Yazılıkaya with its impressive reliefs of gods and kings in stone (Alaura 2006; Schachner 2011a: 21-32; Şentürk, et al. 2001). In 1893-94 Ernst Chantre directed the first major excavations at Temple 1, the elite citadel at Büyükkale, and Yazılıkaya (Chantre 1898). In addition to further elucidating the Bronze Age architecture, his discoveries included a small repertoire of cuneiform tablets that, with the later discovery of palace archives by Winkler and Makridi in 1906, helped in the decipherment and description of the Hittite language by Hrozný. These data later helped to identify the remains of Boğazköy as Hattuša – capital of the Hittites.

Winkler and Makridi's excavations of Büyükkale and small sondages elsewhere at the site, which lasted from 1906-07 and 1911-12, were bolstered by the efforts of Puchstein and Kohl beginning in 1907. Puchstein effectively helped manage a comprehensive survey of the city and select excavations of fortifications and temples in the Upper City (Puchstein 1912). After a nearly two decades from 1931-39 and 1952-77, Kurt Bittel directed excavations focused primarily on work at Büyükkale which finished in 1966. Extensive excavation projects moved to the Lower City, Temple 1, and further detailed work at Yazılıkaya. Since 1952, work at Boğazköy has been uninterrupted. This work, which operated under the auspices of the Deutsche Orient-Gesellschaft and the Deutsches Archäologisches Institut, generated some of the first stratigraphic control concerning the development of the city and ushered in a new era of empirical material studies concerning Hittite archaeology.

From 1978 to 1993, Peter Neve, an architectural historian, resumed detailed research of Temple 1 and domestic architecture in the Lower City. Afterwards, he began excavations at the

so-called Südburg fortress, Nişantaşı, and an elaborate investigation of the entire Upper City temple precinct and monumental city walls and gates. His work demonstrated a broad new understanding of the development and distribution of cult architecture in the Upper City (Neve 1996).

Jürgen Seeher directed the project from 1994 to 2005. His experience and previous focus as a prehistorian helped influence a novel program of intensive archaeological investigations focused on the absolute chronology and economic life of the city from the point of view of archaeological remains. His excavations at Büyükkaya, a prominent high place in the north of the city, revealed for the first time in central Anatolia a continuous and well-documented stratigraphy tracking changes from the Late Bronze Age with intact Early Iron Age and Middle to Late Iron Age deposits. This work, which began first with Neve in 1993 the year before his retirement, has demonstrated how the Hittite capital gradually declined, was reused, and then experienced a reemergence as a prominent polity during the Mid to Late Iron Age. His later work focused on select excavations of monumental grain silos, water reservoirs, and urban infrastructure in the Sarıkale Valley.

In 2006 Andreas Schachner continued work in the Sarıkale Valley and then in 2009, he began a large new program in the Lower City to understand both the development of the city from its Bronze Age beginnings into the capital of the Hittite Empire. This renewed work has also shed light on the large cut rock Kesikkaya and its associated Hittite monumental architecture, terraced Iron Age structures, and Galatian architecture. Other excavations by Schachner at Yenicekale, the middle plateau between Yenicekale and Sarıkale, and the city wall have variously revealed fundamental data to the design and dating of both monumental and domestic architecture in the northwestern slope of the Upper City.

Table 4.1: Total number of copper alloy samples from Boğazköy and Kerkenes Dağ that were analyzed for chemical composition in this study.

| | <i>Region</i> | <i>Subregion</i> | <i>Time Period</i> | | | | | |
|------------------------|-------------------------|-------------------------|--------------------|------------|------------|------------|------------------|----|
| | | | <i>EBA</i> | <i>MBA</i> | <i>LBA</i> | <i>EIA</i> | <i>MIA / LIA</i> | |
| Boğazköy | Büyükkale | - | | | 3 | | 2 | |
| | Büyükkaya | - | 8 | | 115 | 35 | 52 | |
| | Lower City | City Wall | | | | 3 | | 4 |
| | | Kesikkaya, Northwest | | 16 | | 195 | | 3 |
| | | Kesikkaya, Posternmauer | | | | 9 | | |
| | | Kesikkaya, South | | | | 30 | | 10 |
| | | Northern Quarter | | 3 | | 13 | | 9 |
| | | Temple 1 Magazines | | | | 6 | | |
| | Northwest Slope | Granary | | | | 29 | | 11 |
| | | Middle Plateau | | | | 1 | | |
| | | Northwest Slope | | 2 | | 1 | | |
| | Upper City | Yenicekale | | | | | | 1 |
| | | East Reservoirs | | | | 8 | | 2 |
| | | King's Gate | | | | 1 | | |
| | | Lion's Gate | | | | 1 | | |
| | | Nişantepe | | | | 1 | | 1 |
| | | South Reservoirs | | | | 9 | | |
| | | Südburg | | | | 1 | | 6 |
| | | Temple Quarter | | | | 71 | | |
| | | Upper City | | | | | | 3 |
| Yerkapı | | | | | 1 | | 1 | |
| Upper City West | Middle Plateau | | | | 28 | | | |
| | Sarıkale Valley | | | | 362 | | 8 | |
| | Yenicekale | | | | 5 | | 1 | |
| Total | | | 8 | 21 | 892 | 35 | 114 | |
| Kerkenes Dağ | Cappadocian Gate | - | | | | | 32 | |
| | Megaron | - | | | | | 1 | |
| | Palace | - | | | | | 28 | |
| | South West | - | | | | | 1 | |
| | Street | - | | | | | 4 | |
| | Urban Block 8 | - | | | | | 7 | |
| Total | | | | | | | 73 | |

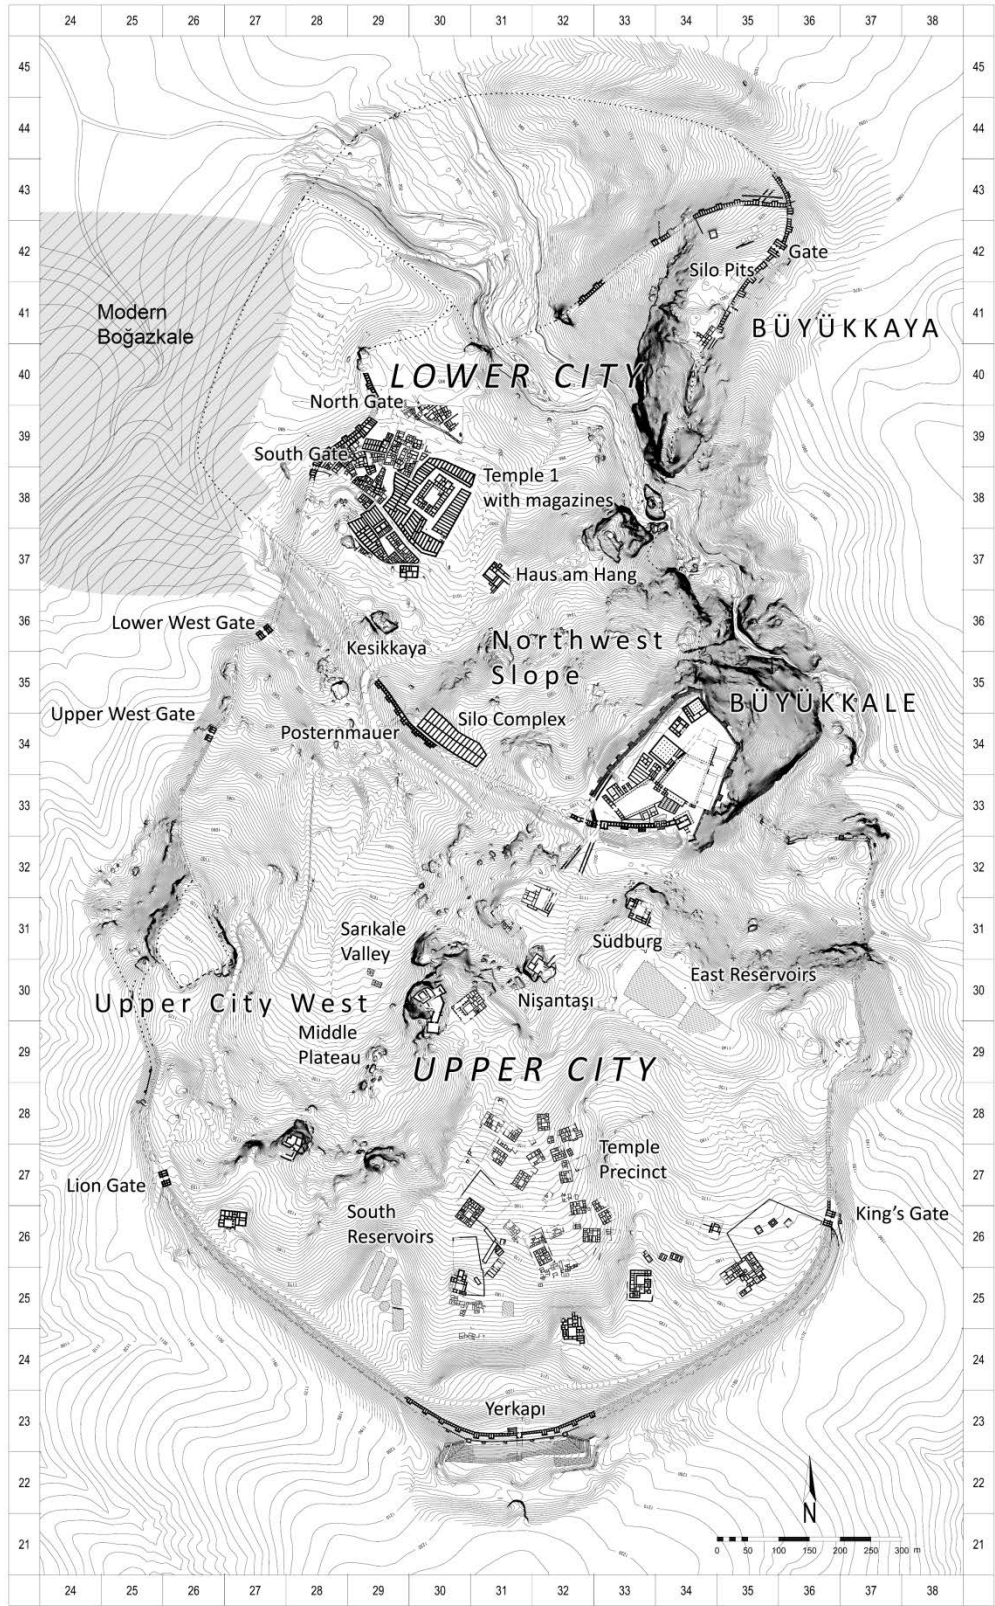


Figure 4.1: Map of Boğazköy with emphasis on the Late Bronze Age. Note most recent excavations at the Lower City are not shown here (courtesy of the Boğazköy Expedition).

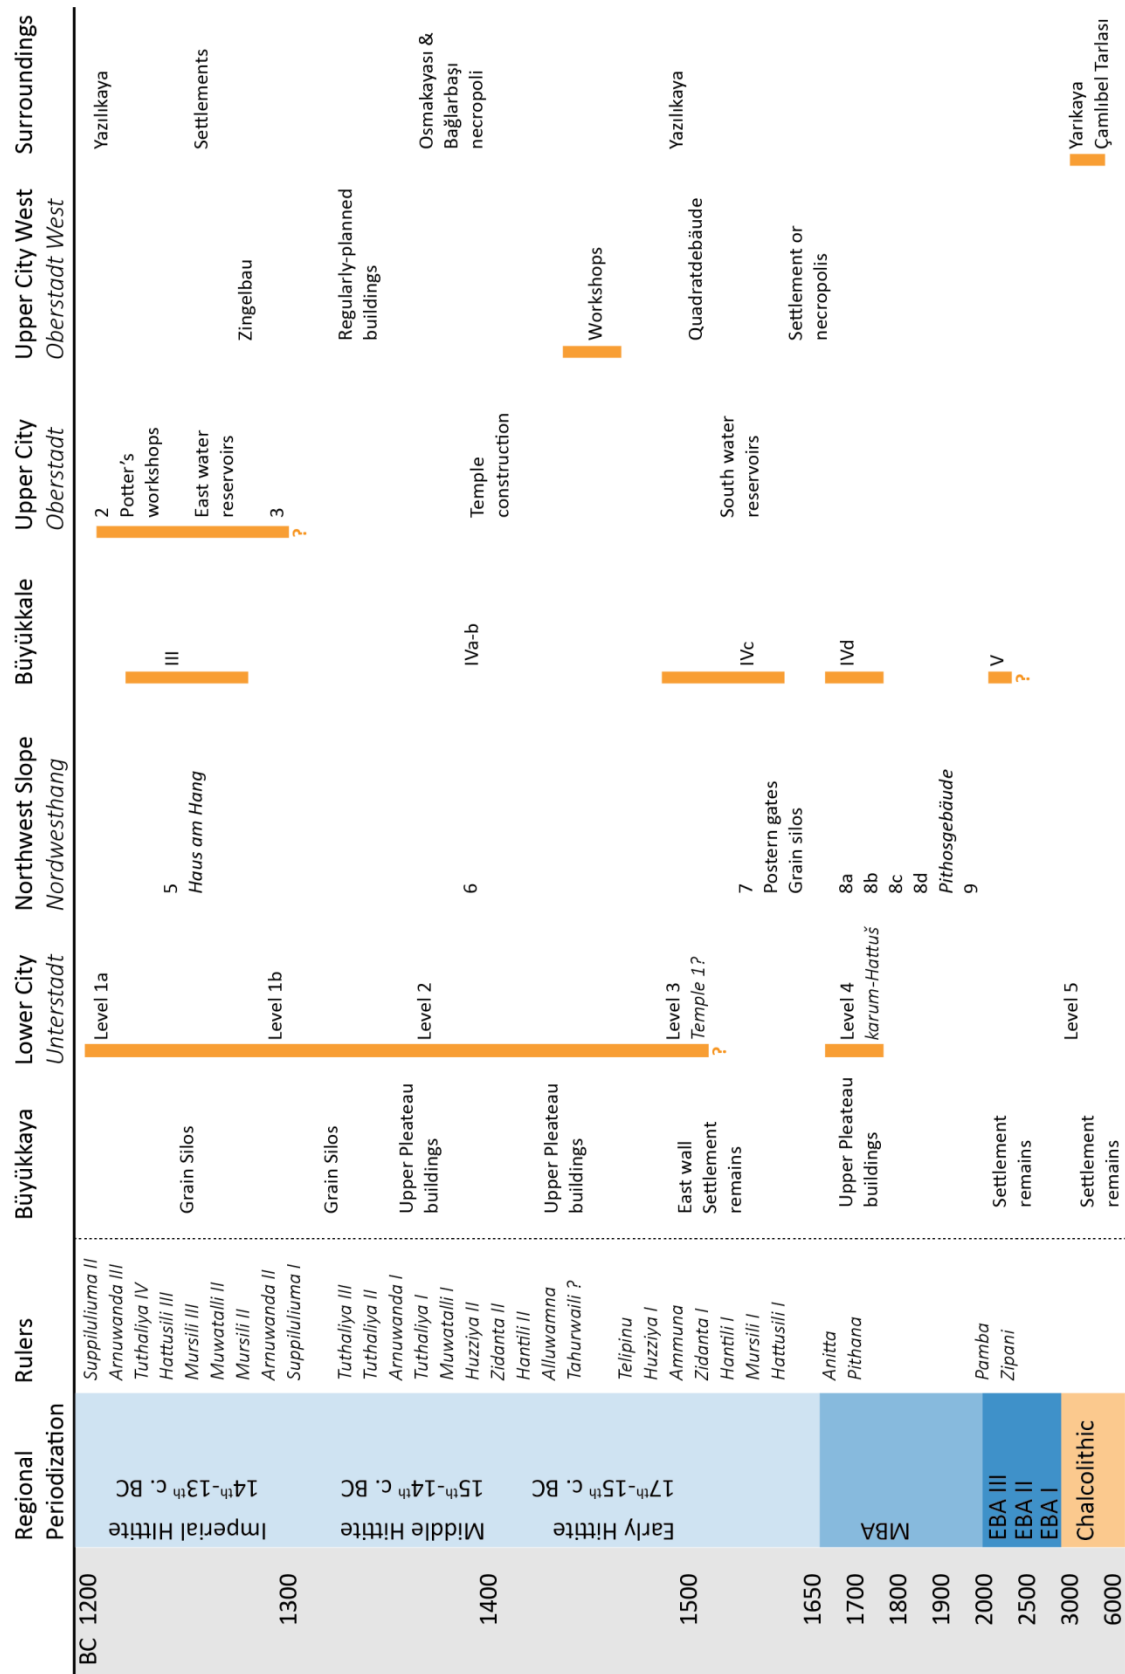


Figure 4.2: Chronological development, stratigraphic periods, and key features from locations at Boğazköy-Hattuşa from the Chalcolithic until the end of the Late Bronze Age. Bars represent periods of positively identified metal production (adapted from Schachner 2011: 14-15).

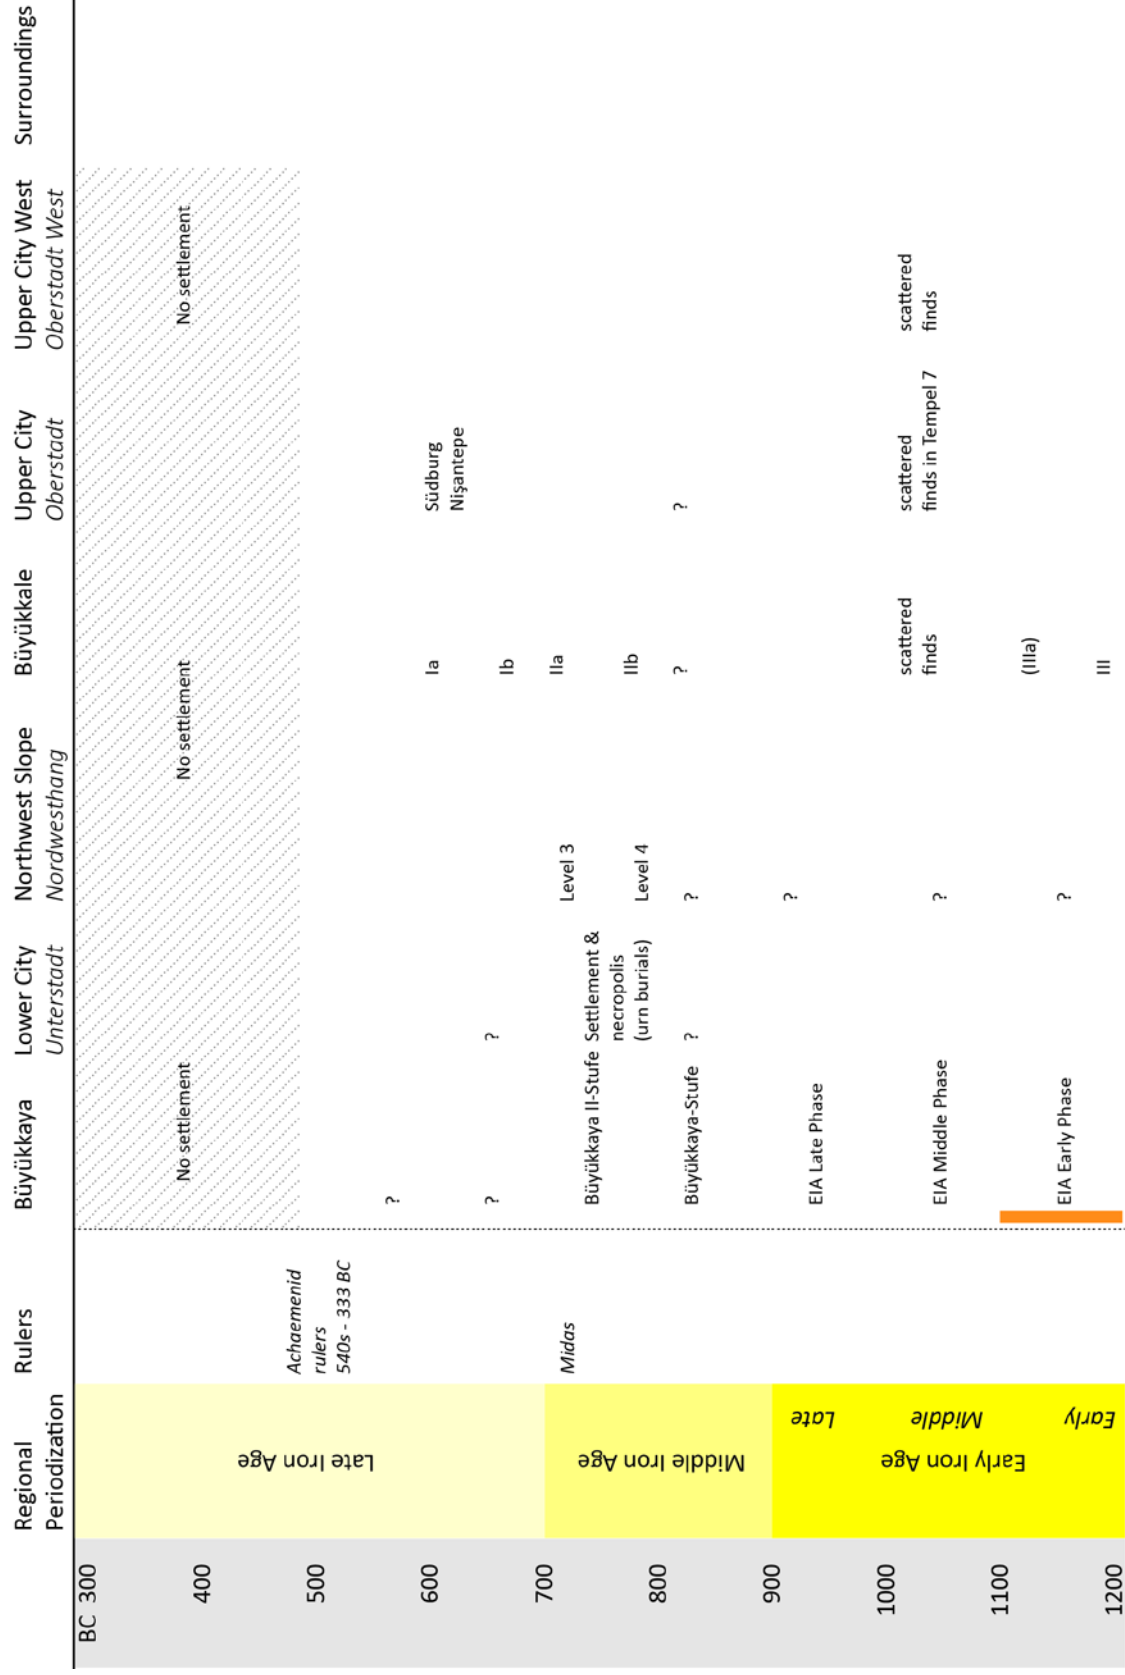


Figure 4.3: Chronological development, stratigraphic periods, and key features from locations at Boğazköy-Hattuša during the Iron Age. Bars represent periods of positively identified metal production (adapted from Schachner 2011: 16-17).

Given the multifaceted nature of the site with a highly variable topographic terrain and extensive excavations over the years in different localities of the site, the chronological framework is quite complex (Mielke 2006: 14-18). This complexity has further problematized historical inference based on the rich textual record (Klinger 2006; Seeher 2008). Thanks to the application of modern absolute dating techniques, the issues of intrasite synchronization are being resolved (Schoop and Seeher 2006; Seeher 2006a). Figures 4.2 and 4.3 represent the relative and absolute chronology that is used in this dissertation, incorporating the most recent synthesis of the site by Schachner (2011a).

4.2.1 Büyükkaya

Büyükkaya is the name of a prominent rocky ridge in the northeastern area of the walled city. It measures roughly 550 x 200m, and its southwestern rock face of the ridge plunges around 100 m down to the Lower City. Two arms of the Hittite city wall bound the northern corner of this region, which can be further broken down into three distinct areas, including the upper, middle, and lower plateaus. After initial investigations by Bittel in 1952 and 1954, renewed and focused investigations were undertaken by Neve in 1993 and then Seeher from 1994 to 1998. This region of the Boğazköy is important in particular because of its intact multi-period period remains which date from the Early Chalcolithic (6th millennium BC) and then after a gap continuously from the end of the EBA III through to the Middle Iron Age, including one of the only well-dated Early Iron Age sequences in central Anatolia (Genz 2004; Schoop and Seeher 2006). Material remains dating to the EBA and EIA both demonstrate that metal production was a central activity in this region. Analyses of copper alloy objects include eight from the late EB III, 115 from the LBA, 35 from the EIA, and 52 from the Middle Iron Age.

Significant Late Bronze Age developments in this region included the monumental construction of city walls throughout the Lower City dated to the 16th century BC. Associated finds to a large multi-roomed building complex on the Upper Plateau date the building to the Büyükkale IVa-b phases (early Empire period) (Seeher 1999: 328). The northern city wall and earthen silos with stone lined floors are associated with somewhat later radiocarbon dates placing these structures into the Empire period 14th-12th centuries BC (Schoop and Seeher 2006: 58).

Early Iron Age strata are located on the Middle Plateau of Büyükkaya, where excavations revealed a series of contexts stratigraphically above stone-lined Hittite silo pits (Genz 2004; Seeher 1998). The oldest phase of this settlement consists of a series of small pits and post-holes. The middle phase consists of several wide rectangular and shallow pits measuring up to 8 x 5 m associated with numerous post-holes. The remains of wooden revetments or supports suggest that these pits functioned as semi-subterranean structures, possibly functioning as pigsties (Seeher 2010: 223). In the last phase, a small rectangular metal workshop with stone foundations and an oven structure was found in association with crucible tuyère fragments, slag, and metal tools. Radiocarbon analyses dated these phases between ca. 1200-1000 BC (Schoop and Seeher 2006: 58-60; Seeher 2000: 374). All samples come from these occupational phases except for a socketed chisel (ETD 96/31) which was recovered from a mixed context in the lower plateau of Büyükkaya with later Phrygian type and local Early Iron Age pottery. Comprehensive resettling of all the plateaus is noted during the 9th century BC and by the 8th century the upper plateau was fortified (Seeher 1999: 327-328).

4.2.2 Büyükkale

Büyükkale is located in the center of the city on a large raised plateau ca. 250 x 140m in size that is surrounded on all sides by steep slopes and exposed rocky cliffs that fall into the

Lower City and Northwestern Slope. The relative chronology of deposits here consist of five major phases dating from the EBA III with near continuous occupation through till the Mid to Late Iron Age. The monumental building project of a palace during the Imperial Hittite period ca. 14th-12th centuries BC (Büyükkale III) overlaid most of the previous remains, including known domestic architecture during the MBA (Büyükkale IVd) and Early Hittite (Büyükkale IVc) phases. The Imperial Hittite palace located here included several distinct structures, including a reception hall, courtyards, residence for palace officials, and several rooms dedicated to the palace archives. Following the abandonment of the palace during the 12th century BC, a large fortified Phrygian building was constructed over the Hittite palace during the 9th-8th centuries BC of the Middle Iron Age (Neve 1982).

A total of six diagnostic objects from Büyükkale were available for analysis, all of which are previously published (Boehmer 1972). Three objects dating to the Late Bronze Age include a cast shaft-hole axe (Bo 477/d) from Room B of the level IIIb palace; a stylized belt with gold wire (Bo 284/e) from Room A; and a planoconvex ingot (Boehmer 1972, Nr. 190) found in a poor context of the burnt debris behind the back gate of the Phrygian eastern tower dated to level 1a. Two further objects clearly dating to the 9th-8th century BC include a bilobate arrowhead (Bo 443/i/3) from debris over Building D and one fibula (Bo 307/n) found in the east canal in Phrygian debris.

4.2.3 Lower City and Northwestern Slope

The Lower City, or alternatively called the *Altstadt* or Old City, of Boğazköy consists of several distinct areas bounded by the postern wall and Büyükkaya to the south, the city wall to the north and west, and to the east the topography dips into the Budaközü before reaching the

west-facing cliffs of Büyükkaya. This region is characteristically flat, allowing for the urban infrastructure to develop less restricted as elsewhere at the site. While this region is dominated by the so-called Hittite period Great Temple (Temple 1), the Lower City has a deeper settlement history extending to at least the late 3rd millennium BC and Middle Bronze Age. There is good reason to infer that the remains of this earlier city functioned prominently within the framework of the Middle Bronze Age trading network described in Chapter 3. Evidence from a contemporary Old Assyrian text (Kt 89/k 387b) from Kültepe refers to the city of *Hattuš* as one with a king, a palace, and a hinterland over which he ruled (Barjamovic 2011: 287).

The earlier urban phase in the Lower City are evinced in the northern quarters excavated in 1938-1957 by Bittel and the new work directed by Schachner since 2009 in the region northwest of Kesikkaya and adjacent to the 16th century BC Early Hittite postern wall. A small sample of metal objects coming from these earlier contexts were collected for analysis, including three from Bittel's excavations in the northern quarter and another 16 derived from secure domestic contexts northwest of Kesikkaya. The majority of these objects include eye needles, pins, and discarded weapons; however, a single planoconvex ingot (Bo 11/590), discovered in a room with a pyrotechnological installation, presents conclusive evidence for secondary production during this period of the city (Schachner 2012: 89, 91, fig. 11; Lehner and Schachner in press). A further two samples come from MBA contexts along the northwestern slope up to the Büyükkale, including a spearpoint from the so-called *Pithosgebäude* (Bo 311/s). A large curved and flat knife (Bo 645/t) from these general contexts, possibly dating to the Büyükkale IVd period was also analyzed.

By the end of the 16th century BC and coinciding with developments across the city, the densely settled Lower City transformed as the rest of the city developed under Imperial Hittite

rule (Schachner 2011a: 71-82). With the construction of the postern walls, Temple 1, rows of storage magazines, large multi-roomed elite residence, and large paved streets, the Lower City was transformed into a space of monumentality. Associated with the residential quarters of this area north of Temple 1, Müller-Karpe cogently describes a range of secondary metallurgical activities (1994: 80-82). It is clear from these analyses that by the Imperial Hittite period ca. 14th-12th century BC, and perhaps earlier, many metal production activities operated independently of state institutions yet were still sponsored by elite households. Recent work focused on the large and cut spire of rock called Kesikkaya, has further revealed how large monumental architecture, dating perhaps to the early phases of Imperial Period, was integrated with the natural landscape (Schachner 2014: 104). In addition to material from these phases, metal remains associated with an early Imperial Hittite period *Hallenhaus* structure (Schachner 2010: 167-168) and other fragmentary buildings demonstrate a wide variety of tool and ornament consumption. From these contexts, 195 samples come from the Hittite houses and related deposits, six samples come from contexts within the Temple 1 magazines, and a further 39 come from contexts associated monumental architecture and exposures of the city walls.

Further analyses come from objects derived from contexts associated with the large scale granaries, which were excavated by Seeher in 1999 and 2000. These monumental granaries are located directly on the northern side of the postern walls and downslope to the west of Büyükkale. Several radiocarbon dates place the construction of the granaries into the 16th century BC (Seeher 2006b: 74), which coincide with the construction of the postern walls and is contemporary with the construction of the southern water reservoirs of the upper city (Schachner 2009a; Schoop and Seeher 2006: 59-60). A total sample of 29 objects was selected from these contexts, including mostly pins, needles, tools, and projectiles. A single flat, curved blade knife

from earlier excavations in this area (Bo 645/t), dating to BK phase IVc or IVb, was also sampled for analysis.

The Iron Age in the Lower City and Northwestern Slope primarily dates to the Middle and Late Iron Age. Three regions in particular had securely dated materials. First, Middle Iron Age remains from above the Temple 1 magazines, include examples of cult architecture and a large necropolis with a wide variety of internment types (Neve 1973: 142, fig.141; 1975: 95). Seven examples of fibulae, a socketed lance, and finely hammered sheet were analyzed from these contexts. Second, recent excavations south of Kesikkaya have unearthed a large terraced Iron Age building (Schachner 2014: 99-103), from which nine objects were analyzed, including fragments of wire, tools, and a single bilobate socketed arrowhead. Scattered Iron Age objects associated with debris next to the city wall during restoration in 2012 and 2013 were also analyzed. Two objects from excavations northwest of Kesikkaya, including a double headed pin and a fragment of sheet metal, were also analyzed. Finally, 11 objects from Late Iron Age structures above and near to the LBA granaries deposits were examined for analysis (Genz 2006, 2007). These include examples of wire, needles, sheet metal, and a fibula.

4.2.4 Upper City

Whereas the urban development of the Lower City and Büyükkale extends into the Early Bronze Age, the earliest securely dated structures in the Upper City date to the mid to late 16th century BC, including the so-called *Südteiche* or South Reservoirs (Schoop and Seeher 2006: 60-62; Seeher 2006d, 2008). This important fact reshapes our understanding of the development of the Upper City and its monuments, which were previously thought to have been constructed only during the Imperial Hittite period during the time of Ḫattušili III or Tudḫaliya IV early in the 13th

century BC. Now, along with the monumental constructions of the Lower City, including the construction of the silos and postern walls, the Upper City represents an important extension of state power to a couple centuries earlier during the beginning of the Hittite imperial strategies (Schachner 2009a).

Compared again with the Lower City, the layout of the Upper City is quite different (Neve 1996). The flat plateau of this southernmost extent of the city supported the construction of at least 30 temples, the majority of which are located in the so-called central Temple Quarter (Neve 1999). The largest temples (Temples 2, 3, 5, 30, and 31) are located outside of the Temple Quarter in conspicuous areas of the Upper City. The southern city walls, together with the massive Yerkapı construction and distinct gateways, project further monumentality at the city (Neve 2001). Other monumental buildings were characteristically constructed on prominent rises of rock, including the buildings at Sarıkale, Yenicekale, and Nişantaş, yet the functions of these buildings remain somewhat unknown. A couple of large buildings just south of the postern wall and west of Temple 31 and the Südburg, including the so-called *Westbau*, functioned as a palace archive as indicated by the preservation of over 1000 sealed bullae in various rooms (Herbordt, et al. 2011; Neve 1996: 52-58). Mielke (2011a: 171) has argued that the *Nordbau* was used as official stables due to its proximity to the palace at Büyükkale. Late Hittite phases of the Temple Quarter have provided some evidence of shifting use of the temples in addition to reuse of the space for workshop activities, including pottery production and possibly also metal production (Müller-Karpe 1988; 1994: 82-84).

Ninety-two objects were analyzed from the Upper City. These include 71 objects from the temple quarter including also several objects from the Temple 7 inventory on Sarıkale. These objects are comprised of many diagnostic types, including sickles, various axes, stemmed

arrowheads, tools, armor plates, and pins. Two separate copper ingots were also analyzed from these contexts, including a planoconvex ingot (Bo 83/819) from Temple 7 and a quarter oxhide ingot from a house cellar context in between Temples 4 and 6 (Neve 1979: 301) dated to the 14th century BC. These objects will be published by Herbordt (in prep), where she analyzes their contextual significance within the temples, especially as they relate to the economic functioning of these institutions and their inventories.

With the assistance of Andreas Schachner in 2013, we were also able to analyze a small sample of one of the copper alloy dowels which were used to fasten the cyclopean masonry located at the northwestern side of the King's Gate (MA- 136337). A single lamellar headed pin discovered during clearance of the Yerkapı (Bo 82/19) was also included in this analysis. Additionally, the surface measurement of the well-known inscribed sword of Tudḫaliya II which was found by chance near the Lion Gate in 1991 during road clearance (Neve 1993: 648-652; Ünal, et al. 1992). Several small tools, needles, pins, and indeterminate sheet metal from the East and South Reservoirs were also analyzed.

The Early Iron Age and the early phases of the Middle Iron Age in this region of Boğazköy have produced only scattered finds at the Sarıkale. However by the late 7th century BC, evidence for Phrygian settlement around the Nişantaş/Südburg area south of Büyükkale demonstrates significant investment in fortification not unlike Kerkenes Dağ. A total of six objects were analyzed from the Nişantaş/Südburg area, including a two-part composite ornament (Bo 89/29), a pair of tweezers (Bo 89/31), two fibulae (Bo 88/37 and Çorum Müzesi Inv.1-2430-91), and two toggle pins (Bo 89/128 and Bo 89/99).

4.2.5 Upper City West

The Upper City West comprises a low, northwards down-sloping valley which spatially connects the Lower City and the Upper City. Investigations led by Seeher began here in 2001 until 2005 and were resumed by Schachner in 2006 until 2008. Among many important details, research in this region has provided first an empirical understanding of the chronological development of the Upper City north of the postern wall. Second, investigations have shed some light on domestic architecture during the Imperial Hittite phases of the city in addition to large regularly planned buildings of unknown function. Two areas of focus were established first in the Sarikale Valley and then later on the middle plateau between Yenicekale and Sarikale further to the south. Excavations in the Sarikale Valley have revealed at least six major phases of development. The oldest phase dates to the end of the 16th century BC and consists of two regularly planned structures (so-called *Quadratgebäude*) roughly 19 x 19m and 17.8 x 16.2m in dimensions (Seeher 2006c: 171-179). In 2008, another building probably dating to this phase (Gebäude 7) was found, in which were found two diagnostic metal objects of known types, including a copper alloy knife (Bo 08/217) and a lugged axe (Bo 08/227) (Schachner 2009b: 28).

The following phase is defined by a heavily eroded building overlaying *Quadratgebäude* 2. This phase is followed by another phase, which is characterized by intact secondary metal production installations, including a large earthen bowl shaped furnace and a melting crucible dating to the late 15th to 14th century BC (Seeher 2004: 70; 2006c: 175-176). The next phase is referred to as the *Badezimmer-Horizont* which is characterized by heavily fragmented structures, one of which had the remains of a terracotta bathtub installation (Seeher 2004: 67-69). Excavated from the same area were a tuyère fragment and a rod-ingot mold, together with other raw materials and tools (Seeher 2005: 70). The following phases are characterized by more

fragmentary structures with pottery dating to the 14th-13th centuries BC, and finally the so-called *Zingelbaukomplex*, which consists of a large building measuring approximately 31.5 x 25m (Seeher 2003: 7). A total of 362 objects were sampled and analyzed from these contexts. The vast majority of these objects consist of fragmentary wire, needles, pins, and indeterminate sheet metal; however this large sample size, clearly dating from the 16th-14th centuries BC, represents the largest set of metal analyses from the site. A further 28 samples come from the so-called GAL-MEŠEDI elite residence located on the middle plateau, which dates to the early 14th or early 13th centuries BC (Lehner in press-a; Schachner 2008, 2009b, 2015, in press-a). From the excavations at the small monumental complex at Yenicekale, I analyzed a further 5 objects dating to the Imperial Hittite period and another from the Middle Iron Age (Schachner in press-b).

4.3 Kerkenes Dağ

Located approximated 50km to the southeast of Boğazköy, the low granitic mountain of Kerkenes Dağ was the chosen location for the new foundation of an Iron Age capital in the mid to late 7th century BC. Based primarily on circumstantial evidence, this city is most likely to be identified with ancient Pteria, mentioned by Herodotus (Przeworski 1929; Summers 1997: 86; 2006a: 166-167). Archaeological investigations of the material culture present at the city demonstrate that it was culturally Phrygian, at least from evidence derived from elite contexts. This is most convincingly argued on the basis of fragmentary texts and graffiti written in the Old Phrygian language (Brixhe and Summers 2007); evidence of cult practice from images, graffiti and semi-iconic idols well known across Phrygian central Anatolia (Summers 2006a: 181); and the distinct architectural traditions that include free-standing two-roomed buildings with pitched,

thatch-covered roofs (Langis-Barsetti 2013; Summers and Summers 2006). Within perhaps no more than three generations of time, the city was destroyed and abandoned during the mid-6th century BC, perhaps due to prolonged conflict between Croesus, the king of Lydia, and the westward expanding powers of Persia ruled then by Cyrus the Great in the 540s BC.

Without any evidence for earlier occupation on the mountain, Kerkenes is thus a new city with elite foundations that echo Phrygian rule. The city may be what Summers and Summers (2013: 138) call an “ideal” city, because evidence of overarching design and control of the city planning can be found in many contexts across several scales across the site. The urban layout, composed of radially aligned compounds and streets, demonstrates clear evidence of centralized planning. Encompassing 271 hectares of urban space, the 7.5kms of city wall, composed entirely of hewn uncut granite blocks, extensive glacis fortifications, and periodic towers, are passable only through one of seven monumental gateways. Within the city, a large urban compound with a heavily fortified monumental entranceway is interpreted to be a palace, while a diversity of separate urban compounds extend into nearly all open space in the city. Other buildings across the site, including several monumental two-roomed buildings or halls, appear to have non-domestic functions, perhaps correlating with conspicuous cultic institutions (Summers 2007; Summers, et al. 2004). Outside of the city walls and located on prominent ridges, several immense tumuli serve as burial monuments most probably of the rulers of the city.

The first archaeological investigations of the site were conducted by Erich Schmidt in 1928, who was then part of the Oriental Institute excavations at Alişar Höyük, directed by Hans Henning von der Osten. Schmidt’s test trenches across the city, in addition to the cartographic surveys by F. Blackburn in 1927, helped provide crucial evidence for the initial dating of the site, which they placed into the pre-Hellenistic Iron Age (Schmidt 1929; Summers and Summers

1998). The site did not receive further serious attention until 1993, when Geoffrey and Françoise Summers began a long-term project at the site under the auspices of the British Institute of Archaeology in Ankara. One of the initial and on-going foci of research at the site has been the intensive surveying on the site, including extensive subsurface remote sensing, have effectively mapped out much of the urban block layout of the site (Branting 2004; Branting and Summers 2002; Branting, et al. 2007). Selective excavations began in 1996 and 1998 with several new test trenches. Beginning in 1999 and into 2000, clearance of the so-called Palace Complex fortification and Cappadocian Gate began, and in 2002-2005 larger scale excavations of these structures revealed their impressive preservation and the first conclusive details of cultural affinity associated with the city and its development. Further clearance and excavations of the Cappadocian Gate resumed in 2007 and finished in 2011. Investigations in the central and northern city were initiated in 2003 with the excavation of a megaron styled building and in 2010 with the excavation of a monumental two-roomed structure. Finally, the excavation of so-called Urban Block 8 in the northern end of the city, which was first investigated in 1996, continues to uncover domestic contexts to complement our understanding of the city which has been understood in terms of elite contexts until recently.

Samples of copper and copper alloy objects were collected predominantly from the Palace Complex and Cappadocian Gate, where there was a greater diversity of finds. Because of the depositional history at the site, in addition to the fact that there is very little overburden from later periods, all samples are chronologically contemporaneous and are assumed to be bounded in date by the 7th-6th century BC date of the city.

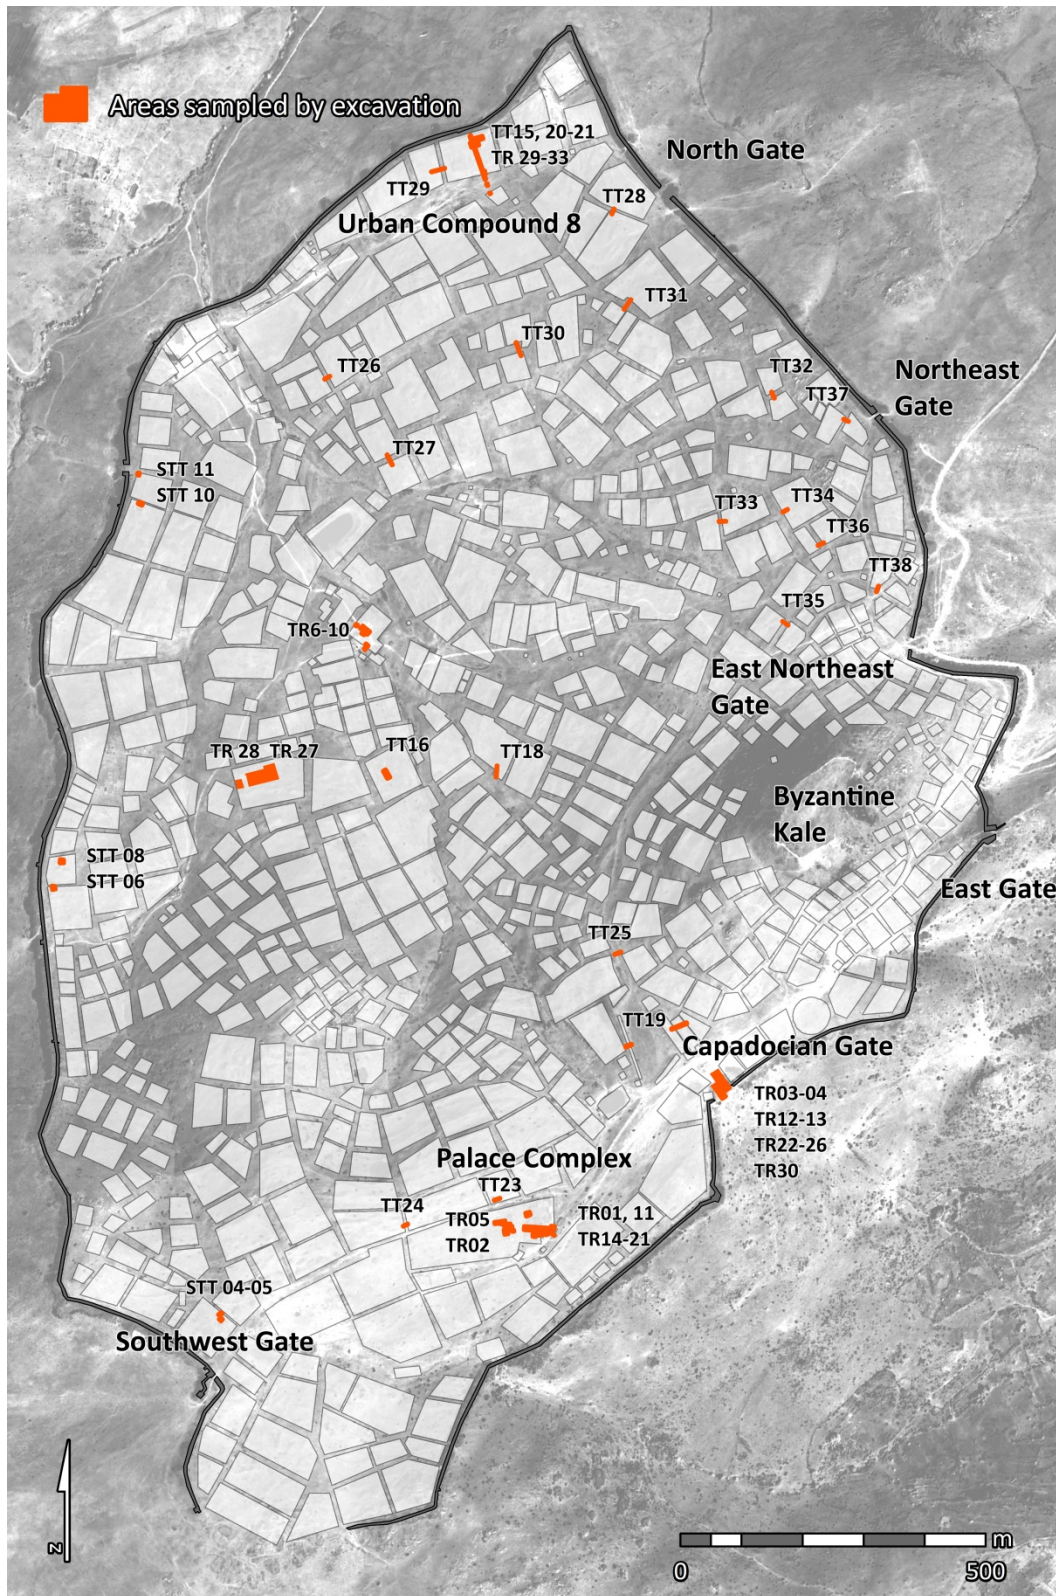


Figure 4.4: Iron Age city plan of Kerkenes Dag noting areas sampled by excavation up to 2014. Data from the project archive and Branting (2004).

4.3.1 Palace Complex

The Palace Complex is located on a high rise in the southern city along a major transport corridor linking the Southwest Gate, the Cappadocian Gate and further extensions into the lower elevations of the city to the north. The complex occupies the single largest walled urban compound in the city and is the only compound that has been fortified with a glacis. Clearance and excavations at the Palace Complex extending from 1999 to 2005 were focused on the articulation and relation of the glacis fortifications, the so-called Monumental Entrance into the compound, and two large two-roomed structures immediately afterwards. This work has been summarized in Summers and Summers (2008), who describe three phases of development (see also Figure 4.4). First, two compounds were separately laid out, including Structure A which was initially fortified with a glacis fortification similar in construction to the city walls. It is unclear what the function of this early building was. In the following phase, Structure A was joined with the urban compound immediately to its west with a stone pavement leading up to the so-called Audience Hall and the Ashlar Building. The final phase of construction comprised the addition of the Monumental Entranceway, which also included the addition of semi-iconic stele and a monument crafted from stone with Phrygian dedicatory inscriptions (Brixhe and Summers 2007; Draycott and Summers 2008). Taken together, this complex is exemplary as a material extension of state power in an appropriate context, presumably also the residence of the ruler over the city and state.

In association with the stone monuments and architectural embellishments of the Palace Complex monumental entranceway were many objects of metal (151 total objects, nearly half of the total excavated from the site), predominantly iron, that appear to function primarily as architectural support and decoration. Several meters of well-preserved iron bands together with

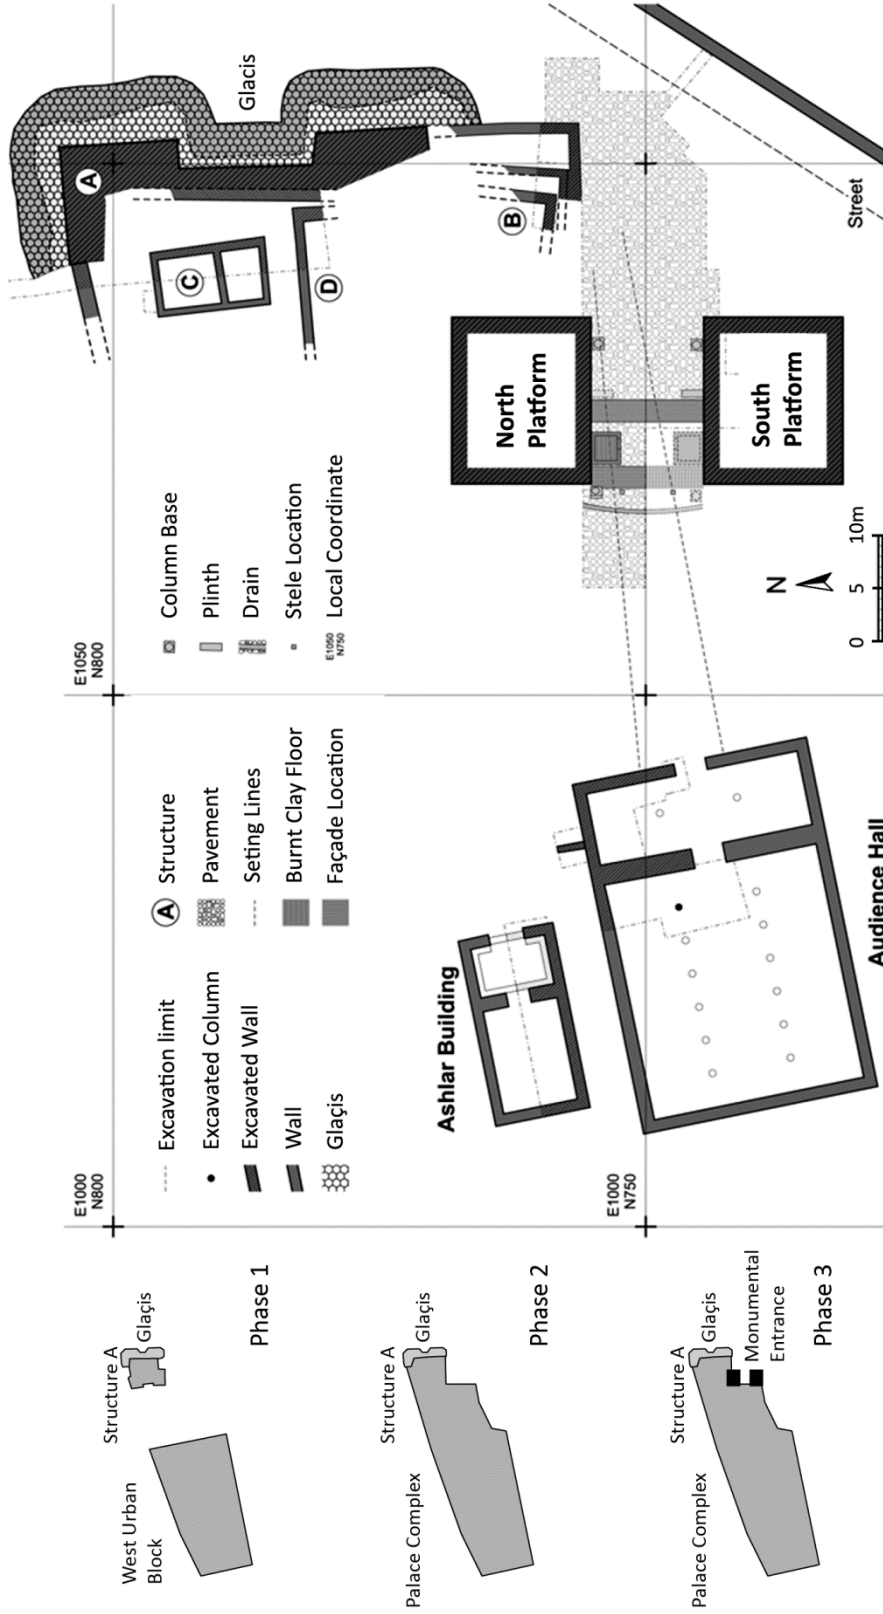


Figure 4.5: Schematic of developmental phases of the Palace Complex and its plan according to clearance and excavations from 1999 to 2005 (adapted from Summers and Summers 2008: figs. 22, 27).

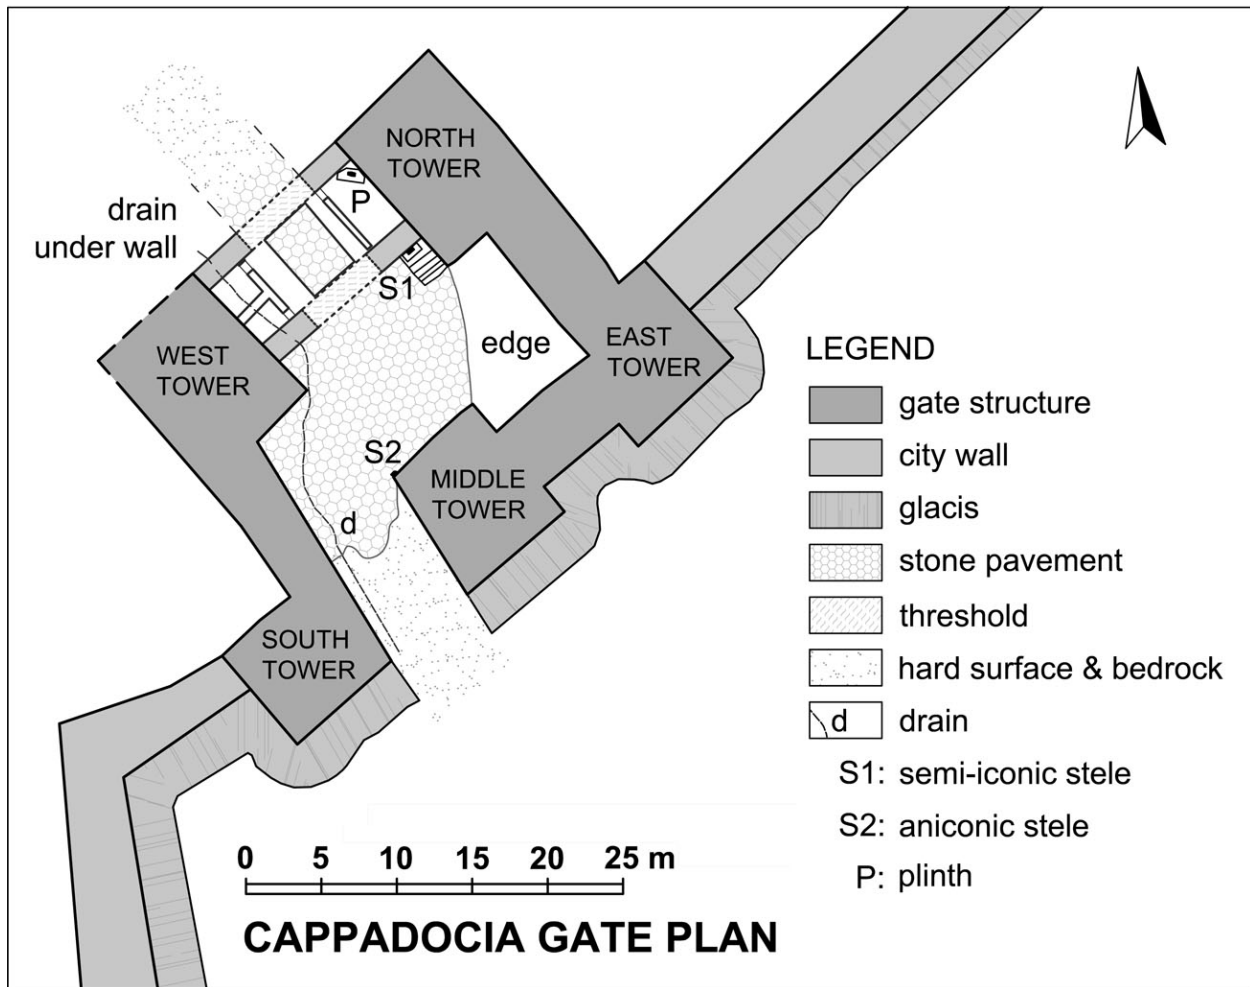


Figure 4.6: Cappadocia Gate Plan (Kerkenes Dağ Project archives).

15+ cm round-headed iron spikes likely held together large wooden doors situated between the north and south platform. Objects of different copper alloys, lead, silver and gold were also found lying on the pavement surface or in collapsed debris. Among the copper and copper alloy objects, samples include a single sample of a nail from the Ashlar Building, two pins from Structure D, and 26 diverse objects consisting mostly of decorative sheet metal, nails, and wire fragments from the Monumental Entranceway. Several of the smaller fragile objects were also discovered in between pavement stones. The most striking examples of copper metallurgy come from the sheet metal examples, including two finely hammered and crafted twin facing ibex

(02TR01U02met01 and 02TR01U02met02), which probably decorated the wooden planks of the entrance doorway. These objects further demonstrate the use of tin washing to create a silver-colored coating, which has direct technological parallels from Urartian shields discovered at Ayanis (Ingo, et al. 2010).

4.3.2 Cappadocian Gate

This gateway complex is located in the southeastern side of the city walls and is one of five such monumental entranceways into the city on the eastern side (Figure 4.6). The structure is composed of five towers, three in the front and two in the back, which flank an offset central passageway leading into the city (Summers in press). Clearance and excavations beginning in 1999, with particular intensive focus in 2010-2011, revealed that this structure probably had multiple functions in addition to defense and the control of transportation. Elements of cult evinced by presence of an aniconic stele and stepped monument inside of the passage chamber suggest that the gate complex was invested with visual aspects of ideology. This similar pattern is also present at the Monumental Entrance of the Palace complex, where semi-iconic crenulations flanked at least one side of the passageway. Collapsed walls and intense burning demonstrate that the structure was intentionally destroyed in a single event. Two individuals were found crushed below the collapsed and burnt debris (Summers n.d.).

A range of metal objects were discovered in these contexts, including as in the Palace a great deal of architectural iron in the form of finely forged bands and spikes which held the wooden planks of the doorway together. A single example of a delicately crafted gold and electrum attachment piece with granulation was discovered below the collapsed rubble suggesting that it was lost shortly before the structure was destroyed. Copper alloys in the form

of finely hammered sheet metal, pins, nails, needles, and lobate arrowheads were also discovered in these contexts. A total of 32 these copper alloy objects were sampled for analysis.

4.3.3 Urban Quarters and Streets

Select excavations elsewhere in the city, including those of Schmidt in 1927, have shed some further light on the organization of the city and the various activities that took place outside of the contexts of the Palace Complex and Cappadocian Gate. This work has primarily sought to simultaneously ground truth the extensive subsurface remote sensing data and to examine select identifiable urban contexts, including aspects of urban organization and household dynamics.

First, excavations led by Branting focused on street deposits across the city. Preserved deposits, mostly preserved alongside the outside of buildings, contained diagnostic compacted microstrata that formed during the use-life of the city. I sampled two objects from TT25, including a fibula and wire fragment, a double headed pin from TT27, and fibula fragment from TT31. Second in 2003, excavations in the lower central city examined so-called megaron structures and adjacent buildings within a single urban compound (Summers et al. 2004). This work primarily confirmed and added to the interpretation of the remote sensing data. While the activities associated with these buildings are unclear, excavations confirmed that the city burning extended into the lower city. No indications of domestic activity were preserved within these structures. Fragments of a small trinket mold (K03.157) suggest that metallurgical activities may have possibly occurred within the compound however no pyrotechnological debris was noted here. Few metal remains were recovered during these excavations aside from a rosette headed tack and a single trilobite arrowhead (03TR06UI2met01), which was sampled for analysis. Later excavations at the nearby large two-roomed structure (referred to as a “Temple”), yielded no

preserved deposits however an adjacent building at the backside of the structure had several intact contexts, indicating that this small building may have been used for storage (unpublished, but see Branting et al. in Summers and Summers 2011: 5-7).

Third, ongoing excavations in the northern residential quarter of the city, which was first sampled by excavation in 1996, have begun to reveal the entire urban compound (Urban Compound 8). Remote sensing data most recently published by Langis-Barsetti (2013) demonstrate that this compound contains a diversity of structure types, including a large two-roomed hall (Summers 2007: 259). This compound experienced significant burning before it was abandoned. In one storage room, excavations recovered the remains of what was probably a piece of intricate furniture decorated with carved ivory. A diverse assemblage of metal objects, including iron, silver, gold, and copper alloys, attest to the breadth of access individuals had at this urban compound. A total of seven objects from these contexts were sampled for analysis, including pin fragments (98TT21U01met02, 96TT15U13met05, and 11TR29U14met02), sheet metal (11TR29U34met02 and 11TR29U34met03), a large piece of forged copper (97TT15U00met01), and a single bilobate arrowhead (11TR29U32met01).

4.4 Conclusion

In this dissertation a sample of over 1000 objects were analyzed from Boğazköy and Kerkenes Dağ, two of the largest regional centers in Central Anatolia. The results of the compositional analyses are presented and discussed in Chapter 5. Artifact samples cut across a wide chronological, contextual, and typological matrix. Despite the complexity of the site, Boğazköy has one of the best empirically and stratigraphically defined settlement history in central Anatolia, including structures and deposits across several diverse social contexts. This

important fact allowed the sampling of objects ranging across these social contexts, from domestic/residential structures and activity areas to those directly associated with the palace and temple. By far the bulk of the samples were taken from Late Bronze Age and Mid to Late Iron Age contexts. This is mostly due to the fact that the majority materials from Boğazköy date to these periods, and materials securely dated to the Early Bronze Age and Middle Bronze Age are exceedingly rare. These data constitute the first well-defined and description of copper metallurgy inferred from finished objects dating to these periods in central Anatolia.

A further set of objects from the site of Kerkenes Dağ were sampled and analyzed. Most of these samples come from contexts within the Palace Complex and Cappadocian Gate, but several others come from domestic contexts in the north of the city. The most striking characteristic of these samples is that they all date within the life of the city ca. late 7th century – 540s BC. The chronological resolution is so fine from this site that these objects effectively comprise a tight range of time within the Late Iron Age.

This allows the effective comparison with Boğazköy in two distinct ways. First, from a cultural-historical point of view, it is now possible to describe any patterns of metal production and consumption from these periods over time. Second, a cross-cultural comparison between sites and contexts allow the testing of hypotheses, first outlined in Chapter 1, regarding the evolution of top tier regional centers and the fundamental relationship between trade and social organization.

CHAPTER 5: COMPOSITIONAL ANALYSIS OF COPPER ALLOYS

5.1 Introduction

In this chapter, the results of bulk chemical analyses of 1141 archaeological metal objects from Boğazköy and Kerkenes Dağ are presented and discussed. These data highlight how these two regional centers strategically accessed a wide variety of copper metal resources and technologies. These patterns reflect socioeconomic processes that effectively characterize how individuals and institutions organized production, exchange, and consumption over time. The bulk of the data, as described in the previous chapter, principally derives from contexts associated with the approximate height of political and economic activity as capitals of archaic states, and by extension, the climax of Bronze Age and Iron Age urbanism in central Anatolia. At Boğazköy further data is included here from earlier and later contexts to develop a chronologically bracketed understanding of metal industries at the site. These data examine how metal technologies developed in the context of expansionist states.

The compositional data were quantified using x-ray fluorescence spectrometry (XRF), including both a bench-top energy dispersive XRF (EDXRF) and an in-field portable XRF analyzer (pXRF). EDXRF analyses were conducted at the Curt-Engelhorn-Zentrum Archäometrie (CEZA) in Mannheim, Germany during the 2012-2013 academic year, and pXRF analyses were conducted on site in the field in Turkey during the summer of 2013. Compositional data from both methods are presented in Appendix B and C, respectively.

Details of the analytical techniques used in this dissertation, including sample preparation, instrumental parameters, accuracy, precision and sensitivity are presented below. I include also a brief discussion on data treatment and presentation, following which the EDXRF and pXRF data are presented and a rationale for the comparability between analytical methods is determined. The descriptive statistics of the compositional data are then discussed in a univariate manner element by element. Subsequently, I examine the relationships between elements and archaeological assemblages through bivariate and multivariate statistical analyses.

5.2 Analytical methods

Samples of archaeological metal were collected in the field from 2008-2013 with the main purpose of bulk compositional analysis. In practice, excavated metal objects are first mechanically cleaned down to the stable corrosion layers by conservators, photographed, and drawn. Compositional analyses are completed later using three non-destructive instrumental methods and these can be ranked according to their invasiveness to the sample (See Table 5.1). Where possible, additional sample material was taken in order to allow observation by optical microscopy. In general, samples consisted of small cuttings (ca. 1-5mm) or drillings of objects. Most objects were inevitably impacted by environmental degradation and were visibly affected by corrosion. Careful effort was taken to abrade mechanically all corrosion from preserved metal in the sample to avoid contamination in the analysis. Subsequent to abrasion, samples were then roughly polished using dry sandpaper grades 600 and 1200.

5.2.1 Analytical parameters and instrumentation

Most samples are first analyzed using a portable x-ray fluorescence analyzer (pXRF). The main benefit of this analyzer is that it is portable so that analysis can be conducted directly in the field or in the museum. This method is often the only possible method to date to conduct compositional analysis, especially fragile and highly valuable museum display objects. While quantitative analysis of copper alloys is theoretically possible, several limitations are important to consider here (see also Heginbotham, Bezur et al. 2010; Liritzis and Zacharias 2011). First, without careful invasive sample preparation, pXRF essentially analyzes the surface of the object, which is often altered by the corrosion of the original cast or forged shape. Selective corrosion of elements like iron and tin may therefore produce misleading deviations from the original metal composition. Other effects which determine the surface chemistry of metal objects, such as inverse segregation of alloy phases, plating/coating, or even conservation treatments, can produce very misleading results derived from surface analysis. To mitigate the effects of these limitations, small minimally perceivable areas of corrosion were removed mechanically where possible prior to analysis. These objects were then immediately retreated and conserved for storage. On an average working day in the field, about 30 to 40 objects could be photographed, prepared, analyzed, and finally conserved for storage.

Select prepared samples were analyzed for composition by EDXRF using methods outlined by Lutz and Pernicka (1996). In general, samples are further prepared to carefully remove all visible corrosion where possible. Often this also resulted in reducing clippings into several smaller pieces to help ensure a more accurate reading of the average composition. This method has a distinct advantage over pXRF in that it analyzes bulk composition and is therefore more reflective of the original composition of the metal. Detection limits and accuracy are

generally much improved using this method; however limitations include invasive sampling and longer analysis times. For select samples scanning electron microscopy equipped with an EDX analyzer was employed in order to determine phase compositions and microstructures.

In addition to the sample macroscopic effects described above, other matrix effects associated with x-ray fluorescence techniques above can include significant instrumental error into the analysis. While many of these effects, including the absorption or enhancement of x-rays into the matrix, can be quickly modeled and corrected in the software quantification procedures, significant instrumental errors may result from irresolvable spectra of overlapping x-ray emissions. This is particularly important for archaeological copper alloys because of a number of important elements which can be potentially hidden from analysis. Typically, sensitivity decreases for some elements where photon emissions of similar energies are not resolvable by the XRF detector. This is particularly true of lead (Pb), because this element has several complex emission spectra that can overlap with a range of other important elements common to archaeological copper. For example, the As $K\alpha$, which overlaps with the Pb $L\alpha$ line, can be totally obscured if the Pb concentration is too high. This can also be true for the zinc $K\alpha$ line which overlap with the Cu $K\beta$ line. Therefore with the presence of relatively elevated concentrations of overlapping elements, the sensitivity will be reduced and the minimum detection limit increases.

The summary statistics for measurements of standard reference materials using both pXRF and EDXRF are presented in Tables 5.2, 5.3, and 5.4. In order to determine the analytical precision and accuracy of both these methods, data which further informs instrumental comparability, several measurements of industrial and in-house standards were analyzed. Nominal values of the standards are compared against an average of several measurements

(accuracy) and their relative standard deviation (precision). The minimal detection limit for each method is also calculated using Equation 5.1 below. This calculation is another measure of precision which determines probabilistically the lowest concentration that is reliably measurable in a given material matrix. Concentrations below this for either of the methods are considered here as semi-quantitative indicators. Results from these analyses demonstrate that the EDXRF methods used in this study are generally superior to the pXRF methods. EDXRF is more sensitive to lower concentrations and more accurate across a wide range of concentrations by an order of magnitude.

Table 5.1: Analytical parameters of instrumentation to measure elemental composition used in this study.

| Method | Purpose | Analytical Parameters |
|---|---|--|
| pXRF Thermo NITON XL3t | In field non-destructive / semi-quantitative compositional analysis of the artifact surface to characterize the type of metal alloy. | General Metal mode, 2 averaged analysis points, 100 s analysis time. |
| EDXRF Thermo QUANTX | Quantitative bulk analysis of elemental composition | See Lutz and Pernicka (1996). |
| SEM-EDS Zeiss EVO MA 25 scanning electron microscope with a Bruker QUANTAX silicon drift EDX detector | Characterization of materials, backscatter electron imaging to examine heterogeneity and composition. Semi-quantitative compositional analysis of solid metal phases and inclusions observed within the sample using spot/area analysis. | Backscatter electron (BSE) imaging: accelerating voltage 30 kV, average dead-time 35-40%, and working distance 6.8 – 7.4 mm (all semi-quantitative measurements taken at 7.0 mm and 1500x magnification). Elemental concentrations are ZAF standardless corrected and normalized to 100 wt%. |

Equation 1: Minimum detection limit (MDL) using the Student t's method.

$$MDL = T(n - 1, 1 - \alpha = 0.99) \times \sqrt{\sum_{i=1}^{1=n} \frac{(X_i - \bar{X})^2}{n - 1}}$$

Table 5.2: Summary of mean values, standard deviation, relative standard deviation (%RSD), and minimum detection limit (MDL) for 13 elements and calculated from one standard reference material CTIF B12 (tin bronze) using pXRF. Results derive from 10 measurements taken intermittently throughout the duration of this study.

| Element | CTIF B12 | | | | |
|----------------|----------|------------------|--------------------|------|------|
| | Nominal | Observed Average | Standard Deviation | %RSD | MDL |
| Cu wt.% | 85.65 | 86 | 0.021 | 0.02 | 0.09 |
| Mn wt.% | 0.235 | 0.24 | 0.004 | 1.87 | 0.02 |
| Fe wt.% | 0.162 | 0.19 | 0.004 | 2.20 | 0.02 |
| Co wt.% | - | - | - | - | - |
| Ni wt.% | 2.63 | 2.66 | 0.009 | 0.33 | 0.04 |
| Zn wt.% | 0.60 | 0.51 | 0.008 | 1.54 | 0.04 |
| As wt.% | 0.111 | 0.05 | 0.004 | 7.62 | 0.02 |
| Ag wt.% | - | - | - | - | - |
| Sn wt.% | 9.57 | 10.3 | 0.02 | 0.17 | 0.08 |
| Sb wt.% | 0.117 | 0.12 | 0.003 | 2.34 | 0.01 |
| Au wt.% | - | - | - | - | - |
| Pb wt.% | 0.201 | 0.26 | 0.004 | 1.41 | 0.02 |
| Bi wt.% | - | - | - | - | - |

Table 5.3: Compositional analysis of known copper alloy nominal standards which occupy a broad compositional range. In general, analytical accuracy noticeably decreases at concentrations less than 0.10 wt. % which is within the error range necessary to determine the major and many minor constituents. Industrial and in-house standards were analyzed at the Curt-Engelhorn-Zentrum Archäometrie

| Standard | | Cu | Sn | As | Pb | Sb | Ni | Co | Fe | Zn | Bi | Ag |
|------------|--------|-------|---------|--------|---------|---------|---------|---------|---------|---------|---------|---------|
| MET1 | pXRF | 73 | 4.23 | 4.48 | 3.39 | 1.97 | 2.65 | 2.90 | 2.29 | 3.52 | - | 1.85 |
| | Std | 73.3 | 3.85 | 4.89 | 3.34 | 1.84 | 2.71 | 2.8 | 2.47 | 3.53 | 0.0001 | 2.08 |
| | %error | 0.8 | 9.8 | 8.4 | 1.4 | 6.8 | 2.3 | 3.6 | 7.4 | 0.4 | | 11.0 |
| MET2 | pXRF | 78 | 6.45 | 2.82 | 4.27 | 3.88 | 0.95 | 0.87 | 0.95 | 1.15 | | 1.01 |
| | Std | 77.1 | 6.61 | 3.00 | 4.32 | 3.9 | 1.00 | 0.74 | 0.85 | 1.05 | 0.0001 | 1.16 |
| | %error | 0.7 | 2.4 | 6.0 | 1.3 | 0.6 | 5.2 | 17.3 | 11.8 | 9.9 | | 13.3 |
| MET3 | pXRF | 96 | 0.47 | 0.33 | 0.54 | 0.44 | 0.47 | 0.50 | 0.45 | 0.51 | | 0.28 |
| | Std | 95.7 | 0.47 | 0.37 | 0.58 | 0.47 | 0.45 | 0.46 | 0.47 | 0.47 | 0.0001 | 0.3 |
| | %error | 0.3 | 0.2 | 11.6 | 7.1 | 6.4 | 3.8 | 9.1 | 4.0 | 8.5 | | 7.0 |
| BAM-376 | pXRF | 100 | 0.04 | 0.01 | 0.04 | | 0.02 | 0.03 | 0.02 | 0.13 | 0.02 | 0.01 |
| | Std | | 0.02473 | 0.0199 | 0.0236 | 0.0202 | 0.0209 | 0.02079 | 0.02346 | 0.02173 | 0.02 | 0.0163 |
| | %error | | 41.5 | 34.7 | 48.3 | | 28.2 | 20.3 | 27.5 | 516.7 | 15.0 | 20.2 |
| ERM-EB-374 | pXRF | 92 | 7.77 | - | - | - | - | - | - | 0.09 | - | - |
| | Std | 92.22 | 7.6 | | 0.00083 | | 0.00327 | | 0.004 | 0.00404 | | 0.00121 |
| | %error | 0.1 | 2.2 | | | | | | | 2004.0 | | |
| BAM-367 | pXRF | 89 | 0.02 | - | 0.04 | - | 9.23 | 0.07 | 1.40 | - | - | 0.01 |
| | Std | 87.88 | 0.0105 | | 0.0298 | | 9.72 | 0.0498 | 1.443 | 0.0715 | | |
| | %error | 1.5 | 109.5 | | 37.6 | | 5.0 | 46.6 | 3.3 | | | |
| BAM-211 | pXRF | 87 | 10.61 | 0.07 | 0.96 | 0.05 | 0.08 | - | 0.07 | 0.66 | - | 0.04 |
| | Std | 87.71 | 10.6 | 0.0213 | 0.74 | 0.033 | 0.122 | | 0.11 | 0.56 | 0.002 | 0.059 |
| | %error | 0.3 | 0.1 | 223.9 | 29.3 | 36.4 | 34.4 | | 32.7 | 17.9 | | 32.2 |
| BAM-375 | pXRF | 58 | 0.17 | 0.08 | 3.63 | - | 0.10 | 0.02 | 0.20 | 37.76 | 0.02 | 0.02 |
| | Std | 58.32 | 0.209 | 0.0231 | 2.9 | 0.0122 | 0.105 | 0.01964 | 0.207 | 38.02 | 0.00686 | 0.0166 |
| | %error | 0.6 | 16.7 | 237.7 | 25.1 | | 3.1 | 6.9 | 2.9 | 0.7 | 249.9 | 3.6 |
| BAM-227 | pXRF | 84 | 6.09 | 0.17 | 5.23 | 0.13 | 0.26 | - | 0.13 | 3.47 | 0.02 | 0.02 |
| | Std | 85.57 | 6.01 | 0.081 | 4.12 | 0.16 | 0.284 | | 0.129 | 3.46 | 0.0088 | |
| | %error | 1.3 | 1.4 | 112.3 | 26.9 | 20.6 | 10.2 | | 0.8 | 0.2 | 93.2 | |
| BAM-228 | pXRF | 85 | 10.02 | - | 1.49 | 0.09 | 0.09 | - | 0.01 | 3.36 | 0.01 | - |
| | Std | 85.34 | 9.76 | 0.024 | 1.24 | 0.078 | 0.109 | | 0.036 | 3.32 | 0.0086 | |
| | %error | 0.5 | 2.6 | 100.0 | 20.1 | 14.1 | 18.3 | | 72.2 | 1.3 | 27.9 | |
| NBS-398 | pXRF | 100 | - | - | - | - | - | - | - | 0.04 | - | - |
| | Std | | 0.00048 | 0.0025 | 0.00099 | 0.00075 | 0.0007 | 0.00028 | 0.00114 | 0.0024 | 0.0002 | 0.00201 |
| | %error | | | | | | | | | 1525.0 | | |
| NBS-399 | pXRF | 100 | - | - | - | - | 0.05 | - | - | 0.09 | - | 0.014 |
| | Std | | 0.009 | 0.0047 | 0.0114 | 0.003 | 0.0506 | 0.00005 | 0.002 | | 0.00105 | 0.0117 |
| | %error | | | | | | 11.1 | | | | | 19.658 |
| NBS-400 | pXRF | 100 | - | 0.01 | 0.03 | - | 0.07 | - | - | 0.05 | - | 0.03 |
| | Std | | 0.02 | 0.014 | 0.0128 | 0.0102 | 0.0603 | 0.00006 | 0.0041 | 0.0114 | 0.00245 | 0.0181 |
| | %error | | | 7.1 | 142.2 | | 7.8 | | | 364.9 | | 65.7 |

Table 5.4: Summary of mean values, standard deviation, relative standard deviation (%RSD), and minimum detection limit (MDL) for 15 elements and calculated from two standard reference materials BAM376 (pure copper) and BAM211 (copper tin bronze) using EDXRF. Calculated from 30 measurements taken during each measurement cycle throughout the duration of this study.

| Element | BAM376 | | | | | BAM211 | | | | |
|----------------|----------------|-------------------------|---------------------------|-------------|------------|----------------|-------------------------|---------------------------|-------------|------------|
| | <i>Nominal</i> | <i>Observed Average</i> | <i>Standard Deviation</i> | <i>%RSD</i> | <i>MDL</i> | <i>Nominal</i> | <i>Observed Average</i> | <i>Standard Deviation</i> | <i>%RSD</i> | <i>MDL</i> |
| Cu wt.% | - | 100 | 0.006 | 0.0 | 0.024 | 87.71 | 88 | 0.108 | 0.1 | 0.413 |
| Mn wt.% | 0.02059 | 0.02 | 0.002 | - | 0.006 | 0.0019 | bdl | - | - | - |
| Fe wt.% | 0.02346 | 0.023 | 0.002 | 8.6 | 0.008 | 0.11 | 0.117 | 0.002 | 2.0 | 0.009 |
| Co wt.% | 0.02079 | 0.02 | 0.002 | 8.1 | 0.006 | - | 0.001 | 0.001 | 141.2 | 0.003 |
| Ni wt.% | 0.0209 | 0.027 | 0.003 | 9.7 | 0.010 | 0.122 | 0.133 | 0.003 | 2.1 | 0.010 |
| Zn wt.% | 0.02173 | 0.007 | 0.004 | 57.4 | 0.015 | 0.56 | 0.439 | 0.050 | 11.3 | 0.189 |
| As wt.% | 0.01999 | 0.019 | 0.002 | 11.9 | 0.009 | 0.0213 | 0.009 | 0.003 | 37.2 | 0.012 |
| Se wt.% | 0.021 | 0.024 | 0.001 | 3.2 | 0.003 | 0.00114 | 0.003 | 0.001 | 35.8 | 0.003 |
| Ag wt.% | 0.0163 | 0.015 | 0.000 | 2.7 | 0.002 | 0.059 | 0.049 | 0.001 | 1.9 | 0.004 |
| Sn wt.% | 0.02473 | 0.026 | 0.001 | 4.8 | 0.005 | 10.6 | 10.09 | 0.096 | 0.9 | 0.366 |
| Sb wt.% | 0.0202 | 0.017 | 0.001 | 6.1 | 0.004 | 0.033 | 0.026 | 0.002 | 5.7 | 0.006 |
| Te wt.% | 0.0215 | 0.02 | 0.001 | 5.8 | 0.005 | - | 0.001 | 0.001 | 91.7 | 0.002 |
| Au wt.% | - | 0.002 | 0.001 | 89.2 | 0.005 | - | 0.025 | 0.006 | 21.9 | 0.021 |
| Pb wt.% | 0.0236 | 0.021 | 0.002 | 7.9 | 0.006 | 0.74 | 0.675 | 0.012 | 1.8 | 0.047 |
| Bi wt.% | 0.02 | 0.018 | 0.001 | 7.0 | 0.005 | 0.002 | 0.005 | 0.001 | 26.7 | 0.006 |

5.2.2 Comparing methods and reproducibility

It is useful to compare analyses of similar samples across instruments to determine the degree of comparability between them. For this study, 34 select objects of archaeological metal were analyzed using both methods. Results highlight two important considerations and can be observed in bivariate scatter plots for each element in Figures 5.1-5.3. Linear regressions were computed to test the coherence of the data, where a goodness of fit statistic (R^2) was computed to observe any trends in instrumental accuracy and patterns of over- or under-estimation of the calculated concentration values. First, the previously ascertained differences in sensitivity are reflected in the results, where objects low in concentration of measured elements do not correlate

significantly, however higher concentrations improve in correlation. Second, this is complicated however by the effects of surface chemistry and corrosion. Elevated concentrations of iron (Fe) often indicate the presence of corrosion or other contaminants of the bulk chemistry. Furthermore, tin selectively corrodes out of bronze and is deposited on the object's surface in a complex assortment of corrosion minerals. Even small amounts of corrosion left over after sample preparation could theoretically greatly affect the calculation of elemental concentration which would thus be potentially quite misleading. The selective corrosion of tin and deposition of iron as contaminants is a likely explanation for the large differences in these elements between pXRF and EDXRF methods. Arsenic, lead, nickel, and cobalt all have highly significant agreement between the two methods ($R^2 > 0.95$), while the remaining elements have significant or insignificant correlations. Zinc has a highly insignificant correlation ($R^2 < 0.01$), and this is probably explained by its low concentration relative to higher concentrations of copper. These results demonstrate that extreme caution is necessary when combining results from different methods without considering how quantifications behave across standard reference materials and samples. Nevertheless, these results do demonstrate that qualitative or semi-quantitative comparisons between methods are reproducible and permit the testing of the central hypotheses in this study.

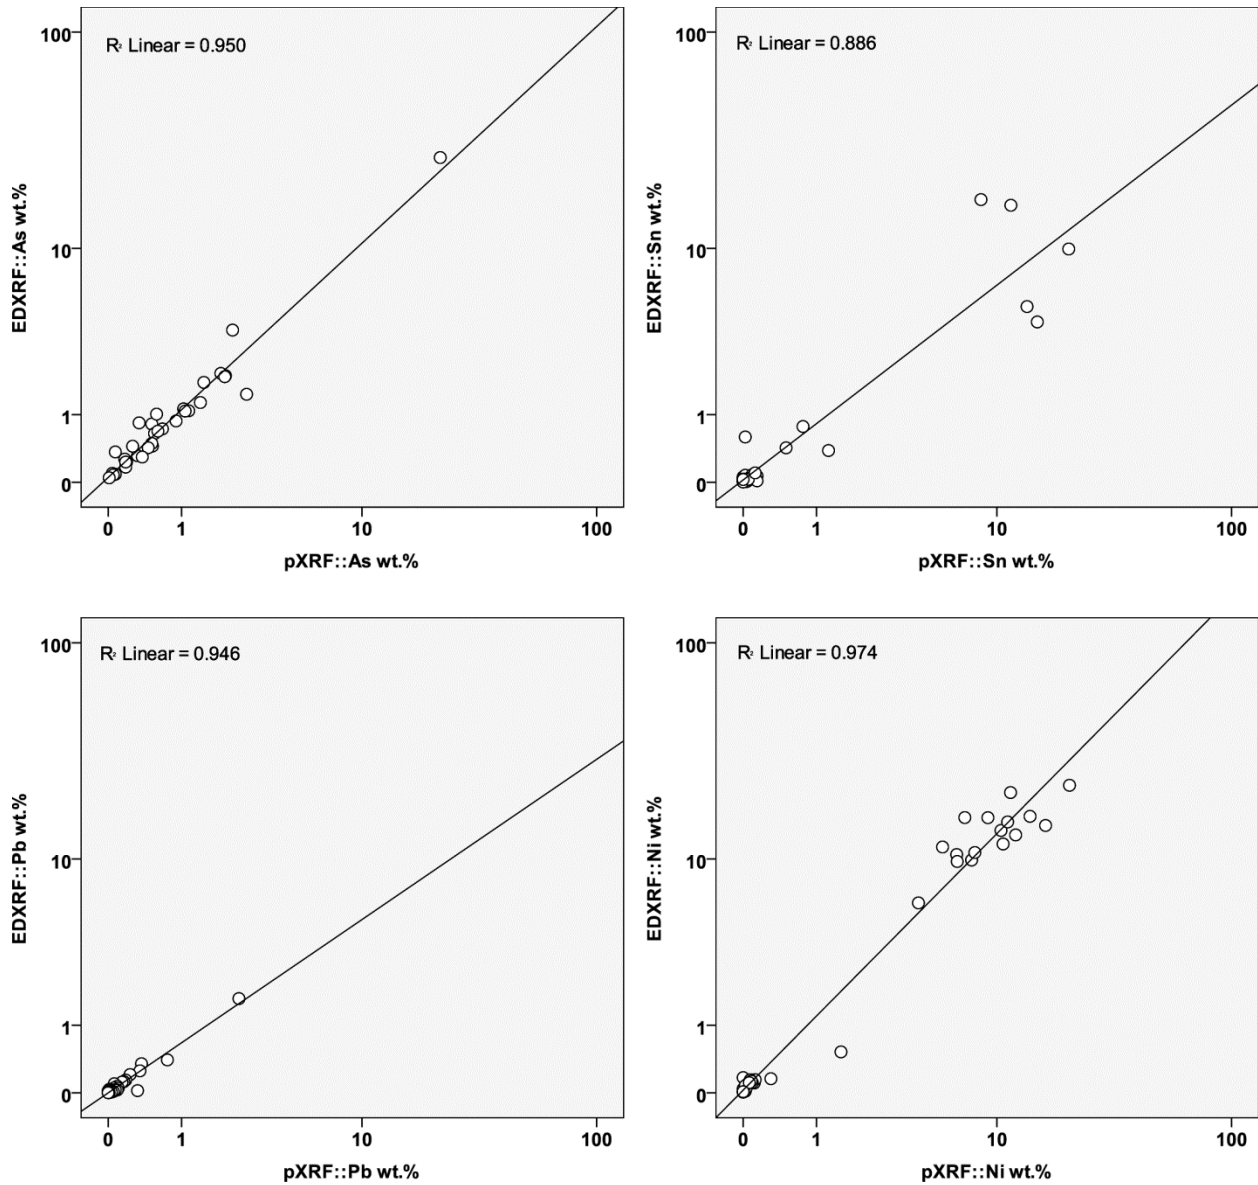


Figure 5.1: Comparison of EDXRF and pXRF methods across elements arsenic (As), tin (Sn), lead (Pb), and nickel (Ni).

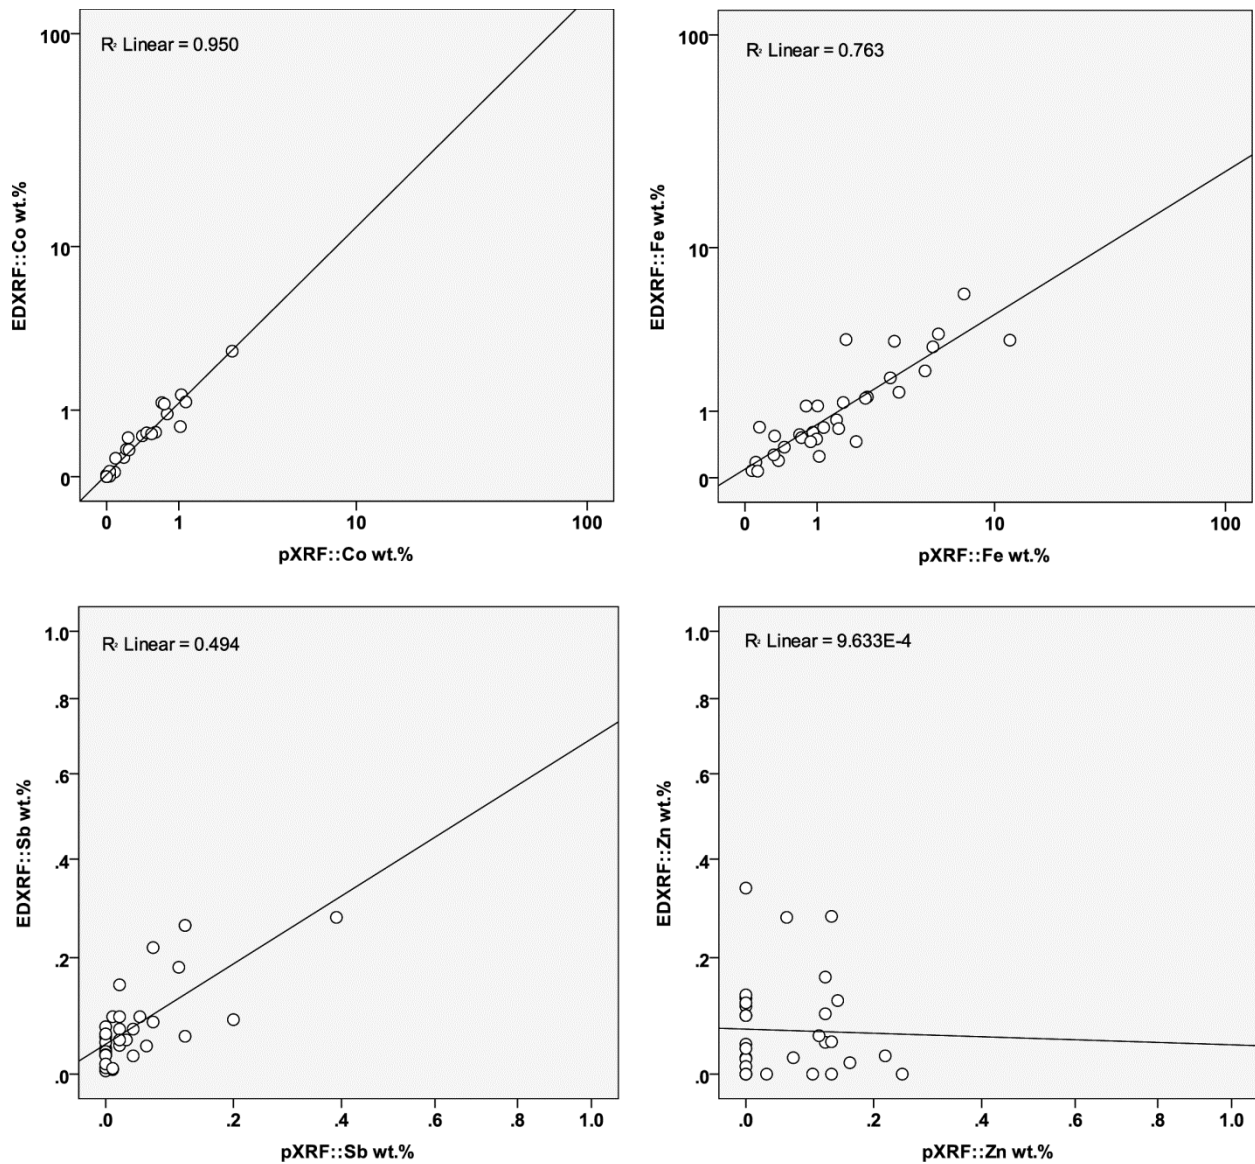


Figure 5.2: Comparison of EDXRF and pXRF methods across elements cobalt (Co), iron (Fe), antimony (Sb), and zinc (Zn).

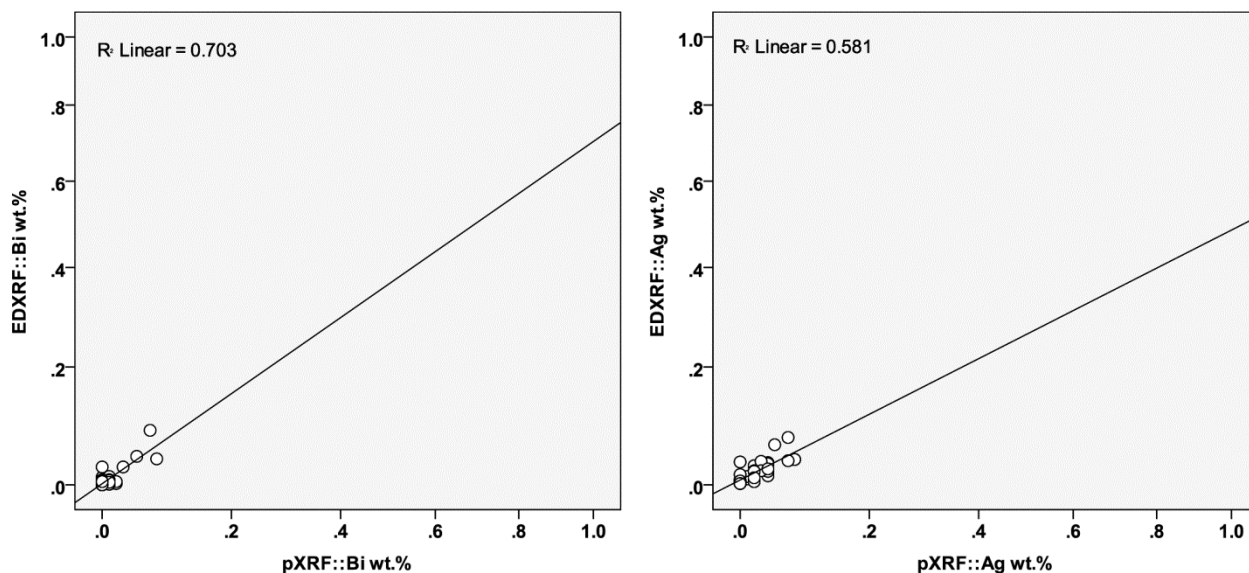


Figure 5.3: Comparison of EDXRF and pXRF methods across elements bismuth (Bi) and silver (Ag).

5.3 Distribution of major and minor elements

The results of the all compositional analyses using pXRF and EDXRF can be found in Appendix B and C. The discussion below employs simple statistical summaries of the elemental concentration data. Aside from copper, all the analyzed major and minor elements are described individually here by giving the mean average, median, absolute range, and the 5th-95th percentile range. Furthermore, the statistical summaries for each period and site are presented in two broad subset categories: a summary for tin bronze (i.e. all objects containing more than 1% tin) and a summary for copper (i.e. all objects containing less than 1% tin). A single sample of silvered copper (Cu-Ag) from Kerkenes Dağ will not be discussed as part of the statistical description. For all elements, concentration distributions are presented graphically as frequency histograms in log scale to aid the interpretation.

These subset groups closely resemble functional groups of copper alloy types, however this analysis does not make an a priori assumption about the intentionality of these alloy types. These types reflect empirically defined groups observed in the total assemblage, and as such they are treated here as quantitative types rather than known culturally or historically determined categories of metal or technology. The cut-off of 1% for most elements follows similar analytical programs, except for zinc which I consider at 5% or more due to the high variability in zinc content of ores and smelting conditions (see also Thornton 2007). Additionally, these subset groups defined here most likely represent intentional mixing during some stage in the production sequence. This is possible to assume because these elements often do not co-occur in common copper ore types at such high concentrations, especially in the case of tin and zinc. These elements often only enter the metal system through the intentional addition of different ore types in a mixed/co-smelting technique, through a cementation process of adding different ore minerals into molten copper, or in the later remelting of different metal types together in a crucible. This issue is discussed further in the discussion section of this chapter.

5.3.1 Arsenic

Arsenic content is an important marker for ore choice, reduction technologies, and alloying traditions; however, it is often impossible to discriminate among these processes because significant concentrations of arsenic can be attained in any and each of these principle steps or decisions during the production sequence (Lechtman 1991, 1996; Lechtman and Klein 1999). For this reason there is considerable debate regarding the functionality of arsenic in archaeological metal (Thornton 2010), which is further kindled by the lack of strong empirical

evidence left in the archaeological record of arsenical copper production (Rehren, et al. 2012; Thornton, et al. 2009).

A summary of the EDXRF and pXRF arsenic measurements from this study are given in Table 5.5 and histograms in Figure 5.4. There is significant variation between assemblages with the commonly observed drop-off of its concentration over time. At Boğazköy during the EBA average arsenic content is ca. 1.8% with a high deviation from the mean given even the smaller sample size. Arsenic content ranges between 0.04 – 3.98% demonstrating that copper production incorporating arsenical ores varied during this time period, likely also reflecting reuse. This likely reflects the intentional alloying of copper with arsenic to improve the performance characteristics of pure copper. The equivalent pattern is observed for the MBA and LBA assemblages with a noted trend for the decrease in arsenic content. During the LBA, several outlier samples with an arsenic content > 5.0%, including pins, needles, and edged-tools, all attest to the presence of an arsenical copper production tradition, but these examples amount to less than one percent of the total analyzed assemblage for the LBA. One remarkable disc-shaped cast pendant (ETD 98/21), with iconographic solar motifs of stylized concentric circles has an arsenic content of 26.9% (Figure 5.9). Compared against the known corpus of copper technologies in all of Anatolia, this object is unique, with the possible technological parallels from late EBA burial goods of cast arsenical copper from Horoztepe (Smith 1973) and other objects of exceptionally high arsenic content from the Caucasus (Meliksetian, et al. 2011). This distinctly silvery alloy is typical of arsenical coppers with high arsenic content, and it is almost impossible that this alloy could have been produced accidentally. Preliminary microscopic investigations reveal that this object was likely cast and cooled rapidly allowing for only limited segregation of arsenic to the cooler surfaces. This observation rules out the possibility that the

object's arsenic content is primarily superficial, the result of arsenic sweating, inverse segregation, or a coating from direct contact with arsenic-enriched hot vapor. High arsenical copper is also shown by the well-known EBA cast bronze bull from Horoztepe mentioned above, however in this case superficially-enriched arsenic appears to be the result of inverse segregation rather than vapor coating (see Smith 1973 for a discussion of the microstructure). More likely is the addition of arsenical minerals to a smelt or molten copper to produce high arsenical copper. Minerals such as the brightly colored arsenic sulphides realgar (As_4S_4) and orpiment (As_4S_3), which are known in north-central Anatolia (Özbal, et al. 2008), could have been directly added to molten copper, allowing the reduction and diffusion of arsenic.

Table 5.5: Arsenic (As) content of copper alloys at Boğazköy and Kerkenes Dağ.

| Arsenic % | Copper | | | Tin Bronze | | |
|------------------------|--------|--------|---------------|------------|--------|---------------|
| | Mean | Median | Range | Mean | Median | Range |
| Boğazköy (EBA) | 1.87 | 1.32 | < 0.04 - 3.98 | | | |
| Boğazköy (MBA) | 1.18 | 1.06 | < 0.10 - 3.17 | | | |
| Boğazköy (LBA) | 1.36 | 1.02 | < 0.11 - 3.81 | 0.98 | 0.79 | < 0.15 - 2.50 |
| Boğazköy (EIA) | 0.81 | 0.54 | < 0.12 - 1.74 | 0.65 | 0.58 | < 0.24 - 1.26 |
| Boğazköy (MIA/LIA) | 0.7 | 0.58 | < 0.04 - 1.53 | 0.36 | 0.28 | < 0.01 - 1.04 |
| Kerkenes Dağ (MIA/LIA) | 0.06 | | | 0.18 | 0.11 | < 0.01 - 0.68 |

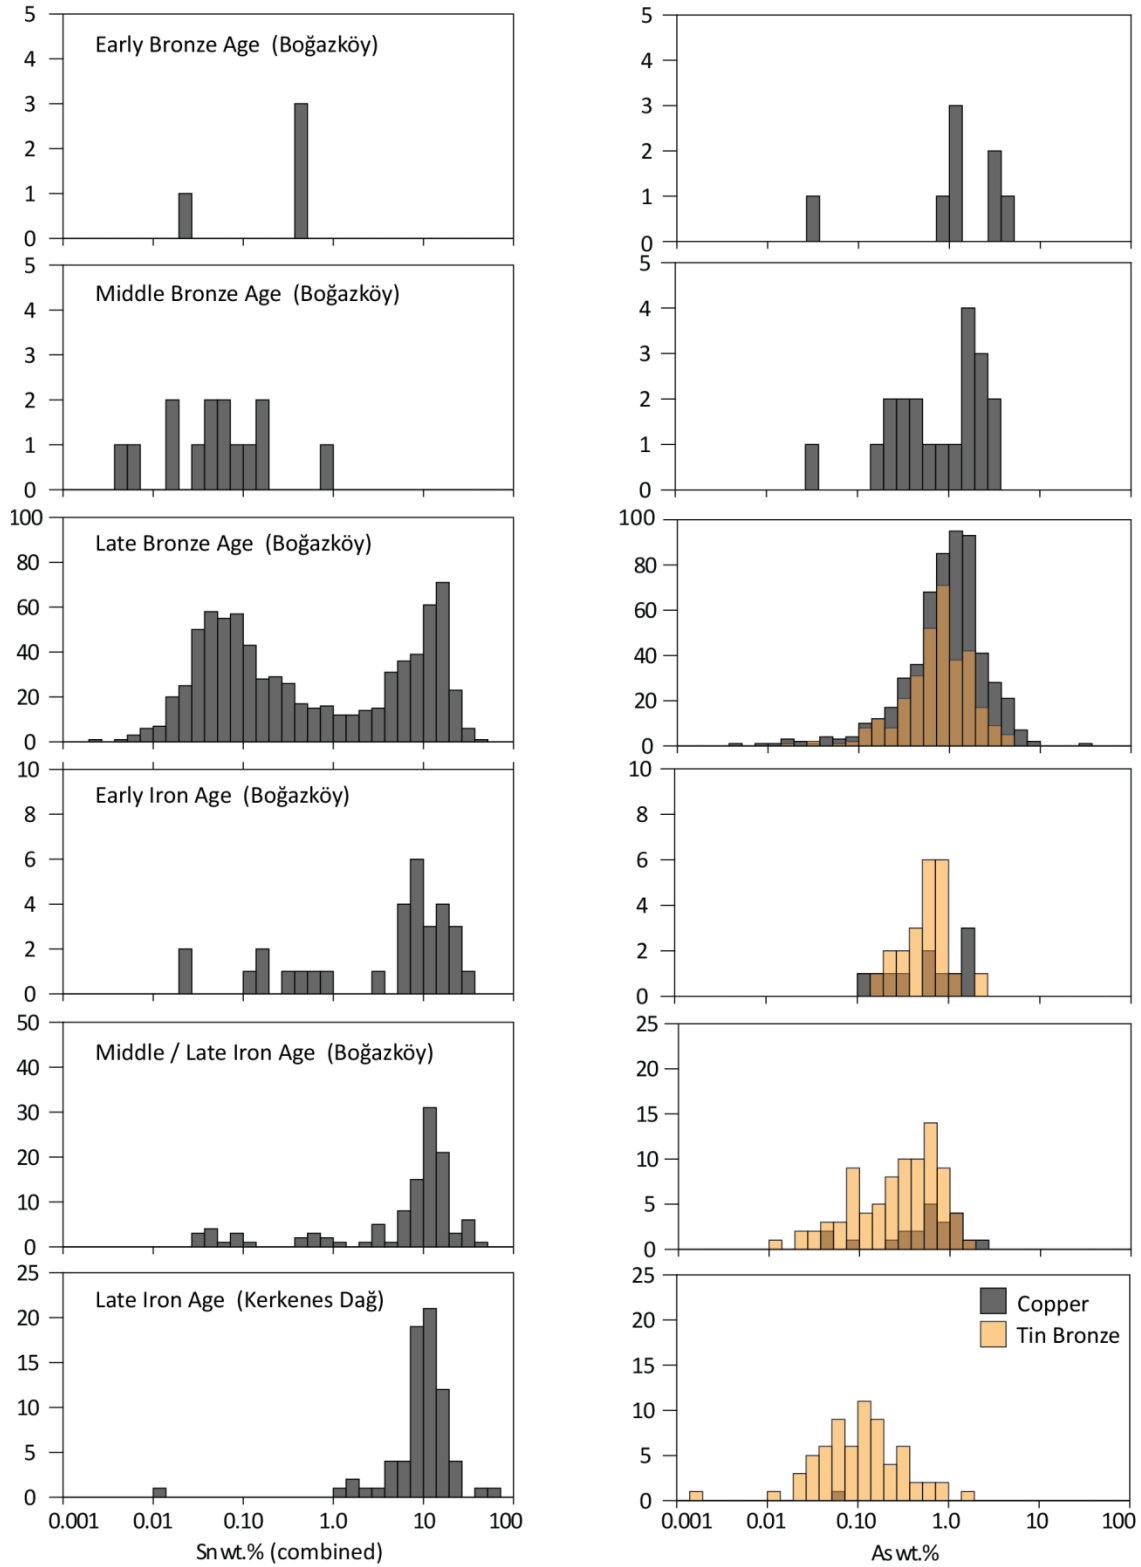


Figure 5.4: Diachronic frequency histograms of tin (Sn) and arsenic (As) from Boğazköy and Kerkenes Dağ. Note that distribution of tin is not differentiated between copper and tin bronze.



Figure 5.5: Cast pendant (ETD 98/21) from Boğazköy. This broken pendant is produced with an exceptionally high arsenic content (26.9% As) and low traces of other elements. This alloy is distinctly silvery in color.

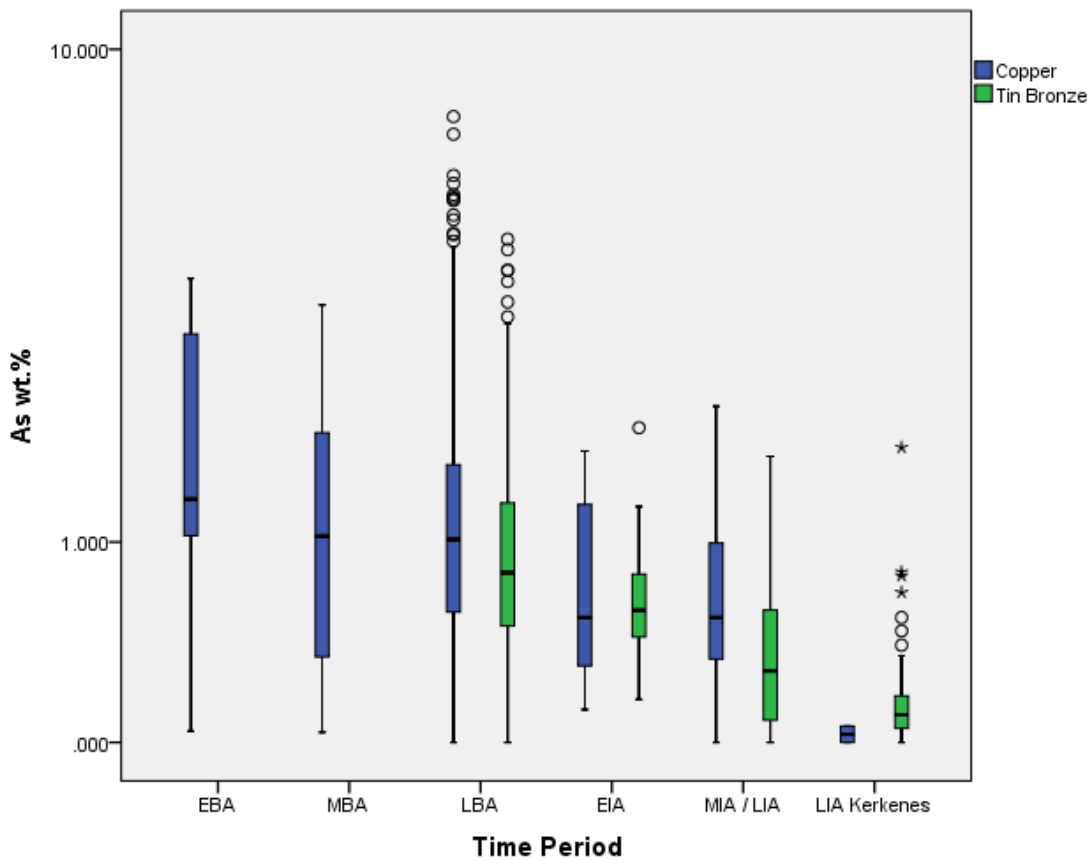


Figure 5.6: Boxplot of arsenic (As) content through time for all objects from the EBA to the LIA at Boğazköy and Kerkenes Dağ. Bars and whiskers show quartile ranges, circles and asterisks symbolize outliers.

There is also a small difference in the average arsenic content between copper and tin bronze, where tin bronzes typically have less arsenic than copper unalloyed with tin. Figure 5.10 demonstrates the marginal deficiency of arsenic among the tin bronzes through time at Boğazköy. During the LBA and the EIA, the presence of ternary Cu-As-Sn alloys is likely explained by recycling practices (Lehner 2014b). This is consistent with the possibility that these alloy types, in aggregate, were treated differentially, which demonstrates an awareness of the effects of arsenic in copper, even in low concentrations around 1.0% As. The difference in arsenic content between copper and tin bronze becomes greater during the Middle Iron Age, where copper alloyed with tin generally has less arsenic, and those alloys with high zinc (>5.0%) are remarkably deficient in arsenic.

During the Iron Age, arsenic content generally falls into a range 0.1-1.6%, with an average and median within the range of 0.5-0.8%. This pattern contrasts with previous Bronze Age production strategies, which is likely explained by increased efficiencies in copper smelting and a decline in the use of common arsenical minerals like arsenopyrite (FeAsS), arsenic sulphides realgar (As_4S_4) and orpiment (As_2S_3), and even more rare minerals like enargite (Cu_3AsS_4), all of which are known to occur in polymetallic copper sulphide deposits across Anatolia. Analyses of copper from 7th-6th c. BC contexts at Kerkenes Dağ demonstrate an even further constrained presence of arsenic, with an average content around 0.1-0.2%. Few analyses of archaeological copper from Anatolia dating to this time period have been analyzed to date, so a comparative understanding of parallel industries is not possible at this time. Analyses of Urartian and Late Assyrian metalwork, however, indicate a broadly similar technology in terms of low arsenic content (Curtis 2013; Hughes, et al. 1981).

5.3.2 Tin

Table 5.6: Tin (Sn) content of copper alloys at Boğazköy and Kerkenes Dağ.

| Tin % | Copper | | | Tin Bronze | | |
|------------------------|--------|--------|---------------|------------|--------|-------------|
| | Mean | Median | Range | Mean | Median | Range |
| Boğazköy (EBA) | 0.16 | 0.01 | < 0.01 - 0.44 | | | |
| Boğazköy (MBA) | 0.08 | 0.03 | < 0.01 - 0.50 | | | |
| Boğazköy (LBA) | 0.11 | 0.05 | < 0.01 - 0.51 | 10.5 | 9.9 | 1.21 - 22.3 |
| Boğazköy (EIA) | 0.24 | 0.16 | < 0.01 - 0.96 | 12.8 | 9.9 | 5.69 - 26.5 |
| Boğazköy (MIA/LIA) | 0.25 | 0.07 | < 0.01 - 0.77 | 12.9 | 11.6 | 3.07 - 28.8 |
| Kerkenes Dağ (MIA/LIA) | 0.01 | 0.01 | < 0.01 - 0.01 | 12.3 | 10.4 | 1.94 - 23.9 |

Scholars have recognized for several decades that copper with significant levels of tin, much higher than would have been present in locally-produced Anatolian copper, was present in the region since at least the early third millennium BC (see Chapter 2). In fact, because tin and copper never cooccur in any major copper deposits of Anatolia, we can reasonably assume that copper-tin (Cu-Sn) alloys were produced by the intentional addition of tin to copper to create tin bronze. This provides for an important marker of long-distance exchange and intentionality among technological choices, however the precise economic structures and technological traditions associated with early bronze production are hotly debated because scholars still do not fully understand the origin of tin as a material nor the technological steps by which it was alloyed with copper (Pare 2000; Radivojević and Rehren 2015; Radivojević, et al. 2013).

Tin concentrations measured from all assemblages are summarized in Table 5.6 and illustrated in Figure 5.4. No tin bronzes were observed for the earliest time periods represented at Boğazköy, with tin content remaining unchanged and ranging from < 0.01-0.44% during the EBA and <0.01-0.50% during the MBA. These results contrast strongly with previous work done regarding the Early and Middle Bronze Ages. Until now and for the lack of better data, we

assumed that the spread of tin consumption was highly regular among polities across Anatolia. The data from this study, however, points towards a highly irregular consumption pattern of tin across the region, demonstrating how the tin trade did not pervade into all regions, or it is at least not well represented empirically in the contexts at Boğazköy. The lack of tin bronze (the definition of tin bronze in this study copper with more than 1% tin) during these formative periods suggests that tin consumption and its trade did not enter into this small polity until the transformation of the site into the administrative and ritual center of the Hittite Empire during the beginning of the LBA.

During the LBA, the median and mean tin content are both within the well-known 1:10 tin-copper ratio observed across the Near East during the third and second millennia BC. Tin ranges from 1.21-22.3% which demonstrates that tin content was not always selected for a 1:10 alloy. Low tin objects, especially those within 1.0-5.0% range, is largely consistent with the recycling of different imported copper alloys, involving the mixing of tin-bronze objects with local copper. In total, 326 of the 889 LBA objects analyzed in this study contain more than 1% tin, and are thus classified as tin bronzes. This represents about 37% of the entire assemblage, where roughly 33% of the assemblage is arsenical copper and 24% are of pure copper.

The replacement of arsenical copper and pure copper can also be observed in terms of the ratio of tin bronze alloys to other categories of copper alloys. During the EIA there is a noticeable increase in the use of tin to alloy with copper, when bronze accounts for roughly 67% of the assemblage (22 of 33 objects). In general, tin displays a well-known bimodal distribution in the assemblage. This reflects intentionality in alloying. A noticeable mode occurs around 0.4 wt. %, which is a rather enriched presence of tin suggesting that traces of tin entered the metal in a workshop where tin was processed periodically. A second mode exists around the well

documented 1:10 ratio. The 1:10 ratio in producing intentional tin bronzes exists cross-culturally, however variations in the concentration of tin demonstrates that this ratio was more of a rule of thumb for a range of concentrations. Among tin bronzes there is a large range from 5.7-26.5% tin, and while this range is likely exaggerated due to surface effects in the analysis, this large range still attests to a significant deviation from the mean ratio of 1:10. At the lower end of the second mode, around 1.0-4.0%, there is little change in the working properties of the alloy (including color, hardness, tensile strength, etc.), which suggests that alloys in this range are produced by mixing metals through a process of recycling.

Together with a large assemblage of production debris, two samples of very well preserved bronze casting waste (ETD 97/236 and ETD 97/239) associated with a casting workshop located at Büyükkaya (Seeher 1998): fig. 11) demonstrates the production of tin bronze during the later phase of the EIA. A large concentration of iron (1-2.5 wt.%) was trapped in the copper metal, most likely in oxide form, which suggests that either the casting debris comes from a fairly impure copper or iron was enriched on the surface as corrosion within intragranular cracks of the metal. Both samples were fairly enriched in tin with concentrations over 15% and up to 19.2% however they vary in the amount of lead and silver. This suggests that several episodes of remelting and casting are represented in the assemblage. A relatively high concentration of silver 1.37% found in sample ETD 97/236 suggests further that this metal was derived from the remelting of scavenged metal that were plated in silver – a practice well known to earlier periods in Anatolia and several examples exist in Boğazköy.

During the Middle and Late Iron Age occupation at Boğazköy, represented by 117 objects predominantly from occupational contexts at Büyükkaya, Kesikkaya, and the Sarıkaya Valley, the ratio of tin bronze increases relative to copper and arsenical copper. Among the

MIA/LIA assemblages at Boğazköy, 79% are classified as tin bronze, accounting for more than twice the ratio of tin bronze during the Late Bronze Age. At Kerkenes Dağ, from 74 copper alloy objects nearly all are alloyed with tin, with roughly 89% of the assemblage total comprising tin bronze and 8% of the assemblage comprising tinned low zinc brasses (Cu-Sn-Zn). Only one object from Kerkenes Dağ is classified as pure copper – a small dome-headed tack from the Palace Complex (05TR21U09met03).

5.3.3 Lead

Lead may enter copper alloys through either its intentional addition or unintentionally through the smelting of copper ores together with lead minerals which are commonly present with polymetallic ores in Anatolia. Furthermore, the reducibility of lead is quite high relative to copper, in addition to its lower melting temperature, permits the entrapment of lead metal into smelted copper up to several percent before one might remove visible lead minerals. The advantages of lead in a copper alloy would likely have been noticed by smiths for its diagnostic properties in lowering the melting temperature of the alloy, improving the castability, and ductility, among a range of other performance characteristics. These advantages led many early smiths to intentionally add lead metal into alloys, especially when casting objects into complex molds. Because these two trajectories explain the presence of lead, and are not necessarily mutually exclusive, it is often impossible to determine convincingly which trajectory was in operation. Exceptions include when excessive amounts of lead are measured, often in the range of greater than 8-10% lead.

The lead (Pb) concentrations observed in objects analyzed for this study are summarized in Table 5.7 and Figure 5.5. Median lead concentrations are between 0.11-0.17% for the Early and Middle Bronze Age with little variation between the two periods. During the Late Bronze Age, the median value for lead remains in the 0.12-0.19 range across alloy groups, however a much higher variation in lead concentration is observable across the assemblage. 19 copper alloy objects from the LBA assemblages have more than 2.0% lead, with one object observed with a 22% lead concentration. This object is a small cast figurine of a horned bull with a bottom socket (Bo 89/41) which was discovered in the northwestern section of the Südburg. This concentration almost certainly is derived from the intentional addition of lead into the low tin bronze alloy.

A similar pattern is observed during the Iron Age, where a small proportion of tin bronzes have appreciable concentrations of lead. During the Early Iron Age at Boğazköy, only two objects have greater than 2.0% lead, including a single cast stemmed and spurred arrowhead of distinct design (Bo 97/25) with around 26% lead. Objects dating to later phases of the Iron Age at Boğazköy demonstrate a great use of leaded tin bronzes. Around 15% of the total assemblage appears to be leaded, including mostly, although not exclusively, cast objects like bilobate/trilobate arrowheads and fibulae. Interestingly, not all arrowheads and fibulae are leaded tin bronzes, which demonstrates wide variation in alloy choice across broad categories of common metal object types. At Kerkenes Dağ, leaded tin bronzes are also common among cast objects like fibulae and arrowheads, providing excellent primary evidence that leading tin bronzes was a commonly practiced technology and widespread in central Anatolia during the Iron Age.

Table 5.7: Lead (Pb) content of copper alloys at Boğazköy and Kerkenes Dağ.

| Lead % | Copper | | | Tin Bronze | | |
|------------------------|--------|--------|---------------|------------|--------|---------------|
| | Mean | Median | Range | Mean | Median | Range |
| Boğazköy (EBA) | 0.34 | 0.17 | < 0.01 - 1.50 | | | |
| Boğazköy (MBA) | 0.21 | 0.11 | < 0.01 - 0.76 | | | |
| Boğazköy (LBA) | 0.30 | 0.12 | < 0.01 - 1.29 | 0.44 | 0.19 | < 0.01 - 1.29 |
| Boğazköy (EIA) | 0.18 | 0.18 | < 0.02 - 0.47 | 1.71 | 0.22 | < 0.05 - 6.14 |
| Boğazköy (MIA/LIA) | 0.34 | 0.09 | < 0.02 - 1.13 | 1.38 | 0.36 | < 0.01 - 5.48 |
| Kerkenes Dağ (MIA/LIA) | 0.07 | 0.07 | < 0.07 - 0.07 | 1.48 | 0.26 | < 0.02 - 9.07 |

5.3.4 Iron

Iron content in the objects measured in this study can be relatively high, where concentrations can reach in excess of 4.0% iron in some objects. These high values, which in one sample from Kerkenes Dağ reaches as high as 19.3% iron (11TR24U21met02), are likely the result of iron-rich contamination at the surface and in intra-granular corrosion. However results in the 1.0-4.0% range are entirely possible, indicative of a smelting technology operating at reasonably high temperatures and increased reducing environments (Cooke and Aschenbrenner 1975: 264; Craddock and Meeks 1987). Iron content can also indicate proximity to the original smelt in the production chain, where each remelting event could lead to decreases in iron which would oxidize rapidly. Therefore, it becomes difficult to determine with bulk analyses like XRF whether elevated concentrations of iron are the result of contamination, bimetallic microstructure, or small amounts of iron alloyed with copper. In these cases, often the only method to determine the actual concentration of iron in copper is with EPMA analysis coupled with microscopy.

A large miscibility gap in the iron-copper thermodynamic system prevents the two metals from forming an alloy. At around 835°C a solid phase of 98.1% iron will be in equilibrium with a

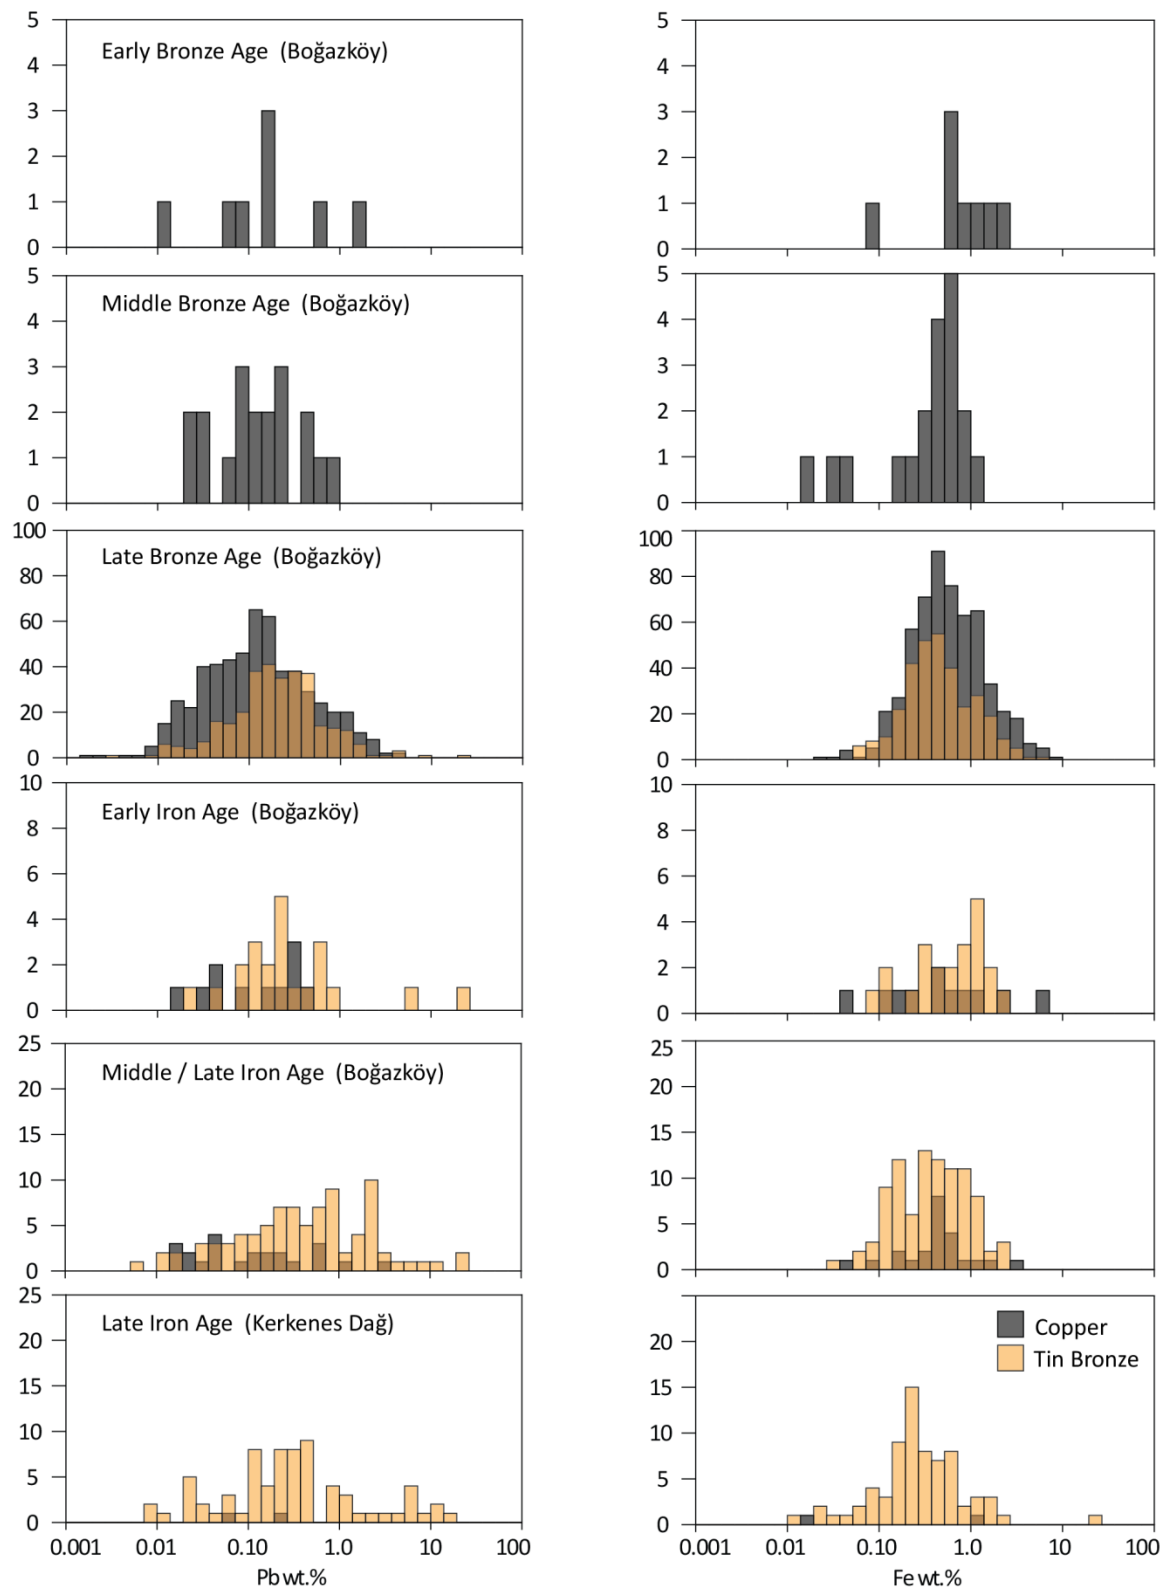


Figure 5.7: Diachronic frequency histograms of lead (Pb) and iron (Fe) from from Boğazköy and Kerkenes Dağ.

liquid phase of copper containing 98.7 copper, whereupon cooling the resultant material would be a highly segregated, brittle bimetallic and not an alloy (Cooke and Aschenbrenner 1975: 259). Further adding to the complexity of this system, experiments have shown that once other alloying agents like arsenic, tin, nickel, and cobalt are added to the iron-copper system, the solubility limit of iron increases. Cooke and Aschenbrenner also note that there should be no major difference in the performance characteristics of a few percent of iron in copper (1975: 266), however further quantitative research of this sort should be undertaken to test their experimental results.

Iron content in the objects analyzed in this study are summarized in Table 5.8 and presented graphically in Figure 5.5. During the earliest periods, iron content ranges from 0.02-2.08% with a single mode around 0.60%. A couple of pins from Büyükkaya (Bo 96/38 and ETD 97/196) have iron concentrations around 2.08 and 1.45% respectively and a single flat knife from the Lower City (Bo 348/h) with a value of 1.38%, all of which demonstrate the range in which iron content is reflected across a range of finished object types. A single planoconvex ingot from a residential context in the Lower City is remarkably deficient in iron (Bo 11/590, 0.04% iron), suggesting that this ingot may have been refined before arriving to Boğazköy.

During the Late Bronze Age, the larger sample size permits a more refined understanding of the distribution of iron concentration across the assemblage. A single mode exists around 0.60% iron and is well distributed in a range of 0.13-2.76%, with objects as high as 8.39% iron. There is an appreciable difference between copper/arsenical copper and tin bronze in iron content. In aggregate, iron content is lower in tin bronze alloys suggesting that purer copper was chosen to alloy with tin before the production of finished objects, or the alloying process itself drew iron out of the molten copper. That iron content is generally higher among arsenical copper

alloys also suggests that iron minerals were associated with arsenical copper production specifically, an observation that is consistent with iron arsenide production at Early Bronze Age Arisman in Iron (Rehren, et al. 2012). Two locally produced pure planoconvex copper ingots from Late Bronze Age Boğazköy (Bo 83/819 and Boehmer 1972: Nr. 190) attest to some of these patterns. These demonstrate a significant range in iron content, ranging from 3.2 to 0.07% iron, yet remarkably deficient in arsenic (0.05 to 0.09% As respectively).

The remarkable presence of cupronickel at Boğazköy, defined as alloys with greater than 1% Ni, also demonstrate significant quantities of iron. This is likely explained by the increased miscibility of iron in nickel and cobalt than with copper alone. This interesting observation, which has only been observed previously in a few samples from Kaman Kalehöyük (Hirao and Enomoto 1997), suggests that iron minerals played a significant role in the reduction of nickel rich copper ores or mixed ore smelts.

During the Iron Age, nascent concentrations of iron appear to increase briefly during the Early Iron Age and then drop again during subsequent periods. A single lamellar disc headed pin (Bo 97/35) from Büyükkaya has a concentration of 5.6% iron but also significant concentrations of arsenic (1.1%) and nickel (2.6%). Tin bronze casting waste (ETD 97/239 and ETD 97/236) is also enriched in iron (2.5% and 1.05%, respectively), which demonstrates the accidental presence of iron in the production of cast tin bronze objects. In aggregate the average iron concentration decreases during the Middle and Late Iron Ages with a mode value at 0.48%, however several objects have concentrations between 2-3.0% iron. At Kerkenes Dağ, the average iron content is even lower, with only two examples above 2.0% iron, including two indeterminate tools (11TR29U34met02 and 11TR24U21met02). The modal value for this assemblage is around 0.25%.

Table 5.8: Iron (Fe) content of copper alloys at Boğazköy and Kerkenes Dağ.

| Iron % | Copper | | | Tin Bronze | | |
|------------------------|--------|--------|---------------|------------|--------|---------------|
| | Mean | Median | Range | Mean | Median | Range |
| Boğazköy (EBA) | 0.91 | 0.68 | < 0.09 - 2.08 | | | |
| Boğazköy (MBA) | 0.49 | 0.41 | < 0.02 - 1.15 | | | |
| Boğazköy (LBA) | 0.85 | 0.53 | < 0.13 - 2.76 | 0.65 | 0.43 | < 0.11 - 1.86 |
| Boğazköy (EIA) | 1.06 | 0.46 | < 0.04 - 5.63 | 0.81 | 0.76 | < 0.10 - 1.57 |
| Boğazköy (MIA/LIA) | 0.61 | 0.46 | < 0.09 - 1.86 | 0.54 | 0.39 | < 0.09 - 1.56 |
| Kerkenes Dağ (MIA/LIA) | 0.02 | | | 0.63 | 0.24 | < 0.03 - 1.24 |

5.3.5 Nickel and Cobalt

Nickel and cobalt, together with iron, often co-occur among ore deposits in Anatolia, and because of their similar physical properties they often behave similarly (Davis 2000). For this reason, very significant correlations between nickel and cobalt are often observed among archaeological copper alloys, especially when concentrations exceed 1000 ppm in either element. Additionally, nickel and cobalt are excellent indicators of the kinds of ores used in the primary reduction of the copper metal, as has been demonstrated for Bronze Age copper alloys derived from nickel-containing falhores across central Europe (Krause 2003) and nickel-rich copper sulphides in the highlands of the Near East (Hauptmann 2007: 297; Tadmor, et al. 1995) and the Arabian Peninsula (see Weeks 2004: and references therein).

Concentration summaries of nickel are found below in Tables 5.9 and 5.10 respectively, and they are displayed in histograms in Figure 5.6. Nickel ranges from less than the detection limit at <0.01 to 0.04% during the Early Bronze Age, but during the Middle Bronze Age a small mode in the 0.2-0.3% range occurs, indicative in the utilization of a new ore source. This observation also holds for recent analyses of copper alloys at the regional center of EBA and MBA Kültepe-*Kaniš* in central Anatolia (Lehner, et al. 2015). This is consistent with an

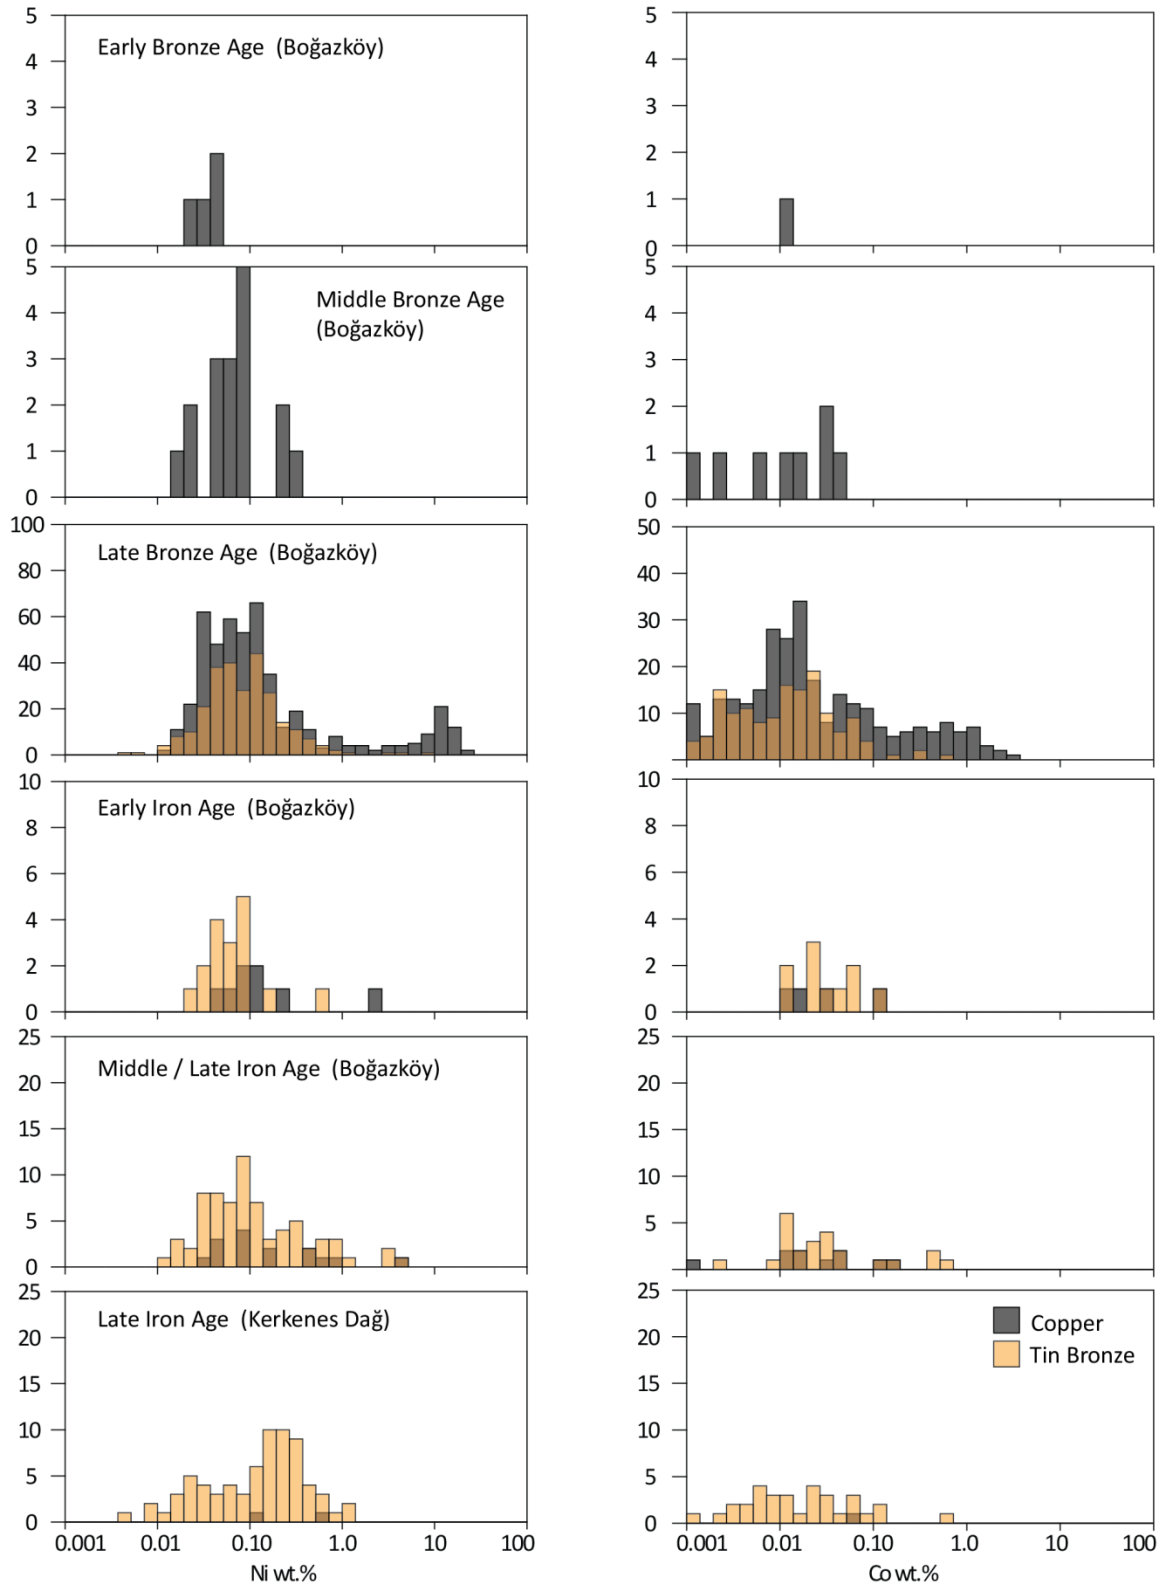


Figure 5.8: Diachronic frequency histograms of nickel (Ni) and cobalt (Co) from from Boğazköy and Kerkenes Dağ.

increase in the geographic scope and use of increasingly diverse ore choices as the polity size increased.

In addition to this distinct modality, the concentration of nickel and cobalt during the Late Bronze Age at Boğazköy demonstrates two more modalities, both of which can be further characterized as kinds of cupronickel alloy. Cupronickel, which will be discussed further below, is an alloy of nickel with copper and has distinct performance characteristics that distinguish it from arsenical copper. For the purposes of this study, low nickel cupronickel has a nickel content of 1.0-10% and high nickel cupronickel has a content of >10% nickel. These categories are well represented in the Late Bronze Age assemblage at Boğazköy.

The second modality, or low nickel cupronickel, is represented by a diverse array of 34 finished objects found without pattern across contexts at Boğazköy. Aside from two examples, low nickel cupronickel is not alloyed with tin, and is more commonly alloyed with arsenic in excess of 1% As, and it displays a reddish color. This alloy type is well known across the Old World (Slotta 2001) and can be observed as early as the Late Chalcolithic from the metal hoard at Nahal Mishmar (Tadmor et al. 1995, see also Hauptman et al. 2004). It is generally considered that nickel entered the copper here through the unintentional smelting of nickel-rich copper sulphide ores which are common to the ophiolitic deposits spanning from Cyprus, the eastern Taurides, and the southern Arabian Peninsula. A stamp seal excavated (Bo 05/13) from the Late Bronze Age workshop context in the Sarıkale Valley at Boğazköy (Herbordt in Seeher 2006c: 176, 186), which is composed of three distinct alloy types together in one composite object, indicates how specialist metal craftworkers had access to multiple copper alloy types and utilized them selectively (Figure 5.12). This modality of cupronickel is also observed, although much

less so, during the Middle and Late Iron Age objects at Boğazköy, which is indicative of either recycling or continued use of nickel-rich ores in the region.

High nickel cupronickel represents the third modality of nickel concentration and is comprised exclusively by 35 objects dating to the Late Bronze Age Anatolian cupronickel dating to the Late Bronze Age was likely produced from a mixed ore smelting process with sulphides like arsenopyrites and chalcopyrites together with minerals rich in nickel and cobalt such as pentlandite or siegenite. Copper-nickel-cobalt sulphide ore sources are rare in Turkey, however exceptions include but are not limited to the Pancarlı copper-nickel source near to Bitlis (Çağatay 1987) and the nickel-iron sulphide deposits near to Divriği, Sivas (Harada, et al. 1971). Because the solubility limits of cobalt and iron increase with nickel, nickel copper alloys tend to exhibit high correlations with these traces. One striking example is a large typical rolled head pin (Bo 09/972) with a composition of 22.4 wt.% Ni, 2.7 wt.% Co, 5.8 wt.% Fe, and the remainder is copper with traces of tin (Figure 5.13). Backscatter analysis using SEM-EDS detected a compositional gradient of these four elements with high nickel phases upwards of 33.7 wt.% Ni, 5.3 wt.% Co, and 11.3 wt.% Fe.

However, two major variables determine the composition of nickel, cobalt, and iron in copper alloys. First, copper nickel sulphide ores will have varying initial compositions of cobalt and iron. Second, these elements have varying oxidation stabilities in relation to temperature, which means that their composition depends partly on the smelting environment. Figure 5.13 compares cobalt and nickel across time periods and sites to demonstrate how these two variables may affect the observed compositions. In these data, there are at least two positive trends, best visible in the Late Bronze Age assemblage. These data are inconclusive by themselves in

determining which of the two above variables are more important. However the data are consistent with at least two major copper nickel sources, two smelting technologies, or both.

Cupronickel at Boğazköy appears to be limited to ornaments composed of finely hammered sheet pendants, pins, and seals. The chain links of the tin bronze tablet with the inscribed treaty between Tudḫaliya IV and Kurunta of Tarhuntassa were also made from cupronickel with around 6.49-7.17 wt.% Ni and impurities of cobalt and iron (Zimmermann, et al. 2010). Low nickel cupronickel (ca. 1.0-8.0 wt.% Ni) is well-known to the Near East, with early examples from the Nahal Mishmar hoard and elsewhere in Syro-Mesopotamia and the upper Euphrates (Hauptmann, et al. 2002b; Hauptmann and Pernicka 2004; Tadmor, et al. 1995). High nickel cupronickel is better known in the archaeological literature as occurring with Bactrian coinage ca. 170 B.C. (Cheng and Schwitter 1957; Howard-White 1963; Schwitter and Cheng 1962) which are suggested to derive from nickel-rich ore bodies in East Asia (Chen, et al. 2009). The Bactrian alloys differ because they are often also alloyed with zinc or lead. High nickel cupronickel may be considered exceptional because nickel changes the color of copper rapidly to a silvery color with increasing concentrations, and it alters the working properties of copper, too. At higher concentrations of nickel, copper-nickel alloys become more ductile however they work-harden quickly upon cold hammering. These characteristics would have surely been noticed by metal smiths.

There is no reason to suggest that the technologies behind the production of Bactrian coinage and those represented at Hattuša are genetically linked, however its precocious development in Anatolia, apparently, is certainly intriguing. A few examples have been also noted at Kaman-Kalehöyük (Hirao and Enomoto 1997) and in an unprovenanced example of a bracelet with an inlaid and stylized electrum repoussé presentation scene from Çorum province

with around 16.5 wt.% Ni and 2 wt.% Co (Lehner in press-b). Another unprovenanced example of a figurine in 'Hittite' style is known to the Levant with around 17 wt.% Ni and 2.1 wt.% Co (Northover 1998).


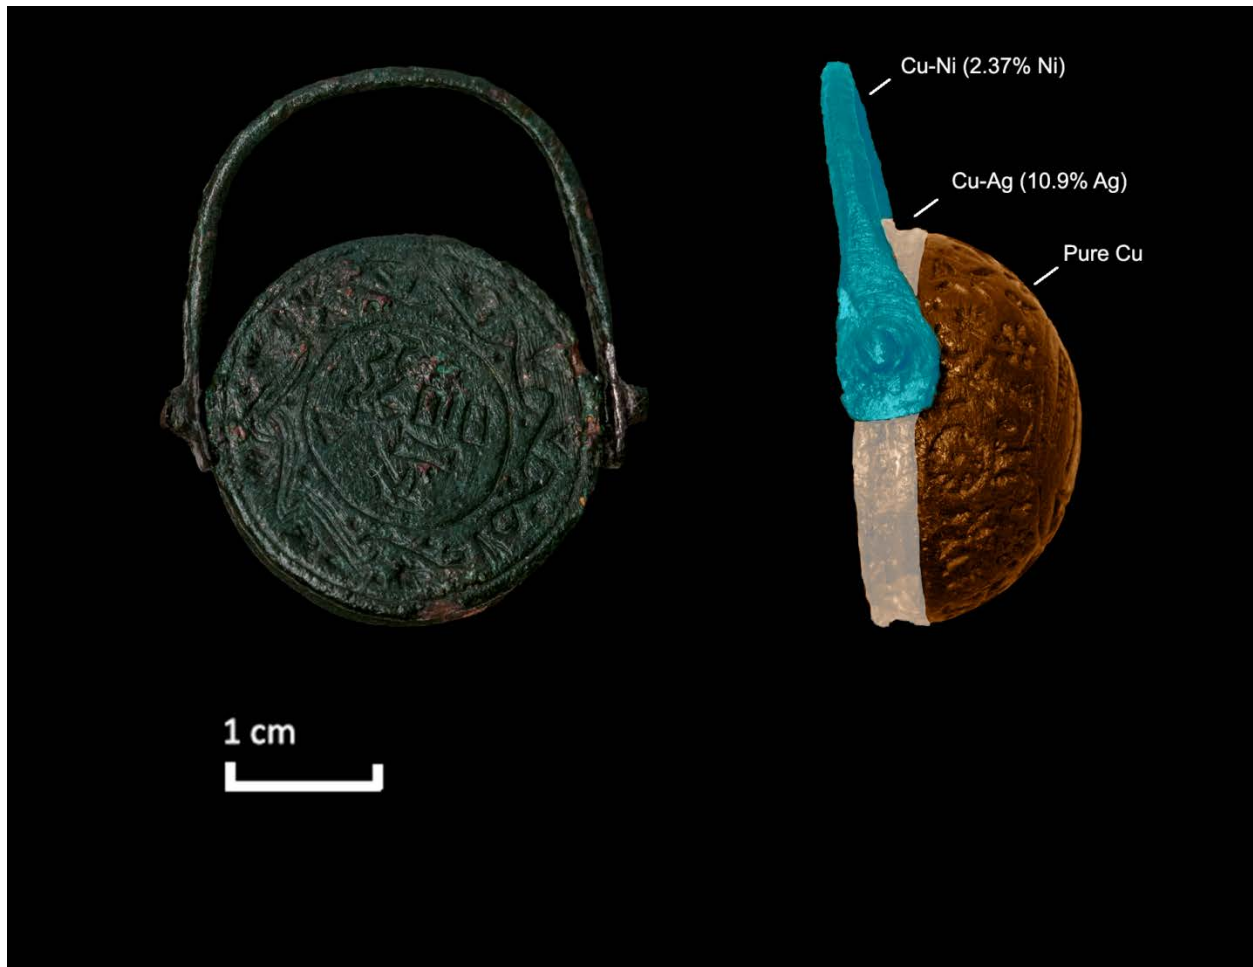


Figure 5.9: Stamp seal (Bo 05/13) composed of three separate copper alloys, including an attached band of low nickel cupronickel.

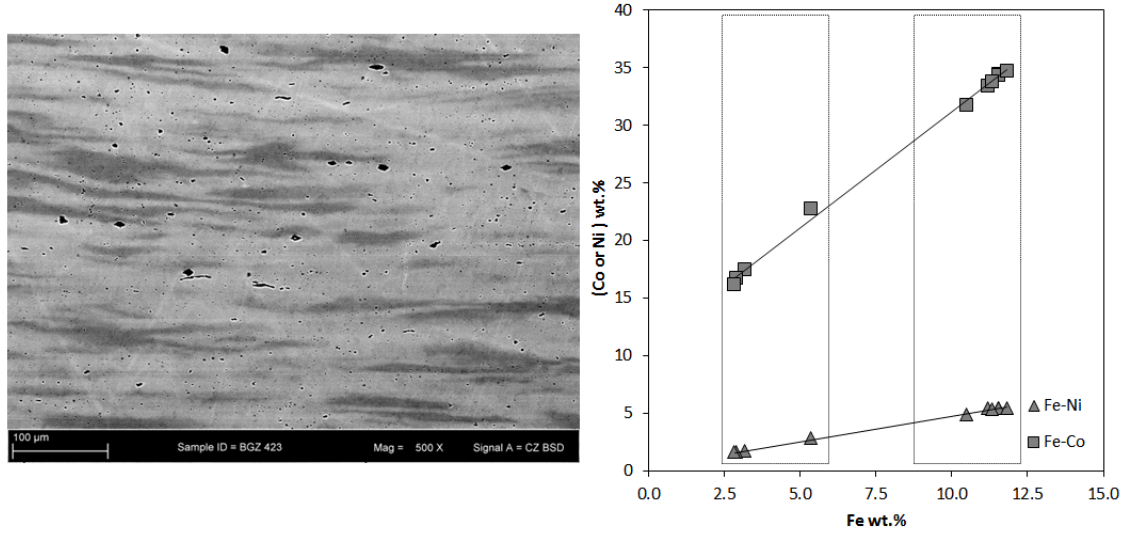

| | Cu wt.% | Fe wt.% | Co wt.% | Ni wt.% |
|--------------------|---------|---------|---------|---------|
| Dark phase | 49.6 | 11.3 | 5.3 | 33.7 |
| Light phase | 78.5 | 2.9 | 1.6 | 16.7 |

Figure 5.10: In depth analysis of rolled head pin (Bo 09/972) from the Sarikale Valley of Boğazköy. Point analyses across light and dark phases in the backscatter electron image (center) indicates a very strong coherence among related elements nickel, cobalt, and iron, reflecting the original casting segregation.

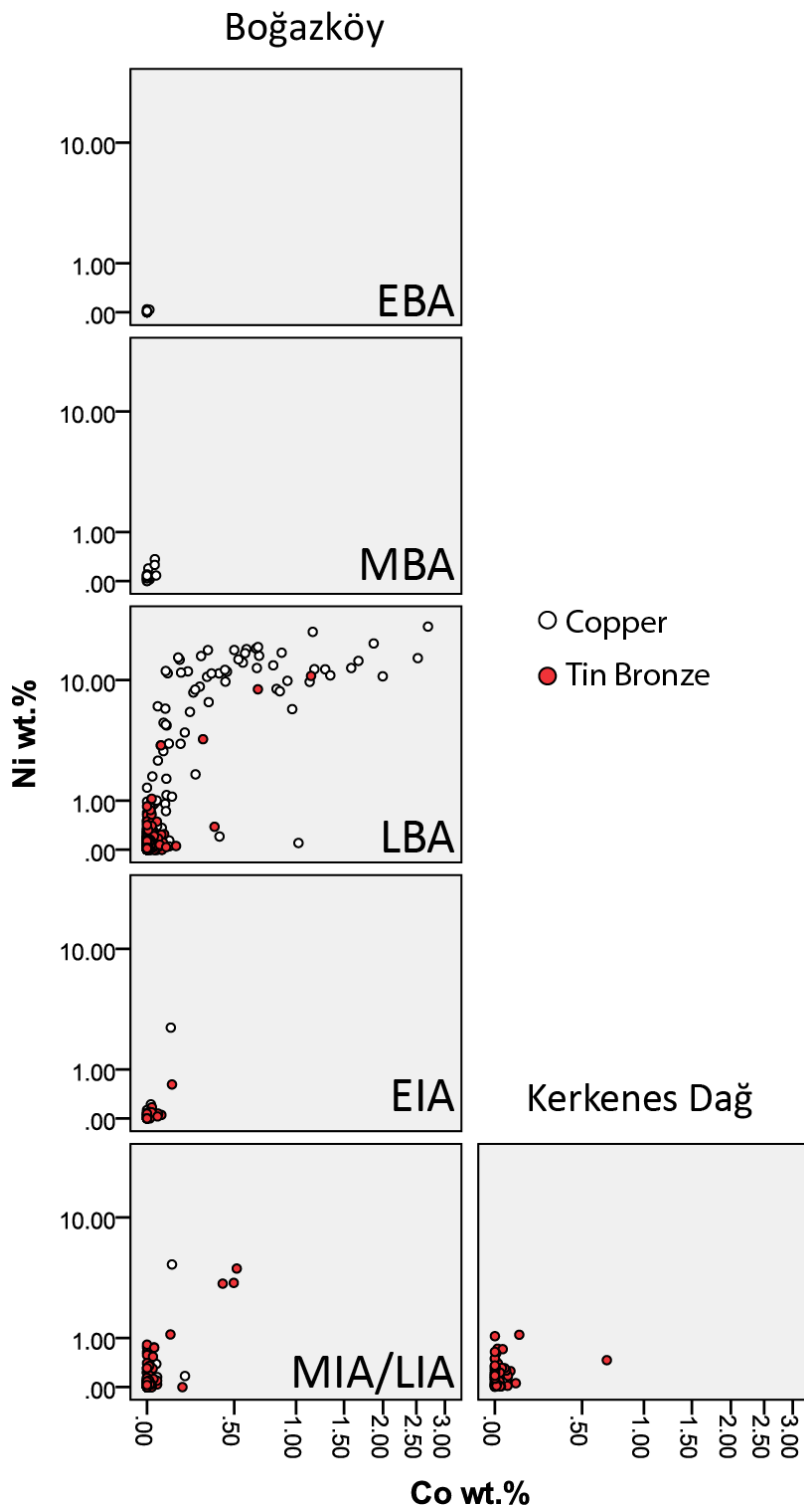


Figure 5.11: Concentrations of nickel (Ni) and cobalt (Co) compared across time periods and sites in this study.



Figure 5.12: Select examples of finished objects produced of high nickel cupronickel (>10.0 wt.% Ni) from Boğazköy dating to the Late Bronze Age.

Table 5.9: Nickel (Ni) content of copper alloys at Boğazköy and Kerkenes Dağ.

| Nickel % | Copper | | | Tin Bronze | | |
|------------------------|--------|--------|---------------|------------|--------|---------------|
| | Mean | Median | Range | Mean | Median | Range |
| Boğazköy (EBA) | 0.02 | 0.01 | < 0.01 - 0.04 | | | |
| Boğazköy (MBA) | 0.08 | 0.07 | < 0.01 - 0.31 | | | |
| Boğazköy (LBA) | 1.18 | 0.07 | < 0.01 - 11.2 | 0.18 | 0.06 | < 0.01 - 0.40 |
| Boğazköy (EIA) | 0.30 | 0.08 | < 0.01 - 2.61 | 0.08 | 0.05 | < 0.01 - 0.17 |
| Boğazköy (MIA/LIA) | 0.33 | 0.05 | < 0.01 - 0.75 | 0.25 | 0.06 | < 0.01 - 0.82 |
| Kerkenes Dağ (MIA/LIA) | 0.12 | | | 0.22 | 0.17 | < 0.01 - 0.71 |

Table 5.10: Cobalt (Co) content of copper alloys at Boğazköy and Kerkenes Dağ.

| Cobalt % | Copper | | | Tin Bronze | | |
|------------------------|--------|--------|---------------|------------|--------|---------------|
| | Mean | Median | Range | Mean | Median | Range |
| Boğazköy (EBA) | 0.00 | < 0.01 | < 0.01 - 0.01 | | | |
| Boğazköy (MBA) | 0.01 | < 0.01 | < 0.01 - 0.04 | | | |
| Boğazköy (LBA) | 0.07 | < 0.01 | < 0.01 - 0.45 | 0.02 | < 0.01 | < 0.01 - 0.06 |
| Boğazköy (EIA) | 0.02 | < 0.01 | < 0.01 - 0.12 | 0.02 | < 0.01 | < 0.01 - 0.07 |
| Boğazköy (MIA/LIA) | 0.02 | < 0.01 | < 0.01 - 0.12 | 0.02 | < 0.01 | < 0.01 - 0.12 |
| Kerkenes Dağ (MIA/LIA) | 0.06 | | | 0.02 | < 0.01 | < 0.01 - 0.08 |

5.3.6 Antimony, Silver, and Zinc

The concentrations of antimony (Sb), silver (Ag), and zinc (Zn) are summarized below in Tables 5.11, 5.12, and 5.13, respectively. Histograms of the respective elements are also given in Figures 5.7-5.8. These elements are generally considered trace elements in Bronze Age and Iron Age copper alloys, and they are often indicative of the types of ores used in the primary production of raw copper. In particular, antimony and silver are sensitive to ore attribution studies because these metals tend to maintain their relative ratios from ore to metal, however ore smelting technologies may alter these ratios depending on temperature and reducing conditions. There are no general trends noticed from these trace elements that are considered meaningful in this study across all time periods for antimony and silver, aside from the possibility that there may exist a bimodal distribution for silver during the Early and Middle Bronze Ages.

At Kerkenes Dağ, there is an important rise in the content of zinc alloyed with copper among select objects. This is particularly remarkable because zinc vaporizes rapidly and is generally lost to the air in most open smelting and melting environments. Zinc in excess of 5% is noted for several samples from Kerkenes Dağ, which suggests that zinc may have been intentionally controlled for using a cementation process. In this process, zinc ores may be directly added to molten copper into a covered crucible, which prevents zinc vapor from escaping, effectively entrapping the metal into an alloy of brass (Thornton 2007). Craddock (1978) and Forbes (1964: 268-269) in fact posited that copper-zinc alloys were innovated first in Anatolia, as evinced by the discovery and analysis of early brass artifacts from Tumulus MM at Gordion (Steinberg 1981). Yet it is clear that copper-zinc alloys are dated much earlier into the first half of the 3rd millennium BC in the Aegean and Mesopotamia (Thornton 2007: 126). The finds are exceedingly rare which suggest that the production of early copper-zinc alloys was either quite limited in production or the result of accidental production from zinc-rich copper ores. The development of brass in the Iron Age, which is poorly understood in the pre-Roman periods, suggests that metalsmiths selected ores specifically to create alloys ultimately similar to tin bronze but altered the alloy to produce a metal that was increasingly similar to gold.

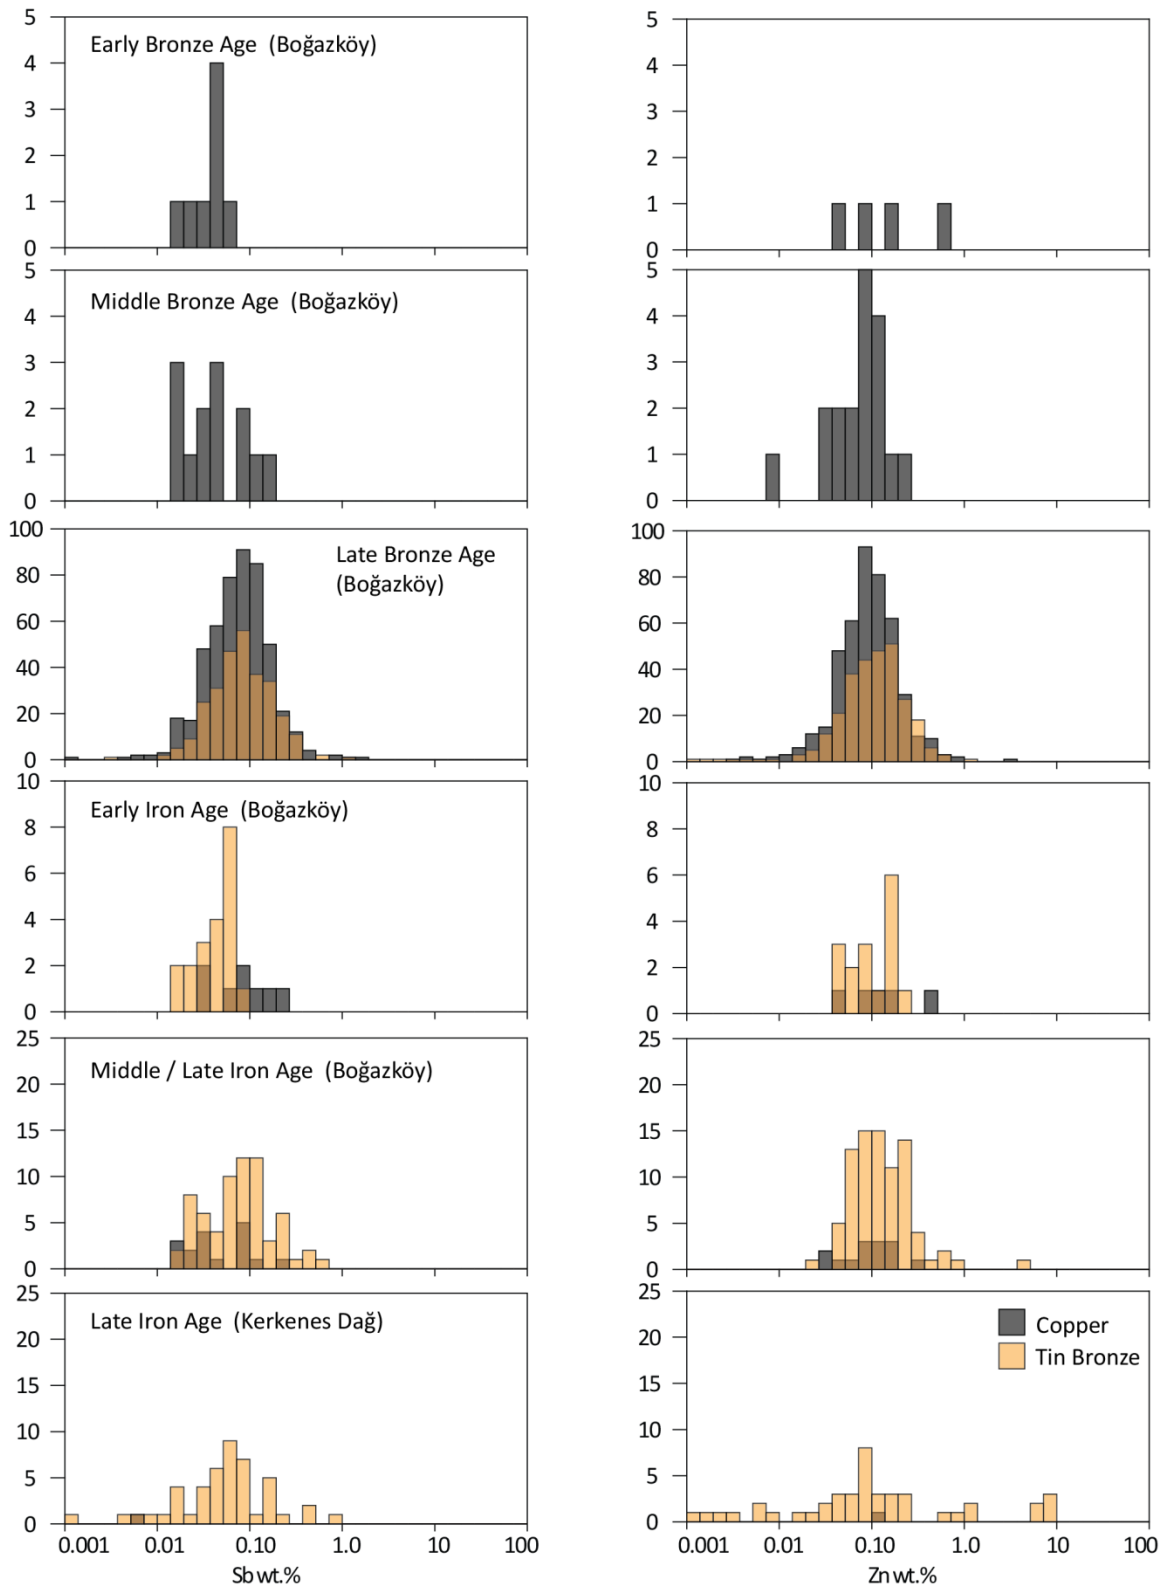


Figure 5.13: Diachronic frequency histograms of antimony (Sb) and zinc (Zn) from Boğazköy and Kerkenes Dağ.

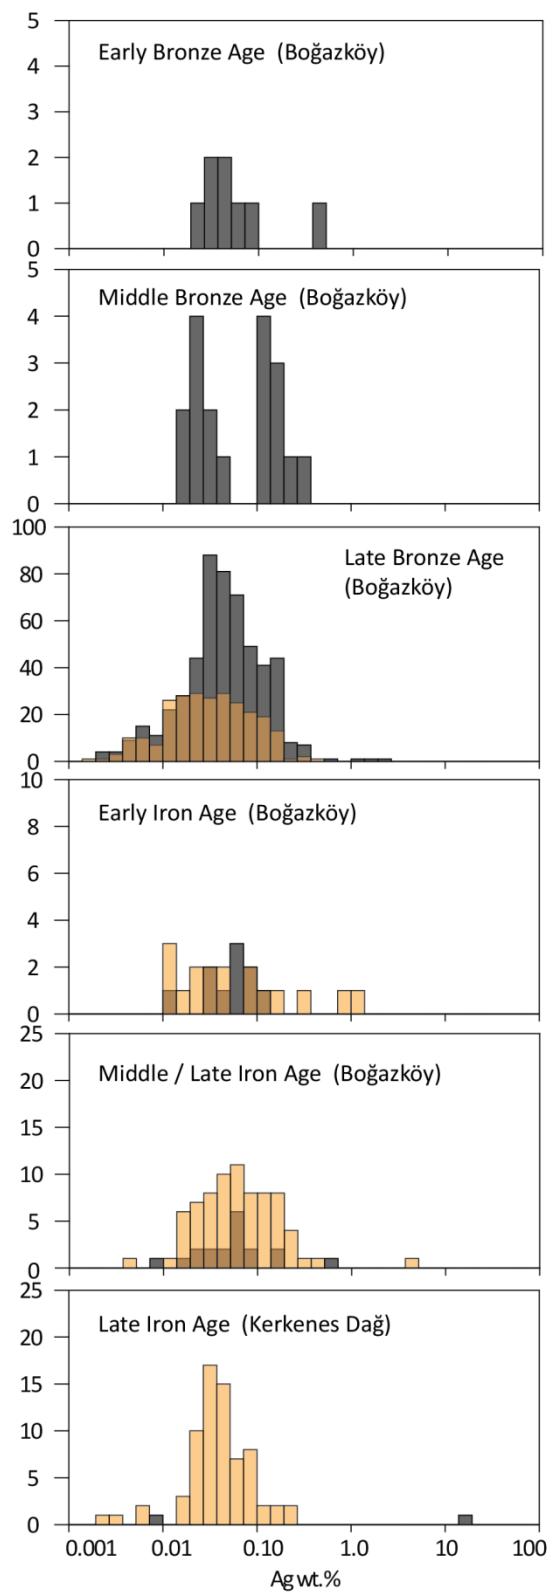


Figure 5.14: Diachronic frequency histograms of silver (Ag) from Boğazköy and Kerkenes Dağ.

Table 5.11: Antimony (Sb) content of copper alloys at Boğazköy and Kerkenes Dağ.

| Antimony % | Copper | | | Tin Bronze | | |
|------------------------|--------|--------|---------------|------------|--------|---------------|
| | Mean | Median | Range | Mean | Median | Range |
| Boğazköy (EBA) | 0.04 | 0.04 | < 0.02 - 0.06 | | | |
| Boğazköy (MBA) | 0.03 | 0.02 | < 0.01 - 0.13 | | | |
| Boğazköy (LBA) | 0.09 | 0.07 | < 0.01 - 0.24 | 0.09 | 0.07 | < 0.01 - 0.26 |
| Boğazköy (EIA) | 0.07 | 0.07 | < 0.01 - 0.22 | 0.04 | 0.04 | < 0.01 - 0.06 |
| Boğazköy (MIA/LIA) | 0.05 | 0.03 | < 0.01 - 0.18 | 0.08 | 0.06 | < 0.01 - 0.24 |
| Kerkenes Dağ (MIA/LIA) | 0.01 | | | 0.07 | 0.03 | < 0.01 - 0.24 |

Table 5.12: Zinc (Zn) content of copper alloys at Boğazköy and Kerkenes Dağ.

| Zinc % | Copper | | | Tin Bronze | | |
|------------------------|--------|--------|---------------|------------|--------|---------------|
| | Mean | Median | Range | Mean | Median | Range |
| Boğazköy (EBA) | 0.10 | 0.03 | < 0.10 - 0.56 | | | |
| Boğazköy (MBA) | 0.08 | 0.08 | < 0.10 - 0.18 | | | |
| Boğazköy (LBA) | 0.10 | 0.08 | < 0.10 - 0.26 | 0.12 | 0.10 | < 0.10 - 0.33 |
| Boğazköy (EIA) | 0.07 | < 0.01 | < 0.10 - 0.38 | 0.09 | 0.07 | < 0.10 - 0.18 |
| Boğazköy (MIA/LIA) | 0.07 | 0.06 | < 0.10 - 0.18 | 0.19 | 0.10 | < 0.10 - 0.38 |
| Kerkenes Dağ (MIA/LIA) | 0.12 | | | 0.09 | < 0.10 | < 0.10 - 0.56 |

Table 5.13: Silver (Ag) content of copper alloys at Boğazköy and Kerkenes Dağ.

| Silver % | Copper | | | Tin Bronze | | |
|------------------------|--------|--------|---------------|------------|--------|---------------|
| | Mean | Median | Range | Mean | Median | Range |
| Boğazköy (EBA) | .09 | .04 | < 0.10 - 0.56 | | | |
| Boğazköy (MBA) | .09 | .04 | < 0.10 - 0.18 | | | |
| Boğazköy (LBA) | .06 | .04 | < 0.10 - 0.26 | 0.12 | 0.10 | < 0.10 - 0.33 |
| Boğazköy (EIA) | .05 | .05 | < 0.10 - 0.38 | 0.09 | 0.07 | < 0.10 - 0.18 |
| Boğazköy (MIA/LIA) | .07 | .05 | < 0.10 - 0.18 | 0.19 | 0.10 | < 0.10 - 0.38 |
| Kerkenes Dağ (MIA/LIA) | .01 | | | 0.09 | 0.00 | < 0.10 - 0.56 |

5.4 Discussion and Conclusion

Figure 5.15 displays the progression of alloy types observed from nearly 1200 objects from Boğazköy and Kerkenes Dağ, demonstrating a progression of several alloy types over time with the greatest diversity occurring during the Late Bronze Age. Relatively pure copper and arsenical copper alloys are most common during the Early and Middle Bronze Age. Surprisingly few objects during the Middle Bronze Age are copper tin bronzes. This may be an effect of sample size and deserves to be investigated further.

The diversity of alloy types dramatically increases during the Late Bronze Age. This comes as somewhat intuitive because we know that the Hattuša as a polity radically increases in size and political and economic influence. Metallurgical technologies and traditions during this time period also develop more standard alloy types as trade in pure metal ingots proliferated, as evinced by the Uluburun shipwreck materials (Hauptmann, et al. 2002a; Yalçın, et al. 2005). Tin bronzes become noticeably more common during this time period, and ternary Cu-As-Sn alloys also appear which is suggestive of recycling but is also consistent with intentional alloying. Leaded alloys also appear during this time period. As previously observed, high nickel copper alloys appear during this time and their use appears to be limited to the Late Bronze Age, however a couple examples of copper-tin bronzes with nickel appear during the Middle and Late Iron Age. This alloy group, which includes Cu-Ni, Cu-As-Ni, Cu-Ni-Sn, and quaternary systems, demonstrates the wide use of this material. It is not yet clear if this alloy group is limited to particular functional tool types or ornaments, but its performance characteristics would have noticeably different from other copper alloys.

Alloying traditions during the Iron Age continue the use of copper tin bronzes for the production of both cast and forged shapes. The use of arsenical copper dramatically decreases

during throughout the Iron Age, which likely reflects overarching changes in both local trade networks and primary reduction technologies. Leaded bronzes appear first during the Late Bronze Age; however this technology only proliferates successfully during the Iron Age with the introduction of more sophisticated casting technologies. The adoption of bronzes with significant zinc contents (ca. 1.0-10 wt.% Zn) is evinced from several samples at Kerkenes Dağ, which demonstrates the rise of a new alloy type. The innovation and adoption of this alloy, otherwise known as brass, proliferates in use only during the Roman period several centuries later. The isolation of zinc for alloying with copper in the production of brass involves a drastically different production sequence than bronze production, and it is generally considered to begin large-scale proliferation during the Roman Period (Craddock 1995; Thornton 2007). Low zinc brasses (ca. 1.0-10 wt.% Zn) are discernable in earlier periods and are likely the result of mixed smelting where zinc is introduced via a cementation process.

To observe the effects of sample size on diversity, Figure 5.16 plots the number of alloy types against the number of samples analyzed for the cultural time period in question. A clear logarithmic distribution suggests that sample size does not directly determine alloy type diversity. However the possible number of alloys is limited, which would also distribute in the same way as in sample populations with high diversity. In any case, some general conclusions can be made. These data support the intuitive theory that polity size determines the abundance and diversity of both resource types and technologies (Kline and Boyd 2010). The geographic scope of the Hittite polity would have been extensive, promoting the movement of materials and cultural knowledge over long distances in order to finance the workings of the regional center of Hattuša. Conversely, conservative alloy preference during the Early-Middle Bronze Age and the

Early Iron Age suggests diversity in complex technologies were not as available as they were during the height of the Hittite empire.

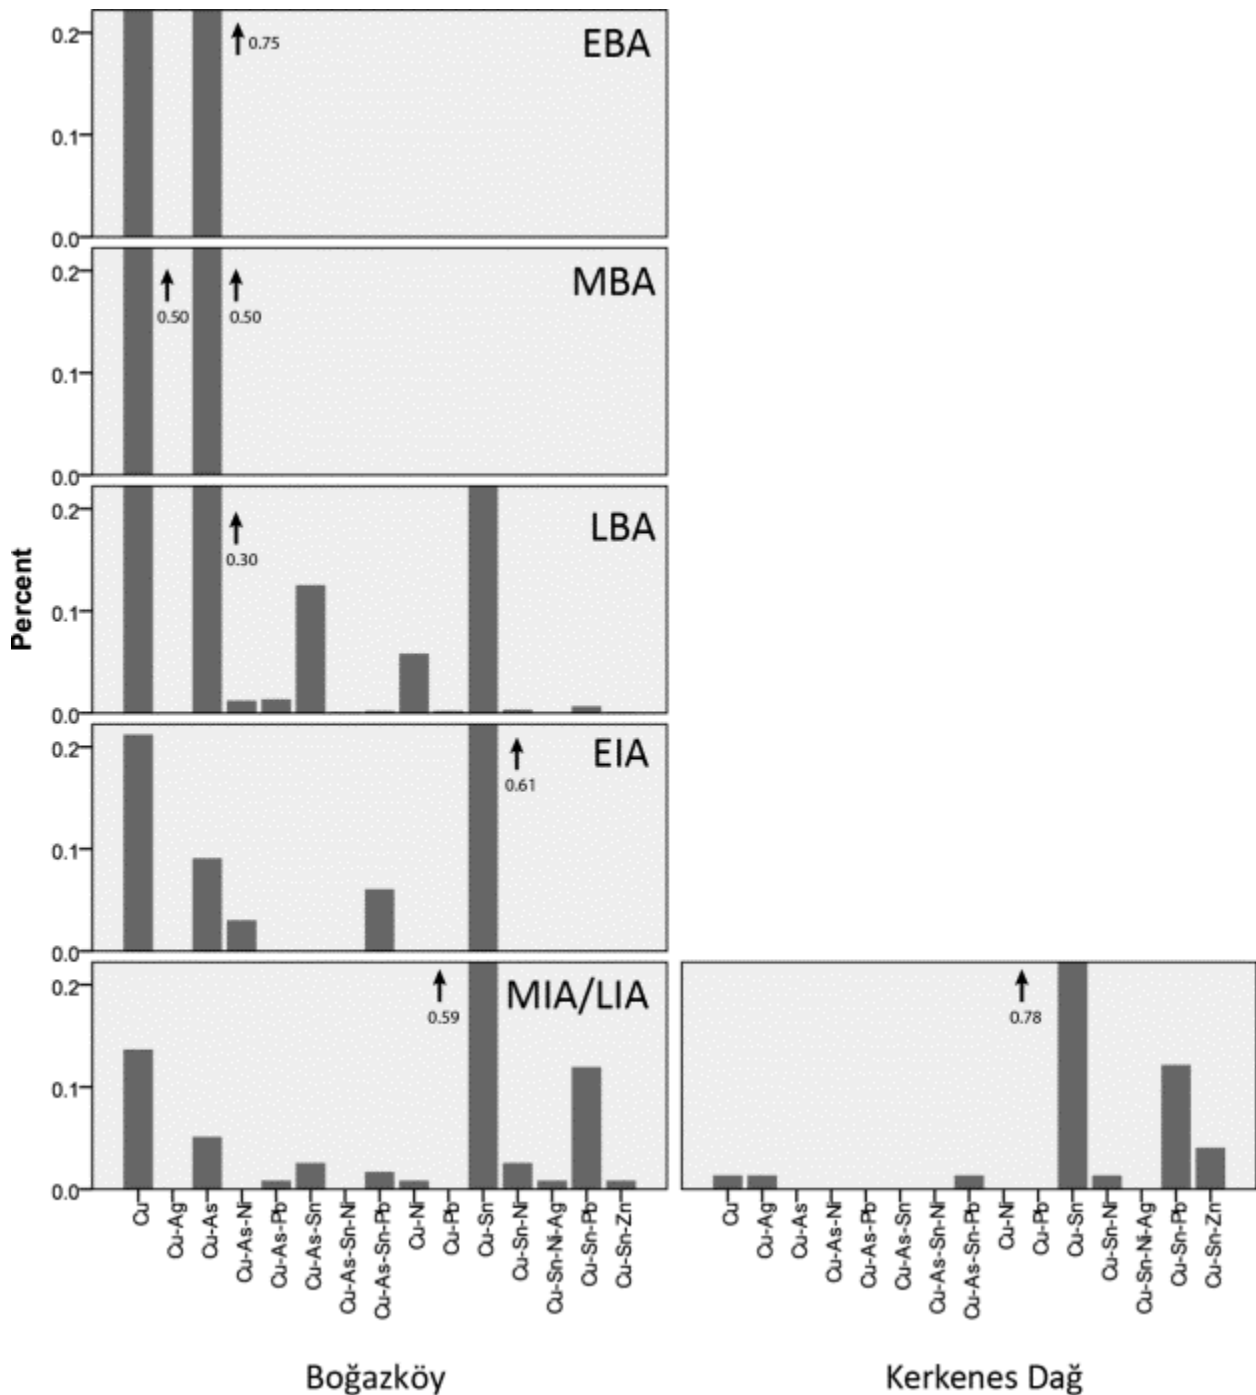


Figure 5.15: Copper alloy consumption profile at Boğazköy and Kerkenes Dağ from the Early Bronze Age to the Middle/Late Iron Age. The y-axis scale is enhanced to show the distribution of alloy types below 0.10 of the assemblage group. Those above the scale are noted with arrows and their respective ratios.

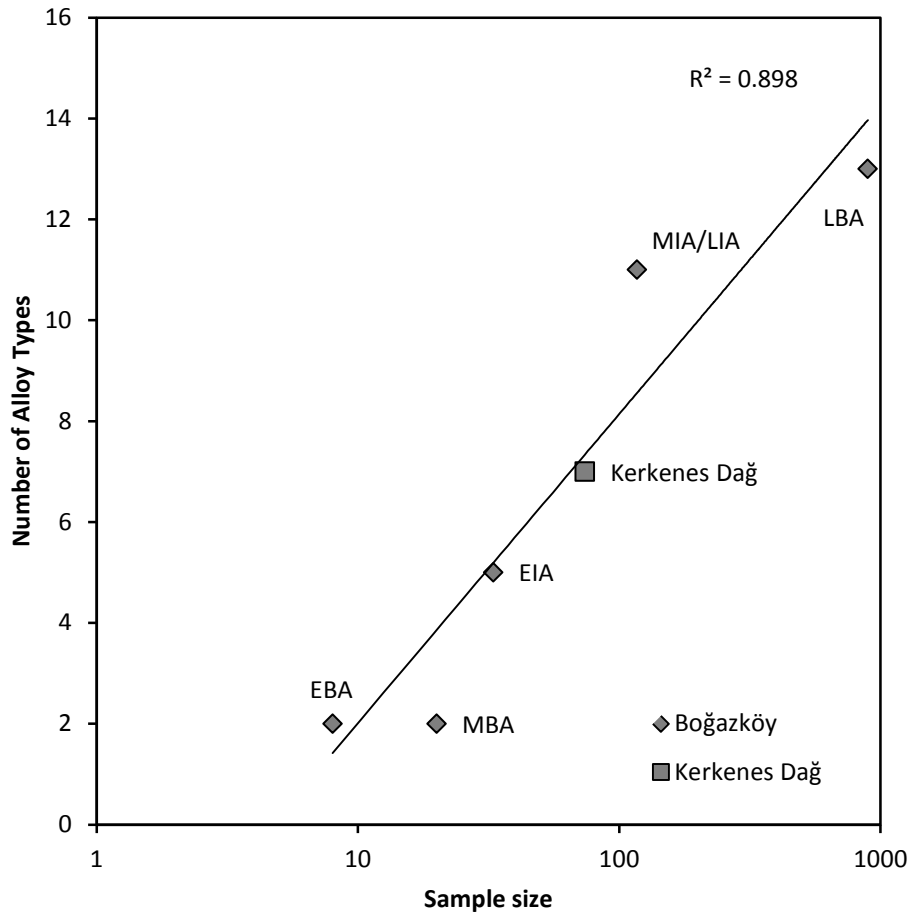


Figure 5.16: Comparison of copper alloy types versus sample size. A significant logarithmic distribution demonstrates that sample size probably affects the distribution and diversity of observed alloy types per time period.

CHAPTER 6: THE EMERGENCE OF THE METAL CRAFT ECONOMY IN THE BRONZE AND IRON AGES OF CENTRAL ANATOLIA (c.2300-400 B.C.)

6.1 Introduction

In Anatolia, the rise of metal industries during the Bronze and Iron Ages can be linked to several factors. Following Yener (Yener 2000), first industries appear to have initially adopted optimal strategies based on the manipulation of diverse local resources, including a myriad of mineral ore assemblages across Anatolia. This developed into distinct metallurgical traditions across space and time, reflecting the emergence of regionalized cultures during the 4th and early 3rd millennia BC. Lastly, the increased labor specialization and exchange associated with the rise of complex societies during the mid-3rd millennium BC gave rise to the spatial segregation of metallurgical activities and ultimately the development of a “multi-tiered hierarchy” of production. Highland production sites provisioned agricultural low lands and regional centers with primary metals for further refinement and remelting into finished products during secondary production. This further allowed elites in regional centers to effectively sponsor technological activities associated with metal production, and thereby monitor the distribution and valuation of metal commodities and finished goods in the emergence of a trade-based finance system (Bachhuber 2011).

In this concluding chapter, I further link metal industries to models of state finance. These models help explain how polities or indeed factions within polities would sponsor specialized production and trade of metal. The social organization of metal specialization and trade during the rise of the Hittite Empire, its decline, and the subsequent rise of complex Iron Age polities

are exemplary of how states utilized scarce resources to finance their activities. I argue that the problems associated with state emergence, more specifically the challenges inherent to expansion and competition, determined in part how states attempted to mobilize resources in central Anatolia.

6.2 State fiscal systems and metallurgy: staple finance vs. wealth finance

To mitigate problems associated with population density pressures and resource scarcities, such as dangerous levels of within group competition, state institutions often needed to expand access to agricultural staples, commodities, finished goods, and labor. Spencer (2010) theorizes that expanding polities eventually reach a limit at which point large qualitative shifts in administrative mechanisms (bureaucracies, hierarchies, etc.) give rise to fundamentally transformative changes in how the polity or group of polities are organized. One of the principle problems expanding states face is how to sufficiently acquire and mobilize resources to adequately finance expansionistic strategies of trade and war in addition to the state institutions built around these strategies. D'Altroy and Earle argue that the key factors associated with the fiscal organization of these strategies include “the capacity of the subject groups for gross surplus production, a required state investment in political and economic security, and the potential efficiency of production, logistical, and disbursement mechanisms” (D'Altroy and Earle 1985: 188).

D'Altroy and Earle further identify two distant strategies of state finance (Table 6.1). The first strategy, *wealth finance*, “involves the manufacture and procurement of special products” that “may be amassed as direct payment from subservient populations, or they may be produced by craft specialists attached to the central authorities” (D'Altroy and Earle 1985: 188). These

products are then used as media of exchange or payment for other goods and services, thus wealth in this case is used as a form of currency. The values of these products are culturally contingent, based on accepted valuation systems, and the products are often convertible into staple goods usually through some type of market transaction. Two advantages of this system is that wealth products often are less costly to store and transport, making them easier to control, and these goods further promote political alliance building through long-distance trade. Furthermore, long-distance trade in the form of tribute economies confer greater control over the means of payment, which in turn limits the capacity of peripheral polities to form an independent financial base and controls factional competition (Brumfiel 1994). The main disadvantage of wealth products, including most copper alloy products in the ancient Near East, is that they often have restricted intrinsic use values and they must be converted into staple goods for non-agriculturalists.

One important element in wealth finance is precisely where in the commodity chains involved in wealth production that controls are exercised. As described more thoroughly in Chapter 2, metal production involves a complex network of labor and resources whose activities have coalesced and dispersed variously through time. These production strategies likely reflect how they were incorporated into society as a whole. By the EB II in Anatolia ca. 2600-2300 BC, metal production activities exhibit significant degrees of labor specialization, where primary and secondary production activities were spatially discrete. Commodity chains at this point witnessed bottlenecks of control at the point of secondary production, whose activities were largely held within regional centers and in relative proximity to elite members of society.

Conversely, significant measures of the resources that a state can extract from a pre-modern economy are most likely to be related directly or indirectly to the agricultural production

of staple surpluses. *Staple finance* “involves obligatory payments in kind to the state of subsistence goods such as grain, livestock, and clothing” (D'Altroy and Earle 1985: 188). These goods are then paid out by state institutions to personnel and agents of the state who require them to meet basic household needs. This system effectively centralizes everyday subsistence surplus produced as tribute in agricultural peripheries, keeps them in centralized storage in regional centers, and then remobilizes these surpluses in a redistributive system (Earle 2011). One of the largest disadvantages of staple finance systems is the costliness of transporting perishable bulk subsistence goods across long distances. For this reason, staple finance systems appear to have been most effective among smaller polities where the management of agricultural surpluses did not require long distance transport. Furthermore, intensive agricultural production strategies carry significant risk (Marston 2012) and can initiate systemic social failures and famines in bad years (Garnsey and Morris 1989; Wright, et al. 1989).

Yet despite these fundamental problems, large-scale staple finance systems are known to many chiefly societies and archaic states, especially in areas where intensive agricultural systems produced sizeable surpluses per unit labor such as in southern Mesopotamia (Algaze 2008: 41; Jursa 2010: 99; Jursa and Garcia 2015: 120) and Lower Egypt (Jursa and Garcia 2015: 156; Wenke 1989). One way large-scale staple finance systems overcame transport costs was through the decentralization of storage away from the political center. By strategically distributing centers of collection to select region centers, the transport costs associated with mobilizing surpluses can be greatly reduced and their distribution made more efficient. Ruling elite would have to relinquish some control over these resources, risking the loss of control of territories; however, power structures could be maintained in the form of landed estates attached to noble families or other governing institutions associated with the state (eg., temples).

Table 6.1: Expectations following from theoretical archaic state fiscal systems (adapted from D'Altroy and Earle 1985; Stein 1994, 1999).

| Wealth finance | Staple finance |
|--|--|
| 1) exotic goods as markers of status in a prestige goods economy | 1) economic differentiation |
| 2) centrally located attached specialists focusing on the production of prestige goods | 2) centralized storage facilities for staples |
| 3) pronounced differentiation of elites, especially through their emphasis on foreign connections as means of access to exotic knowledge and goods | 3) evidence for rural production of surpluses |
| 4) higher levels of inter-regional competition and warfare | 4) either village-based craft production, or high proportions of local, as opposed to long-distance exchange |
| | 5) evidence for either ritual, kinship-based, or coercive modes of surplus mobilization |

6.3 Surplus finance and wealth finance during the Bronze and Iron Ages in central Anatolia

Wealth and staple finance strategies should be understood as heuristic categories. While most if not all examples of archaic complex societies never solely relied on one strategy alone, it is none the less possible to observe shifts among these strategies over time in central Anatolia. Furthermore, shifts in these strategies appear to be correlated to the sizes of the political entities, suggesting that the geographic scope of the territories and sociopolitical networks were determining factors in how archaic states in central Anatolia operated. The distribution of copper

alloy types, their evolution through cultural transmission and selection, and the provenance of their raw materials attest to significant shifts in the ways the state institutions acquired and provisioned value-added goods. As discussed in the beginning of Chapter 3, the development of polities during the EB II/III and MBA (ca. late 3rd and early 2nd millennia BC), data from elite burials and architecture show how metal goods, specifically tin bronze, was incorporated into developed systems of status. Furthermore, the development of regional centers during the late 3rd millennium BC more generally is attributed to the strategies of trade and war that served to coalesce political factions into scores of polities across central Anatolia (Selover 2015). These polities were linked by strategic participation in long-distance trade networks and alliances, and within the context of greater resource acquisition, polities also competed for access and political dominance. The production of copper, silver, gold, and, to a much lesser extent, iron commodities locally available within Anatolia at this time helped drive further interaction and integration of the region.

By the beginning of the 2nd millennium BC, several sites rose to prominence in central Anatolia, including Kültepe, Acmehöyük and Karahöyük-Konya. These polities competed for access to and dominance in the trade of high value-added goods, including mostly commodities of foreign textiles and tin. Texts indicate clearly that the ruling Anatolian elite sponsored the trade of wealth surplus in a kind of market exchange. Craft workshops associated both with palaces and lower city residences provide further evidence of the multiple trajectories wealth was produced in these societies. The distribution and organization of staple surplus is poorly known during this time period; however, it is increasingly likely that agricultural and pastoral strategies were intensified to support not only increases in population densities but also the rise of emerging expansionistic strategies during the end of the MBA (Arbuckle 2012; Atici 2014).

Conflagrations and subsequent abandonment of these centers coincided with the rise of a new political entity during the 17th century BC slightly north of this region at Boğazköy, which was previously the center of a small kingdom at Hattuš. By the 16th century, this site rose to prominence as a major ceremonial and economic central place. Formed within the context of intense competition, this polity expanded to be the center of the Hittite state. As Schachner (2009a) and Glatz (2009) demonstrated, the imperial foundations of Hattuša were based on large-scale regional changes, including structural modifications in the settlement organization depopulation strategies, the development of truly monumental architecture with corporate and administrative functions, and building projects including dams, water reservoirs, and granaries.

Textual and archaeological data from the Hittite capital demonstrates that this prominent Bronze Age state utilized both wealth and staple finance strategies to maintain their bureaucracies and expansionistic activities. Significant economic differentiation both within and between polities is evident (settlement systems, architectural variation in quantity and quality, textual evidence of administrative systems). However, nearly all research on Hittite Anatolia has focused on large sites dominated by elite contexts, so we know very little about the daily life realities of commoner participation in the state (Mielke 2011b). Nearly all of the excavated remains at Boğazköy attest to state infrastructure and elite residences and therefore it is exceedingly difficult to determine empirically the wider spectrum of economic differentiation within the Hittite state as a whole. Centralized storage of subsistence goods is evident at Boğazköy with the emergence of such activities at least into the early 2nd millennium BC (Schachner 2009a; Seeher 2006b; Strupler 2013). The monumental storage of grains at the state granaries at Boğazköy, in addition to taxation lists and land tenures systems which document the centralization of staple production, attest to the role of staple finance and institutional control of

rural staple surplus production. Surpluses were primarily mobilized persuasively and coercively through tribute (in the form of gifts and tax) and religious rituals and festivals, and these activities were primarily provisioned by the landed estates of the palace and temples. According to the Hittite Laws, wages for labor and services could be made in measures of grain or weights of silver, which was widely convertible into surplus goods.

Specialization and exchange in wealth surpluses, predominantly in the form of primary metal commodities and finished goods, provided an important mechanism of networked state interaction across its territory and potential political alliances. Similar to the organization of Mycenaean wealth finance systems, the production of value added metal goods operated primarily to create and maintain political networks between ruling members of the state and other regional elites whose cooperation determined in part the success of the state (Galaty and Parkinson 2007; Parkinson, et al. 2013).

Metal production throughout the Middle and Late Bronze Age occurs within the context of detached specialists who were provisioned, in part, by state institutions including the palace and temples. Metalsmiths who processed gold would have had their raw materials almost entirely provisioned by the state. Current data suggests that metal production activities occurred within the urban infrastructure of Boğazköy; however, depending somewhat on how one interprets the functional attributes of Boğazköy as a capital and how residential contexts were integrated into the city, these somewhat autonomous and proximate production activities were probably sponsored by state institutions. Bulk metals, in the form of primary commodities (ingots) and finished goods, were provisioned from subject polities as far as Cyprus and Syria, however the majority of copper metal imports appear to have been procured from Anatolian sources within

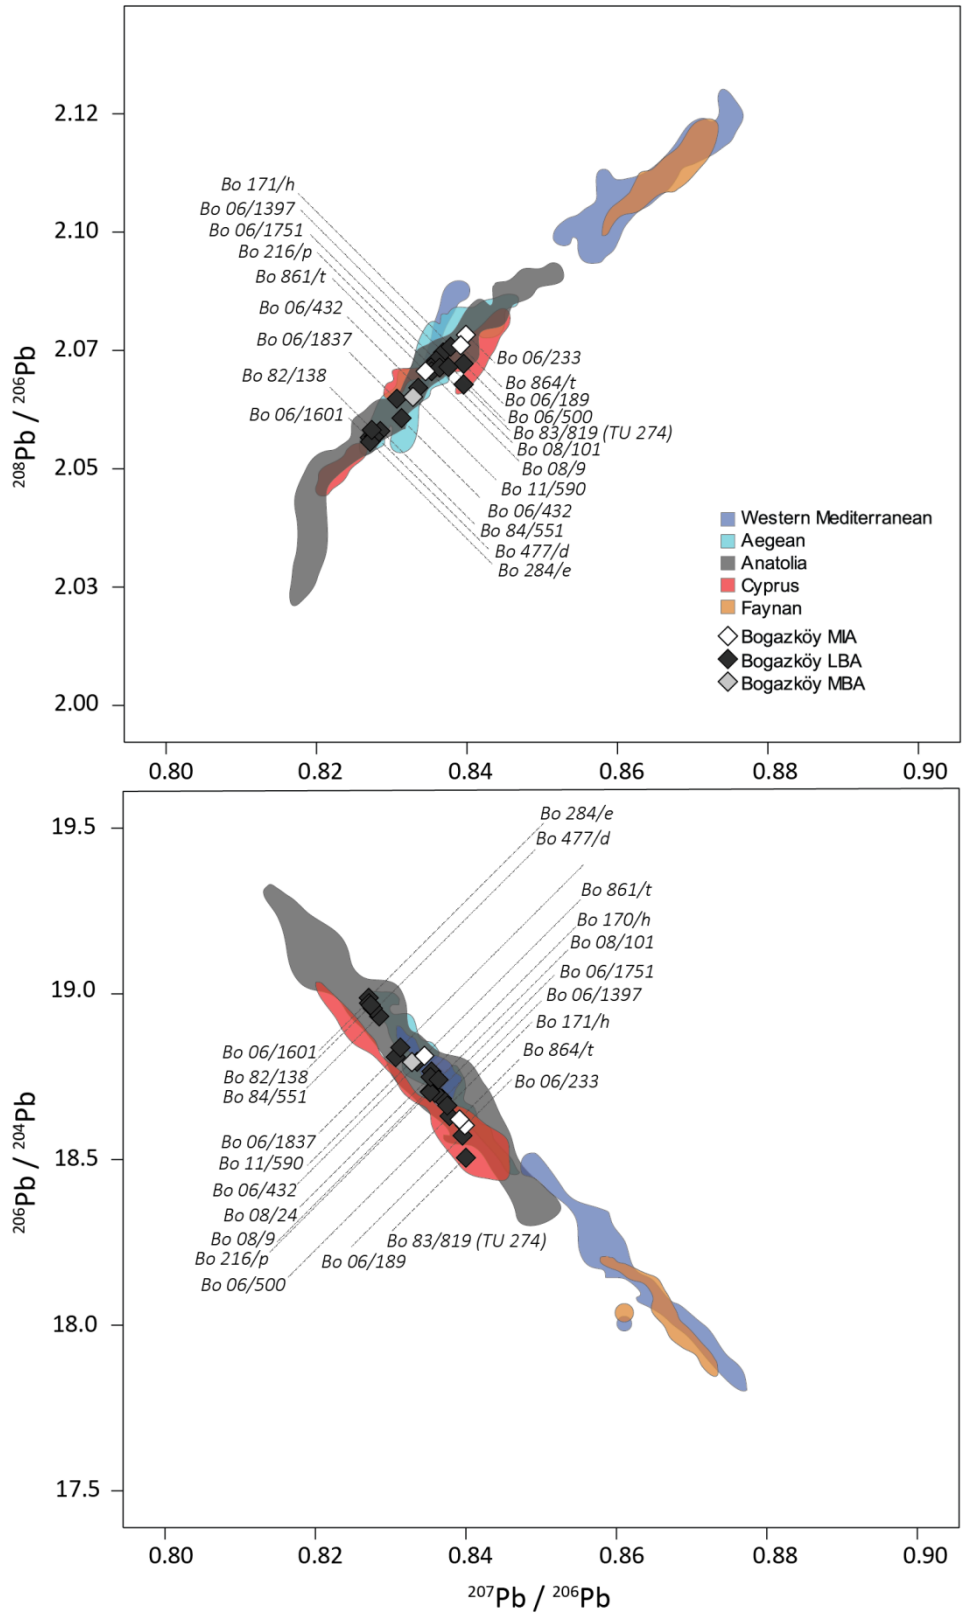


Figure 6.1: Preliminary lead isotope biplots comparing known ores to select artifacts recovered from Late Bronze Age and Iron Age contexts at Boğazköy.

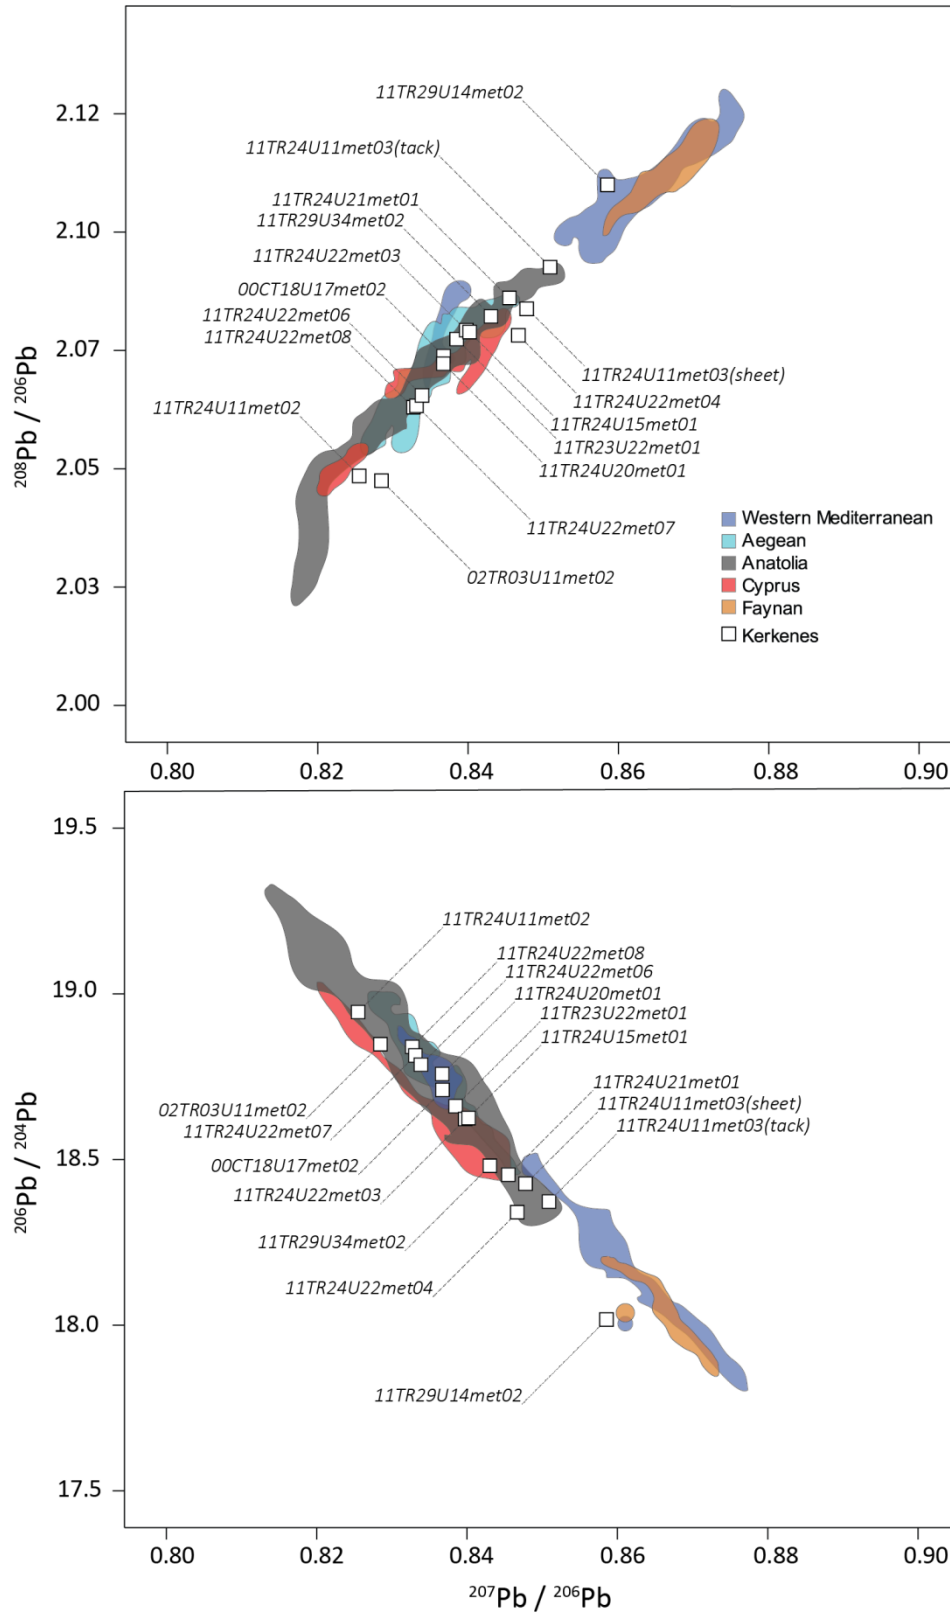


Figure 6.2: Preliminary lead isotope biplots comparing known ores to select artifacts recovered from Iron Age contexts at Kerkenes Dağ.

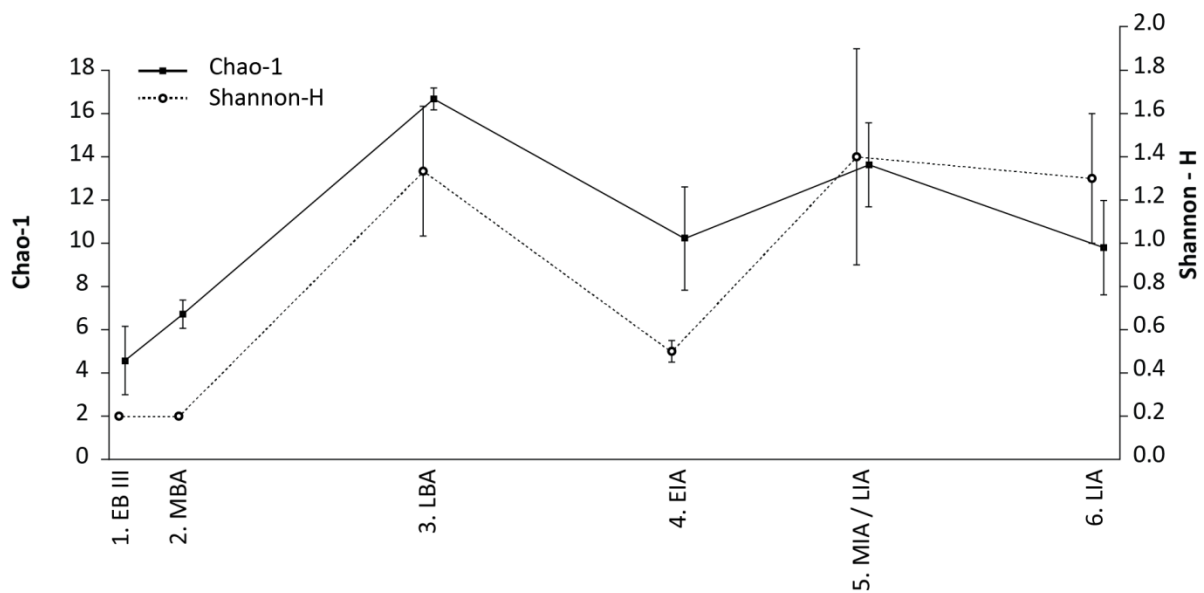
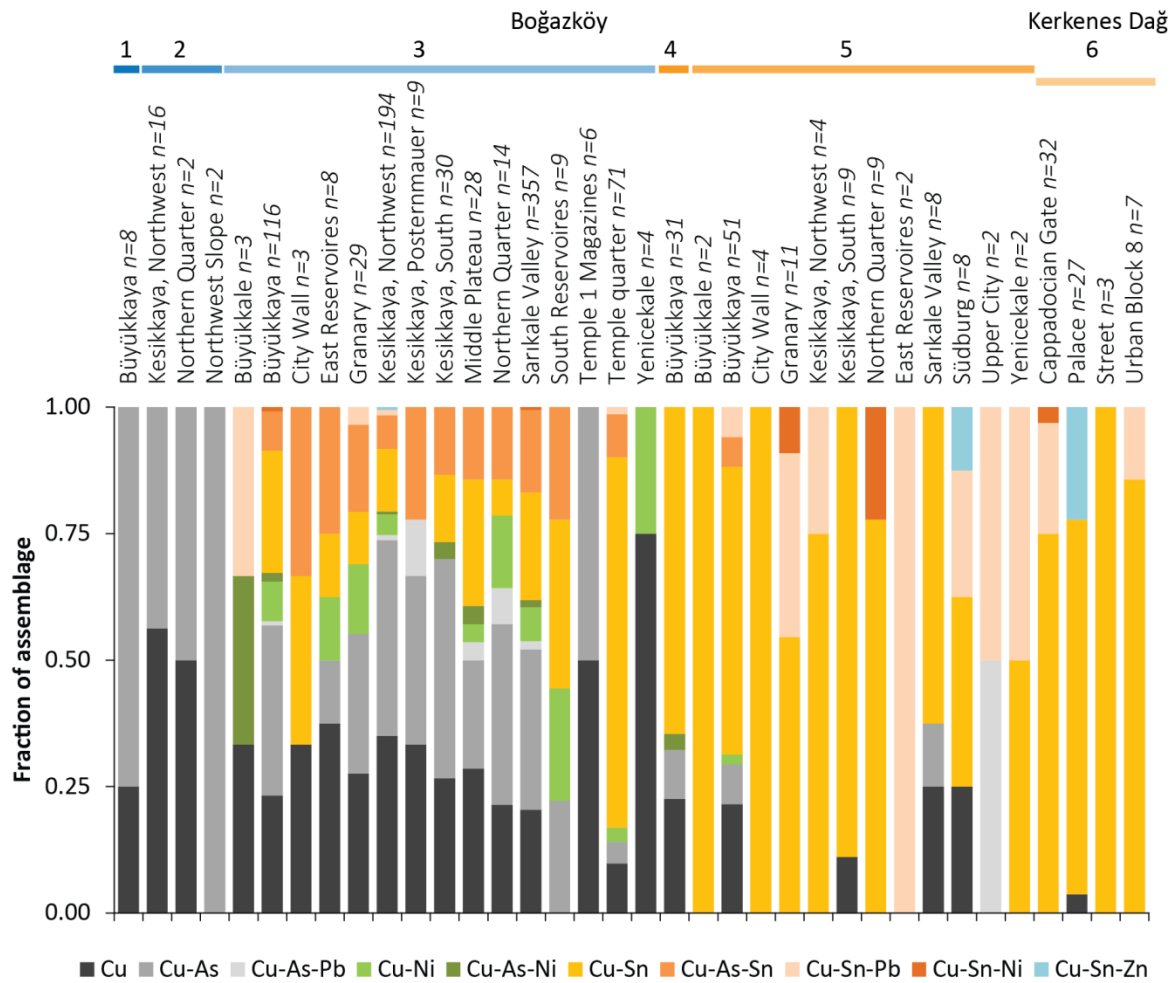


Figure 6.3: Diachronic change in abundance ratios of copper alloy types among finished goods across observed contexts (top) and type diversity measures (Chao-1 and Shannon-H) during each respective time period (bottom).

the Taurides (Figure 6.1)³. The obvious exception is a quarter piece of an oxhide ingot, which almost certainly produced from Cypriot copper from Apliki (Bo 79/206, Stos-Gale, et al. 1997: 117). In their attempts to monopolize all long-distance trade and elite craft production, rulers effectively placed exotic and high value added goods within a cultural system of status.

Categorical status can be observed within the bronze industries and consumption profiles of Hittite Anatolia. On the one hand, consumption profiles associated with residential contexts at Boğazköy demonstrate a reproducible pattern showing that around a quarter of the copper consumed was unalloyed. A further quarter to third of these assemblages consists of arsenical copper. Copper alloyed with tin, which was most likely procured through long-distance exchange, comprises between a quarter and third of these assemblages. The reverse pattern is observed among temple contexts, where finished goods produced from tin bronzes dominate over 75% of the assemblage (see Figure 6.2). This result is consistent with temple inventory lists that document the accumulation of tin bronze as part of a wealth finance system.

After the collapse of the Hittite Empire ca. 1200 BC, the reemergence of polities in central Anatolia ushered in a novel political system during the 9th century BC. Much less is known about the organization of the political economy at this time, but investigations at Gordion, which was probably the center of the expanding Phrygian state, suggest that elites adopted a drastically different fiscal system. Unlike at Boğazköy-Hattuša, where significant investments in storage demonstrate a large-scale staple finance system, no such structures are known to Gordion or later at Kerkenes Dağ. Yet at Gordion, archaeobotanical research has however demonstrated an intensification of agricultural and pastoral production that coincides with the rise of the Phrygian state (Marston 2012; Miller, et al. 2009). The intensive production of staple goods

³ Lead isotope analysis is a well-accepted method to provenance a range of materials. Methods of analysis and the results for several objects used in this dissertation are further described in Appendix D. Previously published ore data are referenced therein.

would no doubt have served to support an expanding political system, yet we know very little how staple goods were provisioned by the state, presumably through a state controlled system of land tenure and taxation.

Further investigations support a fiscal system that was primarily sponsored the production and trade of status goods (Voigt and Henrickson 2000a: 50). This is demonstrated at Gordion, where the centralized production of textiles associated with elite structures at the site (Burke 2010, 2011). The increased presence of exotic goods, including vessels produced of fine ceramic, glass, and bronze, further attest to the centrality of long-distance trade. Perhaps most striking are the scores of massive tumuli, which included the burials of single individuals together with unprecedented high value burial goods (Kohler 1995; Young 1981). Mid to Late Iron Age cremation burials in the lower town of Boğazköy also attest to the inclusion of exotic status goods, including bronze fibulae and vessels, jewelry produced of precious metals, some of which included in finely crafted cremation urns (Boehmer 1979; Genz forthcoming). This pronounced differentiation of elites, especially based on the emphasis on foreign connections and exotic materials, further supports the role of wealth finance among polities during the Iron Age in central Anatolia.

A similar pattern is observed at Kerkenes Dağ; however, to date there are no production contexts yet discovered aside from a large oven found in a residential context of the southern city that was interpreted to be used for bread production (Schmidt 1929: 234-237). Furthermore, the large monumental tumuli that surround the city, if indeed dated synchronically with the city, likely attest to a similar differentiation of elites and political economy. High value crafted goods found in the city, including a finely carved ivory plaque from Urban Block 8 (Dusinberre 2002) and gold/electrum ornament (Summers in press; Summers and Summers 2012), among few other

examples of ivory and precious metals, suggest that communities at the city maintained relationships with polities in western Anatolia and, indirectly, the Mediterranean world. The repertoire of pottery from Kerkenes Dağ demonstrates the local provisioning of several sources or workshops within central Anatolia (Kealhofer, et al. 2010), yet little to no evidence exists for any transport of exotic transport vessels. The pottery of Middle and Late Iron Age Boğazköy demonstrates a similar limitation, thus supporting the idea that perishable trade goods contained in vessels must have declined since the Bronze Age (Kealhofer, et al. 2009: 296). There is however an increase in exotic table wares at Boğazköy during the Mid to Late Iron Age.

Data from the copper alloy analyses however suggest that tin bronze was almost exclusively consumed relative to most other alloy types (Figure 6.2). This pattern is similar to analyses completed on Late Assyrian copper alloys from Nimrud (Curtis 2013) and other analyses of 8th century BC copper alloys from Phrygia and Urartu (Atasoy and Buluç 1982; Çukur and Kunç 1989; Hirao and Enomoto 1993; Hirao and Enomoto 1997; Hughes, et al. 1981; Twilley 1996), where tin was probably imported. Lead isotope analyses of select Kerkenes objects indicate that copper was provisioned from at least four separate source areas in Anatolia, including the Pontides, central and eastern Taurides, and north central Anatolian sources (Figure 6.2). A single sample of a scroll headed pin however is inconsistent with most known Anatolian ores and is isotopically and compositionally similar to ores from the western Mediterranean, including Sardinia and Spain, and possibly also Oman. Unlike copper metal from Hittite Anatolia, which appears mostly to have been provisioned from local sources and also those from Cyprus, Late Iron Age communities at Kerkenes Dağ were able to participate in a much more broad system of metal exchange that extended from the western Mediterranean to southern Mesopotamia (Sherratt and Sherratt 1993). Evidence from these analyses also suggest that trade

of Pontic copper reached Kerkenes Dağ, which are currently absent from analyses of the Hittite copper alloys from Boğazköy but have been documented for the second millennium contexts elsewhere at Middle Bronze Age Kültepe (Lehner 2014a) and Late Bronze Age Kaman-Kalehöyük (Enomoto and Hirao 1999; Hirao and Enomoto 1994; Hirao, et al. 1992).

Figure 6.3 further distills how technological diversity among copper alloys is represented within the observed assemblages over time. Alloy type abundance measures, which are simple ratios of the subtotal assemblage, provide an excellent measure of alloy preference. This approach remains underutilized because modern techniques are only beginning to move beyond the select analysis of samples to more comprehensive approaches such as completed in this dissertation. This consumption profile indicates the behavioral choices in aggregate that individuals made given available alloy types. Here it is possible to observe the effects of context on consumption profiles. The distinguishing characteristic of the Late Bronze Age assemblages is, as mentioned above, the difference between temple contexts and residential contexts elsewhere in the city, especially those well represented at the Sarıkale Valley and the residential sector northwest of Kesikkaya. Tin bronze, which is a well-accepted marker of long-distance trade and status, is particularly well represented among the temple assemblages. The transition into the Iron Age is accompanied with a rapid decline in the consumption of arsenical copper and their exclusive replacement with tin bronze, leaded tin bronze, and early brass metal. This development demonstrates how metalsmiths had increasing access to exotic resources like tin to produce well-crafted alloys in quantities that were not apparently reached during earlier periods.

Two further statistic measures were calculated to determine the relative diversity of all possible alloys per time period. These measures include the Chao-1 and Shannon-H statistics. The Chao-1 measure is a non-parametric estimator of paradigmatic class richness, which is the

number of different possible classes, given a sample population (Eren et al. 2012). The Shannon-H diversity index measure of diversity accounts for class abundance and evenness in a subset population. Both measures were computed using PAST (Hammer et al. 2001). These measures demonstrate similar significant patterns and empirically support the positive relationship between polity size and technological diversity (Kline and Boyd 2010). During the Late Bronze Age, a rapid increase in both alloy class richness and diversity is followed by a decline during the Early Iron Age and a subsequent rise during the reestablishment of polity at Boğazköy.

An independent line of evidence also comes from Iron Age pottery from these prominent regional centers. Analyses of ceramic bulk composition from Gordion, Boğazköy, and Kerkenes Dağ, collectively demonstrate a positive relationship with political complexity (Grave, et al. 2009; Kealhofer, et al. 2009; Kealhofer, et al. 2010). The authors of this research, correctly in my view, logically connect increases in compositional group types with a florescence in trade and a rise in political complexity. Figure 6.4 demonstrates this relationship using absolute type counts and Shannon-H diversity. The emergence of political complexity, especially documented in the pottery and metal assemblages from these regional centers, is therefore intimately connected to the craft economy.

6.4 Conclusion

Here I argued that the emergence and development of metal technologies, specifically copper metallurgy, are intrinsically linked to the strategies that states employed in the

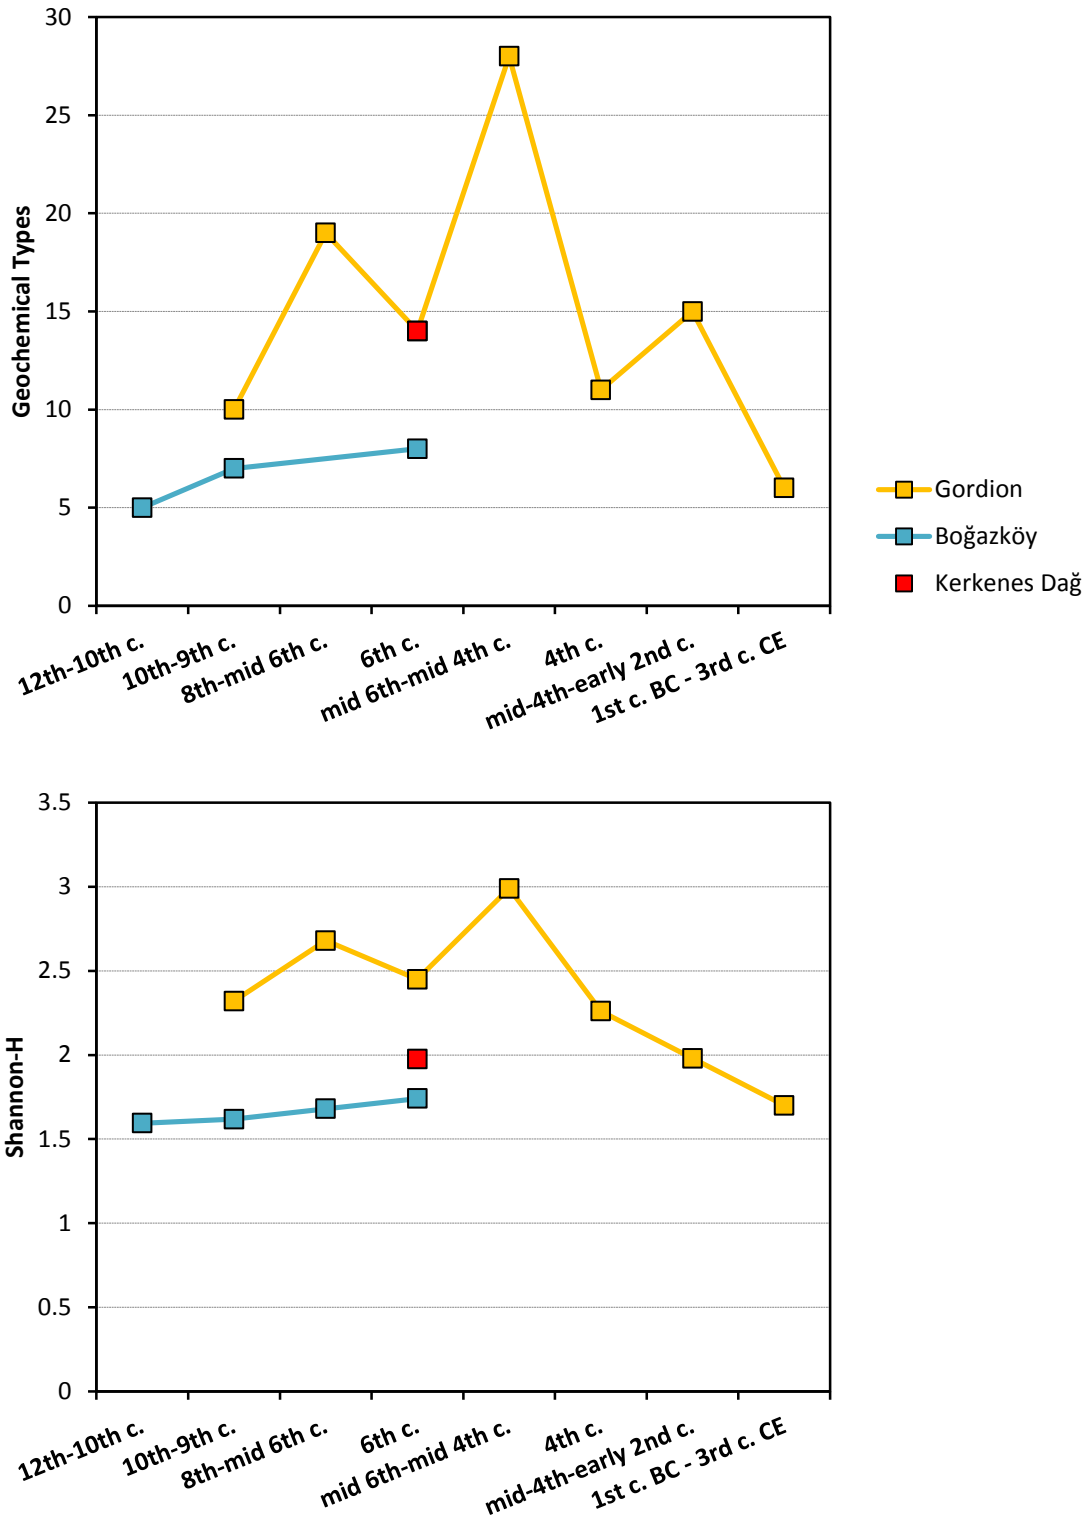


Figure 6.4: Diversity indices of geochemical groups of pottery from Gordion, Boğazköy, and Kerkenes Dağ through time (data from Grave, et al. 2009; Kealhofer, et al. 2009; Kealhofer, et al. 2010); (top) absolute geochemical type frequency, (bottom) Shannon-H diversity, correcting for sample size and evenness among the sample groups.

organization of political and economic activities. By delineating the locations of production activities, including acquisition, primary, and secondary production, it is clear that by the end of the 3rd millennium BC, labor specialization was widespread and geographically situated. Instead of workshops performing most activities, pronounced divisions of labor were supported by long-distance exchange. These labor divisions helped support the development of wealth finance strategies that were widely adopted by the time of the Old Assyrian trade. Part of the strategy of Hittite domination appears to have asserted control over these wealth financing strategies. Furthermore, in an effort to create territorial dominance, the Hittite state developed an elaborate staple financing strategy that served to simultaneously integrate agricultural zones and to finance large-scale military activities. This is also reflected in the compositional and isotopic profiles of analyzed objects in this study, which point towards a widespread and diverse copper technology that is unlike its counterparts elsewhere in the Near East and Aegean regions. After the decline of the Hittite state, smaller states reemerged once again with elites who attempted to dominate the region through control of long-distance trade in modified wealth finance system. Compositional and isotopic data demonstrate that the polity at Kerkenes Dağ was capable of acquiring resources from most major copper source areas in Anatolia, in addition to a single example of bronze that appears to match sources in the western Mediterranean. Yet despite the diversity of sources, copper technologies at Kerkenes Dağ are almost entirely limited to tin bronze technology, further suggesting that long-distance trade and wealth finance structured the political economy.

This work serves to demonstrate not only the interrelation of strategies of economic and political expansion but also how these strategies are reflected in changes in labor organization and trade. In north central Anatolia, which witnessed several periods of expansion, this is observed through proxies within the variations of copper metal technology and the

transformations evident in economic networks which supplied producers and consumers over time. During the Bronze Age, a proliferation of metal alloy and form types develops; however, this sociotechnic transformation appears to be dominated by a regional inter-Anatolian network of copper trade. During the Iron Age, metal alloy types decrease, but the network of copper commodity trade increases in size. This is further demonstrated by the near exclusive consumption of tin bronze, highlighting how the trade of foreign commodities into central Anatolia, and thereby large-scale cooperation within a craft economy, developed alongside the emergence of polities in the region.

APPENDIX A: OBJECT CONTEXTUAL DATA

Contextual data for each object, where available, are listed for each object and sample in the tables below. Each object has a unique inventory number, and in some cases, also a Mannheim number (MA- X) which refers to the lab inventory in use at the Curt-Engelhorn-Zentrum Archäometrie. Context from Boğazköy is described here in one of two ways. First, for earlier excavations including materials from P. Neve's excavations, contexts are described either in terms of location or are directly cited from published final excavation volumes. Objects from earlier excavations at Boğazköy have been published, and their descriptions and contexts are contained within excavation volumes. These include R. Boehmer's small finds volumes concerning excavations from 1952-1969 (1972) and excavations in the Lower City from 1970-1978 (1979). Contextual information of P. Neve's excavations in the Upper City, including excavations at the Temple Quarter, Südburg and Nişantepe, has also been graciously provided by S. Herbordt ahead of publication. Where contextual information was not available, representing only a very small fraction of the entire study, objects were designated a time period based on well-understood regional typology.

For later excavations at Boğazköy by Seeher and then Schachner, contexts were numerically coded and their detailed descriptions can be found in publication or within the project archives. Detailed information and access to select objects from excavations at Büyükkaya (1993-1998), the Northwest Slope of Büyükkale (1998-2000), the vicinity around the Eastern Reservoirs (1996-1998), and the Southern Reservoirs (2000-2001) were also courteously made available by Jürgen Seeher and Ayşe Baykal-Seeher (final publication of excavations at Büyükkaya and the Southern Reservoirs are forthcoming; Baykal-Seeher 2006; Seeher 2006b).

Objects from excavations in the western Upper City (2001-2009), including excavations in the Sarikale Valley, the Middle Plateau, and Yenicekale, were also made available by J. Seeher and A. Schachner. The final publication of these objects is forthcoming.

Objects from excavations at Kerkenes Dağ have their contexts coded within the object numbering format, where the trench (TR) and unit (U) numbers are provided. Given the understood development and short one period chronology at Kerkenes, we can assume all objects from this study date to sometime between the 7th-6th centuries BC.

| Mannheim Number | Object Number | Location | Object Type | Alloy type | Context (number or description) |
|--------------------------|---------------|-----------------------------------|----------------------|------------|---------------------------------|
| BOĞAZKÖY | | | | | |
| EARLY BRONZE AGE | | | | | |
| | Bo 96/38 | Büyükkaya | Pin, conical | Cu-As | 347/411.59 |
| | Bo 97/98 | Büyükkaya | Pin, nodular | Cu | 347/410.294 |
| | ETD 97/196 | Büyükkaya | Pin, indeterminate | Cu-As | 348/410.48 |
| | ETD 97/206 | Büyükkaya | Wire, round section | Cu-As | 347/410.194 |
| | ETD 97/213 | Büyükkaya | Awl | Cu-As | 348/310.44 |
| | ETD 97/219 | Büyükkaya | Pin, shaft fragment | Cu-As | 347/410.230 |
| | ETD 97/221 | Büyükkaya | Awl | Cu | 348/410.50 |
| | ETD 98/12 | Büyükkaya | Eye needle, fragment | Cu-As | 348/411.113 |
| MIDDLE BRONZE AGE | | | | | |
| MA-132227 | Bo 10/199 | Lower City - Kesikkaya, Northwest | Awl | Cu-As | 57 |
| MA-132259 | Bo 10/332 | Lower City - Kesikkaya, Northwest | Pin, lenticular | Cu-As | 74 |
| MA-132246 | Bo 10/341 | Lower City - Kesikkaya, Northwest | Awl | Cu-As | 74 |
| MA-132250 | Bo 10/482 | Lower City - Kesikkaya, Northwest | Indeterminate | Cu | 112 |
| MA-132303 | Bo 11/590 | Lower City - Kesikkaya, Northwest | Ingot, planoconvex | Cu | 71 |
| | Bo 13/445 | Lower City - Kesikkaya, Northwest | Pin, lamellar | Cu-As | 11 |
| | Bo 13/450 | Lower City - Kesikkaya, Northwest | Socketed pike | Cu | 31 |
| | Bo 13/458 | Lower City - Kesikkaya, Northwest | Pin, unique | Cu-As | 33 |
| | Bo 13/459 | Lower City - Kesikkaya, Northwest | Eye needle, fragment | Cu | 33 |
| | Bo 13/462 | Lower City - Kesikkaya, Northwest | Pin, disc | Cu-As | 33 |
| | Bo 13/463 | Lower City - Kesikkaya, Northwest | Eye needle, fragment | Cu | 33 |
| | Bo 13/564 | Lower City - Kesikkaya, Northwest | Pin, square | Cu-As | 43 |
| | Bo 13/569 | Lower City - Kesikkaya, Northwest | Socketed pike | Cu | 49 |
| | Bo 13/631 | Lower City - Kesikkaya, Northwest | Pin, nodular | Cu | 57 |

| Mannheim Number | Object Number | Location | Object Type | Alloy type | Context (number or description) |
|------------------------|-----------------------|-----------------------------------|------------------------|-------------------|--|
| | Bo 13/668 | Lower City - Kesikkaya, Northwest | Eye needle, fragment | Cu | 49 |
| | Bo 13/670 | Lower City - Kesikkaya, Northwest | Eye needle, fragment | Cu | 49 |
| MA-132546 | Bo 143/l | Lower City - Northern Quarter | Staff blade | Cu-As | Boehmer 1972: n. 59 |
| MA-132560 | Bo 345/h | Lower City - Northern Quarter | Staff blade | Cu-As | Boehmer 1972: n. 60 |
| MA-132557 | Bo 348/h | Lower City - Northern Quarter | Knife, flat and curved | Cu | Boehmer 1972: n. 256 |
| MA-132556 | Bo 311/s | Northwest Slope - Northwest Slope | Spearpoint | Cu-As | Boehmer 1972: n. 199 |
| MA-132558 | Bo 400/s | Northwest Slope - Northwest Slope | Staff blade | Cu-As | Boehmer 1972: n. 57 |
| LATE BRONZE AGE | | | | | |
| MA-132188 | Bo 284/e | Büyükkale | Belt sheet | Cu-As-Ni | Boehmer 1972: n. 179 |
| MA-132189 | Bo 284/e | Büyükkale | Belt sheet, gold wire | Au | Boehmer 1972: n. 179 |
| MA-132180 | Bo 477/d | Büyükkale | Shaft-hole axe | Cu-Sn-Pb | Boehmer 1972: n. 17 |
| MA-136322 | Boehmer 1972: Nr. 190 | Büyükkale | Ingot, planoconvex | Cu | Boehmer 1972: n. 190 |
| MA-132553 | Bo 254/k | Büyükkaya | Shaft-hole axe | Cu-As-Sn | Boehmer 1972: n. 18 |
| | Bo 92/225 | Büyükkale | Figurine | Cu-Sn | P/14 |
| | Bo 94/1 | Büyükkaya | Pin, lenticular | Cu-Ni | 355/430.54 |
| | Bo 94/109 | Büyükkaya | Pendant, lunulae | Cu-As-Ni | 356/432.38 |
| | Bo 94/113 | Büyükkaya | Pin, square | Cu-As | 355/428.17 |
| | Bo 94/116 | Büyükkaya | Awl | Cu-As | 355/428.94 |
| | Bo 94/14 | Büyükkaya | Pin, rolled | Cu-As | 354/430.9 |
| | Bo 94/141 | Büyükkaya | Arrowhead, lance-form | Cu | 357/431.67 |
| | Bo 94/20 | Büyükkaya | Pin, unique | Cu-As | 356/431.11 |
| | Bo 94/21 | Büyükkaya | Pin, double headed | Cu-Sn | 356/431.13 |
| | Bo 94/28 | Büyükkaya | Arrowhead, stemmed | Cu-Sn | 355/430.57 |
| | Bo 94/36 | Büyükkaya | Awl | Cu-As-Sn | 354/430.98 |
| | Bo 94/37 | Büyükkaya | Edged chisel | Cu-Sn | 354/430.90 |

| Mannheim Number | Object Number | Location | Object Type | Alloy type | Context (number or description) |
|------------------------|----------------------|-----------------|--------------------------|-------------------|--|
| | Bo 94/4 | Büyükkaya | Arrowhead, stemmed | Cu | 355/430.12 |
| | Bo 94/40 | Büyükkaya | Pin, fungiform | Cu-As-Pb | 355/430.175 |
| | Bo 94/57 | Büyükkaya | Pin, disc | Cu-Sn | 355/430.270 |
| | Bo 94/76 | Büyükkaya | Pin, disc | Cu-As | 354/430.146 |
| | Bo 94/9 | Büyükkaya | Pendant, lunulae | Cu | 355/430.49 |
| | Bo 95/100 | Büyükkaya | Rod | Cu-Sn | 352/427.122 |
| | Bo 95/111 | Büyükkaya | Spiral | Cu-Sn | 355/431.41 |
| | Bo 95/113 | Büyükkaya | Pin, incised disc | Cu-Ni | 355/427.104 |
| | Bo 95/119 | Büyükkaya | Pin, pyramidal | Cu-As-Sn | 354/427.110 |
| | Bo 95/25 | Büyükkaya | Flat axe, indeterminate | Cu-Sn | 354/427.44 |
| | Bo 95/27 | Büyükkaya | Pin, disc | Cu-As | 354/427.58 |
| | Bo 95/41 | Büyükkaya | Arrowhead, stemmed | Cu-Sn | 355/431.106 |
| | Bo 95/76 | Büyükkaya | Pin, incised disc | Cu | 355/427.61 |
| | Bo 95/80 | Büyükkaya | Indeterminate | Cu-As-Ni | 350/427.34 |
| | Bo 95/82 | Büyükkaya | Pin, disc | Cu | 352/427.96 |
| | Bo 95/95 | Büyükkaya | Flat axe, indeterminate | Cu-Sn | 353/422.43 |
| | Bo 96/120 | Büyükkaya | Winged axe | Cu-As-Sn | 347/410.139 |
| | Bo 96/34 | Büyükkaya | Pin, nodular | Cu-Sn | 356/427.114 |
| | Bo 96/36 | Büyükkaya | Spiral | Cu-Sn | 355/426.27 |
| | Bo 96/48 | Büyükkaya | Insert, axe-shaped | Cu-As-Sn | 354/421.122 |
| | Bo 97/101 | Büyükkaya | Pin, conical | Cu-As | 353/421.205 |
| | Bo 97/102 | Büyükkaya | Pendant, decorated sheet | Cu-Ni | 345-7/413-5.65 |
| | Bo 97/16 | Büyükkaya | Figurine | Cu-Sn | 352/420.502 |
| | Bo 97/18 | Büyükkaya | Awl | Cu-As | 348/411.36 |
| | Bo 97/19 | Büyükkaya | Awl | Cu-As | 353/421.254 |
| | Bo 97/23 | Büyükkaya | Pin, fungiform | Cu-As | 348/410.15 |

| Mannheim Number | Object Number | Location | Object Type | Alloy type | Context (number or description) |
|------------------------|----------------------|-----------------|------------------------|-------------------|--|
| | Bo 97/24 | Büyükkaya | Awl | Cu-As | 348/411.54 |
| | Bo 97/27 | Büyükkaya | Pin, lamellar | Cu-As | 348/411.66 |
| | Bo 97/33 | Büyükkaya | Pin, lamellar disc | Cu-Ni | 345-7/413-5.245 |
| | Bo 97/37 | Büyükkaya | Pin, nodular | Cu | 348/411.41 |
| | Bo 98/13 | Büyükkaya | Staff blade | Cu | 348/410.165 |
| | ETD 94/127 | Büyükkaya | Eye needle, fragment | Cu-Ni | 356/431.25 |
| | ETD 94/191 | Büyükkaya | Pin, rolled | Cu-Sn | 356/431.44 |
| | ETD 94/192 | Büyükkaya | Bead | Cu | 356/431.41 |
| | ETD 94/198 | Büyükkaya | Eye needle, fragment | Cu-As | 357/431.26 |
| | ETD 94/215 | Büyükkaya | Ring, wire | Cu-Ni | 357/431.29 |
| | ETD 94/217 | Büyükkaya | Eye needle, fragment | Cu-Ni | 354/430.101 |
| | ETD 94/234 | Büyükkaya | Pin, shaft fragment | Cu-As | 355/430.214 |
| | ETD 94/246 | Büyükkaya | Awl | Cu-As | 356/431.56 |
| | ETD 94/248 | Büyükkaya | Eye needle | Cu | 356/431.65 |
| | ETD 94/263 | Büyükkaya | Edged chisel | Cu | 357/431.26 |
| | ETD 94/356 | Büyükkaya | Arrowhead, stemmed | Cu-Sn | 354-355/430.170 |
| | ETD 94/4 | Büyükkaya | Wire, round section | Cu-As-Sn | 355/430.10 |
| | ETD 94/460 | Büyükkaya | Pendant, indeterminate | Cu-Sn | 356/431.153 |
| | ETD 94/471 | Büyükkaya | Awl | Cu-Sn | 357/431.46 |
| | ETD 94/479a | Büyükkaya | Awl | Cu-As | 354/430.159 |
| | ETD 94/479b | Büyükkaya | Indeterminate | Cu-Sn | 354/430.159 |
| | ETD 94/481 | Büyükkaya | Pin, shaft fragment | Cu-As | 356/431.69 |
| | ETD 94/482 | Büyükkaya | Awl | Cu-As | 355/431.69 |
| | ETD 94/486 | Büyükkaya | Awl | Cu | 355/430.265 |
| | ETD 94/6 | Büyükkaya | Awl | Cu-Sn | 355/430.10 |
| | ETD 94/7 | Büyükkaya | Awl | Cu-As | 355/430.10 |

| Mannheim Number | Object Number | Location | Object Type | Alloy type | Context (number or description) |
|------------------------|----------------------|-----------------|--------------------------|-------------------|--|
| | ETD 95/212a | Büyükkaya | Awl | Cu-As-Sn | 355/427.100 |
| | ETD 95/212b | Büyükkaya | Eye needle, fragment | Cu-Sn | 355/427.100 |
| | ETD 95/228A | Büyükkaya | Wire, round section | Cu-As | 350/427.67 |
| | ETD 95/228B | Büyükkaya | Awl | Cu-Sn | 350/427.67 |
| | ETD 95/228C | Büyükkaya | Awl | Cu-Sn | 350/427.67 |
| | ETD 95/228D | Büyükkaya | Awl | Cu | 350/427.67 |
| MA-136329 | ETD 95/231 | Büyükkaya | Sheet ring | Cu-Ni | 352/427-428.83 |
| | ETD 95/232 | Büyükkaya | Eye needle, fragment | Cu-As | 355/427.165 |
| | ETD 95/262 | Büyükkaya | Awl | Cu-As-Sn | 355/427.103 |
| | ETD 95/269 | Büyükkaya | Pin, lenticular | Cu | 356/430.170 |
| | ETD 95/272 | Büyükkaya | Awl | Cu-Sn | 395/432.54 |
| | ETD 95/283 | Büyükkaya | Pin, conical | Cu-As | 355/427.149 |
| | ETD 95/284A | Büyükkaya | Pendant, decorated sheet | Cu-Ni | 355/432.52 |
| | ETD 95/284B | Büyükkaya | Pendant, decorated sheet | Cu-Sn | 355/432.52 |
| | ETD 95/83 | Büyükkaya | Pin, lamellar disc | Cu-As | 357/431.155 |
| | ETD 96/32 | Büyükkaya | Arrowhead, stemmed | Cu | 354/421.48 |
| | ETD 96/33 | Büyükkaya | Awl | Cu | 359/428.6 |
| | ETD 96/34 | Büyükkaya | Pin, nodular | Cu | 355/427.135 |
| | ETD 96/35 | Büyükkaya | Pin, shaft fragment | Cu-Sn | 359/428.14 |
| | ETD 96/36 | Büyükkaya | Awl | Cu-As | 356/427.54 |
| | ETD 96/37 | Büyükkaya | Awl | Cu | 347/410.6 |
| | ETD 96/41 | Büyükkaya | Awl | Cu | 359/428.16 |
| | ETD 96/42 | Büyükkaya | Awl | Cu | 355/427.184 |
| | ETD 96/43 | Büyükkaya | Awl | Cu-As-Sn | 359/429.5 |
| | ETD 96/45 | Büyükkaya | Arrowhead, indeterminate | Cu-As | 356/427.209 |
| | ETD 96/54 | Büyükkaya | Rod | Cu | 359/428.8 |

| Mannheim Number | Object Number | Location | Object Type | Alloy type | Context (number or description) |
|------------------------|----------------------|-----------------|-------------------------------|-------------------|--|
| | ETD 96/62 | Büyükkaya | Awl | Cu | 344/301.38 |
| | ETD 97/212 | Büyükkaya | Awl | Cu-As | 359/426.41 |
| | ETD 97/218 | Büyükkaya | Awl | Cu-As | 348/411.35 |
| | ETD 97/229 | Büyükkaya | Rod | Cu-As | 353/421.180 |
| | ETD 97/233 | Büyükkaya | Awl | Cu-As | 354/421.180 |
| | ETD 97/240 | Büyükkaya | Awl | Cu-As | 352/420.86 |
| | ETD 97/241 | Büyükkaya | Pin, shaft fragment | Cu-As | 348/410.27 |
| | ETD 97/242 | Büyükkaya | Insert, hammer-shaped | Cu-Sn | 345/413.40 |
| | ETD 97/243 | Büyükkaya | Awl | Cu | 358/426.5 |
| | ETD 97/246 | Büyükkaya | Arrowhead, sheet | Cu | 352/420.419 |
| | ETD 97/251 | Büyükkaya | Axe or hatchet, indeterminate | Cu-Sn | 353/421.194 |
| | ETD 97/255 | Büyükkaya | Pin, incised lamellar disc | Cu-As | 347/427.14 |
| | ETD 97/256 | Büyükkaya | Awl | Cu-As | 345/413.83 |
| | ETD 97/257 | Büyükkaya | Awl | Cu-As | 347/412.2 |
| | ETD 97/268 | Büyükkaya | Awl | Cu-As | 347/415.P3 |
| | ETD 98/06 | Büyükkaya | Eye needle | Cu-Sn | 353/420.347 |
| | ETD 98/07 | Büyükkaya | Tube, sheet | Cu-Sn-Ni | 305/346.10 |
| | ETD 98/09 | Büyükkaya | Tool, indeterminate | Cu-As | 346/414.663 |
| | ETD 98/11 | Büyükkaya | Eye needle, fragment | Cu | 349/410.158 |
| | ETD 98/13 | Büyükkaya | Eye needle, fragment | Cu | 345/414.335 |
| | ETD 98/16 | Büyükkaya | Tool, indeterminate | Cu-As | 348/410.108 |
| | ETD 98/18 | Büyükkaya | Pin, lenticular | Cu | 346/413.736 |
| MA-136321 | ETD 98/21 | Büyükkaya | Pendant, indeterminate | Cu-As | 348/410.164 |
| | ETD 98/22 | Büyükkaya | Awl | Cu | 343/414.436 |
| | ETD 98/23 | Büyükkaya | Edged chisel | Cu-As | 346/413.638 |
| | ETD 99/88 | Granary | Awl | Cu-Sn-Pb | 309/341.25 |

| Mannheim Number | Object Number | Location | Object Type | Alloy type | Context (number or description) |
|------------------------|----------------------|-----------------------------------|----------------------|-------------------|--|
| | Bo 13/125 | Lower City - City Wall | Pin, disc | Cu-As-Sn | 0 |
| | Bo 13/655 | Lower City - City Wall | Edged chisel | Cu | 0 |
| | Bo 13/803 | Lower City - City Wall | Indeterminate | Cu-Sn | 380 |
| | Bo 09/780 | Lower City - Kesikkaya, Northwest | Pin, nodular | Cu-Pb | 381 |
| | Bo 09/1057 | Lower City - Kesikkaya, Northwest | Pin, lamellar | Cu | 615 |
| | Bo 09/1063 | Lower City - Kesikkaya, Northwest | Awl | Cu | 604 |
| | Bo 09/1074 | Lower City - Kesikkaya, Northwest | Pin, shaft fragment | Cu | 611 |
| MA-136336 | Bo 09/1095 | Lower City - Kesikkaya, Northwest | Indeterminate | Cu | 630 |
| | Bo 09/1131 | Lower City - Kesikkaya, Northwest | Knife, indeterminate | Cu | 1130 |
| | Bo 09/1177 | Lower City - Kesikkaya, Northwest | Pin, shaft fragment | Cu | 1128 |
| | Bo 09/118 | Lower City - Kesikkaya, Northwest | Pin, shaft fragment | Cu-Sn | 115 |
| | Bo 09/121 | Lower City - Kesikkaya, Northwest | Pin, lenticular | Cu | 66 |
| | Bo 09/125 | Lower City - Kesikkaya, Northwest | Wire, round section | Cu-As | 55 |
| | Bo 09/140 | Lower City - Kesikkaya, Northwest | Pin, shaft fragment | Cu | 69 |
| | Bo 09/148 | Lower City - Kesikkaya, Northwest | Ring, wire | Cu-As | 81 |
| | Bo 09/150 | Lower City - Kesikkaya, Northwest | Eye needle | Cu | 81 |
| | Bo 09/156 | Lower City - Kesikkaya, Northwest | Edged chisel | Cu-Sn | 71 |
| | Bo 09/194 | Lower City - Kesikkaya, Northwest | Eye needle, fragment | Cu-As | 91 |
| | Bo 09/198 | Lower City - Kesikkaya, Northwest | Indeterminate | Cu-As | 103 |
| | Bo 09/211 | Lower City - Kesikkaya, Northwest | Wire, round section | Cu | 115 |
| | Bo 09/212 | Lower City - Kesikkaya, Northwest | Eye needle, fragment | Cu-Sn | 115 |
| | Bo 09/274 | Lower City - Kesikkaya, Northwest | Wire, round section | Cu-As | 128 |
| | Bo 09/278 | Lower City - Kesikkaya, Northwest | Eye needle, fragment | Cu-Sn | 128 |
| | Bo 09/282 | Lower City - Kesikkaya, Northwest | Awl | Cu-Sn | 130 |
| | Bo 09/283 | Lower City - Kesikkaya, Northwest | Ring, wire | Cu-As | 128 |
| | Bo 09/284 | Lower City - Kesikkaya, Northwest | Arrowhead, stemmed | Cu | 127 |

| Mannheim Number | Object Number | Location | Object Type | Alloy type | Context (number or description) |
|------------------------|----------------------|-----------------------------------|-----------------------|-------------------|--|
| | Bo 09/285 | Lower City - Kesikkaya, Northwest | Eye needle | Cu | 127 |
| | Bo 09/293 | Lower City - Kesikkaya, Northwest | Awl | Cu | 127 |
| | Bo 09/298 | Lower City - Kesikkaya, Northwest | Pin, nodular | Cu-As | 131 |
| | Bo 09/321 | Lower City - Kesikkaya, Northwest | Arrowhead, lance-form | Cu | 142 |
| | Bo 09/322 | Lower City - Kesikkaya, Northwest | Awl | Cu-As | 141 |
| | Bo 09/324 | Lower City - Kesikkaya, Northwest | Ring, wire | Cu | 141 |
| | Bo 09/325 | Lower City - Kesikkaya, Northwest | Pin, lenticular | Cu-Sn | 142 |
| | Bo 09/351 | Lower City - Kesikkaya, Northwest | Pin, disc | Cu-Sn | 144 |
| MA-136326 | Bo 09/355 | Lower City - Kesikkaya, Northwest | Pin, lenticular | Cu-Ni | 144 |
| | Bo 09/376 | Lower City - Kesikkaya, Northwest | Eye needle, fragment | Cu | 154 |
| | Bo 09/377 | Lower City - Kesikkaya, Northwest | Eye needle, fragment | Cu | 154 |
| | Bo 09/378 | Lower City - Kesikkaya, Northwest | Pin, incised disc | Cu-As | 154 |
| | Bo 09/398 | Lower City - Kesikkaya, Northwest | Awl | Cu-As | 157 |
| | Bo 09/400 | Lower City - Kesikkaya, Northwest | Pin, shaft fragment | Cu | 159 |
| | Bo 09/404 | Lower City - Kesikkaya, Northwest | Eye needle | Cu-Sn | 159 |
| | Bo 09/405 | Lower City - Kesikkaya, Northwest | Pin, conical | Cu-As | 160 |
| | Bo 09/420 | Lower City - Kesikkaya, Northwest | Pin, shaft fragment | Cu | 165 |
| | Bo 09/457 | Lower City - Kesikkaya, Northwest | Awl | Cu-As | 178 |
| | Bo 09/461 | Lower City - Kesikkaya, Northwest | Eye needle | Cu | 175 |
| | Bo 09/484 | Lower City - Kesikkaya, Northwest | Pin, lamellar | Cu-As | 193 |
| | Bo 09/499 | Lower City - Kesikkaya, Northwest | Edged chisel | Cu-As-Sn | 204 |
| | Bo 09/503 | Lower City - Kesikkaya, Northwest | Knife, indeterminate | Cu | 301 |
| | Bo 09/504 | Lower City - Kesikkaya, Northwest | Edged chisel | Cu-Sn | 301 |
| | Bo 09/511 | Lower City - Kesikkaya, Northwest | Pin, shaft fragment | Cu-Ni | 301 |
| | Bo 09/53 | Lower City - Kesikkaya, Northwest | Sheet, indeterminate | Cu | 20 |
| | Bo 09/583 | Lower City - Kesikkaya, Northwest | Pin, lenticular | Cu-As | 331 |

| Mannheim Number | Object Number | Location | Object Type | Alloy type | Context (number or description) |
|------------------------|----------------------|-----------------------------------|----------------------|-------------------|--|
| | Bo 09/656 | Lower City - Kesikkaya, Northwest | Pin, nodular | Cu-As | 352 |
| | Bo 09/660 | Lower City - Kesikkaya, Northwest | Sheet, indeterminate | Cu-As | 353 |
| | Bo 09/686 | Lower City - Kesikkaya, Northwest | Arrowhead, stemmed | Cu-Sn | 361 |
| | Bo 09/687 | Lower City - Kesikkaya, Northwest | Pin, disc | Cu-As-Sn | 361 |
| | Bo 09/699 | Lower City - Kesikkaya, Northwest | Pin, disc | Cu-As | 354 |
| | Bo 09/715 | Lower City - Kesikkaya, Northwest | Pin, pyramidal | Cu-As-Sn | 362 |
| | Bo 09/775 | Lower City - Kesikkaya, Northwest | Edged chisel | Cu | 390 |
| | Bo 09/797 | Lower City - Kesikkaya, Northwest | Pin, shaft fragment | Cu-Ni | 404 |
| | Bo 09/803 | Lower City - Kesikkaya, Northwest | Eye needle, fragment | Cu | 407 |
| | Bo 09/811 | Lower City - Kesikkaya, Northwest | Pin, lenticular | Cu-As-Sn | 403 |
| | Bo 09/827 | Lower City - Kesikkaya, Northwest | Pin, shaft fragment | Cu-Pb | 507 |
| | Bo 09/835 | Lower City - Kesikkaya, Northwest | Eye needle | Cu | 511 |
| | Bo 09/880 | Lower City - Kesikkaya, Northwest | Eye needle | Cu | 532 |
| MA-136338 | Bo 09/972 | Lower City - Kesikkaya, Northwest | Pin, rolled | Cu-Ni | 591 |
| | Bo 09/991 | Lower City - Kesikkaya, Northwest | Eye needle, fragment | Cu | 598 |
| MA-132213 | Bo 10/13 | Lower City - Kesikkaya, Northwest | Awl | Cu-As | 1 |
| MA-132244 | Bo 10/186 | Lower City - Kesikkaya, Northwest | Sheet, indeterminate | Cu-As | 47 |
| MA-132267 | Bo 10/189 | Lower City - Kesikkaya, Northwest | Pin, indeterminate | Cu-Sn | 53 |
| MA-132232 | Bo 10/190 | Lower City - Kesikkaya, Northwest | Eye needle | Cu-As | 47 |
| MA-132209 | Bo 10/20 | Lower City - Kesikkaya, Northwest | Awl | Cu-As-Sn | 6 |
| MA-132229 | Bo 10/233 | Lower City - Kesikkaya, Northwest | Awl | Cu-As | 69 |
| MA-132230 | Bo 10/236 | Lower City - Kesikkaya, Northwest | Awl | Cu-Sn | 69 |
| MA-132219 | Bo 10/238 | Lower City - Kesikkaya, Northwest | Pin, incised disc | Cu-As | 68 |
| MA-132211 | Bo 10/24 | Lower City - Kesikkaya, Northwest | Edged chisel | Cu-Sn | 0 |
| MA-132231 | Bo 10/242 | Lower City - Kesikkaya, Northwest | Eye needle | Cu-As | 68 |
| MA-132220 | Bo 10/243 | Lower City - Kesikkaya, Northwest | Pin, disc | Cu | 69 |

| Mannheim Number | Object Number | Location | Object Type | Alloy type | Context (number or description) |
|------------------------|----------------------|-----------------------------------|--------------------------|-------------------|--|
| MA-132242 | Bo 10/244 | Lower City - Kesikkaya, Northwest | Pin, disc | Cu | 69 |
| MA-132241 | Bo 10/249 | Lower City - Kesikkaya, Northwest | Pin, square | Cu | 68 |
| MA-132266 | Bo 10/250 | Lower City - Kesikkaya, Northwest | Pin, indeterminate | Cu-As-Sn | 68 |
| MA-132240 | Bo 10/251 | Lower City - Kesikkaya, Northwest | Pin, conical | Cu-As | 68 |
| MA-132245 | Bo 10/254 | Lower City - Kesikkaya, Northwest | Indeterminate | Cu | 67 |
| MA-132239 | Bo 10/257 | Lower City - Kesikkaya, Northwest | Arrowhead, indeterminate | Cu | 99 |
| MA-132238 | Bo 10/282 | Lower City - Kesikkaya, Northwest | Edged chisel | Cu-As | 73 |
| MA-132237 | Bo 10/287 | Lower City - Kesikkaya, Northwest | Pin, shaft fragment | Cu-As | 78 |
| MA-132235 | Bo 10/305 | Lower City - Kesikkaya, Northwest | Pin, shaft fragment | Cu | 83 |
| MA-132236 | Bo 10/307 | Lower City - Kesikkaya, Northwest | Pin, shaft fragment | Cu | 83 |
| MA-132233 | Bo 10/323 | Lower City - Kesikkaya, Northwest | Eye needle, fragment | Cu-As | 177 |
| MA-132234 | Bo 10/343 | Lower City - Kesikkaya, Northwest | Knife, indeterminate | Cu-As | 64 |
| MA-132224 | Bo 10/37 | Lower City - Kesikkaya, Northwest | Eye needle, fragment | Cu-Ni | 8 |
| MA-132268 | Bo 10/372 | Lower City - Kesikkaya, Northwest | Eye needle | Cu | 92 |
| MA-132226 | Bo 10/38 | Lower City - Kesikkaya, Northwest | Ring, wire | Cu-As | 8 |
| MA-132269 | Bo 10/389 | Lower City - Kesikkaya, Northwest | Pin, indeterminate | Cu | 89 |
| MA-132247 | Bo 10/391 | Lower City - Kesikkaya, Northwest | Pin, indeterminate | Cu-As | 89 |
| MA-132248 | Bo 10/392 | Lower City - Kesikkaya, Northwest | Pin, indeterminate | Cu-As | 89 |
| MA-132270 | Bo 10/393 | Lower City - Kesikkaya, Northwest | Awl | Cu-Sn | 89 |
| MA-132264 | Bo 10/394 | Lower City - Kesikkaya, Northwest | Pin, indeterminate | Cu-As | 89 |
| MA-132249 | Bo 10/402 | Lower City - Kesikkaya, Northwest | Waste, casting | Cu | 89 |
| MA-132272 | Bo 10/404 | Lower City - Kesikkaya, Northwest | Eye needle | Cu-As | 89 |
| MA-132271 | Bo 10/416 | Lower City - Kesikkaya, Northwest | Indeterminate | Cu-As-Ni | 87 |
| MA-132251 | Bo 10/456 | Lower City - Kesikkaya, Northwest | Pin, indeterminate | Cu-As | 99 |
| | Bo 10/492 | Lower City - Kesikkaya, Northwest | Pin, disc | Cu | 99 |
| MA-132260 | Bo 10/496 | Lower City - Kesikkaya, Northwest | Indeterminate | Cu-Sn | 107 |

| Mannheim Number | Object Number | Location | Object Type | Alloy type | Context (number or description) |
|------------------------|----------------------|-----------------------------------|----------------------------|-------------------|--|
| MA-132223 | Bo 10/53 | Lower City - Kesikkaya, Northwest | Tube, sheet | Cu-Sn-Pb | 13 |
| MA-132208 | Bo 10/59 | Lower City - Kesikkaya, Northwest | Pin, indeterminate | Cu-As | 15 |
| MA-132214 | Bo 10/64 | Lower City - Kesikkaya, Northwest | Indeterminate | Cu-As-Pb | 15 |
| MA-132228 | Bo 10/843 | Lower City - Kesikkaya, Northwest | Pin, shaft fragment | Cu-As-Sn | 520 |
| MA-132276 | Bo 10/846 | Lower City - Kesikkaya, Northwest | Indeterminate | Cu-Sn-Zn | 523 |
| MA-132252 | Bo 10/853 | Lower City - Kesikkaya, Northwest | Pin, indeterminate | Cu-Sn | 509 |
| MA-132280 | Bo 10/893 | Lower City - Kesikkaya, Northwest | Edged chisel | Cu-As-Sn | 545 |
| MA-132221 | Bo 10/904 | Lower City - Kesikkaya, Northwest | Pin, lenticular | Cu-As | 552 |
| MA-132279 | Bo 10/928 | Lower City - Kesikkaya, Northwest | Edged chisel | Cu | 555 |
| MA-132215 | Bo 10/935 | Lower City - Kesikkaya, Northwest | Full-handled dagger | Cu-As | 563 |
| MA-132217 | Bo 10/935 | Lower City - Kesikkaya, Northwest | Full-handled dagger, rivet | Cu-As | 563 |
| MA-132295 | Bo 11/492 | Lower City - Kesikkaya, Northwest | Arrowhead, stemmed | Cu-As | 54 |
| MA-132296 | Bo 11/502 | Lower City - Kesikkaya, Northwest | Pin, indeterminate | Cu-As | 56 |
| MA-132292 | Bo 11/522 | Lower City - Kesikkaya, Northwest | Awl | Cu-As | |
| MA-132297 | Bo 11/527 | Lower City - Kesikkaya, Northwest | Indeterminate | Cu-As | 59 |
| | Bo 11/535 | Lower City - Kesikkaya, Northwest | Wire, round section | Cu | |
| MA-132290 | Bo 11/591 | Lower City - Kesikkaya, Northwest | Nail | Cu-As | 64 |
| | Bo 12/06 | Lower City - Kesikkaya, Northwest | Edged chisel | Cu-As-Sn | |
| | Bo 13/304 | Lower City - Kesikkaya, Northwest | Awl | Cu-Sn | 0 |
| | Bo 13/305 | Lower City - Kesikkaya, Northwest | Sheet, indeterminate | Cu | 0 |
| | Bo 13/327 | Lower City - Kesikkaya, Northwest | Awl | Cu-As-Sn | 4 |
| | Bo 13/328 | Lower City - Kesikkaya, Northwest | Eye needle, fragment | Cu | 4 |
| | Bo 13/340 | Lower City - Kesikkaya, Northwest | Edged chisel | Cu-As | 6 |
| | Bo 13/342 | Lower City - Kesikkaya, Northwest | Spiral | Cu-As | 7 |
| | Bo 13/344 | Lower City - Kesikkaya, Northwest | Edged chisel | Cu-As | 7 |
| | Bo 13/346 | Lower City - Kesikkaya, Northwest | Pin, lamellar | Cu-Sn | 7 |

| Mannheim Number | Object Number | Location | Object Type | Alloy type | Context (number or description) |
|------------------------|----------------------|-----------------------------------|--------------------------|-------------------|--|
| | Bo 13/351 | Lower City - Kesikkaya, Northwest | Ring, wire | Cu-Sn-Pb | 6 |
| | Bo 13/363 | Lower City - Kesikkaya, Northwest | Eye needle | Cu-As | 8 |
| | Bo 13/364 | Lower City - Kesikkaya, Northwest | Indeterminate | Cu | 7 |
| | Bo 13/377 | Lower City - Kesikkaya, Northwest | Arrowhead, indeterminate | Cu | 13 |
| | Bo 13/381 | Lower City - Kesikkaya, Northwest | Flat axe, indeterminate | Cu-Sn | 14 |
| | Bo 13/382 | Lower City - Kesikkaya, Northwest | Indeterminate | Cu | 8 |
| | Bo 13/388 | Lower City - Kesikkaya, Northwest | Knife, indeterminate | Cu-As | 8 |
| | Bo 13/392 | Lower City - Kesikkaya, Northwest | Eye needle, fragment | Cu-As | 8 |
| | Bo 13/393 | Lower City - Kesikkaya, Northwest | Pin, lenticular | Cu-As-Sn | 16 |
| | Bo 13/396 | Lower City - Kesikkaya, Northwest | Eye needle | Cu-As | 15 |
| | Bo 13/398 | Lower City - Kesikkaya, Northwest | Eye needle, fragment | Cu-As-Sn | 16 |
| | Bo 13/403 | Lower City - Kesikkaya, Northwest | Ring, wire | Cu-Sn | 16 |
| | Bo 13/413 | Lower City - Kesikkaya, Northwest | Pin, indeterminate | Cu-Ni | 18 |
| | Bo 13/418 | Lower City - Kesikkaya, Northwest | Indeterminate | Cu | 15 |
| | Bo 13/419 | Lower City - Kesikkaya, Northwest | Pin, shaft fragment | Cu-As | 15 |
| | Bo 13/421 | Lower City - Kesikkaya, Northwest | Eye needle, fragment | Cu-As | 0 |
| | Bo 13/425 | Lower City - Kesikkaya, Northwest | Edged chisel | Cu-As | 18 |
| | Bo 13/426 | Lower City - Kesikkaya, Northwest | Indeterminate | Cu | 18 |
| | Bo 13/449 | Lower City - Kesikkaya, Northwest | Eye needle, fragment | Cu | 0 |
| | Bo 13/466 | Lower City - Kesikkaya, Northwest | Eye needle, fragment | Cu-As | 32 |
| | Bo 13/471 | Lower City - Kesikkaya, Northwest | Ring, wire | Cu | 32 |
| | Bo 13/472 | Lower City - Kesikkaya, Northwest | Ring, wire | Cu | Bo10.99 |
| | Bo 13/473 | Lower City - Kesikkaya, Northwest | Eye needle, fragment | Cu | 30 |
| | Bo 13/476 | Lower City - Kesikkaya, Northwest | Pin, pyramidal | Cu-As | 35 |
| | Bo 13/479 | Lower City - Kesikkaya, Northwest | Indeterminate | Cu | 30 |
| | Bo 13/488 | Lower City - Kesikkaya, Northwest | Indeterminate | Cu | 38 |

| Mannheim Number | Object Number | Location | Object Type | Alloy type | Context (number or description) |
|------------------------|----------------------|-----------------------------------|----------------------|-------------------|--|
| | Bo 13/492 | Lower City - Kesikkaya, Northwest | Pin, disc | Cu-As | 99 |
| | Bo 13/499 | Lower City - Kesikkaya, Northwest | Eye needle, fragment | Cu-As | 0 |
| | Bo 13/500 | Lower City - Kesikkaya, Northwest | Eye needle | Cu-As | 38 |
| | Bo 13/520 | Lower City - Kesikkaya, Northwest | Eye needle, fragment | Cu | 41 |
| | Bo 13/527 | Lower City - Kesikkaya, Northwest | Indeterminate | Cu | 59 |
| | Bo 13/529 | Lower City - Kesikkaya, Northwest | Pin, square | Cu-As | 41 |
| | Bo 13/535 | Lower City - Kesikkaya, Northwest | Eye needle, fragment | Cu-As | 40 |
| | Bo 13/538 | Lower City - Kesikkaya, Northwest | Pin, square | Cu-As | 41 |
| | Bo 13/543 | Lower City - Kesikkaya, Northwest | Indeterminate | Cu | 20 |
| | Bo 13/548 | Lower City - Kesikkaya, Northwest | Eye needle, fragment | Cu | 42 |
| | Bo 13/568 | Lower City - Kesikkaya, Northwest | Eye needle, fragment | Cu-As | 43 |
| | Bo 13/573 | Lower City - Kesikkaya, Northwest | Pin, shaft fragment | Cu-As | 52 |
| | Bo 13/585 | Lower City - Kesikkaya, Northwest | Eye needle | Cu-As | 70 |
| | Bo 13/586 | Lower City - Kesikkaya, Northwest | Pin, pyramidal | Cu-As | 56 |
| | Bo 13/587 | Lower City - Kesikkaya, Northwest | Awl | Cu-Sn | 55 |
| | Bo 13/589 | Lower City - Kesikkaya, Northwest | Pin, pyramidal | Cu-As | 43 |
| | Bo 13/591 | Lower City - Kesikkaya, Northwest | Awl | Cu-As | 64 |
| | Bo 13/592 | Lower City - Kesikkaya, Northwest | Eye needle | Cu | 43 |
| | Bo 13/595 | Lower City - Kesikkaya, Northwest | Eye needle | Cu | 71 |
| | Bo 13/606 | Lower City - Kesikkaya, Northwest | Indeterminate | Cu | 59 |
| | Bo 13/610 | Lower City - Kesikkaya, Northwest | Waste, casting | Cu-As | |
| | Bo 13/618 | Lower City - Kesikkaya, Northwest | Sheet, indeterminate | Cu-As-Sn | 70 |
| | Bo 13/620 | Lower City - Kesikkaya, Northwest | Awl | Cu-As-Pb | 5 |
| | Bo 13/622 | Lower City - Kesikkaya, Northwest | Ring, wire | Cu-Sn | 60 |
| | Bo 13/622? | Lower City - Kesikkaya, Northwest | Eye needle | Cu | 74 |
| | Bo 13/623 | Lower City - Kesikkaya, Northwest | Sheet, indeterminate | Cu-Sn | 60 |

| Mannheim Number | Object Number | Location | Object Type | Alloy type | Context (number or description) |
|------------------------|----------------------|--------------------------------------|----------------------|-------------------|--|
| | Bo 13/624 | Lower City - Kesikkaya, Northwest | Pin, shaft fragment | Cu-As | 43 |
| | Bo 13/625 | Lower City - Kesikkaya, Northwest | Pin, shaft fragment | Cu-As-Sn-Pb | 43 |
| | Bo 13/626 | Lower City - Kesikkaya, Northwest | Eye needle | Cu-As | 43 |
| | Bo 13/628 | Lower City - Kesikkaya, Northwest | Indeterminate | Cu-Sn | 60 |
| | Bo 13/632 | Lower City - Kesikkaya, Northwest | Pin, square | Cu-As | 43 |
| | Bo 13/633 | Lower City - Kesikkaya, Northwest | Edged chisel | Cu-As | 0 |
| | Bo 13/639 | Lower City - Kesikkaya, Northwest | Eye needle | Cu-As | 43 |
| | Bo 13/642 | Lower City - Kesikkaya, Northwest | Eye needle, fragment | Cu | 43 |
| | Bo 13/643 | Lower City - Kesikkaya, Northwest | Pin, pyramidal | Cu | 43 |
| | Bo 13/646 | Lower City - Kesikkaya, Northwest | Sheet, indeterminate | Cu | 43 |
| | Bo 13/648 | Lower City - Kesikkaya, Northwest | Indeterminate | Cu | 67 |
| | Bo 13/659 | Lower City - Kesikkaya, Northwest | Eye needle, fragment | Cu | 0 |
| | Bo 13/664 | Lower City - Kesikkaya, Northwest | Pin, fungiform | Cu-As | 0 |
| | Bo 13/677 | Lower City - Kesikkaya, Northwest | Indeterminate | Cu-Ni | 8 |
| | Bo 13/678 | Lower City - Kesikkaya, Northwest | Indeterminate | Cu | 6 |
| | Bo 13/679 | Lower City - Kesikkaya, Northwest | Indeterminate | Cu-Ni | 6 |
| | Bo 13/680 | Lower City - Kesikkaya, Northwest | Indeterminate | Cu-As | 16 |
| | Bo 13/681 | Lower City - Kesikkaya, Northwest | Pin, shaft fragment | Cu | 20 |
| MA-132210 | Bo 10/1512 | Lower City - Kesikkaya, Posternmauer | Pin, shaft fragment | Cu-As-Sn | 304 |
| MA-132207 | Bo 10/507 | Lower City - Kesikkaya, Posternmauer | Pin, shaft fragment | Cu | 301 |
| MA-132212 | Bo 10/544 | Lower City - Kesikkaya, Posternmauer | Edged chisel | Cu-As-Sn | 310 |
| MA-132222 | Bo 10/554 | Lower City - Kesikkaya, Posternmauer | Eye needle, fragment | Cu-As | 530 |
| MA-132273 | Bo 10/558 | Lower City - Kesikkaya, Posternmauer | Pin, nodular | Cu-As | 331 |
| MA-132263 | Bo 10/566 | Lower City - Kesikkaya, Posternmauer | Pin, indeterminate | Cu-As | 314 |
| MA-132274 | Bo 10/574 | Lower City - Kesikkaya, Posternmauer | Pin, shaft fragment | Cu | 336 |
| MA-132298 | Bo 11/909 | Lower City - Kesikkaya, Posternmauer | Nail | Cu | 603 |

| Mannheim Number | Object Number | Location | Object Type | Alloy type | Context (number or description) |
|------------------------|----------------------|--------------------------------------|--------------------------------|-------------------|--|
| | Bo 13/588 | Lower City - Kesikkaya, Postermmauer | Pin, pyramidal | Cu-As-Pb | 56 |
| MA-132253 | Bo 10/1232 | Lower City - Kesikkaya, South | Pin, indeterminate | Cu-As-Sn | 723 |
| MA-132243 | Bo 10/1234 | Lower City - Kesikkaya, South | Eye needle, fragment | Cu | 723 |
| MA-132277 | Bo 10/1277 | Lower City - Kesikkaya, South | Eye needle | Cu-As | 746 |
| MA-132254 | Bo 10/1282 | Lower City - Kesikkaya, South | Pin, indeterminate | Cu-As | 752 |
| MA-132255 | Bo 10/1283 | Lower City - Kesikkaya, South | Indeterminate | Cu-Sn | 750 |
| MA-132258 | Bo 10/1291 | Lower City - Kesikkaya, South | Hook | Cu-As-Sn | 757 |
| MA-132257 | Bo 10/1292 | Lower City - Kesikkaya, South | Eye needle, fragment | Cu-As | 738 |
| MA-132261 | Bo 10/1294 | Lower City - Kesikkaya, South | Edged chisel | Cu-As-Sn | 738 |
| MA-132262 | Bo 10/1295 | Lower City - Kesikkaya, South | Pin, indeterminate | Cu-As | 738 |
| MA-132256 | Bo 10/1297 | Lower City - Kesikkaya, South | Pin, shaft fragment | Cu-As-Sn | 758 |
| MA-132278 | Bo 10/1302 | Lower City - Kesikkaya, South | Pin, rolled | Cu-As | 758 |
| MA-132284 | Bo 11/15 | Lower City - Kesikkaya, South | Pin, pyramidal | Cu-As | 603 |
| MA-132294 | Bo 11/18 | Lower City - Kesikkaya, South | Nail | Cu | 605 |
| MA-132286 | Bo 11/4 | Lower City - Kesikkaya, South | Pin, square | Cu-As | 303 |
| MA-132293 | Bo 11/42 | Lower City - Kesikkaya, South | Indeterminate | Cu-Sn | 311 |
| MA-132289 | Bo 11/65 | Lower City - Kesikkaya, South | Nail | Cu-As | 338 |
| | Bo 11/8 | Lower City - Kesikkaya, South | Pin, disc | Cu | 307 |
| | Bo 13/101 | Lower City - Kesikkaya, South | Pin, shaft fragment | Cu-As | 331 |
| | Bo 13/116 | Lower City - Kesikkaya, South | Wire, round section | Cu | 338 |
| | Bo 13/122 | Lower City - Kesikkaya, South | Arrowhead, lance-form | Cu-As | 338 |
| | Bo 13/135 | Lower City - Kesikkaya, South | Arrowhead, stemmed and spurred | Cu-As | 342 |
| | Bo 13/177 | Lower City - Kesikkaya, South | Pin, shaft fragment | Cu-Sn | 357 |
| | Bo 13/18 | Lower City - Kesikkaya, South | Awl | Cu-As | 306 |
| | Bo 13/204 | Lower City - Kesikkaya, South | Awl | Cu-Sn | 353 |
| | Bo 13/238 | Lower City - Kesikkaya, South | Awl | Cu-As | 367 |

| Mannheim Number | Object Number | Location | Object Type | Alloy type | Context (number or description) |
|------------------------|----------------------|---------------------------------|--------------------------------|-------------------|---|
| MA-136341 | Bo 13/39 | Lower City - Kesikkaya, South | Pin, lamellar | Cu-As-Ni | 323 |
| | Bo 13/61 | Lower City - Kesikkaya, South | Indeterminate | Cu | 0 |
| | Bo 13/64 | Lower City - Kesikkaya, South | Awl | Cu | 316 |
| | Bo 13/76 | Lower City - Kesikkaya, South | Indeterminate | Cu | 323 |
| | Bo 13/82 | Lower City - Kesikkaya, South | Edged chisel | Cu | 304 |
| MA-132185 | Bo 170/h | Lower City - Northern Quarter | Flat axe, lugged | Cu-As | Boehmer 1972: n. 24 |
| MA-132183 | Bo 171/h | Lower City - Northern Quarter | Flat axe, indeterminate | Cu-Sn | Boehmer 1972: n. 25 |
| MA-132187 | Bo 173/h | Lower City - Northern Quarter | Arrowhead, lance-form | Cu-As | Boehmer 1972: n. 203 |
| MA-132190 | Bo 216/p | Lower City - Northern Quarter | Figurine | Cu-As-Pb | Boehmer 1972: n. 170 |
| | Bo 503/o | Lower City - Northern Quarter | Sheet, decorated | Cu-Ni | Boehmer 1972: n. 169 |
| | Bo 73/141 | Lower City - Northern Quarter | Arrowhead, stemmed and spurred | Cu-As-Sn | J/20-I/1, foundation pit of the robbed out wall. |
| | Bo 73/167 | Lower City - Northern Quarter | Full-handled dagger | Cu | J/19-I/10, from debris under the stone rubble over the wall of House 11 |
| | Bo 74/7 | Lower City - Northern Quarter | Arrowhead, lance-form | Cu-As | J/20 ridge between II/2 and II/2-NW |
| | Bo 77/146 | Lower City - Northern Quarter | Saw | Cu | K/20-II/3, House/basin 43, under the stone rubble over the floor, directly in front of the SW-wall of the basin |
| MA-132173 | Bo 77/385a | Lower City - Northern Quarter | Figurine | Cu-As | K/20-IV/3 north, in the northeastern pithos wall. terraced house adjacent to Temple 1 |
| MA-132172 | Bo 77/385b | Lower City - Northern Quarter | Figurine | Cu | K/20-IV/3 north, in the northeastern pithos wall. terraced house adjacent to Temple 1 |
| MA-132184 | Bo 91/h | Lower City - Northern Quarter | Staff blade | Cu-As-Sn | Boehmer 1972: n. 64 |
| MA-132186 | Bo 95/h | Lower City - Northern Quarter | Arrowhead, lance-form | Cu-As | Boehmer 1972: n. 828 |
| MA-132218 | Bo 10/1409 | Lower City - Temple 1 Magazines | Edged chisel | Cu-As | 907 |
| MA-132265 | Bo 10/1425 | Lower City - Temple 1 Magazines | Edged chisel | Cu-As | 914 |
| MA-132288 | Bo 11/1203 | Lower City - Temple 1 Magazines | Arrowhead, stemmed and spurred | Cu | 904 |
| MA-132283 | Bo 11/1205 | Lower City - Temple 1 Magazines | Eye needle, fragment | Cu | 904 |
| MA-132282 | Bo 11/1215 | Lower City - Temple 1 Magazines | Arrowhead, sheet | Cu-As | 908 |
| MA-132291 | Bo 11/1223 | Lower City - Temple 1 Magazines | Awl | Cu | 912 |

| Mannheim Number | Object Number | Location | Object Type | Alloy type | Context (number or description) |
|------------------------|----------------------|---------------------------|----------------------|-------------------|--|
| | ETD 99/54 | Northwest Slope - Granary | Sheet, indeterminate | Cu-Ni | 310/343.16 |
| | ETD 99/55 | Northwest Slope - Granary | Awl | Cu | 309/343.52 |
| | ETD 99/57 | Northwest Slope - Granary | Awl | Cu-Ni | 309/343.103 |
| | ETD 99/58 | Northwest Slope - Granary | Eye needle | Cu | 308/343.16 |
| | ETD 99/59 | Northwest Slope - Granary | Awl | Cu-Sn | 309/344.145 |
| | ETD 99/60 | Northwest Slope - Granary | Wire, round section | Cu | 309/343.34 |
| | ETD 99/67 | Northwest Slope - Granary | Eye needle, fragment | Cu-As | 308/343.68 |
| | ETD 99/68 | Northwest Slope - Granary | Wire, round section | Cu | 311/342.8 |
| | ETD 99/69 | Northwest Slope - Granary | Eye needle, fragment | Cu | 309/343.180 |
| | ETD 99/70 | Northwest Slope - Granary | Pin, shaft fragment | Cu-As | 310/343.45 |
| | ETD 99/71 | Northwest Slope - Granary | Awl | Cu-As | 309/343.36 |
| | ETD 99/73 | Northwest Slope - Granary | Awl | Cu-As-Sn | 309/343.16 |
| | ETD 99/75 | Northwest Slope - Granary | Sheet, indeterminate | Cu-Ni | 311/342.14 |
| | ETD 99/76 | Northwest Slope - Granary | Eye needle, fragment | Cu-As | 309/343.225 |
| | ETD 99/80 | Northwest Slope - Granary | Wire, round section | Cu-As-Sn | 311/342.30 |
| | ETD 99/81 | Northwest Slope - Granary | Indeterminate | Cu-As-Sn | 311/342.2 |
| | ETD 99/82 | Northwest Slope - Granary | Indeterminate | Cu-As | 311/342.2 |
| | ETD 99/83 | Northwest Slope - Granary | Awl | Cu-As-Sn | 311/342.2 |
| | ETD 99/85 | Northwest Slope - Granary | Pin, shaft fragment | Cu-Sn | 311/342.2 |
| | ETD 99/86 | Northwest Slope - Granary | Awl | Cu-As | 311/342.23 |
| | ETD 99/87 | Northwest Slope - Granary | Awl | Cu-As | 309/341.28 |
| | ETD 99/89 | Northwest Slope - Granary | Wire, round section | Cu | 308/346.26 |
| | ETD 99/90 | Northwest Slope - Granary | Wire, round section | Cu-Sn | 308/346.26 |
| | ETD 99/92 | Northwest Slope - Granary | Eye needle, fragment | Cu | 308/346.48 |
| | ETD 99/93 | Northwest Slope - Granary | Arrowhead, stemmed | Cu-As | 308/344.11 |
| | ETD 99/94 | Northwest Slope - Granary | Eye needle, fragment | Cu | 311/342.50 |

| Mannheim Number | Object Number | Location | Object Type | Alloy type | Context (number or description) |
|------------------------|----------------------|-----------------------------------|------------------------|-------------------|---|
| | ETD 99/95 | Northwest Slope - Granary | Eye needle, fragment | Cu-Ni | 311/342.54 |
| | ETD 99/96 | Northwest Slope - Granary | Awl | Cu-As-Sn | 311/342.42 |
| | Bo 07/2742 | Northwest Slope - Middle Plateau | Eye needle, fragment | Cu-As-Pb | 1578 |
| MA-132179 | Bo 645/t | Northwest Slope - Northwest Slope | Knife, flat and curved | Cu-As-Sn | Boehmer 1972: n. 258 |
| | ETD 96/39 | Upper City - East reservoirs | Awl | Cu | 344/300.28 |
| | ETD 96/44 | Upper City - East reservoirs | Awl | Cu | 346/303.40 |
| | ETD 96/47 | Upper City - East reservoirs | Eye needle | Cu-As | 244/301.34 |
| | ETD 96/50 | Upper City - East reservoirs | Insert, hammer-shaped | Cu-Sn | 344/308.6 |
| | ETD 96/51 | Upper City - East reservoirs | Ring, wire | Cu-As-Sn | 344/303.6 |
| | ETD 96/53 | Upper City - East reservoirs | Sheet, indeterminate | Cu-Ni | 344/301.33 |
| | ETD 96/59 | Upper City - East reservoirs | Eye needle | Cu | 342/299.12 |
| | ETD 96/61 | Upper City - East reservoirs | Awl | Cu-As-Sn | 342/299.21 |
| MA-136337 | Dowel_1 | Upper City - King's Gate | Dowel | Cu-As | Sample taken in situ from the dowel fastening two cut cyclopean blocks of the interior jamb of the southern gate tower (described in Puchstein 1912: 67). |
| | 10-1-92 | Upper City – near to Lion's Gate | Sword | Cu-Sn | Neve 1993: 648-652, Ünal et al. 1992 |
| | Bo 91/2414 | Upper City - Nişantepe | Shaft-hole axe | Cu-Sn | M/12-a/2 (NW) |
| | ETD 00/10 | Upper City - South reservoirs | Wire, round section | Cu-As-Sn | 293/255.3 |
| | ETD 00/11 | Upper City - South reservoirs | Eye needle, fragment | Cu-As | 298/252.21 |
| | ETD 00/16 | Upper City - South reservoirs | Sheet, indeterminate | Cu-Sn | 298/252.12 |
| | ETD 00/17 | Upper City - South reservoirs | Waste, casting | Cu-Sn | 292/256.5 |
| | ETD 00/6 | Upper City - South reservoirs | Pin, unique | Cu-Sn | 295/254.6 |
| | ETD 00/7 | Upper City - South reservoirs | Eye needle, fragment | Cu-As | 295/254.13 |
| | ETD 00/8 | Upper City - South reservoirs | Wire, round section | Cu-Ni | 298/252.10 |
| | ETD 00/9 | Upper City - South reservoirs | Eye needle, fragment | Cu-As-Sn | 298/253.20 |
| | ETD 98/15 | Upper City - South reservoirs | Wire, round section | Cu-Ni | 305/346.22 |
| | Bo 89/41 | Upper City - Südburg | Figurine | Cu-Sn-Pb | N/21-g/1, northwestern section of the Südburg, in |

| Mannheim Number | Object Number | Location | Object Type | Alloy type | Context (number or description) |
|------------------------|----------------------|-----------------------------|--------------------------------|-------------------|---|
| | Bo 78/113 | Upper City - Temple quarter | Stylus | Cu-Sn | rubble with fired brick over the western wall of the Hittite West House. Temple 6, Room 30a |
| MA-132196 | Bo 79/206 | Upper City - Temple quarter | Ingot, oxhide | Cu | House 2; L7-g/5 south, located immediately in front of the inside of the northern wall of the "Uraikellers" 40cm below the surface and stone collapse (Müller-Karpe, in Neve 1980: 301,303-304; Stos-Gale, et al. 1997: 111, n. TU174). |
| | Bo 81/8 | Upper City - Temple quarter | Pin, conical | Cu-Sn | |
| MA-132563 | Bo 82/102 | Upper City - Temple quarter | Armor plate | Cu-Sn | Temple 7, Room 25 |
| MA-132562 | Bo 82/103 | Upper City - Temple quarter | Armor plate | Cu-Sn | Temple 7, Room 8 |
| MA-132301 | Bo 82/109a | Upper City - Temple quarter | Arrowhead, stemmed | Cu | Temple 7, Room 24 |
| MA-132534 | Bo 82/109b | Upper City - Temple quarter | Arrowhead, stemmed | Cu | Temple 7, Room 24 |
| MA-132176 | Bo 82/112 | Upper City - Temple quarter | Armor plate | Cu-Sn | Temple 7, Room 25 |
| MA-132182 | Bo 82/138 | Upper City - Temple quarter | Flat axe, lugged | Cu-Sn | Temple 7, Room 9 |
| MA-132565 | Bo 82/139 | Upper City - Temple Quarter | Sickle | Cu-As-Sn-Pb | Temple 7 |
| MA-132175 | Bo 82/140 | Upper City - Temple quarter | Armor plate | Cu-Sn | Temple 7, Room 9 |
| MA-132181 | Bo 82/141 | Upper City - Temple quarter | Knife, flat and curved | Cu-As-Sn | Temple 7, Room 9 |
| | Bo 82/148 | Upper City - Temple quarter | Sickle | Cu | Temple 7, Room 9 |
| | Bo 83/220 | Upper City - Temple quarter | Pin, rolled | Cu-Sn | Temple 9 |
| | Bo 83/310 | Upper City - Temple quarter | Pin, rolled | Cu-Sn | Temple 9, Room 27 |
| | Bo 83/442 | Upper City - Temple quarter | Arrowhead, lance-form | Cu-As | Temple 11 |
| | Bo 83/444 | Upper City - Temple quarter | Arrowhead, lance-form | Cu-As | Temple 9, Room 27 |
| | Bo 83/450 | Upper City - Temple quarter | Full-handled dagger | Cu | Temple 9, Room 27 |
| MA-132578 | Bo 83/580 | Upper City - Temple quarter | Arrowhead, lance-form | Cu-Sn | Temple 12 |
| MA-132582 | Bo 83/712 | Upper City - Temple quarter | Arrowhead, stemmed | Cu-Sn | Temple 12 |
| MA-136323 | Bo 83/819 | Upper City - Temple quarter | Ingot, planoconvex | Cu | Temple 7 |
| | Bo 83/889 | Upper City - Temple quarter | Arrowhead, stemmed and spurred | Cu-Sn | Temple 12 |

| Mannheim Number | Object Number | Location | Object Type | Alloy type | Context (number or description) |
|------------------------|--------------------------------------|-----------------------------|--------------------------------|-------------------|--|
| | Bo 84/22 | Upper City - Temple quarter | Figurine | Cu-Sn | Temple 8 |
| | Bo 84/341 | Upper City - Temple quarter | Pin, conical | Cu-Sn | M/8-h/3 |
| | Bo 84/531 | Upper City - Temple quarter | Stylus | Cu-Sn | Temple 8 |
| MA-132178 | Bo 84/551 | Upper City - Temple quarter | Wrapped socket axe | Cu-Sn | Temple 5 |
| | Bo 84/563 | Upper City - Temple quarter | Figurine | Cu-Sn | Temple 4 |
| | Bo 85/117 | Upper City - Temple quarter | Pin, incised disc | Cu-Ni | M/8-b/8 |
| | Bo 85/144 | Upper City - Temple quarter | Edged chisel | Cu-Sn | Temple 20 |
| | Bo 85/153 | Upper City - Temple quarter | Pin, rolled | Cu-Sn | House 21, Room 12 |
| MA-132299 | Bo 85/449 | Upper City - Temple quarter | Flat axe, indeterminate | Cu-Sn | |
| | Bo 85/515 | Upper City - Temple quarter | Arrowhead, lance-form | Cu | Temple 26 |
| MA-132300 | Bo 85/71 | Upper City - Temple quarter | Indeterminate | Cu-Sn | |
| MA-132587 | Bo 86/101 | Upper City - Temple quarter | Arrowhead, stemmed and spurred | Cu-As-Sn | M/7-a/10 |
| | Bo 86/168 | Upper City - Temple quarter | Armor plate | Cu-Sn | House 26 |
| | Bo 86/282 | Upper City - Temple quarter | Arrowhead, lance-form | Cu-As-Sn | House 26 |
| MA-132586 | Bo 86/321 | Upper City - Temple quarter | Arrowhead, stemmed and spurred | Cu | House 26 |
| | Bo 86/411 | Upper City - Temple quarter | Hook | Cu-Sn | M/7-g/9 |
| MA-136343 | Bo 86/427 | Upper City - Temple quarter | Armor plate | Cu-Ni | House 34, Room 3 |
| | Bo 86/431 | Upper City - Temple quarter | Eye needle | Cu-As | M/6-f/1 |
| MA-132177 | Bo 86/94 | Upper City - Temple quarter | Wrapped socket axe | Cu-Sn | House 31 |
| | Herbordt Kat ify-39 (12); Bo 82-214b | Upper City - Temple quarter | Armor plate | Cu-Sn | Temple 9, Room 1 |
| | Herbordt Kat ify-39 (14); Bo 82-314a | Upper City - Temple quarter | Armor plate | Cu-Sn | Temple 9, Room 1 |
| | Herbordt Kat ify-39 (15); Bo 82-314a | Upper City - Temple quarter | Armor plate | Cu-Sn | Temple 9, Room 1 |
| | Herbordt Kat ify-39 (16); Bo 82-214a | Upper City - Temple quarter | Armor plate | Cu-As-Sn | Temple 9, Room 1 |
| | Herbordt Kat ify-39 (2); Bo 82-214b | Upper City - Temple quarter | Armor plate | Cu-Sn | Temple 9, Room 1 |

| Mannheim Number | Object Number | Location | Object Type | Alloy type | Context (number or description) |
|------------------------|--------------------------------------|-----------------------------|--------------------|-------------------|--|
| | Herbordt Kat ify-39 (20); Bo 82-314a | Upper City - Temple Quarter | Armor plate | Cu-Sn | Temple 9, Room 1 |
| | Herbordt Kat ify-39 (22); Bo 82-314a | Upper City - Temple quarter | Armor plate | Cu-Sn | Temple 9, Room 1 |
| | Herbordt Kat ify-39 (23); Bo 82-214b | Upper City - Temple quarter | Armor plate | Cu-Sn | Temple 9, Room 1 |
| | Herbordt Kat ify-39 (24); Bo 82-314a | Upper City - Temple quarter | Armor plate | Cu-Sn | Temple 9, Room 1 |
| | Herbordt kat ify-39 (25); Bo 82-314a | Upper City - Temple quarter | Armor plate | Cu-Sn | Temple 9, Room 1 |
| | Herbordt Kat ify-39 (26); Bo 82-314a | Upper City - Temple quarter | Armor plate | Cu-Sn | Temple 9, Room 1 |
| | Herbordt Kat ify-39 (27); Bo 82-314a | Upper City - Temple quarter | Armor plate | Cu-Sn | Temple 9, Room 1 |
| | Herbordt Kat ify-39 (28); Bo 82-314a | Upper City - Temple quarter | Armor plate | Cu-As-Sn | Temple 9, Room 1 |
| | Herbordt Kat ify-39 (29); Bo 82-314a | Upper City - Temple quarter | Armor plate | Cu-Sn | Temple 9, Room 1 |
| | Herbordt Kat ify-39 (3); Bo 82-314a | Upper City - Temple quarter | Armor plate | Cu-Sn | Temple 9, Room 1 |
| | Herbordt Kat ify-39 (32); Bo 82-314a | Upper City - Temple quarter | Armor plate | Cu-Sn | Temple 9, Room 1 |
| | Herbordt Kat ify-39 (35); Bo 82-214b | Upper City - Temple quarter | Armor plate | Cu-Sn | Temple 9, Room 1 |
| | Herbordt Kat ify-39 (36); Bo 82-314a | Upper City - Temple quarter | Armor plate | Cu-Sn | Temple 9, Room 1 |
| | Herbordt Kat ify-39 (39); Bo 82-314a | Upper City - Temple quarter | Armor plate | Cu-Sn | Temple 9, Room 1 |
| | Herbordt Kat ify-39 (4); Bo 82-314a | Upper City - Temple quarter | Armor plate | Cu-Sn | Temple 9, Room 1 |
| | Herbordt Kat ify-39 (41); Bo 82-314a | Upper City - Temple quarter | Armor plate | Cu-Sn | Temple 9, Room 1 |
| | Herbordt Kat ify-39 (42); Bo 82-314a | Upper City - Temple quarter | Armor plate | Cu-Sn | Temple 9, Room 1 |
| | Herbordt kat ify-39 (43); Bo 82-314a | Upper City - Temple quarter | Armor plate | Cu-Sn | Temple 9, Room 1 |
| | Herbordt Kat ify-39 (44); Bo 82-314a | Upper City - Temple quarter | Armor plate | Cu-Sn | Temple 9, Room 1 |

| Mannheim Number | Object Number | Location | Object Type | Alloy type | Context (number or description) |
|------------------------|--------------------------------------|----------------------------------|--------------------------------|-------------------|--|
| | Herbordt Kat ify-39 (45); Bo 82-314a | Upper City - Temple quarter | Armor plate | Cu-Sn | Temple 9, Room 1 |
| | Herbordt Kat ify-39 (51); Bo 82-314a | Upper City - Temple quarter | Armor plate | Cu-Sn | Temple 9, Room 1 |
| | Herbordt Kat ify-39 (6); Bo 82-314a | Upper City - Temple quarter | Armor plate | Cu-Sn | Temple 9, Room 1 |
| | Herbordt Kat ify-39 (7); Bo 82-314a | Upper City - Temple quarter | Armor plate | Cu-As-Sn | Temple 9, Room 1 |
| | Herbordt Kat ify-39 (8); Bo 82-314a | Upper City - Temple quarter | Armor plate | Cu-Sn | Temple 9, Room 1 |
| | scale 9 | Upper City - Temple quarter | Armor plate | Cu-Sn | Inventory ID not preserved, probably part of the cache of armor plates discovered in Temple 9, Room 1. |
| | Bo 82/19 | Upper City - Yerkapı | Pin, lamellar | Cu-Sn | found in the debris over the lower stair section on the eastern slope of Yerkapı. |
| MA-132308 | Bo 06/1058 | Upper City West - Middle Plateau | Pin, incised disc | Cu-As-Ni | 521 |
| | Bo 06/1115 | Upper City West - Middle Plateau | Arrowhead, indeterminate | Cu-Sn | 533 |
| | Bo 06/1133 | Upper City West - Middle Plateau | Pin, shaft fragment | Cu-Sn | 549 |
| MA-132323 | Bo 06/1141 | Upper City West - Middle Plateau | Arrowhead, stemmed and spurred | Cu-As-Sn | 543 |
| MA-132408 | Bo 06/1148 | Upper City West - Middle Plateau | Pin, incised disc | Cu-As | 546 |
| | Bo 07/2668 | Upper City West - Middle Plateau | Eye needle | Cu | 1543 |
| | Bo 07/2685 | Upper City West - Middle Plateau | Awl | Cu-Sn | 1521 |
| | Bo 07/2690 | Upper City West - Middle Plateau | Pin, conical | Cu-Sn | 1552 |
| | Bo 07/2691 | Upper City West - Middle Plateau | Rod | Cu-As | 1552 |
| | Bo 07/2748 | Upper City West - Middle Plateau | Pin, conical | Cu-As-Sn | 1582 |
| | Bo 07/2819 | Upper City West - Middle Plateau | Eye needle, fragment | Cu | 1595 |
| MA-136342 | Bo 08/1510 | Upper City West - Middle Plateau | Pin, incised disc | Cu-Ni | 1503 |
| | Bo 08/1544 | Upper City West - Middle Plateau | Pin, shaft fragment | Cu | 1516 |
| | Bo 08/358 | Upper City West - Middle Plateau | Pin, lenticular | Cu | 153 |
| | Bo 08/359 | Upper City West - Middle Plateau | Pin, rolled | Cu-As-Sn | 153 |
| | Bo 08/393 | Upper City West - Middle Plateau | Wire, round section | Cu-Sn | 172 |

| Mannheim Number | Object Number | Location | Object Type | Alloy type | Context (number or description) |
|------------------------|----------------------|-----------------------------------|--------------------------------|-------------------|--|
| | Bo 08/403 | Upper City West - Middle Plateau | Awl | Cu-Sn | 15 |
| | Bo 08/415 | Upper City West - Middle Plateau | Pin, shaft fragment | Cu-As | 177 |
| | Bo 08/826 | Upper City West - Middle Plateau | Awl | Cu | 807 |
| | Bo 08/892 | Upper City West - Middle Plateau | Eye needle | Cu | 811 |
| | Bo 08/914 | Upper City West - Middle Plateau | Edged chisel | Cu-As | 0 |
| | Bo 08/931 | Upper City West - Middle Plateau | Awl | Cu | 843 |
| | Bo 08/934 | Upper City West - Middle Plateau | Ornament | Cu | 848 |
| | Bo 08/952 | Upper City West - Middle Plateau | Pin, lenticular | Cu-As | 853 |
| | Bo 09/54 | Upper City West - Middle Plateau | Eye needle | Cu-As | 0 |
| | Bo 09/64 | Upper City West - Middle Plateau | Wire, round section | Cu-Sn | 24 |
| | Bo 09/73 | Upper City West - Middle Plateau | Insert, hammer-shaped | Cu-As-Sn | 29 |
| | Bo 02/39 | Upper City West - Sarikale Valley | Arrowhead, stemmed and spurred | Cu-Sn | found on the floor context of a structure in 292/309 |
| | Bo 02/41 | Upper City West - Sarikale Valley | Arrowhead, lance-form | Cu | 292/309.60 |
| | Bo 02/45 | Upper City West - Sarikale Valley | Shouldered axe | Cu-As-Sn | 292/304.107 |
| | Bo 02/49 | Upper City West - Sarikale Valley | Knife, flat and straight | Cu | 292/309.67 |
| | Bo 02/50 | Upper City West - Sarikale Valley | Indeterminate | Cu | 292/308.72 |
| | Bo 02/55 | Upper City West - Sarikale Valley | Knife, flat and curved | Cu | found on the floor context of a structure in 292/309 |
| | Bo 03/21 | Upper City West - Sarikale Valley | Arrowhead, lance-form | Cu | 291/309.61 |
| | Bo 03/41 | Upper City West - Sarikale Valley | Insert, axe-shaped | Cu-Sn | 291/305.79 |
| | Bo 04/30 | Upper City West - Sarikale Valley | Arrowhead, stemmed | Cu-As-Sn | 293/305.71 |
| | Bo 04/32 | Upper City West - Sarikale Valley | Arrowhead, lance-form | Cu | 293/307.118 |
| | Bo 04/34 | Upper City West - Sarikale Valley | Awl | Cu-As | 293/306.210 |
| | Bo 05/13 | Upper City West - Sarikale Valley | Seal | Cu, composite | 293/305.293; Herbordt 2006: 184. |
| | Bo 05/21 | Upper City West - Sarikale Valley | Arrowhead, indeterminate | Cu | |
| | Bo 05/23 | Upper City West - Sarikale Valley | Arrowhead, indeterminate | Cu | |
| | Bo 05/25 | Upper City West - Sarikale Valley | Knife, flat and straight | Cu-As | 293/306.290 |

| Mannheim Number | Object Number | Location | Object Type | Alloy type | Context (number or description) |
|------------------------|----------------------|-----------------------------------|--------------------------|-------------------|--|
| | Bo 05/29 | Upper City West - Sarikale Valley | Stylus | Cu-Sn | 293/305.252 |
| | Bo 05/30 | Upper City West - Sarikale Valley | Indeterminate | Cu-As-Sn | 294/306.97 |
| | Bo 05/31 | Upper City West - Sarikale Valley | Indeterminate | Cu-Sn | |
| | Bo 05/33 | Upper City West - Sarikale Valley | Pin, rolled | Cu-As-Sn | |
| | Bo 05/34 | Upper City West - Sarikale Valley | Pin, rolled | Cu-As | |
| | Bo 05/36 | Upper City West - Sarikale Valley | Pin, conical | Cu-As-Sn | |
| | Bo 05/38 | Upper City West - Sarikale Valley | Pin, disc | Cu-As | |
| | Bo 05/51 | Upper City West - Sarikale Valley | Knife, indeterminate | Cu-As-Sn | |
| MA-132461 | Bo 06/1018 | Upper City West - Sarikale Valley | Indeterminate | Cu-As | 230 |
| | Bo 06/1039 | Upper City West - Sarikale Valley | Awl | Cu-Sn | 230 |
| MA-132359 | Bo 06/106 | Upper City West - Sarikale Valley | Indeterminate | Cu-As-Pb | 21 |
| MA-132343 | Bo 06/108 | Upper City West - Sarikale Valley | Pendant, decorated sheet | Cu-Ni | 31 |
| MA-132433 | Bo 06/124 | Upper City West - Sarikale Valley | Pin, conical | Cu | 22 |
| MA-132339 | Bo 06/127 | Upper City West - Sarikale Valley | Indeterminate | Cu-Sn | 22 |
| MA-132387 | Bo 06/1302 | Upper City West - Sarikale Valley | Pin, indeterminate | Cu-As | 703 |
| MA-132428 | Bo 06/1342 | Upper City West - Sarikale Valley | Indeterminate | Cu-Sn | 712 |
| MA-132533 | Bo 06/1359 | Upper City West - Sarikale Valley | Eye needle | Cu | 724 |
| MA-132385 | Bo 06/1364 | Upper City West - Sarikale Valley | Indeterminate | Cu-As | 724 |
| MA-132529 | Bo 06/137 | Upper City West - Sarikale Valley | Sheet, indeterminate | Cu-As | 42 |
| MA-132532 | Bo 06/1378 | Upper City West - Sarikale Valley | Tweezers | Cu-As | 730 |
| | Bo 06/1387 | Upper City West - Sarikale Valley | Pin, lenticular | Cu-As | 729 |
| MA-132328 | Bo 06/1395 | Upper City West - Sarikale Valley | Pin, lenticular | Cu-As | 736 |
| MA-132306 | Bo 06/1397 | Upper City West - Sarikale Valley | Indeterminate | Cu-As | 729 |
| MA-132464 | Bo 06/1399 | Upper City West - Sarikale Valley | Indeterminate | Cu-As | 734 |
| MA-132334 | Bo 06/1439 | Upper City West - Sarikale Valley | Pin, fungiform | Cu-As | 752 |
| MA-132379 | Bo 06/1440 | Upper City West - Sarikale Valley | Eye needle, fragment | Cu | 752 |

| Mannheim Number | Object Number | Location | Object Type | Alloy type | Context (number or description) |
|------------------------|----------------------|-----------------------------------|-----------------------|-------------------|--|
| MA-132450 | Bo 06/1446 | Upper City West - Sarikale Valley | Eye needle, fragment | Cu-As-Pb | 752 |
| MA-132327 | Bo 06/1449 | Upper City West - Sarikale Valley | Eye needle, fragment | Cu | 752 |
| MA-132369 | Bo 06/1458 | Upper City West - Sarikale Valley | Eye needle | Cu-As | 756 |
| MA-132386 | Bo 06/1464 | Upper City West - Sarikale Valley | Eye needle | Cu-As | 756 |
| MA-132522 | Bo 06/1465 | Upper City West - Sarikale Valley | Pin, incised disc | Cu-As | 756 |
| MA-132316 | Bo 06/1469 | Upper City West - Sarikale Valley | Pin, lenticular | Cu | 760 |
| MA-132331 | Bo 06/1481 | Upper City West - Sarikale Valley | Ring, wire | Cu-As-Sn | 1481 |
| MA-132456 | Bo 06/1483 | Upper City West - Sarikale Valley | Eye needle, fragment | Cu-As | 751 |
| MA-132442 | Bo 06/1497 | Upper City West - Sarikale Valley | Indeterminate | Cu-As-Pb | 756 |
| MA-132384 | Bo 06/1500 | Upper City West - Sarikale Valley | Ring, wire | Cu | 756 |
| MA-132449 | Bo 06/1506 | Upper City West - Sarikale Valley | Eye needle, fragment | Cu | 195 |
| MA-132366 | Bo 06/1508 | Upper City West - Sarikale Valley | Pin, disc | Cu-Sn | 184 |
| MA-132319 | Bo 06/1512 | Upper City West - Sarikale Valley | Indeterminate | Cu-Sn | 198 |
| MA-132392 | Bo 06/1513 | Upper City West - Sarikale Valley | Armor plate | Cu-Sn | 196 |
| MA-132397 | Bo 06/153 | Upper City West - Sarikale Valley | Indeterminate | Cu-As | 24 |
| MA-132312 | Bo 06/156 | Upper City West - Sarikale Valley | Pin, indeterminate | Cu-Ni | 25 |
| MA-132500 | Bo 06/1563 | Upper City West - Sarikale Valley | Indeterminate | Cu-As-Sn | 216 |
| MA-132452 | Bo 06/1565 | Upper City West - Sarikale Valley | Pin, indeterminate | Cu-Sn | 219 |
| MA-132478 | Bo 06/1567 | Upper City West - Sarikale Valley | Pin, lenticular | Cu-As | 216 |
| MA-132470 | Bo 06/1576 | Upper City West - Sarikale Valley | Indeterminate | Cu-As | 187 |
| MA-132498 | Bo 06/1582 | Upper City West - Sarikale Valley | Indeterminate | Cu-As | 0 |
| MA-132474 | Bo 06/1599 | Upper City West - Sarikale Valley | Indeterminate | Cu-Sn | 233 |
| MA-132437 | Bo 06/160 | Upper City West - Sarikale Valley | Awl | Cu-Sn | 27 |
| MA-132350 | Bo 06/1600 | Upper City West - Sarikale Valley | Indeterminate | Cu-As | 231 |
| MA-132444 | Bo 06/1601 | Upper City West - Sarikale Valley | Insert, hammer-shaped | Cu-Sn | 231 |
| MA-132406 | Bo 06/1609 | Upper City West - Sarikale Valley | Arrowhead, lance-form | Cu-As-Sn | 237 |

| Mannheim Number | Object Number | Location | Object Type | Alloy type | Context (number or description) |
|------------------------|----------------------|-----------------------------------|------------------------|-------------------|--|
| MA-132325 | Bo 06/1614 | Upper City West - Sarikale Valley | Indeterminate | Cu-As | 236 |
| MA-132400 | Bo 06/1616 | Upper City West - Sarikale Valley | Indeterminate | Cu | 230 |
| MA-132373 | Bo 06/164 | Upper City West - Sarikale Valley | Indeterminate | Cu | 24 |
| MA-132465 | Bo 06/1654 | Upper City West - Sarikale Valley | Indeterminate | Cu-As-Pb | 253 |
| MA-132473 | Bo 06/1654_2 | Upper City West - Sarikale Valley | Indeterminate | Cu-Sn | 253 |
| MA-132338 | Bo 06/1656 | Upper City West - Sarikale Valley | Indeterminate | Cu-Sn | 255 |
| MA-132505 | Bo 06/166 | Upper City West - Sarikale Valley | Pin, pyramidal | Cu | 24 |
| MA-132502 | Bo 06/168 | Upper City West - Sarikale Valley | Eye needle | Cu | 0 |
| MA-132371 | Bo 06/1688 | Upper City West - Sarikale Valley | Indeterminate | Cu-As | 260 |
| MA-132429 | Bo 06/1694 | Upper City West - Sarikale Valley | Awl | Cu-Sn | 260 |
| MA-132445 | Bo 06/1715 | Upper City West - Sarikale Valley | Eye needle | Cu | 272 |
| MA-132463 | Bo 06/1716 | Upper City West - Sarikale Valley | Indeterminate | Cu | 269 |
| MA-132311 | Bo 06/172 | Upper City West - Sarikale Valley | Indeterminate | Cu-Ni | 28 |
| MA-132499 | Bo 06/1730 | Upper City West - Sarikale Valley | Pin, unique | Cu | 278 |
| MA-132383 | Bo 06/1739 | Upper City West - Sarikale Valley | Indeterminate | Cu-Sn | 280 |
| MA-132476 | Bo 06/1742 | Upper City West - Sarikale Valley | Pin, shaft fragment | Cu-Sn | 280 |
| MA-132439 | Bo 06/1751 | Upper City West - Sarikale Valley | Pin, unique | Cu-As | 284 |
| MA-132466 | Bo 06/1753 | Upper City West - Sarikale Valley | Awl | Cu-Sn | 283 |
| MA-132203 | Bo 06/1754 | Upper City West - Sarikale Valley | Knife, flat and curved | Cu-Sn | 284 |
| MA-132398 | Bo 06/1755 | Upper City West - Sarikale Valley | Indeterminate | Cu-As-Sn | 0 |
| MA-132330 | Bo 06/1758 | Upper City West - Sarikale Valley | Indeterminate | Cu-Sn | 289 |
| MA-132430 | Bo 06/1758_2 | Upper City West - Sarikale Valley | Indeterminate | Cu-Sn | 289 |
| MA-132421 | Bo 06/1759 | Upper City West - Sarikale Valley | Awl | Cu-As-Sn | 284 |
| MA-132352 | Bo 06/1762 | Upper City West - Sarikale Valley | Pin, lenticular | Cu-As | 283 |
| MA-132335 | Bo 06/1763 | Upper City West - Sarikale Valley | Pin, shaft fragment | Cu-Sn | 291 |
| MA-132394 | Bo 06/1764 | Upper City West - Sarikale Valley | Indeterminate | Cu-As | 291 |

| Mannheim Number | Object Number | Location | Object Type | Alloy type | Context (number or description) |
|------------------------|----------------------|-----------------------------------|-----------------------|-------------------|--|
| MA-132489 | Bo 06/1768 | Upper City West - Sarikale Valley | Awl | Cu-As-Sn | 291 |
| MA-132372 | Bo 06/1771 | Upper City West - Sarikale Valley | Insert, hammer-shaped | Cu-Sn | 291 |
| MA-132471 | Bo 06/1802 | Upper City West - Sarikale Valley | Pin, shaft fragment | Cu-As | 428 |
| MA-132310 | Bo 06/1803 | Upper City West - Sarikale Valley | Pin, indeterminate | Cu-As-Ni | 428 |
| MA-132348 | Bo 06/1806 | Upper City West - Sarikale Valley | Eye needle | Cu | 429 |
| MA-132401 | Bo 06/1817 | Upper City West - Sarikale Valley | Eye needle | Cu | 426 |
| MA-132472 | Bo 06/1825 | Upper City West - Sarikale Valley | Indeterminate | Cu-As-Sn | 436 |
| MA-132357 | Bo 06/1834 | Upper City West - Sarikale Valley | Indeterminate | Cu-Sn | 419 |
| MA-132475 | Bo 06/1835 | Upper City West - Sarikale Valley | Indeterminate | Cu-As | 447 |
| MA-132443 | Bo 06/1837 | Upper City West - Sarikale Valley | Indeterminate | Cu-As | 447 |
| MA-132382 | Bo 06/1844 | Upper City West - Sarikale Valley | Indeterminate | Cu-As | 449 |
| MA-132309 | Bo 06/1874 | Upper City West - Sarikale Valley | Awl | Cu-Sn | 419 |
| MA-132377 | Bo 06/189 | Upper City West - Sarikale Valley | Eye needle | Cu-Ni | 30 |
| MA-132434 | Bo 06/1933 | Upper City West - Sarikale Valley | Nail | Cu-As | 1 |
| MA-132434 | Bo 06/1954 | Upper City West - Sarikale Valley | Indeterminate | Cu-As | 6 |
| MA-132367 | Bo 06/1957 | Upper City West - Sarikale Valley | Sheet, indeterminate | Cu-Au-Ag | 1 |
| MA-132477 | Bo 06/2009 | Upper City West - Sarikale Valley | Seal | Cu-Sn | 767 |
| MA-132358 | Bo 06/2016 | Upper City West - Sarikale Valley | Indeterminate | Cu | 767 |
| MA-132493 | Bo 06/2019 | Upper City West - Sarikale Valley | Indeterminate | Cu-As | 767 |
| MA-132501 | Bo 06/2028 | Upper City West - Sarikale Valley | Eye needle | Cu-As | 901 |
| MA-132356 | Bo 06/2036 | Upper City West - Sarikale Valley | Pin, shaft fragment | Cu-Sn | 901 |
| MA-132305 | Bo 06/2037 | Upper City West - Sarikale Valley | Indeterminate | Cu-Ni | 901 |
| MA-132318 | Bo 06/2039 | Upper City West - Sarikale Valley | Indeterminate | Cu-As | 901 |
| MA-132321 | Bo 06/2049 | Upper City West - Sarikale Valley | Insert, hammer-shaped | Cu-Sn | 903 |
| MA-132454 | Bo 06/2056 | Upper City West - Sarikale Valley | Eye needle | Cu | 905 |
| MA-132361 | Bo 06/207 | Upper City West - Sarikale Valley | Pin, indeterminate | Cu-As-Sn | 47 |

| Mannheim Number | Object Number | Location | Object Type | Alloy type | Context (number or description) |
|------------------------|----------------------|-----------------------------------|--------------------------|-------------------|--|
| MA-132414 | Bo 06/2075 | Upper City West - Sarikale Valley | Awl | Cu-As-Sn | 905 |
| MA-132487 | Bo 06/2089 | Upper City West - Sarikale Valley | Awl | Cu-As | 909 |
| MA-132418 | Bo 06/2090 | Upper City West - Sarikale Valley | Eye needle | Cu-As | 909 |
| MA-132525 | Bo 06/2094 | Upper City West - Sarikale Valley | Arrowhead, lance-form | Cu-As | 912 |
| MA-132410 | Bo 06/210 | Upper City West - Sarikale Valley | Indeterminate | Cu-Sn | 47 |
| MA-132482 | Bo 06/2103 | Upper City West - Sarikale Valley | Indeterminate | Cu-As | 0 |
| MA-132354 | Bo 06/2110 | Upper City West - Sarikale Valley | Eye needle | Cu-Ni | 912 |
| MA-132322 | Bo 06/212 | Upper City West - Sarikale Valley | Indeterminate | Cu-Sn | 42 |
| MA-132315 | Bo 06/2127 | Upper City West - Sarikale Valley | Pin, nodular | Cu-As-Sn | 920 |
| MA-132480 | Bo 06/2130 | Upper City West - Sarikale Valley | Pin, rolled | Cu-As | 1012 |
| MA-132488 | Bo 06/2142 | Upper City West - Sarikale Valley | Eye needle | Cu-As | 920 |
| MA-132419 | Bo 06/215 | Upper City West - Sarikale Valley | Indeterminate | Cu-As-Sn | 43 |
| MA-132479 | Bo 06/2152 | Upper City West - Sarikale Valley | Pin, conical | Cu-Ni | 775 |
| MA-132332 | Bo 06/2153 | Upper City West - Sarikale Valley | Eye needle | Cu-As | 920 |
| MA-132492 | Bo 06/2182 | Upper City West - Sarikale Valley | Knife, flat and straight | Cu | 767 |
| MA-132417 | Bo 06/2192 | Upper City West - Sarikale Valley | Pin, lenticular | Cu-As-Sn | 911 |
| MA-132415 | Bo 06/2229 | Upper City West - Sarikale Valley | Pin, lenticular | Cu | 911 |
| MA-132497 | Bo 06/223 | Upper City West - Sarikale Valley | Pin, conical | Cu-As | 0 |
| MA-132523 | Bo 06/2236 | Upper City West - Sarikale Valley | Pin, disc | Cu-As | 779 |
| MA-132425 | Bo 06/2237 | Upper City West - Sarikale Valley | Pin, lenticular | Cu-As | 779 |
| MA-132375 | Bo 06/2244 | Upper City West - Sarikale Valley | Eye needle | Cu-As | 933 |
| MA-132403 | Bo 06/2251 | Upper City West - Sarikale Valley | Edged chisel | Cu | |
| MA-132494 | Bo 06/2253 | Upper City West - Sarikale Valley | Pin, lenticular | Cu-As-Sn | 766 |
| MA-132494 | Bo 06/2263 | Upper City West - Sarikale Valley | Indeterminate | Cu-As | 766 |
| MA-132345 | Bo 06/2269 | Upper City West - Sarikale Valley | Arrowhead, lance-form | Cu | 766 |
| MA-132345 | Bo 06/2294 | Upper City West - Sarikale Valley | Awl | Cu-Sn | 937 |

| Mannheim Number | Object Number | Location | Object Type | Alloy type | Context (number or description) |
|------------------------|----------------------|-----------------------------------|--------------------------------|-------------------|--|
| MA-132342 | Bo 06/2298 | Upper City West - Sarikale Valley | Ring, wire | Cu-Sn-Ni | 941 |
| | Bo 06/23 | Upper City West - Sarikale Valley | Sheet, decorated | Cu | 1 |
| | Bo 06/2350 | Upper City West - Sarikale Valley | Ring, wire | Cu-As-Sn | 765 |
| MA-132462 | Bo 06/2359 | Upper City West - Sarikale Valley | Pin, indeterminate | Cu | 948 |
| MA-132304 | Bo 06/2361 | Upper City West - Sarikale Valley | Indeterminate | Cu-Ni | 948 |
| MA-132351 | Bo 06/2376 | Upper City West - Sarikale Valley | Eye needle | Cu-As | 950 |
| MA-132317 | Bo 06/2378 | Upper City West - Sarikale Valley | Eye needle, fragment | Cu-As | 950 |
| MA-132344 | Bo 06/239 | Upper City West - Sarikale Valley | Pin, shaft fragment | Cu-Sn | 73 |
| MA-132363 | Bo 06/2398 | Upper City West - Sarikale Valley | Eye needle | Cu-As | 967 |
| MA-132411 | Bo 06/2400 | Upper City West - Sarikale Valley | Arrowhead, stemmed and spurred | Cu-Sn | 971 |
| MA-132364 | Bo 06/2403 | Upper City West - Sarikale Valley | Pin, lenticular | Cu-As | 970 |
| MA-132355 | Bo 06/2409 | Upper City West - Sarikale Valley | Eye needle | Cu | 970 |
| MA-132453 | Bo 06/241 | Upper City West - Sarikale Valley | Eye needle, fragment | Cu-Sn | 73 |
| MA-132508 | Bo 06/242 | Upper City West - Sarikale Valley | Eye needle | Cu-As-Sn | 74 |
| MA-132346 | Bo 06/2428 | Upper City West - Sarikale Valley | Sheet ring | Cu-Ni | 971 |
| MA-132402 | Bo 06/250 | Upper City West - Sarikale Valley | Indeterminate | Cu | 74 |
| MA-132340 | Bo 06/254 | Upper City West - Sarikale Valley | Indeterminate | Cu-Sn | 17 |
| MA-132468 | Bo 06/257 | Upper City West - Sarikale Valley | Armor plate | Cu-Sn | 17 |
| MA-132349 | Bo 06/258 | Upper City West - Sarikale Valley | Indeterminate | Cu | 17 |
| MA-132409 | Bo 06/259 | Upper City West - Sarikale Valley | Edged chisel | Cu-Sn | 82 |
| MA-132486 | Bo 06/265 | Upper City West - Sarikale Valley | Eye needle, fragment | Cu-As-Sn | 17 |
| MA-132483 | Bo 06/266 | Upper City West - Sarikale Valley | Pin, shaft fragment | Cu-As | 17 |
| MA-132485 | Bo 06/267 | Upper City West - Sarikale Valley | Indeterminate | Cu-As-Sn | 17 |
| MA-132484 | Bo 06/268 | Upper City West - Sarikale Valley | Indeterminate | Cu | 17 |
| MA-132469 | Bo 06/268_2 | Upper City West - Sarikale Valley | Indeterminate | Cu-As | 17 |
| MA-132381 | Bo 06/272 | Upper City West - Sarikale Valley | Eye needle, fragment | Cu-Sn | 68 |

| Mannheim Number | Object Number | Location | Object Type | Alloy type | Context (number or description) |
|------------------------|----------------------|-----------------------------------|--------------------------------|-------------------|--|
| MA-132491 | Bo 06/274 | Upper City West - Sarikale Valley | Indeterminate | Cu-As | 43 |
| MA-132423 | Bo 06/284 | Upper City West - Sarikale Valley | Awl | Cu-Sn | 301 |
| MA-132337 | Bo 06/293 | Upper City West - Sarikale Valley | Eye needle | Cu-As | 302 |
| MA-132391 | Bo 06/305 | Upper City West - Sarikale Valley | Pin, indeterminate | Cu-As | 30 |
| MA-132448 | Bo 06/313 | Upper City West - Sarikale Valley | Indeterminate | Cu-Sn | 53 |
| MA-132376 | Bo 06/314 | Upper City West - Sarikale Valley | Indeterminate | Cu-Sn | 54 |
| MA-132320 | Bo 06/317 | Upper City West - Sarikale Valley | Pin, lenticular | Cu-As-Sn | 54 |
| MA-132324 | Bo 06/319 | Upper City West - Sarikale Valley | Ring, wire | Cu-As-Sn | 28 |
| MA-132395 | Bo 06/326 | Upper City West - Sarikale Valley | Edged chisel | Cu-Sn | 29 |
| MA-132506 | Bo 06/353 | Upper City West - Sarikale Valley | Pin, shaft fragment | Cu-Sn | 57 |
| MA-132459 | Bo 06/368 | Upper City West - Sarikale Valley | Indeterminate | Cu-Sn | 318 |
| MA-132496 | Bo 06/410 | Upper City West - Sarikale Valley | Indeterminate | Cu-As | 39 |
| MA-132495 | Bo 06/413 | Upper City West - Sarikale Valley | Pin, nodular | Cu-As-Sn | 39 |
| MA-132326 | Bo 06/415 | Upper City West - Sarikale Valley | Indeterminate | Cu-As | 39 |
| MA-132507 | Bo 06/417 | Upper City West - Sarikale Valley | Pin, disc | Cu | 39 |
| MA-132404 | Bo 06/429 | Upper City West - Sarikale Valley | Awl | Cu-As | 403 |
| MA-132440 | Bo 06/440 | Upper City West - Sarikale Valley | Indeterminate | Cu-As | 406 |
| MA-132336 | Bo 06/441 | Upper City West - Sarikale Valley | Pin, shaft fragment | Cu-As | 406 |
| MA-132341 | Bo 06/454 | Upper City West - Sarikale Valley | Awl | Cu-Sn | 411 |
| MA-132431 | Bo 06/476 | Upper City West - Sarikale Valley | Pin, pyramidal | Cu-As-Sn | 413 |
| MA-132518 | Bo 06/486 | Upper City West - Sarikale Valley | Arrowhead, stemmed and spurred | Cu-As-Sn | 419 |
| MA-132438 | Bo 06/489 | Upper City West - Sarikale Valley | Eye needle, fragment | Cu-As | 421 |
| MA-132307 | Bo 06/492 | Upper City West - Sarikale Valley | Sheet, indeterminate | Cu-Ni | 404 |
| MA-132333 | Bo 06/499 | Upper City West - Sarikale Valley | Eye needle | Cu-As | 429 |
| MA-132389 | Bo 06/500 | Upper City West - Sarikale Valley | Pin, lenticular | Cu-As | 128 |
| MA-132426 | Bo 06/506 | Upper City West - Sarikale Valley | Pin, shaft fragment | Cu-As-Sn | 74 |

| Mannheim Number | Object Number | Location | Object Type | Alloy type | Context (number or description) |
|------------------------|----------------------|-----------------------------------|--------------------------------|-------------------|--|
| MA-132368 | Bo 06/513 | Upper City West - Sarikale Valley | Indeterminate | Cu-Sn | 121 |
| MA-132446 | Bo 06/514 | Upper City West - Sarikale Valley | Pin, conical | Cu-As-Sn | 121 |
| MA-132347 | Bo 06/521 | Upper City West - Sarikale Valley | Sheet, indeterminate | Cu-As | 124 |
| MA-132413 | Bo 06/532 | Upper City West - Sarikale Valley | Eye needle | Cu-As-Sn | 125 |
| MA-132422 | Bo 06/533 | Upper City West - Sarikale Valley | Awl | Cu-As-Sn | 0 |
| MA-132362 | Bo 06/548 | Upper City West - Sarikale Valley | Awl | Cu-Sn | 80 |
| MA-132313 | Bo 06/549 | Upper City West - Sarikale Valley | Pin, rolled | Cu-Ni | 80 |
| MA-132374 | Bo 06/555 | Upper City West - Sarikale Valley | Pin, rolled | Cu-As | 131 |
| MA-132390 | Bo 06/563 | Upper City West - Sarikale Valley | Eye needle | Cu-As | 139 |
| MA-132441 | Bo 06/567 | Upper City West - Sarikale Valley | Sheet, indeterminate | Cu | 123 |
| MA-132481 | Bo 06/578 | Upper City West - Sarikale Valley | Eye needle, fragment | Cu-Sn | 130 |
| MA-132420 | Bo 06/585 | Upper City West - Sarikale Valley | Eye needle | Cu-As | 145 |
| MA-132412 | Bo 06/608 | Upper City West - Sarikale Valley | Pin, shaft fragment | Cu-Sn | 157 |
| MA-132467 | Bo 06/617 | Upper City West - Sarikale Valley | Pin, rolled | Cu-Sn | 148 |
| MA-132460 | Bo 06/635 | Upper City West - Sarikale Valley | Indeterminate | Cu-As-Sn | 171 |
| MA-132451 | Bo 06/647 | Upper City West - Sarikale Valley | Arrowhead, stemmed and spurred | Cu-As-Sn | 170 |
| MA-132329 | Bo 06/649 | Upper City West - Sarikale Valley | Pin, shaft fragment | Cu-Sn | 175 |
| MA-132432 | Bo 06/661 | Upper City West - Sarikale Valley | Eye needle | Cu-As | 175 |
| MA-132416 | Bo 06/668 | Upper City West - Sarikale Valley | Arrowhead, stemmed and spurred | Cu-As | 179 |
| MA-132365 | Bo 06/673 | Upper City West - Sarikale Valley | Indeterminate | Cu-As | 178 |
| MA-132455 | Bo 06/677 | Upper City West - Sarikale Valley | Sheet, indeterminate | Cu-As-Sn | 175 |
| MA-132353 | Bo 06/680 | Upper City West - Sarikale Valley | Pin, shaft fragment | Cu-Sn | 175 |
| MA-132314 | Bo 06/69 | Upper City West - Sarikale Valley | Wire, round section | Cu-Sn-Ni | 6 |
| MA-132427 | Bo 06/711 | Upper City West - Sarikale Valley | Indeterminate | Cu-As | 89 |
| MA-132490 | Bo 06/735 | Upper City West - Sarikale Valley | Indeterminate | Cu-As | 316 |
| MA-132458 | Bo 06/740 | Upper City West - Sarikale Valley | Indeterminate | Cu-Sn | 319 |

| Mannheim Number | Object Number | Location | Object Type | Alloy type | Context (number or description) |
|------------------------|----------------------|-----------------------------------|----------------------|-------------------|--|
| MA-132201 | Bo 06/753 | Upper City West - Sarikale Valley | Sheet, decorated | Cu-Sn | 306 |
| MA-132447 | Bo 06/770 | Upper City West - Sarikale Valley | Indeterminate | Cu-As | 319 |
| MA-132396 | Bo 06/773 | Upper City West - Sarikale Valley | Indeterminate | Cu-As | 318 |
| MA-132360 | Bo 06/78 | Upper City West - Sarikale Valley | Eye needle | Cu-As | 16 |
| MA-132378 | Bo 06/819 | Upper City West - Sarikale Valley | Indeterminate | Cu-As-Sn | 336 |
| MA-132399 | Bo 06/82 | Upper City West - Sarikale Valley | Eye needle, fragment | Cu | 17 |
| MA-132424 | Bo 06/83 | Upper City West - Sarikale Valley | Indeterminate | Cu-Sn | 18 |
| MA-132436 | Bo 06/861 | Upper City West - Sarikale Valley | Indeterminate | Cu-As | 82 |
| MA-132435 | Bo 06/93 | Upper City West - Sarikale Valley | Pin, shaft fragment | Cu-As-Sn | 18 |
| MA-132457 | Bo 06/97 | Upper City West - Sarikale Valley | Indeterminate | Cu-Sn | 23 |
| | Bo 07/1225 | Upper City West - Sarikale Valley | Ring, wire | Cu-As-Ni | 611 |
| | Bo 07/1288 | Upper City West - Sarikale Valley | Pin, shaft fragment | Cu | 624 |
| | Bo 07/1301 | Upper City West - Sarikale Valley | Awl | Cu-As | 629 |
| | Bo 07/1720 | Upper City West - Sarikale Valley | Awl | Cu-Sn | 709 |
| | Bo 07/1745 | Upper City West - Sarikale Valley | Awl | Cu-Sn | 720 |
| | Bo 07/1755 | Upper City West - Sarikale Valley | Awl | Cu | 722 |
| | Bo 07/1802 | Upper City West - Sarikale Valley | Pin, lamellar | Cu-As | 740 |
| | Bo 07/1810 | Upper City West - Sarikale Valley | Pin, disc | Cu-As-Sn | 741 |
| | Bo 07/1818 | Upper City West - Sarikale Valley | Wire, round section | Cu-Ni | 745 |
| | Bo 07/1821 | Upper City West - Sarikale Valley | Awl | Cu-Ni | 745 |
| | Bo 07/1860 | Upper City West - Sarikale Valley | Pin, disc | Cu-As-Sn | 758 |
| MA-136335 | Bo 07/1871 | Upper City West - Sarikale Valley | Ring, wire | Cu-Ni | 761 |
| | Bo 07/1874 | Upper City West - Sarikale Valley | Sheet, decorated | Cu-As | 761 |
| | Bo 07/1920 | Upper City West - Sarikale Valley | Pin, indeterminate | Cu-As-Sn | 777 |
| | Bo 07/1921 | Upper City West - Sarikale Valley | Pin, indeterminate | Cu-As | 777 |
| | Bo 07/1936 | Upper City West - Sarikale Valley | Pin, fungiform | Cu-As-Sn | 781 |

| Mannheim Number | Object Number | Location | Object Type | Alloy type | Context (number or description) |
|------------------------|----------------------|-----------------------------------|----------------------|-------------------|--|
| | Bo 07/2045 | Upper City West - Sarikale Valley | Eye needle, fragment | Cu | 1006 |
| | Bo 07/2054 | Upper City West - Sarikale Valley | Pin, shaft fragment | Cu-Sn | 1006 |
| | Bo 07/2055 | Upper City West - Sarikale Valley | Eye needle | Cu | 1006 |
| | Bo 07/2079 | Upper City West - Sarikale Valley | Pin, incised disc | Cu-As-Ni | 1018 |
| | Bo 07/2087 | Upper City West - Sarikale Valley | Eye needle | Cu-As-Pb | 1020 |
| | Bo 07/2089 | Upper City West - Sarikale Valley | Awl | Cu-Sn | 1018 |
| | Bo 07/2093 | Upper City West - Sarikale Valley | Pin, incised disc | Cu-As | 1013 |
| MA-136332 | Bo 07/2101 | Upper City West - Sarikale Valley | Pin, disc | Cu-Ni | 1019 |
| | Bo 07/2104 | Upper City West - Sarikale Valley | Pin, lamellar disc | Cu-As | 1021 |
| | Bo 07/2121 | Upper City West - Sarikale Valley | Eye needle, fragment | Cu | 1030 |
| | Bo 07/2129 | Upper City West - Sarikale Valley | Eye needle, fragment | Cu-Sn | 1027 |
| | Bo 07/2130 | Upper City West - Sarikale Valley | Sheet, indeterminate | Cu | 1027 |
| | Bo 07/2143 | Upper City West - Sarikale Valley | Awl | Cu | 1039 |
| MA-136331 | Bo 07/2149 | Upper City West - Sarikale Valley | Ornament | Cu-As-Ni | 1030 |
| MA-136328 | Bo 07/2151 | Upper City West - Sarikale Valley | Pin, lenticular | Cu-Ni | 1030 |
| | Bo 07/2154 | Upper City West - Sarikale Valley | Pin, shaft fragment | Cu-As | 1035 |
| | Bo 07/2200 | Upper City West - Sarikale Valley | Pin, fungiform | Cu-Sn | 1050 |
| MA-136333 | Bo 07/2204 | Upper City West - Sarikale Valley | Pin, fungiform | Cu-Ni | 1053 |
| | Bo 07/2211 | Upper City West - Sarikale Valley | Pin, shaft fragment | Cu | 1053 |
| | Bo 07/2215 | Upper City West - Sarikale Valley | Pin, shaft fragment | Cu | 1053 |
| | Bo 07/2221 | Upper City West - Sarikale Valley | Pin, disc | Cu-As | 1053 |
| | Bo 07/2224 | Upper City West - Sarikale Valley | Pin, incised disc | Cu-As | 1053 |
| | Bo 07/2227 | Upper City West - Sarikale Valley | Eye needle | Cu-As | 1053 |
| | Bo 07/2228 | Upper City West - Sarikale Valley | Pin, shaft fragment | Cu-Ni | 1053 |
| | Bo 07/2235 | Upper City West - Sarikale Valley | Pin, disc | Cu-As | 1057 |
| | Bo 07/2239 | Upper City West - Sarikale Valley | Ring, wire | Cu-Sn | 1053 |

| Mannheim Number | Object Number | Location | Object Type | Alloy type | Context (number or description) |
|------------------------|----------------------|-----------------------------------|----------------------|-------------------|--|
| | Bo 07/2240 | Upper City West - Sarikale Valley | Eye needle | Cu | 1053 |
| | Bo 07/2252 | Upper City West - Sarikale Valley | Pin, shaft fragment | Cu | 1053 |
| | Bo 07/2256 | Upper City West - Sarikale Valley | Pin, disc | Cu-As-Sn | 1060 |
| | Bo 07/2258 | Upper City West - Sarikale Valley | Eye needle | Cu | 1059 |
| | Bo 07/2260 | Upper City West - Sarikale Valley | Eye needle, fragment | Cu | 1061 |
| | Bo 07/2269 | Upper City West - Sarikale Valley | Awl | Cu-As-Sn | 1046 |
| | Bo 07/2272 | Upper City West - Sarikale Valley | Pin, conical | Cu | 1059 |
| | Bo 07/2305 | Upper City West - Sarikale Valley | Pin, conical | Cu-As-Sn-Ni | 1074 |
| | Bo 07/2354 | Upper City West - Sarikale Valley | Pin, shaft fragment | Cu-Sn | 1079 |
| | Bo 07/2397 | Upper City West - Sarikale Valley | Wire, round section | Cu-As | 1078 |
| | Bo 07/2422 | Upper City West - Sarikale Valley | Pin, disc | Cu-As-Sn | 1120 |
| | Bo 07/2445 | Upper City West - Sarikale Valley | Awl | Cu | 0 |
| | Bo 07/2456 | Upper City West - Sarikale Valley | Eye needle, fragment | Cu | 1124 |
| | Bo 07/2458 | Upper City West - Sarikale Valley | Sheet, indeterminate | Cu | 1124 |
| | Bo 07/2460 | Upper City West - Sarikale Valley | Pin, disc | Cu-As | 1125 |
| | Bo 07/2470 | Upper City West - Sarikale Valley | Wire, round section | Cu-As | 1125 |
| | Bo 07/2471 | Upper City West - Sarikale Valley | Edged chisel | Cu-As-Sn | 1134 |
| | Bo 07/2483 | Upper City West - Sarikale Valley | Eye needle, fragment | Cu | 1104 |
| | Bo 07/2484 | Upper City West - Sarikale Valley | Awl | Cu-As-Sn | 1141 |
| | Bo 07/2637 | Upper City West - Sarikale Valley | Sheet, indeterminate | Cu | 1523 |
| | Bo 07/2707 | Upper City West - Sarikale Valley | Sheet, indeterminate | Cu-Ni | 1560 |
| MA-132197 | Bo 07/29 | Upper City West - Sarikale Valley | Arrowhead, stemmed | Cu-Sn | 764 |
| | Bo 07/3402 | Upper City West - Sarikale Valley | Arrowhead, stemmed | Cu | 1142 |
| | Bo 07/3431 | Upper City West - Sarikale Valley | Awl | Cu-As-Sn | 1163 |
| | Bo 07/3440 | Upper City West - Sarikale Valley | Pin, lenticular | Cu | 1168 |
| | Bo 07/3441 | Upper City West - Sarikale Valley | Pin, lenticular | Cu-As | 1168 |

| Mannheim Number | Object Number | Location | Object Type | Alloy type | Context (number or description) |
|------------------------|----------------------|-----------------------------------|--------------------------|-------------------|--|
| | Bo 07/3444 | Upper City West - Sarikale Valley | Sheet, decorated | Cu-As | 1170 |
| | Bo 07/3457 | Upper City West - Sarikale Valley | Pin, unique | Cu-As | 1172 |
| | Bo 07/3460 | Upper City West - Sarikale Valley | Hammer | Cu-As | 1170 |
| | Bo 07/3481 | Upper City West - Sarikale Valley | Eye needle | Cu | 1180 |
| | Bo 07/3484 | Upper City West - Sarikale Valley | Awl | Cu-As-Sn | 1180 |
| | Bo 07/3490 | Upper City West - Sarikale Valley | Eye needle, fragment | Cu-As | 1180 |
| | Bo 07/3509 | Upper City West - Sarikale Valley | Eye needle, fragment | Cu-As | 1143 |
| | Bo 07/3571 | Upper City West - Sarikale Valley | Insert, hammer-shaped | Cu-Sn | 1080 |
| MA-136334 | Bo 07/3594 | Upper City West - Sarikale Valley | Pendant, decorated sheet | Cu-Ni | 1201 |
| | Bo 07/3606 | Upper City West - Sarikale Valley | Pin, conical | Cu | 1207 |
| | Bo 07/3693 | Upper City West - Sarikale Valley | Edged chisel | Cu-Sn | 1229 |
| | Bo 07/3694 | Upper City West - Sarikale Valley | Edged chisel | Cu-Sn | 1229 |
| | Bo 07/3723 | Upper City West - Sarikale Valley | Awl | Cu-Sn | 1234 |
| MA-136325 | Bo 07/3735 | Upper City West - Sarikale Valley | Arm ring | Cu-Ni | 1221 |
| | Bo 07/3739 | Upper City West - Sarikale Valley | Insert, axe-shaped | Cu-As-Sn | 1149 |
| | Bo 07/3798 | Upper City West - Sarikale Valley | Pin, pyramidal | Cu-As | 1172 |
| | Bo 07/3803 | Upper City West - Sarikale Valley | Pin, nodular | Cu-Sn | 1221 |
| | Bo 07/3811 | Upper City West - Sarikale Valley | Pin, shaft fragment | Cu-As | 1221 |
| | Bo 07/3816 | Upper City West - Sarikale Valley | Wire, round section | Cu-As | 1221 |
| | Bo 08/100 | Upper City West - Sarikale Valley | Eye needle, fragment | Cu-As | 27 |
| MA-132199 | Bo 08/101 | Upper City West - Sarikale Valley | Seal | Cu-As-Sn | 30 |
| | Bo 08/102 | Upper City West - Sarikale Valley | Pin, fungiform | Cu | 25 |
| | Bo 08/105 | Upper City West - Sarikale Valley | Ring, wire | Cu-As-Sn | 0 |
| | Bo 08/132 | Upper City West - Sarikale Valley | Ring, wire | Cu-Sn | 37 |
| | Bo 08/134 | Upper City West - Sarikale Valley | Insert, hammer-shaped | Cu-Sn | 36 |
| | Bo 08/140 | Upper City West - Sarikale Valley | Pin, fungiform | Cu-As-Sn | 37 |

| Mannheim Number | Object Number | Location | Object Type | Alloy type | Context (number or description) |
|------------------------|----------------------|-----------------------------------|------------------------|-------------------|--|
| | Bo 08/143 | Upper City West - Sarikale Valley | Ring, wire | Cu-Ni | 37 |
| | Bo 08/1511 | Upper City West - Sarikale Valley | Sheet, indeterminate | Cu-Sn | 1502 |
| | Bo 08/156 | Upper City West - Sarikale Valley | Eye needle | Cu-As | 43 |
| MA-132549 | Bo 08/16 | Upper City West - Sarikale Valley | Eye needle, fragment | Cu | |
| | Bo 08/160 | Upper City West - Sarikale Valley | Pin, lenticular | Cu-As-Sn | 43 |
| | Bo 08/197 | Upper City West - Sarikale Valley | Pin, fungiform | Cu | 49 |
| | Bo 08/212 | Upper City West - Sarikale Valley | Pin, nodular | Cu-As | 49 |
| MA-132205 | Bo 08/217 | Upper City West - Sarikale Valley | Knife, flat and curved | Cu-As | 67 |
| MA-132198 | Bo 08/227 | Upper City West - Sarikale Valley | Flat axe, lugged | Cu-As-Sn | 67 |
| MA-132206 | Bo 08/229 | Upper City West - Sarikale Valley | Arrowhead, stemmed | Cu-Sn | 68 |
| | Bo 08/236 | Upper City West - Sarikale Valley | Pin, lenticular | Cu-As | 68 |
| | Bo 08/25 | Upper City West - Sarikale Valley | Eye needle | Cu | 7 |
| | Bo 08/255 | Upper City West - Sarikale Valley | Pin, shaft fragment | Cu-As-Sn | 83 |
| | Bo 08/258 | Upper City West - Sarikale Valley | Awl | Cu-As | 52 |
| MA-136324 | Bo 08/264 | Upper City West - Sarikale Valley | Eye needle | Cu-Ni | 78 |
| | Bo 08/27 | Upper City West - Sarikale Valley | Eye needle | Cu-As-Sn | 2 |
| | Bo 08/28 | Upper City West - Sarikale Valley | Eye needle | Cu-Sn | 2 |
| | Bo 08/300 | Upper City West - Sarikale Valley | Edged chisel | Cu-As | Q2 |
| | Bo 08/36 | Upper City West - Sarikale Valley | Eye needle | Cu-As | 11 |
| | Bo 08/37 | Upper City West - Sarikale Valley | Eye needle, fragment | Cu | 2 |
| | Bo 08/42 | Upper City West - Sarikale Valley | Pin, fungiform | Cu-As-Pb | 10 |
| | Bo 08/43 | Upper City West - Sarikale Valley | Pin, shaft fragment | Cu-As-Sn | 3 |
| | Bo 08/44 | Upper City West - Sarikale Valley | Pin, disc | Cu-As | 10 |
| MA-132552 | Bo 08/5 | Upper City West - Sarikale Valley | Pin, nodular | Cu-As | |
| | Bo 08/53 | Upper City West - Sarikale Valley | Eye needle | Cu-As-Sn | 11 |
| | Bo 08/57 | Upper City West - Sarikale Valley | Eye needle, fragment | Cu | 17 |

| Mannheim Number | Object Number | Location | Object Type | Alloy type | Context (number or description) |
|------------------------|----------------------|-----------------------------------|--------------------------------|-------------------|--|
| | Bo 08/66 | Upper City West - Sarikale Valley | Eye needle, fragment | Cu-As-Sn | 20 |
| | Bo 08/69 | Upper City West - Sarikale Valley | Eye needle | Cu-Sn | 20 |
| | Bo 08/73 | Upper City West - Sarikale Valley | Edged chisel | Cu-As | 20 |
| | Bo 08/77 | Upper City West - Sarikale Valley | Awl | Cu-As | 23 |
| | Bo 08/841 | Upper City West - Sarikale Valley | Awl | Cu | 853 |
| | Bo 08/859 | Upper City West - Sarikale Valley | Indeterminate | Cu | 814 |
| | Bo 08/87 | Upper City West - Sarikale Valley | Pin, lenticular | Cu-As | 25 |
| | Bo 08/884 | Upper City West - Sarikale Valley | Sheet, indeterminate | Cu | 822 |
| MA-132204 | Bo 08/9 | Upper City West - Sarikale Valley | Pendant, lunulae | Cu-As-Ni | 0 |
| | Bo 08/966 | Upper City West - Sarikale Valley | Wire, round section | Cu | 859 |
| | Bo 07/519 | Upper City West - Yenicekale | Sheet, indeterminate | Cu | 503 |
| | Bo 07/523 | Upper City West - Yenicekale | Sheet, indeterminate | Cu | 505 |
| MA-136328 | Bo 07/576 | Upper City West - Yenicekale | Ornament | Cu-Ni | 505 |
| | Bo 07/578 | Upper City West - Yenicekale | Sheet, indeterminate | Cu | 515 |
| | Bo 07/591 | Upper City West - Yenicekale | Edged chisel | Cu-As-Sn-Pb | 525 |
| EARLY IRON AGE | | | | | |
| | Bo 96/31 | Büyükkaya | Socketed chisel | Cu-As-Sn-Pb | 353/421.82 |
| | Bo 96/45 | Büyükkaya | Pin, rolled | Cu-Sn | 353/421.72 |
| | Bo 96/85 | Büyükkaya | Tweezers | Cu-Sn | 353/420.107 |
| | Bo 97/25 | Büyükkaya | Arrowhead, stemmed and spurred | Cu-As-Sn-Pb | 352/421.182 |
| | Bo 97/26 | Büyükkaya | Awl | Cu-Sn | 352/420.385 |
| | Bo 97/31 | Büyükkaya | Arrowhead, stemmed | Cu-Sn | 353/420.257 |
| | Bo 97/35 | Büyükkaya | Pin, lamellar disc | Cu-As-Ni | 352/421.192 |
| | Bo 97/38 | Büyükkaya | Horse bit | Cu-As-Sn | 352/421.172 |
| | Bo 97/87 | Büyükkaya | Knife, flat and curved | Cu-Sn | 353/420.326 |

| Mannheim Number | Object Number | Location | Object Type | Alloy type | Context (number or description) |
|-----------------|---------------|-----------|-------------------------------|------------|---------------------------------|
| | Bo 97/90 | Büyükkaya | Edged chisel | Cu-Sn | 353/420.330 |
| | Bo 97/93 | Büyükkaya | Rivet | Au | 352/421.294 |
| | Bo 97/93 | Büyükkaya | Rivet | Cu | 352/421.294 |
| | Bo 97/94 | Büyükkaya | Knife, flat and straight | Cu-Sn | 352/420.507 |
| | Bo 97/97 | Büyükkaya | Flat axe, lugged | Cu | 352/420.454 |
| | Bo 97/99 | Büyükkaya | Axe or hatchet, indeterminate | Cu-Sn | 352/420.391 |
| | ETD 96/31 | Büyükkaya | Pin, indeterminate | Cu-As | 354/427.178 |
| | ETD 96/38 | Büyükkaya | Pin, nodular | Cu-Sn | 352/421.68 |
| | ETD 96/46 | Büyükkaya | Pin, shaft fragment | Cu | 352/421.62 |
| | ETD 97/197 | Büyükkaya | Ring, wire | Cu-Sn | 352/420.535 |
| | ETD 97/198 | Büyükkaya | Eye needle, fragment | Cu-Sn | 352/420.390 |
| | ETD 97/203 | Büyükkaya | Pin, shaft fragment | Cu-Sn | 352/420.479 |
| | ETD 97/215 | Büyükkaya | Pin, indeterminate | Cu | 352/426.344 |
| | ETD 97/225 | Büyükkaya | Awl | Cu-Sn | 353/420.292 |
| | ETD 97/235 | Büyükkaya | Pin, indeterminate | Cu | 352/420.394 |
| | ETD 97/236 | Büyükkaya | Waste, casting | Cu-Sn | 352/421.170 |
| | ETD 97/239 | Büyükkaya | Waste, casting | Cu-Sn | 352/421.220 |
| | ETD 97/245 | Büyükkaya | Sheet, indeterminate | Cu | 353/420.289 |
| | ETD 97/253 | Büyükkaya | Arrowhead, indeterminate | Cu-As | 352/420.443 |
| | ETD 97/261 | Büyükkaya | Awl | Cu-Sn | 352/420.301 |
| | ETD 97/265 | Büyükkaya | Awl | Cu-Sn | 353/420.242 |
| | ETD 97/273 | Büyükkaya | Tool, indeterminate | Cu-Sn | 352/420.323 |
| | ETD 97/340A | Büyükkaya | Pin, lenticular | Cu-Sn | 352/420.364 |
| | ETD 97/340B | Büyükkaya | Awl | Cu-Sn | 352/420.364 |
| | ETD 97/340C | Büyükkaya | Awl | Cu-As | 352/420.364 |
| | ETD 97/340D | Büyükkaya | Awl | Cu | 352/420.364 |

| Mannheim Number | Object Number | Location | Object Type | Alloy type | Context (number or description) |
|-------------------------------|----------------------|-----------------|-----------------------------|-------------------|--|
| | ETD 98/04 | Büyükkaya | Sheet, indeterminate | Cu-Sn | 352/420.353 |
| MIDDLE / LATE IRON AGE | | | | | |
| MA-132554 | Bo 307/n | Büyükkale | Fibula | Cu-Sn | Boehmer 1972: n. 87 |
| MA-132559 | Bo 443/1/3 | Büyükkale | Bilobate socketed arrowhead | Cu-Sn | Boehmer 1972: n. 890 |
| | Bo 94/122 | Büyükkaya | Pin, nodular | Cu | 356/430.16 |
| | Bo 94/32 | Büyükkaya | Ingot, ring | Cu-As-Sn | 357/431.3 |
| | Bo 94/35 | Büyükkaya | Pin, nodular | Cu | 354/430.48 |
| | Bo 95/12 | Büyükkaya | Toggle Pin | Cu-Sn | 354/428.98 |
| | Bo 95/126 | Büyükkaya | Fibula | Cu-Sn | 355/431.260 |
| | Bo 95/13 | Büyükkaya | Fibula | Cu-As-Sn | 357/431.145 |
| | Bo 95/69 | Büyükkaya | Ingot, rod | Cu-Sn-Pb | 352/427.50 |
| | Bo 96/67 | Büyükkaya | Fibula | Cu-Sn | 356/427.169 |
| | Bo 97/30 | Büyükkaya | Indeterminate | Cu-Sn | 353/420.329 |
| | ETD 94/125 | Büyükkaya | Eye needle, fragment | Cu-Sn | 356/431.22 |
| | ETD 94/126 | Büyükkaya | Pin, shaft fragment | Cu-Sn | 356/431.22 |
| | ETD 94/178 | Büyükkaya | Wire, round section | Cu-Sn | 355/430.90 |
| | ETD 94/19 | Büyükkaya | Ring, wire | Cu | 355/430.27 |
| | ETD 94/211 | Büyükkaya | Wire, round section | Cu-Ni | 357/431.16 |
| | ETD 94/212 | Büyükkaya | Wire, round section | Cu | 357/431.16 |
| | ETD 94/241 | Büyükkaya | Rivet | Cu-Sn-Pb | 355/430.225 |
| | ETD 94/261 | Büyükkaya | Fibula | Cu | 356/432.3 |
| | ETD 94/284 | Büyükkaya | Ingot, rod | Cu-Sn | 355/428.16 |
| | ETD 94/330 | Büyükkaya | Pin, shaft fragment | Cu-Sn | 357/431.117 |
| | ETD 94/390 | Büyükkaya | Eye needle | Cu-Sn | 355/428.91 |
| | ETD 94/463 | Büyükkaya | Ring, wire | Cu-Sn-Ni-Ag | 356/431.142 |

| Mannheim Number | Object Number | Location | Object Type | Alloy type | Context (number or description) |
|-----------------|---------------|-----------|------------------------|------------|---------------------------------|
| | ETD 94/470 | Büyükkaya | Bead | Cu-Sn | 354/430.134 |
| | ETD 94/475 | Büyükkaya | Awl | Cu-As-Sn | 357/431.82 |
| | ETD 94/483 | Büyükkaya | Awl | Cu-Sn | 355/430.276 |
| | ETD 94/5 | Büyükkaya | Wire, round section | Cu-Sn | 355/430.10 |
| | ETD 95/268 | Büyükkaya | Waste, casting | Cu-Sn | 352/427-428.29 |
| | ETD 96/25 | Büyükkaya | Pin, double headed | Cu-Sn | 344/303.4 |
| | ETD 96/26 | Büyükkaya | Pendant, indeterminate | Cu-Sn-Pb | 356/427.122 |
| | ETD 96/48 | Büyükkaya | Wire, round section | Cu-As | 352/421.28 |
| | ETD 96/49 | Büyükkaya | Sheet, indeterminate | Cu-Sn | 346/410.14 |
| | ETD 96/52 | Büyükkaya | Wire, square section | Cu | 353/427.16 |
| | ETD 96/56 | Büyükkaya | Rod | Cu | 347/410.36 |
| | ETD 97/195 | Büyükkaya | Awl | Cu-Sn | 347/428.9 |
| | ETD 97/202A | Büyükkaya | Awl | Cu | 348/414.3 |
| | ETD 97/202B | Büyükkaya | Pin, shaft fragment | Cu-Sn | 348/414.3 |
| | ETD 97/209 | Büyükkaya | Indeterminate | Cu-Sn | 347/415.P18 |
| | ETD 97/211 | Büyükkaya | Indeterminate | Cu | 346/430.22 |
| | ETD 97/227 | Büyükkaya | Pin, nodular | Cu-As | 359/426.40 |
| | ETD 97/231 | Büyükkaya | Indeterminate | Cu-Sn | 347/415.P9 |
| | ETD 97/232 | Büyükkaya | Ring, wire | Cu-Sn | 347/412.7 |
| | ETD 97/234 | Büyükkaya | Awl | Cu-As | 352/420.76 |
| | ETD 97/238 | Büyükkaya | Eye needle | Cu-Sn | 357/427.24 |
| | ETD 97/259 | Büyükkaya | Awl | Cu-Sn | 345/413.102 |
| | ETD 97/262 | Büyükkaya | Ring, wire | Cu-Sn | 352/420.5 |
| | ETD 97/269 | Büyükkaya | Sheet, indeterminate | Cu-Sn | 347/410.148 |
| | ETD 97/271 | Büyükkaya | Spiral | Cu-Sn | 357/427.9 |
| | ETD 97/272 | Büyükkaya | Indeterminate | Cu | 352/420.17 |

| Mannheim Number | Object Number | Location | Object Type | Alloy type | Context (number or description) |
|------------------|---------------|-----------------------------------|-------------------------------------|-------------|---------------------------------|
| | ETD 97/341 | Büyükkaya | Toggle Pin | Cu-Sn | 347/428.7 |
| | ETD 98/08 | Büyükkaya | Wire, round section | Cu-Sn | 346/413.498 |
| | ETD 98/10 | Büyükkaya | Fibula | Cu-As | 345/413.330 |
| | ETD 98/20 | Büyükkaya | Ring, wire | Cu-Sn | 348/414.450 |
| | ETD 98/26 | Büyükkaya | Fibula | Cu | 347/414.664 |
| | Bo 99/17 | Granary | Bilobate socketed arrowhead | Cu-Sn-Pb | 309/343.2 |
| | Bo 99/18 | Granary | Bilobate socketed arrowhead, barbed | Cu-Sn-Pb | 311/344.11 |
| | Bo 99/19 | Granary | Bilobate socketed arrowhead, barbed | Cu-Sn-Pb | 309/343.43 |
| | ETD 99/65 | Granary | Sheet, indeterminate | Cu-Sn-Pb | 309/344.98 |
| MA-132281 | Bo 11/14 | Kesikkaya - Kesikkaya, South | Bilobate socketed arrowhead, barbed | Cu-As-Sn-Pb | 0 |
| | Bo 12/08 | Lower City - City Wall | Fibula | Cu-Sn | 0 |
| | Bo 13/103 | Lower City - City Wall | Sheet, decorated | Cu-Sn | 0 |
| | Bo 13/29 | Lower City - City Wall | Sheet, decorated | Cu-Sn | 0 |
| | Bo 13/6 | Lower City - City Wall | Sheet, decorated | Cu-Sn | 0 |
| | Bo 09/1064 | Lower City - Kesikkaya, Northwest | Fibula | Cu-Sn | 604 |
| | Bo 09/1712 | Lower City - Kesikkaya, Northwest | Fibula | Cu-Sn-Pb | 645 |
| MA-132225 | Bo 10/9 | Lower City - Kesikkaya, Northwest | Pin, double headed | Cu-Sn | 2 |
| | Bo 11/35 | Lower City - Kesikkaya, South | Eye needle | Cu-Sn | 305 |
| | Bo 13/10 | Lower City - Kesikkaya, South | Awl | Cu-Sn | 302 |
| | Bo 13/113 | Lower City - Kesikkaya, South | Pin, shaft fragment | Cu-Sn | 339 |
| | Bo 13/119 | Lower City - Kesikkaya, South | Wire, round section | Cu-Sn | 343 |
| | Bo 13/130 | Lower City - Kesikkaya, South | Indeterminate | Cu-Sn | 342 |
| | Bo 13/198 | Lower City - Kesikkaya, South | Wire, round section | Cu-Sn | 367 |
| | Bo 13/42 | Lower City - Kesikkaya, South | Bilobate socketed arrowhead, barbed | Cu-Sn | 313 |
| | Bo 13/65 | Lower City - Kesikkaya, South | Wire, round section | Cu | 338 |

| Mannheim Number | Object Number | Location | Object Type | Alloy type | Context (number or description) |
|------------------------|----------------------|-------------------------------|-------------------------------------|-------------------|---|
| | Bo 13/97 | Lower City - Kesikkaya, South | Rod | Cu-Sn | 322 |
| MA-132561 | Bo 554/p | Lower City - Northern Quarter | Fibula | Cu-Sn | Boehmer 1972: n. 161 |
| | Bo 73/57b | Lower City - Northern Quarter | Fibula | Cu-Sn | J/19-20; Phrygian urn grave 2/73; Neve 1975: 95 |
| | Bo 73/57c | Lower City - Northern Quarter | Fibula | Cu-Sn | J/19-20; Phrygian urn grave 2/73; Neve 1975: 95 |
| | Bo 73/59b | Lower City - Northern Quarter | Fibula | Cu-Sn-Ni | J/19 temple terrace, Phrygian urn grave 3/73; Neve 1975: 95 |
| | Bo 73/59c | Lower City - Northern Quarter | Fibula | Cu-Sn-Ni | J/19 tempel terrace, Phrygian Urn Grave 3/73; Neve 1975: 95 |
| | Bo 73/59d | Lower City - Northern Quarter | Fibula | Cu-Sn | J/19 Phrygian pithos burial (3/73); Neve 1975: 95 |
| | Bo 73/77 | Lower City - Northern Quarter | Fibula | Cu-Sn | J/19-20, trench 1/8, over the stone debris, 1.5m northwest of urn 2/73; Neve 1975: 95 |
| MA-132194 | Bo 861/t | Lower City - Northern Quarter | Socketed lance | Cu-Sn | Boehmer 1972: n. 207 |
| MA-132191 | Bo 864/t | Lower City - Northern Quarter | Sheet, decorated | Cu-Sn | Boehmer 1972: n. 171 |
| | ETD 99/61 | Northwest Slope - Granary | Wire, round section | Cu-Sn | 309/343.100 |
| | ETD 99/62 | Northwest Slope - Granary | Eye needle, fragment | Cu-Sn | 308/343.51 |
| | ETD 99/63 | Northwest Slope - Granary | Fibula | Cu-Sn | 309/343.84 |
| | ETD 99/64 | Northwest Slope - Granary | Eye needle, fragment | Cu-Sn | 309/342.57 |
| | ETD 99/66 | Northwest Slope - Granary | Wire, round section | Cu-Sn | 310/343.33 |
| | ETD 99/77 | Northwest Slope - Granary | Wire, round section | Cu-Sn | 308/342.17 |
| | ETD 99/91 | Northwest Slope - Granary | Sheet, indeterminate | Cu-Sn-Ni | 309/343.102 |
| | Bo 07/566 | Northwest Slope - Yenicekale | Fibula | Cu-Sn-Pb | 515 |
| | 1-106-85 | Upper City | Bilobate socketed arrowhead, barbed | Cu-As-Sn-Pb | |
| | 1-42-88 | Upper City | Trilobate socketed arrowhead | Cu-As-Pb | |
| | 1-85-89 | Upper City | Bilobate socketed arrowhead | Cu-Sn-Pb | |
| | ETD 96/11 | Upper City - East reservoirs | Fibula | Cu-Sn-Pb | 341/299.7 |
| | ETD 96/55 | Upper City - East reservoirs | Bilobate socketed arrowhead | Cu-Sn-Pb | 347/303.2 |
| | Bo 88/37 | Upper City - Nişantepe | Fibula | Cu-Sn | M/12-d/7 |
| | 1-3-88 | Upper City - Südburg | Bilobate socketed arrowhead, barbed | Cu-Sn-Pb | |

| Mannheim Number | Object Number | Location | Object Type | Alloy type | Context (number or description) |
|------------------------|----------------------|-----------------------------------|-----------------------|-------------------|--|
| | 1-2430-91 | Upper City - Südburg | Fibula | Cu-Sn-Zn | |
| | Bo 89/128 | Upper City - Südburg | Toggle Pin | Cu-Sn-Pb | N/12-h/6 |
| | Bo 89/29 | Upper City - Südburg | Ornament | Cu | N/12-k/6 |
| | Bo 89/31 | Upper City - Südburg | Tweezers | Cu-Sn | N/12-f/2 |
| | Bo 89/99 | Upper City - Südburg | Toggle Pin | Cu | O/12-g/5-6 |
| | 1-1990-81 | Upper City - Yerkapi | Pin, double headed | Cu-Sn | found during restoration of the Yerkapi complex. |
| | Bo 05/28 | Upper City West - Sarikale Valley | Tweezers | Cu-Sn | |
| MA-132393 | Bo 06/1639 | Upper City West - Sarikale Valley | Indeterminate | Cu-Sn | 230 |
| MA-132380 | Bo 06/1765 | Upper City West - Sarikale Valley | Indeterminate | Cu-As | 283 |
| MA-132200 | Bo 06/233 | Upper City West - Sarikale Valley | Fibula | Cu | 0 |
| MA-132405 | Bo 06/2330 | Upper City West - Sarikale Valley | Eye needle, fragment | Cu | 944 |
| MA-132370 | Bo 06/515 | Upper City West - Sarikale Valley | Insert, hammer-shaped | Cu-Sn | 78 |
| MA-132512 | Bo 06/561 | Upper City West - Sarikale Valley | Ring, wire | Cu-Sn | 131 |
| | Bo 07/1325 | Upper City West - Sarikale Valley | Fibula | Cu-Sn | 636 |
| | Bo 07/508 | Upper City West - Yenicekale | Sheet, indeterminate | Cu-Sn | 501 |
| KERKENES DAĞ | | | | | |
| LATE IRON AGE | | | | | |
| | 00CT11U01met01 | Cappadocian Gate | Tack | Cu-Sn | CT11 U01 |
| | 00CT50U02met01 | Cappadocian Gate | Tweezers | Cu-Sn | CT50 U02 |
| | 00CT51U01met01 | Cappadocian Gate | Fibula | Cu-Sn | CT51 U01 |
| MA-132591 | 02TR03U11met02 | Cappadocian Gate | Sheet, indeterminate | Cu-Sn | TR03 U11 |
| | 02TR04U04met03 | Cappadocian Gate | Eye needle, fragment | Cu-Sn-Ni | TR04 U04 |

| Mannheim Number | Object Number | Location | Object Type | Alloy type | Context (number or description) |
|------------------------|----------------------|------------------|-------------------------------------|-------------------|--|
| | 09CAPP000met01 | Cappadocian Gate | Pin, double headed | Cu-Sn | CAPP U00 |
| MA-132600 | 10TR13U14met02 | Cappadocian Gate | Sheet, indeterminate | Cu-Sn | TR13 U14 |
| | 10TR13U16met01 | Cappadocian Gate | Bilobate socketed arrowhead, barbed | Cu-Sn-Pb | TR13 U16 |
| MA-132620 | 11TR23U08met01 | Cappadocian Gate | Bilobate socketed arrowhead, barbed | Cu-Sn-Pb | TR23 U08 |
| MA-132601 | 11TR23U11met01 | Cappadocian Gate | Trilobate socketed arrowhead | Cu-Sn-Pb | TR23 U11 |
| MA-132607 | 11TR23U12met01 | Cappadocian Gate | Sheet, indeterminate | Cu-Sn | TR23 U12 |
| MA-132597 | 11TR23U21met01 | Cappadocian Gate | Sheet, indeterminate | Cu-Sn | TR23 U21 |
| MA-132594 | 11TR23U22met01 | Cappadocian Gate | Pin, double headed | Cu-Sn | TR23 U22 |
| | 11TR23U36met01 | Cappadocian Gate | Pin, double headed | Cu-Sn | TR23 U36 |
| | 11TR24U06met01 | Cappadocian Gate | Pin, shaft fragment | Cu-Sn-Pb | TR24 U06 |
| MA-132629 | 11TR24U11met01 | Cappadocian Gate | Sheet, indeterminate | Cu-Sn-Pb | TR24 U11 |
| MA-132631 | 11TR24U11met02 | Cappadocian Gate | Nail | Cu-Sn | TR24 U11 |
| MA-132626 | 11TR24U11met03 | Cappadocian Gate | Nail | Cu-Sn | TR24 U11 |
| MA-132615 | 11TR24U11met03 | Cappadocian Gate | Sheet, indeterminate | Cu-Sn | TR24 U11 |
| MA-133069 | 11TR24U11met04 | Cappadocian Gate | Trilobate socketed arrowhead | Cu-Sn-Pb | TR24 U11 |
| MA-132593 | 11TR24U11met05 | Cappadocian Gate | Sheet, indeterminate | Cu-Sn | TR24 U11 |
| MA-132608 | 11TR24U15met01 | Cappadocian Gate | Pin, double headed | Cu-Sn | TR24 U15 |
| MA-132612 | 11TR24U17met01 | Cappadocian Gate | Tack | Cu-Sn | TR24 U17 |
| MA-132624 | 11TR24U20met01 | Cappadocian Gate | Pin, double headed | Cu-Sn | TR24 U20 |
| MA-132606 | 11TR24U21met01 | Cappadocian Gate | Pin, double headed | Cu-Sn | TR24 U21 |
| MA-132613 | 11TR24U21met02 | Cappadocian Gate | Tool, indeterminate | Cu-As-Sn-Pb | TR24 U21 |
| MA-132619 | 11TR24U22met03 | Cappadocian Gate | Spiral | Cu-Sn | TR24 U22 |
| MA-132622 | 11TR24U22met04 | Cappadocian Gate | Pin, double headed | Cu-Sn | TR24 U22 |
| MA-132614 | 11TR24U22met06 | Cappadocian Gate | Pin, tulip | Cu-Sn | TR24 U22 |
| MA-132605 | 11TR24U22met07 | Cappadocian Gate | Pin, tulip | Cu-Sn | TR24 U22 |
| MA-132596 | 11TR24U22met08 | Cappadocian Gate | Pin, tulip | Cu-Sn-Pb | TR24 U22 |

| Mannheim Number | Object Number | Location | Object Type | Alloy type | Context (number or description) |
|------------------------|----------------------|------------------|--------------------------------------|-------------------|--|
| | 11TR30U10met01 | Cappadocian Gate | Pin, indeterminate | Cu-Sn | TR30 U10 |
| | 03TR06U12met01 | Megaron | Trilobate socketed arrowhead, barbed | Cu-Sn-Pb | TR06 U12 |
| MA-132625 | 00CT18U17met01 | Palace | Pin, double headed | Cu-Sn | CT18 U17 |
| MA-132604 | 00CT18U17met02 | Palace | Pin, shaft fragment | Cu-Sn | CT18 U17 |
| MA-132630 | 02TR01U02met01 | Palace | Sheet, decorated | Cu-Sn | TR01 U02 |
| MA-132628 | 02TR01U02met02 | Palace | Sheet, decorated | Cu-Sn | TR01 U02 |
| | 02TR01U02met04 | Palace | Nail | Cu-Sn | TR01 U02 |
| | 02TR01U07met01 | Palace | Sheet, indeterminate | Cu-Sn-Zn | TR01 U07 |
| | 02TR01U07met02 | Palace | Sheet, indeterminate | Cu-Sn-Zn | TR01 U07 |
| | 02TR02U04met01 | Palace | Sheet, indeterminate | Cu-Sn | TR02 U04 |
| | 02TR02U10met08 | Palace | Ring, wire | Cu-Sn | TR02 U10 |
| | 02TR02U10met09 | Palace | Ring, wire | Cu-Sn | TR02 U10 |
| | 02TR02U10met11 | Palace | Band | Cu-Sn-Zn | TR02 U10 |
| MA-132599 | 03TR05U02met03 | Palace | Nail | Cu-Sn | TR05 U02 |
| MA-132598 | 04TR11U14met01 | Palace | Waste, casting | Cu-Sn | TR11 U14 |
| | 04TR15U01met01 | Palace | Sheet, indeterminate | Cu-Sn | TR15 U01 |
| | 04TR16U15met03 | Palace | Sheet, indeterminate | Cu-Sn | TR16 U15 |
| | 05TR15U09met01 | Palace | Sheet, indeterminate | Cu-Ag | TR15 U09 |
| | 05TR15U14met02 | Palace | Pin, double headed | Cu-Sn | TR15 U14 |
| | 05TR16U17met02 | Palace | Wire, square section, twisted | Cu-Sn | TR16 U17 |
| | 05TR16U17met03 | Palace | Wire, square section | Cu-Sn | TR16 U17 |
| | 05TR17U12met01 | Palace | Ornament | Cu-Sn-Zn | TR17 U12 |
| | 05TR17U14met01 | Palace | Rivet | Cu-Sn-Zn | TR17 U14 |
| | 05TR17U14met01 | Palace | Sheet, decorated | Cu-Sn-Zn | TR17 U14 |
| MA-132627 | 05TR17U14met02 | Palace | Sheet, indeterminate | Cu-Sn | TR17 U14 |
| | 05TR17U14met06 | Palace | Sheet, indeterminate | Cu-Sn | TR17 U14 |

| Mannheim Number | Object Number | Location | Object Type | Alloy type | Context (number or description) |
|------------------------|----------------------|-----------------|-------------------------------------|-------------------|--|
| | 05TR21U09met03 | Palace | Nail | Cu | TR21 U09 |
| | 05TR21U12met01 | Palace | Nail | Cu-Sn | TR21 U12 |
| | 05TR21U17met01 | Palace | Nail | Cu-Sn | TR21 U17 |
| | 96TT17U05met01 | Palace | Nail | Cu-Sn | TT17 U05 |
| | 96ST05U07met02 | South West | Tweezers | Cu-Sn | ST05 U07 |
| MA-132611 | 04TT25U08met01 | Street | Pin, shaft fragment | Cu-Sn | TT25 U08 |
| MA-132609 | 04TT25U08met02 | Street | Wire, round section | Cu-Sn | TT25 U08 |
| MA-132590 | 07TT27U05met01 | Street | Pin, double headed | Cu-Sn | TT27 U05 |
| MA-132595 | 07TT31U04met01 | Street | Fibula | Cu-Sn | TT31 U04 |
| MA-132623 | 11TR29U14met02 | Urban Block 8 | Pin, scroll | Cu-Sn | TR29 U14 |
| MA-132618 | 11TR29U32met01 | Urban Block 8 | Bilobate socketed arrowhead, barbed | Cu-Sn-Pb | TR29 U32 |
| MA-132621 | 11TR29U34met02 | Urban Block 8 | Indeterminate | Cu-Sn | TR29 U34 |
| MA-132617 | 11TR29U34met03 | Urban Block 8 | Sheet, indeterminate | Cu-Sn | TR29 U34 |
| MA-132616 | 96TT15U13met05 | Urban Block 8 | Pin, shaft fragment | Cu-Sn | TT15 U13 |
| MA-132602 | 97TT15U00met01 | Urban Block 8 | Band | Cu-Sn | TT15 U00 |
| MA-132603 | 98TT21U01met02 | Urban Block 8 | Pin, shaft fragment | Cu-Sn | TT21 U01 |

APPENDIX B: EDXRF RESULTS

| Mannheim Number | Object Number | Cu wt. % | Sn wt. % | As wt. % | Pb wt. % | Ni wt. % | Co wt. % | Fe wt. % | Zn wt. % | Sb wt. % | Bi wt. % | Ag wt. % | Au wt. % | Te wt. % | Se wt. % | Mn wt. % |
|--------------------------|-----------------------|----------|----------|----------|----------|----------|-------------|----------|-------------|----------|-------------|----------|-------------|-------------|-------------|-------------|
| BOĞAZKÖY | | | | | | | | | | | | | | | | |
| MIDDLE BRONZE AGE | | | | | | | | | | | | | | | | |
| MA-132227 | Bo 10/199 | 97 | 0.139 | 1.45 | 0.235 | 0.085 | <i>b.d.</i> | 0.687 | 0.086 | 0.092 | 0.012 | 0.048 | 0.015 | 0.004 | 0.002 | 0.002 |
| MA-132259 | Bo 10/332 | 97 | 0.045 | 1.95 | 0.238 | 0.256 | 0.037 | 0.643 | 0.031 | 0.044 | 0.007 | 0.024 | 0.007 | 0.004 | 0.001 | 0.001 |
| MA-132246 | Bo 10/341 | 96 | 0.830 | 1.50 | 0.166 | 0.195 | 0.006 | 0.865 | 0.131 | 0.100 | 0.030 | 0.025 | 0.016 | 0.029 | <i>b.d.</i> | 0.002 |
| MA-132250 | Bo 10/482 | 100 | 0.006 | 0.166 | 0.024 | 0.072 | 0.003 | 0.032 | 0.034 | 0.041 | 0.004 | 0.034 | 0.001 | 0.002 | 0.014 | <i>b.d.</i> |
| MA-132303 | Bo 11/590 | 100 | 0.005 | 0.036 | 0.023 | 0.081 | 0.001 | 0.040 | 0.008 | 0.016 | 0.001 | 0.027 | <i>b.d.</i> | 0.001 | 0.007 | <i>b.d.</i> |
| LATE BRONZE AGE | | | | | | | | | | | | | | | | |
| MA-132188 | Bo 284/e | 94 | 0.347 | 1.36 | 0.024 | 1.04 | 0.020 | 0.134 | 0.019 | 0.057 | 0.012 | 0.228 | 2.450 | 0.010 | 0.008 | <i>b.d.</i> |
| MA-132189 | Bo 284/e | 5 | 0.354 | 0.014 | 0.075 | 0.029 | <i>b.d.</i> | 0.205 | 0.377 | 0.146 | <i>b.d.</i> | 7.312 | 86.652 | 0.037 | <i>b.d.</i> | <i>b.d.</i> |
| MA-132180 | Bo 477/d | 90 | 5.38 | 0.331 | 4.13 | 0.034 | 0.015 | 0.080 | 0.038 | 0.050 | 0.013 | 0.016 | 0.004 | 0.012 | 0.005 | <i>b.d.</i> |
| MA-136322 | Boehmer 1972: Nr. 190 | 99 | 0.011 | 0.086 | 0.030 | 0.522 | 0.004 | 0.077 | <i>b.d.</i> | 0.007 | 0.001 | 0.023 | <i>b.d.</i> | 0.000 | <i>b.d.</i> | <i>b.d.</i> |
| MA-136329 | ETD 95/231 | 82 | 0.028 | 0.688 | 0.007 | 13.08 | 0.562 | 3.15 | 0.048 | 0.055 | 0.004 | 0.025 | 0.003 | 0.003 | <i>b.d.</i> | 0.005 |
| MA-136321 | ETD 98/21 | 72 | 0.045 | 26.92 | 0.348 | 0.156 | 0.003 | 0.176 | 0.113 | 0.262 | 0.013 | 0.014 | <i>b.d.</i> | <i>b.d.</i> | 0.003 | 0.002 |
| MA-136336 | Bo 09/1095 | 99 | 0.006 | 0.095 | 0.031 | 0.129 | 0.049 | 0.270 | <i>b.d.</i> | 0.005 | <i>b.d.</i> | 0.022 | <i>b.d.</i> | 0.004 | <i>b.d.</i> | <i>b.d.</i> |
| MA-136326 | Bo 09/355 | 81 | 0.039 | 1.01 | 0.018 | 15.83 | 0.501 | 1.11 | 0.096 | 0.073 | 0.001 | 0.022 | 0.013 | 0.007 | 0.001 | <i>b.d.</i> |
| MA-136338 | Bo 09/972 | 68 | 0.423 | 0.167 | 0.002 | 22.43 | 2.70 | 5.79 | 0.042 | 0.009 | <i>b.d.</i> | 0.002 | <i>b.d.</i> | 0.003 | <i>b.d.</i> | <i>b.d.</i> |
| MA-132213 | Bo 10/13 | 97 | 0.928 | 1.33 | 0.157 | 0.130 | 0.006 | 0.365 | 0.009 | 0.043 | 0.018 | 0.031 | 0.002 | 0.001 | 0.003 | <i>b.d.</i> |
| MA-132244 | Bo 10/186 | 98 | 0.004 | 1.43 | 0.012 | 0.036 | <i>b.d.</i> | 0.287 | <i>b.d.</i> | 0.053 | 0.004 | 0.007 | <i>b.d.</i> | 0.007 | 0.009 | <i>b.d.</i> |
| MA-132267 | Bo 10/189 | 93 | 4.64 | 0.551 | 0.456 | 0.066 | 0.004 | 0.783 | 0.060 | 0.027 | 0.010 | 0.035 | 0.005 | 0.013 | 0.007 | 0.015 |
| MA-132232 | Bo 10/190 | 97 | 0.041 | 1.14 | 0.199 | 0.726 | 0.092 | 0.439 | 0.067 | 0.034 | 0.001 | 0.013 | 0.004 | 0.003 | 0.004 | <i>b.d.</i> |
| MA-132209 | Bo 10/20 | 95 | 3.36 | 1.46 | 0.131 | 0.051 | 0.001 | 0.278 | 0.004 | 0.059 | 0.005 | 0.020 | 0.001 | 0.005 | 0.007 | <i>b.d.</i> |
| MA-132229 | Bo 10/233 | 94 | 0.324 | 2.93 | 0.063 | 0.318 | 0.010 | 1.06 | 0.044 | 0.764 | 0.034 | 0.042 | 0.005 | <i>b.d.</i> | 0.004 | <i>b.d.</i> |
| MA-132230 | Bo 10/236 | 93 | 3.86 | 0.771 | 0.505 | 0.237 | 0.069 | 0.984 | 0.123 | 0.091 | 0.040 | 0.086 | 0.024 | 0.009 | 0.005 | <i>b.d.</i> |

| Mannheim Number | Object Number | Cu wt. % | Sn wt. % | As wt. % | Pb wt. % | Ni wt. % | Co wt. % | Fe wt. % | Zn wt. % | Sb wt. % | Bi wt. % | Ag wt. % | Au wt. % | Te wt. % | Se wt. % | Mn wt. % |
|-----------------|---------------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|
| MA-132219 | Bo 10/238 | 97 | 0.058 | 1.52 | 0.126 | 0.137 | 0.010 | 1.37 | 0.053 | 0.041 | 0.006 | 0.022 | 0.005 | b.d. | 0.002 | b.d. |
| MA-132211 | Bo 10/24 | 93 | 6.59 | 0.457 | 0.038 | 0.078 | 0.005 | 0.122 | 0.001 | 0.028 | 0.001 | 0.005 | 0.004 | 0.004 | 0.006 | b.d. |
| MA-132231 | Bo 10/242 | 96 | 0.038 | 2.06 | 1.51 | 0.110 | 0.017 | 0.249 | 0.167 | 0.087 | 0.008 | 0.026 | 0.041 | 0.006 | 0.006 | b.d. |
| MA-132220 | Bo 10/243 | 98 | 0.028 | 0.886 | 0.042 | 0.110 | 0.008 | 0.518 | 0.019 | 0.046 | 0.013 | 0.030 | 0.002 | 0.001 | 0.003 | b.d. |
| MA-132242 | Bo 10/244 | 98 | 0.081 | 0.838 | 0.089 | 0.107 | 0.005 | 0.531 | 0.203 | 0.087 | 0.041 | 0.035 | 0.051 | b.d. | 0.010 | 0.001 |
| MA-132241 | Bo 10/249 | 99 | 0.024 | 0.543 | 0.053 | 0.137 | 0.007 | 0.384 | 0.159 | 0.117 | b.d. | 0.054 | b.d. | b.d. | b.d. | b.d. |
| MA-132266 | Bo 10/250 | 92 | 4.56 | 1.74 | 0.586 | 0.074 | 0.004 | 0.986 | 0.090 | 0.060 | 0.015 | 0.023 | 0.015 | 0.008 | 0.002 | 0.013 |
| MA-132240 | Bo 10/251 | 95 | 0.033 | 2.63 | 0.408 | 0.075 | 0.008 | 1.01 | 0.226 | 0.116 | 0.011 | 0.024 | 0.088 | 0.009 | 0.004 | 0.002 |
| MA-132245 | Bo 10/254 | 99 | 0.011 | 0.012 | 0.008 | 0.015 | 0.004 | 0.413 | 0.682 | 0.035 | 0.004 | 0.028 | 0.121 | 0.009 | 0.008 | b.d. |
| MA-132239 | Bo 10/257 | 100 | 0.012 | 0.050 | 0.016 | 0.066 | 0.001 | 0.048 | 0.019 | 0.029 | 0.006 | 0.010 | 0.005 | 0.002 | 0.001 | b.d. |
| MA-132238 | Bo 10/282 | 97 | 0.049 | 2.08 | 0.118 | 0.129 | 0.001 | 0.394 | 0.119 | 0.117 | 0.033 | 0.101 | 0.020 | b.d. | 0.008 | 0.002 |
| MA-132237 | Bo 10/287 | 96 | 0.089 | 2.60 | 0.433 | 0.136 | 0.004 | 1.00 | 0.073 | 0.065 | 0.002 | 0.021 | 0.015 | b.d. | 0.001 | 0.008 |
| MA-132235 | Bo 10/305 | 99 | 0.019 | 0.551 | 0.117 | 0.066 | 0.004 | 0.137 | 0.110 | 0.048 | 0.009 | 0.012 | 0.038 | 0.014 | 0.008 | 0.001 |
| MA-132236 | Bo 10/307 | 99 | 0.030 | 0.572 | 0.106 | 0.076 | b.d. | 0.162 | 0.078 | 0.035 | 0.013 | 0.010 | 0.065 | 0.002 | 0.001 | b.d. |
| MA-132233 | Bo 10/323 | 98 | 0.012 | 1.74 | 0.156 | 0.052 | 0.004 | 0.304 | 0.108 | 0.035 | 0.004 | 0.010 | 0.036 | 0.009 | 0.014 | b.d. |
| MA-132234 | Bo 10/343 | 97 | 0.045 | 1.91 | 0.056 | 0.112 | 0.006 | 0.269 | 0.032 | 0.025 | 0.017 | 0.036 | b.d. | 0.002 | 0.003 | b.d. |
| MA-132224 | Bo 10/37 | 87 | 0.038 | 0.523 | 0.122 | 11.23 | 0.172 | 0.644 | 0.024 | 0.050 | 0.014 | 0.036 | 0.004 | 0.003 | b.d. | b.d. |
| MA-132268 | Bo 10/372 | 99 | 0.020 | 0.366 | 0.039 | 0.063 | b.d. | 0.114 | 0.045 | 0.037 | b.d. | 0.037 | b.d. | b.d. | 0.008 | 0.002 |
| MA-132226 | Bo 10/38 | 98 | 0.024 | 0.511 | 0.054 | 0.275 | 0.012 | 0.720 | 0.090 | 0.066 | 0.013 | 0.095 | 0.036 | b.d. | 0.006 | 0.005 |
| MA-132269 | Bo 10/389 | 99 | 0.011 | 0.296 | 0.077 | 0.035 | 0.011 | 0.166 | 0.119 | 0.062 | 0.010 | 0.009 | 0.029 | b.d. | 0.005 | 0.005 |
| MA-132247 | Bo 10/391 | 95 | 0.030 | 3.56 | 0.468 | 0.045 | 0.004 | 0.971 | 0.157 | 0.107 | 0.019 | 0.024 | 0.011 | 0.002 | 0.005 | b.d. |
| MA-132248 | Bo 10/392 | 97 | 0.001 | 1.68 | 0.065 | 0.409 | 0.001 | 0.397 | 0.172 | 0.257 | 0.010 | 0.014 | 0.018 | 0.004 | b.d. | 0.003 |
| MA-132270 | Bo 10/393 | 89 | 8.91 | 0.826 | 0.270 | 0.178 | 0.004 | 0.165 | 0.100 | 0.076 | 0.015 | 0.021 | 0.016 | 0.008 | 0.005 | b.d. |
| MA-132264 | Bo 10/394 | 98 | 0.018 | 1.02 | 0.076 | 0.395 | 0.031 | 0.470 | 0.095 | 0.081 | 0.004 | 0.050 | 0.007 | 0.004 | 0.002 | b.d. |
| MA-132249 | Bo 10/402 | 99 | 0.020 | 0.150 | 0.055 | 0.093 | 0.066 | 0.595 | 0.126 | 0.055 | b.d. | 0.035 | 0.015 | 0.008 | b.d. | b.d. |
| MA-132272 | Bo 10/404 | 96 | 0.356 | 2.09 | 0.440 | 0.315 | 0.025 | 0.437 | 0.127 | 0.074 | 0.011 | 0.035 | 0.016 | 0.016 | 0.004 | b.d. |
| MA-132271 | Bo 10/416 | 85 | 0.031 | 1.24 | 0.044 | 11.39 | 0.451 | 1.97 | 0.108 | 0.038 | 0.010 | 0.023 | 0.025 | 0.011 | 0.002 | 0.003 |
| MA-132251 | Bo 10/456 | 98 | 0.022 | 1.31 | 0.075 | 0.067 | 0.003 | 0.217 | 0.088 | 0.091 | 0.017 | 0.039 | 0.031 | 0.006 | 0.006 | b.d. |

| Mannheim Number | Object Number | Cu wt. % | Sn wt. % | As wt. % | Pb wt. % | Ni wt. % | Co wt. % | Fe wt. % | Zn wt. % | Sb wt. % | Bi wt. % | Ag wt. % | Au wt. % | Te wt. % | Se wt. % | Mn wt. % |
|-----------------|---------------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|
| MA-132260 | Bo 10/496 | 94 | 4.28 | 0.805 | 0.135 | 0.248 | 0.031 | 0.426 | 0.140 | 0.053 | b.d. | 0.012 | 0.010 | 0.003 | 0.005 | b.d. |
| MA-132223 | Bo 10/53 | 87 | 8.03 | 0.219 | 4.04 | 0.119 | 0.004 | 0.337 | 0.139 | 0.107 | b.d. | 0.123 | 0.036 | 0.007 | 0.002 | 0.009 |
| MA-132208 | Bo 10/59 | 98 | 0.151 | 1.25 | 0.064 | 0.110 | 0.001 | 0.199 | 0.016 | 0.061 | 0.018 | 0.029 | 0.003 | 0.002 | 0.006 | b.d. |
| MA-132214 | Bo 10/64 | 95 | 0.074 | 1.67 | 2.03 | 0.237 | 0.008 | 0.913 | 0.057 | 0.065 | 0.018 | 0.060 | 0.011 | 0.006 | 0.001 | b.d. |
| MA-132228 | Bo 10/843 | 95 | 1.81 | 2.15 | 0.242 | 0.487 | 0.047 | 0.465 | 0.038 | 0.036 | 0.020 | 0.035 | 0.004 | 0.002 | 0.003 | b.d. |
| MA-132276 | Bo 10/846 | 91 | 6.73 | 0.551 | 0.252 | 0.051 | 0.002 | 0.132 | 1.169 | 0.028 | 0.022 | 0.054 | 0.124 | b.d. | 0.014 | b.d. |
| MA-132252 | Bo 10/853 | 94 | 3.48 | 0.895 | 1.06 | 0.050 | 0.004 | 0.472 | 0.164 | 0.121 | 0.022 | 0.109 | 0.052 | 0.014 | 0.004 | b.d. |
| MA-132280 | Bo 10/893 | 93 | 3.52 | 1.84 | 0.394 | 0.147 | 0.008 | 0.530 | 0.379 | 0.150 | 0.018 | 0.050 | 0.152 | 0.012 | 0.022 | 0.003 |
| MA-132221 | Bo 10/904 | 97 | 0.466 | 1.56 | 0.160 | 0.324 | b.d. | 0.240 | 0.047 | 0.053 | 0.010 | 0.018 | 0.009 | b.d. | 0.002 | b.d. |
| MA-132279 | Bo 10/928 | 98 | 0.038 | 0.570 | 0.344 | 0.053 | b.d. | 0.351 | 0.198 | 0.110 | 0.017 | 0.096 | 0.107 | 0.002 | 0.016 | 0.036 |
| MA-132215 | Bo 10/935 | 98 | 0.009 | 1.10 | 0.033 | 0.059 | 0.021 | 0.804 | 0.045 | 0.031 | b.d. | 0.013 | 0.012 | 0.002 | 0.004 | b.d. |
| MA-132217 | Bo 10/935 | 98 | 0.039 | 0.766 | 0.067 | 0.062 | 0.001 | 0.699 | 0.107 | 0.075 | 0.027 | 0.030 | 0.053 | 0.011 | b.d. | 0.001 |
| MA-132295 | Bo 11/492 | 97 | 0.064 | 1.12 | 0.140 | 0.064 | 0.016 | 0.459 | 0.278 | 0.150 | 0.042 | 0.033 | 0.135 | b.d. | 0.008 | 0.007 |
| MA-132296 | Bo 11/502 | 97 | 0.026 | 1.09 | 0.017 | 0.177 | 0.050 | 0.702 | 0.479 | 0.186 | 0.015 | 0.022 | 0.138 | 0.007 | 0.023 | 0.006 |
| MA-132292 | Bo 11/522 | 95 | 0.061 | 2.97 | 0.164 | 0.074 | 0.011 | 0.320 | 0.839 | 0.255 | 0.035 | 0.022 | 0.125 | 0.008 | 0.003 | b.d. |
| MA-132297 | Bo 11/527 | 97 | 0.098 | 1.05 | 0.123 | 0.089 | 0.008 | 0.354 | 0.385 | 0.454 | 0.072 | 0.064 | 0.030 | b.d. | 0.003 | b.d. |
| MA-132290 | Bo 11/591 | 98 | 0.033 | 1.35 | 0.045 | 0.131 | 0.004 | 0.154 | 0.075 | 0.088 | 0.016 | 0.035 | 0.020 | 0.006 | b.d. | b.d. |
| MA-132210 | Bo 10/1512 | 90 | 6.85 | 2.01 | 0.332 | 0.128 | 0.011 | 0.315 | 0.005 | 0.090 | 0.011 | 0.041 | 0.001 | 0.002 | 0.004 | b.d. |
| MA-132207 | Bo 10/507 | 99 | 0.008 | 0.497 | 0.037 | 0.082 | 0.006 | 0.409 | 0.026 | 0.027 | 0.004 | 0.021 | 0.009 | 0.002 | 0.010 | b.d. |
| MA-132212 | Bo 10/544 | 90 | 7.13 | 2.08 | 0.334 | 0.128 | 0.013 | 0.365 | 0.047 | 0.100 | 0.010 | 0.043 | 0.005 | 0.003 | 0.005 | b.d. |
| MA-132222 | Bo 10/554 | 97 | 0.282 | 1.83 | 0.045 | 0.053 | 0.002 | 0.523 | 0.069 | 0.153 | 0.022 | 0.094 | 0.046 | 0.038 | 0.011 | b.d. |
| MA-132273 | Bo 10/558 | 97 | 0.023 | 1.98 | 0.245 | 0.048 | 0.010 | 0.812 | 0.011 | 0.042 | 0.007 | 0.031 | 0.006 | 0.001 | 0.009 | b.d. |
| MA-132263 | Bo 10/566 | 98 | 0.064 | 1.21 | 0.056 | 0.153 | 0.009 | 0.463 | 0.066 | 0.109 | 0.023 | 0.076 | 0.008 | 0.008 | 0.003 | 0.001 |
| MA-132274 | Bo 10/574 | 99 | 0.019 | 0.392 | 0.036 | 0.011 | 0.003 | 0.471 | 0.431 | 0.001 | 0.003 | 0.021 | 0.095 | b.d. | 0.008 | b.d. |
| MA-132298 | Bo 11/909 | 98 | 0.008 | 0.202 | 0.098 | 0.073 | 0.005 | 1.32 | b.d. | 0.007 | 0.003 | 0.012 | 0.004 | 0.002 | b.d. | 0.001 |
| MA-132253 | Bo 10/1232 | 94 | 2.72 | 1.01 | 1.03 | 0.040 | 0.002 | 0.497 | 0.093 | 0.085 | 0.021 | 0.091 | 0.020 | 0.010 | 0.004 | 0.001 |
| MA-132243 | Bo 10/1234 | 99 | 0.036 | 0.231 | 0.025 | 0.037 | 0.009 | 0.314 | 0.160 | 0.093 | 0.012 | 0.006 | 0.048 | 0.034 | 0.015 | 0.007 |
| MA-132277 | Bo 10/1277 | 97 | 0.118 | 1.63 | 0.282 | 0.169 | 0.008 | 0.262 | 0.054 | 0.030 | 0.005 | 0.048 | 0.006 | b.d. | 0.001 | b.d. |

| Mannheim Number | Object Number | Cu wt. % | Sn wt. % | As wt. % | Pb wt. % | Ni wt. % | Co wt. % | Fe wt. % | Zn wt. % | Sb wt. % | Bi wt. % | Ag wt. % | Au wt. % | Te wt. % | Se wt. % | Mn wt. % |
|-----------------|---------------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|
| MA-132254 | Bo 10/1282 | 98 | 0.044 | 1.07 | 0.191 | 0.051 | 0.003 | 0.505 | 0.043 | 0.064 | 0.010 | 0.035 | 0.003 | 0.006 | 0.002 | b.d. |
| MA-132255 | Bo 10/1283 | 93 | 4.81 | 0.972 | 0.101 | 0.145 | 0.006 | 0.702 | 0.069 | 0.035 | b.d. | 0.041 | 0.011 | 0.004 | 0.004 | 0.005 |
| MA-132258 | Bo 10/1291 | 94 | 3.24 | 1.58 | 0.241 | 0.041 | 0.002 | 0.714 | 0.086 | 0.057 | 0.004 | 0.016 | 0.026 | 0.006 | 0.009 | b.d. |
| MA-132257 | Bo 10/1292 | 97 | 0.882 | 1.10 | 0.074 | 0.052 | b.d. | 0.565 | 0.053 | 0.063 | 0.039 | 0.006 | b.d. | b.d. | 0.014 | 0.003 |
| MA-132261 | Bo 10/1294 | 92 | 6.10 | 1.56 | 0.191 | 0.030 | 0.005 | 0.336 | 0.124 | 0.050 | 0.011 | 0.017 | 0.015 | 0.016 | 0.007 | b.d. |
| MA-132262 | Bo 10/1295 | 97 | 0.304 | 2.20 | 0.174 | 0.061 | 0.001 | 0.341 | 0.051 | 0.058 | 0.010 | 0.049 | 0.016 | b.d. | 0.003 | b.d. |
| MA-132256 | Bo 10/1297 | 92 | 5.84 | 1.04 | 0.056 | 0.151 | 0.009 | 0.632 | 0.092 | 0.066 | 0.029 | 0.045 | 0.006 | b.d. | 0.008 | 0.001 |
| MA-132278 | Bo 10/1302 | 96 | 0.018 | 2.30 | 0.733 | 0.035 | 0.001 | 0.670 | 0.054 | 0.108 | 0.010 | 0.033 | 0.005 | 0.008 | 0.009 | b.d. |
| MA-132284 | Bo 11/15 | 93 | 0.049 | 5.20 | 0.135 | 0.076 | b.d. | 1.33 | 0.105 | 0.138 | 0.041 | 0.036 | b.d. | b.d. | 0.002 | b.d. |
| MA-132294 | Bo 11/18 | 99 | 0.071 | 0.197 | 0.022 | 0.090 | b.d. | 0.044 | 0.369 | 0.106 | 0.060 | 0.034 | 0.080 | 0.018 | b.d. | b.d. |
| MA-132286 | Bo 11/4 | 95 | 0.074 | 3.76 | 0.122 | 0.106 | 0.015 | 0.506 | 0.280 | 0.219 | 0.028 | 0.030 | 0.101 | b.d. | 0.006 | 0.005 |
| MA-132293 | Bo 11/42 | 86 | 11.89 | 0.937 | 0.149 | 0.112 | 0.009 | 0.382 | 0.034 | 0.079 | 0.007 | 0.023 | 0.006 | 0.008 | 0.007 | b.d. |
| MA-132289 | Bo 11/65 | 96 | 0.079 | 2.57 | 0.149 | 0.063 | b.d. | 0.689 | 0.047 | 0.074 | 0.009 | 0.037 | 0.007 | 0.006 | b.d. | b.d. |
| MA-136341 | Bo 13/39 | 89 | 0.071 | 1.07 | 0.054 | 6.01 | 0.221 | 3.47 | b.d. | 0.085 | 0.003 | 0.040 | b.d. | 0.005 | 0.002 | b.d. |
| MA-132185 | Bo 170/h | 98 | 0.098 | 1.44 | 0.305 | 0.029 | b.d. | 0.298 | 0.076 | 0.095 | 0.040 | 0.047 | 0.007 | 0.002 | 0.009 | b.d. |
| MA-132183 | Bo 171/h | 89 | 9.29 | 0.591 | 0.081 | 0.071 | 0.007 | 0.265 | 0.069 | 0.043 | b.d. | 0.095 | 0.014 | 0.006 | 0.001 | 0.002 |
| MA-132187 | Bo 173/h | 97 | 0.081 | 1.32 | 0.130 | 0.138 | 0.011 | 0.339 | 0.433 | 0.159 | 0.006 | 0.058 | 0.092 | 0.006 | 0.002 | b.d. |
| MA-132190 | Bo 216/p | 94 | 0.287 | 1.23 | 3.79 | 0.149 | 0.010 | 0.140 | 0.067 | 0.057 | 0.017 | 0.051 | 0.098 | 0.004 | 0.005 | b.d. |
| MA-132173 | Bo 77/385a | 98 | | 2.40 | | | | | | | | | | | | |
| MA-132172 | Bo 77/385b | 97 | 0.042 | 0.766 | 0.063 | 0.041 | 0.007 | 0.123 | 0.331 | 0.184 | 0.033 | 1.387 | 0.124 | 0.006 | 0.024 | 0.004 |
| MA-132184 | Bo 91/h | 94 | 1.56 | 1.51 | 0.035 | 0.144 | 0.003 | 0.133 | 0.063 | 0.082 | 0.009 | 0.191 | 1.771 | 0.015 | 0.005 | b.d. |
| MA-132186 | Bo 95/h | 97 | 0.098 | 2.52 | 0.102 | 0.138 | 0.002 | 0.152 | 0.005 | 0.126 | 0.006 | 0.033 | 0.003 | b.d. | 0.002 | b.d. |
| MA-132218 | Bo 10/1409 | 94 | 0.010 | 4.50 | 0.366 | 0.060 | 0.004 | 0.648 | 0.035 | 0.054 | 0.046 | 0.029 | 0.007 | 0.001 | 0.004 | 0.001 |
| MA-132265 | Bo 10/1425 | 96 | 0.054 | 2.17 | 0.260 | 0.370 | 0.015 | 0.795 | 0.187 | 0.104 | 0.006 | 0.022 | 0.032 | b.d. | b.d. | b.d. |
| MA-132288 | Bo 11/1203 | 98 | 0.096 | 0.975 | 0.018 | 0.067 | b.d. | 0.467 | 0.194 | 0.216 | 0.002 | 0.113 | 0.015 | b.d. | b.d. | b.d. |
| MA-132283 | Bo 11/1205 | 98 | 0.012 | 0.838 | 0.036 | 0.076 | 0.006 | 0.498 | 0.099 | 0.061 | 0.028 | 0.038 | 0.037 | 0.022 | 0.004 | b.d. |
| MA-132282 | Bo 11/1215 | 97 | 0.770 | 1.08 | 0.070 | 0.054 | 0.003 | 0.695 | 0.165 | 0.182 | 0.008 | 0.076 | 0.044 | 0.010 | 0.006 | 0.016 |
| MA-132291 | Bo 11/1223 | 98 | 0.024 | 0.388 | 0.068 | 0.139 | 0.025 | 0.554 | 0.253 | 0.127 | 0.021 | 0.004 | 0.013 | 0.022 | b.d. | b.d. |

| Mannheim Number | Object Number | Cu wt. % | Sn wt. % | As wt. % | Pb wt. % | Ni wt. % | Co wt. % | Fe wt. % | Zn wt. % | Sb wt. % | Bi wt. % | Ag wt. % | Au wt. % | Te wt. % | Se wt. % | Mn wt. % |
|-----------------|---------------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|
| MA-132179 | Bo 645/t | 95 | 2.34 | 1.73 | 0.123 | 0.132 | 0.005 | 0.668 | 0.039 | 0.164 | 0.002 | 0.049 | 0.088 | 0.006 | 0.005 | b.d. |
| MA-136337 | Dowel_1 | 97 | 0.056 | 1.95 | 0.253 | 0.145 | 0.006 | 0.376 | 0.026 | 0.030 | 0.045 | 0.036 | b.d. | 0.023 | 0.003 | 0.009 |
| MA-132196 | Bo 79/206 | 95 | 0.073 | 0.326 | 0.034 | 0.036 | 0.061 | 3.73 | 0.401 | 0.142 | 0.008 | 0.016 | 0.155 | 0.001 | 0.029 | b.d. |
| MA-132301 | Bo 82/109a | 99 | 0.017 | 0.270 | 0.065 | 0.053 | 0.004 | 0.272 | 0.221 | 0.101 | 0.010 | 0.015 | 0.049 | 0.014 | 0.013 | b.d. |
| MA-132176 | Bo 82/112 | 81 | 17.14 | 0.816 | 0.099 | 0.017 | b.d. | 0.250 | 0.018 | 0.262 | 0.002 | 0.008 | 0.003 | 0.009 | 0.014 | b.d. |
| MA-132182 | Bo 82/138 | 95 | 3.77 | 0.252 | 0.048 | 0.017 | 0.002 | 0.405 | 0.056 | 0.018 | 0.005 | 0.005 | 0.097 | 0.005 | 0.010 | b.d. |
| MA-132175 | Bo 82/140 | 83 | 16.12 | 0.364 | 0.012 | 0.007 | 0.001 | 0.519 | 0.029 | 0.010 | 0.001 | 0.002 | 0.003 | 0.006 | 0.013 | 0.003 |
| MA-132181 | Bo 82/141 | 93 | 4.09 | 1.58 | 1.26 | 0.012 | 0.002 | 0.202 | 0.001 | 0.042 | 0.001 | 0.004 | 0.011 | 0.007 | 0.009 | b.d. |
| MA-136323 | Bo 83/819 | 96 | 0.014 | 0.046 | 0.018 | 0.111 | 0.058 | 3.22 | b.d. | 0.031 | b.d. | 0.002 | b.d. | 0.011 | 0.066 | 0.012 |
| MA-132178 | Bo 84/551 | 96 | 1.72 | 0.929 | 0.058 | 0.320 | 0.006 | 0.359 | 0.016 | 0.038 | 0.004 | 0.088 | 0.004 | 0.002 | 0.012 | b.d. |
| MA-132299 | Bo 85/449 | 92 | 5.98 | 0.887 | 0.267 | 0.066 | b.d. | 0.351 | 0.547 | 0.176 | 0.027 | 0.018 | 0.101 | b.d. | 0.024 | b.d. |
| MA-132300 | Bo 85/71 | 85 | 13.81 | 0.357 | 0.040 | 0.016 | 0.002 | 0.258 | b.d. | 0.003 | 0.003 | 0.006 | b.d. | 0.003 | 0.010 | b.d. |
| MA-136343 | Bo 86/427 | 86 | 0.100 | 0.231 | 0.001 | 11.83 | 1.18 | 0.545 | 0.118 | 0.094 | 0.005 | 0.011 | 0.022 | 0.015 | b.d. | 0.002 |
| MA-132177 | Bo 86/94 | 89 | 10.08 | 0.524 | 0.091 | 0.032 | 0.029 | 0.434 | 0.051 | 0.193 | 0.008 | 0.005 | 0.009 | 0.008 | 0.005 | b.d. |
| MA-132308 | Bo 06/1058 | 87 | 0.032 | 1.67 | 0.059 | 9.02 | 0.278 | 1.26 | 0.005 | 0.145 | 0.039 | 0.051 | 0.004 | 0.016 | 0.002 | b.d. |
| MA-132323 | Bo 06/1141 | 80 | 14.56 | 3.93 | 0.257 | 0.058 | b.d. | 1.09 | b.d. | 0.107 | 0.006 | 0.005 | b.d. | 0.003 | 0.006 | 0.012 |
| MA-132408 | Bo 06/1148 | 97 | 0.068 | 1.26 | 0.686 | 0.097 | b.d. | 0.190 | 0.048 | 0.098 | 0.050 | 0.052 | 0.001 | 0.013 | 0.005 | b.d. |
| MA-136342 | Bo 08/1510 | 82 | 0.006 | 0.424 | 0.014 | 15.09 | 0.578 | 1.29 | 0.097 | 0.046 | 0.006 | 0.021 | 0.015 | 0.002 | 0.001 | b.d. |
| MA-132461 | Bo 06/1018 | 98 | 0.015 | 0.952 | 0.086 | 0.033 | b.d. | 0.308 | 0.059 | 0.080 | 0.011 | 0.004 | 0.024 | 0.006 | 0.013 | 0.002 |
| MA-132359 | Bo 06/106 | 92 | 0.020 | 4.13 | 2.07 | 0.101 | 0.020 | 1.20 | 0.133 | 0.126 | 0.012 | 0.036 | 0.018 | 0.003 | 0.002 | 0.002 |
| MA-132343 | Bo 06/108 | 89 | 0.692 | 0.269 | 0.024 | 8.39 | 0.855 | 0.441 | 0.254 | 0.025 | 0.002 | 0.002 | 0.041 | b.d. | 0.002 | b.d. |
| MA-132433 | Bo 06/124 | 99 | 0.234 | 0.547 | 0.196 | 0.033 | b.d. | 0.186 | 0.024 | 0.045 | 0.002 | 0.006 | 0.005 | 0.002 | 0.015 | b.d. |
| MA-132339 | Bo 06/127 | 89 | 9.83 | 0.369 | 0.051 | 0.005 | b.d. | 0.180 | 0.019 | 0.018 | 0.004 | 0.014 | 0.006 | 0.006 | 0.007 | b.d. |
| MA-132387 | Bo 06/1302 | 98 | 0.087 | 1.08 | 0.501 | 0.035 | 0.001 | 0.267 | 0.027 | 0.108 | 0.029 | 0.063 | 0.008 | 0.007 | 0.037 | 0.002 |
| MA-132428 | Bo 06/1342 | 85 | 13.20 | 0.465 | 0.808 | 0.037 | 0.001 | 0.366 | 0.082 | 0.057 | 0.012 | 0.053 | 0.011 | 0.001 | 0.002 | b.d. |
| MA-132385 | Bo 06/1364 | 97 | 0.041 | 1.68 | 0.172 | 0.051 | 0.002 | 0.324 | 0.134 | 0.154 | 0.029 | 0.078 | 0.058 | 0.010 | 0.001 | 0.008 |
| MA-132328 | Bo 06/1395 | 96 | 0.034 | 2.16 | 0.120 | 0.153 | 0.009 | 0.245 | 0.447 | 0.218 | 0.027 | 0.028 | 0.051 | 0.033 | 0.014 | 0.002 |
| MA-132306 | Bo 06/1397 | 89 | 0.319 | 7.72 | 0.156 | 0.767 | 0.016 | 1.09 | 0.181 | 0.208 | 0.013 | 0.083 | 0.035 | 0.011 | 0.014 | 0.004 |

| Mannheim Number | Object Number | Cu wt. % | Sn wt. % | As wt. % | Pb wt. % | Ni wt. % | Co wt. % | Fe wt. % | Zn wt. % | Sb wt. % | Bi wt. % | Ag wt. % | Au wt. % | Te wt. % | Se wt. % | Mn wt. % |
|-----------------|---------------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|
| MA-132464 | Bo 06/1399 | 97 | 0.067 | 1.27 | 0.571 | 0.045 | 0.001 | 0.258 | 0.156 | 0.341 | 0.037 | 0.087 | 0.036 | 0.008 | 0.009 | b.d. |
| MA-132334 | Bo 06/1439 | 91 | 0.416 | 0.695 | 0.746 | 0.102 | 0.054 | 0.469 | 3.494 | 1.442 | 0.030 | 0.280 | 0.932 | 0.314 | 0.003 | 0.006 |
| MA-132379 | Bo 06/1440 | 98 | 0.065 | 0.620 | 0.094 | 0.085 | b.d. | 0.707 | 0.260 | 0.151 | 0.016 | 0.046 | 0.075 | b.d. | 0.030 | 0.002 |
| MA-132450 | Bo 06/1446 | 93 | 0.574 | 0.740 | 1.86 | 0.309 | 0.003 | 3.23 | 0.113 | 0.096 | 0.036 | 0.004 | 0.028 | 0.001 | 0.004 | 0.026 |
| MA-132327 | Bo 06/1449 | 97 | 0.107 | 0.936 | 0.133 | 0.282 | 0.003 | 0.403 | 0.577 | 0.354 | b.d. | 0.050 | 0.195 | 0.011 | 0.019 | 0.002 |
| MA-132369 | Bo 06/1458 | 97 | 0.097 | 1.63 | 0.068 | 0.079 | 0.004 | 0.990 | 0.091 | 0.136 | b.d. | 0.034 | 0.019 | b.d. | 0.002 | b.d. |
| MA-132386 | Bo 06/1464 | 97 | 0.098 | 1.51 | 0.866 | 0.088 | 0.001 | 0.223 | 0.151 | 0.115 | 0.033 | 0.045 | 0.031 | 0.009 | 0.005 | b.d. |
| MA-132316 | Bo 06/1469 | 98 | 0.032 | 0.984 | 0.039 | 0.138 | b.d. | 0.133 | 0.094 | 0.118 | 0.019 | 0.148 | 0.030 | 0.014 | 0.018 | 0.005 |
| MA-132331 | Bo 06/1481 | 93 | 1.76 | 4.12 | 0.533 | 0.121 | 0.007 | 0.363 | 0.044 | 0.150 | 0.016 | 0.034 | 0.012 | 0.004 | 0.001 | b.d. |
| MA-132456 | Bo 06/1483 | 97 | 0.039 | 2.10 | 0.014 | 0.153 | 0.001 | 0.378 | 0.158 | 0.121 | 0.006 | 0.005 | 0.021 | b.d. | 0.011 | b.d. |
| MA-132442 | Bo 06/1497 | 99 | 0.009 | 0.931 | 0.106 | 0.070 | b.d. | 0.176 | 0.009 | 0.044 | 0.004 | 0.027 | 0.019 | 0.003 | 0.003 | b.d. |
| MA-132384 | Bo 06/1500 | 98 | 0.078 | 0.553 | 0.041 | 0.101 | 0.013 | 0.533 | 0.072 | 0.385 | b.d. | 0.008 | 0.008 | 0.003 | 0.003 | b.d. |
| MA-132449 | Bo 06/1506 | 99 | 0.015 | 0.629 | 0.060 | 0.018 | 0.002 | 0.087 | 0.061 | 0.073 | 0.007 | 0.003 | 0.015 | 0.005 | 0.014 | b.d. |
| MA-132366 | Bo 06/1508 | 84 | 14.32 | 0.876 | 0.122 | 0.036 | 0.003 | 0.219 | 0.057 | 0.083 | 0.007 | 0.012 | 0.009 | 0.007 | 0.009 | b.d. |
| MA-132319 | Bo 06/1512 | 94 | 4.85 | 0.722 | 0.004 | 0.046 | 0.004 | 0.371 | b.d. | 0.052 | b.d. | 0.005 | 0.054 | 0.002 | 0.010 | b.d. |
| MA-132392 | Bo 06/1513 | 85 | 13.93 | 0.428 | 0.176 | 0.021 | b.d. | 0.266 | 0.120 | 0.104 | 0.007 | 0.003 | 0.050 | 0.013 | 0.008 | b.d. |
| MA-132397 | Bo 06/153 | 97 | 0.318 | 1.87 | 0.270 | 0.111 | 0.001 | 0.299 | 0.020 | 0.166 | 0.012 | 0.039 | 0.004 | 0.004 | 0.010 | b.d. |
| MA-132312 | Bo 06/156 | 90 | 0.027 | 0.726 | 0.010 | 4.24 | 0.192 | 4.44 | 0.090 | 0.047 | 0.001 | 0.031 | 0.007 | b.d. | 0.001 | b.d. |
| MA-132500 | Bo 06/1563 | 92 | 5.11 | 1.53 | 0.163 | 0.276 | b.d. | 0.430 | 0.379 | 0.246 | 0.027 | 0.035 | 0.060 | 0.022 | 0.011 | 0.010 |
| MA-132452 | Bo 06/1565 | 86 | 12.45 | 0.636 | 0.166 | 0.062 | 0.001 | 0.297 | 0.007 | 0.032 | 0.023 | 0.048 | 0.003 | b.d. | 0.005 | b.d. |
| MA-132478 | Bo 06/1567 | 95 | 0.077 | 3.58 | 0.091 | 0.116 | 0.044 | 0.535 | 0.075 | 0.157 | 0.003 | 0.028 | 0.017 | 0.007 | 0.007 | 0.002 |
| MA-132470 | Bo 06/1576 | 98 | 0.096 | 1.25 | 0.280 | 0.091 | 0.006 | 0.281 | 0.143 | 0.128 | 0.021 | 0.048 | 0.038 | 0.011 | 0.005 | b.d. |
| MA-132498 | Bo 06/1582 | 93 | 0.041 | 5.65 | 0.150 | 0.161 | 0.007 | 1.05 | 0.062 | 0.140 | b.d. | 0.004 | 0.010 | b.d. | 0.001 | 0.004 |
| MA-132474 | Bo 06/1599 | 87 | 11.67 | 0.670 | 0.197 | 0.065 | b.d. | 0.062 | b.d. | 0.061 | 0.001 | 0.037 | 0.005 | 0.004 | 0.010 | b.d. |
| MA-132437 | Bo 06/160 | 92 | 7.13 | 0.162 | 0.054 | 0.028 | b.d. | 0.268 | 0.207 | 0.119 | 0.009 | 0.002 | 0.056 | 0.014 | 0.008 | 0.002 |
| MA-132350 | Bo 06/1600 | 98 | 0.046 | 1.19 | 0.038 | 0.407 | 0.009 | 0.308 | 0.019 | 0.047 | 0.001 | 0.028 | 0.004 | 0.001 | 0.006 | b.d. |
| MA-132444 | Bo 06/1601 | 82 | 15.71 | 0.966 | 0.079 | 0.635 | 0.021 | 0.265 | 0.067 | 0.042 | 0.005 | 0.006 | 0.014 | 0.008 | 0.012 | b.d. |
| MA-132406 | Bo 06/1609 | 85 | 12.23 | 1.62 | 0.217 | 0.023 | b.d. | 0.429 | b.d. | 0.112 | 0.012 | 0.049 | 0.010 | 0.002 | 0.007 | b.d. |

| Mannheim Number | Object Number | Cu wt. % | Sn wt. % | As wt. % | Pb wt. % | Ni wt. % | Co wt. % | Fe wt. % | Zn wt. % | Sb wt. % | Bi wt. % | Ag wt. % | Au wt. % | Te wt. % | Se wt. % | Mn wt. % |
|-----------------|---------------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|
| MA-132325 | Bo 06/1614 | 97 | 0.114 | 1.60 | 0.273 | 0.164 | b.d. | 0.441 | 0.066 | 0.098 | 0.027 | 0.034 | b.d. | 0.003 | 0.004 | b.d. |
| MA-132400 | Bo 06/1616 | 98 | 0.073 | 0.931 | 0.225 | 0.087 | 0.006 | 0.276 | 0.044 | 0.053 | b.d. | 0.010 | 0.032 | 0.004 | 0.008 | b.d. |
| MA-132373 | Bo 06/164 | 98 | 0.121 | 0.736 | 0.152 | 0.255 | 0.006 | 0.337 | 0.133 | 0.224 | 0.010 | 0.030 | 0.029 | 0.003 | 0.005 | b.d. |
| MA-132465 | Bo 06/1654 | 98 | 0.041 | 0.538 | 0.247 | 0.063 | 0.008 | 0.740 | 0.078 | 0.088 | 0.025 | 0.038 | 0.030 | 0.001 | 0.004 | b.d. |
| MA-132473 | Bo 06/1654_2 | 86 | 12.87 | 0.493 | 0.043 | 0.010 | 0.005 | 0.260 | b.d. | 0.031 | 0.002 | 0.006 | 0.003 | 0.006 | 0.017 | 0.001 |
| MA-132338 | Bo 06/1656 | 93 | 5.40 | 0.786 | 0.108 | 0.459 | 0.021 | 0.102 | 0.039 | 0.058 | 0.002 | 0.020 | 0.005 | 0.006 | 0.004 | b.d. |
| MA-132502 | Bo 06/168 | 99 | 0.028 | 0.287 | 0.044 | 0.052 | 0.014 | 0.358 | 0.258 | 0.070 | 0.013 | 0.009 | 0.051 | 0.012 | 0.010 | 0.004 |
| MA-132371 | Bo 06/1688 | 99 | 0.017 | 0.437 | 0.040 | 0.032 | 0.010 | 0.243 | 0.026 | 0.041 | 0.003 | 0.004 | 0.029 | 0.017 | 0.010 | b.d. |
| MA-132429 | Bo 06/1694 | 94 | 5.40 | 0.376 | 0.096 | 0.069 | 0.001 | 0.063 | 0.028 | 0.032 | b.d. | 0.018 | 0.047 | 0.008 | 0.004 | b.d. |
| MA-132445 | Bo 06/1715 | 98 | 0.030 | 0.626 | 0.035 | 0.085 | 0.038 | 0.500 | 0.413 | 0.226 | 0.026 | b.d. | 0.092 | 0.018 | 0.004 | 0.004 |
| MA-132463 | Bo 06/1716 | 99 | 0.160 | 0.537 | 0.033 | 0.029 | b.d. | 0.183 | 0.024 | 0.063 | 0.001 | 0.047 | 0.004 | 0.008 | 0.011 | b.d. |
| MA-132311 | Bo 06/172 | 83 | 0.069 | 0.197 | 0.042 | 13.42 | 1.67 | 1.37 | 0.219 | 0.086 | 0.020 | 0.017 | 0.051 | 0.012 | b.d. | b.d. |
| MA-132499 | Bo 06/1730 | 99 | 0.439 | 0.602 | 0.053 | 0.141 | 0.003 | 0.094 | 0.050 | 0.069 | 0.003 | 0.013 | 0.011 | 0.009 | 0.003 | b.d. |
| MA-132383 | Bo 06/1739 | 84 | 14.94 | 0.635 | 0.271 | 0.103 | 0.008 | 0.157 | 0.042 | 0.069 | 0.033 | 0.027 | 0.065 | 0.003 | 0.005 | b.d. |
| MA-132476 | Bo 06/1742 | 83 | 15.92 | 0.422 | 0.054 | 0.045 | b.d. | 0.091 | 0.002 | 0.042 | 0.004 | 0.013 | 0.008 | 0.001 | 0.010 | b.d. |
| MA-132439 | Bo 06/1751 | 93 | 0.078 | 5.92 | 0.158 | 0.096 | b.d. | 0.389 | 0.006 | 0.135 | 0.016 | 0.040 | b.d. | 0.004 | 0.003 | b.d. |
| MA-132466 | Bo 06/1753 | 85 | 13.25 | 0.699 | 0.162 | 0.052 | 0.003 | 0.366 | 0.111 | 0.094 | 0.018 | 0.021 | 0.009 | b.d. | 0.008 | b.d. |
| MA-132203 | Bo 06/1754 | 94 | 4.34 | 0.969 | 0.203 | 0.085 | 0.006 | 0.445 | 0.075 | 0.082 | 0.007 | 0.011 | 0.033 | 0.002 | 0.012 | 0.004 |
| MA-132398 | Bo 06/1755 | 86 | 12.30 | 1.41 | 0.117 | 0.048 | 0.004 | 0.274 | 0.099 | 0.121 | 0.009 | 0.020 | 0.025 | 0.011 | 0.009 | 0.002 |
| MA-132330 | Bo 06/1758 | 98 | 1.31 | 0.569 | 0.021 | 0.044 | 0.002 | 0.260 | 0.141 | 0.065 | 0.019 | 0.008 | 0.023 | 0.015 | 0.011 | b.d. |
| MA-132430 | Bo 06/1758_2 | 86 | 12.32 | 0.763 | 0.077 | 0.072 | 0.061 | 0.434 | 0.033 | 0.058 | 0.016 | 0.035 | 0.008 | 0.006 | 0.004 | b.d. |
| MA-132421 | Bo 06/1759 | 93 | 5.61 | 1.03 | 0.211 | 0.079 | b.d. | 0.230 | 0.026 | 0.090 | 0.003 | 0.033 | 0.030 | 0.005 | 0.003 | b.d. |
| MA-132352 | Bo 06/1762 | 98 | 0.060 | 1.53 | 0.107 | 0.053 | b.d. | 0.246 | 0.030 | 0.107 | 0.016 | 0.042 | 0.003 | b.d. | 0.006 | b.d. |
| MA-132335 | Bo 06/1763 | 98 | 1.03 | 0.465 | 0.053 | 0.074 | 0.005 | 0.435 | 0.029 | 0.041 | 0.005 | 0.004 | 0.005 | 0.013 | 0.011 | b.d. |
| MA-132394 | Bo 06/1764 | 98 | 0.061 | 1.47 | 0.178 | 0.138 | 0.017 | 0.277 | 0.044 | 0.186 | 0.005 | 0.065 | 0.005 | b.d. | 0.003 | b.d. |
| MA-132489 | Bo 06/1768 | 87 | 9.72 | 1.09 | 1.32 | 0.118 | 0.018 | 0.255 | 0.070 | 0.078 | 0.016 | 0.021 | 0.028 | 0.006 | 0.005 | b.d. |
| MA-132372 | Bo 06/1771 | 84 | 15.02 | 0.510 | 0.051 | 0.018 | 0.004 | 0.287 | 0.032 | 0.062 | 0.001 | 0.004 | 0.002 | 0.009 | 0.021 | b.d. |
| MA-132471 | Bo 06/1802 | 95 | 0.105 | 3.27 | 0.311 | 0.259 | 0.014 | 1.14 | 0.133 | 0.121 | 0.008 | 0.029 | 0.027 | 0.006 | 0.005 | b.d. |

| Mannheim Number | Object Number | Cu wt. % | Sn wt. % | As wt. % | Pb wt. % | Ni wt. % | Co wt. % | Fe wt. % | Zn wt. % | Sb wt. % | Bi wt. % | Ag wt. % | Au wt. % | Te wt. % | Se wt. % | Mn wt. % |
|-----------------|---------------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|
| MA-132310 | Bo 06/1803 | 87 | 0.140 | 1.31 | 0.131 | 4.79 | 0.096 | 5.75 | b.d. | 0.165 | 0.052 | 0.078 | 0.012 | 0.006 | 0.003 | 0.014 |
| MA-132348 | Bo 06/1806 | 99 | 0.008 | 0.653 | 0.178 | 0.036 | 0.001 | 0.420 | 0.023 | 0.134 | 0.006 | 0.004 | 0.005 | 0.006 | 0.012 | b.d. |
| MA-132401 | Bo 06/1817 | 97 | 0.152 | 0.799 | 0.048 | 0.980 | 0.045 | 0.692 | 0.160 | 0.076 | 0.012 | 0.013 | 0.059 | 0.003 | 0.006 | b.d. |
| MA-132472 | Bo 06/1825 | 93 | 3.05 | 1.54 | 0.242 | 0.438 | 0.020 | 1.60 | 0.085 | 0.118 | 0.012 | 0.006 | 0.021 | 0.014 | 0.012 | b.d. |
| MA-132357 | Bo 06/1834 | 94 | 3.92 | 0.803 | 0.138 | 0.073 | 0.002 | 0.530 | 0.083 | 0.060 | 0.001 | 0.004 | 0.049 | 0.003 | 0.015 | 0.001 |
| MA-132475 | Bo 06/1835 | 98 | 0.026 | 1.42 | 0.031 | 0.031 | 0.001 | 0.446 | 0.084 | 0.145 | 0.006 | 0.019 | 0.095 | b.d. | 0.005 | b.d. |
| MA-132443 | Bo 06/1837 | 99 | 0.007 | 0.288 | 0.014 | 0.028 | b.d. | 0.178 | 0.017 | 0.027 | 0.002 | 0.001 | 0.009 | 0.002 | b.d. | b.d. |
| MA-132382 | Bo 06/1844 | 97 | 0.213 | 1.26 | 0.362 | 0.096 | 0.002 | 0.321 | 0.105 | 0.137 | 0.002 | 0.028 | 0.030 | 0.004 | 0.003 | b.d. |
| MA-132309 | Bo 06/189 | 86 | 0.042 | 0.324 | 0.028 | 11.81 | 1.29 | 0.272 | 0.065 | 0.073 | 0.001 | 0.007 | 0.041 | b.d. | 0.002 | b.d. |
| MA-132377 | Bo 06/1933 | 97 | 0.240 | 1.61 | 0.056 | 0.104 | b.d. | 0.432 | 0.175 | 0.167 | 0.009 | 0.061 | 0.067 | 0.013 | 0.006 | b.d. |
| MA-132434 | Bo 06/1954 | 98 | 0.055 | 1.39 | 0.080 | 0.124 | 0.005 | 0.345 | 0.064 | 0.142 | 0.001 | 0.030 | 0.006 | 0.001 | 0.001 | b.d. |
| MA-132477 | Bo 06/2009 | 85 | 12.63 | 0.111 | 1.18 | 0.018 | 0.014 | 0.606 | 0.084 | 0.074 | 0.010 | 0.020 | 0.005 | 0.012 | b.d. | 0.003 |
| MA-132358 | Bo 06/2016 | 98 | 0.032 | 0.585 | 0.036 | 0.061 | 0.012 | 0.656 | 0.045 | 0.040 | 0.003 | 0.007 | 0.337 | b.d. | 0.010 | b.d. |
| MA-132493 | Bo 06/2019 | 94 | 0.018 | 4.22 | 0.154 | 0.071 | 0.015 | 0.842 | 0.079 | 0.130 | 0.015 | 0.026 | 0.029 | 0.013 | 0.004 | b.d. |
| MA-132501 | Bo 06/2028 | 97 | 0.067 | 1.86 | 0.205 | 0.114 | 0.003 | 0.362 | 0.098 | 0.128 | 0.015 | 0.024 | 0.017 | 0.010 | b.d. | 0.010 |
| MA-132356 | Bo 06/2036 | 87 | 11.60 | 0.885 | 0.045 | 0.116 | 0.007 | 0.201 | 0.098 | 0.093 | 0.007 | 0.021 | 0.037 | 0.001 | 0.006 | b.d. |
| MA-132305 | Bo 06/2037 | 86 | 0.191 | 0.133 | 0.020 | 11.08 | 0.350 | 1.76 | b.d. | 0.038 | 0.001 | 0.007 | 0.015 | 0.001 | b.d. | 0.003 |
| MA-132318 | Bo 06/2039 | 97 | 0.036 | 1.66 | 0.696 | 0.063 | b.d. | 0.433 | 0.037 | 0.066 | 0.040 | 0.024 | b.d. | 0.003 | 0.008 | 0.007 |
| MA-132321 | Bo 06/2049 | 91 | 7.75 | 0.727 | 0.141 | 0.066 | 0.008 | 0.106 | 0.078 | 0.095 | 0.004 | 0.013 | 0.010 | 0.013 | 0.005 | b.d. |
| MA-132454 | Bo 06/2056 | 98 | 0.422 | 0.884 | 0.093 | 0.102 | 0.006 | 0.235 | 0.126 | 0.127 | 0.005 | 0.032 | 0.022 | 0.005 | 0.001 | b.d. |
| MA-132361 | Bo 06/207 | 93 | 4.06 | 1.73 | 0.205 | 0.146 | b.d. | 0.212 | 0.168 | 0.169 | 0.022 | 0.034 | 0.043 | 0.001 | 0.010 | 0.001 |
| MA-132414 | Bo 06/2075 | 76 | 22.02 | 1.54 | 0.173 | 0.032 | 0.009 | 0.230 | 0.063 | 0.089 | 0.016 | 0.058 | 0.004 | 0.006 | 0.005 | b.d. |
| MA-132487 | Bo 06/2089 | 98 | 0.047 | 1.20 | 0.125 | 0.057 | b.d. | 0.279 | 0.038 | 0.062 | 0.017 | 0.029 | 0.007 | b.d. | 0.006 | b.d. |
| MA-132418 | Bo 06/2090 | 94 | 0.097 | 3.44 | 1.82 | 0.044 | 0.009 | 0.416 | 0.045 | 0.099 | 0.011 | 0.056 | 0.012 | 0.013 | 0.001 | b.d. |
| MA-132525 | Bo 06/2094 | 97 | 0.061 | 1.78 | 0.206 | 0.144 | 0.018 | 0.196 | b.d. | 0.278 | 0.002 | 0.040 | b.d. | 0.011 | 0.023 | 0.028 |
| MA-132410 | Bo 06/210 | 83 | 15.52 | 0.919 | 0.139 | 0.059 | 0.002 | 0.082 | 0.075 | 0.091 | 0.011 | 0.056 | 0.012 | 0.007 | 0.005 | b.d. |
| MA-132482 | Bo 06/2103 | 97 | 0.025 | 1.24 | 0.046 | 0.065 | 0.120 | 0.917 | 0.026 | 0.080 | 0.020 | 0.050 | 0.009 | 0.002 | b.d. | b.d. |
| MA-132354 | Bo 06/2110 | 97 | 0.068 | 0.643 | 0.149 | 1.01 | 0.046 | 0.837 | 0.055 | 0.028 | 0.002 | 0.004 | 0.014 | 0.001 | 0.005 | b.d. |

| Mannheim Number | Object Number | Cu wt. % | Sn wt. % | As wt. % | Pb wt. % | Ni wt. % | Co wt. % | Fe wt. % | Zn wt. % | Sb wt. % | Bi wt. % | Ag wt. % | Au wt. % | Te wt. % | Se wt. % | Mn wt. % |
|-----------------|---------------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|
| MA-132322 | Bo 06/212 | 90 | 8.40 | 0.669 | 0.113 | 0.027 | 0.002 | 0.216 | 0.036 | 0.043 | 0.004 | 0.004 | 0.007 | 0.002 | 0.006 | b.d. |
| MA-132315 | Bo 06/2127 | 89 | 8.08 | 1.68 | 0.125 | 0.108 | 0.002 | 0.399 | b.d. | 0.105 | 0.007 | 0.014 | 0.004 | 0.004 | 0.009 | b.d. |
| MA-132480 | Bo 06/2130 | 98 | 0.066 | 1.76 | 0.068 | 0.047 | b.d. | 0.100 | 0.029 | 0.087 | 0.046 | 0.050 | 0.015 | 0.012 | 0.005 | b.d. |
| MA-132488 | Bo 06/2142 | 98 | 0.239 | 1.37 | 0.194 | 0.081 | 0.003 | 0.131 | 0.108 | 0.121 | 0.007 | 0.023 | 0.041 | 0.014 | 0.005 | b.d. |
| MA-132419 | Bo 06/215 | 93 | 4.20 | 1.32 | 0.204 | 0.175 | 0.008 | 0.451 | 0.276 | 0.227 | 0.056 | 0.027 | 0.031 | 0.001 | 0.013 | 0.009 |
| MA-132479 | Bo 06/2152 | 89 | 0.147 | 0.975 | 0.319 | 8.22 | 0.241 | 0.583 | b.d. | 0.113 | 0.030 | 0.062 | 0.010 | 0.006 | b.d. | b.d. |
| MA-132332 | Bo 06/2153 | 98 | 0.103 | 1.61 | 0.024 | 0.038 | b.d. | 0.280 | 0.108 | 0.082 | 0.031 | 0.045 | 0.014 | 0.012 | 0.002 | b.d. |
| MA-132492 | Bo 06/2182 | 99 | 0.017 | 0.467 | 0.036 | 0.062 | 0.008 | 0.419 | 0.102 | 0.074 | 0.013 | 0.008 | 0.049 | 0.004 | 0.011 | 0.003 |
| MA-132417 | Bo 06/2192 | 90 | 6.32 | 1.75 | 0.173 | 0.104 | 0.012 | 1.26 | 0.216 | 0.171 | 0.015 | 0.025 | 0.066 | 0.021 | 0.006 | b.d. |
| MA-132415 | Bo 06/2229 | 99 | 0.034 | 0.421 | 0.029 | 0.049 | 0.003 | 0.260 | 0.065 | 0.038 | 0.012 | 0.006 | 0.019 | 0.013 | 0.002 | b.d. |
| MA-132497 | Bo 06/223 | 98 | 0.038 | 0.836 | 0.175 | 0.029 | 0.001 | 0.289 | 0.055 | 0.073 | 0.028 | 0.017 | 0.008 | 0.002 | 0.007 | 0.001 |
| MA-132425 | Bo 06/2237 | 97 | 0.185 | 1.61 | 0.219 | 0.124 | 0.002 | 0.439 | 0.065 | 0.096 | 0.033 | 0.045 | 0.025 | 0.006 | 0.006 | 0.001 |
| MA-132375 | Bo 06/2244 | 98 | 0.049 | 1.04 | 0.125 | 0.110 | b.d. | 0.329 | 0.162 | 0.135 | 0.014 | 0.021 | 0.057 | 0.002 | 0.005 | b.d. |
| MA-132403 | Bo 06/2253 | 94 | 1.09 | 2.77 | 0.630 | 0.400 | 0.023 | 0.590 | 0.032 | 0.080 | 0.047 | 0.069 | b.d. | 0.005 | 0.002 | 0.002 |
| MA-132494 | Bo 06/2263 | 98 | 0.018 | 1.46 | 0.143 | 0.034 | 0.002 | 0.116 | 0.175 | 0.151 | 0.015 | 0.038 | 0.022 | 0.014 | 0.012 | 0.005 |
| MA-132345 | Bo 06/2294 | 85 | 13.83 | 0.849 | 0.085 | 0.054 | 0.145 | 0.235 | 0.063 | 0.100 | 0.007 | 0.011 | 0.003 | 0.003 | 0.005 | b.d. |
| MA-132342 | Bo 06/2298 | 86 | 3.14 | 0.510 | 0.066 | 8.66 | 0.675 | 0.209 | 0.448 | 0.085 | b.d. | 0.012 | 0.103 | b.d. | 0.006 | b.d. |
| MA-132462 | Bo 06/2359 | 98 | 0.202 | 0.638 | 0.027 | 0.088 | 0.003 | 0.541 | 0.082 | 0.069 | 0.005 | 0.006 | 0.019 | 0.008 | 0.001 | b.d. |
| MA-132304 | Bo 06/2361 | 88 | 0.036 | 0.063 | 0.037 | 11.51 | 0.091 | 0.050 | 0.209 | 0.106 | 0.004 | 0.001 | 0.020 | 0.001 | 0.004 | b.d. |
| MA-132351 | Bo 06/2376 | 97 | 0.196 | 1.62 | 0.204 | 0.118 | 0.003 | 0.419 | 0.035 | 0.063 | 0.015 | 0.049 | 0.003 | 0.005 | 0.007 | b.d. |
| MA-132317 | Bo 06/2378 | 95 | 0.331 | 3.14 | 0.189 | 0.089 | 0.016 | 1.30 | 0.189 | 0.107 | 0.015 | 0.027 | 0.038 | 0.011 | 0.004 | 0.004 |
| MA-132344 | Bo 06/239 | 88 | 10.81 | 0.325 | 0.030 | 0.280 | 0.030 | 0.163 | 0.231 | 0.120 | 0.028 | 0.019 | 0.029 | b.d. | 0.007 | 0.007 |
| MA-132363 | Bo 06/2398 | 98 | 0.023 | 1.49 | 0.160 | 0.103 | 0.001 | 0.400 | 0.048 | 0.038 | 0.029 | 0.046 | 0.012 | 0.010 | 0.011 | b.d. |
| MA-132411 | Bo 06/2400 | 96 | 2.10 | 0.974 | 0.152 | 0.150 | 0.002 | 0.233 | 0.034 | 0.151 | 0.012 | 0.042 | 0.017 | 0.004 | 0.004 | b.d. |
| MA-132364 | Bo 06/2403 | 95 | 0.086 | 3.57 | 1.06 | 0.034 | b.d. | 0.291 | 0.054 | 0.150 | 0.129 | 0.072 | b.d. | 0.036 | 0.009 | b.d. |
| MA-132355 | Bo 06/2409 | 98 | 0.046 | 0.899 | 0.029 | 0.615 | 0.018 | 0.492 | 0.060 | 0.054 | 0.020 | 0.019 | 0.020 | 0.003 | 0.008 | b.d. |
| MA-132453 | Bo 06/241 | 97 | 2.28 | 0.219 | 0.074 | 0.030 | 0.002 | 0.296 | 0.237 | 0.129 | 0.018 | 0.001 | b.d. | b.d. | 0.005 | 0.002 |
| MA-132346 | Bo 06/2428 | 87 | 0.030 | 0.267 | 0.008 | 10.76 | 1.35 | 0.457 | b.d. | 0.016 | 0.001 | 0.006 | b.d. | 0.004 | 0.002 | b.d. |

| Mannheim Number | Object Number | Cu wt. % | Sn wt. % | As wt. % | Pb wt. % | Ni wt. % | Co wt. % | Fe wt. % | Zn wt. % | Sb wt. % | Bi wt. % | Ag wt. % | Au wt. % | Te wt. % | Se wt. % | Mn wt. % |
|-----------------|---------------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|
| MA-132402 | Bo 06/250 | 98 | 0.799 | 0.653 | 0.609 | 0.070 | 0.001 | 0.165 | 0.038 | 0.047 | 0.006 | 0.026 | 0.009 | 0.003 | 0.001 | b.d. |
| MA-132340 | Bo 06/254 | 97 | 1.73 | 0.552 | 0.169 | 0.039 | 0.002 | 0.264 | 0.035 | 0.092 | 0.005 | 0.008 | 0.028 | 0.001 | 0.015 | b.d. |
| MA-132468 | Bo 06/257 | 87 | 10.80 | 0.697 | 0.055 | 0.225 | b.d. | 0.505 | 0.326 | 0.169 | 0.015 | 0.022 | 0.036 | 0.006 | 0.003 | b.d. |
| MA-132349 | Bo 06/258 | 99 | 0.009 | 0.274 | 0.005 | 0.087 | 0.004 | 0.447 | 0.004 | 0.018 | 0.001 | 0.016 | 0.001 | 0.001 | 0.002 | b.d. |
| MA-132409 | Bo 06/259 | 89 | 9.93 | 0.295 | 0.010 | 0.012 | 0.001 | 0.071 | 0.123 | 0.095 | 0.005 | 0.005 | 0.025 | 0.014 | 0.004 | b.d. |
| MA-132486 | Bo 06/265 | 92 | 5.81 | 1.34 | 0.121 | 0.123 | 0.001 | 0.358 | 0.082 | 0.093 | 0.004 | 0.021 | 0.022 | 0.003 | 0.002 | b.d. |
| MA-132483 | Bo 06/266 | 97 | 0.199 | 1.47 | 0.810 | 0.054 | 0.013 | 0.318 | 0.066 | 0.105 | 0.043 | 0.110 | 0.006 | 0.007 | 0.002 | b.d. |
| MA-132485 | Bo 06/267 | 87 | 9.42 | 2.13 | 0.118 | 0.099 | 0.003 | 1.10 | 0.046 | 0.076 | 0.015 | 0.046 | 0.011 | 0.007 | 0.003 | b.d. |
| MA-132484 | Bo 06/268 | 99 | 0.040 | 0.455 | 0.024 | 0.292 | 0.006 | 0.255 | 0.140 | 0.116 | 0.003 | 0.009 | 0.042 | 0.002 | 0.005 | b.d. |
| MA-132469 | Bo 06/268_2 | 93 | 0.049 | 4.66 | 0.106 | 0.051 | 0.052 | 1.41 | 0.104 | 0.146 | 0.003 | 0.065 | 0.028 | b.d. | 0.002 | 0.002 |
| MA-132381 | Bo 06/272 | 90 | 8.21 | 0.661 | 0.188 | 0.040 | 0.005 | 0.747 | 0.083 | 0.084 | 0.008 | 0.007 | 0.018 | 0.009 | 0.005 | 0.006 |
| MA-132491 | Bo 06/274 | 97 | 0.184 | 1.48 | 0.244 | 0.275 | b.d. | 0.462 | 0.101 | 0.140 | 0.024 | 0.050 | 0.025 | 0.002 | 0.003 | 0.003 |
| MA-132423 | Bo 06/284 | 93 | 5.66 | 0.814 | 0.170 | 0.107 | 0.012 | 0.066 | 0.248 | 0.199 | 0.006 | 0.023 | 0.035 | 0.009 | 0.008 | 0.002 |
| MA-132337 | Bo 06/293 | 98 | 0.101 | 1.28 | 0.067 | 0.104 | 0.006 | 0.404 | 0.147 | 0.127 | 0.007 | 0.046 | 0.032 | b.d. | 0.006 | b.d. |
| MA-132391 | Bo 06/305 | 97 | 0.023 | 1.39 | 0.048 | 0.458 | 0.009 | 0.430 | 0.124 | 0.128 | 0.015 | 0.055 | 0.018 | 0.001 | 0.003 | 0.001 |
| MA-132448 | Bo 06/313 | 89 | 9.57 | 0.296 | 0.026 | 0.153 | 0.016 | 0.121 | 0.329 | 0.169 | 0.001 | 0.129 | 0.069 | 0.002 | 0.003 | 0.001 |
| MA-132376 | Bo 06/314 | 92 | 5.53 | 0.832 | 0.323 | 0.172 | 0.053 | 0.583 | 0.103 | 0.113 | 0.011 | 0.023 | 0.015 | 0.010 | 0.011 | b.d. |
| MA-132320 | Bo 06/317 | 80 | 14.03 | 3.11 | 0.372 | 0.206 | 0.026 | 1.18 | 0.396 | 0.267 | 0.007 | 0.052 | 0.056 | b.d. | 0.021 | 0.014 |
| MA-132324 | Bo 06/319 | 90 | 7.02 | 1.03 | 0.960 | 0.260 | 0.013 | 0.316 | 0.326 | 0.202 | 0.026 | 0.017 | 0.044 | 0.011 | 0.012 | 0.002 |
| MA-132395 | Bo 06/326 | 97 | 2.09 | 0.496 | 0.125 | 0.013 | b.d. | 0.141 | 0.023 | 0.097 | 0.007 | 0.011 | 0.005 | 0.010 | 0.014 | b.d. |
| MA-132459 | Bo 06/368 | 83 | 16.31 | 0.637 | 0.050 | 0.016 | b.d. | 0.298 | 0.069 | 0.070 | b.d. | 0.004 | 0.002 | 0.004 | 0.003 | b.d. |
| MA-132496 | Bo 06/410 | 97 | 0.104 | 1.65 | 0.778 | 0.039 | 0.006 | 0.333 | 0.180 | 0.243 | 0.037 | 0.053 | 0.027 | b.d. | 0.005 | b.d. |
| MA-132495 | Bo 06/413 | 95 | 1.08 | 1.92 | 0.139 | 0.145 | 0.005 | 0.896 | 0.207 | 0.176 | b.d. | 0.048 | 0.032 | 0.001 | 0.012 | 0.010 |
| MA-132326 | Bo 06/415 | 98 | 0.092 | 1.05 | 0.081 | 0.099 | 0.009 | 0.545 | 0.035 | 0.054 | 0.003 | 0.016 | b.d. | b.d. | 0.005 | 0.001 |
| MA-132404 | Bo 06/429 | 98 | 0.084 | 1.40 | 0.186 | 0.121 | 0.001 | 0.254 | 0.084 | 0.184 | 0.015 | 0.039 | 0.092 | b.d. | 0.006 | b.d. |
| MA-132440 | Bo 06/440 | 97 | 0.022 | 2.39 | 0.087 | 0.097 | b.d. | 0.193 | 0.105 | 0.182 | 0.018 | 0.049 | 0.019 | b.d. | 0.001 | 0.004 |
| MA-132336 | Bo 06/441 | 97 | 0.163 | 1.48 | 0.094 | 0.173 | 0.011 | 0.462 | 0.182 | 0.141 | 0.014 | 0.045 | 0.033 | 0.001 | 0.005 | b.d. |
| MA-132341 | Bo 06/454 | 95 | 0.272 | 3.68 | 0.354 | 0.121 | 0.014 | 0.519 | 0.028 | 0.121 | 0.055 | 0.058 | 0.024 | 0.008 | 0.008 | 0.001 |

| Mannheim Number | Object Number | Cu wt. % | Sn wt. % | As wt. % | Pb wt. % | Ni wt. % | Co wt. % | Fe wt. % | Zn wt. % | Sb wt. % | Bi wt. % | Ag wt. % | Au wt. % | Te wt. % | Se wt. % | Mn wt. % |
|-----------------|---------------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|
| MA-132431 | Bo 06/476 | 93 | 4.30 | 1.11 | 0.096 | 0.316 | 0.004 | 0.323 | 0.179 | 0.161 | 0.002 | 0.022 | 0.037 | 0.004 | 0.004 | b.d. |
| MA-132438 | Bo 06/489 | 97 | 0.141 | 1.36 | 0.172 | 0.156 | 0.009 | 0.406 | 0.177 | 0.209 | 0.017 | 0.063 | 0.052 | 0.021 | 0.005 | 0.004 |
| MA-132307 | Bo 06/492 | 80 | 0.033 | 0.275 | 0.027 | 17.46 | 1.87 | 0.459 | 0.113 | 0.038 | 0.002 | 0.010 | 0.025 | 0.001 | 0.001 | 0.002 |
| MA-132333 | Bo 06/499 | 98 | 0.208 | 1.29 | 0.138 | 0.083 | b.d. | 0.106 | 0.210 | 0.141 | 0.023 | 0.054 | 0.048 | 0.015 | 0.010 | b.d. |
| MA-132389 | Bo 06/500 | 93 | 0.038 | 5.59 | 0.134 | 0.118 | 0.010 | 0.637 | 0.174 | 0.310 | 0.005 | 0.061 | 0.021 | 0.005 | 0.005 | b.d. |
| MA-132426 | Bo 06/506 | 91 | 6.78 | 1.01 | 0.128 | 0.280 | 0.014 | 0.228 | 0.192 | 0.143 | 0.009 | 0.012 | 0.023 | 0.006 | 0.005 | 0.001 |
| MA-132368 | Bo 06/513 | 90 | 7.97 | 0.922 | 0.265 | 0.115 | 0.013 | 0.620 | 0.062 | 0.091 | 0.007 | 0.026 | 0.015 | 0.002 | 0.011 | b.d. |
| MA-132446 | Bo 06/514 | 92 | 4.97 | 1.64 | 0.499 | 0.202 | 0.001 | 0.292 | 0.075 | 0.129 | 0.014 | 0.049 | 0.022 | 0.005 | 0.007 | b.d. |
| MA-132347 | Bo 06/521 | 96 | 0.333 | 3.39 | 0.062 | 0.052 | 0.005 | 0.076 | 0.069 | 0.086 | 0.169 | 0.076 | 0.001 | 0.012 | 0.013 | b.d. |
| MA-132413 | Bo 06/532 | 89 | 9.13 | 1.23 | 0.199 | 0.217 | 0.023 | 0.186 | 0.160 | 0.140 | 0.013 | 0.035 | 0.011 | 0.013 | 0.008 | b.d. |
| MA-132422 | Bo 06/533 | 85 | 12.32 | 1.01 | 0.302 | 0.048 | 0.003 | 0.688 | 0.353 | 0.204 | 0.009 | 0.019 | 0.068 | 0.003 | 0.004 | b.d. |
| MA-132362 | Bo 06/548 | 91 | 7.98 | 0.526 | 0.062 | 0.044 | 0.001 | 0.125 | 0.113 | 0.040 | 0.010 | 0.006 | 0.020 | 0.005 | 0.004 | b.d. |
| MA-132313 | Bo 06/549 | 87 | 0.018 | 0.129 | 0.027 | 10.60 | 1.99 | 0.369 | 0.114 | 0.079 | b.d. | 0.001 | 0.016 | 0.006 | 0.005 | 0.003 |
| MA-132374 | Bo 06/555 | 97 | 0.029 | 1.76 | 0.289 | 0.025 | 0.009 | 0.588 | 0.253 | 0.169 | 0.008 | 0.028 | 0.042 | 0.032 | b.d. | b.d. |
| MA-132390 | Bo 06/563 | 97 | 0.047 | 1.75 | 0.421 | 0.048 | 0.002 | 0.246 | 0.034 | 0.086 | 0.019 | 0.042 | 0.019 | 0.006 | 0.004 | b.d. |
| MA-132441 | Bo 06/567_1 | 98 | 0.037 | 0.512 | 0.070 | 0.046 | 0.018 | 0.278 | 0.296 | 0.182 | 0.028 | 0.004 | 0.067 | 0.011 | 0.008 | b.d. |
| MA-132481 | Bo 06/578 | 96 | 1.71 | 0.776 | 0.105 | 0.038 | 0.006 | 0.633 | 0.519 | 0.341 | 0.002 | 0.008 | 0.072 | 0.009 | 0.010 | 0.009 |
| MA-132420 | Bo 06/585 | 97 | 0.050 | 1.40 | 0.134 | 0.068 | b.d. | 0.318 | 0.404 | 0.254 | b.d. | 0.040 | 0.093 | 0.022 | 0.014 | 0.002 |
| MA-132412 | Bo 06/608 | 94 | 4.96 | 0.495 | 0.141 | 0.157 | 0.005 | 0.073 | 0.069 | 0.065 | 0.006 | 0.014 | 0.079 | 0.005 | 0.007 | b.d. |
| MA-132467 | Bo 06/617 | 90 | 8.10 | 0.812 | 0.176 | 0.017 | 0.016 | 0.597 | 0.305 | 0.149 | 0.026 | 0.006 | 0.046 | 0.004 | 0.027 | b.d. |
| MA-132460 | Bo 06/635 | 98 | 0.881 | 0.881 | 0.079 | 0.127 | 0.005 | 0.107 | 0.105 | 0.118 | 0.018 | 0.047 | 0.034 | 0.007 | b.d. | 0.002 |
| MA-132451 | Bo 06/647 | 92 | 5.14 | 1.02 | 0.511 | 0.069 | 0.004 | 0.749 | 0.153 | 0.223 | 0.007 | 0.009 | b.d. | 0.005 | 0.006 | b.d. |
| MA-132329 | Bo 06/649 | 89 | 9.22 | 0.824 | 0.144 | 0.080 | 0.010 | 0.229 | 0.009 | 0.069 | 0.008 | 0.013 | 0.014 | 0.004 | 0.007 | b.d. |
| MA-132432 | Bo 06/661 | 97 | 0.052 | 1.93 | 0.153 | 0.069 | 0.002 | 0.187 | 0.042 | 0.172 | 0.042 | 0.059 | 0.008 | 0.007 | 0.006 | 0.001 |
| MA-132416 | Bo 06/668 | 96 | 0.602 | 1.03 | 0.369 | 0.040 | b.d. | 0.914 | 0.145 | 0.355 | 0.027 | 0.032 | 0.020 | 0.009 | 0.003 | 0.006 |
| MA-132365 | Bo 06/673 | 97 | 0.058 | 1.38 | 0.052 | 0.087 | 0.012 | 1.13 | 0.170 | 0.126 | 0.018 | 0.038 | 0.068 | 0.004 | 0.005 | 0.010 |
| MA-132455 | Bo 06/677 | 74 | 23.68 | 1.31 | 0.376 | 0.050 | 0.001 | 0.142 | 0.021 | 0.095 | 0.007 | 0.010 | 0.008 | 0.008 | 0.012 | b.d. |
| MA-132353 | Bo 06/680 | 95 | 3.53 | 0.719 | 0.081 | 0.134 | 0.018 | 0.237 | 0.024 | 0.118 | 0.007 | 0.044 | 0.003 | 0.002 | 0.007 | 0.001 |

| Mannheim Number | Object Number | Cu wt. % | Sn wt. % | As wt. % | Pb wt. % | Ni wt. % | Co wt. % | Fe wt. % | Zn wt. % | Sb wt. % | Bi wt. % | Ag wt. % | Au wt. % | Te wt. % | Se wt. % | Mn wt. % |
|-----------------|---------------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|
| MA-132314 | Bo 06/69 | 72 | 21.58 | 0.387 | 0.940 | 3.77 | 0.298 | 0.228 | b.d. | 0.082 | 0.011 | 0.344 | b.d. | 0.005 | 0.002 | b.d. |
| MA-132427 | Bo 06/711 | 98 | 0.120 | 1.15 | 0.241 | 0.037 | 0.004 | 0.172 | 0.133 | 0.144 | 0.034 | 0.058 | 0.026 | 0.007 | 0.002 | b.d. |
| MA-132490 | Bo 06/735 | 98 | 0.021 | 1.62 | 0.123 | 0.072 | 0.001 | 0.114 | 0.020 | 0.067 | 0.009 | 0.037 | b.d. | 0.003 | 0.003 | b.d. |
| MA-132458 | Bo 06/740 | 96 | 2.59 | 0.902 | 0.129 | 0.135 | 0.002 | 0.239 | 0.082 | 0.203 | 0.009 | 0.021 | 0.010 | 0.001 | 0.001 | b.d. |
| MA-132201 | Bo 06/753 | 87 | 12.00 | 0.176 | 0.063 | 0.024 | 0.004 | 1.07 | 0.002 | 0.034 | 0.003 | 0.016 | 0.001 | 0.008 | 0.002 | 0.002 |
| MA-132447 | Bo 06/770 | 98 | 0.068 | 0.757 | 0.112 | 0.511 | 0.001 | 0.129 | 0.013 | 0.037 | 0.013 | 0.028 | 0.023 | 0.007 | 0.018 | b.d. |
| MA-132396 | Bo 06/773 | 98 | 0.046 | 1.40 | 0.103 | 0.023 | 0.001 | 0.469 | 0.056 | 0.072 | 0.041 | 0.066 | 0.020 | 0.013 | 0.007 | b.d. |
| MA-132360 | Bo 06/78 | 98 | 0.099 | 1.20 | 0.168 | 0.029 | 0.003 | 0.260 | 0.127 | 0.120 | 0.022 | 0.071 | 0.047 | 0.011 | 0.016 | b.d. |
| MA-132378 | Bo 06/819 | 87 | 10.45 | 1.46 | 0.340 | 0.134 | 0.003 | 0.191 | 0.253 | 0.190 | 0.020 | 0.040 | 0.088 | 0.016 | 0.004 | b.d. |
| MA-132399 | Bo 06/82 | 99 | 0.111 | 0.465 | 0.190 | 0.033 | 0.005 | 0.583 | 0.028 | 0.041 | 0.001 | 0.005 | 0.011 | b.d. | 0.006 | b.d. |
| MA-132424 | Bo 06/83 | 96 | 1.51 | 0.986 | 0.159 | 0.205 | 0.015 | 0.385 | 0.220 | 0.213 | 0.015 | 0.053 | 0.058 | 0.004 | 0.010 | 0.002 |
| MA-132436 | Bo 06/861 | 97 | 0.029 | 1.90 | 0.060 | 0.053 | b.d. | 0.607 | 0.030 | 0.089 | 0.001 | 0.013 | 0.012 | 0.001 | 0.001 | b.d. |
| MA-132435 | Bo 06/93 | 91 | 6.55 | 1.53 | 0.278 | 0.103 | 0.009 | 0.662 | 0.042 | 0.105 | 0.018 | 0.027 | 0.006 | 0.005 | 0.008 | b.d. |
| MA-132457 | Bo 06/97 | 91 | 6.90 | 0.832 | 0.142 | 0.078 | 0.020 | 0.200 | 0.202 | 0.145 | 0.020 | 0.033 | 0.053 | 0.020 | 0.005 | 0.005 |
| MA-136335 | Bo 07/1871 | 77 | 0.018 | 0.079 | 0.023 | 20.75 | 1.16 | 0.688 | 0.339 | 0.041 | 0.003 | 0.004 | 0.079 | 0.004 | 0.007 | b.d. |
| MA-136332 | Bo 07/2101 | 86 | 0.002 | 0.874 | 0.014 | 10.51 | 0.322 | 1.83 | b.d. | 0.055 | 0.000 | 0.021 | 0.006 | 0.008 | 0.001 | b.d. |
| MA-136331 | Bo 07/2149 | 80 | 0.032 | 1.46 | 0.029 | 14.51 | 0.685 | 3.20 | 0.126 | 0.073 | 0.007 | 0.021 | 0.022 | 0.004 | 0.002 | 0.001 |
| MA-136328 | Bo 07/2151 | 80 | 0.019 | 0.449 | 0.021 | 16.04 | 0.589 | 2.91 | 0.132 | 0.051 | 0.001 | 0.009 | 0.013 | 0.000 | 0.001 | b.d. |
| MA-136333 | Bo 07/2204 | 83 | 0.020 | 0.488 | 0.020 | 13.74 | 0.530 | 2.05 | 0.024 | 0.036 | 0.008 | 0.013 | 0.015 | 0.004 | b.d. | b.d. |
| MA-132197 | Bo 07/29 | 94 | 4.17 | 0.729 | 0.117 | 0.111 | 0.012 | 0.606 | 0.052 | 0.029 | 0.001 | 0.005 | 0.019 | b.d. | 0.009 | b.d. |
| MA-136334 | Bo 07/3594 | 86 | 0.080 | 0.647 | 0.021 | 11.44 | 0.210 | 1.19 | b.d. | 0.094 | 0.003 | 0.037 | 0.007 | b.d. | 0.001 | b.d. |
| MA-136325 | Bo 07/3735 | 82 | 0.016 | 0.230 | 0.017 | 15.81 | 0.328 | 1.32 | 0.096 | 0.030 | 0.000 | 0.004 | 0.014 | b.d. | 0.001 | b.d. |
| MA-132199 | Bo 08/101 | 92 | 5.78 | 1.51 | 0.099 | 0.155 | 0.014 | 0.426 | 0.039 | 0.034 | 0.011 | 0.019 | 0.008 | b.d. | 0.002 | b.d. |
| MA-132205 | Bo 08/217 | 95 | 0.066 | 1.98 | 1.63 | 0.170 | 0.005 | 0.828 | 0.051 | 0.089 | 0.089 | 0.065 | 0.011 | 0.007 | 0.011 | b.d. |
| MA-132198 | Bo 08/227 | 91 | 5.06 | 2.05 | 0.402 | 0.106 | 0.002 | 1.11 | 0.062 | 0.061 | 0.012 | 0.035 | 0.009 | 0.004 | 0.004 | 0.002 |
| MA-132206 | Bo 08/229 | 97 | 0.384 | 1.26 | 0.049 | 0.042 | 0.012 | 0.670 | 0.027 | 0.045 | 0.005 | 0.014 | 0.006 | 0.004 | 0.007 | b.d. |
| MA-136324 | Bo 08/264 | 88 | 0.033 | 0.312 | 0.018 | 9.88 | 0.922 | 0.568 | 0.012 | 0.077 | 0.001 | 0.006 | 0.026 | 0.002 | 0.006 | b.d. |
| MA-132204 | Bo 08/9 | 82 | 0.193 | 1.28 | 0.072 | 13.68 | 0.164 | 2.02 | 0.440 | b.d. | b.d. | 0.060 | 0.004 | 0.164 | b.d. | 0.062 |

| Mannheim Number | Object Number | Cu wt. % | Sn wt. % | As wt. % | Pb wt. % | Ni wt. % | Co wt. % | Fe wt. % | Zn wt. % | Sb wt. % | Bi wt. % | Ag wt. % | Au wt. % | Te wt. % | Se wt. % | Mn wt. % |
|-------------------------------|----------------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|
| MA-136328 | Bo 07/576 | 87 | 0.590 | 0.446 | 0.011 | 9.73 | 1.13 | 1.44 | b.d. | 0.065 | 0.004 | 0.016 | b.d. | 0.009 | b.d. | b.d. |
| MIDDLE / LATE IRON AGE | | | | | | | | | | | | | | | | |
| MA-132281 | Bo 11/14 | 73 | 2.74 | 1.04 | 21.90 | 0.048 | b.d. | 0.534 | 0.344 | 0.630 | 0.084 | 0.102 | 0.049 | 0.001 | 0.002 | 0.004 |
| MA-132275 | Bo 10/832 | 81 | 17.36 | 0.071 | 0.442 | 0.054 | b.d. | 0.295 | 0.120 | 0.063 | 0.006 | 0.092 | 0.033 | 0.021 | b.d. | b.d. |
| MA-132225 | Bo 10/9 | 86 | 12.83 | 0.263 | 0.239 | 0.025 | b.d. | 0.626 | 0.067 | 0.277 | 0.032 | 0.075 | 0.008 | 0.008 | 0.004 | b.d. |
| MA-132194 | Bo 861/t | 89 | 10.18 | 0.012 | 0.077 | 0.017 | 0.003 | 0.291 | 0.060 | 0.016 | b.d. | 0.022 | 0.022 | b.d. | 0.018 | b.d. |
| MA-132191 | Bo 864/t | 87 | 11.18 | 0.027 | 0.194 | 0.216 | 0.001 | 0.826 | 0.097 | 0.040 | 0.006 | 0.028 | 0.014 | b.d. | 0.004 | 0.002 |
| MA-132393 | Bo 06/1639 | 89 | 10.05 | 0.125 | 0.091 | 0.118 | 0.001 | 0.070 | 0.095 | 0.062 | 0.007 | 0.077 | 0.022 | b.d. | b.d. | b.d. |
| MA-132380 | Bo 06/1765 | 98 | 0.046 | 1.21 | 0.077 | 0.027 | 0.001 | 0.280 | 0.035 | 0.194 | 0.004 | 0.008 | 0.018 | 0.016 | 0.008 | b.d. |
| MA-132200 | Bo 06/233 | 97 | 0.697 | 0.348 | 0.211 | 0.755 | 0.033 | 0.290 | 0.110 | 0.078 | 0.008 | 0.052 | 0.031 | 0.005 | 0.001 | b.d. |
| MA-132405 | Bo 06/2330 | 98 | 0.048 | 0.464 | 0.048 | 0.448 | 0.013 | 0.508 | 0.183 | 0.085 | 0.021 | 0.023 | 0.117 | 0.003 | 0.004 | 0.001 |
| MA-132370 | Bo 06/515 | 89 | 8.74 | 0.598 | 0.906 | 0.100 | 0.010 | 0.134 | 0.024 | 0.078 | 0.005 | 0.005 | 0.016 | 0.002 | 0.003 | b.d. |
| KERKENES DAĞ | | | | | | | | | | | | | | | | |
| LATE IRON AGE | | | | | | | | | | | | | | | | |
| MA-132591 | 02TR03U11met02 | 87 | 11.36 | 0.169 | 0.057 | 0.464 | 0.684 | 0.292 | 0.042 | 0.030 | 0.004 | 0.031 | 0.038 | 0.007 | 0.003 | b.d. |
| MA-132600 | 10TR13U14met02 | 84 | 14.57 | 0.330 | 0.010 | 0.044 | 0.002 | 0.419 | 0.015 | 0.040 | 0.006 | 0.086 | 0.002 | 0.004 | 0.002 | b.d. |
| MA-132620 | 11TR23U08met01 | 88 | 1.94 | b.d. | 9.07 | 0.135 | b.d. | 0.033 | 0.115 | 0.093 | 0.054 | 0.031 | 0.031 | 0.002 | b.d. | b.d. |
| MA-132601 | 11TR23U11met01 | 68 | 16.99 | 0.032 | 12.31 | 0.065 | b.d. | 0.236 | 1.003 | 0.834 | 0.107 | 0.077 | 0.118 | 0.077 | b.d. | 0.013 |
| MA-132607 | 11TR23U12met01 | 91 | 7.18 | 0.127 | 0.296 | 0.612 | 0.006 | 0.242 | 0.026 | 0.026 | 0.004 | 0.051 | 0.019 | 0.004 | 0.003 | b.d. |
| MA-132597 | 11TR23U21met01 | 74 | 24.66 | 0.132 | 0.020 | 0.019 | 0.061 | 1.32 | 0.062 | 0.019 | 0.006 | 0.095 | b.d. | 0.004 | b.d. | 0.001 |
| MA-132594 | 11TR23U22met01 | 79 | 17.96 | 0.780 | 0.962 | 0.036 | 0.004 | 0.480 | 0.073 | 0.238 | 0.041 | 0.183 | 0.019 | b.d. | 0.003 | 0.004 |
| MA-132629 | 11TR24U11met01 | 55 | 37.97 | 0.002 | 5.30 | 0.172 | 0.063 | 1.24 | 0.075 | 0.001 | 0.015 | 0.007 | b.d. | b.d. | 0.001 | 0.002 |
| MA-132631 | 11TR24U11met02 | 89 | 10.13 | 0.077 | 0.037 | 0.185 | 0.012 | 0.140 | 0.100 | 0.044 | b.d. | 0.003 | 0.024 | 0.010 | b.d. | b.d. |
| MA-132626 | 11TR24U11met03 | 95 | 4.42 | 0.091 | 0.056 | 0.090 | 0.022 | 0.190 | 0.007 | 0.016 | 0.003 | 0.014 | 0.002 | 0.001 | 0.002 | b.d. |
| MA-132615 | 11TR24U11met03 | 76 | 21.60 | 0.471 | 0.498 | 0.008 | b.d. | 0.531 | 0.031 | 0.395 | 0.041 | 0.245 | 0.006 | 0.008 | 0.003 | b.d. |
| MA-133069 | 11TR24U11met04 | 30 | 63.55 | 0.680 | 5.05 | 0.005 | b.d. | 0.705 | 0.001 | 0.184 | 0.035 | 0.261 | 0.007 | 0.009 | 0.002 | 0.007 |

| Mannheim Number | Object Number | Cu wt. % | Sn wt. % | As wt. % | Pb wt. % | Ni wt. % | Co wt. % | Fe wt. % | Zn wt. % | Sb wt. % | Bi wt. % | Ag wt. % | Au wt. % | Te wt. % | Se wt. % | Mn wt. % |
|-----------------|----------------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|
| MA-132593 | 11TR24U11met05 | 92 | 7.10 | 0.050 | 0.228 | 0.314 | 0.005 | 0.229 | b.d. | 0.015 | 0.001 | 0.039 | 0.001 | 0.001 | 0.002 | b.d. |
| MA-132608 | 11TR24U15met01 | 91 | 8.55 | 0.153 | 0.196 | 0.212 | 0.005 | 0.217 | 0.038 | 0.047 | 0.008 | 0.049 | 0.016 | 0.003 | 0.011 | b.d. |
| MA-132612 | 11TR24U17met01 | 95 | 3.75 | 0.298 | 0.333 | 0.094 | 0.008 | 0.332 | 0.244 | 0.176 | 0.012 | 0.043 | 0.034 | 0.009 | b.d. | b.d. |
| MA-132624 | 11TR24U20met01 | 94 | 3.88 | 0.036 | 0.379 | 0.721 | 0.013 | 0.544 | 0.240 | 0.079 | 0.001 | 0.018 | 0.038 | b.d. | 0.008 | 0.001 |
| MA-132606 | 11TR24U21met01 | 90 | 8.83 | 0.149 | 0.118 | 0.181 | 0.006 | 0.598 | 0.090 | 0.063 | 0.009 | 0.056 | 0.011 | 0.003 | 0.001 | b.d. |
| MA-132613 | 11TR24U21met02 | 68 | 3.54 | 1.77 | 6.04 | 0.035 | 0.020 | 19.34 | 0.559 | 0.191 | 0.060 | 0.042 | 0.024 | 0.004 | b.d. | 0.152 |
| MA-132619 | 11TR24U22met03 | 92 | 7.35 | 0.175 | 0.288 | 0.113 | 0.004 | 0.193 | 0.127 | 0.061 | 0.001 | 0.033 | 0.024 | b.d. | 0.006 | b.d. |
| MA-132622 | 11TR24U22met04 | 91 | 8.19 | 0.043 | 0.104 | 0.057 | 0.102 | 0.204 | 0.212 | 0.054 | 0.005 | 0.025 | 0.043 | b.d. | 0.004 | 0.002 |
| MA-132614 | 11TR24U22met06 | 82 | 17.02 | 0.115 | 0.829 | 0.023 | 0.008 | 0.064 | 0.073 | 0.059 | 0.011 | 0.039 | 0.006 | 0.006 | 0.005 | b.d. |
| MA-132605 | 11TR24U22met07 | 82 | 16.68 | 0.204 | 1.17 | 0.036 | 0.001 | 0.138 | 0.063 | 0.049 | 0.020 | 0.057 | 0.009 | 0.005 | 0.004 | b.d. |
| MA-132596 | 11TR24U22met08 | 73 | 23.82 | 0.128 | 2.41 | 0.027 | 0.006 | 0.153 | 0.147 | 0.080 | 0.020 | 0.100 | 0.032 | b.d. | 0.002 | 0.006 |
| MA-132625 | 00CT18U17met01 | 89 | 10.37 | 0.088 | 0.220 | 0.103 | 0.001 | 0.046 | 0.089 | 0.100 | 0.007 | 0.036 | 0.012 | 0.004 | 0.007 | b.d. |
| MA-132604 | 00CT18U17met02 | 88 | 11.07 | 0.090 | 0.133 | 0.067 | b.d. | 0.025 | 0.029 | 0.093 | 0.009 | 0.058 | 0.008 | 0.025 | 0.007 | b.d. |
| MA-132630 | 02TR01U02met01 | 90 | 9.99 | 0.053 | 0.008 | 0.025 | b.d. | 0.060 | 0.002 | 0.009 | 0.003 | 0.004 | 0.003 | 0.003 | 0.003 | b.d. |
| MA-132628 | 02TR01U02met02 | 90 | 9.10 | 0.068 | 0.025 | 0.030 | b.d. | 0.104 | 0.132 | 0.070 | 0.007 | 0.007 | 0.059 | 0.010 | 0.010 | b.d. |
| MA-132599 | 02TR01U07met01 | 63 | 27.16 | b.d. | 3.20 | 0.105 | b.d. | 1.01 | 5.502 | 0.028 | 0.020 | 0.046 | 0.198 | b.d. | 0.010 | 0.007 |
| MA-132598 | 04TR11U14met01 | 90 | 9.64 | 0.066 | 0.011 | 0.011 | 0.025 | 0.355 | b.d. | 0.045 | 0.011 | 0.092 | 0.019 | 0.023 | 0.000 | b.d. |
| MA-132598 | 04TR15U01met01 | 89 | 10.40 | 0.061 | 0.022 | 0.010 | 0.029 | 0.203 | b.d. | 0.005 | 0.014 | 0.094 | 0.018 | b.d. | 0.001 | 0.003 |
| MA-132611 | 05TR21U09met03 | 99 | 0.012 | 0.058 | 0.071 | 0.121 | 0.059 | 0.015 | 0.116 | 0.005 | 0.010 | 0.010 | 0.022 | b.d. | 0.002 | b.d. |
| MA-132611 | 04TT25U08met01 | 87 | 12.41 | 0.117 | 0.020 | 0.502 | b.d. | 0.257 | b.d. | 0.006 | 0.009 | 0.044 | 0.021 | 0.037 | 0.006 | 0.006 |
| MA-132609 | 04TT25U08met02 | 86 | 12.62 | 0.132 | 0.026 | 0.489 | b.d. | 0.258 | 0.007 | 0.019 | 0.009 | 0.047 | 0.009 | 0.019 | 0.001 | b.d. |
| MA-132595 | 07TT31U04met01 | 84 | 14.25 | 0.297 | 1.57 | 0.045 | 0.000 | 0.012 | 0.002 | 0.069 | 0.022 | 0.105 | 0.013 | 0.032 | 0.001 | 0.004 |
| MA-132623 | 11TR29U14met02 | 89 | 9.68 | 0.120 | 0.070 | 0.710 | 0.037 | 0.227 | 0.159 | 0.030 | 0.003 | 0.020 | 0.048 | b.d. | 0.008 | 0.001 |
| MA-132618 | 11TR29U32met01 | 88 | 1.73 | 0.090 | 10.20 | 0.024 | b.d. | 0.024 | 0.090 | 0.143 | 0.029 | 0.034 | b.d. | 0.004 | 0.001 | 0.003 |
| MA-132621 | 11TR29U34met02 | 87 | 10.33 | 0.023 | 0.034 | 0.397 | 0.014 | 2.38 | 0.067 | 0.012 | 0.003 | 0.025 | 0.014 | 0.002 | 0.004 | 0.007 |
| MA-132617 | 11TR29U34met03 | 84 | 14.38 | 0.174 | 0.102 | 0.255 | 0.075 | 0.648 | 0.152 | 0.096 | 0.009 | 0.035 | 0.023 | 0.008 | 0.005 | 0.001 |
| MA-132616 | 96TT15U13met05 | 89 | 10.11 | 0.175 | 0.151 | 0.018 | 0.007 | 0.213 | b.d. | 0.035 | 0.005 | 0.036 | 0.014 | 0.015 | b.d. | 0.009 |
| MA-132602 | 97TT15U00met01 | 90 | 8.27 | 0.540 | 0.366 | 0.024 | b.d. | 0.480 | 0.003 | 0.063 | 0.004 | 0.050 | 0.001 | b.d. | b.d. | b.d. |

| Mannheim Number | Object Number | Cu wt. % | Sn wt. % | As wt. % | Pb wt. % | Ni wt. % | Co wt. % | Fe wt. % | Zn wt. % | Sb wt. % | Bi wt. % | Ag wt. % | Au wt. % | Te wt. % | Se wt. % | Mn wt. % |
|--------------------|----------------|-------------|-------------|-------------|-------------|-------------|-------------|-------------|-------------|-------------|-------------|-------------|-------------|-------------|-------------|-------------|
| MA-132603 | 98TT21U01met02 | 89 | 9.17 | 0.803 | 0.442 | 0.016 | <i>b.d.</i> | 0.332 | 0.006 | 0.088 | 0.004 | 0.067 | 0.008 | 0.005 | 0.001 | <i>b.d.</i> |

APPENDIX C: pXRF RESULTS

| Mannheim Number | Object Number | Cu wt. % | Sn wt. % | As wt. % | Pb wt. % | Ni wt. % | Co wt. % | Fe wt. % | Zn wt. % | Sb wt. % | Bi wt. % | Ag wt. % | Au wt. % |
|--------------------------|---------------|----------|-------------|----------|-------------|-------------|-------------|----------|-------------|-------------|-------------|-------------|-------------|
| BOĞAZKÖY | | | | | | | | | | | | | |
| EARLY BRONZE AGE | | | | | | | | | | | | | |
| | Bo 96/38 | 96 | <i>b.d.</i> | 1.37 | 0.59 | <i>b.d.</i> | <i>b.d.</i> | 2.08 | 0.14 | 0.06 | <i>b.d.</i> | 0.09 | <i>b.d.</i> |
| | Bo 97/98 | 99 | <i>b.d.</i> | 0.04 | 0.01 | 0.02 | <i>b.d.</i> | 0.09 | 0.56 | 0.02 | 0.01 | 0.06 | <i>b.d.</i> |
| | ETD 97/196 | 93 | 0.40 | 3.21 | 1.51 | 0.04 | <i>b.d.</i> | 1.45 | 0.05 | 0.04 | 0.02 | 0.04 | <i>b.d.</i> |
| | ETD 97/206 | 97 | <i>b.d.</i> | 1.27 | 0.18 | <i>b.d.</i> | <i>b.d.</i> | 1.12 | <i>b.d.</i> | 0.03 | 0.01 | 0.04 | <i>b.d.</i> |
| | ETD 97/213 | 98 | 0.02 | 1.20 | 0.07 | 0.04 | <i>b.d.</i> | 0.73 | 0.07 | 0.04 | <i>b.d.</i> | 0.03 | <i>b.d.</i> |
| | ETD 97/219 | 96 | <i>b.d.</i> | 3.01 | 0.18 | <i>b.d.</i> | <i>b.d.</i> | 0.63 | <i>b.d.</i> | 0.04 | <i>b.d.</i> | 0.04 | <i>b.d.</i> |
| | ETD 97/221 | 97 | 0.44 | 0.90 | 0.15 | 0.04 | 0.01 | 0.58 | <i>b.d.</i> | 0.02 | <i>b.d.</i> | 0.42 | <i>b.d.</i> |
| | ETD 98/12 | 95 | 0.39 | 3.98 | 0.06 | <i>b.d.</i> | <i>b.d.</i> | 0.62 | <i>b.d.</i> | 0.05 | <i>b.d.</i> | 0.02 | <i>b.d.</i> |
| MIDDLE BRONZE AGE | | | | | | | | | | | | | |
| | Bo 13/445 | 97 | 0.09 | 1.89 | 0.10 | 0.08 | 0.04 | 0.58 | <i>b.d.</i> | 0.05 | 0.02 | 0.14 | <i>b.d.</i> |
| | Bo 13/450 | 99 | <i>b.d.</i> | 0.26 | 0.11 | 0.07 | 0.02 | 0.65 | 0.10 | <i>b.d.</i> | <i>b.d.</i> | 0.11 | <i>b.d.</i> |
| | Bo 13/458 | 95 | 0.17 | 3.54 | 0.44 | 0.36 | 0.04 | 0.39 | 0.08 | 0.03 | 0.02 | 0.15 | <i>b.d.</i> |
| | Bo 13/459 | 98 | <i>b.d.</i> | 0.68 | 0.16 | 0.07 | <i>b.d.</i> | 0.41 | 0.14 | 0.08 | 0.01 | 0.13 | <i>b.d.</i> |
| | Bo 13/462 | 95 | 0.06 | 2.79 | 1.00 | 0.08 | <i>b.d.</i> | 0.54 | <i>b.d.</i> | 0.16 | 0.32 | 0.31 | <i>b.d.</i> |
| | Bo 13/463 | 99 | <i>b.d.</i> | 0.36 | 0.06 | 0.05 | <i>b.d.</i> | 0.17 | 0.12 | <i>b.d.</i> | <i>b.d.</i> | 0.15 | <i>b.d.</i> |
| | Bo 13/564 | 97 | 0.06 | 2.04 | 0.57 | 0.10 | <i>b.d.</i> | 0.21 | 0.08 | 0.03 | <i>b.d.</i> | 0.23 | <i>b.d.</i> |
| | Bo 13/569 | 99 | 0.04 | 0.39 | 0.11 | <i>b.d.</i> | <i>b.d.</i> | 0.35 | 0.07 | <i>b.d.</i> | 0.04 | 0.15 | <i>b.d.</i> |
| | Bo 13/631 | 99 | <i>b.d.</i> | 0.33 | <i>b.d.</i> | <i>b.d.</i> | <i>b.d.</i> | 0.01 | 0.05 | 0.02 | <i>b.d.</i> | 0.13 | <i>b.d.</i> |
| | Bo 13/668 | 99 | <i>b.d.</i> | 0.44 | 0.10 | 0.04 | <i>b.d.</i> | 0.37 | 0.08 | <i>b.d.</i> | <i>b.d.</i> | <i>b.d.</i> | <i>b.d.</i> |
| | Bo 13/670 | 98 | 0.11 | 0.82 | 0.27 | 0.04 | <i>b.d.</i> | 0.41 | 0.05 | 0.01 | 0.01 | 0.03 | <i>b.d.</i> |
| MA-132546 | Bo 143/1 | 97 | 0.02 | 1.98 | 0.04 | 0.04 | <i>b.d.</i> | 0.92 | 0.05 | 0.02 | <i>b.d.</i> | <i>b.d.</i> | <i>b.d.</i> |

| Mannheim Number | Object Number | Cu wt. % | Sn wt. % | As wt. % | Pb wt. % | Ni wt. % | Co wt. % | Fe wt. % | Zn wt. % | Sb wt. % | Bi wt. % | Ag wt. % | Au wt. % |
|------------------------|-----------------------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|
| MA-132557 | Bo 348/h | 98 | 0.02 | 0.26 | 0.42 | 0.02 | b.d. | 1.38 | 0.22 | b.d. | b.d. | 0.01 | b.d. |
| MA-132556 | Bo 311/s | 98 | 0.03 | 1.29 | 0.03 | 0.02 | 0.01 | 0.72 | 0.14 | b.d. | b.d. | 0.02 | b.d. |
| MA-132558 | Bo 400/s | 98 | b.d. | 1.44 | 0.08 | 0.02 | b.d. | 0.41 | 0.09 | b.d. | b.d. | 0.02 | b.d. |
| LATE BRONZE AGE | | | | | | | | | | | | | |
| MA-136322 | Boehmer 1972: Nr. 190 | 98 | 0.04 | 0.07 | 0.09 | 1.52 | 0.03 | 0.07 | 0.25 | 0.01 | 0.00 | 0.03 | b.d. |
| | Bo 94/1 | 88 | b.d. | 0.24 | 0.01 | 11.1 | 0.40 | 0.74 | b.d. | b.d. | 0.00 | b.d. | b.d. |
| | Bo 94/109 | 83 | b.d. | 1.58 | 0.04 | 12.5 | 0.80 | 1.95 | b.d. | 0.06 | 0.01 | 0.02 | b.d. |
| | Bo 94/113 | 98 | 0.04 | 1.07 | 0.14 | 0.03 | b.d. | 0.60 | 0.12 | 0.03 | b.d. | 0.03 | b.d. |
| | Bo 94/116 | 98 | b.d. | 1.27 | 0.10 | 0.07 | b.d. | 0.42 | 0.06 | 0.07 | 0.03 | 0.07 | b.d. |
| | Bo 94/14 | 98 | b.d. | 1.56 | 0.16 | 0.02 | b.d. | 0.20 | 0.07 | 0.02 | b.d. | 0.02 | b.d. |
| | Bo 94/141 | 97 | 0.09 | 0.77 | 0.05 | 0.18 | b.d. | 1.33 | 0.13 | 0.07 | 0.01 | 0.13 | b.d. |
| | Bo 94/20 | 97 | 0.04 | 1.54 | 0.11 | 0.07 | 0.02 | 0.67 | 0.16 | 0.07 | 0.01 | 0.13 | b.d. |
| | Bo 94/21 | 87 | 10.9 | 0.18 | 1.54 | b.d. | b.d. | 0.51 | 0.16 | 0.05 | b.d. | 0.05 | b.d. |
| | Bo 94/28 | 73 | 24.2 | 0.12 | 1.05 | b.d. | b.d. | 0.95 | 0.16 | 0.03 | b.d. | 0.07 | b.d. |
| | Bo 94/36 | 69 | 25.6 | 1.24 | 0.27 | 0.07 | 0.06 | 2.94 | 0.32 | 0.54 | b.d. | 0.10 | b.d. |
| | Bo 94/37 | 73 | 25.1 | 0.64 | 0.40 | 0.12 | b.d. | 0.47 | 0.24 | 0.06 | b.d. | 0.10 | b.d. |
| | Bo 94/4 | 98 | 0.06 | 0.58 | 0.03 | 0.25 | 0.02 | 0.72 | 0.05 | b.d. | 0.01 | 0.02 | b.d. |
| | Bo 94/40 | 92 | 0.21 | 2.54 | 2.28 | b.d. | b.d. | 2.13 | 0.19 | 0.23 | 0.42 | 0.30 | 0.04 |
| | Bo 94/57 | 92 | 6.35 | 0.59 | 0.16 | 0.04 | 0.02 | 0.44 | 0.14 | 0.08 | b.d. | b.d. | b.d. |
| | Bo 94/76 | 97 | 0.04 | 2.08 | 0.11 | 0.02 | b.d. | 0.20 | 0.10 | 0.05 | 0.02 | 0.03 | b.d. |
| | Bo 94/9 | 100 | b.d. | 0.11 | b.d. | 0.05 | 0.01 | 0.12 | 0.07 | b.d. | 0.00 | b.d. | b.d. |
| | Bo 95/100 | 95 | 2.86 | 0.95 | 0.28 | 0.02 | b.d. | 0.69 | 0.12 | 0.09 | b.d. | 0.01 | b.d. |
| | Bo 95/111 | 82 | 16.9 | 0.37 | 0.07 | 0.08 | 0.05 | 0.69 | 0.07 | 0.04 | b.d. | 0.02 | b.d. |
| | Bo 95/113 | 85 | 0.12 | 0.75 | 0.06 | 9.76 | 0.44 | 3.95 | b.d. | 0.06 | 0.02 | 0.05 | b.d. |
| | Bo 95/119 | 94 | 2.39 | 1.69 | 0.05 | 0.04 | 0.06 | 1.20 | 0.14 | 0.03 | b.d. | 0.03 | b.d. |
| | Bo 95/25 | 86 | 11.6 | 0.96 | 0.12 | 0.02 | 0.01 | 1.03 | 0.17 | 0.02 | b.d. | 0.03 | b.d. |
| | Bo 95/27 | 95 | b.d. | 3.19 | 0.28 | 0.97 | b.d. | 0.68 | 0.15 | 0.06 | 0.03 | 0.08 | b.d. |

| Mannheim Number | Object Number | Cu | | Sn | | As | | Pb | | Ni | | Co | | Fe | | Zn | | Sb | | Bi | | Ag | | Au | |
|--------------------|---------------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|
| | | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % |
| Bo 95/41 | | 85 | 13.9 | 0.63 | 0.21 | 0.04 | b.d. | 0.48 | 0.14 | 0.02 | b.d. | 0.12 | b.d. | 0.12 | 0.13 | b.d. | b.d. | 0.02 | 0.01 | 0.13 | 0.03 | 0.35 | b.d. | b.d. | |
| Bo 95/76 | | 98 | b.d. | 0.18 | 0.03 | 0.31 | 0.03 | 0.79 | b.d. | 0.12 | 0.01 | 0.13 | b.d. | 0.07 | 0.14 | 0.35 | b.d. | 0.04 | 0.05 | 0.07 | 0.03 | 0.14 | 0.35 | b.d. | |
| Bo 95/80 | | 85 | 0.04 | 6.11 | 0.89 | 6.59 | 0.05 | 0.27 | 0.10 | 0.10 | 0.03 | 0.03 | 0.03 | 0.03 | 0.03 | 0.03 | 0.03 | 0.03 | 0.03 | 0.03 | 0.03 | 0.03 | 0.03 | b.d. | |
| Bo 95/82 | | 97 | 0.10 | 0.90 | 0.57 | 0.09 | b.d. | 0.75 | 0.08 | 0.04 | 0.05 | 0.07 | b.d. | 0.14 | 0.35 | b.d. | b.d. | 0.04 | 0.05 | 0.07 | 0.03 | 0.14 | 0.35 | b.d. | |
| Bo 95/95 | | 82 | 15.4 | 0.79 | 0.57 | 0.30 | 0.02 | 0.39 | 0.16 | 0.06 | b.d. | 0.03 | 0.03 | 0.03 | 0.03 | 0.03 | 0.03 | 0.03 | 0.03 | 0.03 | 0.03 | 0.03 | 0.03 | b.d. | |
| Bo 96/120 | | 95 | 1.68 | 1.65 | 0.39 | b.d. | b.d. | 1.05 | 0.30 | 0.03 | b.d. | 0.03 | 0.03 | 0.03 | 0.03 | 0.03 | 0.03 | 0.03 | 0.03 | 0.03 | 0.03 | 0.03 | 0.03 | b.d. | |
| Bo 96/34 | | 95 | 2.68 | 0.91 | 0.32 | 0.85 | b.d. | 0.53 | b.d. | 0.04 | 0.01 | b.d. | b.d. | 0.03 | 0.03 | b.d. | b.d. | 0.04 | 0.01 | b.d. | b.d. | b.d. | b.d. | b.d. | |
| Bo 96/36 | | 89 | 8.95 | 0.76 | 0.30 | 0.14 | 0.02 | 1.06 | 0.08 | 0.10 | b.d. | 0.03 | 0.03 | 0.03 | 0.03 | 0.03 | 0.03 | 0.03 | 0.03 | 0.03 | 0.03 | 0.03 | 0.03 | b.d. | |
| Bo 96/48 | | 66 | 29.7 | 1.43 | 0.85 | 0.35 | b.d. | 1.61 | 0.10 | 0.11 | 0.02 | 0.11 | b.d. | 0.05 | 0.04 | 0.04 | 0.04 | 0.04 | 0.04 | 0.04 | 0.04 | 0.04 | 0.04 | b.d. | |
| Bo 97/101 | | 94 | b.d. | 4.57 | 0.20 | 0.09 | 0.03 | 1.01 | 0.06 | 0.06 | b.d. | 0.05 | b.d. | 0.05 | 0.04 | 0.04 | 0.04 | 0.04 | 0.04 | 0.04 | 0.04 | 0.04 | 0.04 | b.d. | |
| Bo 97/102 | | 87 | 0.23 | 0.97 | 0.10 | 11.1 | 0.10 | 0.12 | b.d. | 0.05 | 0.01 | 0.04 | b.d. | 0.13 | 0.13 | b.d. | b.d. | 0.05 | 0.01 | 0.04 | 0.04 | 0.04 | 0.04 | b.d. | |
| Bo 97/16 | | 72 | 25.8 | 0.53 | 0.61 | 0.04 | b.d. | 0.62 | 0.15 | 0.05 | b.d. | 0.13 | b.d. | 0.05 | 0.04 | 0.04 | 0.04 | 0.04 | 0.04 | 0.04 | 0.04 | 0.04 | 0.04 | b.d. | |
| Bo 97/18 | | 94 | 0.10 | 3.98 | 0.48 | b.d. | b.d. | 0.84 | 0.11 | 0.09 | 0.04 | 0.05 | b.d. | 0.05 | 0.04 | 0.04 | 0.04 | 0.04 | 0.04 | 0.04 | 0.04 | 0.04 | 0.04 | b.d. | |
| Bo 97/19 | | 97 | 0.62 | 1.25 | 0.25 | 0.03 | b.d. | 0.33 | b.d. | 0.08 | 0.02 | 0.09 | b.d. | 0.09 | 0.09 | 0.09 | 0.09 | 0.09 | 0.09 | 0.09 | 0.09 | 0.09 | 0.09 | b.d. | |
| Bo 97/23 | | 95 | 0.17 | 3.59 | 0.11 | 0.10 | b.d. | 0.51 | 0.08 | 0.20 | 0.01 | 0.04 | b.d. | 0.04 | 0.04 | 0.04 | 0.04 | 0.04 | 0.04 | 0.04 | 0.04 | 0.04 | 0.04 | b.d. | |
| Bo 97/24 | | 94 | b.d. | 3.56 | 1.02 | 0.07 | b.d. | 0.77 | 0.11 | 0.06 | b.d. | 0.03 | b.d. | 0.03 | 0.03 | 0.03 | 0.03 | 0.03 | 0.03 | 0.03 | 0.03 | 0.03 | 0.03 | b.d. | |
| Bo 97/27 | | 96 | 0.31 | 1.06 | 1.45 | 0.04 | 0.01 | 0.47 | 0.05 | 0.03 | 0.02 | 0.07 | b.d. | 0.07 | 0.07 | 0.07 | 0.07 | 0.07 | 0.07 | 0.07 | 0.07 | 0.07 | 0.07 | b.d. | |
| Bo 97/33 | | 86 | b.d. | 0.45 | 0.03 | 8.71 | 0.83 | 3.54 | b.d. | 0.02 | b.d. | 0.02 | b.d. | 0.02 | 0.02 | 0.02 | 0.02 | 0.02 | 0.02 | 0.02 | 0.02 | 0.02 | 0.02 | b.d. | |
| Bo 97/37 | | 97 | 0.21 | b.d. | 0.17 | 0.19 | b.d. | 2.48 | 0.11 | 0.02 | 0.01 | b.d. | b.d. | 0.02 | 0.01 | b.d. | b.d. | 0.02 | 0.01 | b.d. | b.d. | b.d. | b.d. | b.d. | |
| Bo 98/13 | | 97 | 0.06 | 0.93 | 0.14 | b.d. | b.d. | 1.49 | 0.12 | 0.06 | 0.11 | 0.04 | b.d. | 0.04 | 0.04 | 0.04 | 0.04 | 0.04 | 0.04 | 0.04 | 0.04 | 0.04 | 0.04 | b.d. | |
| ETD 94/127 | | 81 | 0.12 | 0.19 | 0.02 | 14.0 | 2.53 | 2.41 | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | |
| ETD 94/191 | | 88 | 10.2 | 0.53 | 0.51 | b.d. | b.d. | 0.53 | b.d. | 0.05 | 0.02 | 0.04 | b.d. | 0.04 | 0.04 | 0.04 | 0.04 | 0.04 | 0.04 | 0.04 | 0.04 | 0.04 | 0.04 | b.d. | |
| ETD 94/192 | | 100 | b.d. | 0.02 | 0.02 | b.d. | b.d. | 0.14 | 0.08 | b.d. | 0.02 | 0.03 | b.d. | 0.03 | 0.03 | 0.03 | 0.03 | 0.03 | 0.03 | 0.03 | 0.03 | 0.03 | 0.03 | b.d. | |
| ETD 94/198 | | 97 | 0.07 | 1.27 | 0.25 | 0.38 | b.d. | 0.31 | 0.14 | 0.08 | 0.01 | 0.02 | b.d. | 0.02 | 0.02 | 0.02 | 0.02 | 0.02 | 0.02 | 0.02 | 0.02 | 0.02 | 0.02 | b.d. | |
| ETD 94/215 | | 85 | 0.03 | 0.11 | 0.10 | 12.0 | 1.59 | 1.42 | b.d. | b.d. | 0.01 | 0.02 | b.d. | 0.02 | 0.02 | 0.02 | 0.02 | 0.02 | 0.02 | 0.02 | 0.02 | 0.02 | 0.02 | b.d. | |
| ETD 94/217 | | 83 | b.d. | 0.14 | 0.02 | 15.2 | 0.87 | 0.40 | b.d. | 0.01 | b.d. | 0.02 | b.d. | 0.02 | 0.02 | 0.02 | 0.02 | 0.02 | 0.02 | 0.02 | 0.02 | 0.02 | 0.02 | b.d. | |
| ETD 94/234 | | 98 | 0.21 | 1.25 | 0.20 | 0.02 | b.d. | 0.40 | b.d. | 0.09 | 0.02 | 0.19 | b.d. | 0.02 | 0.02 | 0.02 | 0.02 | 0.02 | 0.02 | 0.02 | 0.02 | 0.02 | 0.02 | b.d. | |
| ETD 94/246 | | 97 | 0.27 | 1.23 | 0.09 | 0.28 | 0.03 | 0.46 | 0.08 | 0.06 | 0.01 | 0.02 | b.d. | 0.02 | 0.02 | 0.02 | 0.02 | 0.02 | 0.02 | 0.02 | 0.02 | 0.02 | 0.02 | b.d. | |

| Mannheim Number | Object Number | Cu wt. % | Sn wt. % | As wt. % | Pb wt. % | Ni wt. % | Co wt. % | Fe wt. % | Zn wt. % | Sb wt. % | Bi wt. % | Ag wt. % | Au wt. % |
|------------------|---------------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|
| ETD 94/248 | | 99 | 0.09 | 0.50 | 0.03 | 0.07 | 0.01 | 0.37 | 0.06 | b.d. | b.d. | 0.02 | b.d. |
| ETD 94/263 | | 99 | b.d. | 0.24 | 0.34 | 0.03 | b.d. | 0.73 | 0.04 | 0.02 | 0.01 | 0.02 | b.d. |
| ETD 94/356 | | 79 | 19.1 | 0.45 | 0.28 | b.d. | b.d. | 0.80 | 0.07 | 0.11 | b.d. | b.d. | b.d. |
| ETD 94/4 | | 91 | 4.49 | 2.29 | 0.23 | 0.09 | 0.02 | 1.79 | 0.10 | 0.11 | b.d. | 0.03 | b.d. |
| ETD 94/460 | | 68 | 31.1 | 0.59 | 0.15 | 0.07 | b.d. | 0.33 | 0.09 | b.d. | b.d. | b.d. | b.d. |
| ETD 94/471 | | 84 | 15.1 | 0.37 | 0.09 | 0.02 | b.d. | 0.43 | 0.05 | 0.02 | b.d. | b.d. | b.d. |
| ETD 94/479a | | 98 | b.d. | 1.43 | 0.04 | b.d. | b.d. | 0.84 | b.d. | 0.05 | 0.02 | 0.06 | b.d. |
| ETD 94/479b | | 80 | 17.8 | 0.44 | 0.36 | 0.05 | b.d. | 0.76 | 0.14 | 0.06 | b.d. | b.d. | b.d. |
| ETD 94/481 | | 98 | 0.02 | 1.22 | 0.10 | 0.12 | 0.01 | 0.46 | 0.10 | 0.05 | 0.01 | 0.03 | b.d. |
| ETD 94/482 | | 96 | 0.10 | 3.38 | 0.06 | 0.21 | b.d. | 0.34 | 0.11 | 0.06 | 0.02 | 0.03 | b.d. |
| ETD 94/486 | | 98 | 0.04 | 0.74 | 0.04 | 0.18 | 0.06 | 1.06 | 0.17 | 0.01 | 0.00 | 0.04 | b.d. |
| ETD 94/6 | | 90 | 8.94 | 0.55 | 0.08 | 0.13 | b.d. | 0.37 | 0.07 | 0.03 | b.d. | 0.05 | b.d. |
| ETD 94/7 | | 97 | 0.05 | 1.61 | 0.55 | b.d. | b.d. | 0.73 | 0.06 | 0.04 | 0.01 | b.d. | b.d. |
| ETD 95/212a | | 83 | 14.7 | 1.15 | 0.05 | 0.04 | 0.06 | 0.54 | 0.08 | 0.02 | b.d. | b.d. | b.d. |
| ETD 95/212b | | 92 | 4.42 | 0.62 | 0.22 | 0.14 | b.d. | 2.51 | 0.10 | 0.02 | b.d. | b.d. | b.d. |
| ETD 95/228A | | 95 | b.d. | 1.50 | 1.48 | 0.05 | 0.02 | 1.52 | 0.13 | 0.05 | 0.14 | 0.12 | b.d. |
| ETD 95/228B | | 88 | 11.0 | 0.35 | b.d. | b.d. | b.d. | 0.29 | 0.07 | b.d. | b.d. | b.d. | b.d. |
| ETD 95/228C | | 87 | 11.9 | 0.52 | 0.12 | 0.06 | 0.02 | 0.29 | 0.08 | 0.03 | b.d. | 0.07 | b.d. |
| ETD 95/228D | | 99 | 0.11 | 0.64 | 0.06 | 0.03 | b.d. | 0.17 | 0.08 | 0.04 | 0.10 | 0.06 | b.d. |
| MA-136329 | | 83 | b.d. | 0.60 | 0.03 | 12.1 | 0.54 | 3.20 | b.d. | 0.02 | 0.01 | 0.04 | b.d. |
| ETD 95/232 | | 98 | 0.04 | 1.02 | 0.04 | 0.11 | b.d. | 0.37 | 0.07 | 0.07 | b.d. | 0.02 | b.d. |
| ETD 95/262 | | 87 | 11.2 | 1.07 | 0.22 | 0.12 | b.d. | 0.36 | 0.14 | 0.07 | b.d. | 0.01 | b.d. |
| ETD 95/269 | | 98 | 0.04 | 0.86 | 0.24 | 0.07 | b.d. | 0.60 | 0.09 | 0.13 | 0.05 | 0.06 | b.d. |
| ETD 95/272 | | 91 | 7.21 | 0.47 | 0.97 | 0.04 | b.d. | 0.22 | 0.09 | 0.02 | b.d. | 0.04 | b.d. |
| ETD 95/283 | | 95 | b.d. | 2.53 | 0.71 | 0.13 | b.d. | 1.33 | 0.08 | 0.03 | 0.01 | 0.03 | b.d. |
| ETD 95/284A | | 90 | 0.86 | 0.21 | 0.05 | 6.29 | 0.97 | 0.81 | 0.06 | 0.02 | 0.01 | 0.59 | 0.09 |
| ETD 95/284B | | 79 | 19.4 | 0.41 | 0.32 | 0.17 | 0.01 | 0.17 | 0.15 | b.d. | b.d. | b.d. | b.d. |
| ETD 95/83 | | 95 | 0.09 | 2.64 | 1.29 | 0.05 | b.d. | 0.37 | 0.05 | 0.13 | 0.02 | 0.05 | b.d. |

| Mannheim Number | Object Number | Cu | | Sn | | As | | Pb | | Ni | | Co | | Fe | | Zn | | Sb | | Bi | | Ag | | Au | |
|--------------------|---------------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|
| | | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % |
| ETD 96/32 | | 96 | 0.33 | 0.06 | 0.05 | 0.03 | b.d. | 3.10 | 0.16 | b.d. | b.d. | 0.01 | 0.01 | b.d. | 0.16 | 0.05 | 0.27 | 0.01 | b.d. | 0.01 | b.d. | | | | |
| ETD 96/33 | | 99 | 0.04 | 0.59 | 0.07 | b.d. | b.d. | 0.18 | 0.05 | 0.27 | 0.01 | b.d. | 0.01 | b.d. | 0.18 | 0.05 | 0.27 | 0.01 | b.d. | 0.01 | b.d. | | | | |
| ETD 96/34 | | 98 | 0.04 | 0.60 | 0.02 | 0.40 | 0.05 | 0.61 | b.d. | 0.04 | b.d. | 0.04 | b.d. | 0.04 | 0.05 | 0.05 | 0.04 | b.d. | b.d. | b.d. | b.d. | | | | |
| ETD 96/35 | | 97 | 1.48 | 0.88 | 0.36 | 0.02 | b.d. | 0.66 | 0.05 | 0.04 | b.d. | 0.04 | b.d. | 0.04 | 0.05 | 0.04 | b.d. | b.d. | b.d. | b.d. | b.d. | | | | |
| ETD 96/36 | | 98 | 0.09 | 1.20 | 0.12 | b.d. | b.d. | 0.42 | 0.05 | 0.05 | 0.04 | 0.06 | 0.06 | 0.06 | 0.05 | 0.05 | 0.04 | 0.04 | 0.06 | 0.06 | b.d. | | | | |
| ETD 96/37 | | 99 | b.d. | 0.55 | 0.04 | 0.03 | b.d. | 0.18 | 0.04 | 0.08 | 0.01 | 0.04 | 0.04 | 0.04 | 0.08 | 0.01 | 0.04 | 0.04 | 0.04 | 0.04 | b.d. | | | | |
| ETD 96/41 | | 99 | b.d. | 0.63 | 0.03 | 0.07 | b.d. | 0.16 | 0.18 | b.d. | b.d. | 0.16 | b.d. | 0.16 | 0.18 | 0.01 | 0.03 | b.d. | b.d. | b.d. | b.d. | | | | |
| ETD 96/42 | | 99 | 0.80 | 0.29 | 0.02 | b.d. | b.d. | 0.21 | b.d. | b.d. | 0.01 | b.d. | 0.01 | b.d. | 0.21 | b.d. | 0.01 | b.d. | b.d. | b.d. | b.d. | | | | |
| ETD 96/43 | | 85 | 11.5 | 1.62 | 0.44 | 0.03 | b.d. | 0.77 | b.d. | 0.24 | b.d. | 0.77 | b.d. | 0.77 | b.d. | 0.24 | b.d. | 0.05 | 0.05 | 0.05 | b.d. | | | | |
| ETD 96/45 | | 97 | 0.07 | 1.48 | 0.19 | 0.28 | b.d. | 0.42 | b.d. | 0.18 | 0.01 | 0.03 | 0.03 | 0.42 | b.d. | 0.18 | 0.01 | 0.03 | 0.03 | 0.03 | b.d. | | | | |
| ETD 96/54 | | 99 | 0.05 | 0.60 | 0.02 | 0.01 | b.d. | 0.32 | b.d. | 0.04 | b.d. | 0.32 | b.d. | 0.32 | b.d. | 0.04 | b.d. | 0.06 | 0.06 | 0.06 | b.d. | | | | |
| ETD 96/62 | | 99 | 0.03 | 0.72 | 0.07 | 0.15 | b.d. | 0.26 | 0.08 | 0.04 | 0.01 | 0.01 | 0.01 | 0.26 | 0.08 | 0.04 | 0.01 | 0.01 | 0.01 | 0.01 | b.d. | | | | |
| ETD 97/212 | | 97 | 0.60 | 1.43 | 0.33 | 0.03 | b.d. | 0.46 | 0.08 | 0.09 | 0.05 | 0.07 | 0.07 | 0.46 | 0.08 | 0.09 | 0.05 | 0.07 | 0.07 | 0.07 | b.d. | | | | |
| ETD 97/218 | | 98 | b.d. | 1.34 | 0.23 | 0.03 | b.d. | 0.75 | b.d. | 0.01 | 0.01 | 0.01 | 0.01 | 0.75 | b.d. | 0.01 | 0.01 | 0.04 | 0.04 | 0.04 | b.d. | | | | |
| ETD 97/229 | | 98 | b.d. | 1.02 | 0.06 | 0.04 | b.d. | 0.37 | b.d. | 0.45 | b.d. | 0.37 | b.d. | 0.37 | b.d. | 0.45 | b.d. | 0.13 | 0.13 | 0.13 | b.d. | | | | |
| ETD 97/233 | | 97 | b.d. | 2.30 | 0.05 | 0.02 | b.d. | 0.23 | 0.04 | 0.08 | 0.02 | 0.16 | 0.16 | 0.23 | 0.04 | 0.08 | 0.02 | 0.16 | 0.16 | 0.16 | b.d. | | | | |
| ETD 97/240 | | 95 | 0.08 | 3.61 | 0.44 | 0.03 | b.d. | 0.51 | 0.14 | 0.27 | 0.02 | 0.03 | 0.03 | 0.51 | 0.14 | 0.27 | 0.02 | 0.03 | 0.03 | 0.03 | b.d. | | | | |
| ETD 97/241 | | 96 | b.d. | 2.52 | 0.43 | 0.91 | 0.09 | 0.21 | 0.08 | 0.03 | b.d. | 0.21 | 0.08 | 0.21 | 0.08 | 0.03 | b.d. | b.d. | b.d. | b.d. | b.d. | | | | |
| ETD 97/242 | | 82 | 15.8 | 0.73 | 0.97 | 0.05 | 0.01 | 0.13 | 0.10 | 0.11 | b.d. | 0.13 | 0.10 | 0.13 | 0.10 | 0.11 | b.d. | b.d. | b.d. | b.d. | b.d. | | | | |
| ETD 97/243 | | 98 | 0.07 | 0.81 | 0.16 | 0.03 | b.d. | 0.45 | 0.14 | 0.07 | b.d. | 0.45 | 0.14 | 0.45 | 0.14 | 0.07 | b.d. | 0.05 | 0.05 | 0.05 | b.d. | | | | |
| ETD 97/246 | | 98 | b.d. | 0.86 | 0.47 | b.d. | b.d. | 0.16 | 0.14 | 0.08 | 0.07 | 0.16 | 0.14 | 0.16 | 0.14 | 0.08 | 0.07 | 0.11 | 0.11 | 0.11 | b.d. | | | | |
| ETD 97/251 | | 87 | 11.1 | 0.72 | 0.18 | 0.07 | b.d. | 0.60 | 0.06 | 0.04 | b.d. | 0.60 | 0.06 | 0.60 | 0.06 | 0.04 | b.d. | 0.01 | 0.01 | 0.01 | b.d. | | | | |
| ETD 97/255 | | 95 | b.d. | 2.17 | 0.12 | 0.03 | 0.02 | 2.07 | 0.08 | 0.14 | 0.01 | 0.03 | 0.03 | 2.07 | 0.08 | 0.14 | 0.01 | 0.03 | 0.03 | 0.03 | b.d. | | | | |
| ETD 97/256 | | 98 | 0.10 | 1.49 | 0.08 | b.d. | b.d. | 0.35 | b.d. | 0.06 | b.d. | 0.35 | b.d. | 0.35 | b.d. | 0.06 | b.d. | 0.06 | 0.06 | 0.06 | b.d. | | | | |
| ETD 97/257 | | 94 | 0.14 | 4.17 | 0.46 | 0.13 | b.d. | 0.74 | b.d. | 0.02 | b.d. | 0.74 | b.d. | 0.74 | b.d. | 0.02 | b.d. | 0.04 | 0.04 | 0.04 | b.d. | | | | |
| ETD 97/268 | | 94 | 0.62 | 3.60 | 0.77 | 0.03 | b.d. | 0.72 | 0.08 | 0.06 | 0.01 | 0.05 | 0.05 | 0.72 | 0.08 | 0.06 | 0.01 | 0.05 | 0.05 | 0.05 | b.d. | | | | |
| ETD 98/06 | | 88 | 10.3 | 0.65 | 0.08 | b.d. | 0.07 | 0.16 | 0.18 | 0.02 | b.d. | 0.16 | 0.18 | 0.16 | 0.18 | 0.02 | b.d. | 0.14 | 0.14 | 0.14 | b.d. | | | | |
| ETD 98/07 | | 92 | 3.93 | 0.12 | 0.51 | 3.37 | 0.07 | 0.43 | 0.02 | 0.02 | b.d. | 0.43 | 0.02 | 0.43 | 0.02 | 0.02 | b.d. | 0.03 | 0.03 | 0.03 | b.d. | | | | |

| Mannheim Number | Object Number | Cu | | Sn | | As | | Pb | | Ni | | Co | | Fe | | Zn | | Sb | | Bi | | Ag | | Au | |
|--------------------|---------------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|
| | | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % |
| ETD 98/09 | | 97 | 0.02 | 1.83 | 0.16 | 0.04 | b.d. | 0.36 | 0.12 | 0.13 | 0.05 | 0.08 | b.d. | | | | | | | | | | | | |
| ETD 98/11 | | 98 | b.d. | 0.90 | 0.49 | 0.04 | b.d. | 0.23 | 0.08 | 0.08 | 0.03 | 0.06 | b.d. | | | | | | | | | | | | |
| ETD 98/13 | | 98 | 0.80 | 0.75 | 0.25 | 0.05 | b.d. | 0.13 | b.d. | 0.13 | b.d. | 0.02 | b.d. | | | | | | | | | | | | |
| ETD 98/16 | | 98 | 0.06 | 1.16 | 0.14 | 0.05 | b.d. | 0.18 | b.d. | 0.02 | b.d. | 0.02 | b.d. | | | | | | | | | | | | |
| ETD 98/18 | | 98 | 0.06 | 0.74 | 0.03 | 0.02 | b.d. | 0.59 | b.d. | 0.17 | 0.03 | 0.07 | b.d. | | | | | | | | | | | | |
| MA-136321 | | 77 | b.d. | 22.1 | 0.37 | 0.30 | 0.01 | 0.11 | b.d. | 0.12 | 0.01 | 0.02 | b.d. | | | | | | | | | | | | |
| ETD 98/22 | | 98 | b.d. | 0.89 | 0.22 | b.d. | b.d. | 0.43 | b.d. | 0.03 | b.d. | 0.05 | b.d. | | | | | | | | | | | | |
| ETD 98/23 | | 96 | 0.20 | 2.78 | 0.84 | 0.02 | b.d. | 0.42 | b.d. | 0.14 | 0.02 | 0.07 | b.d. | | | | | | | | | | | | |
| Bo 13/125 | | 94 | 2.76 | 1.60 | 0.09 | 0.75 | 0.02 | 0.31 | 0.05 | 0.09 | b.d. | 0.17 | b.d. | | | | | | | | | | | | |
| Bo 13/655 | | 98 | 0.20 | 0.91 | 0.12 | 0.07 | b.d. | 0.32 | 0.08 | 0.07 | 0.04 | 0.18 | b.d. | | | | | | | | | | | | |
| Bo 13/803 | | 89 | 10.7 | b.d. | 0.01 | b.d. | b.d. | 0.47 | b.d. | b.d. | b.d. | b.d. | b.d. | | | | | | | | | | | | |
| Bo 09/780 | | 96 | 0.73 | b.d. | 2.73 | b.d. | b.d. | 0.04 | 0.11 | b.d. | 0.29 | 0.15 | b.d. | | | | | | | | | | | | |
| Bo 09/1057 | | 97 | 0.09 | 0.93 | 0.25 | 0.03 | b.d. | 1.30 | 0.18 | 0.04 | b.d. | 0.04 | b.d. | | | | | | | | | | | | |
| Bo 09/1063 | | 99 | 0.05 | 0.30 | 0.03 | 0.11 | b.d. | 0.20 | 0.09 | 0.05 | b.d. | b.d. | b.d. | | | | | | | | | | | | |
| Bo 09/1074 | | 99 | b.d. | 0.53 | 0.10 | 0.12 | 0.01 | 0.37 | 0.21 | 0.03 | 0.01 | 0.11 | b.d. | | | | | | | | | | | | |
| MA-136336 | | 99 | 0.03 | 0.04 | 0.04 | 0.08 | 0.08 | 0.32 | 0.03 | b.d. | 0.00 | 0.03 | b.d. | | | | | | | | | | | | |
| Bo 09/1131 | | 99 | b.d. | 0.33 | 0.07 | 0.02 | 0.02 | 0.45 | 0.06 | 0.06 | 0.01 | 0.05 | b.d. | | | | | | | | | | | | |
| Bo 09/1177 | | 99 | 0.08 | 0.68 | 0.08 | 0.10 | b.d. | 0.40 | b.d. | 0.03 | 0.02 | 0.04 | b.d. | | | | | | | | | | | | |
| Bo 09/118 | | 83 | 15.2 | 0.89 | 0.12 | 0.09 | b.d. | 0.20 | 0.16 | 0.06 | b.d. | 0.01 | b.d. | | | | | | | | | | | | |
| Bo 09/121 | | 99 | 0.09 | 0.47 | 0.28 | 0.03 | b.d. | 0.24 | 0.10 | b.d. | 0.02 | 0.10 | b.d. | | | | | | | | | | | | |
| Bo 09/125 | | 98 | b.d. | 1.16 | 0.04 | 0.03 | b.d. | 0.96 | 0.07 | 0.04 | 0.01 | 0.03 | b.d. | | | | | | | | | | | | |
| Bo 09/140 | | 99 | b.d. | 0.97 | 0.05 | 0.03 | 0.01 | 0.28 | 0.05 | 0.05 | b.d. | 0.03 | b.d. | | | | | | | | | | | | |
| Bo 09/148 | | 98 | 0.19 | 1.13 | 0.05 | 0.10 | b.d. | 0.76 | b.d. | 0.07 | b.d. | b.d. | b.d. | | | | | | | | | | | | |
| Bo 09/150 | | 99 | b.d. | 0.35 | 0.02 | 0.04 | 0.04 | 0.12 | 0.04 | 0.03 | 0.01 | b.d. | b.d. | | | | | | | | | | | | |
| Bo 09/156 | | 84 | 14.7 | 0.51 | 0.30 | 0.04 | 0.01 | 0.36 | 0.04 | 0.01 | b.d. | 0.03 | b.d. | | | | | | | | | | | | |
| Bo 09/194 | | 97 | 0.07 | 1.10 | 0.13 | 0.16 | b.d. | 1.18 | 0.06 | 0.07 | 0.02 | 0.06 | b.d. | | | | | | | | | | | | |
| Bo 09/198 | | 95 | b.d. | 2.58 | 0.09 | 0.44 | 0.02 | 1.95 | 0.05 | 0.08 | b.d. | 0.03 | b.d. | | | | | | | | | | | | |
| Bo 09/211 | | 99 | b.d. | 0.33 | b.d. | 0.18 | b.d. | 0.17 | 0.04 | 0.02 | b.d. | 0.02 | b.d. | | | | | | | | | | | | |

| Mannheim Number | Object Number | Cu | | Sn | | As | | Pb | | Ni | | Co | | Fe | | Zn | | Sb | | Bi | | Ag | | Au | |
|--------------------|------------------------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|
| | | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % |
| | Bo 09/212 | 89 | 9.56 | 0.66 | 0.41 | 0.04 | 0.02 | 0.42 | 0.07 | 0.03 | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | |
| | Bo 09/274 | 96 | 0.05 | 2.58 | 0.02 | 0.04 | b.d. | 1.34 | 0.05 | 0.05 | 0.01 | 0.02 | 0.05 | 0.01 | 0.02 | 0.05 | 0.01 | 0.02 | 0.05 | 0.01 | 0.02 | 0.05 | 0.05 | 0.05 | |
| | Bo 09/278 | 83 | 15.8 | 0.78 | 0.21 | 0.12 | b.d. | 0.27 | 0.06 | 0.09 | b.d. | b.d. | 0.09 | 0.01 | 0.02 | 0.05 | 0.01 | 0.02 | 0.05 | 0.01 | 0.02 | b.d. | b.d. | b.d. | |
| | Bo 09/282 | 79 | 18.8 | 0.92 | 0.48 | 0.13 | b.d. | 0.20 | b.d. | 0.12 | b.d. | b.d. | 0.12 | 0.08 | 0.03 | 0.03 | 0.03 | 0.03 | 0.03 | 0.03 | 0.03 | b.d. | b.d. | b.d. | |
| | Bo 09/283 | 95 | 0.04 | 2.70 | 0.31 | 0.16 | b.d. | 1.58 | 0.05 | 0.08 | b.d. | b.d. | 0.08 | 0.04 | 0.04 | 0.04 | 0.04 | 0.04 | 0.04 | 0.04 | 0.04 | b.d. | b.d. | b.d. | |
| | Bo 09/284 | 99 | 0.20 | 0.43 | 0.03 | 0.04 | 0.01 | 0.39 | 0.10 | 0.05 | 0.01 | 0.02 | 0.05 | 0.01 | 0.02 | 0.05 | 0.01 | 0.02 | 0.05 | 0.01 | 0.02 | b.d. | b.d. | b.d. | |
| | Bo 09/285 | 98 | 0.14 | 0.62 | 0.05 | 0.02 | b.d. | 0.89 | 0.10 | 0.11 | 0.05 | 0.07 | 0.11 | 0.05 | 0.07 | 0.11 | 0.05 | 0.07 | 0.11 | 0.05 | 0.07 | b.d. | b.d. | b.d. | |
| | Bo 09/293 | 98 | 0.34 | 0.60 | 0.34 | 0.41 | 0.01 | 0.27 | b.d. | 0.07 | 0.02 | 0.03 | 0.07 | 0.02 | 0.03 | 0.07 | 0.02 | 0.03 | 0.07 | 0.02 | 0.03 | b.d. | b.d. | b.d. | |
| | Bo 09/298 | 92 | 0.12 | 1.11 | 0.37 | 2.52 | 0.05 | 4.04 | b.d. | 0.11 | 0.05 | 0.09 | 0.11 | 0.05 | 0.09 | 0.11 | 0.05 | 0.09 | 0.11 | 0.05 | 0.09 | b.d. | b.d. | b.d. | |
| | Bo 09/321 | 98 | 0.39 | 0.77 | 0.15 | 0.06 | b.d. | 0.11 | 0.08 | 0.12 | 0.04 | 0.08 | 0.12 | 0.04 | 0.08 | 0.12 | 0.04 | 0.08 | 0.12 | 0.04 | 0.08 | b.d. | b.d. | b.d. | |
| | Bo 09/322 | 94 | b.d. | 4.00 | 0.41 | 0.11 | 0.04 | 1.05 | b.d. | 0.04 | 0.01 | 0.02 | 0.04 | 0.01 | 0.02 | 0.04 | 0.01 | 0.02 | 0.04 | 0.01 | 0.02 | b.d. | b.d. | b.d. | |
| | Bo 09/324 | 98 | b.d. | 0.93 | 0.64 | b.d. | b.d. | 0.56 | b.d. | 0.05 | 0.08 | 0.13 | 0.05 | 0.08 | 0.13 | 0.05 | 0.08 | 0.13 | 0.05 | 0.08 | 0.13 | b.d. | b.d. | b.d. | |
| | Bo 09/325 | 96 | 1.47 | 0.90 | 0.41 | 0.10 | 0.02 | 0.47 | 0.09 | 0.14 | 0.03 | 0.02 | 0.14 | 0.03 | 0.02 | 0.14 | 0.03 | 0.02 | 0.14 | 0.03 | 0.02 | b.d. | b.d. | b.d. | |
| | Bo 09/351 | 86 | 12.5 | 0.79 | 0.23 | 0.13 | 0.01 | 0.06 | 0.04 | 0.06 | 0.03 | 0.02 | 0.06 | 0.03 | 0.02 | 0.06 | 0.03 | 0.02 | 0.06 | 0.03 | 0.02 | b.d. | b.d. | b.d. | |
| | MA-136326 Bo 09/355 | 91 | 0.05 | 0.58 | 0.02 | 7.12 | 0.23 | 1.01 | b.d. | 0.04 | 0.01 | 0.03 | 0.04 | 0.01 | 0.03 | 0.04 | 0.01 | 0.03 | 0.04 | 0.01 | 0.03 | b.d. | b.d. | b.d. | |
| | Bo 09/376 | 98 | 0.50 | 0.94 | 0.22 | 0.04 | b.d. | 0.17 | b.d. | 0.10 | 0.02 | 0.04 | 0.10 | 0.02 | 0.04 | 0.10 | 0.02 | 0.04 | 0.10 | 0.02 | 0.04 | b.d. | b.d. | b.d. | |
| | Bo 09/377 | 98 | 0.11 | 0.86 | 0.09 | 0.09 | 0.01 | 0.40 | b.d. | 0.04 | b.d. | 0.03 | 0.04 | b.d. | 0.03 | 0.04 | b.d. | 0.03 | 0.04 | b.d. | 0.03 | b.d. | b.d. | b.d. | |
| | Bo 09/378 | 96 | 0.03 | 1.71 | 0.35 | 0.03 | b.d. | 1.06 | 0.05 | 0.77 | 0.01 | 0.04 | 0.05 | 0.01 | 0.04 | 0.05 | 0.01 | 0.04 | 0.05 | 0.01 | 0.04 | b.d. | b.d. | b.d. | |
| | Bo 09/398 | 96 | 0.05 | 1.91 | 0.47 | b.d. | b.d. | 1.69 | 0.06 | 0.03 | b.d. | 0.06 | 0.03 | b.d. | 0.06 | 0.03 | b.d. | 0.06 | 0.03 | b.d. | 0.06 | b.d. | b.d. | b.d. | |
| | Bo 09/400 | 98 | b.d. | 0.81 | 0.16 | 0.34 | 0.03 | 0.51 | b.d. | 0.04 | 0.01 | 0.03 | 0.04 | 0.01 | 0.03 | 0.04 | 0.01 | 0.03 | 0.04 | 0.01 | 0.03 | b.d. | b.d. | b.d. | |
| | Bo 09/404 | 80 | 15.5 | 0.71 | 1.43 | 0.03 | b.d. | 1.98 | b.d. | b.d. | b.d. | 0.11 | 0.03 | b.d. | 0.11 | 0.03 | b.d. | 0.11 | 0.03 | b.d. | 0.11 | b.d. | b.d. | b.d. | |
| | Bo 09/405 | 95 | b.d. | 1.41 | 0.90 | 0.06 | b.d. | 2.21 | 0.14 | 0.09 | 0.02 | 0.10 | 0.09 | 0.02 | 0.10 | 0.09 | 0.02 | 0.10 | 0.09 | 0.02 | 0.10 | 0.03 | 0.03 | 0.03 | |
| | Bo 09/420 | 98 | b.d. | 0.66 | 0.75 | 0.11 | 0.01 | 0.58 | 0.09 | b.d. | b.d. | 0.09 | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | |
| | Bo 09/457 | 97 | 0.06 | 2.46 | 0.55 | 0.02 | 0.01 | 0.21 | 0.03 | 0.07 | 0.01 | 0.05 | 0.07 | 0.01 | 0.05 | 0.07 | 0.01 | 0.05 | 0.07 | 0.01 | 0.05 | b.d. | b.d. | b.d. | |
| | Bo 09/461 | 98 | b.d. | 0.82 | 0.37 | 0.10 | b.d. | 0.56 | 0.17 | b.d. | b.d. | 0.02 | b.d. | b.d. | 0.02 | b.d. | b.d. | 0.02 | b.d. | b.d. | 0.02 | b.d. | b.d. | b.d. | |
| | Bo 09/484 | 96 | 0.04 | 1.30 | 1.40 | 0.04 | b.d. | 0.71 | 0.16 | 0.09 | 0.04 | 0.07 | 0.09 | 0.04 | 0.07 | 0.09 | 0.04 | 0.07 | 0.09 | 0.04 | 0.07 | b.d. | b.d. | b.d. | |
| | Bo 09/499 | 84 | 13.9 | 1.12 | 0.51 | 0.03 | b.d. | 0.22 | 0.04 | b.d. | b.d. | 0.02 | 0.04 | b.d. | 0.02 | 0.04 | b.d. | 0.02 | 0.04 | b.d. | 0.02 | b.d. | b.d. | b.d. | |
| | Bo 09/503 | 98 | 0.16 | 0.94 | 0.25 | 0.02 | b.d. | 0.68 | b.d. | 0.02 | 0.01 | 0.03 | 0.02 | 0.01 | 0.03 | 0.02 | 0.01 | 0.03 | 0.02 | 0.01 | 0.03 | b.d. | b.d. | b.d. | |

| Mannheim Number | Object Number | | | | | | | | | | | |
|---------------------|---------------|-------------|-------------|-------------|-------------|-------------|-------------|-------------|-------------|-------------|-------------|-------------|
| | Cu wt. % | Sn wt. % | As wt. % | Pb wt. % | Ni wt. % | Co wt. % | Fe wt. % | Zn wt. % | Sb wt. % | Bi wt. % | Ag wt. % | Au wt. % |
| Bo 09/504 | 84 | 14.0 | 0.65 | 0.16 | 0.06 | 0.03 | 0.47 | 0.12 | 0.13 | b.d. | b.d. | b.d. |
| Bo 09/511 | 93 | 0.20 | 0.84 | 0.32 | 5.02 | 0.08 | 0.68 | b.d. | 0.09 | 0.07 | 0.06 | b.d. |
| Bo 09/53 | 98 | 0.26 | 0.76 | 0.09 | 0.02 | b.d. | 0.25 | 0.13 | 0.05 | 0.01 | b.d. | b.d. |
| Bo 09/583 | 96 | 0.73 | 1.81 | 0.16 | 0.04 | b.d. | 0.96 | 0.14 | 0.33 | 0.04 | 0.07 | b.d. |
| Bo 09/656 | 94 | 0.04 | 3.05 | 0.13 | 0.93 | 0.02 | 1.31 | b.d. | 0.05 | 0.01 | 0.10 | b.d. |
| Bo 09/660 | 97 | 0.22 | 1.27 | 0.71 | b.d. | b.d. | 0.53 | 0.05 | 0.11 | 0.18 | 0.10 | b.d. |
| Bo 09/686 | 98 | 1.43 | 0.35 | 0.04 | b.d. | b.d. | 0.44 | 0.11 | 0.04 | b.d. | b.d. | b.d. |
| Bo 09/687 | 90 | 5.86 | 1.75 | 0.38 | 0.04 | b.d. | 1.84 | 0.16 | 0.16 | 0.04 | 0.24 | b.d. |
| Bo 09/699 | 94 | 0.03 | 4.03 | 0.06 | 0.18 | b.d. | 1.12 | b.d. | 0.13 | 0.01 | 0.03 | 0.03 |
| Bo 09/715 | 81 | 16.1 | 1.74 | 0.51 | 0.23 | 0.03 | 0.10 | 0.12 | 0.03 | b.d. | 0.02 | b.d. |
| Bo 09/775 | 97 | 0.10 | 0.96 | 1.11 | 0.02 | b.d. | 0.39 | 0.10 | 0.16 | 0.04 | 0.07 | b.d. |
| Bo 09/797 | 93 | 0.19 | 0.69 | 0.05 | 4.86 | 0.09 | 1.11 | b.d. | 0.19 | 0.02 | 0.08 | b.d. |
| Bo 09/803 | 98 | 0.05 | 0.98 | 0.04 | 0.04 | b.d. | 0.20 | 0.13 | 0.11 | 0.06 | 0.09 | b.d. |
| Bo 09/811 | 93 | 3.52 | 1.69 | 0.25 | 0.07 | b.d. | 0.55 | 0.13 | 0.29 | 0.04 | 0.07 | b.d. |
| Bo 09/827 | 96 | b.d. | 0.60 | 2.12 | 0.82 | 0.02 | 0.64 | 0.11 | 0.03 | 0.02 | 0.01 | b.d. |
| Bo 09/835 | 98 | b.d. | 0.82 | 0.13 | 0.19 | 0.08 | 0.86 | 0.10 | b.d. | b.d. | 0.02 | b.d. |
| Bo 09/880 | 98 | 0.04 | 0.78 | 0.15 | 0.17 | b.d. | 0.44 | 0.11 | 0.03 | b.d. | 0.06 | b.d. |
| MA-136338 Bo 09/972 | 69 | 0.50 | 0.18 | 0.01 | 20.8 | 2.34 | 7.20 | b.d. | 0.01 | 0.00 | b.d. | b.d. |
| Bo 09/991 | 98 | 0.25 | 0.44 | 0.34 | b.d. | b.d. | 0.38 | 0.10 | 0.02 | b.d. | 0.03 | b.d. |
| Bo 10/492 | 96 | 0.86 | 0.82 | 0.25 | 0.05 | b.d. | 1.50 | 0.32 | 0.11 | 0.05 | 0.01 | b.d. |
| MA-132295 Bo 11/492 | 97 | 0.08 | 1.04 | 0.18 | 0.02 | b.d. | 1.91 | 0.06 | 0.02 | 0.08 | 0.04 | b.d. |
| Bo 11/535 | 98 | b.d. | 0.76 | 0.16 | 0.07 | 0.02 | 0.82 | 0.08 | b.d. | 0.01 | 0.02 | b.d. |
| Bo 12/06 | 74 | 22.8 | 1.10 | 0.80 | 0.18 | 0.04 | 0.44 | 0.43 | 0.16 | b.d. | b.d. | b.d. |
| Bo 13/304 | 92 | 6.52 | 0.99 | 0.29 | 0.21 | 0.03 | 0.23 | 0.06 | 0.04 | b.d. | 0.04 | b.d. |
| Bo 13/305 | 98 | b.d. | 0.69 | 0.09 | 0.08 | b.d. | 0.69 | 0.14 | b.d. | b.d. | 0.15 | b.d. |
| Bo 13/327 | 92 | 2.78 | 3.26 | 0.75 | 0.19 | b.d. | 1.01 | 0.07 | 0.08 | 0.02 | 0.15 | b.d. |
| Bo 13/328 | 97 | 0.37 | 0.57 | 0.67 | 0.05 | b.d. | 0.92 | 0.10 | b.d. | 0.21 | 0.32 | b.d. |
| Bo 13/340 | 94 | b.d. | 1.24 | 0.46 | b.d. | b.d. | 3.59 | 0.18 | b.d. | b.d. | 0.16 | b.d. |

| Mannheim Number | Object Number | Cu | | Sn | | As | | Pb | | Ni | | Co | | Fe | | Zn | | Sb | | Bi | | Ag | | Au | |
|--------------------|---------------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|
| | | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % |
| Bo 13/342 | | 90 | 0.03 | 2.77 | 2.66 | b.d. | b.d. | 4.78 | 0.19 | b.d. | b.d. | 0.06 | 0.06 | 0.06 | 0.06 | 0.06 | 0.06 | 0.06 | 0.06 | 0.06 | 0.06 | 0.06 | 0.06 | 0.06 | b.d. |
| Bo 13/344 | | 93 | 0.07 | 3.48 | 1.58 | 0.13 | 0.06 | 1.60 | 0.09 | 0.07 | b.d. | 0.07 | 0.07 | 0.07 | 0.07 | 0.07 | 0.07 | 0.07 | 0.07 | 0.07 | 0.07 | 0.07 | 0.07 | 0.07 | b.d. |
| Bo 13/346 | | 82 | 15.6 | 0.58 | 0.85 | 0.09 | b.d. | 0.17 | 0.16 | 0.06 | b.d. | 0.06 | 0.06 | 0.06 | 0.06 | 0.06 | 0.06 | 0.06 | 0.06 | 0.06 | 0.06 | 0.06 | 0.06 | 0.06 | b.d. |
| Bo 13/351 | | 64 | 30.5 | 0.36 | 4.30 | 0.63 | b.d. | 0.34 | 0.18 | b.d. | b.d. | 0.34 | 0.34 | 0.34 | 0.34 | 0.34 | 0.34 | 0.34 | 0.34 | 0.34 | 0.34 | 0.34 | 0.34 | 0.34 | b.d. |
| Bo 13/363 | | 97 | 0.13 | 1.46 | 0.31 | 0.08 | b.d. | 0.95 | 0.05 | 0.06 | b.d. | 0.95 | 0.95 | 0.95 | 0.95 | 0.95 | 0.95 | 0.95 | 0.95 | 0.95 | 0.95 | 0.95 | 0.95 | 0.95 | b.d. |
| Bo 13/364 | | 99 | b.d. | 0.04 | 0.02 | 0.03 | b.d. | 1.00 | 0.10 | b.d. | b.d. | 1.00 | 1.00 | 1.00 | 1.00 | 1.00 | 1.00 | 1.00 | 1.00 | 1.00 | 1.00 | 1.00 | 1.00 | 1.00 | b.d. |
| Bo 13/377 | | 98 | b.d. | 0.64 | 0.08 | 0.17 | b.d. | 0.70 | 0.06 | 0.06 | b.d. | 0.70 | 0.70 | 0.70 | 0.70 | 0.70 | 0.70 | 0.70 | 0.70 | 0.70 | 0.70 | 0.70 | 0.70 | 0.70 | b.d. |
| Bo 13/381 | | 87 | 11.3 | 0.84 | 0.46 | 0.08 | b.d. | 0.25 | 0.07 | b.d. | b.d. | 0.25 | 0.25 | 0.25 | 0.25 | 0.25 | 0.25 | 0.25 | 0.25 | 0.25 | 0.25 | 0.25 | 0.25 | 0.25 | b.d. |
| Bo 13/382 | | 98 | b.d. | 0.04 | 0.02 | b.d. | b.d. | 1.89 | 0.21 | b.d. | b.d. | 1.89 | 1.89 | 1.89 | 1.89 | 1.89 | 1.89 | 1.89 | 1.89 | 1.89 | 1.89 | 1.89 | 1.89 | 1.89 | b.d. |
| Bo 13/388 | | 98 | 0.05 | 1.46 | 0.06 | 0.20 | b.d. | 0.09 | b.d. | 0.05 | b.d. | 0.09 | 0.09 | 0.09 | 0.09 | 0.09 | 0.09 | 0.09 | 0.09 | 0.09 | 0.09 | 0.09 | 0.09 | 0.09 | b.d. |
| Bo 13/392 | | 97 | 0.07 | 1.57 | 0.10 | 0.19 | b.d. | 0.40 | 0.06 | 0.12 | b.d. | 0.40 | 0.40 | 0.40 | 0.40 | 0.40 | 0.40 | 0.40 | 0.40 | 0.40 | 0.40 | 0.40 | 0.40 | 0.40 | b.d. |
| Bo 13/393 | | 89 | 2.57 | 4.12 | 1.45 | 0.05 | b.d. | 2.34 | 0.12 | 0.29 | b.d. | 2.34 | 2.34 | 2.34 | 2.34 | 2.34 | 2.34 | 2.34 | 2.34 | 2.34 | 2.34 | 2.34 | 2.34 | 2.34 | b.d. |
| Bo 13/396 | | 97 | 0.12 | 1.75 | 0.18 | 0.24 | b.d. | 0.43 | 0.12 | 0.03 | b.d. | 0.43 | 0.43 | 0.43 | 0.43 | 0.43 | 0.43 | 0.43 | 0.43 | 0.43 | 0.43 | 0.43 | 0.43 | 0.43 | b.d. |
| Bo 13/398 | | 96 | 1.08 | 1.53 | 0.32 | 0.08 | b.d. | 0.91 | b.d. | 0.11 | b.d. | 0.91 | 0.91 | 0.91 | 0.91 | 0.91 | 0.91 | 0.91 | 0.91 | 0.91 | 0.91 | 0.91 | 0.91 | 0.91 | b.d. |
| Bo 13/403 | | 79 | 20.0 | 0.29 | 0.27 | b.d. | b.d. | 0.56 | 0.10 | b.d. | b.d. | 0.56 | 0.56 | 0.56 | 0.56 | 0.56 | 0.56 | 0.56 | 0.56 | 0.56 | 0.56 | 0.56 | 0.56 | 0.56 | b.d. |
| Bo 13/413 | | 94 | b.d. | 0.10 | 0.02 | 3.03 | b.d. | 3.07 | 0.07 | b.d. | b.d. | 3.07 | 3.07 | 3.07 | 3.07 | 3.07 | 3.07 | 3.07 | 3.07 | 3.07 | 3.07 | 3.07 | 3.07 | 3.07 | b.d. |
| Bo 13/418 | | 95 | b.d. | 0.11 | 0.27 | b.d. | b.d. | 4.66 | 0.17 | b.d. | b.d. | 4.66 | 4.66 | 4.66 | 4.66 | 4.66 | 4.66 | 4.66 | 4.66 | 4.66 | 4.66 | 4.66 | 4.66 | 4.66 | b.d. |
| Bo 13/419 | | 97 | b.d. | 1.54 | 0.56 | 0.04 | b.d. | 0.58 | b.d. | 0.04 | b.d. | 0.58 | 0.58 | 0.58 | 0.58 | 0.58 | 0.58 | 0.58 | 0.58 | 0.58 | 0.58 | 0.58 | 0.58 | 0.58 | b.d. |
| Bo 13/421 | | 97 | 0.15 | 1.59 | 0.14 | 0.21 | b.d. | 0.63 | b.d. | 0.05 | b.d. | 0.63 | 0.63 | 0.63 | 0.63 | 0.63 | 0.63 | 0.63 | 0.63 | 0.63 | 0.63 | 0.63 | 0.63 | 0.63 | b.d. |
| Bo 13/425 | | 96 | 0.12 | 3.06 | 0.15 | 0.16 | b.d. | 0.66 | 0.05 | 0.02 | b.d. | 0.66 | 0.66 | 0.66 | 0.66 | 0.66 | 0.66 | 0.66 | 0.66 | 0.66 | 0.66 | 0.66 | 0.66 | 0.66 | b.d. |
| Bo 13/426 | | 99 | b.d. | 0.11 | 0.30 | b.d. | b.d. | 0.85 | 0.07 | b.d. | b.d. | 0.85 | 0.85 | 0.85 | 0.85 | 0.85 | 0.85 | 0.85 | 0.85 | 0.85 | 0.85 | 0.85 | 0.85 | 0.85 | b.d. |
| Bo 13/449 | | 99 | 0.12 | 0.29 | 0.03 | b.d. | b.d. | 0.55 | b.d. | 0.01 | b.d. | 0.55 | 0.55 | 0.55 | 0.55 | 0.55 | 0.55 | 0.55 | 0.55 | 0.55 | 0.55 | 0.55 | 0.55 | 0.55 | b.d. |
| Bo 13/466 | | 97 | 0.13 | 1.54 | 0.13 | 0.11 | b.d. | 0.76 | 0.10 | 0.09 | b.d. | 0.76 | 0.76 | 0.76 | 0.76 | 0.76 | 0.76 | 0.76 | 0.76 | 0.76 | 0.76 | 0.76 | 0.76 | 0.76 | b.d. |
| Bo 13/471 | | 98 | b.d. | 0.82 | 0.11 | 0.14 | b.d. | 0.58 | 0.05 | b.d. | b.d. | 0.58 | 0.58 | 0.58 | 0.58 | 0.58 | 0.58 | 0.58 | 0.58 | 0.58 | 0.58 | 0.58 | 0.58 | 0.58 | b.d. |
| Bo 13/472 | | 97 | 0.08 | 0.83 | 0.48 | 0.08 | b.d. | 0.50 | 0.12 | 0.03 | b.d. | 0.50 | 0.50 | 0.50 | 0.50 | 0.50 | 0.50 | 0.50 | 0.50 | 0.50 | 0.50 | 0.50 | 0.50 | 0.50 | b.d. |
| Bo 13/473 | | 97 | b.d. | 0.57 | 0.68 | b.d. | b.d. | 1.04 | 0.25 | 0.13 | b.d. | 1.04 | 1.04 | 1.04 | 1.04 | 1.04 | 1.04 | 1.04 | 1.04 | 1.04 | 1.04 | 1.04 | 1.04 | 1.04 | b.d. |
| Bo 13/476 | | 94 | 0.23 | 2.41 | 1.07 | 0.13 | b.d. | 1.80 | 0.11 | 0.04 | b.d. | 1.80 | 1.80 | 1.80 | 1.80 | 1.80 | 1.80 | 1.80 | 1.80 | 1.80 | 1.80 | 1.80 | 1.80 | 1.80 | b.d. |
| Bo 13/479 | | 98 | b.d. | 0.02 | 0.02 | 0.10 | b.d. | 1.21 | 0.34 | b.d. | b.d. | 1.21 | 1.21 | 1.21 | 1.21 | 1.21 | 1.21 | 1.21 | 1.21 | 1.21 | 1.21 | 1.21 | 1.21 | 1.21 | b.d. |

| Mannheim Number | Object Number | | | | | | | | | | | |
|--------------------|---------------|-------------|-------------|-------------|-------------|-------------|-------------|-------------|-------------|-------------|-------------|-------------|
| | Cu wt. % | Sn wt. % | As wt. % | Pb wt. % | Ni wt. % | Co wt. % | Fe wt. % | Zn wt. % | Sb wt. % | Bi wt. % | Ag wt. % | Au wt. % |
| Bo 13/488 | 93 | b.d. | 0.02 | 0.04 | 0.10 | 1.02 | 5.77 | 0.29 | b.d. | 0.02 | 0.02 | b.d. |
| Bo 13/492 | 96 | 0.43 | 2.30 | 0.13 | 0.10 | 0.02 | 0.68 | 0.10 | 0.10 | 0.03 | 0.12 | b.d. |
| Bo 13/499 | 97 | 0.23 | 1.46 | 0.10 | 0.21 | 0.05 | 0.46 | 0.05 | 0.06 | 0.02 | 0.16 | b.d. |
| Bo 13/500 | 98 | 0.06 | 1.15 | 0.45 | 0.07 | 0.04 | 0.21 | 0.07 | 0.14 | 0.02 | 0.16 | b.d. |
| Bo 13/520 | 99 | b.d. | 0.44 | 0.10 | 0.03 | 0.02 | 0.55 | 0.08 | 0.04 | b.d. | 0.08 | b.d. |
| Bo 13/527 | 98 | 0.05 | 0.48 | 0.05 | 0.06 | b.d. | 0.62 | 0.23 | 0.40 | 0.09 | 0.12 | b.d. |
| Bo 13/529 | 94 | 0.11 | 3.80 | 0.17 | 0.28 | b.d. | 1.23 | b.d. | 0.09 | 0.06 | 0.15 | b.d. |
| Bo 13/535 | 95 | b.d. | 1.06 | 0.74 | b.d. | b.d. | 2.53 | 0.19 | b.d. | b.d. | 0.12 | b.d. |
| Bo 13/538 | 98 | b.d. | 1.10 | 0.03 | 0.08 | b.d. | 0.33 | 0.17 | 0.04 | b.d. | 0.14 | b.d. |
| Bo 13/543 | 91 | b.d. | 0.01 | 0.61 | b.d. | b.d. | 8.39 | 0.25 | b.d. | 0.03 | 0.01 | b.d. |
| Bo 13/548 | 98 | 0.04 | 0.59 | 0.12 | b.d. | b.d. | 1.40 | 0.13 | b.d. | b.d. | 0.14 | b.d. |
| Bo 13/568 | 94 | 0.08 | 5.52 | 0.03 | 0.03 | b.d. | 0.03 | 0.08 | b.d. | 0.01 | 0.23 | b.d. |
| Bo 13/573 | 97 | 0.33 | 1.53 | 0.11 | 0.06 | b.d. | 0.28 | 0.10 | 0.11 | 0.01 | 0.18 | b.d. |
| Bo 13/585 | 97 | b.d. | 1.54 | 0.71 | b.d. | b.d. | 0.76 | 0.10 | b.d. | 0.01 | 0.18 | b.d. |
| Bo 13/586 | 94 | 0.07 | 2.99 | 0.71 | 0.11 | 0.03 | 1.46 | b.d. | 0.04 | b.d. | 0.15 | b.d. |
| Bo 13/587 | 82 | 14.9 | 1.00 | 1.29 | b.d. | b.d. | 0.57 | 0.17 | b.d. | b.d. | 0.17 | b.d. |
| Bo 13/589 | 96 | b.d. | 1.65 | 1.22 | 0.06 | 0.03 | 0.36 | b.d. | 0.05 | 0.03 | 0.19 | b.d. |
| Bo 13/591 | 96 | 0.05 | 1.48 | 0.24 | 0.18 | b.d. | 1.38 | 0.23 | 0.04 | 0.05 | 0.07 | b.d. |
| Bo 13/592 | 98 | b.d. | 0.66 | 0.05 | 0.03 | b.d. | 0.60 | 0.13 | 0.07 | 0.01 | 0.13 | b.d. |
| Bo 13/595 | 98 | b.d. | 0.13 | 0.24 | 0.04 | b.d. | 1.54 | 0.30 | b.d. | b.d. | 0.05 | b.d. |
| Bo 13/606 | 99 | b.d. | 0.28 | 0.02 | b.d. | 0.05 | 0.62 | 0.15 | 0.02 | b.d. | 0.16 | b.d. |
| Bo 13/610 | 97 | 0.04 | 1.46 | 1.10 | b.d. | b.d. | 0.37 | 0.16 | 0.09 | 0.06 | 0.06 | b.d. |
| Bo 13/618 | 94 | 2.00 | 1.00 | 1.18 | b.d. | b.d. | 1.49 | 0.20 | 0.05 | b.d. | 0.10 | 0.03 |
| Bo 13/620 | 92 | 0.32 | 4.18 | 2.25 | 0.10 | 0.02 | 1.14 | 0.15 | 0.09 | 0.02 | 0.22 | b.d. |
| Bo 13/622 | 79 | 18.0 | 0.75 | 1.21 | 0.06 | b.d. | 0.21 | 0.12 | 0.04 | b.d. | 0.15 | b.d. |
| Bo 13/623 | 80 | 18.8 | 0.58 | 0.30 | b.d. | b.d. | 0.14 | 0.20 | b.d. | b.d. | 0.14 | b.d. |
| Bo 13/624 | 94 | 0.06 | 2.67 | 0.17 | 0.19 | b.d. | 2.72 | 0.05 | 0.08 | b.d. | 0.15 | b.d. |
| Bo 13/625 | 82 | 12.0 | 1.73 | 2.96 | 0.06 | b.d. | 0.94 | 0.07 | 0.05 | b.d. | 0.19 | b.d. |

| Mannheim Number | Object Number | | | | | | | | | | | |
|--------------------|---------------|-------------|-------------|-------------|-------------|-------------|-------------|-------------|-------------|-------------|-------------|-------------|
| | Cu wt. % | Sn wt. % | As wt. % | Pb wt. % | Ni wt. % | Co wt. % | Fe wt. % | Zn wt. % | Sb wt. % | Bi wt. % | Ag wt. % | Au wt. % |
| Bo 13/626 | 98 | b.d. | 1.02 | 0.06 | b.d. | b.d. | 0.62 | b.d. | 0.03 | 0.01 | 0.14 | b.d. |
| Bo 13/628 | 72 | 26.4 | 0.07 | 0.06 | 0.04 | b.d. | 0.72 | 0.17 | b.d. | b.d. | 0.06 | b.d. |
| Bo 13/632 | 96 | 0.07 | 2.37 | 0.21 | 0.13 | 0.07 | 0.50 | b.d. | 0.04 | b.d. | 0.15 | b.d. |
| Bo 13/633 | 93 | 0.09 | 5.55 | 0.04 | 0.09 | b.d. | 0.44 | 0.16 | 0.26 | 0.01 | 0.17 | b.d. |
| Bo 13/639 | 97 | 0.03 | 1.76 | 0.18 | 0.04 | b.d. | 0.39 | 0.09 | 0.10 | 0.01 | 0.19 | b.d. |
| Bo 13/642 | 98 | 0.20 | 0.73 | 0.13 | 0.04 | b.d. | 0.20 | 0.06 | 0.20 | 0.09 | 0.16 | b.d. |
| Bo 13/643 | 97 | b.d. | 0.40 | 0.15 | 0.21 | 0.40 | 1.13 | 0.05 | 0.05 | 0.03 | 0.17 | b.d. |
| Bo 13/646 | 99 | b.d. | 0.29 | 0.10 | 0.03 | b.d. | 0.33 | 0.09 | b.d. | b.d. | 0.16 | b.d. |
| Bo 13/648 | 97 | 0.06 | 0.71 | 0.38 | b.d. | b.d. | 1.30 | 0.09 | 0.04 | b.d. | 0.08 | b.d. |
| Bo 13/659 | 98 | 0.07 | 0.60 | 0.03 | 0.03 | b.d. | 0.54 | 0.18 | b.d. | b.d. | 0.14 | b.d. |
| Bo 13/664 | 97 | 0.10 | 1.81 | 0.10 | b.d. | b.d. | 0.67 | b.d. | 0.11 | 0.02 | 0.15 | b.d. |
| Bo 13/677 | 83 | 0.06 | 0.47 | 0.01 | 12.0 | 0.67 | 3.47 | b.d. | b.d. | 0.01 | 0.02 | b.d. |
| Bo 13/678 | 99 | b.d. | 0.02 | b.d. | b.d. | b.d. | 1.02 | 0.07 | 0.02 | 0.01 | b.d. | b.d. |
| Bo 13/679 | 96 | b.d. | 0.16 | 0.04 | 1.73 | 0.09 | 1.97 | 0.20 | b.d. | b.d. | 0.04 | b.d. |
| Bo 13/680 | 98 | 0.07 | 1.57 | 0.18 | 0.05 | b.d. | 0.18 | 0.10 | 0.09 | 0.04 | 0.07 | b.d. |
| Bo 13/681 | 98 | b.d. | 0.37 | 0.02 | b.d. | b.d. | 0.42 | 0.78 | b.d. | b.d. | 0.03 | b.d. |
| Bo 13/588 | 91 | 0.07 | 3.51 | 2.51 | 0.18 | 0.02 | 2.54 | 0.16 | 0.07 | b.d. | 0.18 | b.d. |
| MA-132286 Bo 11/4 | 96 | 0.03 | 2.25 | 0.16 | 0.05 | b.d. | 0.93 | 0.13 | 0.07 | 0.03 | 0.02 | b.d. |
| MA-132293 Bo 11/42 | 77 | 20.4 | 1.01 | 0.28 | 0.12 | b.d. | 0.51 | 0.24 | 0.07 | b.d. | 0.09 | b.d. |
| Bo 11/8 | 95 | b.d. | 0.71 | 0.10 | 0.08 | 0.03 | 3.29 | 0.31 | b.d. | 0.02 | 0.08 | b.d. |
| Bo 13/101 | 95 | 0.15 | 3.63 | 0.09 | 0.20 | b.d. | 0.95 | b.d. | 0.11 | 0.01 | 0.10 | b.d. |
| Bo 13/116 | 99 | b.d. | 0.29 | 0.07 | b.d. | b.d. | 0.30 | b.d. | b.d. | b.d. | 0.17 | b.d. |
| Bo 13/122 | 95 | 0.06 | 2.60 | 0.35 | b.d. | b.d. | 1.32 | b.d. | 0.16 | 0.12 | 0.28 | b.d. |
| Bo 13/135 | 97 | 0.14 | 1.70 | 0.10 | b.d. | b.d. | 0.35 | 0.11 | 0.09 | 0.03 | 0.17 | b.d. |
| Bo 13/177 | 91 | 7.78 | 0.79 | 0.19 | 0.11 | b.d. | 0.31 | 0.04 | 0.08 | b.d. | 0.01 | b.d. |
| Bo 13/18 | 93 | 0.12 | 4.79 | 0.28 | 0.46 | b.d. | 1.31 | b.d. | 0.23 | 0.02 | 0.16 | 0.05 |
| Bo 13/204 | 82 | 16.2 | 0.06 | 0.14 | 0.49 | b.d. | 0.69 | 0.05 | b.d. | b.d. | 0.18 | b.d. |
| Bo 13/238 | 98 | 0.09 | 1.31 | 0.09 | 0.03 | b.d. | 0.23 | b.d. | 0.14 | 0.03 | 0.04 | b.d. |

| Mannheim Number | Object Number | Cu wt. % | Sn wt. % | As wt. % | Pb wt. % | Ni wt. % | Co wt. % | Fe wt. % | Zn wt. % | Sb wt. % | Bi wt. % | Ag wt. % | Au wt. % |
|------------------|---------------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|
| | Bo 13/39 | 89 | 0.09 | 1.07 | 0.06 | 4.24 | 0.18 | 5.41 | 0.10 | 0.07 | 0.01 | 0.08 | b.d. |
| | Bo 13/61 | 95 | b.d. | 0.17 | 1.28 | b.d. | b.d. | 2.67 | 0.22 | 0.12 | 0.05 | 0.05 | b.d. |
| | Bo 13/64 | 98 | b.d. | 0.79 | 0.18 | 0.05 | b.d. | 0.31 | 0.27 | b.d. | b.d. | 0.15 | b.d. |
| | Bo 13/76 | 100 | 0.02 | 0.01 | 0.01 | 0.02 | 0.01 | 0.14 | 0.04 | b.d. | 0.00 | 0.13 | b.d. |
| | Bo 13/82 | 98 | b.d. | 0.77 | 0.07 | 0.36 | 0.07 | 0.60 | 0.08 | b.d. | b.d. | 0.15 | b.d. |
| | Bo 503/o | 72 | 0.07 | 0.03 | b.d. | 2.68 | 0.23 | 2.82 | 0.61 | b.d. | 0.08 | 1.90 | 19.35 |
| | Bo 503/o | 88 | 0.11 | 0.23 | b.d. | 8.06 | 0.31 | 0.67 | 0.08 | b.d. | 0.10 | 2.45 | 5.45 |
| | Bo 73/141 | 97 | 1.12 | 1.20 | 0.07 | 0.13 | 0.01 | 0.29 | b.d. | 0.07 | 0.01 | 0.03 | 0.04 |
| | Bo 73/167 | 99 | 0.08 | 0.59 | 0.04 | 0.07 | b.d. | 0.38 | b.d. | 0.03 | b.d. | 0.09 | b.d. |
| | Bo 74/7 | 97 | 0.43 | 1.57 | 0.14 | 0.14 | 0.01 | 0.41 | 0.08 | 0.07 | 0.02 | 0.06 | b.d. |
| | Bo 77/146 | 98 | 0.11 | 0.99 | 0.03 | 0.08 | b.d. | 0.23 | 0.08 | 0.13 | 0.01 | 0.18 | b.d. |
| | Bo 77/146 | 98 | 0.11 | 0.82 | 0.01 | 0.07 | 0.01 | 0.20 | 0.09 | 0.14 | 0.01 | 0.23 | b.d. |
| | Bo 77/146 | 98 | 0.11 | 0.89 | 0.02 | 0.06 | 0.01 | 0.14 | 0.07 | 0.15 | 0.01 | 0.21 | b.d. |
| | Bo 77/146 | 98 | 0.10 | 0.89 | 0.01 | 0.07 | b.d. | 0.21 | 0.06 | 0.13 | 0.01 | 0.18 | b.d. |
| | Bo 77/146 | 98 | 0.12 | 0.96 | b.d. | 0.06 | 0.01 | 0.17 | b.d. | 0.13 | b.d. | 0.19 | b.d. |
| MA-132283 | Bo 11/1205 | 98 | b.d. | 0.34 | 0.01 | 0.02 | b.d. | 0.99 | 0.13 | b.d. | b.d. | 0.07 | b.d. |
| MA-132282 | Bo 11/1215 | 98 | 0.76 | 1.14 | 0.09 | 0.03 | b.d. | 0.15 | 0.12 | 0.11 | 0.01 | 0.07 | b.d. |
| | ETD 99/54 | 85 | 0.04 | 0.24 | 0.02 | 14.1 | 0.16 | 0.27 | b.d. | b.d. | b.d. | b.d. | b.d. |
| | ETD 99/55 | 98 | b.d. | 0.97 | 0.08 | 0.13 | 0.02 | 0.58 | 0.07 | 0.06 | 0.02 | 0.04 | b.d. |
| | ETD 99/57 | 88 | b.d. | 0.97 | 0.08 | 8.62 | 0.25 | 2.26 | b.d. | 0.06 | 0.01 | 0.12 | b.d. |
| | ETD 99/58 | 99 | 0.03 | 0.89 | 0.04 | 0.02 | b.d. | 0.38 | b.d. | 0.02 | 0.01 | 0.03 | b.d. |
| | ETD 99/59 | 89 | 10.1 | 0.70 | 0.14 | 0.03 | b.d. | 0.36 | 0.06 | 0.07 | b.d. | 0.02 | b.d. |
| | ETD 99/60 | 99 | b.d. | 0.86 | 0.02 | 0.06 | 0.02 | 0.31 | b.d. | 0.03 | 0.01 | 0.03 | b.d. |
| | ETD 99/67 | 97 | 0.09 | 1.07 | 0.27 | 0.28 | 0.01 | 0.77 | 0.08 | 0.07 | 0.02 | b.d. | b.d. |
| | ETD 99/68 | 98 | 0.08 | 0.80 | 0.05 | 0.02 | b.d. | 0.65 | b.d. | 0.01 | 0.01 | 0.02 | b.d. |
| | ETD 99/69 | 98 | 0.04 | 0.72 | 0.11 | 0.11 | b.d. | 0.83 | 0.08 | 0.03 | b.d. | 0.03 | b.d. |
| | ETD 99/70 | 96 | 0.07 | 1.32 | 0.54 | 0.07 | 0.01 | 1.14 | 0.06 | 0.36 | 0.03 | 0.03 | b.d. |
| | ETD 99/71 | 98 | b.d. | 1.33 | 0.13 | 0.12 | b.d. | 0.26 | b.d. | 0.15 | 0.01 | 0.04 | b.d. |

| Mannheim Number | Object Number | | | | | | | | | | | |
|--------------------|---------------|-------------|-------------|-------------|-------------|-------------|-------------|-------------|-------------|-------------|-------------|-------------|
| | Cu wt. % | Sn wt. % | As wt. % | Pb wt. % | Ni wt. % | Co wt. % | Fe wt. % | Zn wt. % | Sb wt. % | Bi wt. % | Ag wt. % | Au wt. % |
| ETD 99/73 | 89 | 6.71 | 2.43 | 0.41 | 0.10 | 0.02 | 1.37 | 0.04 | 0.10 | 0.03 | 0.09 | b.d. |
| ETD 99/75 | 97 | b.d. | 0.66 | 0.11 | 1.40 | b.d. | 1.05 | b.d. | b.d. | b.d. | b.d. | b.d. |
| ETD 99/76 | 97 | b.d. | 1.16 | 0.13 | 0.90 | 0.03 | 0.81 | b.d. | 0.02 | b.d. | b.d. | b.d. |
| ETD 99/80 | 92 | 4.57 | 2.40 | 0.24 | 0.10 | b.d. | 0.39 | 0.05 | 0.14 | 0.01 | 0.05 | 0.03 |
| ETD 99/81 | 83 | 14.3 | 1.64 | 0.12 | b.d. | b.d. | 0.29 | 0.19 | 0.35 | b.d. | 0.08 | b.d. |
| ETD 99/82 | 96 | 0.13 | 2.61 | 0.82 | 0.06 | b.d. | 0.49 | 0.14 | 0.04 | b.d. | 0.06 | b.d. |
| ETD 99/83 | 92 | 4.51 | 1.47 | 0.44 | b.d. | b.d. | 1.33 | 0.26 | b.d. | b.d. | 0.04 | b.d. |
| ETD 99/85 | 87 | 10.9 | 0.51 | 0.22 | b.d. | b.d. | 0.55 | 0.09 | 0.57 | b.d. | 0.06 | b.d. |
| ETD 99/86 | 97 | 1.00 | 1.51 | 0.11 | 0.08 | 0.02 | 0.64 | b.d. | 0.09 | b.d. | 0.05 | b.d. |
| ETD 99/87 | 97 | 0.31 | 1.65 | 0.11 | 0.09 | 0.02 | 0.51 | b.d. | 0.10 | 0.01 | 0.03 | b.d. |
| ETD 99/88 | 82 | 14.6 | 0.46 | 2.28 | b.d. | b.d. | 0.72 | b.d. | 0.12 | 0.07 | 0.05 | b.d. |
| ETD 99/89 | 99 | 0.17 | 0.66 | 0.04 | b.d. | b.d. | 0.25 | 0.05 | 0.07 | b.d. | b.d. | b.d. |
| ETD 99/90 | 87 | 12.2 | 0.42 | 0.36 | 0.07 | 0.03 | 0.14 | 0.10 | b.d. | b.d. | b.d. | b.d. |
| ETD 99/92 | 98 | 0.14 | 0.65 | 0.14 | 0.05 | b.d. | 0.34 | 0.06 | 0.06 | 0.10 | 0.06 | b.d. |
| ETD 99/93 | 96 | 0.46 | 1.76 | 0.28 | 0.02 | b.d. | 1.00 | b.d. | 0.21 | 0.03 | 0.14 | b.d. |
| ETD 99/94 | 98 | 0.64 | 0.89 | 0.05 | 0.14 | 0.04 | 0.22 | b.d. | 0.04 | b.d. | 0.10 | b.d. |
| ETD 99/95 | 83 | 0.04 | 0.25 | 0.03 | 14.4 | 0.29 | 1.39 | b.d. | 0.05 | b.d. | 0.02 | b.d. |
| ETD 99/96 | 80 | 17.2 | 1.51 | b.d. | 0.07 | b.d. | 1.12 | b.d. | 0.14 | b.d. | b.d. | b.d. |
| Bo 07/2742 | 89 | 0.62 | 3.99 | 4.86 | 0.04 | 0.02 | 1.24 | b.d. | 0.07 | b.d. | 0.07 | b.d. |
| Bo 92/225 | 85 | 13.7 | 0.55 | 0.26 | b.d. | b.d. | 0.32 | 0.19 | 0.08 | 0.02 | 0.16 | b.d. |
| ETD 96/39 | 99 | 0.02 | 0.24 | 0.01 | b.d. | b.d. | 0.22 | b.d. | 0.02 | b.d. | 0.01 | b.d. |
| ETD 96/44 | 99 | 0.31 | 0.60 | 0.06 | b.d. | b.d. | 0.23 | b.d. | 0.02 | 0.01 | 0.04 | b.d. |
| ETD 96/47 | 98 | 0.23 | 1.27 | 0.07 | 0.10 | b.d. | 0.27 | b.d. | 0.07 | 0.01 | 0.04 | b.d. |
| ETD 96/50 | 84 | 15.0 | 0.56 | 0.01 | b.d. | b.d. | 0.28 | b.d. | 0.06 | b.d. | b.d. | b.d. |
| ETD 96/51 | 90 | 6.29 | 2.07 | 0.43 | 0.11 | 0.01 | 0.45 | b.d. | 0.17 | 0.04 | 0.06 | b.d. |
| ETD 96/53 | 87 | 0.32 | 0.17 | 0.14 | 11.7 | 0.44 | 0.24 | b.d. | b.d. | b.d. | 0.02 | b.d. |
| ETD 96/59 | 98 | 0.06 | 0.66 | 0.10 | b.d. | b.d. | 1.11 | 0.10 | 0.04 | 0.01 | 0.02 | b.d. |
| ETD 96/61 | 81 | 16.0 | 1.10 | 0.63 | 0.14 | b.d. | 0.43 | 0.11 | 0.07 | 0.02 | 0.04 | b.d. |

| Mannheim Number | Object Number | Cu | | Sn | | As | | Pb | | Ni | | Co | | Fe | | Zn | | Sb | | Bi | | Ag | | Au | |
|--------------------|---------------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|
| | | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % |
| MA-136337 | Dowel_1 | 97 | b.d. | 2.01 | 0.35 | 0.12 | 0.01 | 0.46 | b.d. | b.d. | 0.05 | 0.05 | 0.46 | b.d. | b.d. | 0.43 | 0.10 | b.d. | b.d. | 0.10 | b.d. | b.d. | b.d. | b.d. | |
| | 10-1-92 | 72 | 23.6 | 0.50 | 0.67 | b.d. | 0.05 | 2.37 | b.d. | b.d. | b.d. | 0.05 | 2.37 | b.d. | b.d. | 0.43 | 0.10 | b.d. | b.d. | 0.10 | b.d. | b.d. | b.d. | b.d. | |
| | 10-1-92 | 75 | 21.3 | 0.53 | 0.54 | b.d. | b.d. | 2.68 | b.d. | b.d. | b.d. | b.d. | 2.68 | b.d. | 0.35 | 0.10 | b.d. | b.d. | 0.10 | b.d. | b.d. | b.d. | b.d. | b.d. | |
| | 10-1-92 | 76 | 21.8 | 0.52 | 0.20 | 0.02 | 0.02 | 0.85 | 0.20 | 0.02 | 0.02 | 0.02 | 0.85 | 0.14 | 0.14 | 0.10 | 0.10 | b.d. | b.d. | 0.10 | b.d. | b.d. | b.d. | b.d. | |
| | 10-1-92 | 77 | 19.5 | 0.54 | 0.77 | b.d. | b.d. | 1.70 | 0.77 | b.d. | b.d. | b.d. | 1.70 | 0.39 | 0.39 | 0.10 | 0.10 | b.d. | b.d. | 0.10 | b.d. | b.d. | b.d. | b.d. | |
| | 10-1-92 | 78 | 21.0 | 0.44 | 0.01 | b.d. | b.d. | b.d. | 0.01 | b.d. | b.d. | b.d. | b.d. | 0.88 | 0.03 | 0.11 | 0.11 | b.d. | b.d. | 0.11 | b.d. | b.d. | b.d. | b.d. | |
| | 10-1-92 | 80 | 16.5 | 0.35 | 0.26 | b.d. | 0.04 | 2.28 | 0.26 | b.d. | 0.04 | 0.04 | 2.28 | 0.31 | 0.12 | 0.12 | b.d. | b.d. | 0.12 | b.d. | b.d. | b.d. | b.d. | b.d. | |
| | 10-1-92 | 81 | 16.0 | 0.28 | 0.04 | b.d. | b.d. | 2.42 | 0.04 | b.d. | b.d. | b.d. | 2.42 | 0.18 | 0.11 | 0.11 | b.d. | b.d. | 0.11 | b.d. | b.d. | b.d. | b.d. | b.d. | |
| | 10-1-92 | 82 | 15.1 | 0.33 | 0.37 | b.d. | 0.04 | 1.40 | 0.37 | b.d. | 0.04 | 0.04 | 1.40 | 0.32 | 0.10 | 0.10 | b.d. | b.d. | 0.10 | b.d. | b.d. | b.d. | b.d. | b.d. | |
| | 10-1-92 | 82 | 16.2 | 0.32 | 0.02 | b.d. | b.d. | 0.68 | 0.02 | b.d. | b.d. | b.d. | 0.68 | 0.27 | 0.12 | 0.12 | b.d. | b.d. | 0.12 | b.d. | b.d. | b.d. | b.d. | b.d. | |
| | ETD 00/10 | 90 | 7.93 | 1.24 | 0.21 | 0.14 | b.d. | 0.20 | 0.21 | 0.14 | b.d. | b.d. | 0.20 | 0.06 | 0.04 | 0.04 | 0.06 | 0.09 | 0.09 | 0.04 | 0.04 | 0.04 | 0.04 | 0.04 | |
| | ETD 00/11 | 93 | b.d. | 3.04 | 1.85 | 0.07 | 0.10 | 1.55 | 1.85 | 0.07 | 0.10 | 0.10 | 1.55 | b.d. | 0.08 | 0.04 | 0.08 | 0.08 | 0.08 | 0.04 | 0.04 | 0.04 | 0.04 | 0.04 | |
| | ETD 00/16 | 91 | 8.16 | 0.51 | 0.02 | 0.04 | 0.09 | 0.26 | 0.02 | 0.04 | 0.09 | 0.09 | 0.26 | b.d. | 0.02 | 0.04 | 0.02 | 0.02 | 0.02 | 0.04 | 0.04 | 0.04 | 0.04 | 0.04 | |
| | ETD 00/17 | 74 | 24.0 | 0.23 | 0.01 | 0.05 | b.d. | 1.23 | 0.01 | 0.05 | b.d. | b.d. | 1.23 | 0.10 | 0.12 | 0.12 | b.d. | b.d. | 0.12 | b.d. | b.d. | b.d. | b.d. | b.d. | |
| | ETD 00/6 | 92 | 6.19 | 0.75 | 0.18 | 0.05 | 0.03 | 0.41 | 0.18 | 0.05 | 0.03 | 0.03 | 0.41 | 0.05 | 0.05 | 0.05 | 0.05 | 0.05 | 0.05 | 0.05 | 0.05 | 0.05 | 0.05 | 0.05 | |
| | ETD 00/7 | 98 | 0.35 | 1.04 | 0.05 | b.d. | b.d. | 0.69 | 0.05 | b.d. | b.d. | b.d. | 0.69 | b.d. | 0.01 | 0.01 | 0.01 | 0.07 | 0.07 | 0.01 | 0.01 | 0.01 | 0.01 | 0.01 | |
| | ETD 00/8 | 86 | b.d. | 1.10 | 0.01 | 7.05 | 0.33 | 5.36 | 0.01 | 7.05 | 0.33 | 0.33 | 5.36 | 0.08 | 0.01 | 0.01 | 0.08 | 0.08 | 0.01 | 0.01 | 0.01 | 0.01 | 0.01 | 0.01 | |
| | ETD 00/9 | 93 | 5.16 | 1.01 | 0.19 | 0.06 | b.d. | 0.33 | 0.19 | 0.06 | b.d. | b.d. | 0.33 | 0.07 | 0.04 | 0.04 | 0.07 | 0.07 | 0.04 | 0.04 | 0.04 | 0.04 | 0.04 | 0.04 | |
| | ETD 98/15 | 79 | b.d. | 0.44 | 0.02 | 16.5 | 0.68 | 3.44 | 0.02 | 16.5 | 0.68 | 0.68 | 3.44 | 0.08 | 0.01 | 0.01 | 0.08 | 0.08 | 0.01 | 0.01 | 0.01 | 0.01 | 0.01 | 0.01 | |
| | Bo 89/41 | 73 | 3.18 | 0.85 | 21.97 | 0.02 | b.d. | 0.08 | 21.97 | 0.02 | b.d. | b.d. | 0.08 | 0.30 | 0.05 | 0.05 | 0.30 | 0.30 | 0.05 | 0.05 | 0.05 | 0.05 | 0.05 | 0.05 | |
| | Bo 78/113 | 89 | 9.64 | 0.61 | 0.05 | 0.04 | b.d. | 0.17 | 0.05 | 0.04 | b.d. | b.d. | 0.17 | 0.06 | 0.13 | 0.13 | 0.06 | 0.04 | 0.04 | 0.13 | 0.13 | 0.13 | 0.13 | 0.13 | |
| | Bo 81/8 | 92 | 5.77 | 0.30 | 0.13 | 0.23 | b.d. | 1.60 | 0.13 | 0.23 | b.d. | b.d. | 1.60 | 0.10 | 0.07 | 0.07 | 0.10 | 0.07 | 0.07 | 0.07 | 0.07 | 0.07 | 0.07 | 0.07 | |
| MA-132563 | Bo 82/102 | 95 | 4.41 | 0.04 | 0.01 | b.d. | b.d. | 0.46 | 0.01 | b.d. | b.d. | b.d. | 0.46 | b.d. | 0.01 | 0.01 | b.d. | b.d. | 0.01 | 0.01 | 0.01 | 0.01 | 0.01 | 0.01 | |
| MA-132562 | Bo 82/103 | 92 | 4.29 | 0.22 | 0.08 | b.d. | b.d. | 2.77 | 0.08 | b.d. | b.d. | b.d. | 2.77 | 0.09 | 0.06 | 0.06 | 0.09 | 0.06 | 0.06 | 0.06 | 0.06 | 0.06 | 0.06 | 0.06 | |
| MA-132301 | Bo 82/109a | 100 | b.d. | 0.21 | b.d. | 0.03 | 0.01 | 0.18 | b.d. | 0.03 | 0.01 | 0.01 | 0.18 | b.d. | 0.02 | 0.02 | b.d. | b.d. | 0.02 | 0.02 | 0.02 | 0.02 | 0.02 | 0.02 | |
| MA-132176 | Bo 82/112 | 90 | 8.46 | 0.51 | 0.06 | 0.02 | b.d. | 1.04 | 0.06 | 0.02 | b.d. | b.d. | 1.04 | 0.16 | 0.12 | 0.12 | 0.16 | 0.12 | 0.12 | 0.12 | 0.12 | 0.12 | 0.12 | 0.12 | |
| MA-132175 | Bo 82/140 | 87 | 11.6 | 0.07 | b.d. | b.d. | b.d. | 0.72 | b.d. | b.d. | b.d. | b.d. | 0.72 | 0.22 | 0.22 | 0.22 | 0.22 | 0.22 | 0.22 | 0.22 | 0.22 | 0.22 | 0.22 | 0.22 | |
| | Bo 82/148 | 98 | 0.71 | 0.32 | 0.01 | 0.02 | 0.01 | 0.98 | 0.01 | 0.02 | 0.01 | 0.01 | 0.98 | 0.10 | 0.01 | 0.01 | 0.10 | 0.01 | 0.01 | 0.01 | 0.01 | 0.01 | 0.01 | 0.01 | |

| Mannheim Number | Object Number | Cu wt. % | Sn wt. % | As wt. % | Pb wt. % | Ni wt. % | Co wt. % | Fe wt. % | Zn wt. % | Sb wt. % | Bi wt. % | Ag wt. % | Au wt. % |
|------------------|--------------------------------------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|
| | Bo 83/220 | 89 | 9.63 | 0.46 | 0.17 | 0.05 | b.d. | 0.08 | 0.13 | 0.09 | b.d. | 0.01 | b.d. |
| | Bo 83/310 | 90 | 8.38 | 0.74 | 0.15 | 0.15 | 0.01 | 0.06 | 0.13 | 0.05 | b.d. | 0.01 | b.d. |
| | Bo 83/442 | 97 | 0.08 | 1.14 | 1.04 | 0.18 | 0.01 | 0.26 | 0.06 | 0.10 | 0.05 | 0.05 | b.d. |
| | Bo 83/444 | 98 | 0.03 | 1.33 | 0.03 | b.d. | b.d. | 0.48 | 0.08 | 0.08 | 0.01 | 0.06 | b.d. |
| | Bo 83/450 | 99 | 0.03 | 0.71 | 0.09 | 0.05 | 0.01 | 0.24 | 0.06 | 0.07 | 0.02 | 0.04 | b.d. |
| MA-132578 | Bo 83/580 | 82 | 16.4 | 0.78 | 0.13 | 0.03 | b.d. | 0.29 | b.d. | 0.05 | b.d. | 0.02 | b.d. |
| MA-132582 | Bo 83/712 | 84 | 14.7 | 0.53 | 0.20 | b.d. | b.d. | 0.51 | 0.06 | 0.04 | b.d. | b.d. | b.d. |
| MA-136323 | Bo 83/819 | 98 | 0.14 | 0.01 | b.d. | 0.06 | 0.03 | 1.64 | 0.13 | b.d. | b.d. | b.d. | b.d. |
| | Bo 83/889 | 97 | 2.30 | 0.53 | 0.01 | 0.02 | b.d. | 0.14 | b.d. | b.d. | b.d. | b.d. | b.d. |
| | Bo 84/22 | 94 | 5.23 | 0.17 | 0.07 | b.d. | b.d. | 0.24 | 0.10 | 0.03 | b.d. | 0.10 | b.d. |
| | Bo 84/341 | 93 | 5.23 | 0.75 | 0.45 | 0.28 | b.d. | 0.31 | 0.14 | 0.05 | b.d. | 0.07 | b.d. |
| | Bo 84/531 | 82 | 16.5 | 0.89 | 0.09 | 0.32 | 0.01 | 0.23 | 0.13 | 0.03 | b.d. | b.d. | b.d. |
| | Bo 84/563 | 83 | 14.9 | 0.90 | 0.65 | 0.07 | b.d. | 0.41 | 0.20 | 0.05 | b.d. | 0.11 | b.d. |
| | Bo 85/117 | 91 | 0.15 | 0.56 | 0.01 | 6.34 | 0.09 | 2.08 | b.d. | 0.08 | 0.01 | 0.04 | b.d. |
| | Bo 85/144 | 83 | 16.2 | 0.17 | 0.01 | b.d. | b.d. | 0.19 | 0.09 | b.d. | b.d. | 0.09 | b.d. |
| | Bo 85/153 | 89 | 10.3 | 0.30 | 0.12 | b.d. | b.d. | 0.20 | b.d. | 0.09 | b.d. | 0.09 | b.d. |
| | Bo 85/515 | 99 | 0.16 | 0.37 | 0.17 | b.d. | b.d. | 0.26 | 0.05 | 0.16 | 0.03 | 0.06 | b.d. |
| MA-132587 | Bo 86/101 | 94 | 1.24 | 2.90 | 0.36 | 0.04 | b.d. | 1.08 | 0.06 | 0.06 | 0.10 | 0.06 | b.d. |
| | Bo 86/168 | 87 | 12.1 | 0.29 | 0.04 | b.d. | 0.03 | 0.49 | 0.19 | 0.05 | b.d. | b.d. | b.d. |
| | Bo 86/282 | 91 | 7.02 | 1.02 | 0.38 | 0.09 | b.d. | 0.12 | 0.08 | 0.11 | b.d. | 0.02 | b.d. |
| MA-132586 | Bo 86/321 | 98 | b.d. | 0.65 | 0.66 | 0.03 | b.d. | 0.70 | b.d. | 0.13 | 0.11 | b.d. | b.d. |
| | Bo 86/411 | 86 | 12.0 | 0.73 | 0.25 | 0.09 | b.d. | 0.39 | 0.14 | 0.05 | b.d. | 0.01 | b.d. |
| | Bo 86/427 | 82 | 16.6 | 0.28 | 0.03 | b.d. | b.d. | 0.77 | 0.23 | b.d. | b.d. | b.d. | b.d. |
| | Bo 86/431 | 97 | 0.45 | 1.40 | 0.18 | 0.08 | b.d. | 0.29 | 0.09 | 0.09 | 0.04 | 0.07 | b.d. |
| | Bo 91/2414 | 84 | 15.2 | 0.55 | 0.12 | b.d. | 0.04 | 0.22 | 0.12 | 0.02 | b.d. | 0.13 | b.d. |
| | Herbordt Kat ify-39 (12); Bo 82-214b | 84 | 11.9 | 0.86 | 0.32 | 0.24 | 0.06 | 1.70 | 0.39 | 0.06 | b.d. | 0.02 | b.d. |
| | Herbordt Kat ify-39 (14); Bo 82-314a | 88 | 10.9 | 0.16 | 0.08 | 0.07 | 0.06 | 0.76 | 0.27 | b.d. | b.d. | b.d. | b.d. |
| | Herbordt Kat ify-39 (15); Bo 82-314a | 86 | 11.7 | 0.97 | 0.98 | 0.16 | 0.03 | 0.36 | 0.19 | 0.06 | b.d. | b.d. | b.d. |

| Mannheim Number | Object Number | Cu wt. % | Sn wt. % | As wt. % | Pb wt. % | Ni wt. % | Co wt. % | Fe wt. % | Zn wt. % | Sb wt. % | Bi wt. % | Ag wt. % | Au wt. % |
|-----------------|--------------------------------------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|
| | Herbordt Kat ify-39 (16); Bo 82-214a | 85 | 11.1 | 1.35 | 0.43 | 0.66 | 0.02 | 1.39 | 0.30 | 0.13 | b.d. | 0.01 | b.d. |
| | Herbordt Kat ify-39 (2); Bo 82-214b | 85 | 13.1 | 0.73 | 0.27 | 0.14 | b.d. | 0.32 | 0.26 | 0.06 | b.d. | 0.02 | b.d. |
| | Herbordt Kat ify-39 (20); Bo 82-314a | 88 | 0.12 | 0.18 | b.d. | 10.7 | 1.15 | 0.33 | b.d. | 0.02 | b.d. | 0.02 | b.d. |
| | Herbordt Kat ify-39 (22); Bo 82-314a | 86 | 12.6 | 0.08 | 0.04 | b.d. | b.d. | 1.22 | 0.08 | 0.10 | b.d. | b.d. | b.d. |
| | Herbordt Kat ify-39 (23); Bo 82-214b | 86 | 12.3 | 0.39 | 0.21 | 0.06 | 0.04 | 0.81 | 0.29 | b.d. | b.d. | b.d. | b.d. |
| | Herbordt Kat ify-39 (24); Bo 82-314a | 88 | 9.89 | 0.16 | 0.01 | b.d. | b.d. | 1.51 | 0.25 | b.d. | b.d. | 0.01 | b.d. |
| | Herbordt Kat ify-39 (25); Bo 82-314a | 86 | 12.3 | 0.30 | 0.15 | 0.07 | b.d. | 0.55 | 0.11 | b.d. | b.d. | 0.02 | b.d. |
| | Herbordt Kat ify-39 (26); Bo 82-314a | 85 | 13.2 | 0.13 | 0.65 | 0.11 | 0.08 | 1.03 | 0.31 | b.d. | b.d. | b.d. | b.d. |
| | Herbordt Kat ify-39 (27); Bo 82-314a | 83 | 13.8 | 0.49 | 0.17 | 0.04 | b.d. | 1.86 | 0.26 | 0.05 | b.d. | 0.01 | b.d. |
| | Herbordt Kat ify-39 (28); Bo 82-314a | 86 | 12.0 | 1.33 | 0.22 | 0.09 | b.d. | 0.53 | 0.08 | 0.06 | b.d. | b.d. | b.d. |
| | Herbordt Kat ify-39 (29); Bo 82-314a | 83 | 14.0 | 0.11 | 0.13 | b.d. | b.d. | 2.47 | 0.19 | 0.14 | b.d. | b.d. | b.d. |
| | Herbordt Kat ify-39 (3); Bo 82-314a | 81 | 15.9 | 0.71 | 0.12 | 0.14 | b.d. | 1.29 | 0.37 | 0.06 | b.d. | 0.02 | b.d. |
| | Herbordt Kat ify-39 (32); Bo 82-314a | 83 | 15.6 | 0.16 | 0.12 | b.d. | b.d. | 1.29 | 0.13 | b.d. | b.d. | b.d. | b.d. |
| | Herbordt Kat ify-39 (35); Bo 82-214b | 85 | 14.3 | 0.65 | 0.04 | 0.03 | b.d. | 0.28 | 0.06 | 0.02 | b.d. | b.d. | b.d. |
| | Herbordt Kat ify-39 (36); Bo 82-314a | 90 | 8.33 | 0.54 | 0.28 | b.d. | b.d. | 0.54 | 0.32 | 0.15 | b.d. | b.d. | b.d. |
| | Herbordt Kat ify-39 (39); Bo 82-314a | 76 | 20.6 | 0.65 | 0.71 | b.d. | b.d. | 1.17 | 0.34 | 0.27 | b.d. | b.d. | b.d. |
| | Herbordt Kat ify-39 (4); Bo 82-314a | 82 | 15.0 | 0.28 | 0.03 | 0.38 | 0.37 | 1.74 | 0.34 | b.d. | b.d. | b.d. | b.d. |
| | Herbordt Kat ify-39 (41); Bo 82-314a | 85 | 13.5 | 0.43 | 0.10 | b.d. | b.d. | 0.30 | 0.13 | 0.04 | b.d. | 0.01 | b.d. |
| | Herbordt Kat ify-39 (42); Bo 82-314a | 80 | 18.3 | 0.48 | 0.12 | 0.04 | b.d. | 0.62 | 0.18 | 0.20 | b.d. | b.d. | b.d. |
| | Herbordt Kat ify-39 (43); Bo 82-314a | 86 | 12.4 | 0.48 | 0.14 | b.d. | b.d. | 0.61 | 0.23 | b.d. | b.d. | 0.01 | b.d. |
| | Herbordt Kat ify-39 (44); Bo 82-314a | 85 | 14.3 | 0.23 | b.d. | b.d. | b.d. | 0.17 | 0.10 | b.d. | b.d. | b.d. | b.d. |
| | Herbordt Kat ify-39 (45); Bo 82-314a | 89 | 8.83 | 0.11 | 0.03 | b.d. | b.d. | 1.72 | 0.18 | 0.04 | b.d. | b.d. | b.d. |
| | Herbordt Kat ify-39 (51); Bo 82-314a | 85 | 12.7 | 0.85 | 0.61 | 0.13 | 0.02 | 0.81 | 0.22 | 0.05 | b.d. | b.d. | b.d. |
| | Herbordt Kat ify-39 (6); Bo 82-314a | 81 | 16.1 | 0.31 | 0.04 | b.d. | b.d. | 2.17 | 0.30 | b.d. | b.d. | b.d. | b.d. |
| | Herbordt Kat ify-39 (7); Bo 82-314a | 88 | 10.0 | 1.13 | 0.34 | 0.13 | b.d. | 0.34 | 0.14 | 0.06 | b.d. | 0.01 | b.d. |
| | Herbordt Kat ify-39 (8); Bo 82-314a | 91 | 6.32 | 0.02 | 0.01 | b.d. | b.d. | 2.04 | 0.23 | b.d. | b.d. | 0.02 | b.d. |
| | scale 9 | 79 | 18.7 | 0.15 | 0.05 | b.d. | b.d. | 1.41 | 0.15 | 0.13 | b.d. | b.d. | b.d. |
| | Bo 82/19 | 83 | 14.6 | 0.56 | 0.12 | b.d. | b.d. | 0.98 | 0.53 | b.d. | b.d. | b.d. | b.d. |

| Mannheim Number | Object Number | Cu | | Sn | | As | | Pb | | Ni | | Co | | Fe | | Zn | | Sb | | Bi | | Ag | | Au | |
|--------------------|---------------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|
| | | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % |
| Bo 06/1115 | | 97 | 1.39 | 0.20 | 0.03 | b.d. | b.d. | 1.64 | 0.06 | b.d. | b.d. | 1.64 | 0.06 | b.d. | b.d. | 0.06 | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | |
| Bo 06/1133 | | 83 | 15.8 | 0.18 | 0.22 | 0.08 | 0.08 | 0.72 | 0.12 | 0.04 | 0.04 | 0.72 | 0.12 | 0.04 | 0.04 | 0.06 | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | |
| Bo 07/2668 | | 97 | 0.04 | 0.87 | 0.09 | b.d. | b.d. | 1.49 | 0.05 | 0.03 | 0.11 | 1.49 | 0.05 | 0.03 | 0.11 | 0.10 | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | |
| Bo 07/2685 | | 88 | 10.1 | 0.75 | 0.30 | 0.06 | 0.06 | 0.16 | 0.08 | 0.08 | 0.08 | 0.16 | 0.08 | 0.08 | 0.03 | 0.03 | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | |
| Bo 07/2690 | | 77 | 21.6 | 0.27 | 0.37 | 0.11 | 0.11 | 0.50 | 0.12 | 0.05 | 0.05 | 0.50 | 0.12 | 0.05 | 0.06 | 0.06 | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | |
| Bo 07/2691 | | 96 | b.d. | 3.10 | b.d. | b.d. | b.d. | 0.46 | 0.08 | 0.11 | 0.18 | 0.46 | 0.08 | 0.11 | 0.18 | 0.01 | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | |
| Bo 07/2748 | | 87 | 9.99 | 1.05 | 0.73 | 0.06 | 0.06 | 0.43 | b.d. | 0.24 | 0.19 | 0.43 | b.d. | 0.24 | 0.19 | 0.08 | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | |
| Bo 07/2819 | | 97 | 0.10 | 0.75 | 0.12 | 0.10 | 0.10 | 1.69 | 0.04 | 0.17 | 0.09 | 1.69 | 0.04 | 0.17 | 0.05 | 0.05 | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | |
| Bo 08/1510 | | 86 | b.d. | 0.46 | 0.02 | 11.2 | 0.47 | 2.18 | b.d. | 0.02 | b.d. | 2.18 | b.d. | 0.02 | 0.03 | 0.03 | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | |
| Bo 08/1544 | | 97 | 0.06 | 0.44 | 1.35 | 0.02 | 0.02 | 0.63 | 0.21 | b.d. | b.d. | 0.63 | 0.21 | b.d. | 0.16 | 0.16 | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | |
| Bo 08/358 | | 99 | 0.05 | 0.39 | 0.01 | b.d. | b.d. | 0.15 | b.d. | 0.05 | b.d. | 0.15 | b.d. | 0.05 | 0.24 | 0.24 | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | |
| Bo 08/359 | | 86 | 12.2 | 1.10 | 0.14 | 0.06 | 0.06 | 0.33 | 0.17 | 0.27 | b.d. | 0.33 | 0.17 | 0.27 | 0.01 | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | |
| Bo 08/393 | | 95 | 3.12 | 0.80 | 0.14 | 0.03 | 0.03 | 0.42 | 0.16 | 0.07 | b.d. | 0.42 | 0.16 | 0.07 | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | |
| Bo 08/403 | | 89 | 9.32 | 0.58 | 0.08 | b.d. | b.d. | 0.48 | 0.14 | 0.03 | b.d. | 0.48 | 0.14 | 0.03 | 0.16 | 0.16 | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | |
| Bo 08/415 | | 98 | 0.09 | 1.20 | 0.50 | 0.03 | 0.03 | 0.22 | b.d. | 0.13 | 0.04 | 0.22 | b.d. | 0.13 | 0.11 | 0.11 | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | |
| Bo 08/826 | | 98 | 0.09 | 0.82 | 0.21 | 0.06 | 0.06 | 0.12 | 0.08 | 0.07 | 0.03 | 0.12 | 0.08 | 0.07 | 0.05 | 0.05 | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | |
| Bo 08/892 | | 97 | b.d. | 0.94 | 1.06 | 0.03 | 0.03 | 0.29 | 0.09 | 0.08 | 0.03 | 0.29 | 0.09 | 0.08 | 0.04 | 0.04 | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | |
| Bo 08/914 | | 95 | b.d. | 4.06 | 0.01 | 0.02 | 0.02 | 0.84 | 0.20 | b.d. | b.d. | 0.84 | 0.20 | b.d. | 0.04 | 0.04 | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | |
| Bo 08/931 | | 99 | 0.07 | 0.62 | 0.10 | 0.03 | 0.03 | 0.31 | 0.04 | 0.08 | 0.02 | 0.31 | 0.04 | 0.08 | 0.19 | 0.19 | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | |
| Bo 08/934 | | 98 | 0.90 | 0.58 | 0.10 | 0.04 | 0.04 | 0.38 | 0.08 | 0.07 | 0.02 | 0.38 | 0.08 | 0.07 | 0.05 | 0.05 | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | |
| Bo 08/952 | | 94 | 0.29 | 4.05 | 0.30 | 0.08 | 0.08 | 0.58 | 0.07 | 0.22 | 0.01 | 0.58 | 0.07 | 0.22 | 0.04 | 0.04 | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | |
| Bo 09/54 | | 97 | 0.10 | 1.69 | 0.81 | 0.06 | 0.06 | 0.29 | 0.12 | 0.07 | 0.01 | 0.29 | 0.12 | 0.07 | 0.06 | 0.06 | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | |
| Bo 09/64 | | 91 | 7.44 | 0.75 | 0.16 | 0.12 | 0.12 | 0.40 | 0.20 | 0.17 | b.d. | 0.40 | 0.20 | 0.17 | 0.02 | 0.02 | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | |
| Bo 09/73 | | 67 | 31.3 | 1.26 | 0.20 | 0.10 | 0.10 | 0.21 | 0.08 | 0.11 | b.d. | 0.21 | 0.08 | 0.11 | 0.05 | 0.05 | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | |
| Bo 02/39 | | 98 | 1.21 | 0.52 | 0.18 | b.d. | b.d. | 0.13 | 0.09 | 0.14 | 0.05 | 0.13 | 0.09 | 0.14 | 0.06 | 0.06 | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | |
| Bo 02/41 | | 98 | 0.10 | 0.57 | 0.73 | b.d. | b.d. | 0.73 | 0.08 | 0.09 | 0.07 | 0.73 | 0.08 | 0.09 | 0.06 | 0.06 | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | |
| Bo 02/45 | | 89 | 8.49 | 1.22 | 0.13 | 0.13 | 0.13 | 0.50 | b.d. | 0.05 | 0.01 | 0.50 | b.d. | 0.05 | 0.03 | 0.03 | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | |
| Bo 02/49 | | 99 | 0.06 | 0.23 | 0.38 | b.d. | b.d. | 0.20 | 0.09 | 0.10 | 0.06 | 0.20 | 0.09 | 0.10 | 0.09 | 0.09 | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | |

| Mannheim Number | Object Number | Cu | | Sn | | As | | Pb | | Ni | | Co | | Fe | | Zn | | Sb | | Bi | | Ag | | Au | |
|--------------------|-----------------------------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|
| | | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % |
| | Bo 02/50 | 98 | 0.03 | 0.31 | 0.07 | 0.32 | b.d. | b.d. | 1.14 | 0.08 | 0.03 | 0.01 | 0.01 | b.d. | | | | | | | | | | | |
| | Bo 02/55 | 97 | 0.60 | 0.98 | 0.65 | 0.04 | b.d. | b.d. | 0.72 | 0.07 | 0.13 | 0.13 | 0.08 | b.d. | | | | | | | | | | | |
| | Bo 03/21 | 98 | 0.12 | 0.59 | 0.02 | b.d. | b.d. | b.d. | 0.82 | 0.09 | 0.07 | 0.05 | 0.11 | b.d. | | | | | | | | | | | |
| | Bo 03/41 | 79 | 20.6 | 0.13 | 0.02 | 0.06 | b.d. | b.d. | 0.44 | 0.14 | b.d. | b.d. | 0.03 | b.d. | | | | | | | | | | | |
| | Bo 04/30 | 58 | 38.3 | 1.42 | 0.19 | 0.52 | b.d. | b.d. | 1.23 | 0.19 | 0.06 | b.d. | 0.04 | b.d. | | | | | | | | | | | |
| | Bo 04/32 | 97 | 0.99 | 0.49 | 0.29 | b.d. | b.d. | b.d. | 1.15 | 0.10 | 0.06 | 0.04 | 0.05 | b.d. | | | | | | | | | | | |
| | Bo 04/34 | 96 | b.d. | 2.53 | 0.75 | b.d. | b.d. | b.d. | 1.06 | b.d. | 0.09 | 0.01 | b.d. | b.d. | | | | | | | | | | | |
| | Bo 05/13 | 87 | 0.16 | 1.12 | 0.17 | 0.04 | b.d. | b.d. | 0.94 | 0.11 | 0.04 | 0.02 | 10.86 | 0.15 | | | | | | | | | | | |
| | Bo 05/13 | 96 | b.d. | 0.12 | 0.02 | 1.90 | 0.25 | b.d. | 0.77 | 0.18 | b.d. | b.d. | 0.37 | 0.12 | | | | | | | | | | | |
| | Bo 05/13 | 97 | b.d. | 0.04 | b.d. | 2.37 | 0.29 | b.d. | 0.38 | 0.05 | b.d. | b.d. | b.d. | b.d. | | | | | | | | | | | |
| | Bo 05/13 | 99 | b.d. | 0.20 | 0.08 | 0.04 | b.d. | b.d. | 0.78 | 0.19 | b.d. | b.d. | 0.02 | b.d. | | | | | | | | | | | |
| | Bo 05/13 | 99 | b.d. | 0.11 | 0.09 | 0.03 | b.d. | b.d. | 0.88 | 0.13 | b.d. | b.d. | 0.02 | b.d. | | | | | | | | | | | |
| | Bo 05/21 | 99 | 0.04 | 0.43 | 0.12 | 0.03 | b.d. | b.d. | 0.35 | 0.17 | 0.02 | b.d. | 0.03 | b.d. | | | | | | | | | | | |
| | Bo 05/23 | 98 | 0.06 | 0.84 | 0.06 | b.d. | b.d. | b.d. | 1.03 | 0.13 | b.d. | 0.01 | 0.01 | b.d. | | | | | | | | | | | |
| | Bo 05/25 | 97 | 0.02 | 1.57 | 0.33 | b.d. | b.d. | b.d. | 0.59 | 0.13 | 0.06 | 0.02 | 0.04 | b.d. | | | | | | | | | | | |
| | Bo 05/29 | 70 | 29.0 | 0.17 | 0.04 | 0.04 | b.d. | b.d. | 0.17 | 0.19 | b.d. | b.d. | 0.02 | b.d. | | | | | | | | | | | |
| | Bo 05/30 | 86 | 2.55 | 3.36 | 0.47 | 0.32 | b.d. | b.d. | 6.88 | 0.21 | 0.31 | 0.03 | 0.07 | b.d. | | | | | | | | | | | |
| | Bo 05/31 | 78 | 21.0 | 0.75 | 0.04 | b.d. | b.d. | b.d. | 0.18 | 0.16 | b.d. | b.d. | b.d. | b.d. | | | | | | | | | | | |
| | Bo 05/33 | 88 | 8.23 | 1.86 | 0.50 | 0.07 | b.d. | b.d. | 0.76 | 0.18 | 0.22 | b.d. | 0.03 | b.d. | | | | | | | | | | | |
| | Bo 05/34 | 94 | 0.44 | 1.65 | 1.07 | 0.04 | b.d. | b.d. | 2.24 | 0.19 | 0.13 | 0.17 | 0.11 | b.d. | | | | | | | | | | | |
| | Bo 05/36 | 75 | 15.6 | 4.50 | 0.42 | 0.25 | 0.08 | b.d. | 3.54 | 0.16 | 0.09 | 0.01 | 0.04 | b.d. | | | | | | | | | | | |
| | Bo 05/38 | 95 | 0.53 | 1.12 | 0.93 | b.d. | b.d. | b.d. | 1.79 | 0.17 | 0.08 | 0.22 | 0.07 | b.d. | | | | | | | | | | | |
| | Bo 05/51 | 86 | 9.34 | 2.03 | 1.39 | 0.08 | b.d. | b.d. | 0.60 | 0.16 | 0.08 | 0.03 | 0.04 | b.d. | | | | | | | | | | | |
| | Bo 06/1039 | 79 | 20.4 | 0.16 | 0.05 | 0.10 | b.d. | b.d. | 0.10 | 0.15 | b.d. | b.d. | 0.10 | b.d. | | | | | | | | | | | |
| | MA-132533 Bo 06/1359 | 97 | 0.03 | 0.61 | 0.01 | 0.10 | b.d. | b.d. | 1.73 | 0.13 | 0.02 | b.d. | 0.05 | 0.01 | | | | | | | | | | | |
| | MA-132529 Bo 06/137 | 97 | 0.29 | 1.43 | 0.30 | 0.04 | 0.01 | 0.82 | 0.91 | 0.06 | 0.01 | b.d. | 0.02 | b.d. | | | | | | | | | | | |
| | MA-132532 Bo 06/1378 | 97 | 0.02 | 1.64 | 0.04 | 0.08 | b.d. | b.d. | 0.91 | 0.06 | 0.13 | 0.01 | 0.04 | b.d. | | | | | | | | | | | |
| | Bo 06/1387 | 93 | 0.33 | 4.46 | 0.18 | 0.68 | b.d. | b.d. | 1.43 | 0.09 | 0.14 | b.d. | 0.05 | b.d. | | | | | | | | | | | |

| Mannheim Number | Object Number | Cu | | Sn | | As | | Pb | | Ni | | Co | | Fe | | Zn | | Sb | | Bi | | Ag | | Au | |
|--------------------|---------------|-------|-------------|-------|-------------|-------------|-------------|-------------|-------------|-------------|-------------|-------------|-------------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|
| | | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % |
| MA-132522 | Bo 06/1465 | 96 | <i>b.d.</i> | 1.70 | 0.19 | 0.05 | 0.02 | 1.45 | 0.05 | 0.32 | 0.01 | 0.03 | <i>b.d.</i> | | | | | | | | | | | | |
| MA-132505 | Bo 06/166 | 98 | <i>b.d.</i> | 0.60 | 0.04 | 0.21 | <i>b.d.</i> | 0.88 | 0.14 | 0.02 | <i>b.d.</i> | 0.02 | <i>b.d.</i> | | | | | | | | | | | | |
| | Bo 06/1874 | 77 | 19.1 | 0.86 | 0.37 | 0.07 | <i>b.d.</i> | 2.18 | 0.22 | 0.07 | <i>b.d.</i> | 0.01 | <i>b.d.</i> | | | | | | | | | | | | |
| MA-132525 | Bo 06/2094 | 97 | 0.12 | 1.47 | 0.23 | 0.07 | <i>b.d.</i> | 0.38 | <i>b.d.</i> | 0.39 | 0.02 | 0.08 | <i>b.d.</i> | | | | | | | | | | | | |
| | Bo 06/2251 | 98 | 0.11 | 0.75 | 0.50 | 0.02 | <i>b.d.</i> | 0.20 | 0.06 | 0.05 | 0.58 | 0.05 | <i>b.d.</i> | | | | | | | | | | | | |
| | Bo 06/2269 | 99 | <i>b.d.</i> | 0.54 | 0.12 | <i>b.d.</i> | 0.01 | 0.22 | 0.08 | 0.08 | <i>b.d.</i> | 0.06 | <i>b.d.</i> | | | | | | | | | | | | |
| | Bo 06/2350 | 92 | 5.24 | 1.38 | 0.38 | 0.04 | <i>b.d.</i> | 0.46 | 0.13 | 0.19 | 0.02 | 0.05 | <i>b.d.</i> | | | | | | | | | | | | |
| MA-132346 | Bo 06/2428 | 90 | 0.05 | 0.17 | 0.01 | 7.93 | 1.05 | 0.88 | <i>b.d.</i> | <i>b.d.</i> | 0.01 | <i>b.d.</i> | <i>b.d.</i> | | | | | | | | | | | | |
| MA-132409 | Bo 06/259 | 79 | 20.7 | 0.38 | 0.03 | <i>b.d.</i> | <i>b.d.</i> | 0.13 | 0.15 | 0.05 | <i>b.d.</i> | 0.02 | <i>b.d.</i> | | | | | | | | | | | | |
| MA-132506 | Bo 06/353 | 83 | 16.6 | 0.24 | <i>b.d.</i> | <i>b.d.</i> | <i>b.d.</i> | 0.31 | 0.11 | <i>b.d.</i> | <i>b.d.</i> | <i>b.d.</i> | <i>b.d.</i> | | | | | | | | | | | | |
| MA-132507 | Bo 06/417 | 97 | 0.04 | 0.66 | 1.38 | <i>b.d.</i> | <i>b.d.</i> | 0.33 | <i>b.d.</i> | 0.08 | 0.05 | 0.07 | <i>b.d.</i> | | | | | | | | | | | | |
| MA-132518 | Bo 06/486 | 92 | 5.11 | 1.58 | 0.36 | 0.07 | <i>b.d.</i> | 0.58 | <i>b.d.</i> | 0.13 | <i>b.d.</i> | 0.04 | <i>b.d.</i> | | | | | | | | | | | | |
| MA-132307 | Bo 06/492 | 81 | 0.04 | 0.24 | <i>b.d.</i> | 16.5 | 1.94 | 0.37 | <i>b.d.</i> | <i>b.d.</i> | <i>b.d.</i> | 0.01 | <i>b.d.</i> | | | | | | | | | | | | |
| | Bo 07/1225 | 75 | 0.06 | 1.32 | 0.04 | 16.2 | 0.66 | 7.03 | <i>b.d.</i> | 0.04 | 0.01 | 0.03 | <i>b.d.</i> | | | | | | | | | | | | |
| | Bo 07/1288 | 99 | 0.05 | 0.79 | 0.06 | 0.03 | <i>b.d.</i> | 0.22 | <i>b.d.</i> | 0.11 | 0.01 | 0.03 | <i>b.d.</i> | | | | | | | | | | | | |
| | Bo 07/1301 | 98 | 0.67 | 1.04 | 0.17 | 0.04 | <i>b.d.</i> | 0.31 | <i>b.d.</i> | 0.13 | 0.03 | 0.07 | <i>b.d.</i> | | | | | | | | | | | | |
| | Bo 07/1720 | 84 | 15.2 | 0.14 | <i>b.d.</i> | <i>b.d.</i> | <i>b.d.</i> | 0.43 | <i>b.d.</i> | <i>b.d.</i> | <i>b.d.</i> | <i>b.d.</i> | <i>b.d.</i> | | | | | | | | | | | | |
| | Bo 07/1745 | 80 | 17.4 | 0.94 | 0.97 | 0.42 | <i>b.d.</i> | 0.21 | <i>b.d.</i> | 0.14 | 0.03 | 0.06 | <i>b.d.</i> | | | | | | | | | | | | |
| | Bo 07/1755 | 97 | 0.11 | 0.75 | 0.04 | 0.35 | <i>b.d.</i> | 1.28 | <i>b.d.</i> | 0.03 | <i>b.d.</i> | <i>b.d.</i> | <i>b.d.</i> | | | | | | | | | | | | |
| | Bo 07/1802 | 94 | 0.08 | 4.04 | 0.23 | 0.11 | <i>b.d.</i> | 1.39 | <i>b.d.</i> | 0.13 | 0.01 | 0.01 | <i>b.d.</i> | | | | | | | | | | | | |
| | Bo 07/1810 | 88 | 6.69 | 2.50 | 1.57 | 0.07 | 0.02 | 0.78 | <i>b.d.</i> | 0.09 | 0.06 | 0.06 | <i>b.d.</i> | | | | | | | | | | | | |
| | Bo 07/1818 | 98 | 0.04 | 0.06 | 0.01 | 1.12 | 0.12 | 0.81 | <i>b.d.</i> | <i>b.d.</i> | <i>b.d.</i> | <i>b.d.</i> | <i>b.d.</i> | | | | | | | | | | | | |
| | Bo 07/1821 | 98 | 0.04 | 0.50 | <i>b.d.</i> | 1.17 | 0.10 | <i>b.d.</i> | <i>b.d.</i> | <i>b.d.</i> | <i>b.d.</i> | 0.02 | <i>b.d.</i> | | | | | | | | | | | | |
| | Bo 07/1860 | 94 | 2.53 | 1.57 | 0.10 | <i>b.d.</i> | <i>b.d.</i> | 2.09 | 0.11 | 0.07 | <i>b.d.</i> | 0.02 | <i>b.d.</i> | | | | | | | | | | | | |
| MA-136335 | Bo 07/1871 | 86 | <i>b.d.</i> | 0.05 | 0.32 | 11.5 | 0.70 | 1.13 | <i>b.d.</i> | <i>b.d.</i> | <i>b.d.</i> | <i>b.d.</i> | <i>b.d.</i> | | | | | | | | | | | | |
| | Bo 07/1874 | 97 | 0.07 | 1.27 | 0.78 | <i>b.d.</i> | <i>b.d.</i> | 0.50 | 0.11 | 0.12 | 0.25 | 0.08 | <i>b.d.</i> | | | | | | | | | | | | |
| | Bo 07/1920 | 90 | 2.91 | 1.17 | 0.39 | 0.11 | <i>b.d.</i> | 3.71 | 0.12 | 1.08 | 0.02 | 0.08 | 0.05 | | | | | | | | | | | | |
| | Bo 07/1921 | 97 | <i>b.d.</i> | 1.77 | 0.42 | 0.02 | <i>b.d.</i> | 1.04 | <i>b.d.</i> | 0.01 | <i>b.d.</i> | 0.02 | 0.04 | | | | | | | | | | | | |

| Mannheim Number | Object Number | Cu wt. % | Sn wt. % | As wt. % | Pb wt. % | Ni wt. % | Co wt. % | Fe wt. % | Zn wt. % | Sb wt. % | Bi wt. % | Ag wt. % | Au wt. % |
|------------------|---------------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|
| | Bo 07/1936 | 87 | 3.91 | 4.70 | 1.32 | 0.17 | b.d. | 2.04 | 0.07 | 0.28 | 0.16 | 0.12 | b.d. |
| | Bo 07/2045 | 98 | 0.05 | 0.49 | 0.14 | b.d. | b.d. | 1.26 | 0.15 | 0.06 | 0.03 | 0.03 | b.d. |
| | Bo 07/2054 | 81 | 17.6 | 0.81 | 0.13 | 0.03 | b.d. | 0.32 | 0.06 | 0.10 | b.d. | b.d. | b.d. |
| | Bo 07/2055 | 99 | b.d. | 0.18 | 0.03 | 0.27 | b.d. | 0.05 | 0.05 | b.d. | 0.02 | 0.06 | b.d. |
| | Bo 07/2079 | 91 | 0.40 | 3.72 | 0.81 | 1.82 | 0.03 | 1.88 | b.d. | 0.31 | 0.03 | 0.09 | b.d. |
| | Bo 07/2087 | 88 | 0.14 | 5.10 | 2.45 | 0.05 | b.d. | 3.55 | 0.11 | 0.06 | 0.16 | 0.20 | 0.10 |
| | Bo 07/2089 | 96 | 2.45 | 0.62 | 0.07 | 0.06 | b.d. | 0.30 | 0.10 | 0.08 | b.d. | 0.02 | b.d. |
| | Bo 07/2093 | 95 | 0.49 | 1.05 | 0.39 | 0.03 | b.d. | 1.96 | 0.08 | 0.12 | 0.46 | 0.23 | b.d. |
| MA-136332 | Bo 07/2101 | 89 | b.d. | 0.90 | 0.05 | 6.52 | 0.24 | 3.04 | b.d. | 0.03 | b.d. | 0.02 | b.d. |
| | Bo 07/2104 | 96 | b.d. | 1.40 | 0.08 | b.d. | 0.02 | 1.24 | b.d. | 1.01 | b.d. | 0.06 | b.d. |
| | Bo 07/2121 | 98 | 0.05 | 0.43 | 0.06 | b.d. | b.d. | 1.60 | 0.04 | b.d. | 0.01 | 0.02 | b.d. |
| | Bo 07/2129 | 85 | 12.3 | 0.87 | 0.41 | 0.06 | b.d. | 1.37 | 0.15 | 0.13 | b.d. | 0.01 | b.d. |
| | Bo 07/2130 | 97 | 0.45 | 0.48 | 0.18 | 0.04 | b.d. | 1.66 | 0.09 | 0.17 | 0.02 | 0.03 | b.d. |
| | Bo 07/2143 | 98 | 0.17 | 0.83 | 0.12 | b.d. | b.d. | 0.59 | b.d. | 0.07 | 0.02 | 0.05 | b.d. |
| MA-136331 | Bo 07/2149 | 68 | 0.05 | 2.70 | 0.07 | 16.4 | 1.03 | 11.7 | b.d. | 0.03 | 0.01 | 0.04 | 0.05 |
| MA-136328 | Bo 07/2151 | 80 | b.d. | 0.52 | 0.01 | 14.0 | 0.60 | 5.08 | b.d. | b.d. | b.d. | 0.01 | b.d. |
| | Bo 07/2154 | 99 | b.d. | 1.04 | 0.02 | 0.07 | 0.01 | 0.23 | b.d. | 0.02 | b.d. | b.d. | b.d. |
| | Bo 07/2200 | 83 | 16.2 | 0.37 | 0.08 | b.d. | b.d. | 0.46 | 0.07 | b.d. | b.d. | b.d. | b.d. |
| MA-136333 | Bo 07/2204 | 84 | b.d. | 0.51 | 0.01 | 10.4 | 0.41 | 4.64 | b.d. | b.d. | b.d. | 0.01 | b.d. |
| | Bo 07/2211 | 99 | 0.37 | 0.10 | 0.08 | b.d. | b.d. | 0.63 | 0.09 | b.d. | b.d. | 0.02 | b.d. |
| | Bo 07/2215 | 97 | b.d. | 0.26 | 0.18 | b.d. | 0.05 | 2.39 | 0.21 | b.d. | b.d. | 0.03 | b.d. |
| | Bo 07/2221 | 95 | 0.06 | 1.00 | 1.12 | 0.13 | b.d. | 1.78 | 0.12 | 0.33 | 0.31 | 0.09 | b.d. |
| | Bo 07/2224 | 96 | 0.05 | 2.13 | 0.55 | 0.04 | b.d. | 1.21 | 0.08 | 0.11 | 0.01 | 0.03 | b.d. |
| | Bo 07/2227 | 97 | 0.20 | 1.58 | 0.18 | 0.06 | b.d. | 0.26 | 0.11 | 0.11 | 0.01 | 0.05 | b.d. |
| | Bo 07/2228 | 91 | 0.05 | 0.59 | 0.14 | 3.37 | 0.07 | 4.60 | 0.07 | 0.13 | 0.03 | 0.07 | b.d. |
| | Bo 07/2235 | 97 | b.d. | 1.54 | 0.69 | b.d. | b.d. | 0.80 | b.d. | 0.08 | 0.02 | 0.03 | b.d. |
| | Bo 07/2239 | 76 | 21.9 | 0.55 | 0.30 | 0.06 | b.d. | 1.26 | 0.17 | 0.09 | b.d. | b.d. | b.d. |
| | Bo 07/2240 | 99 | 0.03 | 0.74 | 0.01 | b.d. | b.d. | 0.21 | 0.13 | b.d. | b.d. | 0.03 | b.d. |

| Mannheim Number | Object Number | Cu | | Sn | | As | | Pb | | Ni | | Co | | Fe | | Zn | | Sb | | Bi | | Ag | | Au | |
|--------------------|---------------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|
| | | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % |
| | Bo 07/2252 | 98 | b.d. | b.d. | 0.23 | b.d. | 1.30 | 0.21 | 0.15 | 0.03 | b.d. | 1.30 | 0.21 | 0.15 | 0.03 | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | |
| | Bo 07/2256 | 94 | 1.20 | 3.11 | 0.72 | 0.08 | 0.50 | 0.19 | 0.19 | 0.04 | 0.05 | 0.50 | 0.19 | 0.19 | 0.04 | 0.05 | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | |
| | Bo 07/2258 | 98 | 0.07 | 0.85 | 0.04 | 0.03 | 0.48 | 0.05 | 0.05 | 0.01 | 0.03 | 0.48 | 0.05 | 0.05 | 0.01 | 0.03 | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | |
| | Bo 07/2260 | 97 | b.d. | 0.85 | 0.86 | b.d. | 0.30 | 0.23 | 0.31 | 0.22 | 0.30 | 0.30 | 0.23 | 0.31 | 0.22 | 0.30 | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | |
| | Bo 07/2269 | 91 | 7.11 | 1.04 | 0.38 | 0.05 | 0.29 | b.d. | 0.09 | b.d. | 0.02 | 0.29 | b.d. | 0.09 | b.d. | 0.02 | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | |
| | Bo 07/2272 | 98 | 0.09 | 0.53 | 1.01 | 0.05 | 0.30 | b.d. | 0.04 | 0.01 | 0.04 | 0.30 | b.d. | 0.04 | 0.01 | 0.04 | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | |
| | Bo 07/2305 | 76 | 20.4 | 1.40 | 0.45 | 1.06 | 0.36 | 0.16 | 0.07 | b.d. | 0.36 | 0.16 | 0.07 | b.d. | 0.07 | 0.07 | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | |
| | Bo 07/2354 | 76 | 22.3 | 0.71 | 0.16 | 0.04 | 0.30 | 0.15 | 0.06 | b.d. | 0.30 | 0.15 | 0.06 | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | |
| | Bo 07/2397 | 97 | 0.21 | 1.26 | 0.57 | 0.04 | 0.38 | b.d. | 0.10 | 0.14 | 0.09 | 0.38 | b.d. | 0.10 | 0.14 | 0.09 | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | |
| | Bo 07/2422 | 89 | 8.01 | 1.23 | 0.35 | b.d. | 0.80 | 0.12 | 0.27 | 0.13 | 0.09 | 0.80 | 0.12 | 0.27 | 0.13 | 0.09 | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | |
| | Bo 07/2445 | 99 | b.d. | 0.35 | 0.22 | b.d. | 0.42 | 0.05 | 0.02 | 0.02 | b.d. | 0.42 | 0.05 | 0.02 | 0.02 | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | |
| | Bo 07/2456 | 98 | 0.07 | 0.46 | 0.20 | b.d. | 0.57 | 0.10 | 0.17 | 0.38 | 0.11 | 0.57 | 0.10 | 0.17 | 0.38 | 0.11 | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | |
| | Bo 07/2458 | 96 | 0.09 | 0.85 | 1.29 | b.d. | 1.25 | 0.13 | 0.03 | 0.03 | 0.05 | 1.25 | 0.13 | 0.03 | 0.03 | 0.05 | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | |
| | Bo 07/2460 | 97 | 0.12 | 1.05 | 0.56 | 0.02 | 0.52 | 0.08 | 0.25 | b.d. | 0.12 | 0.52 | 0.08 | 0.25 | b.d. | 0.12 | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | |
| | Bo 07/2470 | 98 | 0.14 | 1.13 | 0.14 | 0.06 | 0.22 | 0.16 | 0.07 | 0.02 | 0.12 | 0.22 | 0.16 | 0.07 | 0.02 | 0.12 | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | |
| | Bo 07/2471 | 78 | 14.7 | 3.59 | 1.36 | 0.14 | 1.58 | 0.22 | 0.29 | 0.11 | 0.07 | 1.58 | 0.22 | 0.29 | 0.11 | 0.07 | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | |
| | Bo 07/2483 | 98 | 0.07 | 0.89 | 0.37 | 0.05 | 0.62 | 0.15 | 0.12 | 0.03 | 0.05 | 0.62 | 0.15 | 0.12 | 0.03 | 0.05 | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | |
| | Bo 07/2484 | 79 | 18.8 | 1.44 | 0.26 | 0.15 | 0.26 | 0.11 | 0.11 | 0.02 | 0.09 | 0.26 | 0.11 | 0.11 | 0.02 | 0.09 | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | |
| | Bo 07/2637 | 97 | 0.22 | 0.31 | 0.82 | 0.09 | 1.32 | 0.19 | 0.10 | 0.02 | 0.06 | 1.32 | 0.19 | 0.10 | 0.02 | 0.06 | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | |
| | Bo 07/2707 | 95 | 0.02 | 0.04 | b.d. | 3.47 | 1.29 | 0.08 | b.d. | b.d. | 0.01 | 1.29 | 0.08 | b.d. | b.d. | 0.01 | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | |
| MA-132197 | Bo 07/29 | 83 | 15.1 | 0.67 | 0.15 | 0.09 | 0.93 | 0.13 | 0.04 | b.d. | 0.03 | 0.93 | 0.13 | 0.04 | b.d. | 0.03 | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | |
| | Bo 07/3402 | 99 | 0.37 | 0.41 | 0.22 | b.d. | 0.25 | b.d. | 0.04 | b.d. | 0.02 | 0.25 | b.d. | 0.04 | b.d. | 0.02 | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | |
| | Bo 07/3431 | 81 | 16.6 | 1.32 | 0.25 | 0.15 | 0.39 | 0.11 | 0.10 | b.d. | 0.10 | 0.39 | 0.11 | 0.10 | b.d. | 0.10 | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | |
| | Bo 07/3440 | 98 | 0.03 | 0.83 | 0.01 | 0.03 | 1.06 | b.d. | b.d. | b.d. | 0.10 | 1.06 | b.d. | b.d. | b.d. | 0.10 | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | |
| | Bo 07/3441 | 96 | 0.17 | 2.44 | 0.18 | b.d. | 0.77 | 0.11 | 0.08 | b.d. | 0.08 | 0.77 | 0.11 | 0.08 | b.d. | 0.08 | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | |
| | Bo 07/3444 | 98 | 0.14 | 1.31 | 0.16 | b.d. | 0.38 | b.d. | 0.11 | 0.04 | 0.07 | 0.38 | b.d. | 0.11 | 0.04 | 0.07 | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | |
| | Bo 07/3457 | 97 | b.d. | 1.14 | 0.06 | b.d. | 1.41 | 0.05 | 0.04 | b.d. | 0.04 | 1.41 | 0.05 | 0.04 | b.d. | 0.04 | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | |
| | Bo 07/3460 | 96 | 0.14 | 2.03 | 0.13 | 0.12 | 1.20 | 0.06 | 0.06 | 0.01 | 0.03 | 1.20 | 0.06 | 0.06 | 0.01 | 0.03 | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | |

| Mannheim Number | Object Number | Cu | | Sn | | As | | Pb | | Ni | | Co | | Fe | | Zn | | Sb | | Bi | | Ag | | Au | |
|--------------------|---------------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|
| | | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % |
| | Bo 07/3481 | 98 | 0.05 | 0.87 | 0.44 | b.d. | b.d. | 0.80 | 0.80 | 0.11 | 0.08 | 0.10 | b.d. | | | | | | | | | | | | |
| | Bo 07/3484 | 67 | 28.9 | 2.32 | 0.64 | 0.25 | b.d. | 0.92 | 0.92 | 0.11 | 0.16 | 0.09 | b.d. | | | | | | | | | | | | |
| | Bo 07/3490 | 95 | 0.02 | 1.22 | 1.14 | 0.07 | b.d. | 1.97 | 1.97 | 0.06 | b.d. | 0.03 | b.d. | | | | | | | | | | | | |
| | Bo 07/3509 | 96 | 0.14 | 1.90 | 0.22 | b.d. | b.d. | 1.10 | 1.10 | b.d. | 0.05 | 0.09 | b.d. | | | | | | | | | | | | |
| | Bo 07/3571 | 79 | 19.2 | 0.52 | 0.27 | b.d. | b.d. | 0.43 | 0.43 | 0.05 | 0.04 | b.d. | b.d. | | | | | | | | | | | | |
| MA-136334 | Bo 07/3594 | 92 | 0.09 | 0.55 | 0.03 | 5.58 | 0.09 | 1.57 | 1.57 | b.d. | 0.01 | 0.03 | b.d. | | | | | | | | | | | | |
| | Bo 07/3606 | 99 | 0.10 | 0.46 | 0.19 | 0.03 | b.d. | 0.19 | 0.19 | 0.06 | 0.07 | 0.03 | b.d. | | | | | | | | | | | | |
| | Bo 07/3693 | 79 | 19.2 | 0.98 | 0.28 | 0.15 | b.d. | 0.17 | 0.17 | 0.10 | 0.06 | 0.03 | b.d. | | | | | | | | | | | | |
| | Bo 07/3694 | 77 | 21.1 | 0.93 | 0.10 | 0.32 | 0.02 | 0.72 | 0.72 | 0.11 | 0.08 | b.d. | b.d. | | | | | | | | | | | | |
| | Bo 07/3723 | 79 | 18.9 | 0.71 | 0.16 | 0.03 | 0.04 | 0.95 | 0.95 | 0.11 | 0.09 | 0.02 | b.d. | | | | | | | | | | | | |
| MA-136325 | Bo 07/3735 | 88 | b.d. | 0.19 | b.d. | 9.10 | 0.21 | 2.25 | 2.25 | b.d. | b.d. | b.d. | b.d. | | | | | | | | | | | | |
| | Bo 07/3739 | 81 | 15.9 | 2.04 | 0.66 | 0.18 | b.d. | 0.37 | 0.37 | 0.19 | 0.12 | 0.04 | b.d. | | | | | | | | | | | | |
| | Bo 07/3798 | 91 | 0.52 | 4.82 | 1.88 | 0.03 | b.d. | 1.05 | 1.05 | 0.13 | 0.09 | 0.28 | 0.17 | | | | | | | | | | | | |
| | Bo 07/3803 | 94 | 4.43 | 0.88 | 0.11 | 0.03 | b.d. | 0.57 | 0.57 | 0.14 | 0.13 | 0.04 | b.d. | | | | | | | | | | | | |
| | Bo 07/3811 | 97 | 0.06 | 1.81 | 0.09 | 0.04 | b.d. | 0.80 | 0.80 | 0.10 | 0.13 | 0.03 | 0.06 | | | | | | | | | | | | |
| | Bo 07/3816 | 98 | 0.04 | 1.26 | 0.04 | 0.03 | b.d. | 0.47 | 0.47 | 0.13 | 0.04 | b.d. | b.d. | | | | | | | | | | | | |
| | Bo 08/100 | 97 | b.d. | 2.11 | 0.01 | 0.07 | b.d. | 0.25 | 0.25 | 0.07 | 0.05 | 0.01 | 0.03 | | | | | | | | | | | | |
| | Bo 08/102 | 97 | 0.04 | 0.85 | 0.03 | 0.13 | b.d. | 1.44 | 1.44 | 0.09 | 0.02 | 0.01 | 0.04 | | | | | | | | | | | | |
| | Bo 08/105 | 92 | 1.05 | 2.01 | 1.29 | 0.02 | b.d. | 3.24 | 3.24 | 0.26 | 0.06 | 0.02 | 0.08 | | | | | | | | | | | | |
| | Bo 08/132 | 88 | 10.3 | 0.32 | 0.37 | 0.11 | b.d. | 0.58 | 0.58 | 0.12 | 0.19 | b.d. | 0.03 | | | | | | | | | | | | |
| | Bo 08/134 | 80 | 19.1 | 0.43 | 0.14 | b.d. | b.d. | 0.49 | 0.49 | 0.20 | 0.06 | b.d. | b.d. | | | | | | | | | | | | |
| | Bo 08/140 | 89 | 2.67 | 2.71 | 0.43 | b.d. | b.d. | 5.03 | 5.03 | 0.13 | 0.17 | 0.06 | 0.15 | | | | | | | | | | | | |
| | Bo 08/143 | 95 | 0.18 | 0.18 | 0.01 | 3.48 | 0.11 | 0.49 | 0.49 | b.d. | 0.03 | 0.02 | 0.06 | | | | | | | | | | | | |
| | Bo 08/1511 | 89 | 9.23 | 0.99 | 0.55 | 0.06 | b.d. | 0.15 | 0.15 | 0.05 | 0.12 | b.d. | 0.29 | | | | | | | | | | | | |
| | Bo 08/156 | 97 | 0.70 | 1.48 | 0.29 | 0.06 | b.d. | 0.21 | 0.21 | 0.04 | 0.13 | 0.03 | 0.07 | | | | | | | | | | | | |
| MA-132549 | Bo 08/16 | 98 | b.d. | 0.36 | 0.13 | b.d. | b.d. | 1.49 | 1.49 | 0.22 | 0.12 | 0.02 | 0.01 | | | | | | | | | | | | |
| | Bo 08/160 | 77 | 17.9 | 2.47 | 0.29 | b.d. | b.d. | 1.50 | 1.50 | 0.08 | 0.21 | 0.03 | 0.10 | | | | | | | | | | | | |
| | Bo 08/197 | 98 | 0.07 | 0.59 | 0.10 | b.d. | 0.01 | 0.80 | 0.80 | 0.08 | 0.05 | 0.02 | 0.05 | | | | | | | | | | | | |

| Mannheim Number | Object Number | Cu | | Sn | | As | | Pb | | Ni | | Co | | Fe | | Zn | | Sb | | Bi | | Ag | | Au | |
|--------------------|---------------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|
| | | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % |
| | Bo 08/212 | 95 | 0.17 | 1.10 | 0.39 | b.d. | 0.04 | 2.79 | 0.07 | 0.02 | 0.02 | 0.01 | b.d. | | | | | | | | | | | | |
| MA-132205 | Bo 08/217 | 94 | 0.14 | 2.03 | 2.44 | b.d. | b.d. | 1.41 | 0.12 | 0.20 | 0.07 | 0.05 | 0.03 | | | | | | | | | | | | |
| MA-132198 | Bo 08/227 | 83 | 13.6 | 1.90 | 0.75 | 0.11 | b.d. | 0.80 | 0.11 | 0.13 | b.d. | 0.04 | b.d. | | | | | | | | | | | | |
| MA-132206 | Bo 08/229 | 96 | 1.24 | 1.39 | 0.10 | b.d. | 0.02 | 1.46 | 0.07 | 0.06 | 0.02 | 0.04 | b.d. | | | | | | | | | | | | |
| | Bo 08/236 | 92 | 0.34 | 3.25 | 1.66 | 0.03 | b.d. | 1.96 | 0.11 | 0.18 | 0.10 | 0.13 | b.d. | | | | | | | | | | | | |
| | Bo 08/25 | 98 | b.d. | 0.53 | 0.04 | 0.45 | b.d. | 0.74 | b.d. | 0.05 | 0.01 | 0.01 | b.d. | | | | | | | | | | | | |
| | Bo 08/255 | 79 | 16.6 | 2.19 | 0.32 | 0.14 | b.d. | 1.25 | 0.07 | 0.30 | 0.09 | 0.07 | b.d. | | | | | | | | | | | | |
| | Bo 08/258 | 95 | 0.04 | 2.30 | 1.20 | 0.02 | b.d. | 0.75 | b.d. | 0.13 | 0.19 | 0.06 | b.d. | | | | | | | | | | | | |
| MA-136324 | Bo 08/264 | 91 | b.d. | 0.33 | 0.01 | 7.66 | 0.79 | 0.69 | b.d. | b.d. | b.d. | b.d. | b.d. | | | | | | | | | | | | |
| | Bo 08/27 | 95 | 1.30 | 1.14 | 1.77 | 0.04 | b.d. | 0.41 | b.d. | 0.21 | 0.03 | 0.07 | b.d. | | | | | | | | | | | | |
| | Bo 08/28 | 93 | 5.88 | 0.56 | 0.08 | b.d. | 0.04 | 0.48 | 0.06 | 0.06 | b.d. | 0.01 | b.d. | | | | | | | | | | | | |
| | Bo 08/300 | 98 | 0.06 | 1.11 | 0.17 | 0.06 | b.d. | 0.30 | 0.05 | 0.18 | 0.05 | 0.09 | b.d. | | | | | | | | | | | | |
| | Bo 08/36 | 97 | 0.06 | 1.97 | 0.08 | b.d. | b.d. | 0.60 | 0.18 | 0.15 | 0.04 | 0.14 | b.d. | | | | | | | | | | | | |
| | Bo 08/37 | 96 | 0.78 | 0.89 | 0.30 | 0.05 | b.d. | 1.53 | 0.22 | 0.14 | 0.05 | 0.07 | b.d. | | | | | | | | | | | | |
| | Bo 08/42 | 93 | 0.72 | 1.91 | 2.93 | 0.04 | b.d. | 1.09 | 0.12 | 0.08 | 0.14 | 0.14 | b.d. | | | | | | | | | | | | |
| | Bo 08/43 | 77 | 20.7 | 1.68 | 0.30 | 0.03 | b.d. | 0.38 | 0.12 | 0.20 | b.d. | b.d. | b.d. | | | | | | | | | | | | |
| | Bo 08/44 | 95 | 0.11 | 3.81 | 0.09 | b.d. | b.d. | 0.73 | 0.08 | 0.10 | 0.01 | 0.05 | b.d. | | | | | | | | | | | | |
| | Bo 08/53 | 94 | 1.11 | 2.82 | 0.27 | 0.09 | b.d. | 1.56 | 0.13 | 0.15 | 0.02 | 0.08 | b.d. | | | | | | | | | | | | |
| | Bo 08/57 | 99 | 0.04 | 0.28 | 0.03 | 0.04 | 0.06 | 0.40 | 0.09 | 0.02 | 0.01 | b.d. | b.d. | | | | | | | | | | | | |
| | Bo 08/66 | 90 | 7.79 | 1.29 | 0.19 | 0.07 | b.d. | 0.24 | 0.05 | 0.20 | 0.02 | 0.03 | b.d. | | | | | | | | | | | | |
| | Bo 08/69 | 88 | 10.8 | 0.72 | 0.15 | 0.04 | b.d. | 0.31 | 0.07 | 0.15 | b.d. | b.d. | b.d. | | | | | | | | | | | | |
| | Bo 08/73 | 91 | 0.12 | 7.20 | 0.24 | 0.13 | b.d. | 1.27 | 0.04 | 0.13 | b.d. | 0.06 | b.d. | | | | | | | | | | | | |
| | Bo 08/77 | 97 | b.d. | 1.68 | 0.42 | b.d. | b.d. | 0.32 | 0.08 | 0.18 | 0.13 | 0.11 | b.d. | | | | | | | | | | | | |
| | Bo 08/841 | 98 | b.d. | 0.68 | 0.02 | b.d. | b.d. | 0.85 | 0.11 | b.d. | b.d. | 0.10 | b.d. | | | | | | | | | | | | |
| | Bo 08/859 | 97 | 0.31 | 0.69 | 0.38 | b.d. | b.d. | 1.17 | 0.42 | b.d. | b.d. | 0.09 | b.d. | | | | | | | | | | | | |
| | Bo 08/87 | 97 | 0.24 | 1.62 | 0.29 | 0.05 | b.d. | 0.69 | 0.06 | 0.06 | 0.09 | 0.05 | b.d. | | | | | | | | | | | | |
| | Bo 08/884 | 98 | 0.03 | 0.76 | 0.39 | 0.04 | b.d. | 0.87 | 0.17 | b.d. | 0.08 | 0.05 | b.d. | | | | | | | | | | | | |
| | Bo 08/966 | 99 | 0.24 | 0.29 | 0.03 | b.d. | b.d. | 0.12 | 0.10 | 0.03 | 0.01 | b.d. | b.d. | | | | | | | | | | | | |

| Mannheim Number | Object Number | Cu | | Sn | | As | | Pb | | Ni | | Co | | Fe | | Zn | | Sb | | Bi | | Ag | | Au | |
|-----------------------|---------------|------|------|------|-------|------|------|------|------|------|------|------|------|------|------|------|------|------|------|------|------|------|------|------|------|
| | | wt.% | wt.% | wt.% | wt.% | wt.% | wt.% | wt.% | wt.% | wt.% | wt.% | wt.% | wt.% | wt.% | wt.% | wt.% | wt.% | wt.% | wt.% | wt.% | wt.% | wt.% | wt.% | wt.% | wt.% |
| | Bo 07/519 | 98 | 0.02 | 0.31 | 1.35 | 0.02 | b.d. | 0.13 | b.d. | 0.02 | 0.02 | 0.02 | 0.06 | 0.02 | 0.13 | b.d. | 0.02 | 0.02 | 0.02 | 0.02 | 0.02 | 0.06 | 0.06 | 0.03 | |
| | Bo 07/523 | 99 | 0.02 | 0.11 | 0.50 | b.d. | b.d. | 0.20 | b.d. | b.d. | b.d. | 0.17 | 0.08 | 0.17 | 0.20 | b.d. | 0.17 | 0.08 | 0.17 | 0.08 | 0.08 | 0.08 | 0.08 | b.d. | |
| IMA-136328 | Bo 07/576 | 89 | 0.02 | 0.26 | b.d. | 6.56 | 0.74 | 3.39 | b.d. | 6.56 | 0.74 | 3.39 | b.d. | b.d. | 0.01 | 0.01 | 0.01 | 0.01 | b.d. | 0.01 | b.d. | b.d. | b.d. | b.d. | |
| | Bo 07/578 | 99 | 0.04 | 0.17 | 0.61 | b.d. | b.d. | 0.05 | b.d. | 0.05 | b.d. | 0.05 | 0.01 | 0.08 | 0.05 | b.d. | 0.08 | 0.01 | 0.08 | 0.01 | 0.08 | 0.08 | b.d. | b.d. | |
| | Bo 07/591 | 75 | 11.2 | 2.62 | 9.79 | 0.04 | b.d. | 1.47 | b.d. | 1.47 | 0.05 | 0.15 | 0.05 | 0.15 | 1.47 | 0.05 | 0.15 | 0.05 | 0.15 | 0.05 | 0.03 | 0.03 | 0.03 | b.d. | |
| EARLY IRON AGE | | | | | | | | | | | | | | | | | | | | | | | | | |
| | Bo 96/31 | 84 | 5.82 | 1.97 | 6.14 | 0.07 | b.d. | 1.24 | b.d. | 1.24 | 0.17 | 0.06 | 0.03 | 0.06 | 1.24 | 0.17 | 0.06 | 0.03 | 0.06 | 0.03 | 0.27 | 0.27 | b.d. | b.d. | |
| | Bo 96/45 | 75 | 21.5 | 0.73 | 0.35 | 0.08 | 0.03 | 1.57 | 0.03 | 1.57 | 0.18 | 0.05 | b.d. | 0.05 | 1.57 | 0.18 | 0.05 | b.d. | 0.05 | b.d. | 0.08 | 0.08 | b.d. | b.d. | |
| | Bo 96/85 | 94 | 4.05 | 0.03 | 0.02 | b.d. | b.d. | 1.41 | b.d. | 1.41 | 0.25 | b.d. | b.d. | b.d. | 1.41 | 0.25 | b.d. | b.d. | b.d. | b.d. | 0.01 | 0.01 | 0.01 | b.d. | |
| | Bo 97/25 | 44 | 26.6 | 1.26 | 25.91 | 0.62 | 0.12 | 1.38 | 0.12 | 1.38 | 0.12 | 0.06 | 0.12 | 0.06 | 1.38 | 0.12 | 0.06 | 0.12 | 0.06 | 0.12 | 0.15 | 0.15 | b.d. | b.d. | |
| | Bo 97/26 | 88 | 11.0 | 0.44 | 0.05 | b.d. | 0.01 | 0.35 | 0.01 | 0.35 | 0.09 | 0.02 | b.d. | 0.02 | 0.35 | 0.09 | 0.02 | b.d. | 0.02 | b.d. | b.d. | b.d. | b.d. | b.d. | |
| | Bo 97/31 | 92 | 6.51 | 0.87 | 0.22 | 0.07 | b.d. | 0.32 | b.d. | 0.32 | b.d. | 0.06 | b.d. | 0.06 | 0.32 | b.d. | 0.06 | b.d. | 0.06 | b.d. | 0.02 | 0.02 | 0.02 | b.d. | |
| | Bo 97/35 | 90 | 0.18 | 1.11 | 0.32 | 2.61 | 0.12 | 5.63 | 0.12 | 5.63 | 0.17 | 0.08 | 0.02 | 0.08 | 5.63 | 0.17 | 0.08 | 0.02 | 0.08 | 0.02 | 0.11 | 0.11 | b.d. | b.d. | |
| | Bo 97/38 | 77 | 19.2 | 1.73 | 0.95 | 0.12 | 0.04 | 1.19 | 0.04 | 1.19 | 0.15 | 0.09 | b.d. | 0.09 | 1.19 | 0.15 | 0.09 | b.d. | 0.09 | b.d. | 0.01 | 0.01 | b.d. | b.d. | |
| | Bo 97/87 | 90 | 8.46 | 0.65 | 0.11 | 0.05 | 0.03 | 0.31 | 0.03 | 0.31 | 0.16 | 0.04 | b.d. | 0.04 | 0.31 | 0.16 | 0.04 | b.d. | 0.04 | b.d. | 0.01 | 0.01 | 0.01 | b.d. | |
| | Bo 97/90 | 87 | 11.5 | 0.32 | 0.22 | 0.04 | b.d. | 0.88 | b.d. | 0.88 | 0.17 | 0.03 | b.d. | 0.03 | 0.88 | 0.17 | 0.03 | b.d. | 0.03 | b.d. | 0.10 | 0.10 | b.d. | b.d. | |
| | Bo 97/93 | 96 | 0.16 | 1.00 | 0.28 | 0.06 | b.d. | 2.15 | b.d. | 2.15 | 0.04 | 0.07 | 0.03 | 0.07 | 2.15 | 0.04 | 0.07 | 0.03 | 0.07 | 0.03 | 0.08 | 0.08 | 0.04 | 0.04 | |
| | Bo 97/94 | 89 | 9.10 | 0.79 | 0.18 | 0.05 | 0.07 | 0.55 | 0.07 | 0.55 | 0.18 | 0.03 | b.d. | 0.03 | 0.55 | 0.18 | 0.03 | b.d. | 0.03 | b.d. | 0.01 | 0.01 | b.d. | b.d. | |
| | Bo 97/97 | 99 | 0.02 | 0.24 | 0.18 | 0.11 | b.d. | 0.46 | b.d. | 0.46 | 0.12 | b.d. | b.d. | b.d. | 0.46 | 0.12 | b.d. | b.d. | b.d. | b.d. | 0.09 | 0.09 | b.d. | b.d. | |
| | Bo 97/99 | 92 | 7.22 | 0.64 | 0.12 | 0.10 | 0.01 | 0.13 | 0.01 | 0.13 | 0.05 | 0.06 | b.d. | 0.06 | 0.13 | 0.05 | 0.06 | b.d. | 0.06 | b.d. | 0.04 | 0.04 | b.d. | b.d. | |
| | ETD 96/31 | 97 | 0.28 | 1.74 | 0.19 | 0.13 | b.d. | 0.81 | b.d. | 0.81 | b.d. | 0.13 | b.d. | 0.13 | 0.81 | b.d. | 0.13 | b.d. | 0.13 | b.d. | 0.04 | 0.04 | b.d. | b.d. | |
| | ETD 96/38 | 96 | 2.76 | 0.52 | 0.25 | 0.03 | b.d. | 0.66 | b.d. | 0.66 | 0.05 | 0.05 | b.d. | 0.05 | 0.66 | 0.05 | 0.05 | b.d. | 0.05 | b.d. | 0.01 | 0.01 | b.d. | b.d. | |
| | ETD 96/46 | 98 | b.d. | 0.53 | 0.03 | b.d. | b.d. | 0.59 | b.d. | 0.59 | 0.38 | 0.03 | b.d. | 0.03 | 0.59 | 0.38 | 0.03 | b.d. | 0.03 | b.d. | 0.03 | 0.03 | b.d. | b.d. | |
| | ETD 97/197 | 73 | 23.7 | 0.26 | 0.47 | b.d. | b.d. | 1.52 | b.d. | 1.52 | 0.06 | 0.06 | b.d. | 0.06 | 1.52 | 0.06 | 0.06 | b.d. | 0.06 | b.d. | 0.88 | 0.88 | b.d. | b.d. | |
| | ETD 97/198 | 80 | 17.8 | 0.84 | 0.62 | 0.17 | 0.02 | 0.40 | 0.02 | 0.40 | 0.26 | 0.02 | b.d. | 0.02 | 0.40 | 0.26 | 0.02 | b.d. | 0.02 | b.d. | 0.04 | 0.04 | b.d. | b.d. | |
| | ETD 97/203 | 88 | 10.4 | 0.44 | 0.26 | 0.09 | 0.02 | 0.87 | 0.02 | 0.87 | 0.05 | 0.04 | b.d. | 0.04 | 0.87 | 0.05 | 0.04 | b.d. | 0.04 | b.d. | 0.02 | 0.02 | b.d. | b.d. | |
| | ETD 97/215 | 97 | 0.40 | 0.13 | 0.47 | 0.08 | 0.01 | 1.14 | 0.01 | 1.14 | 0.16 | 0.22 | 0.09 | 0.22 | 1.14 | 0.16 | 0.22 | 0.09 | 0.22 | 0.09 | 0.07 | 0.07 | b.d. | b.d. | |

| Mannheim Number | Object Number | Cu | | Sn | | As | | Pb | | Ni | | Co | | Fe | | Zn | | Sb | | Bi | | Ag | | Au | |
|-------------------------------|---------------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|
| | | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % |
| ETD 97/225 | | 70 | 27.4 | 0.32 | 0.53 | 0.03 | b.d. | 1.16 | b.d. | 0.09 | b.d. | 0.05 | b.d. | 1.16 | b.d. | 0.09 | b.d. | 0.05 | b.d. | 0.09 | b.d. | 0.05 | b.d. | 0.05 | b.d. |
| ETD 97/235 | | 98 | 0.96 | 0.37 | 0.04 | 0.22 | 0.02 | 0.04 | b.d. | 0.02 | 0.02 | 0.02 | 0.02 | 0.04 | b.d. | b.d. | 0.01 | 0.01 | b.d. | 0.01 | 0.01 | 0.01 | 0.01 | b.d. | b.d. |
| ETD 97/236 | | 80 | 16.7 | 0.24 | 0.02 | b.d. | b.d. | 1.05 | b.d. | b.d. | b.d. | b.d. | b.d. | 1.05 | b.d. | b.d. | b.d. | 1.37 | b.d. | b.d. | b.d. | 1.37 | b.d. | b.d. | b.d. |
| ETD 97/239 | | 76 | 19.2 | 0.76 | 0.92 | 0.08 | b.d. | 2.46 | b.d. | b.d. | b.d. | b.d. | b.d. | 2.46 | b.d. | 0.06 | b.d. | 0.14 | b.d. | 0.06 | b.d. | 0.14 | 0.18 | 0.18 | 0.18 |
| ETD 97/245 | | 99 | 0.02 | 0.54 | 0.05 | b.d. | b.d. | 0.23 | b.d. | b.d. | b.d. | b.d. | b.d. | 0.23 | b.d. | 0.03 | 0.01 | 0.03 | b.d. | 0.03 | b.d. | 0.03 | b.d. | b.d. | b.d. |
| ETD 97/253 | | 97 | 0.55 | 1.64 | 0.36 | b.d. | b.d. | 0.15 | b.d. | b.d. | b.d. | b.d. | b.d. | 0.15 | b.d. | 0.17 | b.d. | 0.05 | b.d. | 0.17 | b.d. | 0.05 | b.d. | b.d. | b.d. |
| ETD 97/261 | | 90 | 8.77 | 0.16 | 0.66 | b.d. | b.d. | 0.40 | b.d. | b.d. | b.d. | b.d. | b.d. | 0.40 | b.d. | b.d. | b.d. | 0.01 | b.d. | b.d. | b.d. | 0.01 | b.d. | b.d. | b.d. |
| ETD 97/265 | | 93 | 6.57 | 0.55 | 0.14 | 0.03 | 0.05 | 0.08 | b.d. | 0.05 | 0.03 | 0.05 | 0.05 | 0.08 | b.d. | 0.03 | b.d. | b.d. | b.d. | 0.03 | b.d. | b.d. | b.d. | b.d. | b.d. |
| ETD 97/273 | | 80 | 18.1 | 0.50 | 0.20 | 0.07 | b.d. | 1.39 | b.d. | b.d. | b.d. | b.d. | b.d. | 1.39 | b.d. | 0.02 | b.d. | b.d. | b.d. | 0.02 | b.d. | b.d. | b.d. | b.d. | b.d. |
| ETD 97/340A | | 88 | 9.48 | 0.98 | 0.09 | 0.04 | b.d. | 0.85 | b.d. | b.d. | b.d. | b.d. | b.d. | 0.85 | b.d. | 0.07 | b.d. | 0.01 | b.d. | 0.07 | b.d. | 0.01 | b.d. | b.d. | b.d. |
| ETD 97/340B | | 92 | 7.32 | 0.54 | 0.08 | b.d. | b.d. | 0.20 | b.d. | b.d. | b.d. | b.d. | b.d. | 0.20 | b.d. | 0.04 | b.d. | 0.03 | b.d. | 0.04 | b.d. | 0.03 | b.d. | b.d. | b.d. |
| ETD 97/340C | | 98 | 0.10 | 1.46 | 0.09 | 0.04 | b.d. | 0.39 | b.d. | b.d. | b.d. | b.d. | b.d. | 0.39 | b.d. | 0.09 | 0.12 | 0.05 | b.d. | 0.09 | 0.12 | 0.05 | b.d. | b.d. | b.d. |
| ETD 97/340D | | 100 | b.d. | 0.15 | 0.02 | 0.09 | 0.03 | 0.12 | b.d. | 0.03 | 0.09 | 0.03 | 0.03 | 0.12 | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. |
| ETD 98/04 | | 93 | 5.69 | 0.61 | 0.14 | 0.07 | 0.05 | 0.11 | b.d. | 0.05 | 0.07 | 0.05 | 0.05 | 0.11 | b.d. | 0.03 | b.d. | 0.02 | b.d. | 0.03 | b.d. | 0.02 | b.d. | b.d. | b.d. |
| MIDDLE / LATE IRON AGE | | | | | | | | | | | | | | | | | | | | | | | | | |
| MA-132554 | Bo 307/n | 91 | 8.22 | 0.30 | 0.31 | 0.01 | b.d. | 0.13 | b.d. | b.d. | 0.01 | b.d. | b.d. | 0.13 | b.d. | 0.21 | b.d. | 0.11 | b.d. | 0.21 | b.d. | 0.11 | b.d. | b.d. | b.d. |
| MA-132559 | Bo 443/i/3 | 90 | 8.88 | 0.21 | 0.71 | 0.13 | b.d. | 0.11 | b.d. | b.d. | 0.13 | b.d. | b.d. | 0.11 | b.d. | 0.03 | b.d. | 0.02 | b.d. | 0.03 | b.d. | 0.02 | b.d. | b.d. | b.d. |
| | Bo 94/122 | 97 | b.d. | 0.78 | 0.04 | 0.17 | 0.19 | 1.86 | b.d. | 0.19 | 0.17 | 0.19 | 0.19 | 1.86 | b.d. | b.d. | 0.01 | 0.02 | b.d. | b.d. | 0.01 | 0.02 | 0.02 | b.d. | b.d. |
| | Bo 94/32 | 78 | 17.3 | 1.05 | 0.81 | 0.08 | b.d. | 1.95 | b.d. | b.d. | 0.08 | b.d. | b.d. | 1.95 | b.d. | 0.10 | b.d. | 0.06 | b.d. | 0.10 | b.d. | 0.06 | b.d. | b.d. | b.d. |
| | Bo 94/35 | 97 | 0.74 | 0.93 | 0.11 | 0.08 | b.d. | 0.44 | b.d. | b.d. | 0.08 | b.d. | b.d. | 0.44 | b.d. | 0.09 | 0.02 | 0.08 | b.d. | 0.09 | 0.02 | 0.08 | b.d. | b.d. | b.d. |
| | Bo 95/12 | 85 | 12.2 | 0.48 | 1.90 | 0.04 | b.d. | 0.17 | b.d. | b.d. | 0.04 | b.d. | b.d. | 0.17 | b.d. | 0.02 | b.d. | b.d. | b.d. | 0.02 | b.d. | b.d. | b.d. | b.d. | b.d. |
| | Bo 95/126 | 79 | 19.0 | 0.19 | 0.63 | b.d. | b.d. | 0.65 | b.d. | b.d. | b.d. | b.d. | b.d. | 0.65 | b.d. | 0.09 | b.d. | 0.17 | b.d. | 0.09 | b.d. | 0.17 | b.d. | b.d. | b.d. |
| | Bo 95/13 | 80 | 15.6 | 1.25 | 1.82 | 0.03 | b.d. | 0.41 | b.d. | b.d. | 0.03 | b.d. | b.d. | 0.41 | b.d. | 0.49 | 0.07 | 0.24 | b.d. | 0.49 | 0.07 | 0.24 | b.d. | b.d. | b.d. |
| | Bo 95/69 | 72 | 23.5 | 0.59 | 2.87 | 0.04 | 0.05 | 0.45 | b.d. | 0.05 | 0.04 | 0.05 | 0.05 | 0.45 | b.d. | 0.12 | b.d. | 0.09 | b.d. | 0.12 | b.d. | 0.09 | b.d. | b.d. | b.d. |
| | Bo 96/67 | 87 | 12.3 | 0.44 | 0.40 | 0.08 | b.d. | 0.05 | b.d. | b.d. | 0.08 | b.d. | b.d. | 0.05 | b.d. | 0.02 | b.d. | 0.03 | b.d. | 0.02 | b.d. | 0.03 | b.d. | b.d. | b.d. |
| | Bo 97/30 | 66 | 32.8 | 0.33 | 0.10 | 0.04 | 0.02 | 0.70 | b.d. | 0.02 | 0.04 | 0.02 | 0.02 | 0.70 | b.d. | 0.03 | b.d. | 0.03 | b.d. | 0.03 | b.d. | 0.03 | b.d. | b.d. | b.d. |
| | ETD 94/125 | 88 | 11.6 | 0.14 | 0.17 | b.d. | b.d. | 0.27 | b.d. | b.d. | b.d. | b.d. | b.d. | 0.27 | b.d. | 0.09 | 0.04 | 0.04 | b.d. | 0.09 | 0.04 | 0.04 | b.d. | b.d. | b.d. |

| Mannheim Number | Object Number | Cu | | Sn | | As | | Pb | | Ni | | Co | | Fe | | Zn | | Sb | | Bi | | Ag | | Au | |
|--------------------|---------------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|
| | | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % |
| ETD 94/126 | | 96 | 3.56 | 0.33 | 0.03 | 0.03 | 0.02 | b.d. | b.d. | 0.34 | 0.05 | 0.02 | b.d. | 0.05 | 0.02 | 0.02 | 0.05 | b.d. | b.d. | 0.05 | 0.05 | b.d. | b.d. | b.d. | |
| ETD 94/178 | | 89 | 8.78 | 0.66 | 1.48 | 0.03 | 0.03 | b.d. | b.d. | 0.12 | 0.19 | 0.09 | 0.09 | 0.08 | 0.09 | 0.09 | 0.08 | b.d. | b.d. | 0.08 | 0.08 | b.d. | b.d. | b.d. | |
| ETD 94/19 | | 98 | 0.67 | b.d. | 0.64 | b.d. | 0.64 | b.d. | b.d. | 0.24 | 0.11 | b.d. | b.d. | 0.02 | b.d. | b.d. | 0.02 | b.d. | b.d. | 0.02 | b.d. | b.d. | b.d. | b.d. | |
| ETD 94/211 | | 94 | 0.93 | 0.27 | 0.02 | 0.02 | 4.66 | 0.12 | 0.04 | 0.43 | 0.09 | b.d. | b.d. | 0.01 | 0.04 | 0.02 | 0.01 | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | |
| ETD 94/212 | | 99 | b.d. | 0.32 | 0.03 | 0.03 | 0.04 | b.d. | b.d. | 0.43 | 0.09 | b.d. | b.d. | 0.01 | 0.04 | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | |
| ETD 94/241 | | 91 | 5.52 | 0.64 | 2.03 | 2.03 | 0.30 | 0.03 | 0.03 | 0.15 | 0.13 | 0.06 | 0.01 | 0.15 | 0.06 | 0.01 | 0.49 | 0.10 | 0.06 | 0.01 | 0.49 | 0.10 | 0.10 | 0.10 | |
| ETD 94/261 | | 99 | 0.04 | 0.43 | 0.18 | 0.18 | b.d. | b.d. | b.d. | 0.54 | 0.12 | 0.09 | b.d. | 0.04 | 0.12 | 0.09 | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | |
| ETD 94/284 | | 87 | 12.0 | 0.50 | 0.06 | 0.06 | 0.08 | b.d. | b.d. | 0.15 | 0.05 | 0.03 | b.d. | 0.15 | 0.05 | 0.03 | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | |
| ETD 94/330 | | 84 | 13.9 | 0.08 | 1.20 | 1.20 | b.d. | b.d. | b.d. | 0.79 | 0.18 | 0.14 | b.d. | 0.79 | 0.18 | 0.14 | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | |
| ETD 94/390 | | 86 | 12.2 | 0.76 | 0.37 | 0.06 | 0.06 | 0.01 | 0.01 | 0.49 | 0.09 | 0.24 | b.d. | 0.49 | 0.09 | 0.24 | b.d. | b.d. | b.d. | 0.04 | 0.04 | b.d. | b.d. | b.d. | |
| ETD 94/463 | | 86 | 3.07 | 0.29 | 0.02 | 4.34 | 0.02 | 0.52 | 0.02 | 0.77 | b.d. | b.d. | b.d. | 0.77 | b.d. | b.d. | 4.72 | b.d. | b.d. | 4.72 | b.d. | b.d. | b.d. | b.d. | |
| ETD 94/470 | | 93 | 5.99 | 0.48 | 0.14 | 0.14 | b.d. | b.d. | b.d. | 0.43 | 0.06 | 0.15 | b.d. | 0.43 | 0.06 | 0.15 | b.d. | b.d. | b.d. | 0.01 | 0.01 | b.d. | b.d. | b.d. | |
| ETD 94/475 | | 87 | 10.2 | 1.69 | 0.28 | 0.08 | 0.08 | b.d. | b.d. | 0.79 | 0.04 | 0.09 | 0.01 | 0.79 | 0.04 | 0.09 | 0.01 | 0.04 | 0.01 | 0.04 | 0.04 | b.d. | b.d. | b.d. | |
| ETD 94/483 | | 91 | 7.81 | 0.83 | 0.13 | 0.03 | 0.03 | 0.01 | 0.01 | 0.09 | 0.10 | 0.06 | b.d. | 0.09 | 0.10 | 0.06 | b.d. | b.d. | b.d. | 0.02 | 0.02 | b.d. | b.d. | b.d. | |
| ETD 94/5 | | 97 | 1.13 | 0.62 | 0.16 | 0.35 | 0.01 | 0.01 | 0.01 | 0.26 | 0.06 | b.d. | b.d. | 0.26 | 0.06 | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | |
| ETD 95/268 | | 91 | 8.18 | 0.44 | 0.38 | 0.18 | 0.18 | 0.01 | 0.01 | 0.10 | 0.09 | 0.03 | b.d. | 0.10 | 0.09 | 0.03 | b.d. | b.d. | b.d. | 0.02 | 0.02 | b.d. | b.d. | b.d. | |
| ETD 96/25 | | 82 | 17.0 | 0.24 | 0.36 | 0.04 | 0.04 | b.d. | b.d. | 0.12 | 0.20 | 0.07 | b.d. | 0.12 | 0.20 | 0.07 | b.d. | b.d. | b.d. | 0.08 | 0.08 | b.d. | b.d. | b.d. | |
| ETD 96/26 | | 88 | 7.52 | 0.74 | 2.11 | 0.03 | 0.03 | b.d. | b.d. | 1.19 | 0.08 | 0.09 | b.d. | 1.19 | 0.08 | 0.09 | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | |
| ETD 96/48 | | 98 | 0.42 | 1.06 | 0.14 | 0.14 | b.d. | b.d. | b.d. | 0.46 | b.d. | 0.01 | b.d. | 0.46 | b.d. | 0.01 | b.d. | b.d. | b.d. | 0.06 | 0.06 | b.d. | b.d. | b.d. | |
| ETD 96/49 | | 85 | 12.8 | 0.09 | 0.25 | 0.25 | b.d. | b.d. | b.d. | 1.15 | 0.15 | 0.13 | b.d. | 1.15 | 0.15 | 0.13 | b.d. | b.d. | b.d. | 0.06 | 0.06 | b.d. | b.d. | b.d. | |
| ETD 96/52 | | 98 | 0.03 | 0.70 | 0.55 | 0.15 | 0.15 | 0.05 | 0.05 | 0.58 | 0.05 | 0.05 | b.d. | 0.58 | 0.05 | 0.05 | b.d. | b.d. | b.d. | 0.03 | 0.03 | b.d. | b.d. | b.d. | |
| ETD 96/56 | | 99 | b.d. | 0.53 | 0.02 | 0.02 | b.d. | b.d. | b.d. | 0.47 | 0.08 | b.d. | b.d. | 0.47 | 0.08 | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | b.d. | |
| ETD 97/195 | | 95 | 3.12 | 0.74 | 0.04 | 0.04 | 0.04 | b.d. | b.d. | 0.43 | 0.06 | 0.17 | b.d. | 0.43 | 0.06 | 0.17 | b.d. | b.d. | b.d. | 0.07 | 0.07 | b.d. | b.d. | b.d. | |
| ETD 97/202A | | 99 | b.d. | 0.53 | 0.58 | 0.08 | 0.08 | b.d. | b.d. | 0.19 | b.d. | 0.02 | b.d. | 0.19 | b.d. | 0.02 | b.d. | b.d. | b.d. | 0.06 | 0.06 | b.d. | b.d. | b.d. | |
| ETD 97/202B | | 86 | 11.5 | 0.55 | 0.60 | 0.12 | 0.12 | 0.03 | 0.03 | 0.78 | 0.05 | 0.02 | b.d. | 0.78 | 0.05 | 0.02 | b.d. | b.d. | b.d. | 0.02 | 0.02 | b.d. | b.d. | b.d. | |
| ETD 97/209 | | 92 | 6.29 | 0.80 | 0.12 | 0.15 | 0.15 | b.d. | b.d. | 0.50 | 0.11 | 0.05 | b.d. | 0.50 | 0.11 | 0.05 | b.d. | b.d. | b.d. | 0.10 | 0.10 | b.d. | b.d. | b.d. | |
| ETD 97/211 | | 98 | 0.09 | 0.91 | 0.03 | 0.03 | b.d. | b.d. | b.d. | 0.54 | b.d. | 0.03 | 0.23 | 0.54 | b.d. | 0.03 | 0.23 | 0.05 | 0.05 | 0.05 | 0.05 | b.d. | b.d. | b.d. | |
| ETD 97/227 | | 96 | 0.05 | 2.21 | 0.34 | 0.39 | 0.39 | 0.04 | 0.04 | 0.46 | b.d. | 0.02 | 0.01 | 0.46 | b.d. | 0.02 | 0.01 | 0.04 | 0.04 | 0.04 | 0.04 | b.d. | b.d. | b.d. | |

| Mannheim Number | Object Number | Cu | | Sn | | As | | Pb | | Ni | | Co | | Fe | | Zn | | Sb | | Bi | | Ag | | Au | |
|--------------------|---------------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|
| | | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % | wt. % |
| ETD 97/231 | | 85 | 11.2 | 0.08 | 1.93 | b.d. | b.d. | 1.25 | 0.38 | 0.02 | 0.01 | 0.07 | b.d. | | | | | | | | | | | | |
| ETD 97/232 | | 86 | 12.4 | 0.52 | 0.81 | 0.07 | b.d. | 0.35 | 0.11 | 0.11 | b.d. | 0.03 | b.d. | | | | | | | | | | | | |
| ETD 97/234 | | 97 | 0.68 | 1.53 | 0.12 | 0.09 | b.d. | 0.67 | b.d. | 0.08 | 0.02 | 0.07 | b.d. | | | | | | | | | | | | |
| ETD 97/238 | | 90 | 8.67 | 0.79 | 0.32 | b.d. | 0.02 | 0.30 | 0.11 | 0.09 | b.d. | b.d. | b.d. | | | | | | | | | | | | |
| ETD 97/259 | | 90 | 8.22 | 0.95 | 0.15 | 0.04 | 0.01 | 0.52 | b.d. | 0.09 | b.d. | b.d. | b.d. | | | | | | | | | | | | |
| ETD 97/262 | | 89 | 9.53 | 0.59 | 0.38 | b.d. | 0.02 | 0.14 | b.d. | 0.10 | b.d. | 0.01 | b.d. | | | | | | | | | | | | |
| ETD 97/269 | | 85 | 13.2 | 0.08 | 0.23 | b.d. | b.d. | 0.93 | 0.16 | 0.12 | b.d. | 0.07 | b.d. | | | | | | | | | | | | |
| ETD 97/271 | | 89 | 8.95 | 0.64 | 0.83 | 0.06 | b.d. | 0.30 | 0.08 | 0.06 | b.d. | 0.11 | b.d. | | | | | | | | | | | | |
| ETD 97/272 | | 97 | 0.13 | 0.04 | 1.13 | b.d. | b.d. | 1.06 | 0.08 | b.d. | b.d. | 0.53 | b.d. | | | | | | | | | | | | |
| ETD 97/341 | | 89 | 8.49 | 0.14 | 1.90 | 0.02 | b.d. | 0.11 | 0.27 | 0.10 | 0.03 | 0.12 | b.d. | | | | | | | | | | | | |
| ETD 98/08 | | 85 | 13.5 | 0.37 | 0.74 | 0.06 | b.d. | 0.19 | 0.16 | 0.13 | b.d. | 0.08 | b.d. | | | | | | | | | | | | |
| ETD 98/10 | | 97 | 0.05 | 1.22 | 0.05 | 0.72 | 0.02 | 0.38 | 0.04 | 0.12 | 0.01 | 0.05 | b.d. | | | | | | | | | | | | |
| ETD 98/20 | | 84 | 14.4 | 0.60 | 0.82 | 0.08 | b.d. | 0.15 | b.d. | 0.12 | b.d. | b.d. | b.d. | | | | | | | | | | | | |
| ETD 98/26 | | 99 | 0.08 | 0.08 | 0.02 | b.d. | b.d. | 0.92 | 0.18 | 0.02 | 0.01 | 0.06 | b.d. | | | | | | | | | | | | |
| Bo 12/08 | | 82 | 16.7 | 0.05 | b.d. | 0.03 | b.d. | 1.18 | 0.16 | b.d. | b.d. | 0.02 | b.d. | | | | | | | | | | | | |
| Bo 13/103 | | 83 | 16.0 | b.d. | b.d. | 0.30 | b.d. | 0.39 | 0.07 | b.d. | b.d. | 0.15 | b.d. | | | | | | | | | | | | |
| Bo 13/29 | | 81 | 17.6 | 0.27 | 0.05 | 0.57 | b.d. | 0.26 | 0.12 | b.d. | b.d. | 0.13 | b.d. | | | | | | | | | | | | |
| Bo 13/6 | | 87 | 12.4 | b.d. | b.d. | 0.31 | b.d. | 0.53 | b.d. | b.d. | b.d. | 0.12 | b.d. | | | | | | | | | | | | |
| Bo 09/1064 | | 79 | 18.3 | 0.53 | 0.68 | 0.38 | 0.01 | 0.39 | 0.21 | 0.03 | b.d. | 0.04 | b.d. | | | | | | | | | | | | |
| Bo 09/1712 | | 80 | 16.0 | 0.22 | 2.94 | 0.09 | b.d. | 0.66 | 0.22 | 0.03 | 0.15 | 0.04 | b.d. | | | | | | | | | | | | |
| Bo 11/35 | | 79 | 19.3 | 0.22 | 0.36 | 0.03 | b.d. | 0.22 | 0.26 | 0.24 | 0.01 | 0.19 | b.d. | | | | | | | | | | | | |
| Bo 13/10 | | 84 | 14.6 | 0.10 | 0.09 | 0.06 | b.d. | 0.64 | 0.25 | b.d. | b.d. | 0.17 | b.d. | | | | | | | | | | | | |
| Bo 13/113 | | 79 | 19.2 | 0.28 | 0.66 | b.d. | b.d. | 0.36 | 0.28 | 0.12 | b.d. | 0.21 | b.d. | | | | | | | | | | | | |
| Bo 13/119 | | 92 | 6.64 | 0.86 | 0.04 | 0.09 | b.d. | 0.17 | 0.11 | 0.03 | b.d. | 0.15 | b.d. | | | | | | | | | | | | |
| Bo 13/130 | | 87 | 10.9 | 0.03 | 0.07 | 0.10 | b.d. | 1.19 | 0.55 | b.d. | b.d. | 0.06 | b.d. | | | | | | | | | | | | |
| Bo 13/198 | | 96 | 2.93 | 0.07 | 0.04 | b.d. | b.d. | 0.33 | 0.14 | b.d. | 0.01 | 0.16 | b.d. | | | | | | | | | | | | |
| Bo 13/42 | | 75 | 23.8 | 0.08 | 0.74 | b.d. | b.d. | 0.19 | 0.22 | 0.07 | b.d. | 0.21 | b.d. | | | | | | | | | | | | |
| Bo 13/65 | | 96 | 0.04 | 0.54 | 0.22 | 0.05 | b.d. | 2.91 | 0.29 | 0.03 | 0.02 | 0.06 | b.d. | | | | | | | | | | | | |

| Mannheim Number | Object Number | Cu wt. % | Sn wt. % | As wt. % | Pb wt. % | Ni wt. % | Co wt. % | Fe wt. % | Zn wt. % | Sb wt. % | Bi wt. % | Ag wt. % | Au wt. % |
|------------------|---------------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|
| | Bo 13/97 | 88 | 10.0 | 0.36 | 0.28 | b.d. | b.d. | 0.39 | 0.93 | 0.06 | b.d. | 0.11 | b.d. |
| MA-132561 | Bo 554/p | 88 | 10.3 | 0.23 | 0.38 | b.d. | b.d. | 0.26 | 0.10 | 0.20 | b.d. | 0.06 | b.d. |
| | Bo 73/57b | 86 | 13.4 | 0.05 | 0.21 | 0.12 | 0.01 | 0.16 | 0.26 | b.d. | b.d. | 0.06 | b.d. |
| | Bo 73/57c | 90 | 8.94 | 0.17 | 0.69 | 0.05 | b.d. | 0.10 | 0.13 | 0.12 | b.d. | 0.05 | b.d. |
| | Bo 73/59b | 84 | 12.1 | 0.03 | b.d. | 3.32 | 0.42 | 0.52 | 0.14 | b.d. | b.d. | b.d. | b.d. |
| | Bo 73/59c | 84 | 11.1 | 0.06 | b.d. | 3.36 | 0.50 | 0.61 | 0.05 | b.d. | b.d. | b.d. | b.d. |
| | Bo 73/59d | 89 | 10.3 | 0.46 | b.d. | 0.09 | b.d. | 0.11 | 0.10 | b.d. | b.d. | 0.03 | b.d. |
| | Bo 73/77 | 89 | 10.1 | 0.18 | 0.01 | 0.24 | b.d. | 0.13 | 0.15 | 0.05 | b.d. | 0.05 | b.d. |
| | Bo 99/17 | 64 | 27.6 | 0.32 | 5.48 | 0.64 | b.d. | 1.85 | 0.31 | 0.12 | 0.04 | 0.03 | b.d. |
| | Bo 99/18 | 92 | 4.64 | b.d. | 2.05 | b.d. | b.d. | 0.70 | 0.11 | b.d. | 0.11 | 0.05 | b.d. |
| | Bo 99/19 | 90 | 6.19 | b.d. | 2.14 | 0.75 | 0.03 | 0.66 | 0.09 | b.d. | b.d. | 0.02 | b.d. |
| | ETD 99/61 | 88 | 11.1 | 0.10 | 0.02 | b.d. | b.d. | 0.89 | 0.06 | b.d. | 0.02 | 0.02 | b.d. |
| | ETD 99/62 | 84 | 14.5 | b.d. | 0.01 | 0.54 | 0.03 | 0.45 | b.d. | b.d. | b.d. | b.d. | b.d. |
| | ETD 99/63 | 82 | 15.8 | 0.23 | 0.19 | 0.07 | b.d. | 1.20 | 0.11 | b.d. | b.d. | 0.02 | b.d. |
| | ETD 99/64 | 92 | 5.59 | 0.13 | 0.83 | b.d. | b.d. | 1.07 | 0.09 | b.d. | 0.08 | b.d. | b.d. |
| | ETD 99/65 | 84 | 13.5 | b.d. | 2.09 | 0.03 | b.d. | 0.03 | b.d. | b.d. | b.d. | 0.03 | b.d. |
| | ETD 99/66 | 88 | 11.2 | 0.22 | 0.56 | 0.02 | b.d. | 0.19 | 0.05 | 0.10 | b.d. | 0.05 | b.d. |
| | ETD 99/77 | 85 | 14.1 | 0.02 | b.d. | 0.40 | b.d. | 0.36 | 0.10 | b.d. | b.d. | b.d. | b.d. |
| | ETD 99/91 | 89 | 8.90 | 0.05 | 0.04 | 1.11 | 0.12 | 0.29 | 0.06 | b.d. | b.d. | 0.02 | b.d. |
| | Bo 07/566 | 55 | 36.3 | b.d. | 7.45 | 0.05 | b.d. | 0.50 | 0.60 | 0.49 | b.d. | 0.05 | b.d. |
| | ETD 96/11 | 84 | 13.0 | 0.08 | 2.39 | b.d. | b.d. | 0.34 | 0.07 | 0.07 | b.d. | 0.04 | b.d. |
| | ETD 96/55 | 83 | 2.34 | 0.61 | 12.25 | b.d. | b.d. | 0.96 | b.d. | 0.24 | 0.22 | 0.06 | b.d. |
| | Bo 88/37 | 55 | 40.6 | 0.38 | 1.93 | 0.30 | b.d. | 0.93 | 0.22 | b.d. | b.d. | 0.14 | b.d. |
| | 1-3-88 | 84 | 12.3 | 0.28 | 2.48 | 0.82 | b.d. | 0.14 | 0.14 | 0.03 | b.d. | 0.03 | b.d. |
| | 1-2430-91 | 61 | 30.0 | 0.14 | 1.38 | 0.24 | b.d. | 2.38 | 4.41 | b.d. | 0.02 | 0.17 | b.d. |
| | Bo 89/128 | 76 | 18.5 | 0.39 | 4.50 | b.d. | b.d. | 0.15 | 0.05 | 0.02 | 0.03 | b.d. | b.d. |
| | Bo 89/29 | 89 | 10.3 | 0.05 | 0.04 | 0.06 | 0.01 | 0.08 | 0.10 | 0.03 | b.d. | 0.17 | b.d. |
| | Bo 89/29 | 99 | 0.44 | 0.05 | 0.02 | b.d. | 0.02 | 0.16 | b.d. | b.d. | b.d. | 0.15 | b.d. |

| Mannheim Number | Object Number | Cu wt. % | Sn wt. % | As wt. % | Pb wt. % | Ni wt. % | Co wt. % | Fe wt. % | Zn wt. % | Sb wt. % | Bi wt. % | Ag wt. % | Au wt. % |
|----------------------|----------------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|
| | Bo 89/31 | 90 | 8.96 | 0.39 | 0.12 | 0.08 | b.d. | 0.33 | b.d. | 0.06 | b.d. | 0.32 | b.d. |
| | Bo 89/99 | 99 | 0.03 | 0.62 | 0.04 | 0.07 | 0.01 | 0.42 | b.d. | 0.03 | b.d. | 0.14 | b.d. |
| | 1-106-85 | 56 | 20.4 | 1.07 | 19.45 | 0.76 | b.d. | 1.56 | 0.24 | 0.20 | 0.04 | b.d. | b.d. |
| | 1-42-88 | 95 | 0.09 | 1.06 | 3.44 | 0.04 | b.d. | 0.09 | b.d. | 0.04 | b.d. | 0.04 | 0.03 |
| | 1-85-89 | 88 | 5.86 | 0.66 | 2.47 | 0.10 | 0.05 | 2.35 | 0.10 | b.d. | 0.02 | 0.02 | b.d. |
| | 1-1990-81 | 84 | 14.8 | 0.89 | 0.09 | 0.09 | b.d. | 0.17 | 0.07 | 0.18 | b.d. | 0.23 | b.d. |
| | Bo 05/28 | 90 | 6.98 | 0.43 | 0.86 | 0.12 | b.d. | 1.21 | 0.23 | 0.11 | 0.03 | b.d. | b.d. |
| MA-132512 | Bo 06/561 | 71 | 27.2 | 0.52 | 0.26 | 0.23 | b.d. | 0.78 | 0.26 | 0.08 | b.d. | 0.06 | b.d. |
| | Bo 07/1325 | 84 | 15.4 | 0.17 | 0.01 | 0.14 | b.d. | 0.21 | 0.04 | b.d. | b.d. | b.d. | b.d. |
| | Bo 07/508 | 70 | 28.9 | b.d. | 0.20 | b.d. | 0.18 | 0.74 | 0.13 | 0.05 | b.d. | 0.04 | b.d. |
| KERKENES DAĞ | | | | | | | | | | | | | |
| LATE IRON AGE | | | | | | | | | | | | | |
| | 00CT11U01met01 | 92 | 6.60 | 0.33 | 0.42 | 0.36 | b.d. | 0.28 | b.d. | b.d. | b.d. | 0.03 | b.d. |
| | 00CT50U02met01 | 89 | 9.40 | 0.16 | 0.45 | 0.18 | b.d. | 0.83 | b.d. | b.d. | b.d. | 0.04 | b.d. |
| | 00CT51U01met01 | 88 | 10.1 | 0.13 | 1.04 | 0.33 | b.d. | 0.20 | b.d. | b.d. | b.d. | 0.03 | b.d. |
| | 02TR04U04met03 | 90 | 8.35 | 0.05 | 0.30 | 1.06 | b.d. | 0.24 | b.d. | b.d. | b.d. | 0.04 | b.d. |
| | 09CAPPU00met01 | 92 | 6.50 | 0.10 | 0.19 | 0.65 | b.d. | 0.47 | b.d. | b.d. | b.d. | 0.02 | b.d. |
| | 10TR13U16met01 | 79 | 14.5 | b.d. | 6.03 | 0.29 | b.d. | 0.24 | b.d. | b.d. | b.d. | 0.04 | b.d. |
| | 11TR23U36met01 | 86 | 13.2 | 0.05 | 0.25 | 0.13 | b.d. | 0.07 | b.d. | b.d. | b.d. | 0.03 | b.d. |
| | 11TR24U06met01 | 76 | 19.1 | 0.07 | 3.50 | 0.25 | b.d. | 0.19 | b.d. | 0.43 | b.d. | 0.03 | b.d. |
| | 11TR30U10met01 | 69 | 23.9 | 0.06 | 6.49 | 0.19 | b.d. | 0.16 | b.d. | b.d. | b.d. | 0.10 | b.d. |
| | 03TR06U12met01 | 82 | 3.97 | b.d. | 14.05 | 0.22 | b.d. | 0.09 | b.d. | b.d. | 0.07 | 0.04 | b.d. |
| | 02TR01U02met04 | 84 | 15.5 | 0.03 | 0.19 | 0.31 | 0.03 | 0.25 | b.d. | b.d. | b.d. | 0.03 | b.d. |
| | 02TR01U07met01 | 81 | 9.90 | 0.04 | 0.37 | 0.20 | b.d. | 1.46 | 7.27 | b.d. | b.d. | 0.05 | b.d. |
| | 02TR01U07met02 | 76 | 13.3 | 0.04 | 0.37 | 0.17 | b.d. | 1.89 | 8.00 | b.d. | b.d. | 0.06 | b.d. |
| | 02TR02U04met01 | 98 | 1.32 | 0.05 | 0.39 | 0.05 | 0.01 | 0.11 | b.d. | b.d. | b.d. | 0.06 | b.d. |
| | 02TR02U10met08 | 88 | 9.86 | 0.06 | 0.13 | 1.10 | 0.12 | 0.28 | b.d. | b.d. | b.d. | 0.03 | b.d. |

| Mannheim Number | Object Number | Cu wt. % | Sn wt. % | As wt. % | Pb wt. % | Ni wt. % | Co wt. % | Fe wt. % | Zn wt. % | Sb wt. % | Bi wt. % | Ag wt. % | Au wt. % |
|------------------|----------------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|----------|
| | 02TR02U10met09 | 88 | 10.9 | 0.10 | 0.39 | 0.22 | b.d. | 0.47 | b.d. | b.d. | b.d. | 0.04 | b.d. |
| | 02TR02U10met11 | 81 | 9.16 | 0.03 | 0.25 | 0.21 | b.d. | 1.37 | 7.79 | b.d. | b.d. | 0.04 | b.d. |
| | 02TR05U13met01 | 63 | b.d. | b.d. | 0.41 | 0.45 | b.d. | 0.46 | b.d. | b.d. | 0.34 | 35.18 | 0.16 |
| | 03TR05U02met03 | 91 | 8.06 | 0.22 | 0.49 | 0.35 | b.d. | 0.42 | b.d. | b.d. | b.d. | 0.03 | b.d. |
| | 04TR16U15met03 | 83 | 14.7 | 0.23 | 1.14 | 0.06 | b.d. | 0.09 | 0.72 | 0.06 | 0.01 | 0.08 | b.d. |
| | 05TR15U09met01 | 83 | b.d. | b.d. | 0.20 | 0.57 | b.d. | 1.15 | b.d. | b.d. | 0.12 | 14.50 | 0.09 |
| | 05TR15U14met02 | 81 | 18.1 | 0.07 | 0.23 | 0.17 | b.d. | 0.21 | b.d. | b.d. | b.d. | 0.03 | b.d. |
| | 05TR16U17met02 | 98 | 1.41 | 0.12 | 0.24 | 0.13 | b.d. | 0.09 | b.d. | 0.04 | b.d. | 0.02 | b.d. |
| | 05TR16U17met03 | 85 | 13.7 | 0.28 | 0.98 | 0.11 | b.d. | 0.15 | 0.05 | 0.17 | b.d. | 0.15 | b.d. |
| | 05TR17U12met01 | 84 | 7.55 | 0.09 | 0.32 | 0.32 | b.d. | 1.88 | 5.86 | b.d. | 0.02 | 0.02 | b.d. |
| | 05TR17U14met01 | 81 | 11.5 | 0.35 | 0.38 | 0.08 | b.d. | 0.56 | 5.74 | 0.11 | 0.02 | 0.07 | b.d. |
| | 05TR17U14met01 | 83 | 13.4 | 0.15 | 0.92 | 0.29 | b.d. | 0.96 | 1.37 | b.d. | b.d. | 0.03 | b.d. |
| MA-132627 | 05TR17U14met02 | 87 | 12.1 | 0.03 | 0.05 | 0.26 | 0.05 | 0.35 | b.d. | b.d. | b.d. | 0.03 | b.d. |
| | 05TR17U14met06 | 87 | 11.7 | 0.01 | 0.09 | 0.31 | 0.05 | 0.39 | b.d. | b.d. | b.d. | 0.03 | b.d. |
| | 05TR21U12met01 | 87 | 12.6 | 0.03 | 0.13 | 0.23 | 0.02 | 0.17 | b.d. | b.d. | b.d. | 0.02 | b.d. |
| | 05TR21U17met01 | 86 | 12.7 | 0.02 | 0.26 | 0.17 | b.d. | 0.56 | b.d. | b.d. | b.d. | 0.02 | b.d. |
| | 96TT17U05met01 | 87 | 12.9 | 0.22 | 0.10 | 0.20 | b.d. | 0.16 | b.d. | b.d. | b.d. | b.d. | b.d. |
| | 96ST05U07met02 | 92 | 7.43 | 0.40 | 0.19 | 0.14 | b.d. | 0.35 | b.d. | 0.03 | b.d. | 0.02 | b.d. |

APPENDIX D: LEAD ISOTOPE ANALYSIS RESULTS

Lead isotope analysis is an accepted method in archaeology to determine the provenance of several classes of materials, including many metals (Pernicka 2014: 247). The element lead (Pb) has four stable isotopes ^{208}Pb , ^{207}Pb , ^{206}Pb , and ^{204}Pb . Of these four isotopes, only ^{204}Pb is non-radiogenic where ^{208}Pb , ^{207}Pb and ^{206}Pb are formed by the regular decay of ^{232}Th , ^{235}U and ^{238}U respectively (Allègre 2008: 294-312). The unique relationship among these four isotopes of lead, which are often expressed in ratios, theoretically allow for the calculation of geological age based on principles of radiometric geochronology (ex. U-Pb and Pb-Pb dating). The specificity of lead isotope ratios coupled with the fact that ultra-trace amounts of lead occur in many materials, including most if not all archaeological metals, allows for a robust and relatively straightforward way to ascertain material alteration, transport and provenience (Aggarwal, et al. 2008: 2662). There exist three important conditions concerning the study of lead isotopes to characterize sources and artifacts:

- 1.) The relative concentrations of these four isotopes are assumed to have been uniform throughout the earth at the time it was formed;
- 2.) Isotopes ^{208}Pb , ^{207}Pb , and ^{206}Pb have continued to be formed on earth from the radioactive decay of uranium and thorium. Therefore, naturally occurring lead is composed of a diagnostic mixture of radiogenic and original terrestrial lead

3.) Ratios of lead isotopes vary depending on the geological age of the ore body and the conditions under which it mineralizes, the proportions of which vary among geological formations (Guilbert and Park 2007: 286-290).

Additionally, because different ore sources often have unique lead isotope ratios according to a specific geological origin, *variation among different sources can in some cases be greater than variation within sources* (Weigand, et al. 1977). Under these conditions, the isotopic analyses of metal objects and metal-rich residues, which often contain measurable amounts of lead, can be compared to lead isotopes from known ore sources (Brill and Wampler 1967; Gale and Stos-Gale 1982; Grögler, et al. 1966). Strong similarities among artifacts and ore sources can be used as evidence for their provenance.

While much debate and contention surrounds the nature of artifact-ore relationships and how one ascertains these relationships (Budd, et al. 1996; Budd, et al. 1993; Gale 2001; Knapp 2000) for the purposes of this study, I will judge artifact-ore relationships in terms of source discrimination. Since geographically distinct ore sources can have very similar lead isotope ratios, similarity in isotope ratios does not necessarily equate to congruity in artifact-ore relationships (Pollard, et al. 2007: 17). For this reason, this study aims to eliminate as many conceivably utilized sources as possible based on their isotopic signatures.

Artifact samples were carefully selected and prepared in the laboratory to avoid cross contamination. For non-drilling samples, all surfaces were mechanically abraded using clean, lead-free silica polish and set aside. Samples were further prepared for chemical separation and lead purification for analysis by MC-ICPMS using methods described in Höppner et al. (2005: 303) and Niederschlag et al. (2003).

Comparative lead isotope data for ores used in this study are previously published. These data were generated by decades of research by the Oxford group (Gale, et al. 1997; Gale, et al. 1985; Rohl 1996; Stos-Gale and Gale 2009; Stos-Gale, et al. 1996; Stos-Gale, et al. 1998; Stos-Gale, et al. 1995; Stos-Gale, et al. 1984), the Heidelberg group (Lutz, et al. 1994; Pernicka, et al. 1984; Seeliger, et al. 1985; Wagner, et al. 1986, 1989; Wagner, et al. 2003; Wagner and Öztunalı 2000; Wagner, et al. 1985), research at the Smithsonian Institute (Sayre, et al. 2001; Sayre, et al. 1992; Yener, et al. 1991), the Deutsches Bergbau-Museum (Yalçın and Maass 2013), and select analyses by the Tokyo group (Hirao, et al. 1995).

| Mannheim Number | Find Number | Site | $^{208}\text{Pb}/^{206}\text{Pb}$ | | $^{207}\text{Pb}/^{206}\text{Pb}$ | | $^{206}\text{Pb}/^{204}\text{Pb}$ | | $^{208}\text{Pb}/^{204}\text{Pb}$ | | $^{207}\text{Pb}/^{204}\text{Pb}$ | |
|-----------------|----------------|--------------|-----------------------------------|--|-----------------------------------|--|-----------------------------------|--|-----------------------------------|--|-----------------------------------|--|
| | | | mean | | mean | | mean | | calc mean | | calc mean | |
| MA-132200 | Bo 06/253 | Boğazköy | 2.0783 | | 0.83986 | | 38.663 | | 15.624 | | 18.603 | |
| MA-132303 | Bo 11/590 | Boğazköy | 2.0652 | | 0.83282 | | 38.813 | | 15.652 | | 18.794 | |
| MA-132443 | Bo 06/1837 | Boğazköy | 2.0648 | | 0.83068 | | 38.837 | | 15.624 | | 18.809 | |
| MA-132185 | Bo 170/h | Boğazköy | 2.0717 | | 0.83543 | | 38.878 | | 15.678 | | 18.766 | |
| MA-132306 | Bo 06/1397 | Boğazköy | 2.0746 | | 0.83682 | | 38.762 | | 15.635 | | 18.684 | |
| MA-132389 | Bo 06/500 | Boğazköy | 2.0758 | | 0.83782 | | 38.674 | | 15.609 | | 18.631 | |
| MA-132439 | Bo 06/1751 | Boğazköy | 2.0729 | | 0.83589 | | 38.765 | | 15.632 | | 18.701 | |
| MA-132188 | Bo 284/e | Boğazköy | 2.0566 | | 0.82708 | | 39.051 | | 15.705 | | 18.988 | |
| MA-132204 | Bo 08/9 | Boğazköy | 2.0714 | | 0.83522 | | 38.746 | | 15.623 | | 18.705 | |
| MA-132190 | Bo 216/p | Boğazköy | 2.0714 | | 0.83523 | | 38.741 | | 15.621 | | 18.703 | |
| MA-132198 | Bo 08/24 | Boğazköy | 2.0706 | | 0.83530 | | 38.822 | | 15.661 | | 18.749 | |
| MA-132199 | Bo 08/101 | Boğazköy | 2.0714 | | 0.83636 | | 38.820 | | 15.674 | | 18.741 | |
| MA-132307 | Bo 06/492 | Boğazköy | 2.0607 | | 0.83129 | | 38.819 | | 15.660 | | 18.838 | |
| MA-132309 | Bo 06/189 | Boğazköy | 2.0722 | | 0.83955 | | 38.485 | | 15.592 | | 18.572 | |
| MA-132178 | Bo 84/551 | Boğazköy | 2.0580 | | 0.82847 | | 38.962 | | 15.685 | | 18.932 | |
| MA-132182 | Bo 82/138 | Boğazköy | 2.0568 | | 0.82763 | | 38.989 | | 15.689 | | 18.956 | |
| MA-132183 | Bo 171/h | Boğazköy | 2.0715 | | 0.83753 | | 38.660 | | 15.631 | | 18.663 | |
| MA-132191 | Bo 864/t | Boğazköy | 2.0761 | | 0.83916 | | 38.659 | | 15.626 | | 18.621 | |
| MA-132194 | Bo 861/t | Boğazköy | 2.0706 | | 0.83448 | | 38.954 | | 15.699 | | 18.813 | |
| MA-132444 | Bo 06/1601 | Boğazköy | 2.0557 | | 0.82711 | | 39.001 | | 15.692 | | 18.972 | |
| MA-132476 | Bo 06/1742 | Boğazköy | 2.0671 | | 0.83352 | | 38.851 | | 15.666 | | 18.795 | |
| MA-132180 | Bo 477/d | Boğazköy | 2.0582 | | 0.82735 | | 39.036 | | 15.692 | | 18.966 | |
| MA-132591 | 02TR03U11met02 | Kerkenes Dağ | 2.0475 | | 0.82848 | | 38.591 | | 15.615 | | 18.848 | |
| MA-132594 | 11TR23U22met01 | Kerkenes Dağ | 2.0774 | | 0.83848 | | 38.766 | | 15.647 | | 18.661 | |
| MA-132596 | 11TR24U22met08 | Kerkenes Dağ | 2.0630 | | 0.83272 | | 38.867 | | 15.688 | | 18.840 | |
| MA-132604 | 00CT18U17met02 | Kerkenes Dağ | 2.0738 | | 0.83673 | | 38.801 | | 15.655 | | 18.710 | |
| MA-132605 | 11TR24U22met07 | Kerkenes Dağ | 2.0633 | | 0.83313 | | 38.819 | | 15.675 | | 18.814 | |
| MA-132606 | 11TR24U21met01 | Kerkenes Dağ | 2.0861 | | 0.84550 | | 38.497 | | 15.603 | | 18.454 | |

| Mannheim Number | Find Number | Site | $^{208}\text{Pb}/^{206}\text{Pb}$ | | $^{207}\text{Pb}/^{206}\text{Pb}$ | | $^{206}\text{Pb}/^{204}\text{Pb}$ | | $^{208}\text{Pb}/^{204}\text{Pb}$ | | $^{207}\text{Pb}/^{204}\text{Pb}$ | |
|--------------------|------------------------|--------------|-----------------------------------|---------|-----------------------------------|--------|-----------------------------------|--|-----------------------------------|--|-----------------------------------|--|
| | | | mean | | mean | | mean | | calc mean | | calc mean | |
| MA-132608 | 11TR24U15.met01 | Kerkenes Dağ | 2.0793 | 0.83976 | 38.721 | 15.638 | 18.622 | | | | | |
| MA-132614 | 11TR24U22.met06 | Kerkenes Dağ | 2.0655 | 0.83387 | 38.802 | 15.665 | 18.786 | | | | | |
| MA-132619 | 11TR24U22.met03 | Kerkenes Dağ | 2.0789 | 0.84021 | 38.720 | 15.649 | 18.625 | | | | | |
| MA-132621 | 11TR29U34.met02 | Kerkenes Dağ | 2.0822 | 0.84304 | 38.481 | 15.580 | 18.481 | | | | | |
| MA-132622 | 11TR24U22.met04 | Kerkenes Dağ | 2.0782 | 0.84669 | 38.116 | 15.529 | 18.341 | | | | | |
| MA-132623 | 11TR29U14.met02 | Kerkenes Dağ | 2.1100 | 0.85855 | 38.016 | 15.468 | 18.017 | | | | | |
| MA-132624 | 11TR24U20.met01 | Kerkenes Dağ | 2.0722 | 0.83670 | 38.870 | 15.695 | 18.758 | | | | | |
| MA-132626 | 11TR24U11.met03(tack) | Kerkenes Dağ | 2.0926 | 0.85090 | 38.447 | 15.634 | 18.373 | | | | | |
| MA-132615 | 11TR24U11.met03(sheet) | Kerkenes Dağ | 2.0838 | 0.84779 | 38.398 | 15.622 | 18.427 | | | | | |
| MA-132631 | 11TR24U11.met02 | Kerkenes Dağ | 2.0485 | 0.82551 | 38.809 | 15.639 | 18.945 | | | | | |

REFERENCES

- Adams, R. McC.
1974 Anthropological Perspectives on Ancient Trade. *Current Anthropology* 15:239-249.
-
- 1981 *The Heartland of Cities*. Chicago: University of Chicago Press.
- Adriaens, A., B. Earl, Hadi Özbal, and K. Aslihan Yener
2002 Tin Bronze Metallurgy in Transformation: Analytical Investigation of Crucible Fragments from Tell al-Judaidah, Amuq (Turkey) Dating to Circa 3000-2900 BC. In *Archaeometry* 98. E. Jerem and K.T. Biró, eds. Pp. 273-277. BAR International Series 1043, Vol. II. Oxford: Archaeopress.
- Adriaens, A., P. Veny, F. Adams, R. Sporcken, P. Louette, B. Earl, Hadi Özbal, and K. Aslihan Yener
1999a Analytical Investigation of Archaeological Powders from Göltepe (Turkey). *Archaeometry* 41(1):81-89.
- Adriaens, A., K. Aslihan Yener, and F. Adams
1996 Surface Analysis of Early Bronze Age Ceramic Crucibles from Göltepe, Turkey. In *The Proceedings of the 6th European Conference on Applications of Surface and Interface Analysis*. H.J. Mathieu, B. Reihl, and D. Briggs, eds. Pp. 123-126. Chichester and New York: Wiley & Sons.
-
- 1999b An Analytical Study Using Electron and Ion Microscopy of Thin-walled Crucibles from Göltepe, Turkey. *Journal of Archaeological Science* 26(8):1069-1073.
- Adriaens, A., K. Aslihan Yener, F. Adams, and R. Levi-Setti
1997 SIMS Analyses of Ancient Ceramic Crucibles and Slags from Turkey. In *Tenth International Conference on Secondary Ion Mass Spectrometry SIMS X*. A. Benninghoven, B. Hagenhoff, and H.W. Werner, eds. Pp. 877-880. Chichester and New York: Wiley & Sons.
- Aggarwal, Jugdeep, Judith Habicht-Mauche, and Chelsey Juarez
2008 Application of Heavy Stable Isotopes in Forensic Isotope Geochemistry: A Review. *Applied Geochemistry* 23:2658-2666.
- Akanuma, Hideo
2006 Changes in Iron Use during the 2nd and 1st Millennia B.C. at Kaman-Kalehöyük, Turkey: Composition of Iron Artifacts from Stratum III and Stratum II. *Anatolian Archaeological Studies* 15:207-222.
- Alaura, Silvia
2006 *"Nach Boghasköi!" Zur Vorgeschichte der Ausgrabungen in Boğazköy-Hattuša und zu den archäologischen Forschungen bis zum Ersten Weltkrieg*. Berlin: Harrasowitz.
- Alcock, Susan E., Terence N. D'Altroy, Kathleen D. Morrison, and Carla M. Sinopoli, eds.
2001 *Empires: Perspectives from Archaeology and History*. Cambridge: Cambridge University Press.
- Aldenderfer, Mark S.
1998 *Montane Foragers: Asana and the South-Central Andean Archaic*. Iowa City: University of Iowa Press.

- Algaze, Guillermo
 1993 Expansionary Dynamics of Some Early Pristine States. *American Anthropologist* 95(2):304-333.
- 2005 *The Uruk World System: The Dynamics of Expansion of Early Mesopotamian Civilization*. Chicago: The University of Chicago Press.
- 2008 *Ancient Mesopotamia at the Dawn of Civilization: The Evolution of an Urban Landscape*. Chicago: University of Chicago Press.
- Allègre, Claude J.
 2008 *Isotope Geology*. C. Sutcliffe, transl. Cambridge: Cambridge University Press.
- Alp, Sedat
 1980 Die hethitischen Tontafelentdeckungen auf dem Maşat-Höyük: Vorläufiger Bericht. *Belleten* XLIV:25-59.
- Alparslan, Metin
 2005 Der Handel im Hethiterreich: Ein Interpretationsversuch nach den hethitischen Quellen. In *Das Schiff von Uluburun: Welthandel vor 3000 Jahren*. Ü. Yalçın, C. Pulak, and R. Slotta, eds. Pp. 381-383. Bochum: Deutsches Bergbau-Museum.
- Arbuckle, Benjamin
 2012 Pastoralism, Provisioning and Power at Bronze Age Acemhöyük, Turkey. *American Anthropologist* 114(3):462-476.
- Arik, Remzi Oguz
 1937 *Les fouilles d'Alaca Höyük*. Ankara: Türk Tarih Kurumu.
- Arnold, Jeanne
 1996 Organizational Transformations: Power and Labor among Complex Hunter-Gatherers and Other Intermediate Societies. In *Emergent Complexity: The Evolution of Intermediate Societies*. J. Arnold, ed. Pp. 59-73. Ann Arbor: International Monographs in Prehistory.
- Arsebük, G.
 1986 An Assemblage of Microlithic Engravers from the Chalcolithic Levels of Değirmentepe (Malatya). *Jahrbuch für Kleinasiatische Forschungen* 10:132-142.
- Aruz, Joan
 2006 Central Anatolia and the Aegean (2650-1700 B.C.): Beads, Seals, and Ivories: Enhancing the Case for Interaction. In *Studies in Honor of Hayat Erkanal: Cultural Reflections*. A. Erkanal-Öktü, E. Özgen, S. Günel, A.T. Ökse, H. Hürüymaz, H. Tekin, N. Çınardalı-Karaaslan, B. Uysal, A. Karaduman, A. Engin, R. Spieß, A. Aykurt, R. Tuncel, U. Deniz, and A. Rennie, eds. Pp. 48-58. Istanbul: Homer.
- Atasoy, Ertuğrul, and Sevim Buluç
 1982 Metallurgical and Archaeological Examination of Phrygian Objects. *Anatolian Studies* 32:157-160.
- Atici, Levent
 2014 Tracing Inequality from Assur to Kültepe/Kanesh: Merchants, Donkeys, and Clay Tablets. In *Animals and Inequality in the Ancient World*. B. Arbuckle and S.A. McCarty, eds. Pp. 233-252. Boulder: University Press of Colorado.
- Axelrod, Robert
 1984 *The Evolution of Cooperation*. New York: Basic Books.

- Axelrod, Robert, and W. D. Hamilton
1981 The Evolution of Cooperation. *Science* 211(4489):1390-1396.
- Bachhuber, Chris S.
2006 Aegean Interest on the Uluburun Ship. *American Journal of Archaeology* 110(3):345-363.
- 2008 *Sumptuary Behavior in Early Bronze Age Anatolia: The Royal Tombs of Alacahöyük and the Treasure Deposits of Troy*, University of Oxford.
- Bachhuber, Christopher
2011 Negotiating Metal and Metal Form in the Royal Tombs of Alacahöyük in North-Central Anatolia. In *Interweaving Worlds: Systemic Interactions in Eurasia, 7th to 1st Millennium BC*. T.C. Wilkinson, S. Sherratt, and J. Bennet, eds. Pp. 158-174. Oxford: Oxbow Books.
- Bachhuber, Christopher, and R. Gareth Roberts, eds.
2009 *Forces of Transformation: The End of the Bronze Age in the Mediterranean*. Oxford: Oxbow Books.
- Bachmann, Hans-Gert
1999 On the Early Metallurgy of Gold: Some Answers and More Questions. In *The Beginnings of Metallurgy*. A. Hauptmann and E. Pernicka, eds. Pp. 267-275. Bochum: Deutsches Bergbau-Museum.
- Bair, Jennifer
2009 Global Commodity Chains: Genealogy and Review. In *Frontiers of Commodity Chain Research*. J. Bair, ed. Pp. 1-34. Stanford: Stanford University Press.
- Balkan, Kemal
1955 *Kaniş Karum'unun Kronoloji Problemleri hakkında Müsahedeler*. Ankara: Türk Tarik Kurumu.
- Bar-Yosef Mayer, Daniella E., and N. Porat
2008 Green Stone Beads at the Dawn of Agriculture. *Proceedings of the National Academy of Sciences* 105:8548-8551.
- Barjamovic, Gojko
2011 *Historical Geography of Anatolia in the Old Assyrian Period*. Copenhagen: Museum Tusulanum Press.
- Bass, G. F., Cemal Pulak, and Dominique Collon
1989 The Bronze Age Shipwreck at Uluburun: 1986 Campaign. *American Journal of Archaeology* 93(1):1-29.
- Bayburtoğlu, Bülent, and Selahattin Yıldırım
2008 Gold and Silver in Anatolia. In *Anatolian Metal IV*. Ü. Yalçın, ed. Pp. 43-51. Der Anschnitt 21. Bochum: Deutsches Bergbau-Museum.
- Baykal-Seeher, Ayşe
2006 Kleinfunde aus den Grabungen am Büyükkale-Nordwesthang 1998-2000. In *Ergebnisse der Grabungen an den Ostteichen und am mittleren Büyükkale-Nordwesthang in den Jahren 1996-2000*. J. Seeher, ed. Mainz: von Zabern.
- Beckman, Gary
1995 Hittite Provincial Administration in Anatolia and Syria: The View from Maşat and Emar. In *Atti del II Congresso Internazionale di Hittitologia. Studia Mediterranea*. Pp. 19-37. Pavia: Gianni Iuculano Editore.

- Begemann, Friedrich, Ernst Pernicka, and Sigrid Schmitt-Strecker
 1994 Metal Finds from Ilıpınar and the Advent of Arsenical Copper. *Anatolica* 20:203-219.
- 1995 Thermi on Lesbos: A Case Study of Changing Trade Patterns. *Oxford Journal of Archaeology* 14(2):123-135.
- Begemann, Friedrich, and Sigrid Schmitt-Strecker
 2008 Bleiisotopie und die Provenienz von Metallen. In *Anatolian Metal IV*. Ü. Yalçın, ed. Pp. 125-134. Bochum: Deutsches Bergbau-Museum.
- Begemann, Friedrich, Sigrid Schmitt-Strecker, and Ernst Pernicka
 2003 On the Composition and Provenance of Metal from Beşiktepe (Troia). In *Troia and the Troad: Scientific Approaches*. G. Wagner, E. Pernicka, and H.-P. Uerpmann, eds. Pp. 173-201. Berlin: Springer.
- Belli, Oktay
 1991 Ore Deposits and Mining in Eastern Anatolia in the Urartian Period: Silver, Copper and Iron. In *Urartu: A Metalworking Center in the First Millennium B.C.E.* R. Merhav, ed. Pp. 16-41. Jerusalem: The Israel Museum.
- Bengliyan, A.
 1985 *Trace Element Analysis of Metal Artifacts from the Gedikli Hoard by Atomic Absorption Spectroscopy*, Unpublished MA Thesis, Chemistry, Boğaziçi University.
- Bilgi, Önder
 1984 Metal Objects from İkiztepe - Turkey. *Beiträge zur Allgemeinen und Vergleichenden Archäologie* 6:31-96.
- 1990 Metal Objects from İkiztepe - Turkey. *Beiträge zur Allgemeinen und Vergleichenden Archäologie* 9-10:119-219.
- Blanton, R. E., and Lane Fargher
 2008 *Collective Action in the Formation of Pre-modern States*. New York: Springer.
- Boehmer, Rainer Michael
 1972 *Die Kleinfunde von Bogazköy aus den Grabungskampagnen 1952-1969*. Berlin: G. Mann.
- 1979 *Die Kleinfunde aus der Unterstadt von Boğazköy: Grabungskampagnen 1970-1978* Berlin: Mann.
- Boschma, Ron A., and Koen Frenken
 2011 The Emerging Empirics of Evolutionary Economic Geography. *Journal of Economic Geography*:295-307.
- Bowles, Samuel, and Herbert Gintis
 2011 *A Cooperative Species: Human Reciprocity and Its Evolution*. Princeton: Princeton University Press.
- Boyd, Robert, and Peter J. Richerson
 2009 Culture and the Evolution of Cooperation. *Philosophical Transactions of the Royal Society B* 364(1533):3281-3288.
- Braidwood, Robert J., Joseph E. Burke, and Norman H. Nachtrieb
 1951 Ancient Syrian Coppers and Bronzes. *Journal of Chemical Education* 28(2):87-96.

- Branting, Scott A., Tony J. Wilkinson, John Christiansen, Magnus Widell, Carrie Hritz, Jason Ur, Benjamin Studevent-Hickman, and Mark Altaweel
 2013 The 'External Economy': Networks and Trade. In *Models of Mesopotamian Landscapes*. T.J. Wilkinson, M. Gibson, and M. Widell, eds. Pp. 140-151. Oxford: Archaeopress.
- Branting, Scott Andrew
 2004 *Iron Age Pedestrians at Kerkenes Dag: An Archaeological GIS-T Approach to Movement and Transportation*, Department of Anthropology, State University of New York -- Buffalo.
- Branting, Scott Andrew, and Geoffrey D. Summers
 2002 Modelling Terrain: the Global Positioning System (GPS) Survey at Kerkenes Dağ, Turkey. *Antiquity* 76:639-640.
- Branting, Scott Andrew, Y. Wu, Rangamani Srikrishnan, and Mark R. Altaweel
 2007 SHULGI: A Geospatial Tool for Modeling Human Movement and Interaction. *Proceedings of the Agent 2007 Conference on Complex Interaction and Social Emergence*, Argonne, Illinois, 2007, pp. 475-487. Argonne National Laboratory.
- Brill, R. H., and J. M. Wampler
 1967 Isotope Studies of Ancient Lead. *American Journal of Archaeology* 71(1):63-77.
- Brixhe, Claude, and Geoffrey D. Summers
 2007 Les inscriptions phrygiennes de Kerkenes Dağ (Anatolie centrale). *Kadmos* 45(1-2):93-135.
- Brumfiel, Elizabeth M.
 1994 Factional Competition and Political Development in the New World: An Introduction. In *Factional Competition and Political Development in the New World*. E.M. Brumfiel and J.W. Fox, eds. Pp. 3-14. Cambridge: Cambridge University Press.
- Brumfiel, Elizabeth M. , and Timothy K. Earle
 1987 Specialization, Exchange and Complex Societies: An Introduction. In *Specialization, Exchange and Complex Societies*. E.M. Brumfiel and T.K. Earle, eds. Pp. 1-9. Cambridge: Cambridge University Press.
- Bryce, Trevor
 2002 *Life and Society in the Hittite World*. Oxford: Oxford University Press.
- 2005 *The Kingdom of the Hittites*. Oxford: Oxford University Press.
- Buchholz, Hans-Günter
 1967 Analysen prähistorischer Metallfunde aus Zypern und Nachbarländern. *Berliner Jahrbuch für Vor- und Frühgeschichte* 7:189-256.
- Budd, P., R. Haggerty, A.M. Pollard, B. Scaife, and R.G. Thomas
 1996 Rethinking the Quest for Provenance. *Antiquity* 70:168-174.
- Budd, Paul, A. Mark Pollard, R. G. Thomas, P. A. Williams, and D. Gale
 1993 Evaluating Lead Isotope Data: Further Observations. *Archaeometry* 35(2):241-247.
- Burke, Brendan
 2010 *From Minos to Midas: Ancient Cloth Production in the Aegean and in Anatolia*. Oxford: Oxbow Books.

-
- 2011 Textile Production at Gordion and the Phrygian Economy. In *The Archaeology of Midas and the Phrygians: Recent Work At Gordion*. L. Kealhofer, ed. Pp. 69-81. Philadelphia: University of Pennsylvania Press.
- Butzer, Karl W.
2012 Collapse, Environment, and Society. *Proceedings of the National Academy of Sciences* 109(10):3632-3639.
- Çağatay, A., Y. Altun, and B. Arman
1979 Madenbelenitepe (Soğukpınar-Bursa) Kalay Cevherleşmesinin Mineralojisi. *Maden Tetkik ve Arama Dergisi* 92:40-48.
-
- 1989 Bolkardağ Sulucadere (Ulukışla-Niğde) Kalay İçerikli Çinko-Kurşun Cevherleşmesinin Mineralojisi. *Jeoloji Mühendisleri* 32:15-20.
- Çağatay, A., and R. Pehlivan
1988 Celaller (Niğde-Çamardı) Kalay Cevherleşmesinin Mineralojisi. *Jeoloji Mühendisleri* 32-33:27-31.
- Çağatay, M. N.
1987 The Pancarli Nickel-Copper Sulfide Mineralization, Eastern Turkey. *Mineralium Deposita* 22(3):163-171.
- Caneva, I.
2000 Early Metal Production in Cilicia: A View from Mersin-Ymuktepe. In *Anatolian Metal I*. Ü. Yalçın, ed. Pp. 69-74. Der Anschnitt 13. Bochum: Deutsches Bergbau-Museum.
- Carballo, D. M., ed.
2013 *Cooperation and Collective Action: Archaeological Perspectives*. Boulder: University Press of Colorado.
- Carballo, D. M., Paul B. Roscoe, and Gary Feinman
2012 Cooperation of Collective Action in the Cultural Evolution of Complex Societies. *Journal of Archaeological Method and Theory* (Online First).
- Carter, Elizabeth, Stuart Campbell, and Susan Gauld
2003 Elusive Complexity: New Data From the Late Halaf Domuztepe in South Central Turkey. *Paléorient* 29(2):117-133.
- Carter, Tristan, Stéphan Dubernet, Rachel King, François-Xavier Le Bourdonnec, Marina Milić, Gérard Poupeau, and M. L. Shackley
2008 Eastern Anatolian Obsidians at Çatalhöyük and the Reconfiguration of Regional Interaction in the Early Ceramic Neolithic. *Antiquity* 82:900-909.
- Chantre, Ernst
1898 *Recherches Anthropologiques Dans L'Asie Occidentale: Mission en Cappadoce 1893-1894*. Paris: Ernest Leroux Éditeur.
- Chen, Kunlong, Thilo Rehren, Jianjun Mei, and Congcang Zhao
2009 Special Alloy from Remote Frontiers of the Shang Kingdom: Scientific Study of the Hanzhong Bronzes from Southwest Shanxi, China. *Journal of Archaeological Science* 36(10):2108-2118.
- Cheng, C. F., and C. M. Schwitter
1957 Nickel in Ancient Bronzes. *American Journal of Archaeology* 61(4):351-365.

- Cherry, John F.
1986 Politics and palaces: some problems in Minoan state formation. In *Peer Polity interaction and socio-political change*. New Directions in Archaeology edition. C. Renfrew and J.F. Cherry, eds. Pp. 19-45. Cambridge: Cambridge University Press.
- Chew, S. R.
2001 *World Ecological Degradation: Accumulation, Urbanization, and Deforestation, 3000 B.C.–A.D. 2000*. Walnut Creek, CA: AltaMira.
- Childe, V. Gordon
1930 *The Bronze Age*. Cambridge: Cambridge University Press.
- 1944 Archaeological Ages as Technological Stages. *Journal of the Royal Anthropological Institute* 74:7-24.
- Clark, John E., and J. Parry
1990 Craft Specialization and Cultural Complexity. *Research in Economic Anthropology* 12:289-346.
- Cooke, Strathmore R. B., and Stanley E. Aschenbrenner
1975 The Occurrence of Metallic Iron in Ancient Copper. *Journal of Field Archaeology* 2(3):251-266.
- Costin, Cathy Lynne
1991 Craft Specialization: Issues in Defining, Documenting, and Explaining the Organization of Production. In *Archaeological Method & Theory*. M.B. Schiffer, ed. Pp. 1-56. Tuscon: University of Arizona Press.
- 2001 Craft Production Systems. In *Archaeology at the Millennium: A Sourcebook*. G.M. Feinman and T.D. Price, eds. Pp. 273-379. New York: Springer.
- Courcier, Antoine
2014 Ancient Metallurgy in the Caucauses from the Sixth to the Third Millennium BCE. In *Archaeometallurgy in Global Perspective: Methods and Syntheses*. B.W. Roberts and C.P. Thornton, eds. Pp. 579-664. New York: Springer.
- Craddock, P. T.
1995 *Early Metal Mining and Production*. Edinburgh: Edinburgh University Press.
- Craddock, P.T., and N. D. Meeks
1987 Iron in Ancient Copper. *Archaeometry* 29(2):187-204.
- Craddock, Paul T.
1978 The Composition of the Copper Alloys Used by the Greeks, Etruscan and Roman Civilizations: the Origins and Early Use of Brass. *Journal of Archaeological Science* 5(1):1-16.
- Çukur, Alaaddin, and Şeref Kuşç
1989 Development of Bronze Production Technologies in Anatolia. *Journal of Archaeological Science* 16(3):225-231.
- Curtis, John
2013 *An Examination of Late Assyrian Metalwork with Special Reference to Nimrud*. Oxford: Oxbow Books.
- D'Altroy, Terence N., and Timothy K. Earle
1985 Staple Finance, Wealth Finance, and Storage in the Inka Political Economy. *Current Anthropology* 26(2):187-206.

- Davis, J. R., ed.
2000 *Nickel, Cobalt, and Their Alloys*. Materials Park, OH: ASM International.
- de Jesus, Prentiss S.
1980 *The Development of Prehistoric Mining and Metallurgy in Anatolia*. Oxford: BAR.
- de Martino, Stefano
2003 *Annali e Res Gestae Antico Ittiti*. Pavia: Italian University Press.
- Delmas, A. B., and M. Casanova
1990 The Lapis Lazuli Sources in the Ancient East. In *South Asian Archaeology 1987*. M. Taddei, ed. Pp. 493-506. Rome: IsMEO.
- DeMarrais, Elizabeth, Luis Jaime Castillo, and T. K. Earle
1996 Ideology, Materialization, and Power Strategies. *Current Anthropology* 37(1):15-31.
- Dercksen, Jan Gerrit
1996 *The Old Assyrian Copper Trade in Anatolia*. Istanbul: Nederlands Historisch-Archaeologisch Instituut te Istanbul.
- 2005 Metals According to Documents from Kültepe-Kanish Dating to the Old Assyrian Colony Period. In *Anatolian Metal III*. Ü. Yalçın, ed. Pp. 17-34. Der Anschnitt 18. Bochum: Deutsches Bergbau-Museum.
- 2007 Die Altassyrischen Handelsabgaben in Nordmesopotamien und Anatolien im 19.-18. Jh. v.Chr. in Verträgen und Praxis. In *Geschenke und Steuern, Zölle und Tribute: Antike Abgabenformen in Anspruch und Wirklichkeit*. H. Klinkott, S. Kubisch, and R. Müller-Wollermann, eds. Pp. 187-211. Leiden: Brill.
- Drake, Brandon L.
2012 The Influence of Climatic Change on the Late Bronze Age Collapse and the Greek Dark Ages. *Journal of Archaeological Science* 39(6):1862-1870.
- Draycott, Catherine, and Geoffrey D. Summers
2008 *Sculpture and Inscriptions from the Monumental Entrance to The Palatial Complex at Kerkenes Dağ, Turkey*. Chicago: Oriental Institute Press.
- Drews, Robert
1993 *The End of the Bronze Age: Changes in Warfare and the Catastrophe ca. 1200 B.C.* Princeton: Princeton University Press.
- Düring, Bleda S.
2011 *The Prehistory of Asia Minor: From Complex Hunter-Gathers to Early Urban Societies*. Cambridge: Cambridge University Press.
- Duru, Refik
2006 *Gedikli Karahöyük I. The Results of Excavations Directed by Prof. U. Bahadır Alkım in the Years 1964-1967*. Ankara: Türk Tarik Kurumu.
- Dusinberre, Elspeth
2002 An excavated ivory from Kerkenes Dağ, Turkey: transcultural fluidities, significations of collective identity and the problem of Median art. *Ars Orientalis* 32:17-54.

- Earle, Timothy
2010 Exchange Systems in Prehistory. In *Trade and Exchange: Archaeological Studies from History and Prehistory*. C.D. Dillian and C.L. White, eds. Pp. 205-217. New York: Springer.
- 2011 Redistribution and the Political Economy: The Evolution of the Idea. *American Journal of Archaeology* 115(2):237-244.
- Edens, C. M.
1995 Transcaucasia at the End of the Early Bronze Age. *Bulletin of the American School of Oriental Research* 299/300:53-64.
- Ehlers, Eckert, and Hermann Kreutzmann
2000 High Mountain Ecology and Economy: Potential and Constraints. In *High Mountain Pastoralism in Northern Pakistan*. E. Ehlers and K. Hermann, eds. Pp. 9-36. Stuttgart: Franz Steiner Verlag.
- Emre, Kutlu
1971 *Anadolu Kurşun Figürinleri ve Taş Kalıpları*. Ankara: Türk Tarih Kurumu Basımevi.
- Enomoto, Atsuko, and Yoshimitsu Hirao
1999 Lead Isotope Ratios of Copper Objects Excavated the 12th Season at Kaman Kalehöyük. *Anatolian Archaeological Studies* 8:263-274.
- Erb-Satullo, Nathaniel Lucas, Brian Gilmour, and Nana Khakhutaishvili
in press Crucible Technologies in the Late Bronze-Early Iron Age South Caucasus: Copper Processing, Tin Bronze Production, and the Possibility of Local Tin Exploitation. *Journal of Archaeological Science*.
- Esin, Ufuk
1969 *Kuantitatif Spektrel Analiz Yardımıyla Anadolu'da Başlangıcından Asur Kolonileri Çağına Kadar Bakır ve Tunç Madenciliği*. İstanbul: Taş Matbaası.
- 1982 Tepecik Excavations, 1974. In *Keban Project 1974-75 Activities*. Pp. 95-127. Ankara: METU Press.
- 1985 Değirmentepe (Malatya) Kazıları Arkeometrik Araştırmalarına Toplu Bir Bakış. In *Arkeometrik Ünitesi Bilimsel Toplantı Bildirileri VI*. Pp. 131-151. TÜBİTAK Yayınları 622. Ankara: TÜBİTAK.
- 1990 Değirmentepe (Malatya) Kalkolitik Obeyd Evresi Damga Mühür ve Mühür Baskıları. *Türk Tarih Kongresi* 10:47-56.
- 1995 Early Copper Metallurgy at the Pre-Pottery Site of Aşıklı. In *Readings in Prehistory: Studies Presented to Halet Cambel*. Pp. 61-78. İstanbul: Prehistorya Yayınları.
- 1999 Copper Objects from the Pre-Pottery Neolithic Site of Aşıklı (Kızılkaya Village, Province of Aksaray, Turkey). In *The Beginnings of Metallurgy*. A. Hauptman, E. Pernicka, T. Rehren, and Ü. Yalçın, eds. Pp. 23-30. Der Anschnitt 9. Bochum: Deutsches Bergbau-Museum.

- Esin, Ufuk, and S. Harmankaya
 1988 Değirmentepe (Malatya) Kurtarma Kazısı. *Kazı Sonuçları Toplantısı* 9(1):79-125.
- Ezer, Sabahattin
 2014 Kültepe-Kanesh in the Early Bronze Age. In *Current Research at Kültepe/Kanesh: An Interdisciplinary and Integrative Approach to Trade Networks, Internationalism, and Identity*. L. Atıcı, F. Kulakoğlu, G. Barjamovic, and A. Fairbairn, eds. Pp. 5-23. Boston: American School of Oriental Research.
- Faraldi, F., Altan Çilingiroğlu, E. Angelini, C. Riccucci, T. de Caro, Atilla Batmaz, A. Mezzi, D. Caschera, and B. Cortese
 2013 Micro-Chemical and Micro-Structural Investigation of Archaeological Bronze Weapons from the Ayanis Fortress (Lake Van, Eastern Anatolia, Turkey). *Applied Physics A* 113(4):911-921.
- Feldman, Marian
 2006 *Diplomacy by Design: Luxury Arts and an "International Style" in the Ancient Near East, 1400-1200 BCE*. Chicago: University of Chicago Press.
- Flannery, Kent, and Joyce Marcus
 2012 *The Creation of Inequality: How Our Prehistoric Ancestors Set the Stage for Monarchy, Slavery, and Empire*. Cambridge: Harvard University Press.
- Fleming, Stuart J., Vincent C. Pigott, Charles P. Swann, and Samuel K. Nash
 2005 Bronze in Luristan: Preliminary Analytical Evidence from Copper/Bronze Artifacts Excavated by the Belgian Mission in Iran. *Iranica Antiqua* 40:35-64.
- Floreano, E.
 2001 The Role of Silver in the Domestic Economic System of the Hittite Empire. *Altorientalische Forschungen* 28:209-235.
- Forbes, R. J.
 1964 *Studies in Ancient Technology*. Volume 9. Leiden: E.J. Brill.
- Forlanini, Massimo
 2008 The Historical Geography of Anatolia and the Transition from Karum-Period to the Early Hittite Empire. In *Anatolia and the Jazira during the Old Assyrian Period*. J.G. Dercksen, ed. Pp. 57-86. Leiden: Nederlands Instituut voor het Nabije Oosten.
- Frangipane, Marcella
 1997 Arslantepe-Malatya: External Factors and Local Components in the Development of an Early State. In *Emergence and Change in Early Urban Societies*. L. Manzanilla, ed. Pp. 43-58. New York: Plenum Press.
- 2001a Centralization Processes in Greater Mesopotamia: Uruk "Expansion" as the Climax of Systemic Interactions among Areas of the Greater Mesopotamian Region. In *Uruk Mesopotamia and Its Neighbors*. M.S. Rothman, ed. Pp. 307-348. Santa Fe: School of American Research Press.
- 2001b The Transition Between Two Opposing Forms of Power at Arslantepe (Malatya) at the Beginning of the 3rd Millennium. *TUBA-AR* 4:1-24.
- Frank, Andre Gunder
 1993 Bronze Age world system cycles. *Current Anthropology* 34(4):383-430.

- Fujita, Masahisa, Paul Krugman, and Anthony J. Venables
 1999 *The Spatial Economy: Cities, Regions, and International Trade*. Cambridge: MIT Press.
- Galaty, Michael L., and William A. Parkinson
 2007 Introduction: Putting Mycenaean Palaces in Their Place. In *Rethinking Mycenaean Palaces II: Revised and Expanded Second Edition*. M.L. Galaty and W.A. Parkinson, eds. Pp. 21-28. Cotsen Institute of Archaeology Monograph 60. Los Angeles: UCLA Cotsen Institute of Archaeology.
- Gale, N. H., Z. A. Stos-Gale, G. Maliotis, and N. Annetts
 1997 Lead Isotope Data from the Isotracer Laboratory, Oxford: Archaeometry Data Base 4: Ores from Cyprus. *Archaeometry* 39(1):237-246.
- Gale, Noel
 2001 Archaeology, science-based archaeology and the Mediterranean Bronze Age metals trade: a contribution to the debate. *European Journal of Archaeology* 4(1):113-130.
- Gale, Noel H., and Zofia A. Stos-Gale
 1982 Bronze Age Copper Sources in the Mediterranean: A New Approach. *Science* 216(4541):11-19.
- Gale, Noel H., Zofia A. Stos-Gale, and G. R. Gilmore
 1985 Alloy Types and Copper Sources of Anatolian Copper Alloy Artefacts. *Anatolian Studies* 35:143-173.
- Gambaschidze, I., Andreas Hauptmann, Rainer Slotta, and Ünsal Yalçın
 2001 *Georgien-Schätze aus dem Land des Goldenen Vlies*. Bochum: Deutsches Bergbau-Museum.
- Garnsey, P., and I. Morris
 1989 Risk and the Polis: The Evolution of Institutionalized Responses to Food Supply Problems in the Ancient Greek State. In *Bad Year Economics: Cultural Responses to Risk and Uncertainty*. J. O'Shea and P. Halstead, eds. Pp. 98-105. Cambridge: University of Cambridge Press.
- Garstang, J.
 1953 *Prehistoric Mersin: Yüyük Tepe in Southern Turkey: the Neilson Expedition in Cilicia*. Oxford: Clarendon Press.
- Gates, Marie-Henriette
 2001 Potmarks at Kinet Höyük and the Hittite Ceramic Industry. *Varia Anatolica* 13:137-157.
- Genz, Hermann
 2003 The Early Iron Age in Central Anatolia. In *Identifying Changes : The Transition from Bronze to Iron Ages in Anatolia and Its Neighbouring Regions : Proceedings of the International Workshop, Istanbul, November 8-9, 2002*. B. Fischer, H. Genz, E. Jean, and K. Köroğlu, eds. Pp. 179-192. Istanbul: Türk Eskiçağ Bilimleri Enstitüsü.
-
- 2004 *Büyükkaya I: Die Keramik der Eisenzeit*. Mainz: Philipp von Zabern.

-
- 2006 Die eisenzeitliche Besiedlung im Bereich der Grabungen am mittleren Büyükkale-Nordwesthang 1998–2000. In *Ergebnisse der Grabungen an den Ostteichen und am mittleren Büyükkale-Nordwesthang in den Jahren 1996–2000*. J. Seeher, ed. Pp. 98-158. Mainz: Philipp von Zabern.
-
- 2007 Late Iron Age Occupation on the Northwest Slope at Boğazköy. In *Anatolian Iron Ages 6*. A. Çilingiroğlu and A. Sagona, eds. Pp. 135-151. Leuven: Peeters.
-
- 2011 The Iron Age in Central Anatolia. In *The Black Sea, Greece, Anatolia and Europe in the First Millennium BC*. G.R. Tsetschladze, ed. Leuven: Peeters.
-
- forthcoming *Eisenzeitliche Gräber aus Boğazköy*.
Genz, Hermann, and Andreas Hauptmann
2002 Chalcolithic and EBA Metallurgy in the Southern Levant. In *Anatolian Metal II*. U. Yalcin, ed. Pp. 149-157. Bochum: Deutsches Bergbau Museum.
- Gerber, C.
2006 Zur Stratigraphie der Fürstengräber von Alaca Höyük: neue Einsichten in ein altes Problem. In *Studies in Honour of Hayat Erkanal: Cultural Reflections*. A. Erkanal-Öktü, E. Özgen, S. Günel, A.T. Ökse, H. Hüryılmaz, H. Tekin, N. Çınardalı-Karaaslan, B. Uysal, A. Karaduman, A. Engin, R. Spieß, A. Aykurt, R. Tuncel, U. Deniz, and A. Rennie, eds. Pp. 379-388. Istanbul: Homer Kitab Evi.
- Giles, D. L., and E. P. Kuijpers
1974 Stratiform Copper Deposit, Northern Anatolia, Turkey: Evidence for Early Bronze I (2800 B.C.) Mining Activity. *Science* 186:823-825.
- Gintis, Herbert, Samuel Bowles, Robert Boyd, and Ernst Fehr, eds.
2005 *Moral Sentiments and Material Interests*. Cambridge: MIT Press.
- Glatz, Claudia
2012 Bearing the Marks of Control? Reassessing Pot Marks in Late Bronze Age Anatolia. *American Journal of Archaeology* 116(1):5-38.
- Glatz, Claudia, and Roger Mathews
2009 Empire as Network: Spheres of Material Interaction in Late Bronze Age Anatolia. *Journal of Anthropological Archaeology* 28(2):127-141.
- Glatz, Claudia, and Aimée M. Plourde
2011 Landscape Monuments and Political Competition in Late Bronze Age Anatolia: An Investigation of Costly Signaling Theory. *Bulletin of the American Oriental Society* 361(1):33-66.
- Golden, Jonathan, Thomas E. Levy, and Andreas Hauptmann
2001 Recent Discoveries Concerning Chalcolithic Metallurgy at Shiqmim, Israel. *Journal of Archaeological Science* 28(9):951-963.
- Golden, Jonathan M.
2009 *Dawn of the Metal Age: Technology and Society during the Levantine Chalcolithic*. London: Equinox.

- Goldstone, Jack A., and John F. Haldon
 2009 Ancient States, Empires, and Exploitation: Problems and Perspectives. In *The Dynamics of Ancient Empires: State Power from Assyria to Byzantium*. I. Morris and W. Scheidel, eds. Pp. 3-29. Oxford: Oxford University Press.
- Grave, Peter, Lisa Kealhofer, Ben Marsh, G. Kenneth Sams, Mary M. Voigt, and Keith DeVries
 2009 Ceramic Production and Provenience at Gordion, Central Anatolia. *Journal of Archaeological Science* 36:2162-2176.
- Grave, Peter, Lisa Kealhofer, Ben Marsh, Taciser Sivas, and Hakan Sivas
 2012 Reconstructing Iron Age Community Dynamics in Eskişehir Province, Central Turkey. *Journal of Archaeological Method and Theory* 19(3):377-406.
- Grögler, N., J. Geiss, M. Grünenfelder, and F. C. Houtermans
 1966 Isotopenuntersuchungen zur Bestimmung der Herkunft römischer Bleirohre und Bleibarren. *Zeitschrift für Naturforschung Teil A* 219:1167-1172.
- Guilbert, John, and Charles Frederick Park
 2007 *The Geology of Ore Deposits*. Long Grove: Waveland Press.
- Gunter, Ann C.
 2006 Issues of Hittite Ceramic Production: a View from the Western Frontier. In *Strukturierung und Datierung der hethitischen Archäologie: Voraussetzungen—Probleme—Neue Ansätze*. D.P. Mielke, U.-D. Schoop, and J. Seeher, eds. Pp. 349-363. Istanbul: Ege Yayınları.
- Gürsan-Salzman, Ayşe
 1992 *Alaca Hoyuk: A Reassessment of the Excavation and Sequence of the Early Bronze Age Settlement* PhD Dissertation, Anthropology, University of Pennsylvania.
- Hall, Mark E., and Sharon R. Steadman
 1991 Tin and Anatolia: Another Look. *Journal of Mediterranean Archaeology* 4(1):217-234.
- Harada, Kazuo, Yosuke Tagawa, Kozo Nagashima, Kazuso Nakao, and Noburo Tsukahara
 1971 Pentlandite, Niccolite and Gersdorffite from the Han Deresi and Günes Districts, Near Divrigi, Sivas, Eastern Turkey. *Mineralogical Journal* 6(5):313-322.
- Harrison, Timothy P.
 2008 *Cyprus, the Sea Peoples and the Eastern Mediterranean: Regional Perspectives of Continuity and Change*. Toronto: Canadian Institute for Mediterranean Studies.
- Hauptmann, Andreas
 2000 *Zur frühen Metallurgie des Kupfers in Fenan / Jordanian*. Bochum: Deutsches Bergbau-Museum.
- 2007 *The Archaeometallurgy of Copper*. Berlin, Heidelberg: Springer-Verlag.
- Hauptmann, Andreas, Friedrich Begemann, R. Heitkemper, Ernst Pernicka, and Sigrid Schmitt-Strecker
 1992 Early Copper Production at Feinan, Wadi Arabah, Jordan: The Composition of Ores and Copper. *Archaeomaterials* 6(1-33).
- Hauptmann, Andreas, Robert Maddin, and M.K. Prange
 2002a On the Structure and Composition of Copper and Tin Ingots Excavated from the Shipwreck of Uluburun. *Bulletin of the American Schools of Oriental Research* 328:1-30.

- Hauptmann, Andreas, Sigrid Schmitt-Strecker, Friedrich Begemann, and Alberto Palmieri
2002b Chemical Composition and Lead Isotopy of Metal Objects From the "Royal" Tomb and Other Related Finds At Arslantepe, Eastern Anatolia. *Paléorient* 28(2):43-69.
- Hauptmann, H.
1969 Die Grabungen in der prähistorischen Siedlung auf Yarikkaya. In *Boğazköy 4. Funde aus den Grabungen 1967 und 1968*. K. Bittel, H.G. Güterbock, H. Hauptmann, H. Kühne, and P. Neve, eds. Pp. 66-69. Berlin.
- Hauptmann, Harald
1982 Die Grabungen auf dem Norşun Tepe, 1974. In *Keban Project 1971 Activities*. Pp. 41-70. Ankara: METU Press.
- Hauptmann, Harald, and Ernst Pernicka, eds.
2004 *Die Metallindustrie in Mesopotamien von den Anfängen bis zum 2. Jahrtausend v. Chr.* Radhen: M. Leidorf.
- Hawkins, David
2000 *Corpus of Heirglyphic Luwian Inscriptions, Vol. 1, Part 2*. Berlin and New York: Walter de Gruyter.
- 2002 Anatolia: The End of the Empire and After. In *Die nahöstlichen Kulturen und Griechenland an der Wende vom 2. zum 1. Jahrtausend v. Chr.* E.A. Braun-Holzinger and H. Matthäus, eds. Pp. 143-151. Mönchsee: Bibliopolis.
- Hawkins, J. David
1995 Karkamish and Karatepe: Neo-Hittite City-States in North Syria. In *Civilizations of the Ancient Near East*. J.M. Sasson, ed. Pp. 1295-1307. Peabody: Hendrickson Publishers.
- Hazenbos, Joost
2003 *The Organization of the Anatolian Local Cults During the Thirteenth Century B.C.: An Appraisal of the Hittite Cult Inventories*. Leiden: Brill.
- Healey, Elizabeth
2007 Obsidian as an Indicator of Inter-regional Contacts and Exchange: Three Case-Studies from the Halaf Period. *Anatolian Studies* 57:171-189.
- Helms, Mary W.
1993 *Craft and the Kingly Ideal: Art, Trade, and Power*. Austin: University of Texas Press.
- Helwing, Barbara
2014 Silver in the Early State Societies of Greater Mesopotamia. In *Metalle der Macht – Frühes Gold und Silber*. H. Meller, R. Risch, and E. Pernicka, eds. Halle: Landesamt für Denkmalpflege und Archäologie Sachsen-Anhalt.
- Henrich, Joseph, Robert Boyd, Samuel Bowles, Colin Camerer, Ernst Fehr, and Herbert Gintis, eds.
2004 *Foundations of Human Sociality: Economic Experiments and Ethnographic Evidence from Fifteen Small-Scale Societies*. Oxford: Oxford University Press.
- Henrich, Joseph, Robert Boyd, Samuel Bowles, Colin Camerer, Ernst Fehr, Herbert Gintis, and Richard McElreath
2001 In Search of Homo Economicus: Behavioral Experiments in 15 Small-Scale Societies. *American Economic Review* 91(2):73-78.

- Herbordt, Suzanne
 2006 Seigelfunde aus den Grabungen im Tal vor Sarıkale 2005, in J. Seeher (ed.) Die Ausgrabungen in Boğazköy-Hattuša 2005. *Archäologischer Anzeiger* 2006(1):183-186.
-
- in prep *Kleinfunde aus der Oberstadt von Bogzaköy/Hattusa*. Mainz: von Zabern.
- Herbordt, Suzanne, D. Bawanypeck, and David Hawkins
 2011 *Die Siegel der Großkönige und Großköniginnen auf Tonbulln aus dem Nişantepe-Archiv in Hattusa*. Mainz: von Zabern.
- Hess, K., Andreas Hauptman, H. Wright, and Robert Jr. Whallon
 1998 Evidence of Fourth Millennium BC Silver Production at Fatmalı-Kalecik, East Anatolia. In *Metallurgica Antiqua: In Honour of Hans-Gert Bachmann and Robert Maddin*. T. Rehren, A. Hauptman, and J.D. Muhly, eds. Pp. 57-68. Bochum: Deutsches Bergbau-Museum.
- Hirao, Yoshimitsu, and Atsuko Enomoto
 1993 Chemical Study of Copper Objects Excavated by the Fifth (1990) Excavation Expedition of Kaman-Kalehöyük. *Anatolian Archaeological Studies* 2(33-59).
- Hirao, Yoshimitsu, and J. Enomoto
 1994 Lead Isotope Ratios of Copper Objects excavated by the Fifth (1991) and Seventh (1992) Expeditions of Kaman-Kalehöyük. *Anatolian Archaeological Studies* 3:91-106.
- Hirao, Yoshimitsu, J. Enomoto, and H. Tachikawa
 1995 Lead Isotope Ratios of Copper, Zinc and Lead Minerals in Turkey-In Relation to the Provenance Study of Artifacts. In *Essays on Anatolia and Its Surrounding Civilizations*. T. Mikasa, ed. Pp. 89-114. Wiesbaden: Harrasowitz Verlag.
- Hirao, Yoshimitsu, and Junko Enomoto
 1997 Chemical Analysis of Copper Objects Excavated from 8th and 9th Excavations of Kaman-Kalehöyük. *Anatolian Archaeological Studies* 6:187-221.
- Hirao, Yoshimitsu, M. Sasaki, M. Takenaka, and T. Uchida
 1992 Lead Isotope Ratios of Copper Objects Excavated from Kaman-Kalehöyük. *Anatolian Archaeological Studies* 1(165-186).
- Hoffmann, Inge
 1984 *Der Erlass Telipinus*. Heidelberg: Universitätsverlag Winter.
- Hoffner, Harry A.
 1997 *The Laws of the Hittites: A Critical Edition*. Leiden: Brill.
-
- 2002 Same Thoughts on Merchants and Trade in the Hittite Kingdom. In *Kulturgeschichten. Altorientalistische Studien für Volkert Haas Zum 65. Geburtstag*. T. Richter, D. Prechel, and J. Klingner, eds. Pp. 179-189. Saarbrücken: Saarbrücker Druckerei und Verlag.
- Höppner, Berndt, Martin Bartelheim, M. Huijsmans, Rudiger Krauss, K.-P. Martinek, Ernst Pernicka, and Roland Schwab
 2005 Prehistoric Copper Production in the Inn Valley (Austria), and the Earliest Copper in Central Europe. *Archaeometry* 47(2):293-315.
- Hosler, Dorothy
 1995 Sound, Color and Meaning in the Metallurgy of Ancient West Mexico. *World Archaeology* 27(1):100-115.

- Howard-White, F. B.
1963 *Nickel: An Historical Review*. London: Methuen.
- Hughes, M. J., J. E. Curtis, and E. T. Hall
1981 Analyses of Some Urartian Bronzes. *Anatolian Studies* 31:141-145.
- Imparati, Fiorella
1964 *Le Leggi Ittite*. Rome: Edizione dell'Ateneo.
- 2002 *Palaces and Local Communities in Some Hittite Provincial Seats*. Winona Lake, IN: Eisenbrauns.
- Ingo, G. M., Altan Çilingiroğlu, F. Faraldi, C. Riccucci, M. P. Casaletto, A. Erdem, and Atilla Batmaz
2010 The Bronze Shields Found at the Ayanis Fortress (Van Region, Turkey): Manufacturing Techniques and Corrosion Phenomena. *Applied Physics A*:793-800.
- Ivanova, Mariya
2013 *The Black Sea and the Early Civilizations of Europe, the Near East and Asia*. Cambridge: Cambridge University Press.
- Joffe, Alexander H.
2002 The Rise of Secondary States in the Iron Age Levant. *Journal of the Economic and Social History of the Orient* 45(4):425-467.
- Johnson, Allen, and Timothy Earle
1987 *The Evolution of Human Societies*. Stanford: Stanford University Press.
- Jursa, Michael
2010 *Aspects of the Economic History of Babylonia in the First Millennium BC: Economic Geography, Economic Mentalities, Agriculture, the Use of Money and the Problem of Economic Growth*. Münster: Ugarit-Verlag.
- Jursa, Michael, and Juan Carlos Moreno Garcia
2015 The Ancient Near East and Egypt. In *Fiscal Regimes and the Political Economy of Premodern States*. A. Monson and W. Scheidel, eds. Pp. 115-165. Cambridge: Cambridge University Press.
- Kaniewski, David, Elise Van Campo, Joël Guiot, Sabine Le Burel, Thierry Otto, and Cecile Baeteman
2013 Environmental Roots of the Late Bronze Age Crisis. *PloS ONE* 8(8):DOI: 10.1371/journal.pone.0071004.
- Kaptan, Ergün
1986 Ancient Mining in the Tokat Province, Anatolia: New Finds. *Anatolica* 8:19-36.
- 1990 Türkiye Madencilik Tarihine Ait Buluntular. *Maden Tetkik ve Arama Dergisi* 111:175-186.
- Kealhofer, Lisa, Peter Grave, H. Genz, and Ben Marsh
2009 Post-Collapse: The Re-Emergence of Polity in Iron Age Boğazköy, Central Anatolia. *Oxford Journal of Archaeology* 28(4):275-300.
- Kealhofer, Lisa, Peter Grave, Ben Marsh, Sharon R. Steadman, Ronald Lee Gorny, and Geoffrey D. Summers
2010 Patterns of Iron Age Interaction in Central Anatolia: Three Sites in the Yozgat Region. *Anatolian Studies* 60:71-92.

- Killick, David, and Thomas Fenn
 2012 Archaeometallurgy: The Study of Preindustrial Mining and Metallurgy. *Annual Review of Anthropology* 41:559-575.
- Klengel, Horst
 1975 Zur ökonomischen des hethitischen Staates. *Studi Micenei ed Egeo-Anatolici* 16:181-200.
- 1979 Handel und Kaufleute im hethitischen Reich. *Altorientalische Forschung* 6(69-80).
- 1998 *Geschichte Des Hethitischen Reiches*. Leiden: Brill.
- 2005 Studien zur hethitischen Wirtschaftsgeschichte: Einleitende Bemerkungen. *Altorientalische Forschung* 32:3-22.
- Kline, Michelle A., and Robert Boyd
 2010 Population Size Predicts Technological Complexity in Oceania. *Proceedings of the Royal Society B* 277(1693):2559-2564.
- Klinger, Jörg
 2006 Der Beiträge der Textfunde zur Archäologiegeschichte der hethitischen Hauptstadt. In *Strukturierung und Datierung in der hethitischen Archäologie: Voraussetzungen-Probleme-Neue Ansätze*. D.P. Mielke, U.-D. Schoop, and J. Seeher, eds. Pp. 5-18. Istanbul: Ege Yayınları.
- Knapp, A. Bernard
 1998 Social Approaches to the Archaeology and Anthropology of Mining. In *Social Approaches to an Industrial Past: The Archaeology and Anthropology of Mining*. A.B. Knapp, V.C. Pigott, and E.W. Herbert, eds. Pp. 1-23. London: Routledge.
- 2000 Archaeology, science-based archaeology and the Mediterranean Bronze Age metals trade. *European Journal of Archaeology* 3(1):31-56.
- Kohl, Phil
 1987 The Ancient Economy, Transferable Technologies and the Bronze Age World-System: a View from the Northeastern Frontier of the Ancient Near East. In *Centre And Periphery In The Ancient World*. M. Rowlands, M. Larsen, and K. Kristiansen, eds. Pp. 13-24. Cambridge: Cambridge University Press.
- Kohl, Phillip L.
 2002 Bronze Production and Utilization in Southeastern Daghestan, Russia: c. 3600-1900 B.C. In *Die Anfänge der Metallurgie in der Alten Welt*. M. Bartelheim, E. Pernicka, and R. Krause, eds. Pp. 161-178. Rahden/Westfallien: Verlag Marie Leidorf.
- Kohler, Ellen L.
 1995 *The Lesser Phrygian Tumuli, Part 1: The Inhumations*. Volume II. Philadelphia: University Museum.
- Kohler, T., and D. Maselli
 2009 *Mountains and Climate Change: From Understanding to Action*. Berne: Geogr. Bernesia.

- Kontani, Ryoichi, T. Odaka, H. Sudo, Yuichi S. Hayakawa, Fikri Kulakoğlu, Kutlu Emre, and Güzel Öztürk
2014a Preliminary Report of the Archaeological Survey in Kayseri Province, Turkey (KAYAP), Sixth Season (2013). *Bulletin of the Okayama Orient Museum* 28:25-34.
- Kontani, Ryoichi, Hiroshi Sudo, Yuji Yamaguchi, Yuichi S. Hayakawa, and Takahiro Odaka
2014b An Archaeological Survey in the Vicinity of Kültepe, Kayseri Province, Turkey. In *Current Research at Kültepe-Kanesh*. L. Atici, F. Kulakoğlu, G. Barjamovic, and A. Fairbairn, eds. Pp. 85-94. Atlanta: Lockwood Press.
- Körner, Christian
2003 *Alpine Plant Life*. Berlin: Springer-Verlag.
- 2004 Mountain Biodiversity, Its Causes and Function. *Ambio* 13:11-17.
- Košak, S.
1982 *Hittite Inventory Texts (CTH 241-250)*. Heidelberg.
- Koşay, H. Z.
1938 *Alaca Höyük Hafriyatı. 1936 daki Çalışmalara ve Keşiflere ait İlk Rapor*. Ankara Türk Tarih Kurumu.
- Krause, Rüdiger
2003 *Studien zur kupfer- und frühbronzezeitlichen Metallurgie zwischen Karpatenbecken und Ostsee*. Rahden: Verlag Marie Leidorf.
- Krugman, Paul
1991a *Geography and Trade*. Cambridge: MIT Press.
- 1991b Increasing Returns and Economic Geography. *Journal of Political Economy* 99(3):483-499.
- Kulakoğlu, Fikri
2011 Kültepe-Kaneş: A Second Millennium B.C.E. Trading Center on the Central Plateau. In *The Oxford Handbook of Ancient Anatolia: 10,000-323 B.C.E.* S.R. Steadman and G. McMahon, eds. Pp. 1012-1030. Oxford: Oxford University Press.
- 2014 Kanesh after the Assyrian Colony Period: Current Research at Kültepe and the Question of the End of the Bronze Age Settlement. In *Current Research at Kültepe-Kanesh*. L. Atici, F. Kulakoğlu, G. Barjamovic, and A. Fairbairn, eds. Pp. 85-94. Atlanta: Lockwood Press.
- Kulakoğlu, Fikri, and Güzel Öztürk
2015 New Evidence for International Trade in Bronze Age Central Anatolia: Recently Discovered Bullae from Kültepe-Kanesh. *Antiquity* 89(343).
- Kunç, Şeref, and Alaaddin Çukur
1988 Bakır Buluntularda iz Element Dağılımı. *Arkeometri Sonuçları Toplantısı* 3:97-105.
- Kuruçayırılı, Emre
2011 Akdeniz'in Kuzeydoğu Kıyısında M.Ö. İkinci Binyıl Bakır Metalürjisi. *Arkeometri Sonuçları Toplantısı* 27:247-260.
- Kuruçayırılı, Emre, and Hadi Özbal
2005 New Metal Analysis from Tarsus Gözlüküle. In *Anatolian Metal III*. Ü. Yalçın, ed. Pp. 49-61. Bochum: Deutsches Bergbau Museum.

Langis-Barsetti, Dominique

2013 Results of the 2011 Geophysical Survey at Kerkenes Dağ, Central Anatolia. *Anatolia Antiqua* 21.

Larsen, Mogens Trolle

1967 *Old Assyrian Caravan Procedures*. Istanbul: Nederlands Historisch-Archaeologisch Instituut in het Nabije Oosten.

— 1976 *The Old Assyrian City-State and Its Colonies*. Copenhagen: Akademisk Forlag.

Lechtman, Heather

1991 Production of copper-arsenic alloys in the Central Andes: highland ores and coastal smelters? *Journal of Field Archaeology* 18(1):43-76.

— 1996 Arsenic bronze: dirty copper or chosen alloy? A view from the Americas. *Journal of Field Archaeology* 23(4):477-517.

Lechtman, Heather, and Sabine Klein

1999 The Production of Copper-Arsenic Alloys (Arsenic Bronze) by Cosmelting: Modern Experiment, Ancient Practice. *Journal of Archaeological Science* 26:497-526.

Lehner, Joseph W.

2011 A Preliminary Report on the Microstructure and Microanalysis of Metal from Boğazköy, in In A. Schachner (Ed.), *Die Ausgrabungen in Boğazköy-Ḫattuša 2010*. *Archäologischer Anzeiger* 2011(1):57-64.

— 2014a Metal Technology, Organization, and the Evolution of Long-Distance Trade at Kültepe. In *Current Research at Kültepe/Kanesh: An Interdisciplinary and Integrative Approach to Trade Networks, Internationalism, and Identity*. L. Atıcı, F. Kulakoğlu, G. Barjamovic, and A. Fairbairn, eds. Pp. 135-155. Boston: American School of Oriental Research.

— 2014b A Report on the Archaeometallurgical Research at Boğazköy, In A. Schachner (Ed.), *Die Ausgrabungen in Boğazköy-Ḫattuša 2013*. *Archäologischer Anzeiger* 2014(1):129-137.

— 2014c The Tin Problem Reconsidered: Recent Archaeometallurgical Research on the Anatolian Plateau. *Backdirt: Annual Review of the Cotsen Institute of Archaeology at UCLA* 2014:24-35.

— in press-a Compositional Analysis of Copper Alloys from the Middle Plateau Excavations at Boğazköy. In *Ausgrabungen in der westlichen Oberstadt 1: Das mittlere Plateau zwischen Sarıkale und Yenicekale*. A. Schachner, ed. Mainz: Verlag Philipp von Zabern.

— in press-b pXRF analysis of a Hittite Bracelet at Çorum Museum. In *Uğur Silistreli Armağan Kitabı*. A. Öztan, ed. Ankara: Ankara University Press.

- Lehner, Joseph W., and Andreas Schachner
 in press The Organization of Metal Production at Hattuša: A First Assessment. In *Overturning Certainties: Studies Presented to Kutlu Aslıhan Yener for Her 40 years of Field Archaeology in the Eastern Mediterranean*. Ç. Maner, A. Gilbert, and M. Horowitz, eds. Leiden: Brill.
- Lehner, Joseph W., Evren Yazgan, Ernst Pernicka, and Fikri Kulakoğlu
 2015 Continuity of Tin Bronze Consumption and Production during the Late Third Millennium BC at Kültepe. In *Proceedings of the 1st Kültepe International Meeting*. F. Kulakoğlu and C. Michel, eds. Leuven: Subartu, Brepols.
- Lehner, Joseph W., and K. Aslıhan Yener
 2014 Organization and Specialization of Early Mining and Metal Technologies in Anatolia. In *Archaeometallurgy in Global Perspective*. B.W. Roberts and C.P. Thornton, eds. Pp. 529-557. New York: Springer Verlag.
- Levine, Abigail, Charles Stanish, and P. Ryan Williams
 2013 Trade and Early State Formation in the Northern Titicaca Basin, Peru. *Latin American Antiquity* 24(3):289-308.
- Levy, Thomas E.
 1995 Cult, Metallurgy and Rank Societies-Chalcolithic Period (ca. 4200-3500 BCE). In *The Archaeology of the Holy Land*. T.E. Levy, ed. Pp. 226-244. London: Leicester University Press.
- Lichter, Clemens, ed.
 2007 *Vor 12.000 Jahren in Anatolien. Die ältesten Monumente der Menschheit*. Stuttgart: Theiss Verlag.
- Liverani, Mario
 1987 The Collapse of the Near Eastern Regional System at the End of the Bronze Age: the Case of Syria. In *Centre and Periphery in the Ancient World*. M. Rowlands, M. Larsen, and K. Kristiansen, eds. Pp. 66-73. Cambridge: Cambridge University Press.
- 2014 [1988] *The Ancient Near East: History, Society and Economy*. Oxford: Routledge.
- Lumsden, Stephen
 2008 Material Culture and the Middle Ground in the Old Assyrian Colony Period. In *Old Assyrian Studies in Memory of Paul Garelli*. C. Michel, ed. Pp. 21-43. Leiden: Nederlands Instituut voor het Nabije Oosten.
- Lutz, J., and Ernst Pernicka
 1996 Energy dispersive X-ray fluorescence analysis of ancient copper alloys: empirical values for precision and accuracy. *Archaeometry* 38(2):313-323.
- Lutz, J., Ernst Pernicka, and Günther A. Wagner
 1994 Chalkolitische Kupferverhüttung in Murgul, Ostanatolien. In *Handwerk und Technologie im Alten Orient*. R.B. Wartke, ed. Pp. 59-66. Mainz: Verlag Philipp von Zabern.
- Maddin, R., J. D. Muhly, and Tamara Stech
 1999 Early Metal Working at Çayönü. In *The Beginnings of Metallurgy*. T. Rehren and Ü. Yalçın, eds. Pp. 37-44. Der Anschnitt 9. Bochum: Deutsches Bergbau-Museum.

- Maden Tetkik ve Arama Enstitüsü
 1970 *Arsenic, Mercury, Antimony and Gold Deposits of Turkey*. Ankara: Maden Tetkik ve Arama Enstitüsü.
- 1971 *Iron Ore Deposits of Turkey*. Ankara: Maden Tetkik ve Arama Enstitüsü.
- 1972 *Türkiye Bakır, Kurşun ve Çinko Yatakları*. Ankara: Maden Tetkik ve Arama Enstitüsü.
- Marcus, Joyce
 1998 The Peaks and Valleys of Ancient States: An Extension of the Dynamic Model. In *Archaic States*. G. Feinman and J. Marcus, eds. Pp. 59-94. Santa Fe: School of American Research Press.
- 2008 The Archaeological Evidence for Social Evolution. *Annual Review of Anthropology* 37:251-266.
- Marsh, Ben
 2010 Geoarchaeology of the Human Landscape at Boğazköy-Ḫattuša In A. Schachner (Ed.), *Die Ausgrabungen in Boğazköy-Ḫattuša 2009. Archäologischer Anzeiger* 2010:201-207.
- Marston, John M.
 2012 Agricultural Strategies and Political Economy in Ancient Anatolia. *American Journal of Archaeology* 116(3):377-403.
- Martirosyan, A. A.
 1974 *Argišṭixinili*. Yerevan.
- Mathews, Roger
 2011 A History of Preclassical Archaeology in Anatolia. In *The Oxford Handbook of Ancient Anatolia (10,000-323 BCE)*. S.R. Steadman and G. McMahon, eds. Pp. 34-55. Oxford: Oxford University Press.
- Matthäus, Hartmut
 2005 Kulturaustausch, Handel und Seefahrt im Mittelmeerraum während der Späten Bronzezeit. In *Das Schiff von Uluburun: Welthandel vor 3000 Jahren*. Ü. Yalçın, C. Pulak, and R. Slotta, eds. Pp. 333-366. Bochum: Deutsches Bergbau-Museum.
- Maxwell-Hyslop, Rachel
 1972 The Metals Amūtu and Aši'u in the Kültepe Texts. *Anatolian Studies* 22:159-162.
- McElreath, Richard, and Robert Boyd
 2007 *Mathematical Models of Social Evolution: A Guide for the Perplexed*. Chicago: University of Chicago Press.
- Meeks, N. D.
 1986 Tin-Rich Surfaces on Bronze - Some Experimental and Archaeological Considerations. *Archaeometry* 28(2):133-162.
- Melchert, H. Craig
 1978 The Acts of Hattusili I. *Journal of Near Eastern Studies* 37(1):1-22.
- Meliksetian, Khachatur, Steffen Kraus, Ernst Pernicka, Pavel Avetissyan, Seda Devejian, and Levron Petrosyan
 2011 Metallurgy of Prehistoric Armenia. In *Anatolian Metal V*. Ü. Yalçın, ed. Pp. 201-210. Bochum: Deutsches Bergbau-Museum.

- Meliksetian, Khachatur, Ernst Pernicka, Ruben Badalyan, and Pavel Avetissyan
 2003 Geochemical Characterisation of Armenian Early Bronze Age Metal Artefacts and Their Relation to Copper Ores. In *Gewinnung und Verbreitung von Metallen und Obsidian in Kaukasien*. S. Hansen, A. Hauptmann, I. Motzenbacher, and E. Pernicka, eds. Pp. 41-58. Bonn: Dr. Rudolf Habelt.
- Mellaart, James
 1964 Excavations at Çatal Hüyük. Third Preliminary Report. *Anatolian Studies* 14:39-119.
- Michel, Cécile
 1991 Durhumid, son commerce et ses marchands. In *Marchands, diplomats et empereurs: Etudes sur la civilisation mésopotamienne offertes à Paul Garelli*. D. Charpin and F. Joannès, eds. Pp. 253-273. Paris: Editions Recherche sur les civilisations.
- Mielke, Dirk Paul
 2006 *Die Keramik vom Wesethang*. Rhaden: Leidorf.
- 2011a Hittite Cities: Looking for a Concept. In *Insights into Hittite History and Archaeology*. H. Genz and D.P. Mielke, eds. Pp. 153-194. Leuven: Peeters.
- 2011b Key Sites of the Hittite Empire. In *The Oxford Handbook of Ancient Anatolia. 10,000–323 BCE*. S.R. Steadman and G. McMahon, eds. Pp. 1031-1054. Oxford: Oxford University Press.
- Miller, Naomi F.
 1999 Interpreting Ancient Environment and Patterns of Land Use: Seeds, Charcoal and Archaeological Context. *TUBA-AR* 2:15-29.
- Miller, Naomi F., Melinda A. Zeder, and Susan R. Arter
 2009 From Food and Fuel to Farms and Flocks: The Integration of Plant and Animal Remains in the Study of the Agropastoral Economy at Gordion, Turkey. *Current Anthropology* 50(6):915-924.
- Monna, F., D. Galop, L. Carozza, M. Tual, A. Beyrie, F. Marembert, C. Chateau, J. Dominik, and F. E. Grousset
 2004 Environmental Impact of Early Basque Mining and Smelting Recorded in a High Ash Minerogenic Peat Deposit. *Science of The Total Environment* 327(1-3):197-214.
- Montero Fenollós, J.-L.
 1995 Estudio Provisional del Ajuar Metalico del Conjunto Funerario de los Loci 12 E y 12 W. Tell Qara Quzaq (Siria). Campagna 1992. *Aula Orientalis* 13:25-30.
- 1997 L'activité Métallurgique dans la Vallée du Haut-Euphrate Syrien (IIIe-IIe Millénaires av. J.C. *Akkadica* 103:6-28.
- 2000 La Métallurgie du Bronze dans le Bassin Syromésopotamien au Début du IIIe Millénaire Avant J.-C. In *Proceedings of the First International Congress on the Archaeology of the Ancient Near East*. P. Matthiae, A. Enea, L. Peyronel, and F. Pinnock, eds. Pp. 1093-1104. Rome: Università degli Studi di Roma.
- 2004 La "Tumba de la Princesa" de Qara Quzaq: Metal, Muerte y Prestigio en la Cuenca Sirio-Mesopotámica a Comienzos del III Milenio a.C. *Historiae* 1:36-55.

- Moorey, P. R. S.
 1994 *Ancient Mesopotamian Materials and Industries: The Archaeological Evidence*. Oxford: Clarendon Press.
- Mora, Clelia, and Lorenzo d'Alfonso
 2012 Anatolia after the End of the Hittite Empire. New Evidence from Southern Cappadocia. *Origini* 34:385-398.
- Muhly, James David
 1973a *Copper and Tin: The Distribution of Mineral Resources and The Nature of the Metals trade in the Bronze Age*. Volume 43. New Haven: The Connecticut Academy of Arts and Sciences.
- 1973b Tin trade routes of the Bronze Age. *American Scientist* 61(4):404-413.
- Muhly, James David, and T. A. Wertime
 1973 Evidence for the Sources and Use of Tin during the Bronze Age of the Near East: A Reply to J. E. Dayton. *World Archaeology* 5(1, Colonization):111-122.
- Müller-Karpe, Andreas
 1988 *Hethitische Töpferei der Oberstadt von Hattuša: Ein Beitrag zur Kenntnis spät-grossreichszeitlichen Keramik und Töpferbetriebe unter Zugrundelegung der Grabungsergebnisse von 1978–82 in Boğazköy*. Marburg: Hitzeroth.
- 1994 *Altanatolisches Metallhandwerk*. Neumünster: Wachholtz Verlag.
- Müller-Karpe, Michael
 1989 Neue Forschung zur Frühen Metallverarbeitung in Mesopotamien. *Jahrbuch des Römisch-Germanisches Zentralmuseum* 36(1):179-192.
- Muscarella, Oscar W.
 1988 The Background to the Phrygian Bronze Industry. In *Bronzeworking Centres of Western Asia c. 1000-539 B.C.* J. Curtis, ed. Pp. 177-192. London: Kegan Paul International.
- Neve, Peter
 1973 Die Ausgrabungen der Deutschen Boğazköy Expedition im Jahre 1971. *Türk Arkeoloji Dergisi* 20(1):129-.
- 1975 Boğazköy. *Türk Arkeoloji Dergisi* 22(2):93-119.
- 1980 Die Ausgrabungen in Boğazköy-Hattuša 1979. *Archäologischer Anzeiger* 1980:285-318.
- 1982 *Büyükkale, die Bauwerke: Grabungen 1954-1966*. Berlin: Mann.
- 1993 Die Ausgrabungen in Boğazköy-Hattuša 1992. *Archäologischer Anzeiger* 1993:621-652.
- 1996 *Hattuša: Stadt der Götter und Tempel*. Mainz: Verlag Philipp von Zabern.
- 1999 *Die Oberstadt von Hattuša: Die Bauwerke. I. Das zentrale Tempelviertel*. Berlin: Mann.

-
- 2001 *Die Oberstadt von Hattuša: Die Bauwerke. II. Die Bastion des Sphinxtores und die Tempelviertel am Königs- und Löwentor*. Mainz: Philipp von Zabern.
- Nezafati, Nima, Ernst Pernicka, and Morteza Momenzadeh
2008 Iranian Ore Deposits and Their Role in the Development of the Ancient Cultures. In *Anatolian Metal IV*. Ü. Yalçın, ed. Pp. 77-90. Bochum: Deutsches Bergbau-Museum.
-
- 2009 Introduction of the Deh Hosein Ancient Tin-Copper Mine, Western Iran: Evidence from Geology, Archaeology, Geochemistry and Lead Isotope Data. *TUBA-AR* 12:223-236.
-
- 2011 Ancient Tin: Old Question and a New Answer. *Antiquity* 85(330).
- Niederschlag, E., Ernst Pernicka, T. Seifert, and M. Bartelheim
2003 The determination of lead isotope ratios by multiple collector ICP-MS: a case study of Early Bronze Age artefacts and their possible relation with ore deposits of the Erzgebirge. *Archaeometry* 45(1):61-100.
- Northover, J. Peter
1998 Exotic Alloys in Antiquity. In *Metallurgica Antiqua*. T. Rehren, A. Hauptmann, and J.D. Muhly, eds. Pp. 113-121. Bochum: Deutsches Bergbau-Museum.
- Nowak, Martin A.
2012 Evolving Cooperation. *Theoretical Biology* 299:1-8.
- Oka, Rahul, and Chapurukha M. Kusimba
2008 The Archaeology of Trading Systems, Part 1: Towards a New Trade Synthesis. *Journal of Archaeological Research* 16:339-395.
- Okay, Aral I.
2008 Geology of Turkey: A Synopsis. In *Anatolian Metal IV*. Ü. Yalçın, ed. Pp. 19-42. Bochum: Deutsches Bergbau-Museum.
- Oppenheim, A. Leo
1967 Essay on Overland Trade in the First Millennium B. C. *Journal of Cuneiform Studies* 21:236-254.
- Özbal, Hadi
1985 Değirmentepe Metal, Cüruf ve Filiz Analizleri. In *Arkeometri Ünitesi Bilimsel Toplantısı Bildileri VI*. Pp. 101-113. Ankara: TÜBİTAK.
-
- 2009 New Analytical Data from Göltepe Crucibles. *TUBA-AR* 12(155-163).
- Özbal, Hadi, A. Adriaens, B. Earl, and B. Gedik
1999 Samsun, Amasya, Tokat Illeri Yüzey Araştırmaları. *Arkeometri Sonuçları Toplantısı* 21:47-54.
-
- 2002a Minor Metallic Components Associated with Anatolian Copper and Bronze Artifacts: Indications of the utilization of Polymetallic Ores. In *Archaeometry* 98. E. Jerem and K.T. Biro, eds. Pp. 433-438. BAR International Series 1043. Oxford: Archaeopress.
- Özbal, Hadi, H. Pehlivan, and B. Earl
2001 Durağan ve Bakırçay Arsenik Cevherleşmesinin Jeolojik, Mineralojik ve Kimyasal İncelenmesi. *Arkeometri Sonuçları Toplantısı* 22:29-40.

- Özbal, Hadi, Necip Pehlivan, Mieke Adriaens, Bilge Gedik-Uluocak, and Bryan Earl
2008 Metal Technologies During the Late Chalcolithic and Early Bronze Age in North Central Anatolia: İkiztepe A Case Study. In *Ancient Mining in Turkey and The Eastern Mediterranean*. Ü. Yalçın, H. Özbal, and A.G. Paşamehmetoğlu, eds. Pp. 65-85. Ankara: Atılım University.
- Özbal, Hadi, Necip Pehlivan, Bryan Earl, and Bilge Gedik
2002b Metallurgy at İkiztepe. In *Anatolian Metal II*. Ü. Yalçın, ed. Pp. 39-48. Bochum: Deutsches Bergbau-Museum.
- Özdoğan, Aslı
1999 Çayönü. In *Neolithic in Turkey. The Cradle of Civilization: New Discoveries*. M. Özdoğan and N. Başgelen, eds. Pp. 35-63. Istanbul: Arkeoloji ve Sanat Yayinlari.
- Özdoğan, Mehmet, and A. Özdoğan
1999 Archaeological Evidence on the Early Metallurgy at Çayönü Tepesi. In *The Beginnings of Metallurgy*. A. Hauptman, E. Pernicka, T. Rehren, and Ü. Yalçın, eds. Der Anschnitt 9. Bochum: Deutsches Bergbau-Museum.
- Özgüç, Nimet
1995 Silver and Copper Ingots from Acemhöyük. In *Beiträge zur Kulturgeschichte Vorderasiens. Festschrift für Rainer Michael Boehmer*. U. Finkbeiner, R. Dittmann, and H. Hauptmann, eds. Pp. 513-519. Mainz: von Zabern.
- Özgüç, Tahsin
1950 *Ausgrabungen in Kültepe: Bericht über die im Auftrage der Türkischen historischen Gesellschaft, 1948 durchgeführten Ausgrabungen*. Ankara: Türk Tarih Kurumu Basimevi.
- 1955 Report on a Workshop Belonging to the Late Phase of the Colony Period Ib. *Belleten* 73:77-80.
- 1959 *Kültepe-Kaniş: Aşur Ticaret Kolonilerinin Merkezinde Yapılan Yeni Araştırmalar / New researches at the center of the Assyrian trade colonies*. Ankara: Türk Tarih Kurumu Basimevi.
- 1964 New Finds from Horoztepe. *Anatolia* 8:1-25.
- 1986a Kültepe-Kaniş II: Eski Yakınođu'nun Ticaret Merkezinde Yeni Araştırmalar / New Researches at the Trading Center of the Ancient Near East. Ankara: Türk Tarih Kurumu.
- 1986b New Observations on the Relationship of Kültepe with Southeast Anatolia and North Syria During the Third Millennium B.C. In *Ancient Anatolia : Aspects of Change & Cultural Development, Essays in Honor of Machteld J. Mellink*. J.V. Canby, E. Porada, B.S. Ridgway, and T. Stech, eds. Pp. 31-47. Madison: University of Wisconsin Press.
- Öztürk, Hüseyin, and Nurullah Hanilçi
2009 Metallogenic Evaluation of Turkey: Implications for Tin Sources of Bronze Age Anatolia. *TUBA-AR* 12:105-116.

- Palmieri, A., and Gian Maria Di Nocera
 2000 The Metal Objects from the "Royal" Tomb at Arslantepe (Malatya-Turkey) and the Metalwork Development in the Early Bronze Age. In *Landscapes: Territories, Frontiers and Horizons in the Ancient Near East*. L. Milano, S. de Martino, F.M. Fales, and G.B. Lanfranchi, eds. Pp. 179-190. Padova: Sargon.
- Palmieri, A., Marcella Frangipane, Andreas Hauptmann, and K. Hess
 1999 Early Metallurgy at Arslantepe during the Late Chalcolithic and the Early Bronze Age IA - IB Periods. In *The Beginnings of Metallurgy*. A. Hauptmann, E. Pernicka, T. Rehren, and Ü. Yalçın, eds. Pp. 141-148. Der Anschnitt 9. Bochum: Deutsches Bergbau-Museum.
- Palmieri, A., Kemal Sertok, and Evgenij Chernykh
 1993 From Arslantepe Metalwork to Arsenical Copper Technology in Eastern Anatolia. In *Between the Rivers and Over the Mountains: Archaeologica Anatolica et Mesopotamica Alba Palmieri Dedicata*. M. Frangipane, H. Hauptmann, M. Liverani, P. Matthiae, and M. Mellink, eds. Pp. 573-599. Rome: Dipartimento di Scienze Storiche Archeologiche e Antropologiche dell'Antichità, Università di Roma La Sapienza.
- Pare, Christopher F. E.
 2000 Bronze and the Bronze Age. In *Metals Make the World Go Round: The Supply and Circulation of Metals in Bronze Age Europe*. C.F.E. Pare, ed. Pp. 1-38. Oxford: Oxbow Books.
- Parkinson, William A., Dimitri Nakassis, and Michael L. Galaty
 2013 Crafts, Specialists, and Markets in Mycenaen Greece: Introduction. *American Journal of Archaeology* 117:413-422.
- Payton, R.
 1991 The Uluburun Writing Board Set. *Anatolian Studies* 41:99-110.
- Pehlivan, N. A., and T. Alban
 1986 *Niğde Masifi Altın-Kalay Cevherleş ve Ağır Mineral Çalışmaları Ön Raporu*. Ankara: Maden Tetkik ve Arama Enstitüsü, unpublished report.
- Pernicka, Ernst
 1990 Gewinnung und Verbreitung der Metalle in prähistorischer Zeit. *Jahrbuch des Römisch-Germanischen Zentralmuseum* 37:21-129.
- 1998 Die Ausbreitung der Zinnbronze im 3. Jahrtausend. In *Mensch und Umwelt in der Bronzezeit Europas*. B. Hänsel, ed. Pp. 135-147. Kiel: Oetker-Voges Verlag.
- 2014 Provenance Determination of Archaeological Metal Objects. In *Archaeometallurgy in Global Perspective*. B.W. Roberts and C.P. Thornton, eds. Pp. 239-268. New York: Springer.
- Pernicka, Ernst, Friedrich Begemann, Sigrid Schmitt-Strecker, and Apostolos P. Grimanis
 1990 On the Composition and Provenance of Metal Artefacts from Poliochni on Lemnos. *Oxford Journal of Archaeology* 9(3):263-298.
- Pernicka, Ernst, Clemens Eibner, Önder Öztunalı, and Günther A. Wagner
 2003 Early Bronze Age Metallurgy in the North-East Aegean. In *Troia and the Troad*. G.A. Wagner, E. Pernicka, and H.-P. Uerpmann, eds. Pp. 143-172. Berlin: Springer-Verlag.

- Pernicka, Ernst, Thilo Rehren, and Sigrid Schmitt-Strecker
 1998 Late Uruk Silver Production by Cupellation at Habuba Kabira, Syria. In *Metallurgica Antiqua: In Honour of Hans-Gert Bachmann and Robert Maddin*. T. Rehren, A. Hauptmann, and J.D. Muhly, eds. Pp. 123-134. Der Anschnitt 8. Bochum: Deutsches Bergbau-Museum.
- Pernicka, Ernst, Klaus Schmidt, and Sigrid Schmitt-Strecker
 2002 Zum Metallhandwerk. In *Norstepe: Kleinfunde II*. K. Schmidt, ed. Pp. 115-137. Mainz: Verlag Philipp von Zabern.
- Pernicka, Ernst, Thomas C. Seeliger, Günther Wagner, Friedrich Begemann, Sigrid Schmitt-Strecker, Clemens Eibner, Önder Öztunalı, and István Baranyi
 1984 Archäometallurgische Untersuchungen in Nordwestanatolien. *Jahrbuch des Römisch-Germanisches Zentralmuseum* 31:533-599.
- Peyronel, Luca
 2010 Ancient Near Eastern Economics: The Silver Question Between Methodology and Archaeological Data. In *Proceedings of the 6th International Congress on the Archaeology of the Ancient Near East*. Pp. 925-948. Wiesbaden: Harrassowitz Verlag.
- Pollard, A. M., Catherine Batt, Ben Stern, and S. M. M. Young
 2007 *Analytical Chemistry in Archaeology*. Cambridge: Cambridge University Press.
- Postgate, J. N.
 2007 The Ceramics of Centralisation and Dissolution: a Case Study from Rough Cilicia. *Anatolian Studies* 57:141-150.
- Potter, Antony, and H. Doug Watts
 2011 Evolutionary Agglomeration Theory: Increasing Returns, Diminishing Returns, and the Industry Life Cycle. *Journal of Economic Geography* 11(3):417-455.
- Prange, M. K.
 2001 Vergleichende Untersuchungen zur Charakterisierung des omanischen Kupfers mittels chemischer und isotopischer Analysenmethoden. *Metalla* 8:1-126.
- Przeworski, Stefan
 1929 Die Lage von Pteria. *Archiv Orientalní* 1:312-315.
- Puchstein, Otto
 1912 *Boghasköi: Die Bauwerke*. Leipzig: Hinrichs.
- Pulak, Cemal
 2005 Das Schiffswrack von Uluburun. In *Das Schiff von Uluburun: Welthandel vor 3000 Jahren*. Ü. Yalçın, C. Pulak, and R. Slotta, eds. Pp. 55-102. Bochum: Deutsches Bergbau-Museum.
- Rademakers, Frederik
 2014 Heterogeneity in the Crucible. Some Methodological Issues for Reconstructing Ancient Crucible Metallurgy. Poster presented at the 40th International Symposium on Archaeometry, Los Angeles.
- Radivojević, Miljana, and Thilo Rehren
 2015 Paint it Black: The Rise of Metallurgy in the Balkans. *Journal of Archaeological Method and Theory*.
- Radivojević, Miljana, Thilo Rehren, Julka Kuzmanović-Cvetković, Marija Jovanović, and J. Peter Northover
 2013 Tainted Ores and the Rise of Tin Bronzes in Eurasia, c. 6500 Years Ago. *Antiquity* 87(338):1030-1045.

- Radivojević, Miljana, Thilo Rehren, Ernst Pernicka, Dušan Šljivar, Michael Brauns, and Dušan Borić
 2010 On the Origins of Extractive Metallurgy: New Evidence from Europe. *Journal of Archaeological Science* 37(11):2775-2787.
- Ramage, Andrew, and P. T. Craddock, eds.
 2000 *King Croesus' Gold: Excavations at Sardis and the History of Gold Refining*. London: British Museum Press.
- Redmond, Elsa M., and Charles S. Spencer
 2012 Chiefdoms at the Threshold: The Competitive Origins of the Primary State. *Journal of Anthropological Archaeology* 31(1):22-37.
- Rehren, T., and Miljana Radivojević
 2010 A Preliminary Report on the Slag Samples from Çamlıbel Tarlası. *Archäologischer Anzeiger* 2010:207-216.
- Rehren, Thilo, Loïc Boscher, and Ernst Pernicka
 2012 Large Scale Smelting of Speiss and Arsenical Copper at Early Bronze Age Arisman, Iran. *Journal of Archaeological Science* 39(6):1717-1727.
- Renfrew, Colin
 1969 The Autonomy of the South-East European Copper Age. *Proceedings of the Prehistoric Society* 35:12-47.
- 1973 *Before Civilization*. New York: Alfred A. Knopf.
- 2012 Systems of Value among Material Things: the Nexus of Fungibility and Measure. In *The Construction of Value in the Ancient World*. J.K. Papadopoulos and G. Urton, eds. Pp. 249-260. Los Angeles: Cotsen Institute of Archaeology Press.
- Rice, P. M.
 1981 Evolution of Specialized Pottery Production: A Trial Model. *Current Anthropology* 22(3):219-240.
- Roames, Jim
 2011 The Early Iron Age Metal Workshop at Tell Tayinat, Turkey. *MRS Proceedings* 1319:149-155.
- Roberts, Benjamin W.
 2011 Ancient Technology and Archaeological Cultures: Understanding the Earliest Metallurgy in Eurasia. In *Investigating Archaeological Cultures: Material Culture, Variability, and Transmission*. B.W. Roberts and M.V. Linden, eds. Pp. 137-150. New York: Springer.
- Roberts, Benjamin W., Christopher P. Thornton, and Vincent C. Pigott
 2009 Development of Metallurgy in Eurasia. *Antiquity* 83:1012-1022.
- Rohl, B. M.
 1996 Lead Isotope Data from the Isotracer Laboratory, Oxford: *Archaeometry Data Base 2, Galena from Britain and Ireland*. *Archaeometry* 38(1):165-180.
- Rothman, Mitchell S., ed.
 2001 *Uruk Mesopotamia and Its Neighbors*. Sante Fe: School of American Research Press.
- Sagona, Antonio, and Paul Zimansky
 2009 *Ancient Turkey*. London: Routledge.

- Şahoğlu, Vasif
 2005 The Anatolian Trade Network and the Izmir Region During the Early Bronze Age. *Oxford Journal of Archaeology* 24(4):339-361.
- Sams, G. Kenneth, and Mary M. Voigt
 2011 In Conclusion. In *The New Chronology of Iron Age Gordion*. C.B. Rose and G. Darbyshire, eds. Pp. 155-168. Philadelphia: University of Pennsylvania Museum of Archaeology and Anthropology.
- Sayre, E. V., E. C. Joel, M. J. Blackman, K. Aslıhan Yener, and Hadi Özbal
 2001 Stable Lead Isotope Studies of Black Sea Anatolian Ore Sources and Related Bronze Age and Phrygian Artefacts from Nearby Archaeological Sites: Appendix - New Taurus Ore Data. *Archaeometry* 43(1):77-115.
- Sayre, E. V., K. Aslıhan Yener, E. C. Joel, and I. L. Barnes
 1992 Statistical Evaluation of the Presently Accumulated Lead Isotope Data from Anatolia and Surrounding Regions. *Archaeometry* 34(1):73-105.
- Schachner, Andreas
 2008 Die Ausgrabungen in Bogazköy-Hattuša 2007. *Archäologischer Anzeiger* 2008:113-161.
- 2009a Das 16. Jahrhundert v. Chr. – eine Zeitenwende im hethitischen Zentralanatolien. *Istanbuler Mitteilungen* 59:9-34.
- 2009b Die Ausgrabungen in Bogazköy-Hattuša 2008. *Archäologischer Anzeiger* 2009:21-72.
- 2010 Die Ausgrabungen in Boğazköy-Ḫattuša 2009. *Archäologischer Anzeiger* 2010:161-221.
- 2011a *Hattuscha: Auf der Suche nach dem sagenhaften Großreich der Hethiter*. München: Beck.
- 2011b Von einer anatolischen Stadt zur Hauptstadt eines Großreichs – Entstehung, Entwicklung und Wandel Hattušas in hethitischer Zeit. *Mesopotamia* 46:79-101.
- 2012 Orta Anadolu’da Coğrafya ve Ekonomi: Hititlerin Bıçak Sırtındaki İmparatorluğu. *Colloquium Anatolicum* 11:25-54.
- 2013 Die Arbeiten in Boğazköy-Ḫattuša 2012. *Archäologischer Anzeiger* 2013(1):147-193.
- 2014 Die Ausgrabungen in Boğazköy-Hattuša 2013. *Archäologischer Anzeiger* 2014(1):93-168.
- 2015 Zu Hause beim GAL MEŞEDI in Ḫattuša. In *Saeculum. Gedenkschrift für Heinrich Otten anlässlich seines 100. Geburtstags*. A. Müller-Karpe, E. Rieken, and W. Sommerfeld, eds. Pp. 189-209. Wiesbaden: Otto Harrassowitz.

- , ed.
 in press-a *Ausgrabungen in der westlichen Oberstadt 1: Das mittlere Plateau zwischen Sarikale und Yenicekale*. Mainz: Philipp von Zabern.
- in press-b *Ausgrabungen und Untersuchungen an Yenicekale in der südwestlichen Oberstadt von Boğazköy-Hattuša (2006-2008)*. Mainz: Verlag Philipp von Zabern.
- Schmidt, Erich F.
 1929 Test Excavations in the City on Kerkenes Dagh. *American Journal of Semitic Languages and Literatures* 45(4):83-92.
- Schoop, Ulf-Dietrich
 1995 *Die Geburt des Hephaistos: Technologie und Kulturgeschichte neolithischer Metallverwendung im Vorderen Orient*. Espelkamp: Verlag Marie L. Leidorf.
- 1999 Aspects of Early Metal Use in Neolithic Mesopotamia. In *The Beginnings of Metallurgy*. A. Hauptman, E. Pernicka, T. Rehren, and Ü. Yalçın, eds. Pp. 31-36. Der Anschnitt 9. Bochum: Deutsches Bergbau Museum.
- 2005 *Das anatolische Chalkolithikum. Eine chronologische Untersuchung zur vorbronzezeitlichen Kultursequenz im nördlichen Zentralanatolien und den angrenzenden Gebieten*. Remshalden: Verlag BA Greiner.
- 2008 Ausgrabungen in Çamlıbel Tarlası 2007, In A. Schachner (Ed.), Die Ausgrabungen in Boğazköy-Hattuša 2007. *Archäologischer Anzeiger* 2008:148-157.
- 2009 Ausgrabungen in Çamlıbel Tarlası, In A. Schachner (Ed.), Die Ausgrabungen in Boğazköy-Hattuša 2008. *Archäologischer Anzeiger* 2009:56-69.
- 2010 Ausgrabungen in Çamlıbel Tarlası 2009, In A. Schachner (Ed.), Die Ausgrabungen in Boğazköy-Hattuša 2009. *Archäologischer Anzeiger* 2010:191-216.
- 2011 Çamlıbel Tarlası, ein metallverarbeitender Fundplatz des vierten Jahrtausends v. Chr. im nördlichen Zentralanatolien. In *Anatolian Metal V*. Ü. Yalçın, ed. Pp. 53-68. Bochum: Deutsches Bergbau-Museum.
- Schoop, Ulf-Dietrich, and Jürgen Seeher
 2006 Absolute Chronologie in Boğazköy-Hattuša: Das Potential der Radiokarbonaten. In *Strukturierung und Datierung in der hethitischen Archäologie : Voraussetzungen, Probleme, neue Ansätze*. D.P. Mielke, U.-D. Schoop, and J. Seeher, eds. Pp. 53-75. Istanbul: Ege Yayinlari: Deutsches Archäologisches Institut Abteilung Istanbul.
- Schwitzer, C. M., and C. F. Cheng
 1962 Bactrian Nickel and Chinese Bamboo. *American Journal of Archaeology* 66(1):87-92.
- Scott, David A.
 1991 *Metallography and Microstructure of Ancient and Historic Metals*. Los Angeles: Getty Conservation Institute.

-
- 2011 *Ancient Metals: Microstructure and Metallurgy, Volume 1*. Los Angeles: Conservation Science Press.
- Seeden, H.
1980 *The Standing Amed Figurines in the Levant*. Munich: Beck.
- Seeher, Jürgen
1995 Die Ausgrabungen in Boğazköy-Hattusa 1994. *Archäologischer Anzeiger* 1995:597-625.
-
- 1997 Die Ausgrabungen in Boğazköy-Hattuša 1996. *Archäologischer Anzeiger* 1997:317-341.
-
- 1998 Die Ausgrabungen in Boğazköy-Hattuša 1997. *Archäologischer Anzeiger* 1998(2):215-241.
-
- 1999 Die Ausgrabungen in Boğazköy-Hattuša 1998 und ein neuer topographischer Plan des Stadtgeländes. *Archäologischer Anzeiger* 1999(3):317-344.
-
- 2000 Die Ausgrabungen in Boğazköy-Hattuša 1999. *Archäologischer Anzeiger* 2000:355-376.
-
- 2001 Die Zerstörung der Stadt Hattuša. In *Akten des IV. Internationalen Kongresses für Hethitologie Würzburg. 4.-8. Oktober 1999*. G. Wilhelm, ed. Pp. 623-634. Studien zu den Boğazköy-Texten 45. Wiesbaden: Harrassowitz.
-
- 2003 Die Ausgrabungen in Boğazköy-Hattusa 2002. *Archäologischer Anzeiger* 2003(1):1-24.
-
- 2004 Die Ausgrabungen in Boğazköy-Hattusa 2003. *Archäologischer Anzeiger* 2004(1):59-76.
-
- 2005 Die Ausgrabungen in Boğazköy-Hattusa 2004. *Archäologischer Anzeiger* 2005(1):63-80.
-
- 2006a Chronology in Hattuša: New Approaches to an Old Problem. In *Strukturierung und Datierung in der hethitischen Archäologie : Voraussetzungen, Probleme, neue Ansätze*. D.P. Mielke, U.-D. Schoop, and J. Seeher, eds. Pp. 197-213. Istanbul: Ege Yayınları: Deutsches Archäologisches Institut Abteilung Istanbul.
-
- 2006b Der Althethitische Getreidesilokomplex. In *Ergebnisse der Grabungen an den Ostteichen und am mittleren Büyükkale-Nordwesthang in den Jahren 1996-2000*. J. Seeher, ed. Pp. 45-94. Boğazköy-Berichte 8. Mainz: Verlag Philipp von Zabern.
-
- 2006c Die Ausgrabungen in Boğazköy-Hattusa 2005. *Archäologischer Anzeiger* 2006:171-187.

- 2006d Hattuša-Tuthaliya-Stadt? Argumente für eine Revision der Chronologie der hethitischen Hauptstadt. In *The Life and Times of Hattusili III and Tuthaliya IV. Proceedings of a Symposium Held in Honour of J. de Roos, December 12–13, 2003*. T.P.J. van den Hout, ed. Pp. 131-146. Leiden: Netherlands Institute for the Near East.
- 2008 Abschied von Gewußtem. Die Ausgrabungen in Hattuša am Beginn des 21. Jahrhunderts. In *Hattuša-Boğazköy: Das Hethiterreich im Spannungsfeld des Alten Orients. 6. Internationales Colloquium der Deutschen Orient-Gesellschaft, 22.-24. März 2006, Würzburg*. G. Wilhelm, ed. Pp. 1-13. Wiesbaden: Harrassowitz.
- 2010 After the Empire: Observations on the Early Iron Age in Central Anatolia. In *Luwian and Hittite Studies Presented to J. David Hawkins on the Occasion of His 70th Birthday*. Pp. 220-229. Tel Aviv: Emery and Claire Yass Publications in Archaeology, Institute of Archaeology, Tel Aviv University.
- Seeliger, Thomas C., Ernst Pernicka, G. A. Wagner, Friedrich Begemann, Sigrid Schmitt-Strecker, Clemens Eibner, Önder Öztunalı, and István Baranyi
1985 Archäometallurgische Untersuchungen in Nord- und Ostanatolien. *Jahrbuch des Römisch-Germanisches Zentralmuseum* 32:597-659.
- Seidl, U.
1988 Urartu as a Bronzeworking Centre. In *Bronzeworking Centres of Western Asia, c. 1000-539 B.C.* J.E. Curtis, ed. Pp. 169-176. London: British Museum.
- Selover, Stephanie
2015 *Excavating War: The Archaeology of Conflict in Early Chalcolithic to Early Bronze III Central and Southeastern Anatolia*, Near Eastern Languages and Civilizations, Unpublished PhD Dissertation, University of Chicago.
- Şentürk, Şennur, Nalan Örki, and Eric Jean
2001 *From Boğazköy to Karatepe : Hittitology and the Discovery of the Hittite World*. Istanbul: Yapı Kredi Kültür Sanat Yayıncılık.
- Şenyurt, S. Yücel
2006 Bronze and Iron-Working in Early Iron Age Anatolia: Observations at Büyükdardıç. *Antiquity* 80(310):Online Project Gallery
<http://antiquity.ac.uk/projgall/senyurt/index.html>.
- Şenyurt, S. Yücel, Pervin Arıkan, and Abdullah Zararsız
2006 Analysis of Archaeo-Metallurgical Finds from Büyükdardıç with X-Ray Fluorescence Technique. In *Büyükdardıç. An Early Iron Age Hilltop Settlement in Eastern Anatolia*. S.Y. Şenyurt, ed. Baku-Tbilisi-Ceyhan Crude Oil Pipeline Project Publications of Archaeological Salvage Excavations. Ankara: Gazi University Research Centre for Archaeology.
- Sherratt, Andrew, and Susan Sherratt
1991 From Luxuries to Commodities: The Nature of Mediterranean Bronze Age Trading Systems. In *Bronze Age Trade in the Mediterranean*. N.H. Gale, ed. Jonsered: Paul Astroms Forlag.
- Sherratt, Susan, and Andrew Sherratt
1993 The Growth of the Mediterranean Economy in the Early First Millennium BC. *World Archaeology* 24(3):361-378.

Siegelová, Jana

1986 *Hethitische Verwaltungspraxis im Lichte der Wirtschafts- und Inventairdokumente*. Prague: Národní Muzeum v Praze.

1993 Metalle und Metallurgie. A. II. In den heth. Texten. *Reallexikon der Assyriologie und Vorderasiatischen Archäologie* 8(1-2):112-119.

2005 Metalle in hethitischen Texten. In *Anatolian Metal III*. Ü. Yalçın, ed. Pp. 35-39. Bochum: Deutsches Bergbau Museum.

2008 Metals in Hittite Records. In *Ancient Mining in Turkey and the Eastern Mediterranean*. Ü. Yalçın, H. Özbal, and A.G. Paşamehmetoğlu, eds. Pp. 43-56. Ankara: Atılım University.

Siegelová, Jana, and Hidetoshi Tsumoto

2011 Metals and Metallurgy in Hittite Anatolia. In *Insights into Hittite History and Archaeology*. H. Genz and D.P. Mielke, eds. Pp. 275-300. Leuven: Peeters.

Slotta, Rainer

2001 Zur Geschichte des Nickels. In *250 Jahre Nickel: vom "nickel" zum "EURO". Nickel als Münzmetall*. E. Auer, S. Müller, and R. Slotta, eds. Pp. 29-57. Bochum: Deutsches Bergbau-Museum.

Smith, Adam

2003 *The Political Landscape: Constellations of Authority in Early Complex Polities*. Berkeley: University of California Press.

Smith, C. S.

1973 An Examination of the Arsenic-Rich Coating on a Bronze Bull from Horoztepe. In *Application of Science in Examination of Works of Art*. W.J. Young, ed. Pp. 96-102. Boston: Museum of Fine Arts.

Smith, Michael E.

2004 The Archaeology of Ancient State Economies. *Annual Review of Anthropology* 33:73-102.

Smith, Monica L.

2005 Networks, Territories, and the Cartography of Ancient States. *Annals of the Association of American Geographers* 95(4):832-849.

2007 Territories, Corridors, and Networks: A Biological Model for the Premodern State. *Complexity* 12(4):28-35.

Smith, Richard

1996 An Analysis of the Processes for Smelting Tin. *Mining History: The Bulletin of the Peak District Mines Historical Society* 13(2):91-99.

Solecki, R. S., R. L. Solecki, and A. P. Agelarakis

2004 *The Proto-neolithic Cemetary in Shanidar Cave*. Texas: Texas A&M University Press.

Solecki, Ralph

1969 A Copper Mineral Pendant from Northern Iraq. *Antiquity* 43:311-314.

- Sommer, F., and A. Falkenstein
 1938 *Die hethitisch-akkadische Bilingue des Hattusili I (Labarna II.)*. Munich: Abhandlung der Bayerischen Akademie der Wissenschaften.
- Spencer, Charles S.
 2003 War and Early State Formation in Oaxaca, Mexico. *Proceedings of the National Academy of Sciences* 100(20):11185-11187.
- 2010 Territorial Expansion and Primary State Formation. *Proceedings of the National Academy of Sciences* 107(16):7119-7126.
- Stanish, Charles
 2003 *Ancient Titicaca: The Evolution of Complex Society in Southern Peru and Northern Bolivia*. Berkeley: University of California Press.
- Stanish, Charles, and Abigail Levine
 2011 War and Early State Formation in the Northern Titicaca Basin, Peru. *Proceedings of the National Academy of Sciences* 108(34):13901-13906.
- Steadman, Sharon R., Gregory McMahon, Jennifer C. Ross, Marcia Cassis, Jeffrey D. Geyer, Benjamin Arbuckle, and Madelynn Von Baeyer
 2013 The 2009 and 2012 Seasons of Excavation at Çadır Höyük on the Anatolian North Central Plateau. *Anatolica* 39(113-167).
- Steadman, Sharon R., Jennifer C. Ross, Gregory McMahon, and Ronald Lee Gorny
 2008 Excavations on the North Central Plateau: The Chalcolithic and Early Bronze Age Occupation at Çadır Höyük. *Anatolian Studies* 47-86.
- Stech, Tamara
 1999 Aspects of Early Metallurgy in Mesopotamia and Anatolia. In *The Archaeometallurgy of the Asian Old World*. V.C. Pigott, ed. Pp. 59-72. University Monographs No. 89. Philadelphia: University Museum.
- Stein, G. J.
 2005 The Political Economy of Mesopotamian Colonial Encounters. In *The Archaeology of Colonial Encounters*. G.J. Stein, ed. Pp. 143-171. Santa Fe: School of American Research Press.
- Stein, Gil J.
 1994 Economy, Ritual, and Power in 'Ubaid Mesopotamia. In *Chiefdoms and Early States in the Near East*. G. Stein and M.S. Rothman, eds. Pp. 35-46. Madison: Prehistory Press.
- 1999 *Rethinking World Systems: Diasporas, Colonies, and Interaction in Uruk Mesopotamia*. Tucson: University of Arizona Press.
- 2001 Understanding Ancient State Societies in the Old World. In *Archaeology at the Millennium: A Sourcebook*. G.M. Feinman and T.D. Price, eds. Pp. 353-379. New York: Springer.
- Steinberg, A.
 1981 Analyses of Selected Gordion Bronzes. In *The Three Great Tumuli*. R.S. Young, ed. Pp. 286-289. The Gordion Excavations Final Reports 1. Philadelphia: University Museum Press.

- Stos-Gale, Z. A., and N. H. Gale
 2009 Metal Provenancing Using Isotopes and the Oxford Archaeological Lead Isotope Database (OXALID). *Archaeological and Anthropological Sciences* 1(3):195-213.
- Stos-Gale, Z. A., N. H. Gale, and N. Annetts
 1996 Lead Isotope Data from the Isotrace Laboratory, Oxford: *Archaeometry Data Base 3, Ores from the Aegean, Part 1. Archaeometry* 38(2):381-390.
- Stos-Gale, Z. A., N. H. Gale, N. Annetts, T. Todorov, P. Lilov, A. Raduncheva, and I. Panayotov
 1998 Lead Isotope Data from the Isotrace Laboratory, Oxford: *Arcaeometry Data Base 5, Ores from Bulgaria. Archaeometry* 40(1):217-226.
- Stos-Gale, Z. A., N. H. Gale, J. Houghton, and R. Speakman
 1995 Lead Isotope Data from the Isotrace Laboratory, Oxford: *Arcaeometry Data Base 1, Ores from the Western Mediterranean. Archaeometry* 37(2):407-415.
- Stos-Gale, Z. A., G. Maliotis, N. H. Gale, and N. Annetts
 1997 Lead Isotope Characteristics of the Cyprus Copper Ore Deposits Applied to Provenance Studies of Copper Oxhide Ingots. *Archaeometry* 39(1):83-123.
- Stos-Gale, Zofia. A., Noel. H. Gale, and G. R. Gilmore
 1984 Early Bronze Age Trojan Metal Sources and Anatolians in the Cyclades. *Oxford Journal of Archaeology* 3(3):23-43.
- Strahm, Christian
 1988 Chalkolithikum und Metallikum. *Rassegna di Archeologia* 7:175-192.
- Strahm, Christian, and Andreas Hauptmann
 2009 The Metallurgical Developmental Phases in the Old World. In *Metals and Societies. Studies in Honour of Barbara S. Ottaway*. T.K. Kienlin and B.W. Roberts, eds. Pp. 116-128. Bonn: Habelt.
- Strupler, Néhémie
 2013 Vorratshaltung im mittelbronzezeitlichen Boğazköy - Spiegel einer häuslichen und regionalen Ökonomie. *Istanbuler Mitteilungen* 63:17-50.
- Süel, Aygöl
 1992 Ortaköy: Eine hethitische Stadt mit hethitischen und hurritischen Tontafelentdeckungen. In *Hittite and Other Anatolian and Near Eastern Studies in Honour of Sedat Alp*. H. Otten, E. Akurgal, H. Ertem, and A. Süel, eds. Pp. 487-492. Ankara.
- Summers, Françoise, and Geoffrey Summers, eds.
 2011 *Kerkenes News 13, 2010*. Ankara: METU Press.
- Summers, Geoffrey, ed.
 in press *Excavations at the Cappadocia Gate*. Chicago: Oriental Institute Press.
- Summers, Geoffrey D.
 1997 The Identification of the Iron Age City on Kerkenes Dag in Central Anatolia. *Journal of Near Eastern Studies* 56(2):81-94.
- 2006a Aspects of Material Culture at the Iron Age Capital on the Kerkenes Dağ in Central Anatolia. *Ancient Near Eastern Studies* 43:164-202.
- 2006b Phrygian Expansion to the East: Evidence of Cult from Kerkenes Dağ. *Baghdader Mitteilungen* 37:647-658.

-
- 2007 Public Spaces and Large Halls at Kerkenes. In *Anatolian Iron Ages 6: The Proceedings of the Sixth Anatolian Iron Ages Colloquium Held at Eskişehir, 16-20 August 2004*. A. Çilingiroğlu and A. Sagona, eds. Pp. 241-259. Leuven: Peeters Press.
-
- 2008 Periodisation and Terminology in the Central Anatolia Iron Age: Archaeology, History and Audiences. *Ancient Near Eastern Studies* 45:202-217.
-
- 2009 Between Urartu and Phrygia: The North-Central Anatolian Plateau in the Iron Age. In *Studies in Honour of Altan Çilingiroğlu: A Life Dedicated to Urartu on the Shores of the Upper Sea*. H. Sağlatimur, E. Abay, F. Dedeoğlu, M. Erdalkıran, M.B. Baştürk, and E. Konakçı, eds. Pp. 657-671. Istanbul: Arkeoloji ve Sanat Yayınları.
- Summers, Geoffrey D., and M. E. F. Summers
1998 The Kerkenes Dağ Project. In *Ancient Anatolia: Fifty Years' Work by the British Institute of Archaeology at Ankara*. R. Matthews, ed. Pp. 177-194. London: British Institute of Archaeology at Ankara.
-
- 2006 Aspects of Urban Design at the Iron Age City on the Kerkenes Dağ as Revealed by Geophysical Survey. *Anatolia Antiqua* 14:71-88.
- Summers, Geoffrey D., and M. E. Françoise Summers
2008 A Preliminary Interpretation of Remote Sensing and Selective Excavation at the Palatial Complex, Kerkenes. *Anatolia Antiqua* 16:53-76.
- Summers, Geoffrey D., M. E. Françoise Summers, and Scott Andrew Branting
2004 Megarons and Associated Structures at Kerkenes Dağ: an Interim Report. *Anatolia Antiqua* 12:7-41.
- Summers, Geoffrey, and Françoise Summers
2012 Kerkenes News 14, 2011. Ankara: METU Press.
-
- 2013 The Kale at Kerkenes Dag: An Iron Age Capital in Central Anatolia. In *Cities and Citadels in Turkey: From the Iron Age to the Seljuks*. S. Redford and N. Ergin, eds. Pp. 137-159. Leuven: Peeters.
- Tadmor, Miriam, Dan Kedem, Friedrich Begemann, Andreas Hauptmann, Ernst Pernicka, and Sigrid Schmitt-Strecker
1995 The Naḥal Mishmar Hoard from the Judean Desert: Technology, Composition, and Provenance *Atiqot* 27:95-148.
- Thornton, Christopher P.
2007 Of Brass and Bronze in Prehistoric Southwest Asia. In *Metals and Mines: Studies in Archaeometallurgy*. S. La Niece, D. Hook, and P.T. Craddock, eds. Pp. 123-135. London: Archetype Publications.
-
- 2009 The Emergence of Complex Metallurgy on the Iranian Plateau: Escaping the Levantine Paradigm. *Journal of World Prehistory* 22(3):301-327.
-
- 2010 The Rise of Arsenical Copper in Southeastern Iran. *Iranica Antiqua* 45:31-50.

- Thornton, Christopher P., Thilo Rehren, and V. C. Pigott
 2009 The Production of Speiss (Iron Arsenide) during the Early Bronze Age in Iran. *Journal of Archaeological Science* 26(2):308-316.
- Toteva, Galya Dechkova
 2007 *Local Cultures of Late Achaemenid Anatolia*, Unpublished Ph.D. Dissertation, University of Minnesota.
- Twilley, John
 1996 Scientific Analysis of Six Bronze Fibulae from Kaman-Kalehöyük. *Anatolian Archaeological Studies* 5:237-250.
- Tylecote, R. F.
 1976 *A History of Metallurgy*. London: The Metals Society.
- Ünal, Ahmet, A. Ertekin, and İ Ediz
 1992 The Hittite Sword from Bogazkoy-Hattusa, found 1991 and its Akkadian Inscription. *Müze-Museum* 4:46-52.
- Ur, Jason A.
 2010 *Urbanism and Cultural Landscapes in Northeastern Syria: The Tell Hamoukar Survey, 1999-2001*. Chicago: Oriental Institute Press.
- van de Mierop, Marc
 2014 Silver as a Financial Tool in Ancient Egypt and Mesopotamia. In *Explaining Monetary and Financial Innovation*. P. Bernholz and R. Vaubel, eds. Pp. 17-29. New York: Springer.
- van den Hout, Theo P. J.
 2006 Administration in the Reign of Tuthaliya IV and the Later Years of the Hittite Empire. In *The Life and Times of Hattusili III and Tuthaliya IV. Proceedings of a Symposium held in Honour of J. De Roos, 12-13 December 2003*. T.P.J. van den Hout, ed. Pp. 77-106. Leiden: Nederlands Instituut Voor Het Nabije Oosten.
- Vanden Berghe, L.
 1970 La Nécropole de Kalleh Nisar. *Archéologia* 32:64-73.
- Vandiver, P., K. Aslıhan Yener, and May Leopold
 1992 Third Millennium B.C. Tin Processing Debris from Göltepe (Anatolia). *Materials Issues in Art and Archaeology* III:545-569.
- Veenhof, K. R.
 2008 *Mesopotamia: The Old Assyrian Period*. Fribourg: Academic Press.
- Veenhof, Klaas R.
 1997 "Modern" Features in Old Assyrian Trade. *Journal of the Economic and Social History of the Orient* 40(4):336-366.
- 2003 *The Old Assyrian List of Year Eponyms from Karum Kanish and its Chronological Implications*. Ankara: Türk Tarih Kurumu.
- 2014 Silver in Old Assyrian Trade: Shapes, Qualities and Purification. In *Studies in Economic and Social History of the Ancient Near East in Memory of Péter Vargyas*. Z. Csabai, ed. Pp. 393-422. Budapest: L'Harmattan.

- Vidale, Massimo, and Heather M.-L. Miller
 2000 On the Development of Indus Technical Virtuosity and Its Relation to Social Structure. In *South Asian Archaeology 1997*. M. Taddei and G. de Marco, eds. Pp. 115-132. Rome: Istituto Italian per l’Africa e l’Oriente & Istituto Universitario Orientale, Naples.
- Voigt, Mary, and Robert C. Henrickson
 2000a Formation of the Phrygian State: The Early Iron Age at Gordion. *Anatolian Studies* 50:37-54.
- Voigt, Mary M., and Robert C. Henrickson
 2000b The Early Iron Age at Gordion: The Evidence from the Yassihöyük Sequence. In *The Sea Peoples and their World: A Reassessment*. E.D. Oren, ed. Pp. 327-360. Philadelphia: University of Pennsylvania Museum of Archaeology and Anthropology.
- von Luschan, Felix, and Walter Andrae
 1943 *Ausgrabungen in Sendschirli: Die Kleinfunde von Senschirli*. Volume 5.
- Wagner, G. A., Friedrich Begemann, Clemens Eibner, Joachim Lutz, Önder Öztunalı, Ernst Pernicka, and Sigrid Schmitt-Strecker
 1986 Geochemische und Isotopische Charakteristika Früher Rohstoffquellen für Kupfer, Blei, Silber und Gold in der Türkei. *Jahrbuch des Römisch-Germanisches Zentralmuseum* 33:723-752.
- 1989 Archäometallurgische Untersuchungen an Rohstoffquellen des Frühen Kupfers Ostanatoliens. *Jahrbuch des Römisch-Germanisches Zentralmuseum* 36:637-686.
- Wagner, Günther A. , Irmtud Wagner, Önder Öztunalı, Sigrid Schmitt-Strecker, and Friedrich Bergemann
 2003 Archäometallurgischer Bericht über Feldforschung in Anatolien und bleiisotopische Studien an Erzen und Schlacken. In *Man and Mining - Mensch und Bergbau*. T. Stöllner, G. Körlin, G. Steffens, and J. Cierny, eds. Pp. 475-494. Bochum: Deutsches Bergbau-Museum.
- Wagner, Günther A., and Önder Öztunalı
 2000 Prehistoric Copper Sources in Turkey. In *Anatolian Metals I*. Ü. Yalçın, ed. Pp. 31-67. Bochum: Deutsches Bergbau-Museum.
- Wagner, Günther A., Ernst Pernicka, Thomas C. Seeliger, Önder Öztunalı, István Baranyi, Friedrich Begemann, and Sigrid Schmitt-Strecker
 1985 Geologische Untersuchungen zur Frühen Metallurgie in NW-Anatolien. *Bulletin of the Mineral Research and Exploration Institute of Turkey* 101/102:45-81.
- Waldbaum, Jane C
 1999 The Coming of Iron in the Eastern Mediterranean: Thirty Years of Archaeological and Technological Research. In *The Archaeometallurgy of the Asian Old World*. V.C. Pigott, ed. Pp. 15-26. University Monographs No. 89. Philadelphia: University Museum.
- Weeks, Lloyd
 1999 Lead isotope analyses from Tell Abraç, United Arab Emirates: new data regarding the 'tin problem' in Western Asia. *Antiquity* 73(279):49-64.
- 2004 *Early Metallurgy of the Persian Gulf*. Leiden: Brill.

- Weigand, P. C., G. Harbottle, and E. V. Sayre
 1977 Turquoise Sources and Source Analysis: Mesoamerica and the Southwestern U.S.A. In *Exchange Systems in Prehistory*. T.K. Earle and J.E. Ericson, eds. Pp. 15-34. New York: Academic Press.
- Wenke, Robert
 1989 Egypt: Origins of Complex Societies. *Annual Review of Anthropology* 18:129-155.
- Wilhelm, Gernot
 1997 *Keilschrifttext aus Gebäude A*. Rahden: Verlag Marie Leidorf.
- Wilkinson, D.
 2003a Civilizations as Networks: Trade, War, Diplomacy, and Command-Control States-systems Bonded by Influence, Alliance, and War Relations. *Complexity* 8(1):82-86.
- Wilkinson, T. J.
 2003b *Archaeological Landscapes of the Near East*. Tucson: University of Arizona Press.
- Willcox, George H.
 1974 A History of Deforestation as Indicated by Charcoal Analysis of Four Sites in Eastern Anatolia. *Anatolian Studies* 24:117-133.
- 2002 Evidence for Ancient Forest Cover and Deforestation from Charcoal Analysis of Ten Archaeological Sites on the Euphrates. In *Charcoal Analysis: Methodological Approaches, Paleoecological Results and Wood Uses: Proceedings of the Second International Meeting of Anthropology, Paris, September 2000*. S. Thiébaud, ed. Pp. 141-145. BAR International Series 1063. Oxford: Archaeopress.
- Wittke, Anne-Maria
 2004 *Mušker und Phryger: Ein Beitrag zur Geschichte Anatoliens vom 12. bis zum 7. Jh. v. Chr.* Wiesbaden: Dr. Ludwig Reichert Verlag.
- Wright, Henry T., Richard W. Redding, and Susan M. Pollock
 1989 Monitoring interannual variability: an example from the period of early state development in southwestern Iran. In *Bad Year Economics: Cultural Responses To Risk And Uncertainty*. P. Halstead and J. O'Shea, eds. Pp. 106-113. Cambridge: Cambridge University Press.
- Yakar, Jak
 1984 Regional and Local Schools of Metalwork in Early Bronze Age Anatolia: Part I. *Anatolian Studies* 34:59-86.
- 1985 Regional and Local Schools of Metalwork in Early Bronze Age Anatolia: Part II. *Anatolian Studies* 35:25-38.
- Yalçın, Ünsal
 2000 Frühchalkolitische Metallfunde von Mersin-Yumuktepe: Beginn der extraktiven Metallurgie? *TUBA-AR* 3:111-130.
- 2010 Alacahöyük İlk Tunç Çağı Kral Mezarları Üzerine. *Çorum Kazı ve Araştırmalar Sempozyumu* 1:55-64.

- 2012 Alacahöyük İTÇ Kral Mezarları Üzerine II: Idoller. *Çorum Kazı ve Araştırmalar Sempozyumu 2*:111-122.
- Yalçın, Ünsal, and Önder İpek
2011 Derekutuğun Eski Maden İşletmeleri 2010 Dönemi Kazı Çalışmaları. *Kazı Sonuçları Toplantısı* 33(2):219-238.
- Yalçın, Ünsal, and Alexander Maass
2013 Prähistorische Kupfergewinnung in Derekutuğun, Anatolien. In *Anatolian Metal VI*. Ü. Yalçın, ed. Pp. 153-194. Bochum: Deutsches Bergbau-Museum.
- Yalçın, Ünsal, and Hadi Özbal
2009 Ein Neues Zinnvorkommen in Kayseri-Hisarçık, Zentralanatolien: Ein Vorbericht. *TÜBA-AR* 12:117-122.
- Yalçın, Ünsal, and Ernst Pernicka
1999 Frühneolithische Metallurgie von Aşıklı Höyük. In *The Beginnings of Metallurgy*. A. Hauptman, E. Pernicka, T. Rehren, and Ü. Yalçın, eds. Pp. 45-54. Der Anschnitt 9. Bochum: Deutsches Bergbau-Museum.
- Yalçın, Ünsal, Cemal Pulak, and Rainer Slotta, eds.
2005 *Das Schiff von Uluburun: Welthandel vor 3000 Jahren*. Bochum: Deutsches-Bergbau Museum.
- Yalçın, Ünsal, and H. Gönül Yalçın
2009 Evidence for Early Use of Tin at Tülintepe in Eastern Anatolia. *TUBA-AR* 12:123-142.
- Yener, K. Aslıhan
1986 The Archaeometry of Silver in Anatolia: The Bolkardağ Mining District. *American Journal of Archaeology* 90(4):469-472.
- 1995 Swords, Armor, and Figurines: A Metalliferous View from the Central Taurus. *The Biblical Archaeologist* 58(2):101-107.
- 2000 *The Domestication of Metals: The Rise of Complex Metal Industries in Anatolia*. Leiden: Brill.
- 2009 Strategic Industries and Tin in the Ancient Near East: Anatolia Updated. *TUBA-AR* 12:143-154.
- , ed.
2013 *Across the Border: Late Bronze-Iron Age Relations between Syria and Anatolia*. Leuven: Peeters.
- Yener, K. Aslıhan, Christopher Edens, Timothy P. Harrison, J. Verstraete, and Tony J. Wilkinson
2000 The Amuq Valley Regional Project, 1995-1998. *American Journal of Archaeology* 104(2):163-220.
- Yener, K. Aslıhan, Ayşe Emel Geçkinli, and Hadi Özbal
1996 A Brief Survey of Anatolian Metallurgy Prior to 500 BC. In *Archaeometry 94: The Proceedings of the 29th International Symposium on Archaeometry*. Ş. Demirci, A.M. Özer, and G.D. Summers, eds. Ankara: Türkiye Bilimsel ve Teknik Araştırma Kurumu.

- Yener, K. Aslıhan, Fikri Kulakoğlu, Evren Yazgan, Ryoichi Kontani, Yuichi S. Hayakawa, Joseph W. Lehner, Gonca Dardeniz, Güzel Öztürk, Michael Johnson, Ergün Kaptan, and Abdullah Hacı
- 2015 The Discovery of New Tin Mines and Production Sites near Kültepe, Ancient Kanesh in Turkey: a Third Millennium BC Highland Production Model. *Antiquity*.
- Yener, K. Aslıhan, and Hadi Özbal
- 1986 Bolkardağ Mining District Survey of Silver and Lead in Ancient Anatolia. In *Proceedings of the 24th International Archaeometry Symposium*. J.S. Olin and M.J. Blackman, eds. Pp. 309-320. Washington: Smithsonian Institution Press.
-
- 1987 Tin in the Turkish Taurus Mountains: The Bolkardağ Mining District. *Antiquity* 61(232):64-71.
- Yener, K. Aslıhan, Hadi Özbal, B. Earl, and A. Adriaens
- 2003 The Analyses of Metalliferous Residues, Crucible Fragments, Experimental Smelts, and Ores from Kestel Tin Mine and the Tin Processing Site of Göltepe. In *Mining and Metal Production Through the Ages*. P.T. Craddock and J. Lang, eds. Pp. 181-197. London: The British Museum Press.
- Yener, K. Aslıhan, Hadi Özbal, Ergün Kaptan, Necip Pehlivan, and Martha Goodway
- 1989 Kestel: an Early Bronze Age Source of Tin Ore in the Taurus Mountains, Turkey. *Science* 244:200-203.
- Yener, K. Aslıhan, E. V. Sayre, E. C. Joel, Hadi Özbal, I. L. Barnes, and R. H. Brill
- 1991 Stable Lead Isotope Studies of Central Taurus Ore Sources and Related Artifacts from Eastern Mediterranean Chalcolithic Bronze Age Sites. *Journal of Archaeological Science* 18:541-577.
- Yener, K. Aslıhan, and Pamela B. Vandiver
- 1993 Tin Processing at Göltepe, an Early Bronze Age Site in Anatolia. *American Journal of Archaeology* 97(2):207-238.
- Yıldırım, Tayfun
- 2006 An Early Bronze Age Cemetery at Resuloğlu, Near Uğurludağ, Çorum. A Preliminary Report of the Archaeological Work Carried Out Between Years 2003-2005. *Anatolia Antiqua* 14:1-14.
- Yıldırım, Tayfun, and Thomas Zimmermann
- 2006 News from the Hatti Heartland - The Early Bronze Age Necropoleis of Kalinkaya, Resuloğlu, and Anatolian Metalworking Advances in the Late 3rd Millennium BC. *Antiquity* 80(309).
- Young, Rodney S.
- 1981 *Three Great Early Tumuli*. Volume I. Philadelphia: University Museum.
- Zimansky, Paul
- 1985 *Ecology and Empire: The Structure of the Urartian State*. Chicago: Oriental Institute.
- Zimmermann, Thomas
- 2006 Zu den sogenannten "Pilztaufkeulen" der anatolischen Frühbronzezeit, Zeremonialgerät zwischen Halysbogen and Kuban. *Eurasia Antiqua* 12:127-135.

-
- 2007 Kalinkaya-Toptaštepe, eine chalkolithisch-frühbronzezeitliche Siedlung mit Nekropole im nördlichen Zentralanatolien: Die Grabfunde der Kampagnen von 1971 und 1973. *Istanbul Mitteilungen* 57:7-26.
-
- 2009 Frühmetallzeitliche Eliten zwischen Ostägäis und Taurusgebirge im 3. Jahrtausend v. Chr. – Versuch einer kritischen Bestandsaufnahme. In *Aufstieg und Untergang. Zwischenbilanz des Forschungsschwerpunktes „Studien zu Genese und Struktur von Eliten in vor- und frühgeschichtlichen Gesellschaften*. M. Egg and D. Quast, eds. Pp. 1-29. Mainz: Römisch-Germanischen Zentralmuseums.
-
- 2012 Lapanu - Let (It) Glow! - Recent Archaeometric Analyses of Hattian and Hittite Metalwork In *Proceedings of the 7th International Congress on the Archaeology of the Ancient Near East, 12 April – 16 April 2010*. R. Matthews and J. Curtis, eds. Pp. 303-312. Wiesbaden: Harrassowitz Verlag.
- Zimmermann, Thomas, and Evren Y. Geniş
2012 Arkeometri Gözüyle Kalinkaya-Toptaštepe Erken Tunç Çağı Maden Buluntuları. *Çorum Kazı ve Araştırmalar Sempozyumu* 2:103-110.
- Zimmermann, Thomas, and Önder Ipek
2010 The "Hattian" Metal Assemblage from Bekaroğlu Köyü - An Archaeometrical Footnote. *Anatolia Antiqua* 18:31-34.
- Zimmermann, Thomas, Latif Özen, Yakup Kalaycı, and Rukiye Akdoğan
2010 The Metal Tablet from Boğazköy-Hattuša: First Archaeometric Impressions. *Journal of Near Eastern Studies* 69(2):225-229.
- Zimmermann, Thomas, and Tayfun Yıldırım
2007 Land of Plenty? - New Archaeometric Insights into Central Anatolian Early Bronze Age Metal Consumption in Funeral Contexts. *Antiquity* 81(314).
- Zimmermann, Thomas, Tayfun Yıldırım, Latif Özen, and Abdullah Zararsız
2009 'All that glitters is not gold, nor all that sparkles silver' - Fresh Archaeometrical Data for Central Anatolian Early Bronze Age Metalwork. *Antiquity* 83(321):Online Project Gallery, <http://antiquity.ac.uk/projgall/zimmerman321/index.html>.
- Zwicker, Ulrich
1980 Investigations on the Extractive Metallurgy of Cu/Sb/As Ore and Excavated Smelting Products from Norsun-Tepe (Keban) on the Upper Euphrates (3500 - 2800 B.C.). In *Aspects of Early Metallurgy*. W.A. Oddy, ed. London: British Museum Research Laboratory and The Historical Metallurgy Society.