

# UC Berkeley

## UC Berkeley Previously Published Works

### Title

Large Polarization and Susceptibilities in Artificial Morphotropic Phase Boundary PbZr<sub>1-x</sub>Ti<sub>x</sub>O<sub>3</sub> Superlattices

### Permalink

<https://escholarship.org/uc/item/8zg7n99m>

### Journal

Advanced Electronic Materials, 6(3)

### ISSN

2199-160X

### Authors

Lupi, Eduardo  
Ghosh, Anirban  
Saremi, Sahar  
[et al.](#)

### Publication Date

2020-03-01

### DOI

10.1002/aelm.201901395

Peer reviewed

# Large Polarization and Susceptibilities in Artificial Morphotropic Phase Boundary $\text{PbZr}_{1-x}\text{Ti}_x\text{O}_3$ Superlattices

*Eduardo Lupi, Anirban Ghosh, Sahar Saremi, Shang-Lin Hsu, Shishir Pandya, Gabriel Velarde, Abel Fernandez, Ramamoorthy Ramesh, and Lane W. Martin\**

**The ability to produce atomically precise, artificial oxide heterostructures allows for the possibility of producing exotic phases and enhanced susceptibilities not found in parent materials. Typical ferroelectric materials either exhibit large saturation polarization away from a phase boundary or large dielectric susceptibility near a phase boundary. Both large ferroelectric polarization and dielectric permittivity are attained wherein fully epitaxial  $(\text{PbZr}_{0.8}\text{Ti}_{0.2}\text{O}_3)_n/(\text{PbZr}_{0.4}\text{Ti}_{0.6}\text{O}_3)_{2n}$  ( $n = 2, 4, 6, 8, 16$  unit cells) superlattices are produced such that the overall film chemistry is at the morphotropic phase boundary, but constitutive layers are not. Long- ( $n \geq 6$ ) and short-period ( $n = 2$ ) superlattices reveal large ferroelectric saturation polarization ( $P_s = 64 \mu\text{C cm}^{-2}$ ) and small dielectric permittivity ( $\epsilon_r \approx 400$  at 10 kHz). Intermediate-period ( $n = 4$ ) superlattices, however, exhibit both large ferroelectric saturation polarization ( $P_s = 64 \mu\text{C cm}^{-2}$ ) and dielectric permittivity ( $\epsilon_r = 776$  at 10 kHz). First-order reversal curve analysis reveals the presence of switching distributions for each parent layer and a third, interfacial layer wherein superlattice periodicity modulates the volume fraction of each switching distribution and thus the overall material response. This reveals that deterministic creation of artificial superlattices is an effective pathway for designing materials with enhanced responses to applied bias.**

Superlattices comprised of thin layers of ferroelectric and/or dielectric materials provide ample opportunity for designing artificial heterostructures with tunable and emergent properties. For example, ferroelectrics can exhibit large susceptibilities to electric fields, stress, temperature, etc., which can be enhanced by the competition of structure and polarization between phases and can even lead to the development of novel order parameters.<sup>[1-3]</sup> In this regard, ferroelectric–dielectric superlattices have been widely studied<sup>[4,5]</sup> with particular


interest on  $\text{BaTiO}_3/\text{SrTiO}_3$ <sup>[6-12]</sup> and  $\text{PbTiO}_3/\text{SrTiO}_3$  superlattices.<sup>[13-15]</sup> In  $\text{PbTiO}_3/\text{SrTiO}_3$  superlattices alone, for example, researchers have observed the evolution of novel order (i.e., improper ferroelectricity),<sup>[14]</sup> emergent, smoothly evolving polar structures (e.g., vortices and skyrmions),<sup>[16,17]</sup> and even classical flux-closure-domain structures depending on the periodicity and strain state.<sup>[13]</sup> Considerably less work, however, has focused on superlattices of two different ferroelectric materials<sup>[18,19]</sup> wherein differences in symmetry,<sup>[20]</sup> polarization magnitude and direction, transition temperature,<sup>[21]</sup> etc., provide for an alternative approach to novel and/or enhanced responses and phases. In this regard, the  $\text{PbZr}_{1-x}\text{Ti}_x\text{O}_3$  system provides interesting opportunities as there are both zirconium-rich rhombohedral and titanium-rich tetragonal phases that are bridged by a morphotropic phase boundary<sup>[22,23]</sup> wherein those phases compete and provide for interesting properties (Figure 1a). Polarization rotation at this phase boundary enables an easier route

to switching at much lower coercive fields and thus enhances susceptibilities. While there has been considerable research on the compositional evolution of structure and properties in this system,<sup>[24-26]</sup> little work exists on the creation of artificial heterostructures and superlattices.<sup>[27-29]</sup> That which does exist focuses on long-period (i.e., layers of thickness  $\geq 30$  nm), ferroelectric–ferroelectric heterostructures. We propose the exploration of short-period (down to 2 unit cells) ferroelectric–ferroelectric superlattices bridged across the morphotropic phase boundary in the  $\text{PbZr}_{1-x}\text{Ti}_x\text{O}_3$  system as a potential route to enhanced functionalities. Such a systematic study of ultrathin superlattice periodicities can elucidate the complex interplay of competing energy terms (e.g., elastic, electrostatic, and gradient) present in ferroelectric systems.

Large susceptibilities in the  $\text{PbZr}_{1-x}\text{Ti}_x\text{O}_3$  system have historically been attained by selecting materials in the compositional vicinity of the morphotropic phase boundary.<sup>[30-32]</sup> This typically comes as a trade-off with saturation polarization, as polarization diminishes and susceptibility rises at the phase transition. Here, we take advantage of unit-cell-precise growth to introduce ferroelectric–ferroelectric interfaces as an additional design parameter wherein the material response can be tuned by both

E. Lupi, Dr. A. Ghosh, Dr. S. Saremi, Dr. S. Pandya, G. Velarde, A. Fernandez, Prof. R. Ramesh, Prof. L. W. Martin  
Department of Materials Science and Engineering  
University of California, Berkeley  
Berkeley, CA 94720, USA  
E-mail: lwmartin@berkeley.edu

Dr. S. Saremi, Dr. S.-L. Hsu, Prof. R. Ramesh, Prof. L. W. Martin  
Materials Sciences Division  
Lawrence Berkeley National Laboratory  
Berkeley, CA 94720, USA

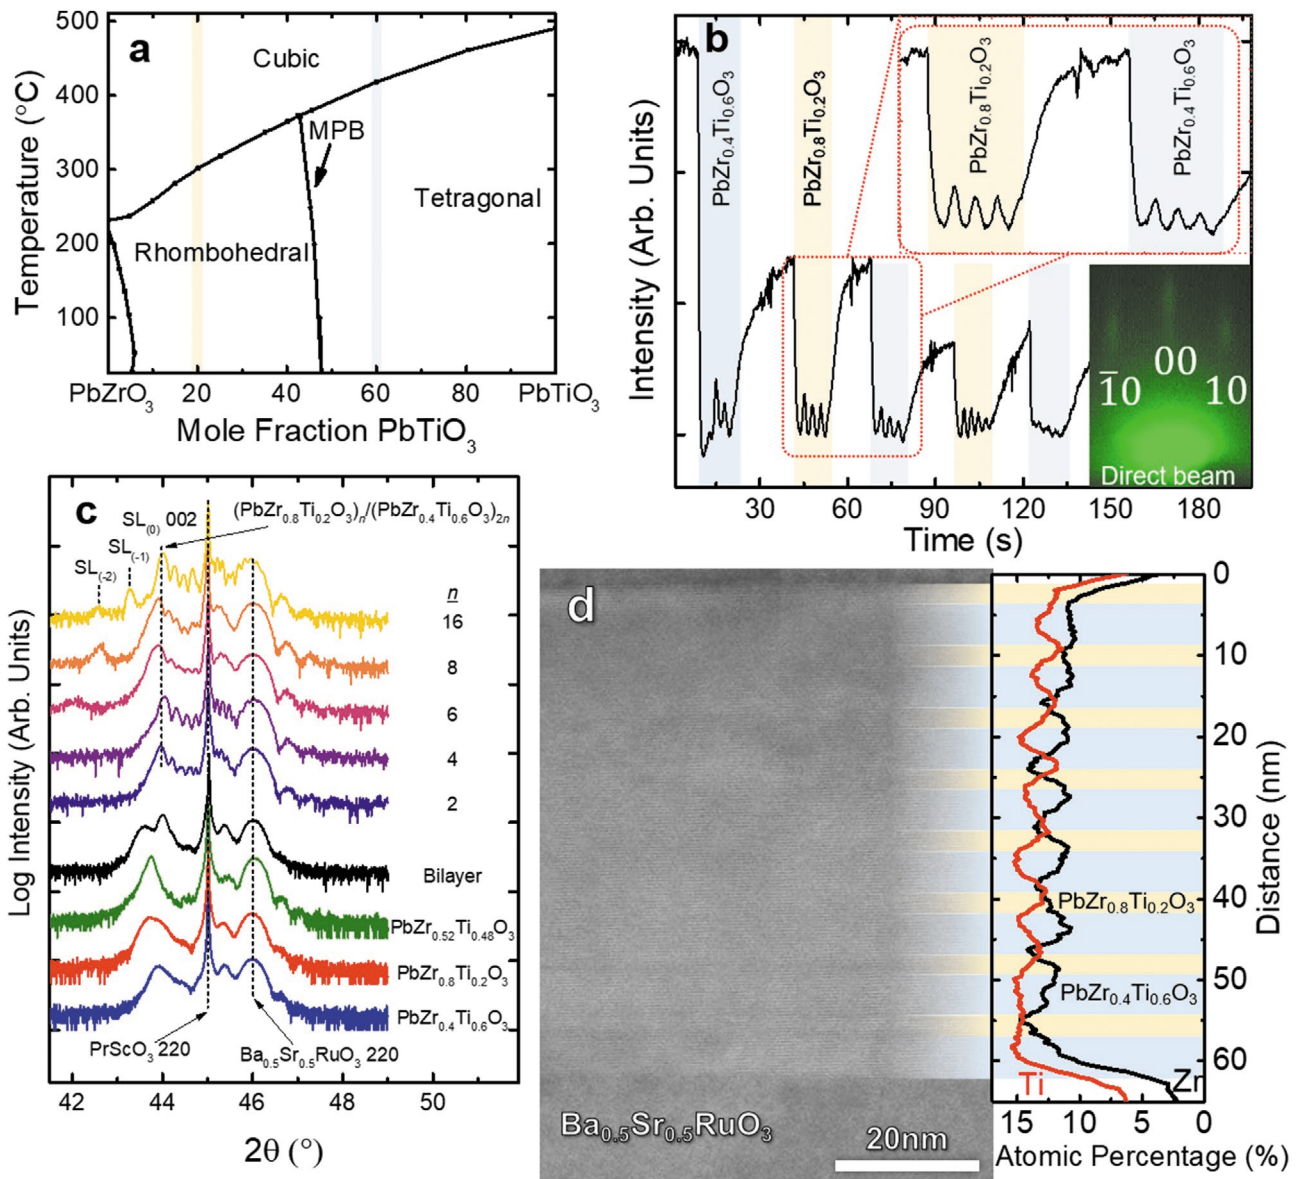

**Figure 1.** a) Phase diagram of the  $\text{PbZr}_{1-x}\text{Ti}_x\text{O}_3$  system with vertical lines indicating the selected parent compositions. RHEED-assisted pulsed-laser deposition growth of the heterostructures demonstrating b) persistent layer-by-layer deposition and sharp interface control. c)  $\theta$ - $2\theta$  X-ray diffraction patterns about the 002-diffraction condition for the various parent, bilayer, and superlattice heterostructures. d) STEM image with overlaid EDS mapping (right) indicating the production of high-quality superlattice structures.

composition and superlattice periodicity. We likewise focus on heterostructures with overall chemistry near the morphotropic phase boundary, but built from compositions far from the phase boundary itself: rhombohedral  $\text{PbZr}_{0.8}\text{Ti}_{0.2}\text{O}_3$  and tetragonal  $\text{PbZr}_{0.4}\text{Ti}_{0.6}\text{O}_3$ . Using reflection high-energy electron diffraction (RHEED)-assisted pulsed-laser deposition, we create atomically precise  $(\text{PbZr}_{0.8}\text{Ti}_{0.2}\text{O}_3)_n/(\text{PbZr}_{0.4}\text{Ti}_{0.6}\text{O}_3)_{2n}$  ( $n = 2, 4, 6, 8,$  and  $16$  unit cells) superlattices with overall film chemistry of  $\text{PbZr}_{0.53}\text{Ti}_{0.47}\text{O}_3$ . As compared to uniform films of the parent materials, the superlattice structures exhibit both large saturation polarization ( $P_s = 64 \mu\text{C cm}^{-2}$ ) and dielectric susceptibility ( $\epsilon_r = 776$  at  $10 \text{ kHz}$  for  $n = 4$  superlattices). ac field-dependent dielectric measurements suggest the presence of both phase-boundary- and parent-like switching events. First-order reversal

curve (FORC) studies reveal separate switching events for each of the parent layers in addition to a third interfacial layer. Ultimately, this reveals that artificial superlattices can be deterministically designed as an effective pathway for enhanced responses to external biases.

Rhombohedral  $\text{PbZr}_{0.8}\text{Ti}_{0.2}\text{O}_3$  and tetragonal  $\text{PbZr}_{0.4}\text{Ti}_{0.6}\text{O}_3$  were chosen for this work because they are robust ferroelectric phases that differ in terms of symmetry, polarization direction, and have relatively close lattice parameters ( $a = 4.115 \text{ \AA}$  for  $\text{PbZr}_{0.8}\text{Ti}_{0.2}\text{O}_3$  and  $a = 4.008 \text{ \AA}$ ,  $c = 4.134 \text{ \AA}$  for  $\text{PbZr}_{0.4}\text{Ti}_{0.6}\text{O}_3$ ) such that high-quality superlattices of various periods can be synthesized. All heterostructures are grown on  $20 \text{ nm}$   $\text{Ba}_{0.5}\text{Sr}_{0.5}\text{RuO}_3/\text{PrScO}_3$  (110) substrates (which were chosen because of the compressive strain<sup>[33]</sup> that is imposed on both


the  $\text{PbZr}_{0.8}\text{Ti}_{0.2}\text{O}_3$  (-2.5%) and  $\text{PbZr}_{0.4}\text{Ti}_{0.6}\text{O}_3$  (-0.3%) layers). Details of the growth are provided in the Experimental Section. To begin, it has been observed in prior studies that the exact chemical composition of the morphotropic phase boundary in  $\text{PbZr}_{1-x}\text{Ti}_x\text{O}_3$  can shift (slightly) toward higher concentrations of zirconium with compressive epitaxial strain.<sup>[34]</sup> Thus, a preliminary study was conducted to assess the average superlattice composition required to access phase-boundary-like behavior, namely an enhancement of dielectric susceptibility.<sup>[35]</sup> To sweep across various average compositions, 80-nm-thick  $(\text{PbZr}_{0.8}\text{Ti}_{0.2}\text{O}_3)_n/(\text{PbZr}_{0.4}\text{Ti}_{0.6}\text{O}_3)_m$  superlattices with varying  $n \times m$  ratios were produced while the total periodicity  $n + m$  was held constant at 12 unit cells (specifically we studied  $n \times m = 7 \times 5$ ,  $5 \times 7$ ,  $4 \times 8$ , and  $3 \times 9$ , corresponding to average superlattice compositions of  $\text{PbZr}_{0.63}\text{Ti}_{0.37}\text{O}_3$ ,  $\text{PbZr}_{0.57}\text{Ti}_{0.43}\text{O}_3$ ,  $\text{PbZr}_{0.53}\text{Ti}_{0.47}\text{O}_3$ , and  $\text{PbZr}_{0.5}\text{Ti}_{0.5}\text{O}_3$ , respectively). Subsequent  $\theta$ - $2\theta$  X-ray diffraction studies reveal high-quality, epitaxial superlattices (Figure S1a, Supporting Information). Capacitor-based dielectric-permittivity measurements (Experimental Section), indicate an enhancement of the out-of-plane dielectric response, akin to that expected near the phase boundary, for the  $4 \times 8$  superlattices (Figure S1b, Supporting Information) which corresponds to an average composition of  $\text{PbZr}_{\text{PbZr}_{0.53}\text{Ti}_{0.47}\text{O}_3}$ . Based on this observation, for the remainder of the study, we fixed the overall heterostructure chemistry to be  $\text{PbZr}_{0.53}\text{Ti}_{0.47}\text{O}_3$  thus requiring the production of various  $n \times 2n$  superlattices.

At this overall film composition, periodicity-dependent studies were completed. Here, we focus on 80-nm-thick het-erostructures including the following variants: 1) superlat-tice structures of the form  $(\text{PbZr}_{0.8}\text{Ti}_{0.2}\text{O}_3)_n/(\text{PbZr}_{0.4}\text{Ti}_{0.6}\text{O}_3)_{2n}$  (with  $n = 2, 4, 6, 8$ , and 16), 2) bilayer structures with 27 nm of  $\text{PbZr}_{0.8}\text{Ti}_{0.2}\text{O}_3$  and 53 nm of  $\text{PbZr}_{0.4}\text{Ti}_{0.6}\text{O}_3$  (i.e., a 1:2 ratio of the parent materials, equivalent to the ratio found in all the superlattices), 3) parent rhombohedral  $\text{PbZr}_{0.8}\text{Ti}_{0.2}\text{O}_3$ , 4) parent tetragonal  $\text{PbZr}_{0.4}\text{Ti}_{0.6}\text{O}_3$ , and 5) morphotropic phase boundary  $\text{PbZr}_{0.52}\text{Ti}_{0.48}\text{O}_3$ . The production of high-quality superlattices was enabled by our ability to achieve layer-by-layer growth as monitored during deposition via RHEED (Figure 1b,c). Throughout (and after growth) the presence of a “streaky” RHEED pattern demonstrates a persistent 2D-growth mode and a smooth surface for a representative superlattice growth (inset, Figure 1b).  $\theta$ - $2\theta$  X-ray diffraction studies of the resulting superlattices reveal epitaxial, 00l-oriented films with superlattice peaks varying as a function of superlattice periodicity (Figure 1c). Wide-angle  $\theta$ - $2\theta$  X-ray studies show no secondary phases and high-quality, epitaxial growth for all heterostructure variants (Figure S2, Supporting Information). Reciprocal space maps about the  $103_{\text{pc}}$ -diffraction conditions for all superlattice heterostructures show fully strained films (Figure S3, Supporting Information). z-contrast, high-angle annular dark-field (HAADF) scanning transmission electron microscopy (STEM) imaging and energy dispersive spectroscopy (EDS) studies were completed for two superlattice structures  $[(\text{PbZr}_{0.8}\text{Ti}_{0.2}\text{O}_3)_n/(\text{PbZr}_{0.4}\text{Ti}_{0.6}\text{O}_3)_{2n}]$  with  $n = 6, 8$  and reveal the production of high-quality heterostructures with smooth interfaces that exhibit no obvious defect structures (Figure S4, Supporting Information). Due to the similar chemistry between the layers (i.e., both layers in the superlattice contain lead, zirconium, and titanium) the z-contrast between the layers is not as distinct as

one might expect for a superlattice made from vastly different materials. To confirm the production of the superlattice structures, EDS studies were employed to map the local chemical variations throughout the superlattice structure (Figure 1d). The EDS signatures from the titanium and zirconium are observed to oscillate or alternate in intensity due to the chemical variations in each layer of the superlattice (i.e., from zirconium-rich  $\text{PbZr}_{0.8}\text{Ti}_{0.2}\text{O}_3$  to titanium-rich  $\text{PbZr}_{0.4}\text{Ti}_{0.6}\text{O}_3$ ) and this helps identify the superlattice structure in the absence of robust z-contrast. All told, the STEM and EDS data, in conjunction with extensive RHEED and X-ray diffraction studies, confirm that high-quality superlattices of various periodicities can be produced. Thus, it is appropriate to proceed to study the impact of superlattice design on dielectric and ferroelectric response.

Frequency-dependent dielectric-permittivity measurements demonstrate low-loss response in all heterostructure variants, but a strong superlattice periodicity dependence of the permittivity itself (Figure 2a,b). Similar studies were completed for the parent tetragonal  $\text{PbZr}_{0.4}\text{Ti}_{0.6}\text{O}_3$  ( $\epsilon_r = 362$  at 10 kHz), the parent rhombohedral  $\text{PbZr}_{0.8}\text{Ti}_{0.2}\text{O}_3$  ( $\epsilon_r = 492$  at 10 kHz), and morphotropic phase boundary  $\text{PbZr}_{0.52}\text{Ti}_{0.48}\text{O}_3$  ( $\epsilon_r = 799$  at 10 kHz) (Figure 2a). Both the  $\text{PbZr}_{0.4}\text{Ti}_{0.6}\text{O}_3$  and  $\text{PbZr}_{0.8}\text{Ti}_{0.2}\text{O}_3$  show low dielectric loss, while the  $\text{PbZr}_{0.52}\text{Ti}_{0.48}\text{O}_3$  shows slightly increased loss consistent with the complex structural evolution under applied external fields (Figure 2b). This range of properties provides an important framework in which to probe the superlattice heterostructures. The dielectric permittivity hovers around  $\approx 400$  (at 10 kHz) for the bilayer heterostructures and all long-period superlattices ( $n \geq 6$ ). At the other end of the spectrum, short-period superlattices ( $n = 2$ ) also exhibit permittivity in a similar range. Intermediate-period superlattices ( $n = 4$ ), however, display dramatically enhanced permittivity ( $\approx 776$  at 10 kHz, Figure 2c). Naively, one might expect that reducing the superlattice period should result in a more uniform, morphotropic-phase-boundary-like heterostructure and, thus, systematically increasing dielectric response. Our observations, however, suggest a more complex evolution of dielectric response with superlattice periodicity and begs the question: what gives rise to the dielectric enhancement in the  $n = 4$  superlattices?

One potential explanation is that reducing the size (or thickness) of the ferroelectric layers is destabilizing the polarization and effectively lowering the Curie temperature which would result in an enhanced room-temperature dielectric permittivity in the ultrathin superlattices. To probe this concept, temperature-dependent dielectric measurements were completed on the parent  $\text{PbZr}_{0.4}\text{Ti}_{0.6}\text{O}_3$  and  $\text{PbZr}_{0.8}\text{Ti}_{0.2}\text{O}_3$  heterostructures and the  $n = 4$  superlattices (Figure S5, Supporting Information). These studies reveal, however, that enhancement in dielectric response does not stem simply from a lower transition temperature as Curie-Weiss analysis of the phase transition shows that the transition temperatures are 580, 500, and 560 °C for  $\text{PbZr}_{0.4}\text{Ti}_{0.6}\text{O}_3$ ,  $\text{PbZr}_{0.8}\text{Ti}_{0.2}\text{O}_3$ , and  $n = 4$  superlattice heterostructures, respectively. To further explore the phase-boundary behavior of this specific superlattice periodicity and deconvolute contributions to the dielectric response, Rayleigh dielectric measurements were employed (Experimental Section). Rayleigh studies utilize ac-field-dependent measurement to probe the behavior of ferroelectric materials in three different regimes: low, high, and switching fields. Both the

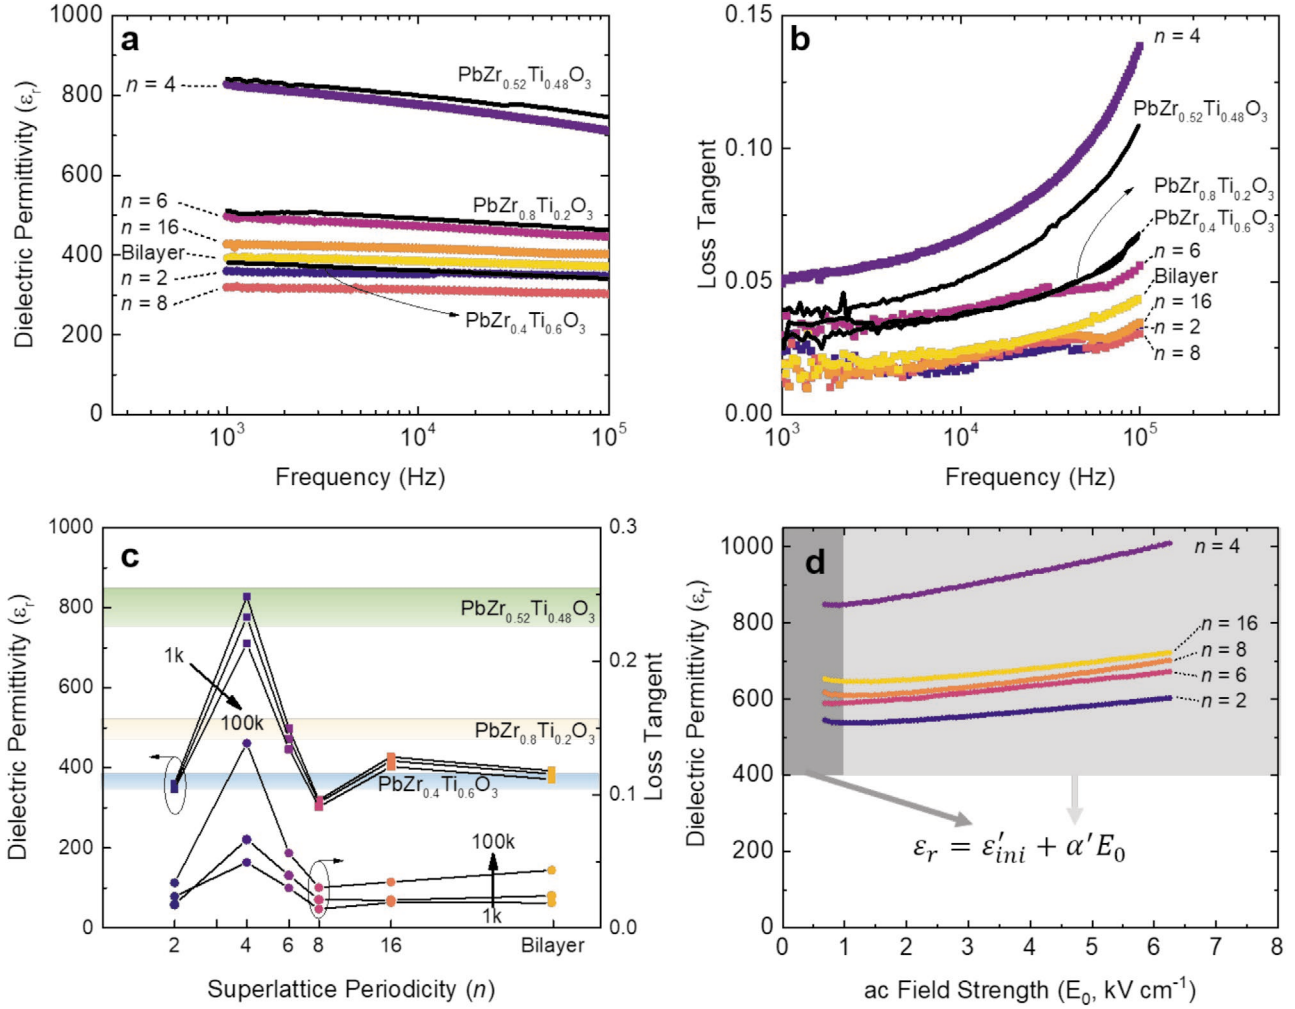

**Figure 2.** a) Dielectric permittivity and b) loss tangent as a function of measurement frequency for the various parent, bilayer, and superlattice heterostructures. c) Summary of the dielectric response (i.e., permittivity on the left axis and loss on the right axis) as a function of superlattice periodicity demonstrating a strong enhancement at a critical superlattice periodicity of  $n=4$  unit cells. d) Rayleigh dielectric measurements at subswitching fields for the various superlattice heterostructures.

low- and high-field regimes are subswitching linear regimes from which the reversible and irreversible extrinsic contributions to dielectric response, respectively, can be extracted. In the low-field regime,<sup>[36]</sup> an enhanced field-independent constant permittivity represented by the reversible Rayleigh parameter  $\epsilon'_{ini}$  indicates large intrinsic lattice and reversible extrinsic contributions.<sup>[37]</sup> In the high-field (Rayleigh regime), a steep linear slope indicated by the Rayleigh coefficient  $\alpha'$  is typical of an enhanced irreversible contribution.<sup>[38]</sup> Thus, the overall dielectric response is represented as

$$\epsilon_r = \epsilon'_{ini} + \alpha' E_0 \quad (1)$$

Analysis of the Rayleigh studies at subswitching fields reveals both parent phases and the bilayer heterostructures to have small  $\epsilon'_{ini}$  ( $\leq 360$ ) and  $\alpha'$  ( $\leq 4$   $\text{cm kV}^{-1}$ ) (Figure S6, Supporting Information), while the phase-boundary  $\text{PbZr}_{0.52}\text{Ti}_{0.48}\text{O}_3$  exhibits large  $\epsilon'_{ini}$  (865) and  $\alpha'$  (87.6  $\text{cm kV}^{-1}$ ) (Table 1). In this context, the intermediate-period superlattices

( $n=4$ ) demonstrate enhanced  $\epsilon'_{ini}$  (805) and  $\alpha'$  (32  $\text{cm kV}^{-1}$ ) (Figure 2d); values considerably larger than those in all other superlattices and similar to literature values for bulk  $\text{PbZr}_{0.52}\text{Ti}_{0.48}\text{O}_3$ .<sup>[37]</sup> This suggests that this periodicity ( $n=4$ ) behaves quite similarly to a phase-boundary material, yet it was created from compositions away from the phase boundary. Motivated by the observation of this strong periodicity dependence of the small-field dielectric response, we proceed to study ferroelectric behavior under large applied fields wherein we expect to observe phase-boundary-like switching behavior.


Polarization and current–electric field hysteresis loops (for brevity shown only at 10 kHz) demonstrate the evolution of both the polarization and switching current in the heterostructures. Hysteresis loops for the parent phases  $\text{PbZr}_{0.8}\text{Ti}_{0.2}\text{O}_3$  (Figure 3a) and  $\text{PbZr}_{0.4}\text{Ti}_{0.6}\text{O}_3$  (Figure 3b) show a large saturation polarization  $P_s = 67 \mu\text{C cm}^{-2}$  and a single switching event as illustrated by the single current peak (yellow for  $\text{PbZr}_{0.8}\text{Ti}_{0.2}\text{O}_3$  and blue for  $\text{PbZr}_{0.4}\text{Ti}_{0.6}\text{O}_3$ ). The  $\text{PbZr}_{0.52}\text{Ti}_{0.48}\text{O}_3$  phase exhibits a much smaller saturation polarization ( $P_s = 45 \mu\text{C cm}^{-2}$ ,

**Table 1.** Dielectric Rayleigh parameters of various superlattice films and heterostructures.


| Film   | $\epsilon'_{ini}$ | $\alpha'$ [cm kV <sup>-1</sup> ] | $\alpha'/\epsilon'_{ini}$ [cm kV <sup>-1</sup> ] |
|--|-------------------|----------------------------------|--|
| PbZr <sub>0.8</sub> Ti <sub>0.2</sub> O <sub>3</sub>   | 362               | 2.8                              | 0.008  |
| PbZr <sub>0.4</sub> Ti <sub>0.6</sub> O <sub>3</sub>   | 338               | 4.1                              | 0.012  |
| PbZr <sub>0.52</sub> Ti <sub>0.48</sub> O <sub>3</sub> | 865               | 87.6                             | 0.101  |
| Bilayer  | 370               | 2.8                              | 0.007  |
| $n = 16$   | 613               | 16.8                             | 0.027  |
| 8  | 583               | 16.8                             | 0.029  |
| 6  | 567               | 16.6                             | 0.029  |
| 4  | 805               | 32                               | 0.040  |
| 2  | 515               | 13.5                             | 0.026  |

Figure 3c). The bilayer (Figure 3d) and superlattice heterostructures (Figure 3e–i) exhibit a consistent  $P_s = 64 \mu\text{C cm}^{-2}$ . In the current loops, two switching events are evident (as illustrated by the two current peaks) with an intensity ratio that is related

enhanced permittivity (i.e., large  $\epsilon_r = 776$  at 10 kHz,  $\epsilon'_{ini} = 805$ , and  $\alpha' = 32 \text{ cm kV}^{-1}$ ) akin to phase-boundary-like response and simultaneously large saturation polarization ( $P_s = 64 \mu\text{C cm}^{-2}$ ) akin to the parent-phase materials and other superlattices.

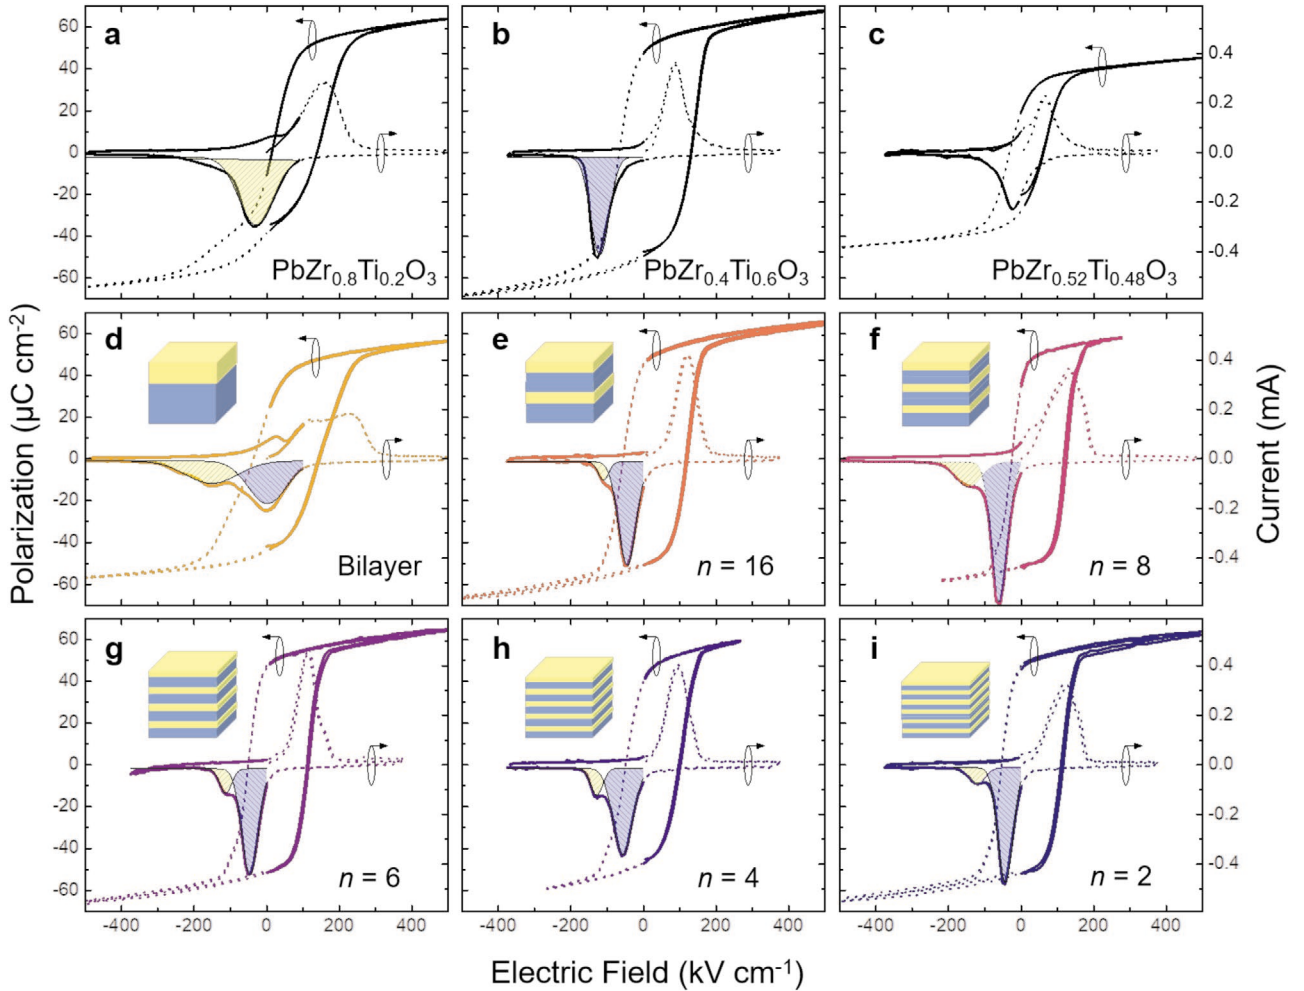


**Figure 3.** Ferroelectric polarization–electric field hysteresis loops (left axis) and ferroelectric current–electric field loops (right axis) behavior (at 10 kHz) for single-layer parent a) PbZr<sub>0.8</sub>Ti<sub>0.2</sub>O<sub>3</sub> and b) PbZr<sub>0.4</sub>Ti<sub>0.6</sub>O<sub>3</sub> as well as single-layer c) phase-boundary PbZr<sub>0.52</sub>Ti<sub>0.48</sub>O<sub>3</sub> heterostructures together with those of d) bilayer and superlattice heterostructures with e)  $n = 16$ , f)  $n = 8$ , g)  $n = 6$ , h)  $n = 4$ , and i)  $n = 2$ . Note that the polarization and current are simultaneously shown to show constant polarization saturation and the split component of polarization switching from each parent phase.

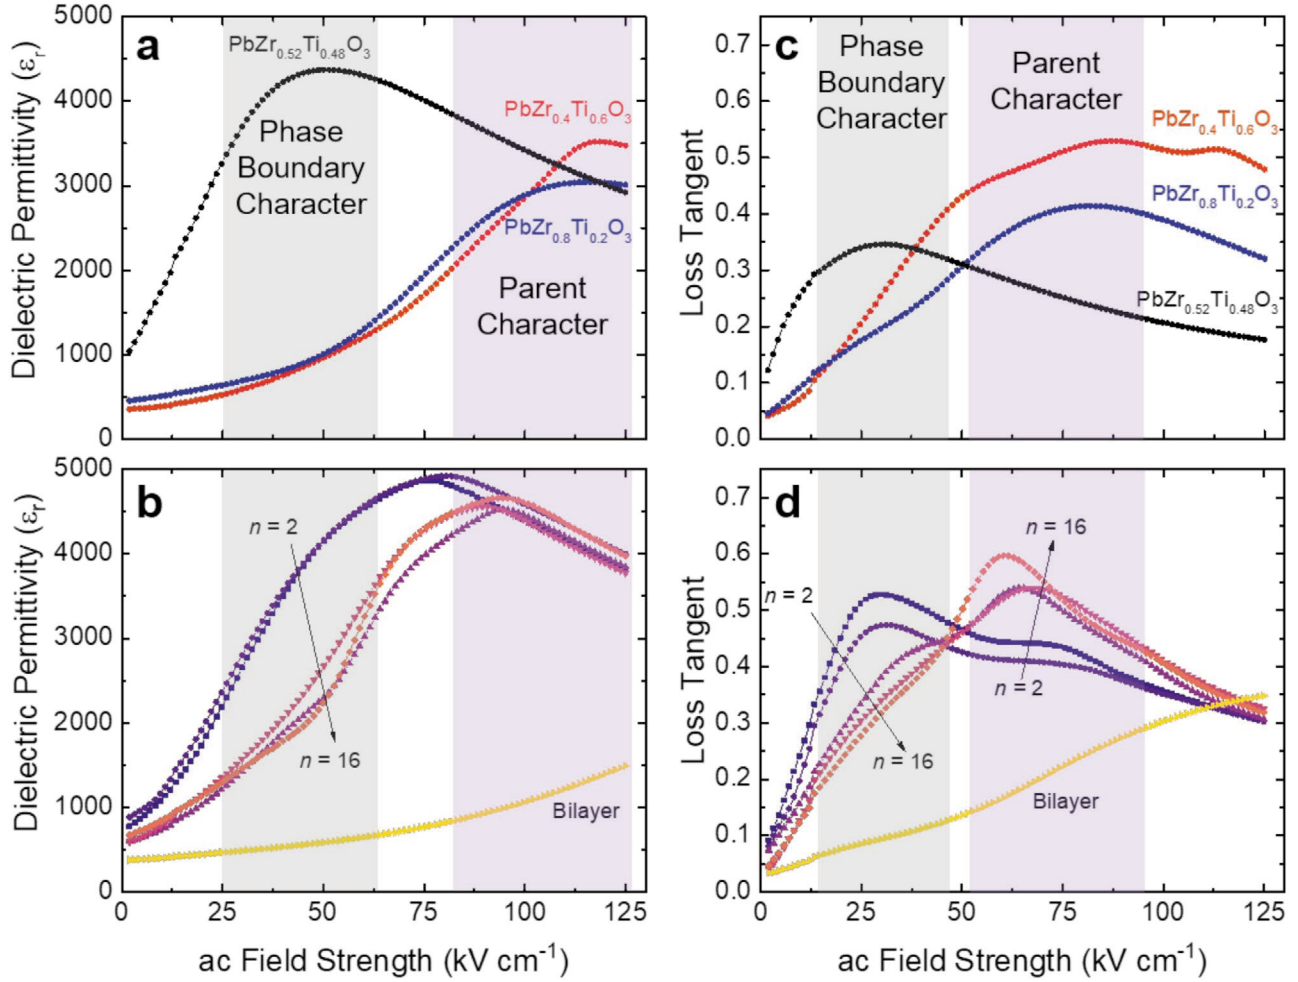

**Figure 4.** Dielectric Rayleigh measurements extended to (large) switching-field regimes indicating the response during switching a) at large ac fields in the parent  $\text{PbZr}_{0.8}\text{Ti}_{0.2}\text{O}_3$  and  $\text{PbZr}_{0.4}\text{Ti}_{0.6}\text{O}_3$  phases and small ac fields in phase-boundary  $\text{PbZr}_{0.52}\text{Ti}_{0.48}\text{O}_3$ . b) Similar data for the various superlattice samples exhibiting a mixture of both small- and large-field effects with  $n = 2, 4$  superlattices showing predominant effects at lower fields and  $n > 4$  superlattices predominant effects at higher fields. Corresponding dielectric loss for c) the parent and phase-boundary materials indicating singular switching events which are contrasted with similar data for the d) superlattice heterostructures which exhibit components of both parent and phase-boundary character.

This unusual combination of large dielectric permittivity and ferroelectric polarization in the intermediate-period superlattices ( $n = 4$ ) calls for further study as a function of external bias. Here, we extend the dielectric Rayleigh measurements (which are typically performed in subswitching fields) to the third regime—the switching-field regime—at higher fields. Parent phases  $\text{PbZr}_{0.8}\text{Ti}_{0.2}\text{O}_3$  and  $\text{PbZr}_{0.4}\text{Ti}_{0.6}\text{O}_3$  exhibit peaks in the dielectric response corresponding to switching at relatively large fields (80–125 kV cm<sup>-1</sup>), whereas phase-boundary  $\text{PbZr}_{0.52}\text{Ti}_{0.48}\text{O}_3$  exhibits a peak corresponding to switching at lower fields (25–60 kV cm<sup>-1</sup>) (Figure 4a). This behavior can be used as a reference frame to understand the response of the superlattice heterostructures which exhibit features similar to both  $\text{PbZr}_{0.52}\text{Ti}_{0.48}\text{O}_3$  (i.e., low-field response within the switching-field regime) and the parent phases  $\text{PbZr}_{0.8}\text{Ti}_{0.2}\text{O}_3$  and  $\text{PbZr}_{0.4}\text{Ti}_{0.6}\text{O}_3$  (i.e., high-field response within the switching-field regime). While all bilayer and superlattice heterostructures exhibit some features of parent- and phase-boundary-like

character in the switching-field regime, the short- and intermediate-period superlattices ( $n = 2, 4$ ) have a particularly pronounced phase-boundary character and the long-period superlattices ( $n \geq 6$ ) and bilayer heterostructures have pronounced parent character (Figure 4b). This mixed phase-boundary- and parent-like character suggests that while aspects of the response of the parent  $\text{PbZr}_{0.8}\text{Ti}_{0.2}\text{O}_3$  and  $\text{PbZr}_{0.4}\text{Ti}_{0.6}\text{O}_3$  materials are maintained, the intimate interfacing of these materials gives rise to a response more akin to  $\text{PbZr}_{0.52}\text{Ti}_{0.48}\text{O}_3$ , most likely at the interface between the two layers. Additional insight in this regard can be extracted from the dielectric loss data taken simultaneously. Again, the  $\text{PbZr}_{0.52}\text{Ti}_{0.48}\text{O}_3$  phase exhibits a peak in loss at lower fields (20–50 kV cm<sup>-1</sup>) while the parent phases  $\text{PbZr}_{0.8}\text{Ti}_{0.2}\text{O}_3$  and  $\text{PbZr}_{0.4}\text{Ti}_{0.6}\text{O}_3$  exhibit peaks in loss at relatively larger fields (50–90 kV cm<sup>-1</sup>) (Figure 4c). Likewise, all superlattice heterostructures exhibit mixed loss character (i.e., loss signatures at both low and high fields), but in general the shorter the superlattice period ( $n \leq 4$ ) the larger the

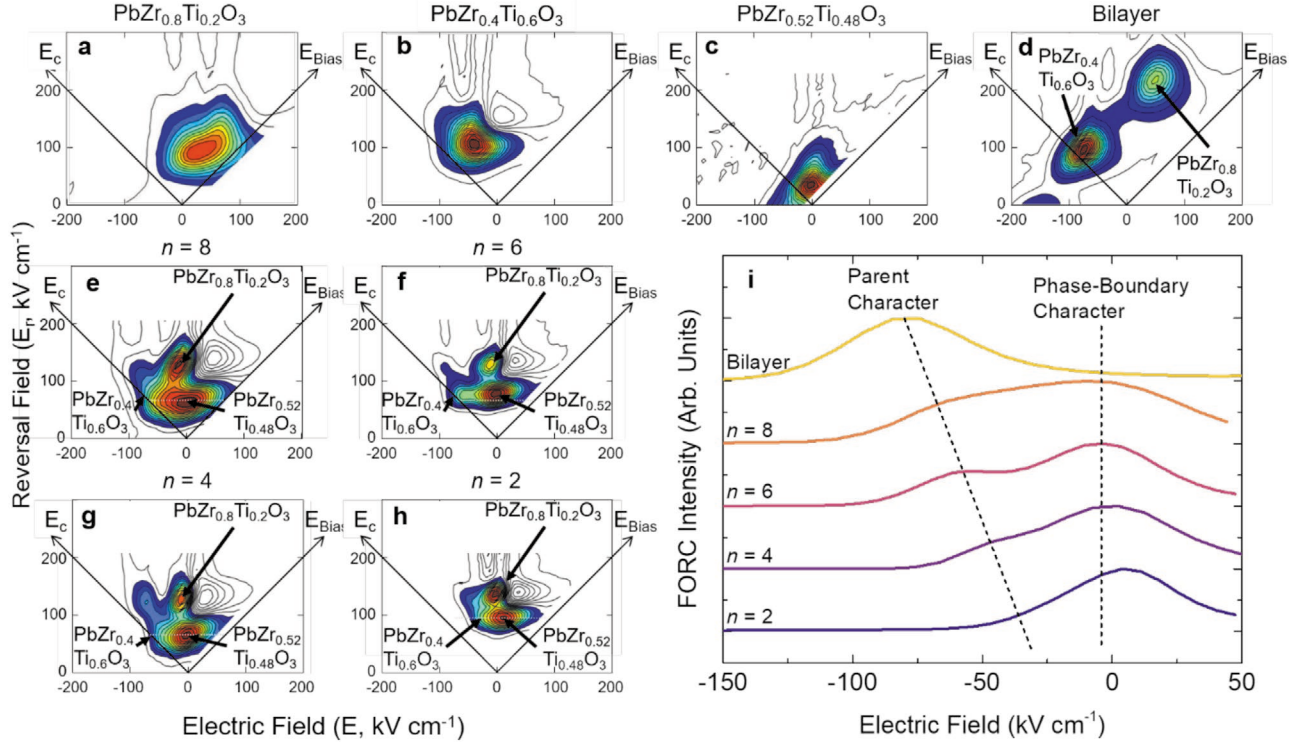

**Figure 5.** Calculated FORC distributions for a) parent-phase  $\text{PbZr}_{0.8}\text{Ti}_{0.2}\text{O}_3$ , b) parent-phase  $\text{PbZr}_{0.4}\text{Ti}_{0.6}\text{O}_3$ , c) phase-boundary  $\text{PbZr}_{0.52}\text{Ti}_{0.48}\text{O}_3$ , d) bilayer heterostructures, as well as e)  $n = 8$ , f)  $n = 6$ , g)  $n = 4$ , and h)  $n = 2$  superlattices. For each FORC analysis, distributions correspond to each of the parent phases and phase-boundary character are labeled/attributed. i) A line profile taken across various contour plots in (d–h) at a reversal field of  $E_r \approx 70 \text{ kV cm}^{-1}$  demonstrating the evolution of FORC distribution intensities with superlattice periodicity.


proportion of the small-field effects, whereas the opposite trend is observed for long-period superlattices. In turn, this suggests that the superlattices with more interfaces exhibit more phase-boundary-like switching behavior, thus a higher permittivity in small fields, while maintaining aspects of ferroelectric polarization switching akin to that of the parent phases  $\text{PbZr}_{0.8}\text{Ti}_{0.2}\text{O}_3$  and  $\text{PbZr}_{0.4}\text{Ti}_{0.6}\text{O}_3$ .

These large-field Rayleigh studies suggest the potential for a complex switching process wherein—particularly in the superlattices—multiple switching phenomena including aspects not only related to the parent phases ( $\text{PbZr}_{0.8}\text{Ti}_{0.2}\text{O}_3$  and  $\text{PbZr}_{0.4}\text{Ti}_{0.6}\text{O}_3$ ), but also to the phase boundary  $\text{PbZr}_{0.52}\text{Ti}_{0.48}\text{O}_3$ . To probe this idea, FORC analysis, which reveals the Preisach distribution of switchable units (so-called hysterons) over bias and coercive fields,<sup>[39]</sup> was performed by measuring a series of minor loops at 1 kHz. All heterostructures were first poled with a negative bias and gradually switched with positive biases of increasing magnitude (Experimental Section; Figure S7, Supporting Information).<sup>[40]</sup> Analyses of the  $\text{PbZr}_{0.8}\text{Ti}_{0.2}\text{O}_3$  (Figure 5a) and  $\text{PbZr}_{0.4}\text{Ti}_{0.6}\text{O}_3$  (Figure 5b) parent phases reveal singular FORC distributions wherein  $\text{PbZr}_{0.4}\text{Ti}_{0.6}\text{O}_3$  has a larger coercive field ( $\approx 70 \text{ kV cm}^{-1}$  versus  $\approx 50 \text{ kV cm}^{-1}$ ). The  $\text{PbZr}_{0.52}\text{Ti}_{0.48}\text{O}_3$  phase-boundary material (Figure 5c) demonstrates a much lower coercive field ( $\approx 20 \text{ kV cm}^{-1}$ ) consistent with the polarization–electric field hysteresis loops (Figure 3). The bilayer heterostructures (Figure 5d) exhibit two distinct distributions likely arising from the two parent-phase layers. These two switching distributions are matched in coercive field ( $\approx 80 \text{ kV cm}^{-1}$ ), which suggests that

the entirety of the film switches together to prevent large penalties in electrostatic energy. Because two-thirds of the total ferroelectric layer volume is comprised of  $\text{PbZr}_{0.4}\text{Ti}_{0.6}\text{O}_3$ , which has a large coercive field, it sets the overall coercive field for the entire film and pushes the switching distribution of the  $\text{PbZr}_{0.8}\text{Ti}_{0.2}\text{O}_3$  component to match in coercive field. In the superlattice heterostructures (Figure 5e–h), a third distribution emerges at lower coercive fields ( $\approx 36 \text{ kV cm}^{-1}$ ) which can be attributed to a phase-boundary-like interfacial region. To better quantify the periodicity-dependent evolution of the different switching distributions, a line-profile of the FORC distribution was taken at a reversal field of  $\approx 70 \text{ kV cm}^{-1}$  (cutting through both the distributions attributed to parent  $\text{PbZr}_{0.4}\text{Ti}_{0.6}\text{O}_3$  and phase-boundary  $\text{PbZr}_{0.52}\text{Ti}_{0.48}\text{O}_3$ ). As the superlattice periodicity is shortened, two changes are observed. First, there is a decrease in the intensity of the distribution attributed to the parent- $\text{PbZr}_{0.4}\text{Ti}_{0.6}\text{O}_3$ -like character simultaneous to an increase in the intensity of the distribution attributed to the phase-boundary-like character (Figure 5i). Second, the distinct switching distributions start to converge as the distribution attributed to the parent- $\text{PbZr}_{0.4}\text{Ti}_{0.6}\text{O}_3$ -like character shifts to lower fields.

Additional insight about the evolution of the heterostructures can be extracted by recalling that the Preisach density of each FORC distribution (Figure 5) also indicates a population map of switching fields in a material,<sup>[41]</sup> thus we can relate the FORC peak intensity to a volume fraction of material responsible for that distribution. For example, in the bilayer heterostructures the ratio of distribution intensities attributed to the parent- $\text{PbZr}_{0.4}\text{Ti}_{0.6}\text{O}_3$ - (blue) and parent- $\text{PbZr}_{0.8}\text{Ti}_{0.2}\text{O}_3$ -like



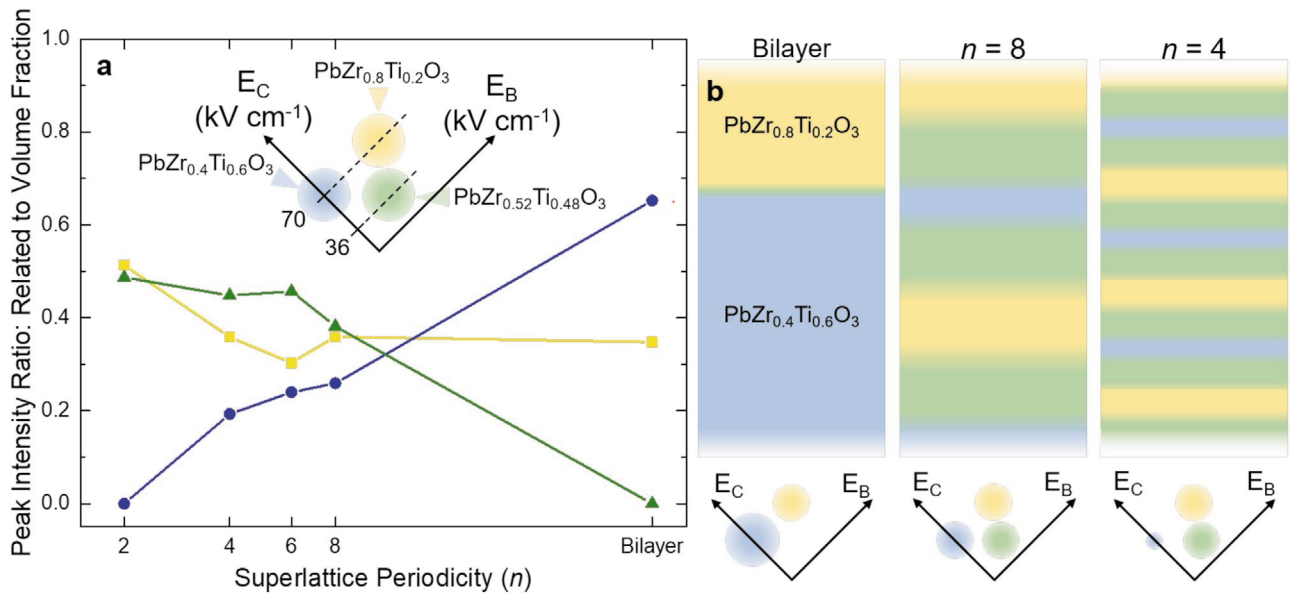

**Figure 6.** Additional analysis of the FORC data showing a) the evolution of peak intensities for various FORC distributions as a function of superlattice periodicity. b) Schematic representation of the evolution of peak intensities for various FORC distributions wherein an increasing phase-boundary-like green peak (quantitative based on the extracted to volume fraction) is found with decreasing superlattice periodicity ( $n$ ).

(yellow) character is consistent with the heterostructure volume fraction (66% PbZr<sub>0.4</sub>Ti<sub>0.6</sub>O<sub>3</sub> and 33% PbZr<sub>0.8</sub>Ti<sub>0.2</sub>O<sub>3</sub>; a 2:1 ratio) (Figure 6a). As the superlattice periodicity is shortened, the intensity of the distribution attributed to the parent-PbZr<sub>0.4</sub>Ti<sub>0.6</sub>O<sub>3</sub>-like character decreases and the intensity of the distribution attributed to the phase-boundary-like character (green) increases. The intensity of the distribution attributed to the parent-PbZr<sub>0.8</sub>Ti<sub>0.2</sub>O<sub>3</sub>-like character remains relatively unchanged with periodicity, which is attributed to the larger difference in chemical proximity to the phase-boundary for this composition than the parent-PbZr<sub>0.4</sub>Ti<sub>0.6</sub>O<sub>3</sub> phase. This suggests that as the number of interfaces is increased, the fraction of material in the superlattices exhibiting phase-boundary-like character increases—a trend shown schematically (and quantitatively based on the intensity evolution of the FORC distributions; Figure 6b). In the bilayer heterostructures, the predominant character is that of the parent phases; essentially no phase-boundary-like character is observed. Upon transition, first to the  $n = 8$  and then to the  $n = 4$  superlattices, however, increasingly strong phase-boundary-like character is observed in the FORC corresponding to increasing interfacial volume behavior more like that material. In the short-period superlattices ( $n = 2$ ), the three FORC distributions merge together, albeit with a higher coercive field than in the reference single-layer phase-boundary PbZr<sub>0.52</sub>Ti<sub>0.48</sub>O<sub>3</sub>, suggesting that even in this ultrathin structure, some remnant parent character is maintained. This also explains why this film retains the same coercive field as other superlattices.

In conclusion, this work examined the role of superlattice periodicity in the observation of simultaneous large susceptibility and polarization in the PbZr<sub>1-x</sub>Ti<sub>x</sub>O<sub>3</sub> system. While atomically precise (PbZr<sub>0.8</sub>Ti<sub>0.2</sub>O<sub>3</sub>)<sub>n</sub>/(PbZr<sub>0.4</sub>Ti<sub>0.6</sub>O<sub>3</sub>)<sub>2n</sub> superlattices with overall film chemistry near the morphotropic phase boundary exhibit uniformly large polarization, there is significant superlattice-periodicity-dependent evolution of the

dielectric permittivity and switching behavior. FORC studies reveal separate switching events for each of the parent layers in addition to a phase-boundary-like interfacial layer—with the intensity of the latter increasing as the superlattice period is shortened. This corresponds to the creation of a large volume fraction of phase-boundary-like character at the interfaces in these heterostructures such that one can simultaneously achieve large polarization (enabled by the remnant parent character in those layers) and large permittivity (enabled by the emergent interfacial phase-boundary-like character layers). Ultimately, this study opens a pathway for artificial heterostructure design to enhance responses to external perturbation.

## Experimental Section

**Heterostructure Growth:** All heterostructures were grown via RHEED-assisted pulsed-laser deposition using a KrF excimer laser (248 nm, LPX-300, Coherent), in an on-axis geometry. Films were grown on 20 nm Ba<sub>0.5</sub>Sr<sub>0.5</sub>RuO<sub>3</sub>/PrScO<sub>3</sub> (110) single-crystal substrates (Crystec) from ceramic targets. The bottom Ba<sub>0.5</sub>Sr<sub>0.5</sub>RuO<sub>3</sub> layer was grown at a heater temperature of 700 °C in an oxygen-partial pressure of 100 mTorr with a laser fluence of 2.0 J cm<sup>-2</sup> and a laser repetition rate of 10 Hz. Parent phases PbZr<sub>0.8</sub>Ti<sub>0.2</sub>O<sub>3</sub> and/or PbZr<sub>0.4</sub>Ti<sub>0.6</sub>O<sub>3</sub>, were deposited at a heater temperature of 610 °C in an oxygen-partial pressure of 100 mTorr with a laser fluence of 1.4 J cm<sup>-2</sup> and a laser repetition rate of 10 Hz using 10% lead-excess targets. PbZr<sub>0.52</sub>Ti<sub>0.48</sub>O<sub>3</sub> was deposited under the same conditions as the parent phases, again using a 10% lead-excess target. The top electrode, 40 nm BaSr<sub>0.5</sub>RuO<sub>3</sub>, was deposited in situ at 610 °C and 100 mTorr immediately after the deposition of ferroelectric layer(s). All heterostructures grown were tri-layers of the form: 20 nm bottom electrode, 80 nm total ferroelectric layer(s), and 40 nm top electrode. After deposition, films were cooled down to room temperature in an oxygen pressure of 760 Torr at a rate of 10 °C min<sup>-1</sup>.

**Ferroelectric and Dielectric Measurements:** All electrical measurements were performed on the above noted capacitor structures with symmetric Ba<sub>0.5</sub>Sr<sub>0.5</sub>RuO<sub>3</sub> electrodes. Top electrodes were lithographically

patterned and ion-milled to define 50  $\mu\text{m}$  diameter circular capacitors. Ferroelectric properties were measured using a Precision Multiferroic Tester (Radiant Technologies). A triangular voltage profile was employed with a maximum bias of up to  $\pm 4$  V. Ferroelectric hysteresis loops were obtained using a bipolar triangular profile at frequencies ranging from 0.1–10 kHz. Dielectric measurements were carried out using an E4990A Impedance Analyzer (Agilent Technologies) at an ac excitation voltage of 10 mV. Rayleigh dielectric measurements were carried out at a frequency of 1 kHz, wherein the ac-field strength was ramped from 5 up to 50 mV for subswitching regimes and 5 mV to 1 V for switching regimes.

**First-Order Reversal Curve Analysis:** FORC analysis was performed by measuring a series of ascending minor loops at 1 kHz with a monopolar triangular voltage profile between a negative saturation field and variable reversal field  $E_r$ . The distribution of elementary switchable units, according to the Preisach model,<sup>[38]</sup> is mapped out by taking the mixed second derivative of polarization with respect to the actual field ( $E$ ) and the reversal field ( $E_r$ ):

$$\rho(E, E_r) = \frac{\delta^2(P_{\text{FORC}}(E, E_r))}{2\delta E \delta E_r} \quad (2)$$

The coordinates of the FORC distribution was converted to coercive-field and bias-field axes:

$$E_C = \frac{E_r - E}{2} \text{ and } E_B = \frac{E_r + E}{2} \quad (3)$$

## Supporting Information

Supporting Information is available from the Wiley Online Library or from the author.

## Acknowledgements

E.L. acknowledges support from the National Science Foundation under grant DMR-1608938. A.G. acknowledges support from the Gordon and Betty Moore Foundation's EPIQS Initiative, under grant GBMF5307. S.S. acknowledges support from the U.S. Department of Energy, Office of Science, Office of Basic Energy Sciences, under Award Number DE-SC-0012375 for the development of ferroelectric thin films. S.P. acknowledges support from the Army Research Office under Grant W911NF-14-1-0104. G.V. acknowledges support from the National Science Foundation under grant DMR-1708615. A.F. acknowledges support from the National Science Foundation under grant OISE-1545907. L.W.M. acknowledges support from the U.S. Department of Energy, Office of Science, Office of Basic Energy Sciences, Materials Sciences and Engineering Division under Contract No. DE-AC02-05-CH11231 (Materials Project program KC23MP) for the growth and study of advanced functional oxide thin films.

## Conflict of Interest

The authors declare no conflict of interest.

## Keywords

dielectrics, ferroelectricity,  $\text{PbZr}_{1-x}\text{Ti}_x\text{O}_3$ , polarization switching, superlattices

- [1] A. Erbil, Y. Kim, R. A. Gerhardt, *Phys. Rev. Lett.* **1996**, *77*, 1628.
- [2] P. Zubko, S. Gariglio, M. Gabay, P. Ghosez, J.-M. Triscone, *Annu. Rev. Condens. Matter Phys.* **2011**, *2*, 141.
- [3] H. N. Lee, H. M. Christen, M. F. Chisholm, C. M. Rouleau, D. H. Lowndes, *Nature* **2005**, *433*, 395.
- [4] O. Nakagawara, T. Shimuta, T. Makino, S. Arai, H. Tabata, T. Kawai, *Appl. Phys. Lett.* **2000**, *77*, 3257.
- [5] H. Tabata, H. Tanaka, T. Kawai, *Appl. Phys. Lett.* **1994**, *65*, 1970.
- [6] K. Johnston, X. Huang, J. B. Neaton, K. M. Rabe, *Phys. Rev. B* **2005**, *71*, 100103.
- [7] T. Shimuta, O. Nakagawara, T. Makino, S. Arai, H. Tabata, T. Kawai, *J. Appl. Phys.* **2002**, *91*, 2290.
- [8] K. Kathan-Galipeau, P. Wu, Y. Li, L.-Q. Chen, A. Soukiassian, X. Xi, G. S. Darrell, D. A. Bonnelli, *ACS Nano* **2011**, *5*, 640.
- [9] N. Ortega, A. Kumar, O. A. Maslova, Y. I. Yuzyuk, J. F. Scott, R. S. Katiyar, *Phys. Rev. B* **2011**, *83*, 144108.
- [10] N. Ortega, A. Kumar, O. Resto, O. A. Maslova, Y. I. Yuzyuk, J. F. Scott, R. S. Katiyar, *J. Appl. Phys.* **2013**, *114*, 104102.
- [11] B. Bein, H.-C. Hsing, S. J. Callori, J. Sinsheimer, P. V. Chinta, R. L. Headrick, M. Dawber, *Nat. Commun.* **2015**, *6*, 10136.
- [12] P. Wu, X. Ma, Y. Li, C. B. Eom, D. G. Schlom, V. Gopalan, L. Q. Chen, *Appl. Phys. Lett.* **2015**, *107*, 122906.
- [13] Y. L. Tang, Y. L. Zhu, X. L. Ma, A. Y. Borisevich, A. N. Morozovska, E. A. Eliseev, W. Y. Wang, Y. J. Wang, Y. B. Xu, Z. D. Zhang, S. J. Pennycook, *Science* **2015**, *348*, 547.
- [14] E. Bousquet, M. Dawber, N. Stucki, C. Lichtensteiger, P. Hermet, S. Gariglio, J. M. Triscone, P. Ghosez, *Nature* **2008**, *452*, 732.
- [15] J. Y. Jo, P. Chen, R. J. Sichel, S. J. Callori, J. Sinsheimer, E. M. Dufresne, M. Dawber, P. G. Evans, *Phys. Rev. Lett.* **2011**, *107*, 55501.
- [16] A. K. Yadav, C. T. Nelson, S. L. Hsu, Z. Hong, J. D. Clarkson, C. M. Schlepütz, A. R. Damodaran, P. Shafer, E. Arenholz, L. R. Dedon, D. Chen, A. Vishwanath, A. M. Minor, L. Q. Chen, J. F. Scott, L. W. Martin, R. Ramesh, *Nature* **2016**, *530*, 198.
- [17] S. Das, Y. L. Tang, Z. Hong, M. A. P. Gonçalves, M. R. McCarter, C. Klewe, K. X. Nguyen, F. Gómez-Ortiz, P. Shafer, E. Arenholz, V. A. Stoica, S. L. Hsu, B. Wang, C. Ophus, J. F. Liu, C. T. Nelson, S. Saremi, B. Prasad, A. B. Mei, D. G. Schlom, J. Íñiguez, P. García-Fernández, D. A. Muller, L. Q. Chen, J. Junquera, L. W. Martin, R. Ramesh, *Nature* **2019**, *568*, 368.
- [18] G. Liu, Q. Zhang, H. H. Huang, P. Munroe, V. Nagarajan, H. Simons, Z. Hong, L. Q. Chen, *Adv. Mater. Interfaces* **2016**, *3*, 1600444.
- [19] F. Xue, J. J. Wang, G. Sheng, E. Huang, Y. Cao, H. H. Huang, P. Munroe, R. Mahjoub, Y. L. Li, V. Nagarajan, L. Q. Chen, *Acta Mater.* **2013**, *61*, 2909.
- [20] N. Sai, B. Meyer, D. Vanderbilt, *Phys. Rev. Lett.* **2000**, *84*, 5636.
- [21] E. D. Specht, H. Christen, D. P. Norton, L. A. Boatner, *Phys. Rev. Lett.* **1998**, *80*, 4317.
- [22] B. Jaffe, R. S. Roth, S. Marzullo, *J. Appl. Phys.* **1954**, *25*, 809.
- [23] B. Noheda, D. E. Cox, G. Shirane, J. A. Gonzalo, L. E. Cross, S.-E. Park, *Appl. Phys. Lett.* **1999**, *74*, 2059.
- [24] R. V. K. Mangalam, J. Karthik, A. R. Damodaran, J. C. Agar, L. W. Martin, *Adv. Mater.* **2013**, *25*, 1761.
- [25] J. C. Agar, A. R. Damodaran, M. B. Okatan, J. Kacher, C. Gammer, R. K. Vasudevan, S. Pandya, L. R. Dedon, R. V. K. Mangalam, G. A. Velarde, S. Jesse, N. Balke, A. M. Minor, S. V. Kalinin, L. W. Martin, *Nat. Mater.* **2016**, *15*, 549.
- [26] J. C. Agar, A. R. Damodaran, G. A. Velarde, S. Pandya, R. V. K. Mangalam, L. W. Martin, *ACS Nano* **2015**, *9*, 7332.
- [27] H. H. Huang, Q. Zhang, E. Huang, R. Maran, O. Sakata, Y. Ehara, T. Shiraishi, H. Funakubo, P. Munroe, N. Valanoor, *Adv. Mater. Interfaces* **2015**, *2*, 1500075.

- [28] D. Bao, R. Scholz, M. Alexe, D. Hesse, *J. Appl. Phys.* **2007**, *101*, 054118.
- [29] I. A. Kornev, L. Bellaiche, *Phys. Rev. Lett.* **2003**, *91*, 116103.
- [30] S. Pandya, G. A. Velarde, R. Gao, A. S. Everhardt, J. D. Wilbur, R. Xu, J. T. Maher, J. C. Agar, C. Dames, L. W. Martin, *Adv. Mater.* **2019**, *31*, 1803312.
- [31] B. Noheda, D. E. Cox, G. Shirane, R. Guo, B. Jones, L. E. Cross, *Phys. Rev. B* **2000**, *63*, 14103.
- [32] E. Cross, *Nature* **2004**, *432*, 24.
- [33] P.-E. Janolin, *J. Mater. Sci.* **2009**, *44*, 5025.
- [34] S. Hoon Oh, H. W. Jang, *Phys. Rev. B* **2000**, *62*, 14757.
- [35] N. A. Pertsev, V. G. Kukhar, H. Kohlstedt, R. Waser, *Phys. Rev. B* **2003**, *67*, 54107.
- [36] D. A. Hall, P. J. Stevenson, *Ferroelectrics* **1999**, *228*, 139.
- [37] N. Bassiri-Gharb, I. Fujii, E. Hong, S. Trolier-Mckinstry, D. V. Taylor, D. Damjanovic, *J. Electroceram.* **2007**, *19*, 49.
- [38] R. Xu, J. Karthik, A. R. Damodaran, L. W. Martin, *Nat. Commun.* **2014**, *5*, 3120.
- [39] A. Stancu, D. Ricinschi, L. Mitoseriu, P. Postolache, M. Okuyama, *Appl. Phys. Lett.* **2003**, *83*, 3767.
- [40] C. R. Pike, A. P. Roberts, K. L. Verosub, *J. Appl. Phys.* **1999**, *85*, 6660.
- [41] Y. Kim, A. Kumar, O. Ovchinnikov, S. Jesse, H. Han, D. Pantel, I. Vrejoiu, W. Lee, D. Hesse, M. Alexe, S. V. Kalinin, *ACS Nano* **2012**, *6*, 491.