

# UC Berkeley

## SEMM Reports Series

### Title

The Modified Kuhn Model of Linear Viscoelasticity

### Permalink

<https://escholarship.org/uc/item/9nz4p6p7>

### Authors

Lubliner, Jacob

Panoskaltsis, Vassilis

### Publication Date

1992-02-01

**REPORT NO.  
UCB/SEMM-92/01**

**STRUCTURAL ENGINEERING  
MECHANICS AND MATERIALS**

**THE MODIFIED KUHN MODEL  
OF LINEAR VISCOELASTICITY**

**BY**

**J. LUBLINER  
AND  
V. P. PANOSKALTSIS**

**FEBRUARY 1992**

**DEPARTMENT OF CIVIL ENGINEERING  
UNIVERSITY OF CALIFORNIA  
BERKELEY, CALIFORNIA**

# THE MODIFIED KUHN MODEL OF LINEAR VISCOELASTICITY

J. Lubliner and V. P. Panoskaltsis  
Department of Civil Engineering  
University of California at Berkeley

## Abstract

A model of linear viscoelasticity introduced by Kuhn et al. to describe rubber is modified by the addition of instantaneous elasticity in order to be applicable to structural materials whose creep is asymptotically logarithmic; this is referred to as the continuous modified Kuhn model. The relaxation function is determined by Laplace transform inversion. Energy dissipation is studied, and in particular the frequency dependence of the loss tangent, which is found to be flat over a large number of cycles if the damping is small, in accordance with observed behavior of structural materials and unlike the usual (Kelvin) model of structural damping. An approximation to the modified model based on a discrete retardation-time spectrum, called the discrete modified Kuhn model, is also studied; this is an internal-variable model which can be extended to account for nonlinear behavior.

## 1 Introduction

Beginning with the experiments of Phillips [1905], the creep of numerous solids (including rubber, glass, various metals, and concrete) has been observed to obey a logarithmic creep law over a wide range of times; that is, at a time  $t$  sufficiently long after the application of stress, the strain is given approximately by

$$\epsilon \propto \ln t. \quad (1)$$

For concrete in the linear range, for example, the creep function

$$J(t) = A + B \log(1 + t/\tau) \quad (2)$$

is often used (U.S. Bureau of Reclamation [1956]) to describe creep over a time range of months or years if  $\tau$  is a characteristic time of the order of one day. Obviously, Equation (2) reduces to the form (1) for  $t$  sufficiently large.



Following Phillips, the creep of rubber was traditionally described by the creep function

$$J(t) = A + B \ln t \quad (3)$$

and its time derivative

$$\dot{J}(t) = \frac{B}{t}. \quad (4)$$

In order to remedy the singularity at  $t = 0$ , Kuhn et al. [1947] proposed to replace the expression (4) for the time derivative of the creep function with

$$\dot{J}(t) = \frac{B}{t}(1 - e^{-Ct}), \quad (5)$$

which has the finite limit  $BC$  as  $t \rightarrow 0$  and has the same behavior as (4) as  $t \gg 1/C$ . Kuhn et al. defined the creep function as the integral of (5) from 0 to  $t$ , with no constant of integration, consistent with the fact that the instantaneous deformation of rubber, based on “glassy” response (i.e. for temperatures below the glass-transition temperature  $T_g$ ; see, e.g., DiBenedetto [1967] or Van Vlack [1989]), is negligible when compared with later deformation (based on “rubbery” response, i.e. for temperature above  $T_g$ ). This creep function can be expressed in terms of the exponential integral (see, e.g., Greenberg [1978], p. 43) as follows:

$$J(t) = B \int_0^t \frac{1 - e^{-Cx}}{x} dx = B[\gamma + \ln(Ct) + \text{Ei}(Ct)], \quad (6)$$

where Ei represents the exponential integral and  $\gamma = 0.5772\dots$  is Euler’s constant. It is seen from this expression that  $J(0) = 0$  and that the logarithmic feature of the observed creep function (3) is preserved.

It is the purpose of the present paper to propose several modifications to the Kuhn creep function (6) that will make it more readily applicable to solids such as concrete (in which the instantaneous strain is not negligible beside the creep strain) and generalizable to multiaxial stress states and to nonlinear behavior.

## 2 The Continuous Modified Kuhn Model

The first modification, at first glance minor but in fact significant in that it makes possible the description of structural materials, is the inclusion of a nonzero constant of integration in the expression for the creep function in order to account for



instantaneous elasticity. The creep function is therefore

$$J(t) = A + B \int_0^t \frac{1 - e^{-Cx}}{x} dx, \quad (7)$$

where  $A$  is the instantaneous elastic compliance.

The second modification involves a change of variable, namely  $Cx = t/\tau$ , where  $\tau$  is the new dummy variable, in order to obtain a rheological representation of the model. The creep function can then be written in the following retardation-time superposition form:

$$J(t) = A + B \int_{1/C}^{\infty} (1 - e^{-t/\tau}) \frac{d\tau}{\tau} \quad (8)$$

This creep function given by (7) or (8) will be said to represent the *continuous modified Kuhn model*, since it is based on a continuous retardation-time spectrum, in order to distinguish it from the *discrete modified Kuhn model* to be discussed in Section 4.

## 2.1 Relaxation Function

The relaxation function  $G(t)$  corresponding to the creep function (8) may be determined by means of Laplace transform methods. It is well known (see, e.g., Christensen [1982] or Flügge [1975]) that the Laplace transforms of the creep and relaxation functions, written respectively as  $\bar{J}(s) \stackrel{\text{def}}{=} \mathcal{L}\{J(t)\}$  and  $\bar{G}(s) \stackrel{\text{def}}{=} \mathcal{L}\{G(t)\}$  (where  $s$  is the transform variable, in general complex), are related by

$$\bar{J}(s)\bar{G}(s) = \frac{1}{s^2}. \quad (9)$$

The relaxation function may therefore be found by inverting  $\bar{G}(s)$  as given by (9). Using the creep function in the form given by Equation (7), we have

$$\bar{J}(s) = \frac{A}{s} + B \int_0^t \left( \int_0^t \frac{1 - e^{-C\tau}}{\tau} d\tau \right) e^{-st} dt,$$

or

$$\bar{J}(s) = \frac{A}{s} + B \mathcal{L} \left\{ \int_0^t f(\tau) d\tau \right\} = \frac{A}{s} + B \frac{\bar{f}(s)}{s}, \quad (10)$$

where

$$f(t) \stackrel{\text{def}}{=} \frac{1 - e^{-Ct}}{t},$$

so that

$$\bar{f}(s) = \mathcal{L}\{f(t)\} = \mathcal{L}\left\{\frac{g(t)}{t}\right\},$$

where

$$g(t) = 1 - e^{-Ct}.$$

From the properties of the Laplace transform it follows that

$$\bar{f}(s) = \int_s^\infty \bar{g}(u) du,$$

while

$$\bar{g}(s) = \int_0^\infty (1 - e^{-C\tau}) e^{-su} du = \frac{1}{s} - \frac{1}{C+s}.$$

Therefore

$$\bar{f}(s) = \int_s^\infty \left( \frac{1}{u} - \frac{1}{u+C} \right) du = \ln \frac{s+C}{s}.$$

As a result of Equation (10), the Laplace transform of the creep function is

$$\bar{J}(s) = \frac{1}{s} \left[ A + B \ln \left( 1 + \frac{C}{s} \right) \right], \quad (11)$$

and by relation (9) the Laplace transform of the relaxation function is found to be

$$\bar{G}(s) = \frac{1}{s \left[ A + B \ln \left( 1 + \frac{C}{s} \right) \right]}.$$

It follows from the Laplace transform inversion theorem that the relaxation function  $G(t)$  is given by the Bromwich integral:

$$G(t) = \mathcal{L}^{-1}[\bar{G}(s)] = \frac{1}{2\pi i} \int_{\alpha-i\infty}^{\alpha+i\infty} \bar{G}(s) e^{st} ds,$$

where  $\alpha$  denotes an abscissa located to the right of any singularity  $\bar{G}(s)$  may have. Hence,

$$G(t) = \frac{1}{2\pi i} \int_{\alpha-i\infty}^{\alpha+i\infty} \frac{e^{st}}{s \left[ A + B \ln \left( 1 + \frac{C}{s} \right) \right]} ds. \quad (12)$$

The integrand must be examined in order to determine its singularities, and in particular poles and branch cuts. The singularity at  $s = 0$  is removable. On the other hand, the one at  $s = s_0$ , where  $A + B \ln(1 + C/s_0) = 0$ , is a pole. We may solve for  $s_0$ , obtaining

$$s_0 = -\frac{C}{1 - e^{-A/B}}. \quad (13)$$

Finally, there is a logarithmic branch cut from on the negative real axis from  $-C$  to  $0$ , since for  $s$  in the interval  $[-C, 0]$ ,  $1 + C/s < 0$ . It is observed from equation (13) that  $s_0 < -C$ . Hence the description in the complex plane is the one portrayed in Figure 1. With the aid of Cauchy's integral theorem, the relaxation function  $G(t)$  given by Equation (12) becomes

$$G(t) = \text{Res}(e^{st}\bar{G}(s), s_0) + \frac{1}{2\pi i}(I_1 + I_2) \quad (14)$$

where  $\text{Res}(e^{st}\bar{G}(s), s_0)$  is the residue of the function  $e^{st}\bar{G}(s)$  associated with the pole  $s = s_0$ , and  $I_1$  and  $I_2$  are the integrals above and below the branch cut, respectively. According to a well-known theorem of complex analysis (see, e.g., [Marsden & Hoffman [1987], p. 268), for a function of the form  $f(s) = g(s)/h(s)$  with  $g$  and  $h$  are analytic at  $s_0$  and  $g(s_0) \neq 0$ ,  $h(s_0) = 0$ , and  $h'(s_0) \neq 0$ , the residue associated with the simple pole at  $s = s_0$  is

$$\text{Res}(f(s), s_0) = \lim_{s \rightarrow s_0} (s - s_0)f(s) = \frac{g(s_0)}{h'(s_0)}$$

Since the present case fulfills all the conditions stated above, the residue is

$$\begin{aligned} \text{Res}(e^{st}\bar{G}(s), s_0) &= \lim_{s \rightarrow s_0} \frac{(s - s_0)e^{st}}{s \left[ A + B \ln \left( 1 + \frac{C}{s} \right) \right]} \\ &= \frac{e^{s_0 t}}{\left\{ s \left[ A + B \ln \left( 1 + \frac{C}{s} \right) \right] \right\}' \Big|_{s=s_0}}. \end{aligned}$$

Some lengthy but straightforward calculations lead to

$$\text{Res}(e^{st}\bar{G}, s_0) = -\frac{e^{-Ct/(1-e^{-A/B})}}{B(e^{A/B} - 1)}. \quad (15)$$



In order to evaluate the integrals  $I_1$  and  $I_2$ , we recall that the logarithm of the complex variable  $s$  is given by

$$\ln s = \ln |s| + i \arg s$$

where  $-\pi < \arg s < \pi$ . Above the branch cut,  $s = re^{i\pi}$ , where  $s \in [-C, 0]$  and  $C > r = -s > 0$ , hence

$$\ln \left( 1 + \frac{C}{s} \right) = \ln \left( \frac{C}{r} - 1 \right) + i\pi.$$

Below the branch cut,  $s = re^{-i\pi}$ ,  $r = -s$ , and hence

$$\ln \left( 1 + \frac{C}{s} \right) = \ln \left( \frac{C}{r} - 1 \right) - i\pi.$$

With the help of these expressions, the integrals  $I_1$  and  $I_2$  become

$$I_1 = \int_C^0 \frac{e^{re^{i\pi}t}}{-r[A + B \ln(C/r - 1) + iB\pi]}(-dr) = - \int_0^C \frac{e^{-rt}}{r[A + B \ln(C/r - 1) + iB\pi]}dr.$$

and,

$$I_2 = \int_0^C \frac{e^{re^{-i\pi}t}}{-r[A + B \ln(C/r - 1) - iB\pi]}(-dr) = \int_0^C \frac{e^{-rt}}{r[A + B \ln(C/r - 1) - iB\pi]}dr.$$

Then since  $I_1$  and  $I_2$  are complex conjugate we obtain,

$$\begin{aligned} \frac{1}{2\pi i}(I_1 + I_2) &= \frac{1}{2\pi i} \int_0^C \left\{ -\frac{e^{-rt}}{r[A + B \ln(C/r - 1) + iB\pi]} + \frac{e^{-rt}}{r[A + B \ln(C/r - 1) - iB\pi]} \right\} dr \\ &= \frac{1}{\pi} \text{Im} \int_0^C \frac{e^{-rt}}{r[A + B \ln(C/r - 1) - iB\pi]} dr. \end{aligned}$$

where Im denotes the imaginary part of a complex quantity. By performing the change of variables  $x = r/C$ , and upon noting that  $0 < r < C$  implies  $0 < x < 1$ , we may transform this integral into

$$\begin{aligned} \frac{1}{2\pi i}(I_1 + I_2) &= \frac{1}{\pi} \text{Im} \int_0^1 \frac{e^{-xCt}}{xC[A + B \ln(1/x - 1) - iB\pi]} C dx \\ &= B \int_0^1 \frac{e^{-xCt}}{x \{ [A + B \ln(1/x - 1)]^2 + (B\pi)^2 \}} dx. \end{aligned}$$

Combining this result with Equations (14) and (15), we obtain the relaxation function in a form in which it may be evaluated by numerical integration, namely

$$G(t) = -\frac{e^{-Ct/(1-e^{-A/B})}}{B(e^{A/B} - 1)} + B \int_0^1 \frac{e^{-x Ct}}{x \{ [A + B \ln(1/x - 1)]^2 + (B\pi)^2 \}} dx.$$

While the integrand blows up at  $x = 0$ , it can be shown that the integral is well behaved there. For sufficiently small  $x$ , the denominator is approximately  $B^2 x [\ln(1/x)]^2$ , so that it is sufficient to examine the behavior of the integral

$$\int_0^h \frac{dx}{x [\ln(1/x)]^2} = \int_0^h \frac{dx}{x (\ln x)^2}$$

for some small  $h$  ( $h \ll 1$ ). By introducing the variable  $u = \ln x$ , this integral becomes

$$\int_{-\infty}^{\ln h} \frac{du}{u^2} = \frac{1}{\ln(1/h)}.$$

### 3 Energy Dissipation

#### 3.1 Thermodynamic Considerations

Energy dissipation in a linearly viscoelastic material may be discussed on the basis of the thermodynamics of materials with internal variables. In this section special attention will be paid to the description of the dissipation by the proposed model, in particular its relation with the frequency of excitation. By way of background it is recalled that if an oscillatory strain of angular frequency  $\omega$ ,

$$\varepsilon(t) = \varepsilon_0 \sin \omega t, \quad (16)$$

is applied to a linear viscoelastic material specimen, the steady-state stress response  $\sigma$  is also oscillatory with the same angular frequency  $\omega$ , but out of phase with the strain. In particular, the stress leads the strain by a phase angle  $\delta(\omega)$  and is given by

$$\sigma(t) = \sigma_0 \sin(\omega t + \delta(\omega)). \quad (17)$$

For simplicity, the explicit dependence of the angle  $\delta$  on  $\omega$  will henceforth be omitted. The dissipated energy, as will be seen, is associated with the phase angle  $\delta$ . If  $\omega t$  is

eliminated between Equations (16–17), the following relation is obtained:

$$\frac{\sigma^2(t)}{\sigma_0^2} + \frac{\varepsilon^2(t)}{\varepsilon_0^2} - 2\sigma(t)\varepsilon(t)\frac{\cos \delta}{\varepsilon_0\sigma_0} = \sin^2 \delta.$$

This equation describes an ellipse in the  $\sigma$ - $\varepsilon$  plane.

The dissipated energy may be calculated by appealing to the first and second laws of thermodynamics. The local form of this law is

$$\rho \dot{u} = \boldsymbol{\sigma} : \dot{\boldsymbol{\varepsilon}} + \rho r - \operatorname{div} \mathbf{h} \quad (18)$$

(see, e.g., Lubliner [1990]), where  $u$  is the internal energy density,  $\rho$  is the material density,  $r$  is the rate of body heating or radiation per unit mass, and  $\mathbf{h}$  is the heat-flux vector (so that  $h = \mathbf{h} \cdot \mathbf{n}$  is the heat outflow per unit time per unit surface with normal vector  $\mathbf{n}$ ). The inner product of the stress with the strain rate tensor represents the mechanical power (also called deformation power or stress power) per unit volume.

Let a *cyclic process* in a material element be defined as a process in which the kinematic and response functions defining the state of the element have the same values at the beginning (time  $t_1$ ) and at the end of the process (time  $t_2$ ). Upon integrating Equation (18) from  $t_1$  to  $t_2$ , it is seen that

$$\int_{t_1}^{t_2} \boldsymbol{\sigma} : \dot{\boldsymbol{\varepsilon}} dt + \int_{t_1}^{t_2} (\rho r - \operatorname{div} \mathbf{h}) dt = 0,$$

since the internal-energy density is a state function and therefore has the same value at instants at which the state is the same. Since the steady-state excitation is a cyclic process, it follows that the integral of the deformation power over a period (equal to the area inside the stress-strain loop in the one-dimensional case) equals the amount of heat produced (or the mechanical energy dissipated) during this time. It is clear from the above derivation that the area of the stress-strain loop represents the dissipated energy only in the case of a steady-state deformation and for a period. It can be mentioned here that Tschoegl [1989] arrives at the same result on the basis of the assumption that the kinetic energy can be neglected for a viscoelastic material; this assumption is unnecessary, and is wrong in general.

The second law of thermodynamics may be expressed by the Kelvin inequality

$$D = \sum_{\alpha} p_{\alpha} \dot{\xi}_{\alpha} \geq 0$$

(Lubliner [1990]), where  $D$  is the intrinsic dissipation (Lemaitre & Chaboche [1990]),

$$p_\alpha = -\rho \frac{\partial \psi}{\partial \xi_\alpha}$$

is the “thermodynamic force” conjugate to the internal variable  $\xi_\alpha$ , and  $\psi$  is the Helmholtz free-energy density per unit mass. It was shown by Lubliner [1972] that the additive decomposition of the strain tensor  $\epsilon$  into elastic ( $\epsilon^e$ ) and inelastic parts ( $\epsilon^i$ ) is compatible with the existence of a free energy density  $\psi(\epsilon, \xi, T)$  if and only if the free energy can be decomposed as follows:

$$\psi(\epsilon, T, \xi) = \psi^e(\epsilon - \epsilon^i(\xi), T) + \psi^i(\xi, T). \quad (19)$$

Then the dissipation becomes

$$D = \sigma : \dot{\epsilon}^i - \rho \sum_\alpha \frac{\partial \psi^i}{\partial \xi_\alpha} \dot{\xi}_\alpha$$

with the help of the standard relation  $\sigma = \rho \partial \psi / \partial \epsilon$ , which is derived in different ways by the “rational thermodynamics” school (Truesdell [1984], Coleman & Gurtin [1967]) and the “accompanying equilibrium state” school (Bataille & Kestin [1975], Germain et al. [1983]); the derivation from the point of view of the “rational thermodynamics” school is known as Coleman’s method (see Woods [1981] for a critique of this school).

If the part of the dissipation made up of the inelastic work rate  $\sigma : \dot{\epsilon}^i$  is integrated through a cyclic process, we obtain

$$\int_{t_1}^{t_2} \sigma : \dot{\epsilon}^i dt = \int_{t_1}^{t_2} \sigma : \dot{\epsilon} dt - \int_{t_1}^{t_2} \sigma : \dot{\epsilon}^e dt.$$

Because of the relation (19), the stress tensor is given by

$$\sigma = \rho \frac{\partial \psi^e}{\partial \epsilon^e}.$$

Hence the second integral of the right-hand side equals the difference of the values of  $\psi^e$  (which is a function of  $\epsilon^e$  and  $T$ ) at the beginning and at the end of the cycle and is zero for isothermal conditions ( $\epsilon^e$  attains the same values at the beginning and end of the cycle for isothermal conditions, since  $\sigma$  does so and  $\epsilon^e = \hat{\epsilon}^e(\sigma, T)$ ). Since  $\epsilon(\sigma, T, \xi)$  and  $\sigma$  attain the same values at the end of the cycle and because specifically

a steady-state cycle is being considered, it is reasonable to assume that in such a cycle the internal-variable vector  $\xi$  also has the same value at the end of the cycle. Hence the integral over a cycle of the second part of the dissipation  $D = -\rho \sum_{\alpha} (\partial \psi^i / \partial \xi_{\alpha}) \dot{\xi}_{\alpha}$  equals zero in an isothermal process, in view of the Equation (19). Hence

$$W_d = \int_{t_1}^{t_2} D dt = \int_{t_1}^{t_2} \sigma : \dot{\epsilon} dt$$

Consequently, we have arrived at the same result as before, i.e. the dissipated energy is given by the area of the stress-strain loop in a steady-state cycle. It is interesting to note that the result based on the second law of thermodynamics is the same as the one based on the first law, but with the additional assumption of isothermal processes.

Upon combining the above results with the relations (16) and (17) and integrating over a period, we obtain the dissipated energy per unit volume in a cycle,

$$W_d = \int \sigma d\epsilon = \int_0^{2\pi/\omega} \sigma_0 \sin(\omega t + \delta) \epsilon_0 \omega \cos \omega t dt,$$

and upon performing the integration,

$$W_d = \sigma_0 \epsilon_0 \pi \sin \delta. \quad (20)$$

Hence the tangent of the phase angle  $\delta$ , known as the loss tangent, is

$$\tan \delta = \frac{W_d}{\pi \sigma_0 \epsilon_0 \cos \delta}.$$

The strain attains its maximum value  $\epsilon_0$  at  $t = T/4$ , and the corresponding value of the stress is  $\sigma = \sigma_0 \cos \delta$ . If  $W_s$  denotes the stored energy per unit volume of a linear elastic material strained up to  $\epsilon_0$  with corresponding stress  $\sigma = \sigma_0 \cos \delta$ , then  $W_s$  is

$$W_s = 1/2 \sigma_0 \epsilon_0 \cos \delta,$$

so that

$$\tan \delta = \frac{W_d}{2\pi W_s}. \quad (21)$$



### 3.2 Comparison with Kelvin Model

The analysis presented above may be compared with that used frequently in structural dynamics. Assume that a body or an element is subjected to a displacement-controlled sinusoidal excitation given by  $\Delta = \Delta_0 \sin \omega t$ . The resulting steady-state force is

$$F = F_0 \sin(\omega t + \delta).$$

As a rule the Kelvin model is used in structural dynamics, though without being explicitly referred to; it is commonly known by other names, such as "viscous model" or "standard structural model," and it is sometimes thought, confusingly, that all linear damping models are Kelvin models. With the Kelvin model, the force-displacement relation is  $F = K\Delta + H\dot{\Delta}$ , where  $K$  and  $H$  are the stiffness and viscous coefficient, respectively, of the element under consideration. By comparing the two expressions for the force, we have the result that  $\cos \delta = K\Delta_0/F_0$  and  $\sin \delta = H\omega\Delta_0/F_0$ . Hence the loss tangent is

$$\tan \delta = \frac{H\omega}{K}. \quad (22)$$

With the help of this expression, the force becomes

$$F = K\Delta + \frac{K}{\omega} \tan \delta \dot{\Delta}.$$

With the preceding expression for  $\sin \delta$  and with Equation (20), the following expression is obtained for the energy dissipated in a complete cycle by the element under consideration:

$$W_d = \pi H \omega \Delta_0^2. \quad (23)$$

If the element comprises a single-degree-of-freedom system with mass  $M$  and natural frequency  $\omega_0 = \sqrt{K/M}$ , then the damping coefficient is  $\xi = H/H_{\text{crit}} = H/2M\omega_0 = H\omega_0/2K$ ; hence the viscous coefficient is  $H = 2M\omega_0\xi = (2K/\omega_0)\xi$ . Comparing this expression for the one previously found for the viscous coefficient,  $H = \tan \delta K/\omega$ , yields the result

$$\xi = \frac{\tan \delta \omega_0}{2 \omega},$$

so that at resonance ( $\omega = \omega_0$ ) the damping coefficient equals one-half the loss tangent.

With the help of Equation (21) it is also found that

$$\xi = \frac{W_d}{4\pi W_s}$$

at resonance. From Equation (23) we observe that the dissipated energy as predicted by the Kelvin model is quadratic in the displacement and linear in the frequency, while from Equation (22) we note that the loss tangent is linear in the frequency. This predicted behavior is contrary to that observed in most structural materials (Nashif et al. [1985], Kelly [1991]), in which the damping coefficient is essentially independent of frequency. This frequency independence is usually modeled by hysteretic damping (Crandall [1963], Kelly [1991], Nashif et al. [1985]), which although convenient in frequency-domain analysis is intractable in time-domain analysis. The latter is often preferable because nonlinearities can then be taken into account.

### 3.3 Frequency Representation

A mathematically powerful way of presenting the loss tangent is by means of the frequency representation which will be used here (Golden & Graham [1988]). Let  $\zeta$  denote the function

$$\zeta(t) = J(0)\delta(t) + \dot{J}(t)H(t) \quad (24)$$

where  $H(t)$  is the Heaviside step function and  $\delta(t)$  is the Dirac delta function. The strain may then be represented (Golden & Graham [1988]) as

$$\varepsilon(t) = \int_{-\infty}^t \zeta(t-t')\sigma(t')dt', \quad (25)$$

where the lower limit may be replaced by  $t_1$  if  $\varepsilon(t) = 0$  for  $t < t_1$ . Similarly we may define

$$\mu(t) = G(0)\delta(t) + \dot{G}(t)H(t),$$

so that

$$\sigma(t) = \int_{-\infty}^t \mu(t-t')\varepsilon(t')dt'. \quad (26)$$

Let  $\hat{\zeta}(\omega)$  denote the Fourier transform of  $\zeta(t)$ , i.e.

$$\hat{\zeta}(\omega) = \int_0^\infty \zeta(t)e^{-i\omega t}dt \stackrel{\text{def}}{=} \mathcal{F}\{\zeta\},$$

with similar definitions for  $\hat{\mu}(\omega)$ ,  $\hat{\sigma}(\omega)$ , and  $\hat{\varepsilon}(\omega)$ . It can easily be shown that

$$\hat{\zeta}(\omega) = i\omega\bar{J}(i\omega), \quad \hat{\mu}(\omega) = i\omega\bar{G}(i\omega),$$

where  $\bar{J}$  and  $\bar{G}$  denote the Laplace transforms as before. By taking the Fourier transforms of Equations (25) and (26) we obtain

$$\hat{\varepsilon}(\omega) = \hat{\zeta}(\omega)\hat{\sigma}(\omega), \quad \hat{\sigma}(\omega) = \hat{\mu}(\omega)\hat{\varepsilon}(\omega),$$

so that

$$\hat{\mu}(\omega) = \frac{1}{\hat{\zeta}(\omega)}.$$

The complex functions  $\hat{\mu}(\omega)$  and  $\hat{\zeta}(\omega)$  are respectively known as the complex modulus and complex compliance. If  $\hat{\mu}(\omega) = \hat{\mu}_1(\omega) + i\hat{\mu}_2(\omega)$ , where  $\mu_1(\omega)$  and  $\mu_2(\omega)$  are usually referred to as the storage modulus and the loss modulus, respectively, then the loss tangent is

$$\tan \delta = \frac{\hat{\mu}_2(\omega)}{\hat{\mu}_1(\omega)}.$$

Similarly, if  $\hat{\zeta}(\omega) = \hat{\zeta}_1(\omega) - i\hat{\zeta}_2(\omega)$ , then

$$\tan \delta = \frac{\hat{\zeta}_2(\omega)}{\hat{\zeta}_1(\omega)}. \quad (27)$$

For the continuous modified Kuhn model it follows from Equation (11) that

$$\hat{\zeta}(\omega) = A + B \ln \left( 1 + \frac{C}{i\omega} \right) = A + B \ln \sqrt{1 + \frac{C^2}{\omega^2}} - iB \tan^{-1} \left( \frac{C}{\omega} \right).$$

The loss tangent of the continuous modified Kuhn model is therefore

$$\tan \delta = \frac{\beta \tan^{-1} \frac{1}{q}}{1 + \beta \ln \left( 1 + \frac{1}{q^2} \right)^{1/2}} \quad (28)$$

where  $\beta = B/A$  and  $q = \omega/C$ . Plots of the creep function  $J(t)$ , as given by Equation (7), against the logarithm of time and of the loss tangent, given by Equation (28), against the logarithm of  $q$  are shown in Figures 2 and 3, respectively. It is observed from the latter plot that for small values of  $\beta$ , the loss tangent is almost constant over a wide frequency range, which is a characteristic of structural materials, and the values are similar to those observed in structural materials. The Kelvin model notoriously fails to predict this type of behavior, since its loss tangent varies linearly with the frequency.

## 4 The Discrete Modified Kuhn Model

Let  $J_N(t)$  denote the following truncated Dirichlet (or Prony) series:

$$J_N(t) = A + B \ln r \sum_{m=0}^N (1 - e^{-Ct/r^m}). \quad (29)$$

where  $r$  is a parameter subject to  $r > 1$ . This series represents the creep function of a generalized Kelvin model, shown in Figure 4, consisting of a spring with compliance  $A$  in series with  $N+1$  Kelvin elements, each of which has the same spring compliance  $B \ln r$ , and whose retardation times form a discrete spectrum with values  $r^m/C$ ,  $m = 0, \dots, N$ . It will be shown that  $J_N(t)$  has as a limit, under conditions that will be specified, the creep function  $J(t)$  of the continuous modified Kuhn model. Consequently the model described by  $J_N(t)$  may be called the *discrete modified Kuhn model*. It is noteworthy that the only parameters describing the model are  $A$ ,  $B$ ,  $r$  and  $N$ , so that the number of parameters is independent of  $N$ .

**Theorem.**

$$J_N(t) \rightarrow J(t) \text{ as } N \rightarrow \infty, r \rightarrow 1+, r^N \rightarrow \infty.$$

It should be noted that the first two conditions,  $N \rightarrow \infty$  and  $r \rightarrow 1+$ , are not sufficient for the third,  $r^N \rightarrow \infty$ , as can be seen from the following counterexample: If  $r$  is given by the sequence  $1 + 1/N$ , then it is seen that  $r \rightarrow 1+$  as  $N \rightarrow \infty$ , while  $r^N = (1 + 1/N)^N \rightarrow e$ .

The proof of the theorem is as follows. The improper integral of the expression (8) for the creep function is given by

$$I \stackrel{\text{def}}{=} \int_{1/C}^{\infty} (1 - e^{-t/\tau}) \frac{d\tau}{\tau} = \lim_{H \rightarrow \infty} \int_{1/C}^H (1 - e^{-t/\tau}) \frac{d\tau}{\tau}.$$

By definition of the Riemann integral, the integral  $I$  is

$$I = \lim_{H \rightarrow \infty} \lim_{\substack{N \rightarrow \infty \\ \|\Delta\tau_m\| \rightarrow 0}} \sum_{m=0}^N f(\tau_m^*) \Delta\tau_m$$

where  $f(\tau) \stackrel{\text{def}}{=} (1 - e^{-t/\tau})/\tau$ ,  $\tau_m^*$  stands for an arbitrary value inside the interval  $\tau_m \leq \tau_m^* \leq \tau_{m+1}$ ,  $\Delta\tau_m = \tau_{m+1} - \tau_m$ , and  $N$  is the number of intervals. It is noted that  $\tau_0$  is equal to  $1/C$ , i.e. it is the lower limit of integration, and that  $H = r^N/C$ ,

hence  $H \rightarrow \infty$  when  $r^N \rightarrow \infty$ . If we now further take  $\tau_m^* = \tau_m$ , the above equation becomes

$$\int_{1/C}^{\infty} (1 - e^{-t/\tau}) \frac{d\tau}{\tau} = \lim_{r^N \rightarrow \infty} \lim_{\substack{N \rightarrow \infty \\ r \rightarrow 1}} \sum_{m=0}^N (1 - e^{-Ct/r^m})(r - 1). \quad (30)$$

If the function  $\ln r$  is expanded in a Taylor series about  $r = 1$ , we obtain

$$\ln r = 0 + (r - 1) - \frac{1}{2}(r - 1)^2 + O((r - 1)^3),$$

or

$$\ln r = (r - 1) + O((r - 1)^2).$$

Then

$$\begin{aligned} \lim_{\substack{r^N \rightarrow \infty \\ N \rightarrow \infty, r \rightarrow 1}} \ln r \sum_{m=0}^N (1 - e^{-Ct/r^m}) &= \lim_{\substack{r^N \rightarrow \infty \\ N \rightarrow \infty, r \rightarrow 1}} [(r - 1) + O(r - 1)^2] \sum_{m=0}^N (1 - e^{-Ct/r^m}) \\ &= \lim_{\substack{r^N \rightarrow \infty \\ N \rightarrow \infty, r \rightarrow 1}} (r - 1) \sum_{m=0}^N (1 - e^{-Ct/r^m}). \end{aligned}$$

This relation, with the help of Equation (30), proves the theorem.

The loss tangent of the discrete modified Kuhn model will be derived with the help of the relation (27). By applying the relation (24) to Equation (29), we obtain

$$\zeta(t) = A\delta(t) + BC \ln r \sum_{m=0}^N \frac{1}{r^m} e^{-Ct/r^m} H(t),$$

so that the complex compliance is

$$\begin{aligned} \hat{\zeta}(\omega) &= A + BC \ln r \sum_{m=0}^N \frac{1}{r^m} \mathcal{F}\{e^{-Ct/r^m}\} \\ &= A + BC \ln r \sum_{m=0}^N \frac{1}{r^m} \frac{(C/r^m) - i\omega}{\omega^2 + (C/r^2)^2} \\ &= A + BC \ln r \sum_{m=0}^N \left( \frac{C}{C^2 + \omega^2 r^{2m}} - i \frac{\omega r^m}{C^2 + \omega^2 r^{2m}} \right). \end{aligned}$$

Consequently the loss tangent is given by

$$\begin{aligned}
 \tan \delta = \frac{\hat{\zeta}_2(\omega)}{\hat{\zeta}_1(\omega)} &= \frac{\sum_{m=0}^N \frac{\omega r^m}{C^2 + \omega^2 r^{2m}}}{\frac{A}{BC \ln r} + \sum_{m=0}^N \frac{C}{C^2 + \omega^2 r^{2m}}} \\
 &= \frac{\sum_{m=0}^N \frac{\omega r^m / C}{1 + \omega^2 r^{2m} / C^2}}{\frac{A}{B \ln r} + \sum_{m=0}^N \frac{1}{1 + \omega^2 r^{2m} / C^2}} \\
 &= \frac{\sum_{m=0}^N \frac{q r^m}{1 + q^2 r^{2m}}}{\frac{1}{\beta \ln r} + \sum_{m=0}^N \frac{1}{1 + q^2 r^{2m}}},
 \end{aligned}$$

where  $\beta = B/A$  and  $q = \omega/C$  as before. Plots of the creep function and of the loss tangent, shown in Figures 5 and 6, respectively, confirm the convergence to the continuous modified Kuhn model with increasing  $N$ ; in the range shown, the curves corresponding to  $N \geq 100$  are virtually indistinguishable from those for the continuous model.

An important feature of the discrete model is the fact that it is an internal-variable model. For any stress history  $\sigma(t)$  such that  $\sigma(-\infty) = 0$ , the strain  $\varepsilon(t)$  may be written as

$$\begin{aligned}
 \varepsilon(t) &= \int_{-\infty}^t J_N(t-t') d\sigma(t') \\
 &= \varepsilon^e(t) + \sum_{m=0}^N \alpha_m(t),
 \end{aligned}$$

where

$$\varepsilon^e(t) = A\sigma, \quad \alpha_m(t) = B \ln r \int_{-\infty}^t \left(1 - e^{-C(t-t')/r^m}\right) d\sigma(t').$$



It can easily be seen that each  $\alpha_m(t)$  obeys the rate equation

$$\dot{\alpha} + \frac{C}{r^m} \alpha = \frac{BC \ln r}{r^m} \sigma$$

corresponding to the Kelvin model. The discrete model can be extended into the nonlinear range by replacing the right-hand side of the rate equation with a nonlinear function of  $\sigma$ ; for example, the factor  $\sigma$  can be replaced, in accordance with rate-process theory, by  $D \sinh(\sigma/D)$ , where  $D$  is a constant.

## References

- Christensen, R.M. [1982], *Theory of Viscoelasticity: An Introduction*, Academic Press
- Bataille, J., and J. Kestin [1975], L'interprétation physique de la thermodynamique rationnelle, *J. Méc.*, **14**, 365–384
- Coleman, B.D., and M.E. Gurtin [1967], Thermodynamics with internal state variables, *J. Chem. Phys.*, **47**, 597–613
- DiBenedetto, A.T. [1967], *The Structure and Properties of Materials*, McGraw-Hill
- Flügge, W. [1975], *Viscoelasticity*, Springer-Verlag (Berlin–New York)
- Germain, P., Q.S. Nguyen, and P. Suquet [1983], Continuum thermodynamics, *J. Appl. Mech.*, **50**, 1010–1020
- Golden, J.M., and G.A.C. Graham [1988], *Boundary-Value Problems in Linear Viscoelasticity*, Springer-Verlag (Berlin–New York)
- Greenberg, M.D. [1978], *Foundations of Applied Mathematics*, Prentice-Hall
- Kelly, J.M. [1991], *Dynamic and Failure Characteristics of Bridgestone Isolation Bearings*, Report No. UCB/EERC-91/04, Earthquake Engineering Research Center, University of California at Berkeley
- Kuhn, W., O. Kunzle, and A. Preissmann [1947], Relaxationszeitspektrum, Elastizität und Viskosität von Kautschuk, *Helv. Chim. Acta*, **30**, 307–328 and 464–486
- Lemaitre, J., and J.-L. Chaboche [1990], *Mechanics of Solid Materials*, Cambridge University Press
- Lubliner, J. [1972], On the thermodynamic foundations of nonlinear solid mechanics, *Int. J. Nonlin. Mech.*, **7**, 237–254
- Lubliner, J. [1990], *Plasticity Theory*, Macmillan

Marsden, J.E., and M.J. Hoffman [1987], *Basic Complex Analysis*, 2nd ed., W.H. Freeman (New York)

Nashif, A.D., D.I.G. Jones and J.P. Henderson [1985], *Vibration Damping*, John Wiley & Sons

Phillips, P. [1905], The slow stretch in indiarubber, glass and metal wires when subjected to a constant pull, *Phil. Mag.*, Ser. 6, **9**, 513-531

Truesdell, C. [1984], *Rational Thermodynamics*, 2nd ed., Springer-Verlag (New York)

Tschoegl, N.W. [1989], *The Phenomenological Theory of Viscoelastic Behavior: An Introduction*, Springer-Verlag (Berlin-New York)

U.S. Bureau of Reclamation [1956], *Creep of concrete under high intensity loading*, Concrete Laboratory Report No. C-820, Denver, Colorado

Van Vlack, L.H. [1989], *Elements of Materials Science and Engineering*, 6th ed., Addison-Wesley

Woods, L.C. [1981], On the local form of the second law of thermodynamics in continuum mechanics, *Q. Appl. Math.*, **39**, 119-126; The bogus axioms of continuum mechanics, *Bull. Inst. Math. Applns.*, **17**, 98-103

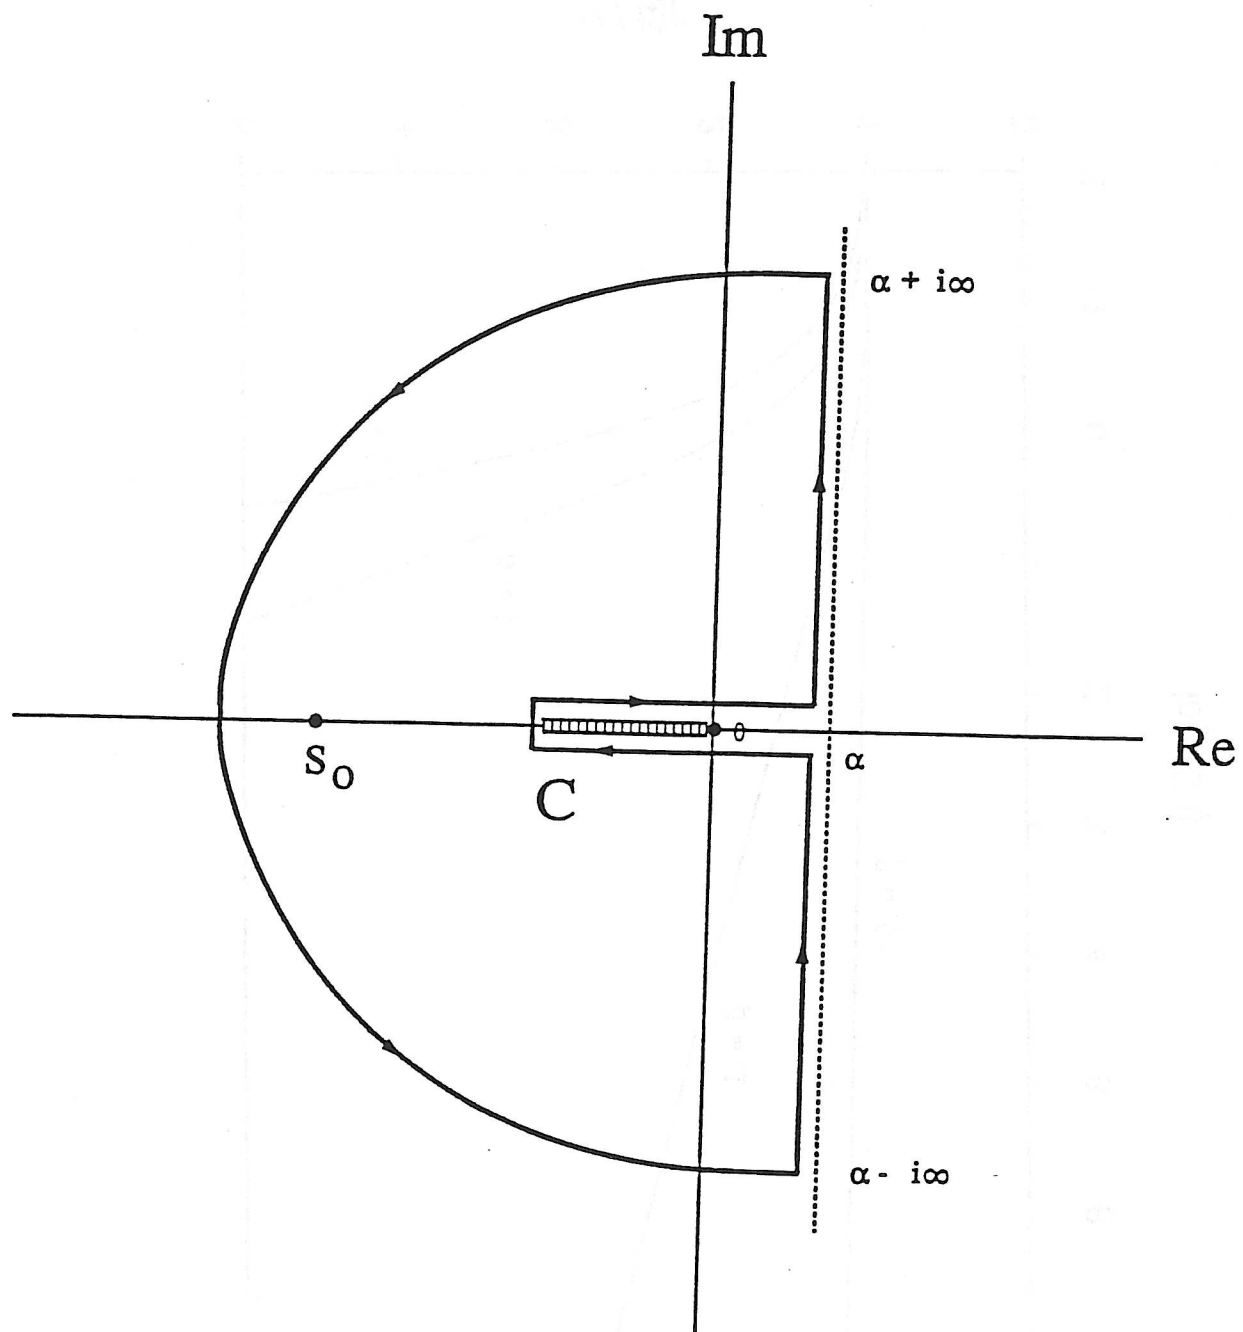


Figure 1: Singularities of  $\bar{G}(s)$

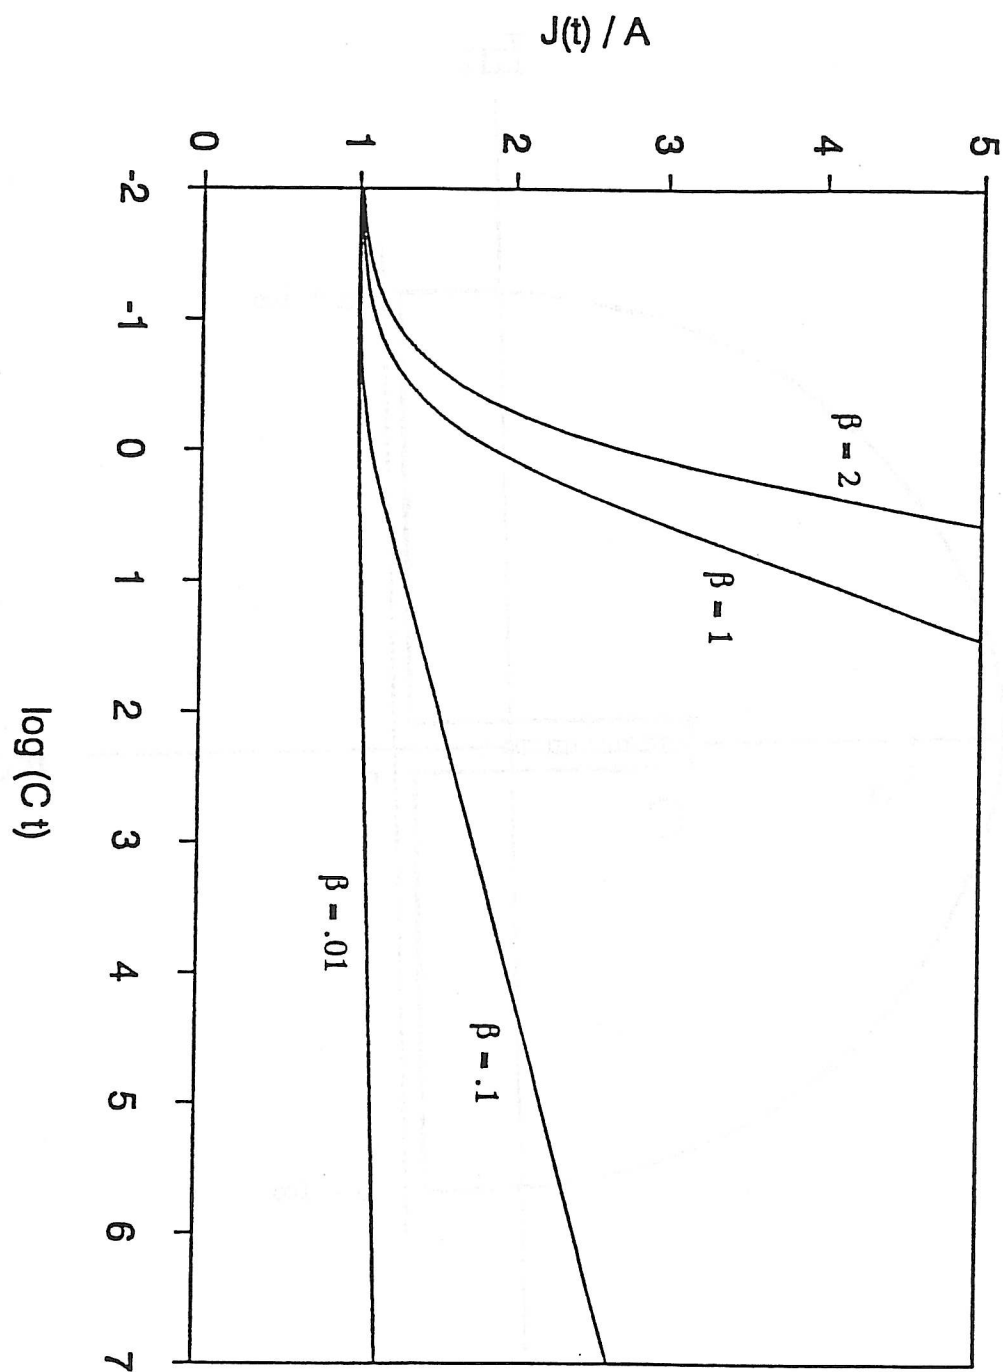


Figure 2: Continuous modified Kuhn model: creep function for various values of  $\beta$

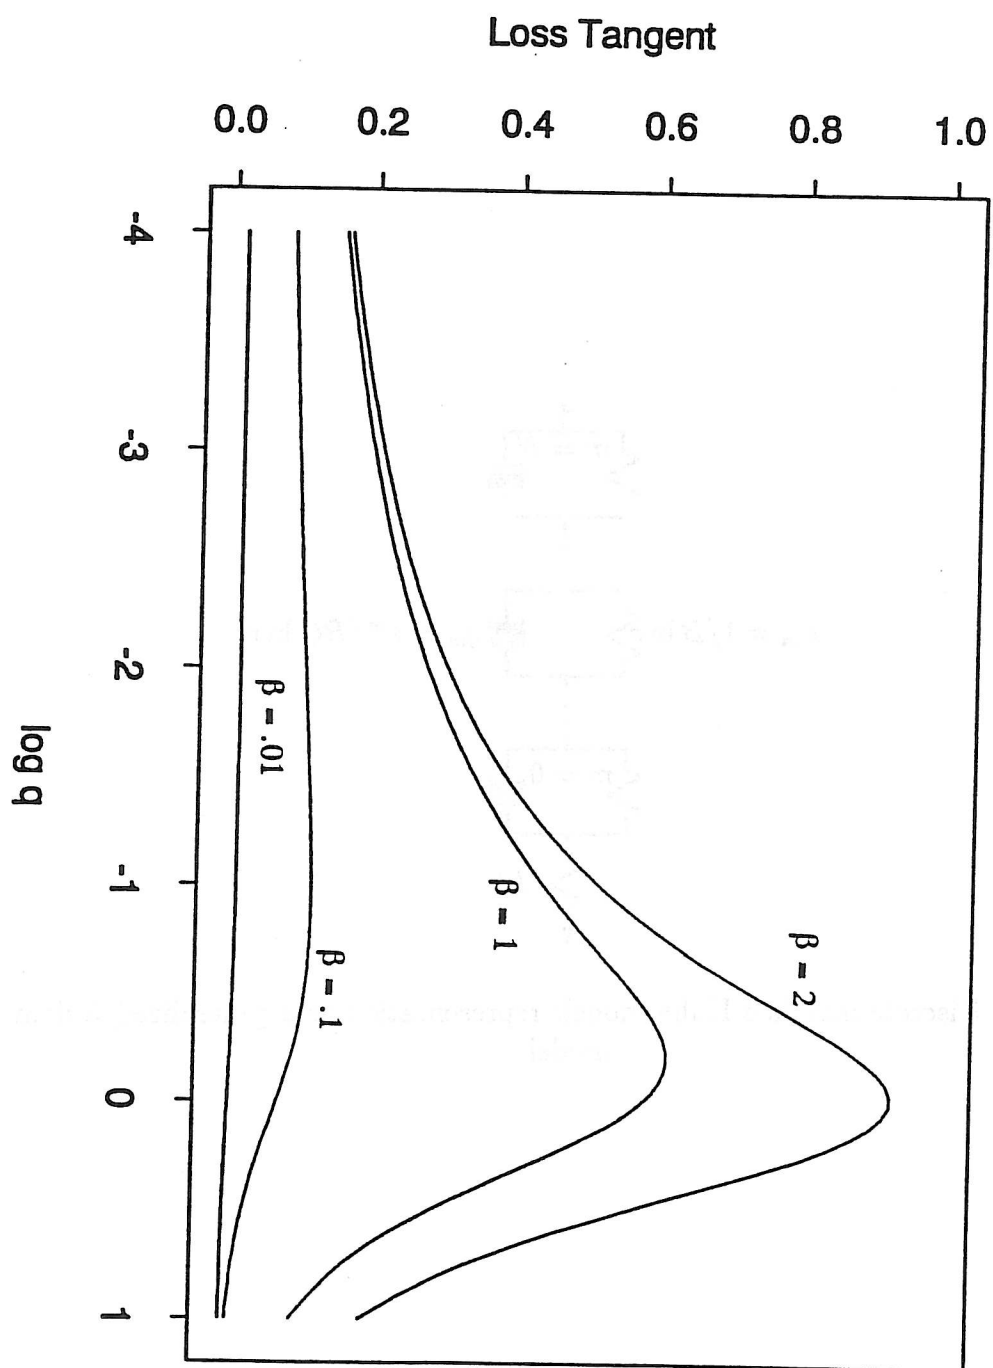


Figure 3: Continuous modified Kuhn model: frequency dependence of loss tangent for various values of  $\beta$

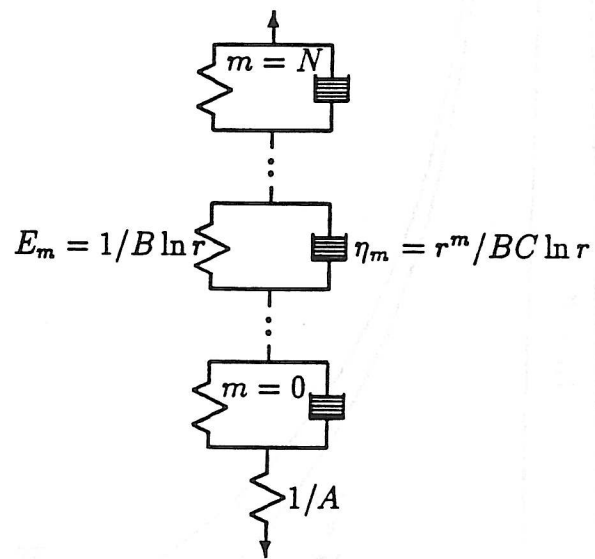


Figure 4: Discrete modified Kuhn model: representation as a generalized Kelvin model

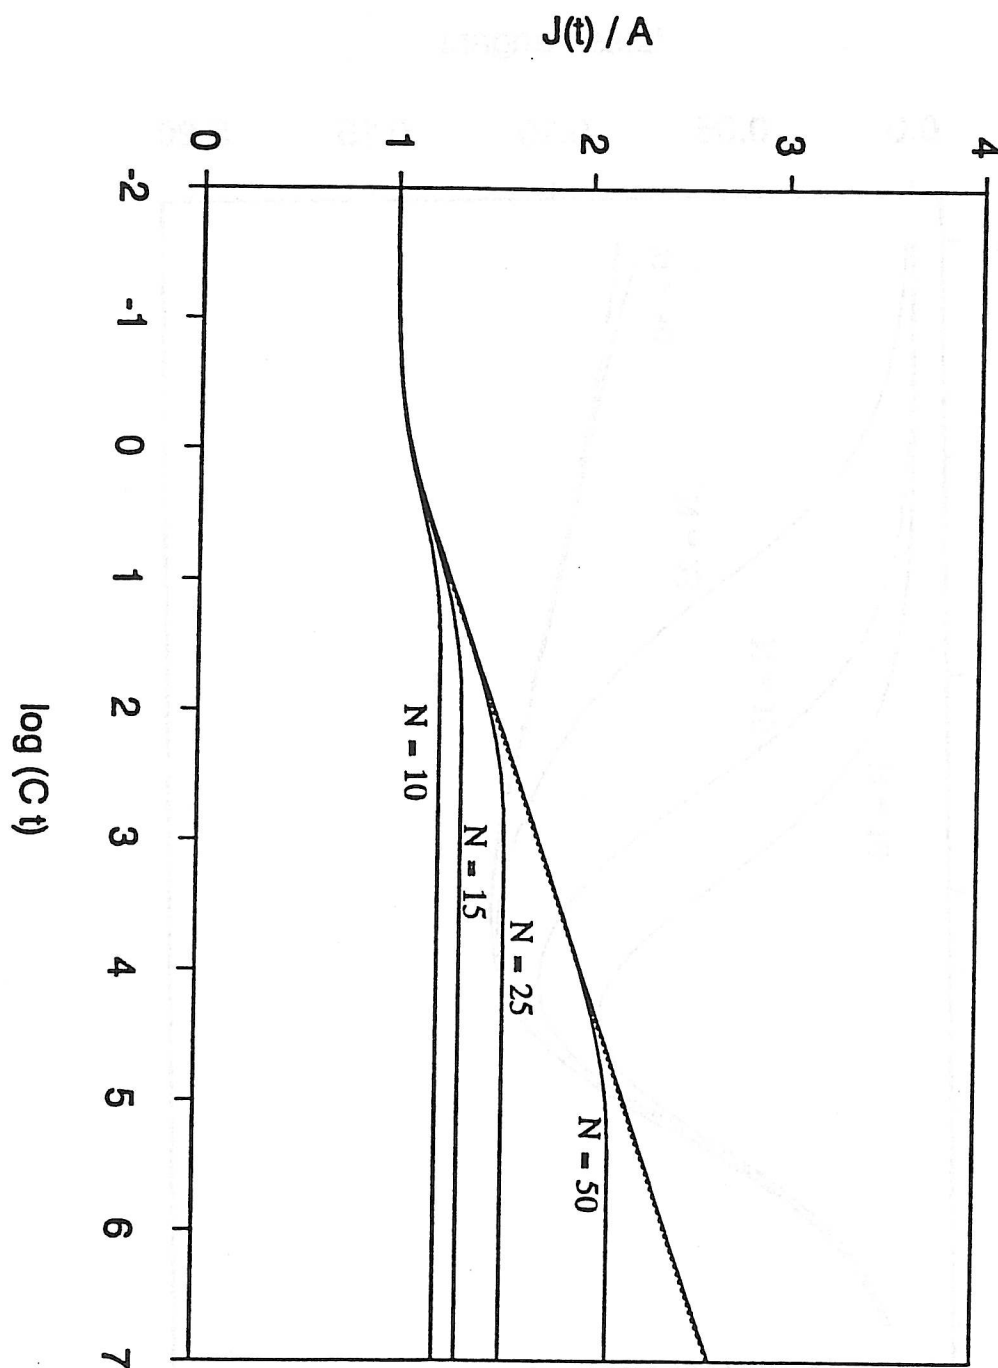


Figure 5: Discrete modified Kuhn model: creep function for various values of  $N$ ;  
 $\beta = 0.1$ ,  $r = 1.25$  (dotted line: continuous model)



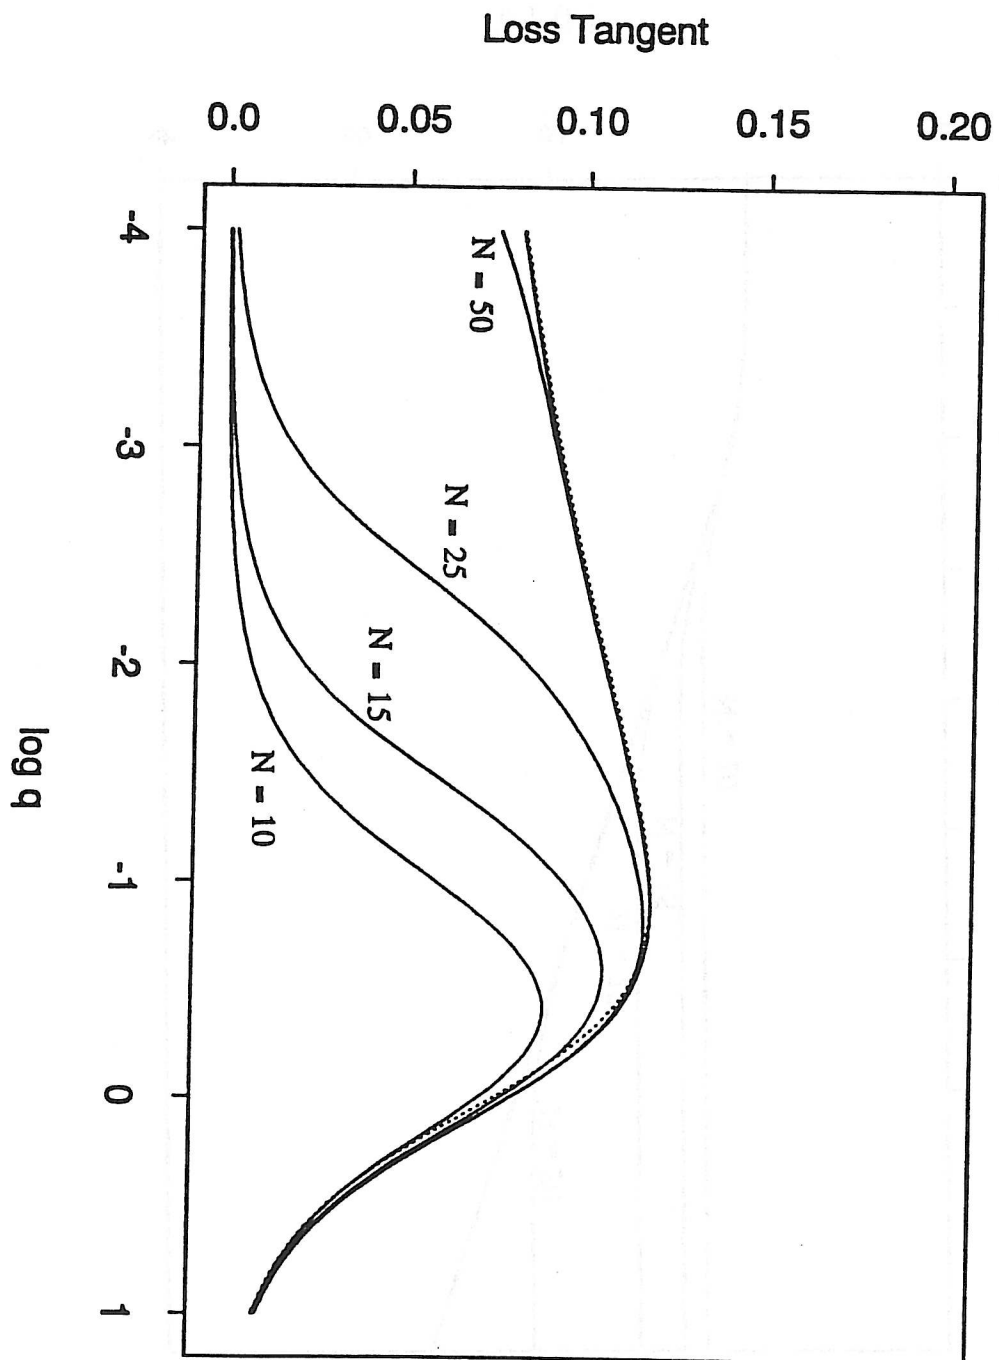


Figure 6: Discrete modified Kuhn model: frequency dependence of loss tangent for various values of  $N$ ;  $\beta = 0.1$ ,  $r = 1.25$  (dotted line: continuous model)