

# UCLA

## UCLA Previously Published Works

### Title

Bubble Transport in Three-Dimensional Gravity Driven Flow, Part I. Mathematical Formulation

### Permalink

<https://escholarship.org/uc/item/9r04z57r>

### Journal

Journal of Non-Crystalline Solids, 336(2)

### Authors

Pilon, Laurent  
Fedorov, Andrei G.  
Ramkrishna, D  
et al.

### Publication Date

2004

Peer reviewed

# Bubble Transport in Three-Dimensional Laminar Gravity Driven Flow - Mathematical Formulation

Laurent Pilon<sup>1</sup>, Andrei G. Fedorov<sup>2</sup>,  
D. Ramkrishna<sup>3</sup>, and Raymond Viskanta<sup>4</sup>

<sup>1</sup> Mechanical and Aerospace Engineering Department  
University of California, Los Angeles - Los Angeles, CA 90095, USA  
Phone: +1 (310)-206-5598, Fax: +1 (310)-206-4830  
E-mail: pilon@seas.ucla.edu

<sup>2</sup> Georgia Institute of Technology  
G.W. Woodruff School of Mechanical Engineering  
Atlanta, GA 30332-0405, USA

Purdue University - West Lafayette, IN 47907, USA

<sup>3</sup> School of Chemical Engineering

<sup>4</sup> School of Mechanical Engineering

September 16, 2003

# ABSTRACT

This paper presents a complete set of coupled equations that govern the bubble transport in three-dimensional gravity driven flow. The model accounts for bubbles growth or shrinkage due to pressure and temperature changes as well as for multiple gas diffusion in and out of the bubbles but neglects bubble coalescence, break-up, and nucleation. The model applies to glass melting furnaces but it could be extended to other two-phase flow applications such as metal and polymer processings, passive cooling systems, and two-phase flow around naval surface ship. Governing equations are given for the key variables which are, in the present case, (1) the refining agent concentration, (2) the gas species dissolved in the liquid phase, and (3) the bubble radius, gas molar fraction, and density function. The method of solution is discussed and based on the modified method of characteristics.

**Keywords:** soda-lime silicate glass, population balance theory, glass properties, refining, bubbles, seeds

# NOMENCLATURE

$A$	Frequency factor in Arrhenius equation
$C$	Mass concentration
$D$	Diffusion coefficient
$D_{eff} _f$	Effective diffusion coefficient of the foam layer
$E$	Activation energy
$f$	Fugacity
$f_1$	Bubble density function
$g$	Specific gravity
$h$	Bubble generation rate per unit volume in the state space
$H_\infty$	Steady-state foam thickness
$\vec{i}, \vec{j}, \vec{k}$	Unit vectors in the physical space
$j, k$	Oxidation indices of the refining agent
$j(x, y)$	Superficial gas velocity at the glassmelt surface
$k_r$	Refining reaction rate constant
$K$	Mass transfer coefficient
$l$	Number of gas species diffusing into and out of the bubbles
$\dot{m}$	Mass flux
$M$	Refining agent ion
$M_i$	Molecular mass of gas species “i”
$\bar{M}$	Mean molecular mass
$p$	Pressure
$p_i$	Partial pressure of gas species “i”
$q$	Order of the refining reaction
$r$	Bubble radius
$R$	Universal gas constant = $8.314J/molK$
$S$	Solubility of the gas species in the molten glass
$T$	Temperature
$t$	Time

$u$	Projection of the velocity vector on the x-axis
$v$	Projection of the velocity vector on the y-axis
$V$	Volume
$\vec{v}$	Velocity vector
$w$	Projection of the velocity vector on the z-axis
$w_r$	Vertical upward velocity of the bubble relative to the glassmelt
$\vec{x}$	Spatial or external coordinates
$x$	Longitudinal location (see Figure 1)
$y$	Spanwise location (see Figure 1)
$z$	Local depth within the glassmelt (see Figure 1)

### Greek symbols

$\alpha$	Parameter [Equation (20)]
$\gamma_i$	Molar fraction of gas species "i" inside the bubble
$\sigma$	Surface tension
$\rho$	Density
$\mu$	Kinematic viscosity

### Subscripts

$b$	Refers to the bubbles
$batch$	Refers to the batch
$comb$	Refers to the combustion space
$diff$	Refers to gas diffusion from the the glassmelt to the gas bubbles
$e$	Equilibrium property at the bubble/glassmelt interface
$i$	Index of the gas species
$int$	Refers to the surface of the glassmelt
$M$	Refers to the refining agent
$n$	Index of the bubble group
$O_2$	Refers to the oxygen
$ref$	Refers to refining reaction
$\infty$	Refers to the bulk of the glassmelt

### Notation

$[X]$  Molar concentration of species X in the glassmelt  
 $\dot{X}$  Derivative of property X with respect to time

# 1 Introduction

The quality of glass products is degraded if gas bubbles and unfused silica grains remain in the molten glass as it is being pulled from of the furnace [1, 2]. Fewer defects, especially fewer remaining bubbles, has become a major requirement in the new quality standards for many commercial glass products. For example, in the TV-glass production, a presence of six bubbles per ton of glass results in 10% rejection rate of the final product, and for new products such as High Definition Television, the quality requirements are even more stringent [3]. For automotive window glass, the most demanding specification requires that gas bubbles be less than 0.5 mm in diameter for transparency purposes [4]. Moreover, for automobile windshield glass, reducing by half the defect density would increase the profitability by more than 2 millions dollars per year per plant [4].



Radiation transfer is main mode of heat transfer in glass melting furnaces. As shown by Pilon and co-workers [5–7] even a small number of entrapped bubbles can affect the radiation characteristics of semitransparent media provided that the bubble radius is much larger than the wavelength of radiation and that the medium is weakly absorbing. Moreover, these bubbles may accumulate or rise to the free liquid surface and form a foam layer which has significant negative effects on the energy efficiency, the glass quality, the productivity, the pollutant emissions, and the furnace integrity [8].

The goal of the present work is to develop a general model for bubble transport, growth and shrinkage in three-dimensional flows. The flow is assumed to be laminar for the sake of simplicity. The bubbles can grow or shrink due to diffusion of gases in and out of the bubbles. The analysis presented is as general as possible and can find applications in many materials processing situations for at least one of the following reasons: (1) for predicting the radiation transfer in liquid containing bubbles, (2) for predicting the foam formation, and/or (3) for improving the quality of manufactured products. Applications to glass melting furnaces appear to be the most natural one since glass is one of the most common and available semitransparent media that is weakly absorbing in the infrared spectral region from 0.2 to 4.5  $\mu\text{m}$  [9, 10]. Moreover, radiation transfer is main mode of heat transfer in glass melting furnaces, and the quality of glass products is degraded if gas bubbles and unfused silica

grains remain in the molten glass as it is being pulled from of the furnace [1,2].

## 1.1 General Description of The Glass Melting Process

Figure 1 shows a schematic of a typical glass melting furnace. During the glass making process, the glass batch is introduced in the glass melting furnace where it spreads due to convection currents in the molten glass and melts due to the heating from the flames in the combustion space and/or from Joule heating in electric melters. Melting of raw batch materials is a complex physicochemical process which involves a large number of chemical reactions and phase transformations occurring over the wide temperature range from 800 to 1200°C [11]. For example, in the typical container glass manufacturing the basic and most important reaction in the batch involve silica, sodium carbonate, and calcium carbonate [12],



Carbon dioxide gas is produced as a result of the last three reactions and it mainly diffuses in the melt [1]. A small fraction of the gas contributes to heterogeneous nucleation of bubbles within or just below the batch. Some of these bubbles pass through the batch and reach the combustion space, while the others are trapped in the melt and are carried with the convection currents in the glass bath. Refining agents, which are involved in the equilibrium redox reactions producing or consuming gases, are usually added to the batch in order to remove undesirable bubbles from the glassmelt [1, 13, 14]. Three types of refining agents are commonly used [15]:

1. Variable-valence metal oxides which release only oxygen, e.g., the antimony oxide ( $\text{Sb}_2\text{O}_5/\text{Sb}_2\text{O}_3$ ), the arsenic oxide ( $\text{As}_2\text{O}_5/\text{As}_2\text{O}_3$ ), and the cesium oxide ( $\text{CeO}_3/\text{CeO}_2$ ) [14, 16–19].



2. Sulphates and sulphites which release a mixture of sulfure dioxide ( $\text{SO}_2$ ) and oxygen [19]. For example, sodium sulfate, ( $\text{Na}_2\text{SO}_4$ ) is used as a refining agent at high temperatures (around  $1800^\circ\text{C}$ ) but it also accelerates the melt formation if introduced in suitable proportions [20]. However, a detailed explanation of the beneficial effects of sulphate is not yet available.
3. Chlorides, bromides, and iodines which evaporate at refining temperature [15].

The fusion of raw materials in the batch and the fining reactions taking place in the glassmelt generate a large number of gas bubbles. A fraction of these bubbles is entrapped on the free surface of the glass to produce the primary foam [12]. Resorption of the remaining small fining gas bubbles, taking place during the conditioning of the glassmelt as it flows from the hot spot in the middle towards the throat of the furnace, also leads to formation of the so-called secondary foam [12]. Visual observations and laboratory scale studies of furnace operations indicate that the foam layers of various thickness can cover a large fraction of the free surface of the molten glass [12, 21].

## 1.2 Literature Review

Previous studies of the bubble behavior in glassmelt were mainly concerned with individual bubbles in an infinitely large quiescent pool of molten glass at a uniform temperature. The simplest of such studies consists of studying the shrinkage or growth of a stationary bubble containing a single gas [22, 23] sometimes accounting for refining reactions [16, 17]. Other studies were concerned with a stationary bubble containing several gases with or without refining reactions [17, 24, 25]. More realistic situations were investigated by accounting for the bubble rise due to buoyancy for a single gas bubble [2, 26] or a bubble containing several gases [27, 28], including the presence of refining reactions [14, 15, 18]. All of these studies show that in the presence of refining agents, only two mechanisms are mainly responsible for the removal of gas bubbles from the melt. They are:

- First, in high temperature regions, the equilibrium of the refining reaction shifts to gas production [1]. Then, the fining gas produced diffuses from the molten glass into

already existing gas bubbles. In addition, gases already contained in bubbles are being diluted by the incoming fining gas [1,29], and, in turn, this enhances the diffusion of gases from the melt into the growing bubbles. Diffusion of fining gases makes bubbles grow in size until the buoyancy force is large enough to enable them to rise to the glassmelt free surface.

- Second, at low temperatures, the equilibrium of the fining reaction shifts to gas consumption resulting in gas diffusion from the bubbles to the melt. Small bubbles, which did not yet grow to a sufficiently large size, then dissolve in the glassmelt [19]. However, recent studies [30,31] demonstrate that the refining reaction involving antimony oxide in TV panel glass was complete and irreversible, i.e., bubble shrinkage due to gas consumption at low temperatures was not clearly evident.

Even though modeling the behavior of individual bubbles gives an insight into the mechanism of bubble generation, growth, and shrinkage, it does not lead to any conclusions about the overall performance of the refining process. To accomplish the latter objective, one approach is to trace bubbles as they grow and shrink while being transported in the glass bath through regions of different temperatures, gas concentrations and pressures [1,13,29,30]. In this approach, bubbles are introduced at the batch/glassmelt interface and are followed individually. All the studies reported [1,13,29,30] assume that probabilistic events such as the bubble coalescence or breakage or bubble nucleation are negligible. Moreover, they neglected the interdependence of gas concentration in the glassmelt and mass transfer in and out of the bubbles thus enabling them to solve successively (1) the glass flow and thermal structure, (2) the gas concentrations dissolved in the glassmelt, and (3) the trajectory and growth or shrinkage of a large number of individual single or multicomponent gas bubbles. The results are analyzed using statistical methods [1] in order to assess the degassing efficiency of a new tank design or new process conditions. The tracing method is a useful technique to elucidate the bubble trajectories in the molten glass. However, it is tedious to implement and does not provide detailed information about the number of bubbles and their size distribution at any given location throughout the tank. Therefore, the bubble-tracing approach cannot account for the coupling between the concentration of gases dissolved in the molten glass,

the bubble density function, the growth rate, and the glass flow and temperature fields. In addition, it can hardly be used to predict foaming at the surface of the glassmelt.

An alternative approach has been proposed by Urgan *et al.* [32] that consists of solving the conservation equation for the total number of bubbles and taking into account the effect of bubbles on the flow and temperature fields of the molten glass through the reduction of the effective density of the two-phase mixture. However, only monodispersed bubbles with constant radius were considered and refining reactions and bubble growth due to pressure change and gas diffusion were neglected.

In contrast, the population balance theory [33] allows one to predict in detail the radius and gas content of polydispersed bubbles and their density function throughout the glass melter. The only attempts to employ population balance theory to the bubble dynamics in glass tanks are due to Roi *et al.* [34] and Balkanli and Urgan [35]. Roi *et al.* [34] proposed a two-dimensional model for calculating the time dependence of the bubble size distribution assuming that the bubble growth rate is independent of the bubble radius. However, the authors admitted that their model “contains substantial simplifications and cannot be used for the exact quantitative modeling of concrete melting vessels”. Balkanli and Urgan [35] presented a more realistic study based on a discretized formulation of the three-dimensional steady state population balance equation (PBE). However, the practical application of both works appear to be very limited since several highly simplifying assumptions have been made such as: (1) refining reactions are not considered, (2) bubble nucleation in the melt and at the refractory walls is neglected, (3) each gas bubble contains only one diffusing gas, and (4) the governing equations for the gas concentration in the molten glass, the bubble growth rate, and bubble population equation are solved independently, i.e., the coupling between these equations is neglected. Moreover, Balkanli and Urgan [35] solved the discretized form of the bubble population balance equation with a coarse grid in the bubble radius space. The limitations of these approaches have been discussed by Kumar and Ramkrishna [36]. In brief, the discrete formulation lacks of *internal consistency*, i.e., some of the moments of the bubble density function  $f_1$  cannot be predicted accurately [36]. In other words, the calculation is designed for certain selected moments of the bubble density function rather than for an estimate of the bubble density function accurate enough for estimating all moments of the

population [33,37].

The purpose of the present work is to propose a simplified yet realistic analysis of the bubble behavior in glass melting furnaces by using the population balance theory [33]. For the first time, it presents a complete set of coupled conservation equations for i) the refining agent concentration, ii) the concentrations of the gases dissolved in the glassmelt, and iii) the bubble density function along with the associated boundary conditions and the closure laws. The model accounts for the three-dimensional convective transport of refining agent, gases, and bubbles as well as for bubble growth due to multiple gas diffusion and by taking into account bubble nucleation along the refractory walls and refining reactions. Finally, the method of characteristics and the associated numerical scheme used for solving the population balance equation in terms of the bubble density function  $f_1$  are briefly described.

## 2 Physical Model

The present analysis simplifies the mathematical formulation by decoupling the liquid and gas phase equations, i.e., the conservation equations for the liquid and gas phases are solved independently and the momentum and energy equation are solved only for the liquid phase assuming that no bubbles are present. Moreover, unlike previous studies [32,35,38] the study predicts the bubble density function  $f_1$  of polydispersed bubbles and enables the accurate post-processing calculation of all the moments of the distribution.

### 2.1 Assumptions

In order to make the problem of bubble generation and transport in the glass melting tank mathematically tractable the following assumptions are made:

1. All the processes are steady state or time independent.
2. The effects of bubbles and dissolved gases on the velocity and on the temperature fields as well as on the thermophysical properties of the glassmelt are not considered.
3. Bubbles are perfectly spherical in shape. This assumption holds for air-molten glass flows at the pressures encountered in the glass melting tank.


4. The bubbles have negligible inertia ( $\rho_b \ll \rho_\infty$ ). This hypothesis is reasonable since very small bubbles are present in the glass bath.
5. The components of the bubble velocity vector, are taken to be the same as those of the molten glass ( $u_\infty, v_\infty, w_\infty$ ), except in the vertical direction where the buoyancy force has to be taken into account. In other words, the slip between the bubble and the glassmelt velocity is neglected except in the vertical direction. This can be justified by the fact that bubble are assumed to be small.
6. The molten glass is considered to be incompressible.
7. Local thermal equilibrium exists between the gas and liquid phases, i.e.,  $T_\infty = T_b = T$ .
8. Coalescence and break up of bubbles are not considered.
9. The gases in a bubble are perfectly mixed, and the gas mixture inside the bubbles behave as an ideal gas.
10. The bubbles are assumed to contain  $l$  different gas species.
11. The diffusing gas species “i” is weakly soluble in the condensed phase (i.e., the Henry’s law is applicable at the bubble/glassmelt interface).
12. The pressure in the bubbles remains close to the atmospheric pressure (maximum 5 atm [39]) so that the ideal gas approximation for fugacity is valid.
13. The diffusing gases neither react with the condensed phase nor undergo dissociation or association.
14. Neither chemical reactions between gases inside a bubble nor dissociation of gas molecules are taken into account.
15. The equilibration kinetics at the bubble surface is assumed to be very rapid, so that the rate limiting process is diffusion of gases in the melt.
16. The analysis presented is restricted to fining reactions that involve variable-valence metal oxides and produce oxygen only (in particular, the antimony oxide  $\text{Sb}_2\text{O}_5$ ).

The above assumptions are commonly used in the treatment of bubble transport in three-dimensional laminar gravity driven flow of molten glass [13, 29–31, 35]. Assumptions regarding the bubble velocity and neglect of the effects of bubbles on the liquid phase flow and temperature fields are the most severe one and their limitations will be discussed later. They have been used to decouple the conservation, momentum, and energy equations of the liquid and gas phases. This approach can be justified by the facts that bubble radius and concentration are small and that the alternative approach solving the coupled governing equations using the two-fluid model lacks mechanistic closure laws accounting, for example, for the interfacial momentum transfer [40]. Moreover, the effect of bubbles on the thermophysical properties of the glassmelt such as the dynamic viscosity, the thermal conductivity, and the specific heat are not clearly known. This is particularly true for the effect of bubbles on the radiation characteristics of molten glass that have been addressed in Ref. [5–7].

## 2.2 Refining Agent Concentration in the Glassmelt

### 2.2.1 Refining Reaction

As mentioned in the Introduction, the refining agent is introduced into the melting tank as part of the batch. As the agent is carried by the flow of the molten glass and encounters high temperature regions, the following reversible chemical reaction for variable-valence metal oxides, written in a generalized form, takes place [41]:



In the case of antimony oxide as a refining agent, Kawachi and Kawase [13, 30] and Kawachi and Kato [31] showed that the rate of the forward reaction can be neglected in the production of TV panel glass. Therefore, the refining reaction can be considered as irreversible with only the decomposition of the refining agent taking place. By assuming a constant oxygen ion activity and by defining  $q$  as the order of the refining reaction occurring at constant volume, the rate of the decomposition reaction can be expressed as [13, 31]

$$-\frac{\partial[M^{k+}]}{\partial t} = \left(\frac{k-j}{4}\right) \frac{\partial[O_2]}{\partial t} = k_r[M^{k+}]^q \quad (6)$$

where the reaction rate constant  $k_r$  is calculated from the Arrhenius' law [30,31],

$$k_r = A \exp\left(-\frac{E}{RT}\right) \quad (7)$$

The pre-exponential parameter  $A$  and the activation energy  $E$  are constants determined experimentally.

### 2.2.2 Fining Agent Concentration

As follows from Equation (6), the oxygen generation rate depends on the concentration of the dissociated form of the refining agent  $M^{k+}$ . Therefore, the local refining agent concentration  $[M^{k+}]$  is required in order to predict the transport of oxygen dissolved in the glass bath as well as the bubble generation rate. The species conservation equation for the refining agent in the glassmelt is given by

$$\frac{\partial[M^{k+}]}{\partial t} + \nabla \cdot (\vec{v}_\infty[M^{k+}]) = \nabla \cdot (D_M \nabla[M^{k+}]) - k_r[M^{k+}]^q \quad (8)$$

where  $[M^{k+}]$  is the molar concentration of metal ions and  $\vec{v}_\infty$  is the local glassmelt velocity vector. The first term on the right hand side of Equation (8) accounts for the metal ion diffusion through the melt, while the last term represents the mass sink due to consumption of ions  $M^{k+}$  by the refining reaction. Although the steady-state solution of the problem is sought, the transient term  $(\partial[M^{k+}]/\partial t)$  has been retained for performing iterative numerical integration which results in the steady-state solution of the molar concentration  $[M^{k+}]$ .

### 2.2.3 Boundary Conditions

Equation (8) can be solved provided that boundary conditions are defined. The batch consists of the raw materials and cullet mixed with the refining agent in the form of oxides such as  $Sb_2O_5$ . The dissociation of the oxide occurs as the temperature increases leading to production of cations and anions such as  $M^{k+}$  and  $O^{2-}$ , respectively. Furthermore, assuming that the concentration of the refining agent is uniform within the batch, and the dissociation reaction at the batch/hot molten glass interface is instantaneous, complete, and irreversible, the concentration of the cations  $[M^{k+}]$  should be constant everywhere at the batch/glassmelt interface:

$$[M^{k+}] = \text{constant} \quad \text{at the batch/glassmelt interface} \quad (9)$$

The specific value of  $[M^{k+}]$  depends on the process and the type of glass produced; it can be determined from operating data. Typically, antimony oxide is added in 0.1 to 1.0 wt.% [19].

Finally, the gradient of the concentration  $[M^{k+}]$  is taken to vanish at the glass/refractory walls and at the free surface of the molten glass

$$\nabla_{\vec{n}}[M^{k+}] = \vec{0} \quad \text{at the glassmelt/refractories interface} \quad (10)$$

$$\nabla_{\vec{n}}[M^{k+}] = \vec{0} \quad \text{at the glassmelt/combustion space interface} \quad (11)$$

Such boundary conditions can be justified by the fact that the diffusion of the cations from the glassmelt to the refractory walls and to the combustion space is negligible.

## 2.3 Dissolved Gas Transport in the Glassmelt

The growth and shrinkage of the bubbles is, in part, caused by gas diffusion into and out of the bubbles due to a difference in concentration of a given gas species between the glassmelt and the gas bubbles. Therefore, one needs to predict the local concentration of each gas species dissolved in the glassmelt.

### 2.3.1 Species Concentration Equation

The transport of major gas species ( $O_2$ ,  $H_2O$ ,  $CO_2$ , and  $N_2$ ) in the glassmelt is governed by the following general species concentration equation [13, 42, 43],

$$\frac{\partial C_{\infty,i}}{\partial t} + \nabla \cdot (\vec{v}_{\infty} C_{\infty,i}) = \nabla \cdot (D_i \nabla C_{\infty,i}) + \dot{m}_{ref,i} - \dot{m}_{diff,i} \quad (12)$$

Here,  $C_{\infty,i}$  and  $D_i$  are the mass concentration and the diffusion coefficient of the dissolved gas species “i” in the glassmelt, respectively. The first term on the right hand side of Equation (12) accounts for mass diffusion of the dissolved gas species “i” in the glassmelt. The source term  $\dot{m}_{ref,i}$  is the volumetric gas production rate due to the refining reaction, and the sink term  $\dot{m}_{diff,i}$  accounts for the volumetric diffusion rate of gas species “i” from the glassmelt into the bubbles. As before, the transient term  $[\partial C_{\infty,i}/\partial t]$  has been retained to enable iterative numerical integration of Equation (12). Note that the last two terms on the right-hand side of Equation (12) have been neglected by Balkanli and Ungan [42], while



Kawachi and Kawase [13] neglected only the last term.

As stated in assumption 2, the analysis presented here is restricted to refining reactions that are complete and irreversible and produce oxygen only. Then, the source term  $\dot{m}_{ref,i}$  vanishes in the case of all gas species but oxygen. Solving Equation (8) for  $[M^{k+}]$  enables one to compute the oxygen generation rate per unit volume of glassmelt at every location in the glassmelt since

$$k_r[M^{k+}]^q = \left(\frac{4}{k-j}\right) \frac{1}{M_{O_2}} \frac{\partial C_{\infty,O_2}}{\partial t} = \left(\frac{4}{k-j}\right) \frac{\dot{m}_{ref,O_2}}{M_{O_2}} \quad (13)$$

After some rearrangement,

$$\dot{m}_{ref,O_2} = \left(\frac{k-j}{4}\right) M_{O_2} k_r [M^{k+}]^q \quad (14)$$

The sink term  $\dot{m}_{diff,i}$  is the total mass of dissolved gas species “i” diffusing from the glassmelt into the bubbles per unit volume of the glassmelt and per unit of time at location  $\vec{x}$  and instant of time  $t$ . It is given by

$$\dot{m}_{diff,i}(\vec{x}, t) = \int_0^1 \dots \int_0^1 \left[ \int_0^\infty K_i(C_{\infty,i} - C_{e,i}) f_1 dr \right] d\gamma_{i,1} \dots d\gamma_{i,l-1} \quad (15)$$

where  $K_i(C_{\infty,i} - C_{e,i})$  is the total mass flow rate of the gas species “i” from the glassmelt across the surface of a bubble of radius  $r$  expressed in [kg/s/bubble]. The concentration difference of gas species “i” between the glassmelt and the bubble/glassmelt interface is  $(C_{\infty,i} - C_{e,i})$ . The bubble density function, i.e., the number of bubbles per unit volume at location  $\vec{x}$  and time  $t$  having equivalent radii that lie within the range  $r$  to  $r + dr$ , and the molar fraction of gas species “i” ranges between  $\gamma_i$  and  $\gamma_i + d\gamma_i$  with  $1 \leq i \leq l-1$  is denoted  $f_1 = f_1[\vec{x}, r, t, (\gamma_i)_{1 \leq i \leq l-1}]$ . Note that all the molar fractions of gas species “i”  $\gamma_i$  sum up to unity. Thus,  $\gamma_l$  can be expressed as a function of the remaining  $(l-1)$  others and cannot be treated as an independent variable. When  $C_{\infty,i} > C_{e,i}$  the gas species “i” diffuses from the glassmelt in the bubbles, whereas when  $C_{\infty,i} < C_{e,i}$  it diffuses from the gas bubbles to the glassmelt. Then,  $\dot{m}_{diff,i}(\vec{x}, t)$  behaves either as a sink (if  $C_{\infty,i} > C_{e,i}$ ) or as a source (if  $C_{\infty,i} < C_{e,i}$ ). To complete the formulation, the closure laws must be specified as well as the boundary conditions.

### 2.3.2 Closure Laws

To make the problem well-posed, the total mass flow of the gas species from the glassmelt to the bubbles and particularly the mass transfer coefficient  $K_i$ , and the gas concentrations at the bubble glassmelt interface,  $C_{e,i}$ , should be defined.

According to Levich [44], for bubbles moving at low relative velocities  $w_r$  (Reynolds number much smaller than unity) in a quiescent liquid containing diffusing gases, the coefficient  $K_i$  can be expressed as

$$K_i = 7.98D_i^{2/3}w_r^{1/3}r^{4/3} \quad (\text{in m}^3/\text{s}) \quad (16)$$

Here,  $D_i$  is the diffusion coefficient of gas species “i” in the glassmelt while  $w_r$  is the relative velocity of the bubble of radius  $r$  with respect to the liquid. Extensive studies have shown that in molten glass small bubbles behave like solid sphere while large spherical bubbles behave like fluid spheres (see Ref. [19] for an in-depth review). According to the Stokes’ law for solid spheres, the small gas bubbles rise in the molten glass with the relative vertical velocity given by:

$$w_r = \frac{2}{9} \frac{\rho_\infty g r^2}{\mu_\infty} \quad (17)$$

On the other hand, in the case of large spherical bubbles in the molten glass, the vertical velocity relative to the molten glass follows the Hadamar-Rybczynski formula [19, 45]:

$$w_r = \frac{1}{3} \frac{\rho_\infty g r^2}{\mu_\infty} \quad (18)$$

Unfortunately, there is no clear criteria regarding what bubbles should be considered as large or small. Experimental results suggested that bubbles of diameter larger than 1 mm can be considered as large and their velocity follows Equation (18) [45]. In brief, the bubble rise velocity with respect to liquid phase can be written as

$$w_r = \alpha \frac{\rho_\infty g r^2}{\mu_\infty} \quad (19)$$

where  $\alpha$  is a parameter that depends on the bubble size according to Equations (17) and (18):

$$\alpha = \begin{cases} 2/9 & \text{for small bubbles } (2r \leq 1\text{mm}) \\ 1/3 & \text{for large bubbles } (2r \geq 1\text{mm}) \end{cases} \quad (20)$$

Note that Equations (17) to (19) correspond to the terminal (i.e., steady state) velocity of spherical bubbles, i.e., the transient motion of bubbles have not been considered for the sake of simplicity and since its formulation is still incomplete and quite involved [46].

In the present analysis, the magnitude of the mass flux is assumed to be relatively small, so that the variations of mass concentration of gas species “i” in both phases are small as well. Then, the local quasi-equilibrium can be assumed to exist at the bubble/molten glass interface [47], which implies the equality of the chemical potentials of the diffusing gas on both sides of the interface. This fact, combined with assumptions 3, 8 and 10, allows us to apply the generalized Henry’s law and obtain the relationship between species concentrations on both sides of the bubble/glassmelt interface [48],

$$C_{e,i} = S_i M_i f_{b,i} \quad (21)$$

Here,  $C_{e,i}$  is the concentration of the diffusing gas “i” at the interface (assumed to be at equilibrium) and  $S_i$  is the solubility of gas species “i” in the glass melt,  $M_i$  is the molecular weight of the species “i”, and  $f_{b,i}$  the fugacity of the species “i” in the bubble. Provided that the pressure is low enough and the ideal gas approximation holds (assumption 9), the fugacity  $f_{b,i}$  is approximately equal to the partial pressure of species “i” ( $p_{b,i}$ ) on the gas side of the interface [39], so that

$$C_{e,i} = S_i M_i p_{b,i} \quad (22)$$

Using an ideal-gas equation of state (assumption 7), the partial pressure of the gas species “i” in the bubble is given by the Raoult’s law:

$$p_{b,i} = \gamma_i p_b \quad (23)$$

where  $\gamma_i$  is the molar fraction of gas species “i” inside the bubble and is such that

$$\sum_{i=1}^l \gamma_i = 1 \quad (24)$$

This results in the following jump condition for the species concentrations at the bubble/glassmelt interface:

$$C_{e,i} = \gamma_i S_i M_i p_b \quad (25)$$

### 2.3.3 Boundary Conditions

According to Balkanli and Ungan [35], the concentration of carbon dioxide ( $\text{CO}_2$ ) at the batch/glassmelt interface can be taken as being the saturation concentration owing to the very high intensity of gas generation due to fusion and melting of the raw batch materials. Also, as speculated by Kawachi and Kawase [13], oxygen ( $\text{O}_2$ ) is supplied in sufficiently large amounts from the combustion space or by refining reactions taking place in the batch to saturate the glassmelt beneath the batch/glassmelt interface; similarly, for nitrogen ( $\text{N}_2$ ) in air fired furnaces. However, transport of nitrogen can be neglected in oxy-fired furnaces since it is present in very small amount.

At the glass/refractory wall interface, the gradient of the concentration of gas species “i” in the glassmelt is assumed to vanish owing to the absence of mass transfer through the refractory walls:

$$\nabla_{\vec{n}} C_{\infty,i} = \vec{0} \quad \text{at the glassmelt/refractories interface} \quad (26)$$

In cases when the free surface of the glassmelt is in direct contact with the combustion gases, the gas concentration at the free surface is given by the Henry’s law [13, 31, 42], i.e.,

$$C_{\infty,i} = S_i M_i p_i|_{int} \quad \text{at the glassmelt/combustion space interface} \quad (27)$$

where  $p_i|_{int}$  is a partial pressure of gas species “i” on the combustion side of the glassmelt/combustion space interface and is obtained from the calculation of the gas species concentrations as well as the flow and temperature fields in the combustion space.

However, if the free surface is covered by a foam blanket then the effect of foam should be accounted for by equating the mass fluxes on both sides of the foam/glassmelt interface, i.e.,

$$D_i(\nabla C_{\infty,i}) = D_{eff}|_{f,i} \nabla(C_{\infty,i}) \quad \text{at the glassmelt/foam interface} \quad (28)$$

where  $D_{eff}|_{f,i}$  is the effective diffusion coefficient of gas species “i” through the foam layer and  $C_i|_{int}$  is the gas concentration at the foam/glassmelt interface. The left-hand side of Equation (28) represents the gas diffusion mass flux on the glass side, while the right-hand side represents that on the foam side. Assuming that the foam thickness is small, a linear

approximation of the gas concentration in the foam layer yields the following mixed boundary condition,

$$D_i \nabla C_{\infty,i} = D_{eff}|_{f,i} \left( \frac{C_i|_{comb} - C_{\infty,i}}{H_\infty} \right) \quad \text{at the glassmelt/foam interface} \quad (29)$$

where  $H_\infty$  is the steady-state foam thickness (see Ref. [49]) and  $C_i|_{comb}$  the gas concentration at the foam/combustion space interface, i.e., at the top of the foam layer. A model for the effective diffusion coefficient of gas species “i” through the foam layer,  $D_{eff}|_{f,i}$  can be found in the literature [50].

## 2.4 Bubble Density Population

### 2.4.1 Single Bubble Environment

A schematic of a single bubble in mechanical and thermal equilibrium with the surrounding molten glass is given in Figure 2, along with the corresponding p-T diagram. The Young-Laplace equation relates the pressure ( $p_b$ ) inside a spherical bubble of radius  $r$  with the pressure ( $p_\infty$ ) in the surrounding glassmelt and the surface tension  $\sigma$  by

$$p_b = p_\infty + \frac{2\sigma}{r} \quad (30)$$

Since the velocity of the viscous molten glass in the glass bath is very small (of the order of 1 cm/s) the pressure field in the tank can be assumed to be purely hydrostatic. Thus, the total pressure inside the bubble is expressed as

$$p_b = p_0 + \rho_\infty g z + \frac{2\sigma}{r} \quad (31)$$

where  $p_0$  is the pressure at the free surface of the molten glass and  $z$  is the local depth within the glassmelt.

Based on Assumption 5, the components of the bubble velocity vector  $\vec{v}_b$  can be expressed as

$$\vec{v}_b(\vec{x}) = u_\infty \vec{i} + v_\infty \vec{j} + (w_\infty - w_r) \vec{k} \quad (32)$$

with  $w_r$  being the upward bubble velocity relative to the molten glass due to the buoyancy force given by Equation (19). Note that according to our convention, the vertical axis is oriented downward. Values of  $u_\infty$ ,  $v_\infty$ , and  $w_\infty$ , are obtained from the thermal-flow computation of molten glass circulation in the bath (see, for example, Ref. [51–55]).

## 2.4.2 Population Balance Equation

As discussed in detail by Ramkrishna [33, 56], the bubble population can be described by a state vector defined in a so-called state space. Each bubble in the glassmelt is characterized by its radius  $r$  and the molar fraction of gas species “i” contained in the bubble  $\gamma_i$ . Let  $f_1[\vec{x}, t, r, (\gamma_i)_{1 \leq i \leq l-1}]$  be the average number density function of bubbles. As already discussed,  $\gamma_l$  cannot be treated as an independent variable. The average number density function  $f_1[\vec{x}, t, r, (\gamma_i)_{1 \leq i \leq l-1}]$  is assumed to be sufficiently smooth to allow differentiation with respect to any of its variables as many times as necessary [33]. Note that the temperature of the bubbles is assumed to be the same as that of the glassmelt, i.e., the local thermal equilibrium prevails. Therefore, although the temperature is important to determining the growth rate of a bubble, it is a continuous phase (glassmelt) variable and hence does not enter the characterization of the bubble state. Considering the bubbles generated and transported by the flow of the glassmelt, and assuming that there are  $l$  gases diffusing into or out of each bubble, the state vector  $\vec{S}$  can be expressed as  $\vec{S} = [x, y, z, t, r, (\gamma_i)_{1 \leq i \leq l-1}]$ . Then, the population balance equation can be expressed as

$$\frac{\partial f_1}{\partial t} + \frac{\partial}{\partial x}(u_\infty f_1) + \frac{\partial}{\partial y}(v_\infty f_1) + \frac{\partial}{\partial z}[(w_\infty - w_r) f_1] + \frac{\partial}{\partial r}(\dot{r} f_1) + \sum_{i=1}^{l-1} \frac{\partial}{\partial \gamma_i}(\dot{\gamma}_i f_1) = h \quad (33)$$

where,  $w_r$  is given by Equation (19). The time rate of change of the bubble radius and of the molar fraction of gas species “i” inside the bubble are denoted by  $\dot{r}$  and  $\dot{\gamma}_i$ , respectively. The transient term  $\partial f_1 / \partial t$  represents the time rate of change of the bubble density, and the other two terms on the left-hand side of Equation (33) represent advection of the bubble density function in the physical space and in the property space, respectively. Finally, the term  $h$  represents the net rate of production of bubbles of a particular state  $(\vec{x}, (\gamma_i)_{1 \leq i \leq l-1})$  at time  $t$ .

The molar fraction of gas species “i” can be expressed as a function of the mass concentrations  $C_{b,i}$  since by definition

$$\gamma_i = \frac{C_{b,i}/M_i}{\sum_{j=1}^l (C_{b,j}/M_j)} = \frac{C_{b,i}RT}{M_i p_b} \quad (34)$$

Then, the time derivative of the molar fraction of gas species “i” in the bubble  $\gamma_i$  can be expressed as

$$\dot{\gamma}_i = \gamma_i \left[ \frac{\dot{C}_{b,i}}{C_{b,i}} - \frac{\rho_\infty g(w_\infty - w_r) - 2\sigma\dot{r}/r^2}{p_b} \right] \quad (35)$$

where  $\dot{r}$  and  $\dot{C}_{b,i}$  are the time rate of change of the bubble radius and of the mass concentration of gas species “i” contained in the bubbles, respectively. Expressions for  $\dot{r}$  and  $\dot{C}_{b,i}$  can be derived from assumptions 8 to 10 by writing the time rate of change of the mass of gas species “i” contained in a spherical bubble of radius  $r$  as [44]

$$\frac{dm_i}{dt} = \frac{d(C_{b,i}V_b)}{dt} = K_i (C_{\infty,i} - \gamma_i S_i M_i p_b) \quad (36)$$

where  $C_{b,i}$  and  $C_{\infty,i}$  are the mass concentrations of gas species “i” in the bubble and in the glassmelt, respectively. Equation (36) indicates that if a bubble contains a single gas, the bubble can only shrink since the concentration of gas dissolved in the glassmelt  $C_{\infty,i}$  (in kg/m<sup>3</sup>) cannot be larger than the gas solubility given by  $S_i M_i (p_0 + \rho_\infty g z)$ . Substituting the expression for  $K_i$  given by Equation (16) and that of  $C_{e,i}$  given by Equation (25) and differentiating the left-hand side of Equation (36) yields

$$\frac{4\pi}{3} r^3 \dot{C}_{b,i} + C_{b,i} 4\pi r^2 \dot{r} = 7.98 (C_{\infty,i} - \gamma_i S_i M_i p_b) D_i^{2/3} w_r^{1/3} r^{4/3} \quad (37)$$

Then, solving for  $\dot{C}_{b,i}$  results in

$$\dot{C}_{b,i} = \frac{1.905}{r} \left( \frac{\alpha \rho_\infty g D_i^2}{\mu_\infty} \right)^{1/3} (C_{\infty,i} - \gamma_i S_i M_i p_b) - \frac{3\dot{r}}{r} C_{b,i} \quad (38)$$

According to the Dalton’s law for ideal gases, the total pressure of the gas mixture in the bubble is given by

$$p_b = \sum_{i=1}^l (p_{b,i}) = \left[ \sum_{i=1}^l \left( \frac{C_{b,i}}{M_i} \right) \right] RT \quad (39)$$

The derivative of Equation (39) with respect to the time  $t$  using the expression for  $\dot{C}_{b,i}$  given by Equation (38) results in

$$\frac{\partial p_b}{\partial t} = \frac{1.905 RT}{r} \left( \frac{\alpha \rho_\infty g}{\mu_\infty} \right)^{1/3} \sum_{i=1}^l \frac{D_i^{2/3}}{M_i} [(C_{\infty,i} - \gamma_i S_i M_i p_b)] - \frac{3\dot{r}}{r} p_b \quad (40)$$

The temperature  $T$  is obtained from the steady-state solution of the thermal-flow calculations of the glassmelt. Substituting the expression for  $p_b$  given by Equation (31) into Equation

(40), assuming that  $\partial p_0/\partial t = 0$  (steady-state), and solving for the growth rate  $\dot{r}$  gives

$$\dot{r} = \frac{0.635RT \left(\frac{\alpha\rho_\infty g}{\mu_\infty}\right)^{1/3} \sum_{i=1}^l \left[ \frac{D_i^{2/3}}{M_i} (C_{\infty,i} - \gamma_i S_i M_i p_b) \right] - \rho_\infty g (w_\infty - w_r) r / 3}{p_0 + \rho_\infty g z + 4\sigma/3r} \quad (41)$$

The first term in the numerator of Equation (41) takes into account the change of radius due to mass transfer at the bubble interface, while the second term accounts for the change in pressure as the bubbles are transported in the glass bath. Such an expression has been previously derived by Balkanli and Ungan [2], but the expression for the term accounting for growth due to the change in pressure appears to be in error as also confirmed by other studies for quiescent glassmelt ( $w_\infty = 0$ ) [14, 28].

Note that the gas and liquid momentum equations have been decoupled and it was assumed that the vertical component of the bubble velocity vector was given by  $w_b = w_\infty - w_r$ . Thus, assumption 5 implies that the bubble velocity field does not satisfy the continuity equation in steady-state, i.e.,  $\nabla \cdot \vec{v}_b \neq 0$  [37]. Therefore, Assumptions 2 and 5 introduce an artificial source in the population balance equation. In order to approximately conserve the total number of bubbles the bubble velocity vector  $\vec{v}_b$  should satisfy

$$\nabla \cdot \vec{v}_b = \vec{v}_\infty - \frac{\partial w_r}{\partial z} \approx 0 \quad (42)$$

Since the molten glass is treated as incompressible, Equation (42) is satisfied if  $\partial w_r/\partial z \ll 1$ . Physically, this corresponds to situation where the bubble growth rate and liquid velocity does not vary significantly along the bubble pathline during the time interval  $t$  and  $t + dt$ .

### 2.4.3 Bubble Generation

Finally, heterogeneous nucleation can occur on the surface of undissolved sand grains or on refractory walls [1]. Nemeč [57] observed in an experimental crucible under uniform temperature conditions that heterogeneous bubble nucleation occurs at the surface of undissolved sand grains only if refining agent is present while homogeneous bubble nucleation could never be observed. It indicates that bubble nucleation takes place if the glassmelt is supersaturated with refining gases, i.e., if the local gas concentration dissolved in the molten glass exceeds the solubility at the local temperature and pressure. Cable and Rasul [58] reported



that heterogeneous bubble nucleation occurred at the surface of the refractory even at small supersaturations. Finally, Roi *et al.* [59] have discussed bubble generation and formation of a bubble curtain consisting of very small bubbles located close to the refractory walls. The authors attributed the formation of a bubble curtain to the combination of an unfavourable temperature distribution and bubble growth rate.

Solving the gas species concentration equation [Equation (12)] for oxygen could possibly yield oxygen concentrations higher than solubility within the glass bath due to the source from the refining reactions. However, such cases are expected only in the refining section of the tank where the number of undissolved sand grains is predicted to be small [60], thus limiting the number of available nucleation sites. Instead, the main mechanism for dissolved oxygen removal from the glassmelt is the diffusion in already existing bubbles to make them grow and rise at the surface. Note also that from a thermodynamics point of view gas diffusion is favored over heterogeneous nucleation. Therefore, given the complexity of the physical phenomena and the controversy regarding the significance and mechanisms of heterogeneous nucleation in glass melting furnaces, heterogeneous nucleation has not been considered in the present study. The validity of this assumption will be examined in view of the numerical results presented in the second part of this document. Moreover, very fine grids close to the walls should be used to account for the entrainment by the flowing liquid of the very small bubbles generated at the refractory walls. Then, the grid size should be smaller than the typical size of a generated bubble making the calculation even more time consuming.

#### 2.4.4 Boundary Conditions

Boundary conditions for the bubble density function  $f_1$  are required to solve the population balance equation (33) and are expressed as follows:

- *At the batch/glassmelt interface* bubbles exist in significant numbers due to the fusion/melting transformations taking place in the batch. The batch coverage is assumed to be known and the gas composition and the bubble density function are the same under the entire surface covered by the batch and does not vary with time. Then, the

boundary condition at the batch/glassmelt interface is expressed as

$$f_1 = f_{1,0} \quad \text{at the glassmelt/batch interface} \quad (43)$$

where  $f_{1,0} = f_{1,0}[r, (\gamma_i)_{1 \geq i \geq l-1}]$  is the bubble density function depending on the fusion/melting process and determined experimentally.

- *At the glassmelt/refractory wall interface* the boundary conditions appear to be controversial. Balkanli and Ungan [35], suggested the use of the weak boundary conditions at the refractory walls. However, Swarts [4] mentioned that the number of bubbles per unit volume generated at the glass/refractory interfaces is significant. Until further experimental results are obtained we will assume that the gradient of  $f_1$  in the normal direction vanishes,

$$\nabla_{\vec{n}} f_1 = \vec{0} \quad \text{at the glassmelt/refractories interface} \quad (44)$$

- *At the free surface of the glassmelt* Balkanli and Ungan [35] used the same boundary condition as that used at the glass/melt/refractory wall interface, i.e.,  $\nabla_{\vec{n}} f_1 = \vec{0}$ . Physically, such a boundary condition means that no bubble can escape through the glassmelt free surface. Obviously, such a boundary condition does not represent the physical phenomena occurring since a single bubble reaching a free interface can either merge with the interface almost instantaneously or bounce back one or several times before stabilizing at the free interface to finally burst [61]. Additional complications appear when bubbles accumulate to form a foam layer at the glassmelt surface. Then, rising bubbles aggregate and coalesce with bubbles in the foams. This phenomena is suspected to be of major importance for onset of foaming. To the best of our knowledge, no boundary conditions for the bubble density function  $f_1$  at the glassmelt free surface and at the glassmelt/foam interface accounting for the physical phenomena described above are available in the literature. Note that the finite difference algorithm needs the definition of these boundary conditions. On the other hand, the method of characteristics used in the present study does not require specification of any boundary condition at the glass/combustion space interface.

The local superficial gas velocity  $j(x, y)$  at the glassmelt surface can be computed from the bubble density function:

$$j(x, y) = \int_0^1 \dots \int_0^1 \left( \int_0^\infty f_1[x, y, z = 0, r, (\gamma_i)_{1 \geq i \geq l-1}] \left( \frac{4\pi r^3}{3} \right) (w_\infty - w_r) dr \right) d\gamma_1 \dots d\gamma_{l-1} \quad (45)$$

Then, the transient and steady-state foam thickness can be predicted from the analysis by Pilon *et al.* [49, 62] for liquid foams generated from viscous liquids. However, the spreading of the foam over the glassmelt surface is not accounted for. The foam layer strongly affects the radiation heat transfer from the combustion space to the glass bath and can significantly reduce the glassmelt temperature [8, 55]. Model for radiation transfer through foam and combined conduction and radiation transfer have been proposed recently [8, 63–66] and should be used to recompute the glassmelt flow and thermal structures. However, this task is beyond the scope of the present work, and the presence of a foam layer will not be considered further.

### 3 Method of Solution of Model Equations

Figure 3 shows the block diagram of essential steps in the procedure which is used to calculate the bubble transport in the glass melting furnace. Previous studies computed the dissolved gas concentration in the melt by neglecting the source term in Equation (12) due to the diffusion of gases in and out of the bubbles [35] and assumed that bubbles contain only one gas species. This simplification reduces the number of independent variables and implies that the dissolved gas concentrations  $C_{\infty, i}$ , the bubble radius  $r$ , and the bubbles density function  $f_1$  can be computed consecutively and independently. In this study, the variables  $C_{\infty, i}$ ,  $r$ ,  $\gamma_i$ , and  $f_1$  are interdependent and determined iteratively until all the solutions are converged as shown in Figure 3. Considering refining reactions that are complete and irreversible enables us to compute the refining agent concentration  $[M^{k+}]$  independently.

The governing conservation equations and boundary conditions for the thermal-fluid calculations of the molten glass along with the numerical method of solution can be found elsewhere [51–54]. The governing partial differential equations for the refining agent concentration  $[M^{k+}]$  and the gas concentrations  $C_{\infty, i}$ , are of parabolic type with the transient term included as an iteration parameter. For the purpose of numerical solution, the equations are discretized over the spatial coordinates by means of the control volume integration

technique [67]. The resulting finite-difference approximation of derivatives produces a system of linear algebraic equations, which are then solved using line-by-line iterative method. The method solves a line of nodes by applying the tri-diagonal matrix inversion algorithm and sweeps the domain of integration in alternating directions along the coordinates axes. A fully implicit and unconditionally stable Euler method with very large time steps is employed to integrate the equations in time until steady-state solution is achieved. Numerical integration of the source/sink terms corresponding to gas diffusion in and out of the bubbles and given by Equation (15) was performed using Simpson's rule for unequally spaced data <sup>1</sup>. The steady-state conditions for the refining agent concentration and the dissolved gas concentrations was assumed to be reached when the residual for each of these variables was less than an arbitrary small value.

The population balance equation [Equation (33)] is solved using the backward (or modified) method of characteristics described by Pilon *et al.*, [37]. In brief, the partial differential equation (33) is transformed into a system of ordinary differential equations by solving it along the characteristic curves in the particle state space defined as

$$\frac{dx}{dt} = u_{\infty}(x, y, z) \quad (46)$$

$$\frac{dy}{dt} = v_{\infty}(x, y, z) \quad (47)$$

$$\frac{dz}{dt} = w_{\infty}(x, y, z) - w_r(x, y, z, r) \quad (48)$$

$$\frac{dr}{dt} = \dot{r}[x, y, z, r, (\gamma_i)_{1 \leq i \leq l-1}, t] \quad (49)$$

$$\frac{d\gamma_i}{dt} = \dot{\gamma}_i[x, y, z, r, (\gamma_i)_{1 \leq i \leq l-1}, t] \quad \text{for } i = 1, \dots, l-1 \quad (50)$$

where  $w_r$ ,  $\dot{r}$ , and  $\dot{\gamma}_i$  are given by Equations (19), (41), and (35), respectively. If we assume that the liquid phase can be treated as incompressible, then, along the characteristic curves, the population balance equation (33) can be written as [37]

$$\frac{Df_1}{Dt} = h + f_1 \left[ \frac{\partial w_r}{\partial z} - \frac{\partial \dot{r}}{\partial r} - \sum_{i=1}^{l-1} \frac{\partial \dot{\gamma}_i}{\partial \gamma_i} \right] \quad (51)$$

---

<sup>1</sup>The Fortran subroutine is available at

[http://www.sali.freesevers.com/engineering/fortran\\_codes/unequal\\_simps.html](http://www.sali.freesevers.com/engineering/fortran_codes/unequal_simps.html)

where  $Df_1/Dt$  denotes the substantial derivative or the total time derivative along the pathline of the bubbles. The partial derivatives of  $w_r$ ,  $\dot{r}$ , and  $\dot{\gamma}_i$  with respect to  $z$ ,  $r$ , and  $\gamma_i$ , respectively, are derived from Equations (19), (41), and (35) and expressed as

$$\frac{\partial w_r}{\partial z} = \frac{2\alpha\rho_\infty g r \dot{r}}{\mu_\infty(w_\infty - w_r)} - \frac{\alpha\rho_\infty g r^2}{\mu_\infty^2} \frac{\partial \mu_\infty}{\partial z} \quad (52)$$

$$\frac{\partial \dot{r}}{\partial r} = \frac{0.63RT \left(\frac{\alpha\rho_\infty g}{\mu_\infty}\right)^{1/3} \sum_{i=1}^l \left(2\sigma\gamma_i S_i D_i^{2/3}/r^2\right) - \frac{\rho_\infty g(w_\infty - 3w_r)}{3}}{p_0 + \rho_\infty g z + 4\sigma/3r} + \frac{4\sigma}{3r^2} \frac{\dot{r}}{p_0 + \rho_\infty g z + 4\sigma/3r} \quad (53)$$

$$\frac{\partial \dot{\gamma}_i}{\partial \gamma_i} = \frac{-\frac{3\dot{r}}{r} - \frac{1.905 S_i RT}{r} \left(\frac{\alpha\rho_\infty g}{\mu_\infty}\right)^{1/3} \left[1 - \frac{\gamma_i(p_0 + \rho_\infty g z)}{p_0 + \rho_\infty g z + 4\sigma/3r}\right] - \frac{\rho_\infty g(w_\infty - w_r) - 2\sigma\dot{r}/r^2}{p_b}}{\quad} \quad (54)$$

Equations (46) to (51) represent a system of ordinary differential equations that can be solved along the characteristic curves by the method of characteristics using inverse marching method with the same staggered grids as those used for computing the glassmelt velocity  $\vec{v}_\infty$ , temperature  $T$ , refining agent  $[M^{k+}]$ , and dissolved gas concentrations  $C_{\infty,i}$  fields enabling the coupling between all the variables. A detailed description of the numerical scheme has been presented by Pilon and Viskanta [37] and need not be repeated here.

The backward method of characteristics (or inverse marching method) is an interpretation of the Lagrangian approach that overcomes the difficulties related to mesh deformation. Based on a prespecified grid, it follows the particles backward in time as opposed to forward in the case of direct marching method. The backward method of characteristics uses a fixed grid that is also used for solving other transport equations such the momentum equation, the energy equation or the gas concentration in the continuous phase by finite-difference methods using a staggered grid as suggested by Patankar [67]. Thus, interactions between the particles or bubbles and the surrounding fluid can be easily accounted for in the numerical scheme. But unlike finite-difference methods that propagate the information along coordinate lines, the method of characteristics propagates the information along the pathlines and thus matches the physics of the flow resulting in accurate numerical results [37]. Other advantages of the method of characteristics are to overcome the numerical diffusion introduced by finite-difference methods [67] and to eliminate the need for outflow boundary conditions

particularly at the glass free surface and glassmelt/foam interface. Moreover, the modified method of characteristics can be used for both transient and steady-state calculations with great accuracy and without problems of numerical instability.

## 4 Conclusion

This paper presented the mathematical formulation of bubble transport and generation in three-dimensional laminar gravity driven flow. The mathematical model has been developed but is not limited to glass manufacturing and can be readily applied to other materials processing problems such as steel, aluminum, and polymers. After careful statement of the physical assumptions, the governing equations for (1) the refining agent concentration, (2) the gas species dissolved in the liquid phase, and (3) the bubble density function are derived. To the best of our knowledge, this study is the first one presenting a complete set of coupled governing equations for the key variables essential to assess the refining performances of a furnace. The method of solution and the convergence criteria are briefly discussed. The results will enable one to predict the quality of the glass, to simulate foaming of the glassmelt, and to determine the number and size distribution of bubbles in the glassmelt which are critical for accurately predicting heat transfer from the combustion space to the glass bath [8,63,64]. The second part of this paper presents the results of sample calculations.

## ACKNOWLEDGEMENTS

This work was supported in part by the U.S. Department of Energy/Glass Industry/Argonne National Laboratory/University collaborative research project.

## References

- [1] R. G. C. Beerkens, “The role of gases in glass melting processes”, *Glastechnische Berichte*, vol. 71, no. 12, pp. 369–380, 1995.

- [2] B. Balkanli and A. Ungan, “Numerical simulation of bubble behaviour in glass melting tanks. Part 1. under ideal conditions”, *Glass Technology*, vol. 37, no. 1, pp. 29–34, 1996.
- [3] J. M Hermans and A. C. Verbeeks, “Gas exchange between bubbles and molten glass”, *Glastechnische Berichte*, vol. 67, no. 2, pp. 49–51, 1994.
- [4] E. L. Swarts, “Bubble generation at glass/refractory interfaces: A review of fundamental mechanisms and practical considerations”, *Glastechnische Berichte*, vol. 65, no. 4, pp. 87–92, 1992.
- [5] L. Pilon and R. Viskanta, “Radiation characteristics of glass containing bubbles”, *Journal of the American Ceramic Society*, vol. 86, no. 8, pp. 1313–1320, 2003.
- [6] D. Baillis, L. Pilon, F. Randranalisoa, and R. Viskanta, “Experimental determination of radiation characteristics of fused-quartz containing bubbles”, *Journal of the Optical Society of America - A (in review)*, 2003.
- [7] D. Baillis, F. Randranalisoa, L. Pilon, and R. Viskanta, “Identification of radiative characteristics of fused quartz containing bubbles using discrete ordinates method with fresnel interfaces”, in *Computational Thermal Radiation in Participating Media - EU-ROTHERM Seminar 73, Mons, Belgium, April 2003*, pp. 215–224.
- [8] A. G. Fedorov and L. Pilon, “Glass foam: formation, transport properties, and heat, mass, and radiation transfer”, *Journal of Non-Crystalline Solids (in press)*, 2002.
- [9] M. Rubin, “Optical properties of soda-lime silicate”, *Solar Energy Materials*, vol. 12, pp. 275–288, 1985.
- [10] C.Z. Tan and J. Arndt, “Refractive index, optical dispersion, and group velocity of infrared wave in silica glass”, *Journal of Physics and Chemistry of Solids*, vol. 62, pp. 1087–1092, 2001.
- [11] A. Ungan and R. Viskanta, “Melting behavior of continuously charged loose batch blankets in glass melting furnaces”, *Glastechnische Berichte*, vol. 59, no. 10, pp. 279–291, 1986.

- [12] P. R. Laimbock, *Foaming of glass melts*, PhD thesis, Technical University of Eindhoven, Eindhoven, The Netherlands, 1998.
- [13] S. Kawachi and Y. Kawase, “Evaluation of bubble removing performance in a TV glass furnace. Part 1. mathematical formulation”, *Glastechnische Berichte*, vol. 71, no. 4, pp. 83–91, 1998.
- [14] E. Itoh, H. Yoshikawa, H. Miura, and Y. Kawase, “A quasi-stationary model for bubble behaviour in glass melts with refining reactions”, *Glass Technology*, vol. 38, no. 4, pp. 134–140, 1997.
- [15] L. Nemeč, “The behaviour of bubbles in glass melts. Part 1. bubble size controlled by diffusion”, *Glass Technology*, vol. 21, no. 3, pp. 134–138, 1980.
- [16] R. G. C Beerkens and H. De Wall, “Mechanism of oxygen diffusion in glassmelts containing variable-valence ions”, *Journal of the American Ceramic Society*, vol. 73, no. 7, pp. 1857–1861, 1990.
- [17] H. Yoshikawa and Y. Kawase, “Significance of redox reactions in glass refining processes”, *Glastechnische Berichte*, vol. 70, no. 2, pp. 31–40, 1997.
- [18] H. Yoshikawa, H. Miura, and Y. Kawase, “Dissolution of bubbles in glassmelts with equilibrium redox reactions: approximations for a moving bubble boundary”, *Journal of Materials Science*, vol. 33, no. 10, pp. 2701–2707, 1998.
- [19] J. E. Shelby, *Handbook of gas diffusion in solids and melts*, ASM International, Materials Park, OH, 1996.
- [20] M. Cable and D. Martlew, “The dissolution of silica in melts containing sodium carbonate, sodium sulphate, and silica”, *Glass Technology*, vol. 37, no. 4, pp. 137–142, 1996.
- [21] J. Shell, “Representative video and operating conditions of the Techneglas furnace C”, Personal Communication, July 1999.



- [22] M. C. Weinberg, P. I. K. Onorato, and D. R. Uhlmann, “Behavior of bubbles in glassmelts: I, dissolution of a stationary bubble containing a single gas”, *Journal of the American Ceramic Society*, vol. 63, pp. 175–180, 1980.
- [23] L. Nemeč, “Diffusion-controlled dissolving of water vapor bubbles in molten glass”, *Glass Technology*, vol. 10, pp. 176–181, 1969.
- [24] M. Cable and J.R. Frade, “Theoretical analysis of the dissolution of multi-component gas bubbles”, *Glastechnische Berichte*, vol. 60, no. 11, pp. 355–362, 1987.
- [25] M. C. Weinberg, P. I. K. Onorato, and D. R. Uhlmann, “Behavior of bubbles in glassmelts: II, dissolution of a stationary bubble containing a diffusing and a non-diffusing gas”, *Journal of the American Ceramic Society*, vol. 63, pp. 435–438, 1980.
- [26] P. I. K. Onorato, M. C. Weinberg, and D. R. Uhlmann, “Behavior of bubbles in glassmelts: III, dissolution and growth of a rising bubble containing a diffusing a single gas”, *Journal of the American Ceramic Society*, vol. 64, pp. 676–682, 1981.
- [27] E. Itoh, H. Yoshikawa, and Y. Kawase, “Modeling of bubble removal from glassmelts at fining temperatures”, *Glastechnische Berichte*, vol. 70, no. 1, pp. 8–16, 1997.
- [28] J. I. Ramos, “Behavior of multicomponent gas bubbles in glass melts”, *Journal of the American Ceramic Society*, vol. 69, no. 2, pp. 149–154, 1986.
- [29] B. Balkanli and A. Ungan, “Numerical simulation of bubble behaviour in glass melting tanks. Part 3. bubble trajectories”, *Glass Technology*, vol. 37, no. 4, pp. 137–142, 1996.
- [30] S. Kawachi and Y. Kawase, “Evaluation of bubble removing performance in a TV glass furnace. Part 2. verification using real furnace data”, *Glastechnische Berichte*, vol. 71, no. 5, pp. 111–119, 1998.
- [31] S. Kawachi and M. Kato, “Evaluation of reaction rate of refining agents”, *Glastechnische Berichte*, vol. 72, no. 6, pp. 182–187, 1999.

- [32] A. Ungan, W.H. Turner, and R. Viskanta, “Effect of gas bubbles on three-dimensional circulation in a glass melting tank”, *Glastechnische Berichte*, vol. 56K, pp. 125–129, 1983.
- [33] D. Ramkrishna, *Population Balances*, Academic Press, San Diego, CA, 2000.
- [34] O. T. Roi, G. Nölle Seidel, and D. Höhne, “Modeling of bubble population in glass melts”, *Glastechnische Berichte*, vol. 67, no. 10, pp. 263–271, 1994.
- [35] B. Balkanli and A. Ungan, “Numerical simulation of bubble behaviour in glass melting tanks. Part 4. bubble number density distribution”, *Glass Technology*, vol. 3, no. 5, pp. 164–168, 1996.
- [36] S. Kumar and D. Ramkrishna, “On the solution of population balance equation by discretization - III nucleation, growth, and aggregation of particles”, *Chemical Engineering Science*, vol. 52, no. 4, pp. 4659–4679, 1997.
- [37] L. Pilon and R. Viskanta, “Modified method of characteristics for solving the population balance equation”, *International Journal for Numerical Methods in Fluids*, vol. 42, pp. 1211–1236, 2003.
- [38] P.M. Carrica, F.J. Bonetto, D.A. Drew, and R.T. Lahey Jr., “The interaction of background ocean air bubbles with a surface ship”, *International Journal for Numerical Methods in Fluids*, vol. 28, pp. 571–600, 1998.
- [39] M. B. King, *Phase equilibrium in mixtures*, Pergamon Press, Oxford, 1969.
- [40] R.T. Lahey and D.A. Drew, “On the development of multidimensional two-fluid models for vapor/liquid two-phase flows”, *Chemical Engineering Communications*, vol. 118, pp. 125–139, 1992.
- [41] R. Pyare, S. P. Singh, A. Singh, and P. Nath, “The  $\text{As}^{3+}$ - $\text{As}^{5+}$  equilibrium in borate and silicate glasses”, *Physics and Chemistry of Glasses*, vol. 23, no. 5, pp. 158–168, 1982.

- [42] B. Balkanli and A. Ungan, “Numerical simulation of bubble behaviour in glass melting tanks. Part 2. gas concentration”, *Glass Technology*, vol. 37, no. 3, pp. 101–105, 1996.
- [43] J.-M. Rousseaux, C. Vial, H. Muhr, and E. Plasari, “CFD simulation of precipitation in the sliding-surface mixing device”, *Chemical Engineering Science*, vol. 56, pp. 1677–1685, 2001.
- [44] V. G. Levich, *Physicochemical hydrodynamics (translate from Russian)*, Englewood Cliffs, Prentice-Hall, NJ, 1962.
- [45] E.M. Hornyak and M.C. Weinberg, “Velocity of a freely rising gas bubble in a soda-lime silicate glass melt”, *Communications of the American Ceramic Society*, vol. 67, no. 11, pp. C244–246, 1984.
- [46] J. J. M. Magnaudet, “The forces acting on bubbles and rigid particles”, in *ASME Fluids Engineering Division Summer Meeting, FEDSM’97, Part 16, Vancouver, Canada*, June 22-26 1997, vol. 16, pp. 1–7.
- [47] R. B. Bird, W.E. Stewart, and E. N. Lightfoot, *Transport Phenomena*, John Wiley & Sons, New York, 1960.
- [48] I. M. Klotz and R. M. Rosenberg, *Chemical thermodynamics*, Krieger Publishing Company, Malabar, FL, 1991.
- [49] L. Pilon, A. G. Fedorov, and R. Viskanta, “Steady-state foam thickness of liquid-gas foams”, *Journal of Colloid and Interface Science*, vol. 242, pp. 425–436, 2001.
- [50] L. Pilon, A. G. Fedorov, and R. Viskanta, “Gas diffusion in closed-cell foams”, *Journal of Cellular Plastics*, vol. 36, pp. 451–474, 2000.
- [51] A. Ungan and R. Viskanta, “Three-dimensional numerical modeling of circulation and heat transfer in a glass melting tank. Part. 1 mathematical formulation”, *Glastechnische Berichte*, vol. 60, no. 3, pp. 71–78, 1987.

- [52] A. Urgan and R. Viskanta, “Three-dimensional numerical modeling of circulation and heat transfer in a glass melting tank. Part. 2 sample simulations”, *Glastechnische Berichte*, vol. 60, no. 4, pp. 115–124, 1987.
- [53] R. Viskanta, “Review of three-dimensional mathematical modeling of glass melting”, *Journal of Non-Crystalline Solids*, vol. 177, pp. 347–362, 1994.
- [54] L. Pilon, G. Zhao, and R. Viskanta, “Three-dimensional flow and thermal structures in glass melting furnaces. Part I. Effects of the heat flux distribution”, *Glass Science and Technology*, vol. 75, no. 2, pp. 55–68, 2002.
- [55] L. Pilon, G. Zhao, and R. Viskanta, “Three-dimensional flow and thermal structures in glass melting furnaces. Part II. Effects of the presence of batch and bubbles”, *Glass Science and Technology*, vol. 75, no. 3, pp. 115–124, 2002.
- [56] D. Ramkrishna, “The status of population balances”, *Review in Chemical Engineering*, vol. 3, no. 1, pp. 49–95, 1985.
- [57] L. Nemeč, “Refining in the glassmelting process”, *Journal of the American Ceramic Society*, vol. 60, no. 9-10, pp. 436–440, 1977.
- [58] M. Cable and C. G. Rasul, “Spontaneous bubble formation in silicate melts at high temperatures: II, effect of we atmospheres and behavior of mixed alkali glasses”, *Journal of the American Ceramic Society*, vol. 50, no. 10, pp. 528–531, 1967.
- [59] O. T. Roi, G. Nölle Seidel, and D. Höhne, “Formation and behavior of bubble curtains in glass melts”, *Glastechnische Berichte*, vol. 68, no. 7, pp. 222–227, 1995.
- [60] A. Urgan, R. U. Payli, and B. Balkanli, “Numerical model of polydispersed silica grain dissolution in glass melting furnaces”, *Journal of the American Ceramic Society*, vol. 77, no. 7, pp. 1921–1927, 1994.
- [61] R. D. Kirkpatrick and M. J. Lockett, “The influence of approach velocity on bubble coalescence”, *Chemical Engineering Science*, vol. 29, pp. 2363–2373, 1974.

- [62] L. Pilon, A. G. Fedorov, and R. Viskanta, “Analysis of transient thickness of pneumatic foams”, *Chemical Engineering Science*, vol. 57, pp. 977–990, 2002.
- [63] A. G. Fedorov and R. Viskanta, “Radiative transfer in a semitransparent glass foam blanket”, *Physics and Chemistry of Glasses*, vol. 41, no. 3, pp. 127–135, 2000.
- [64] A. G. Fedorov and R. Viskanta, “Radiative characteristics of glass foams”, *Journal of the American Ceramic Society*, vol. 83, no. 11, pp. 2769–2776, 2000.
- [65] M. Varady and A.G. Fedorov, “Combined conduction and radiation in glass foams”, *ASME Journal of Heat Transfer*, (*submitted for publication*), 2002.
- [66] M. Varady and A. G. Fedorov, “Combined conduction and radiation in glass foams”, in *International Mechanical Engineering Congress & Exposition IMECE’01*, New York City, N.Y. ASME, November 2001.
- [67] S. Patankar, *Numerical heat transfer and fluid flow*, Hemisphere, Washington, DC, 1980.

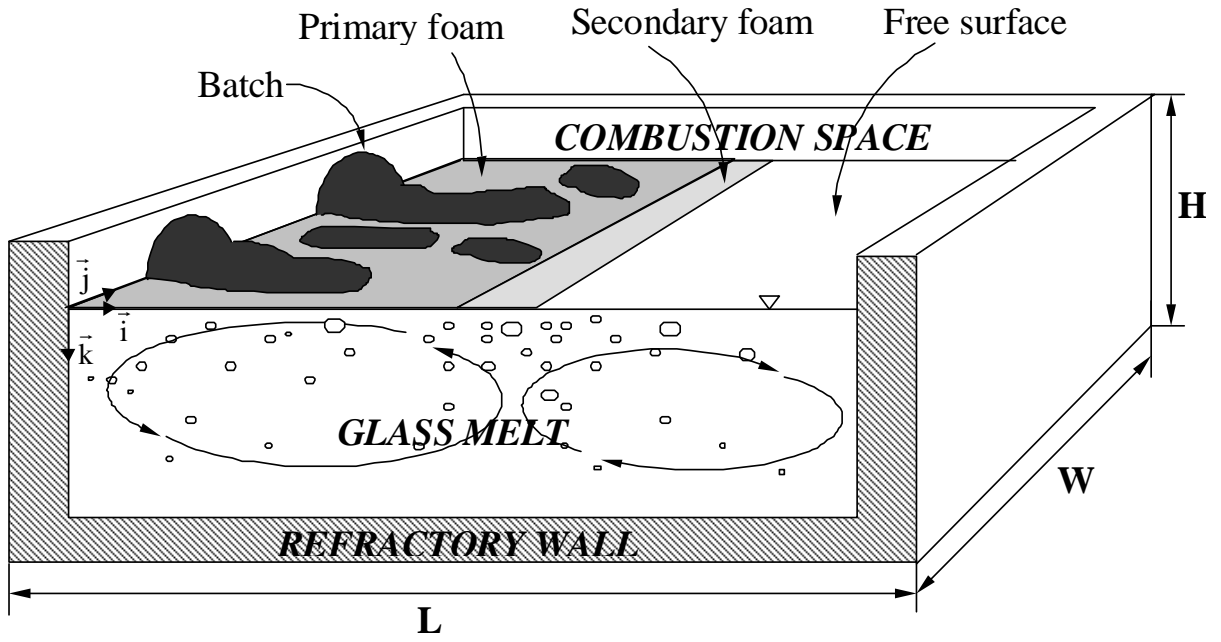


Figure 1: Schematic of a glass melting furnace and the coordinate system.

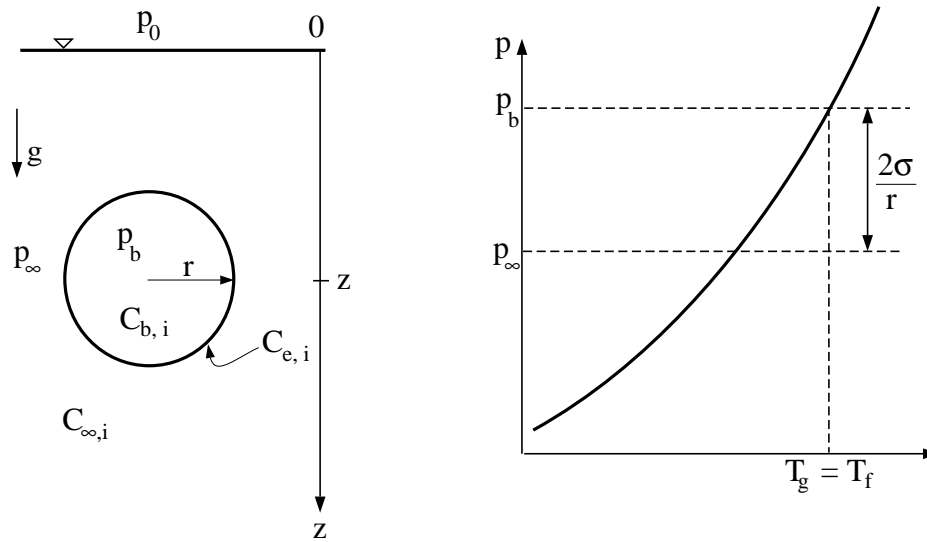


Figure 2: Schematic of a single bubble in thermal equilibrium with the glassmelt and the corresponding p-T diagram.

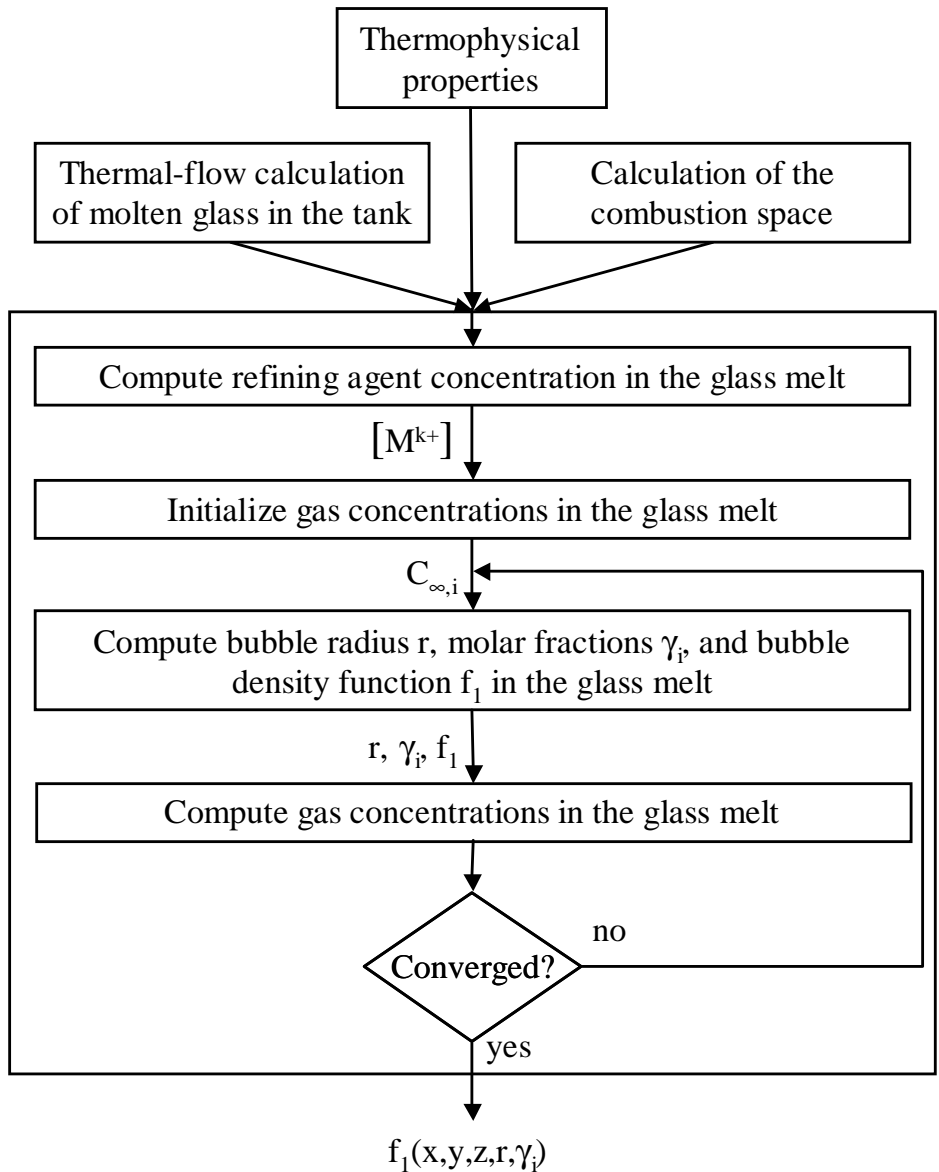


Figure 3: Schematic flow diagram of the computational procedure.